




INSPECTION STANDARD (HT LAB)

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)	13/08/19
Part Name:- GEAR 67	Part No.:- KTE11248232 (A)	Inspection Standard Number	SIP/2105/170	
Customer :- ESCORTS (KUBOTA)	Change Level.:-A,14-01-2020	Part Stage	HT Lab.	


Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	57~61 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	Effective case depth at 550 HV 300gf. & 10sec	*	0.70~1.0 mm	Micro Vickers Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Surface Carbon concentration	*	0.77~0.95 %	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
4.	Internal Oxidation Layer Depth at Tooth Bottom	*	Layer Depth Shall be 25 Microns (um) or less	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
5.	Core Hardness		---	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
6.	Case Micro at PCD	*	Tempered Martensite + Retained austenite 30% max.	Microscope (400x or more Magnification) see std KS-013-0003	1Pc/Lot	HT Lab Report	A
7.	Austenite Grain Size	*	the grain size number shall be 6 or more	Microscope (Three or more visual field shall be check) see std KS-013-0035	1Pc/Lot	HT Lab Report	A
8.	Microstructure	*	Fine pearlite shall have no precipitation within $\frac{1}{2}$ of the lower limit of effective hardend layer depth	Microscope (Three or more visual field shall be check) see std KS-013-0035	1Pc/Lot	HT Lab Report	A
9.	Core Micro	*	LCTM + Baintic	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
10.	Precipitation of Fe ₃ C (cementite) on surface at Tooth top & PCD	*	Granular form is allowable Note that the grain size shall be 5 micron or less	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A

OPEN. SKETCH:-

Material:- SCM420H

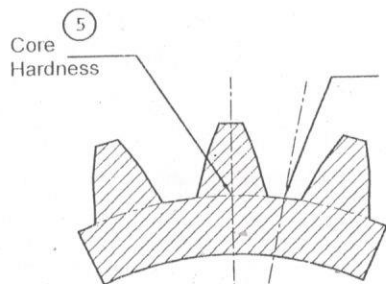


View From A

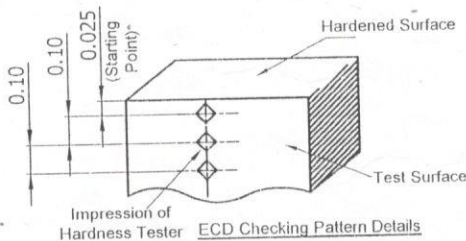


ECD Checking Pattern Details

ECD दांत के नीचे से चेहरे की चौड़ाई के एक तिहाई भाग पर मापनी है

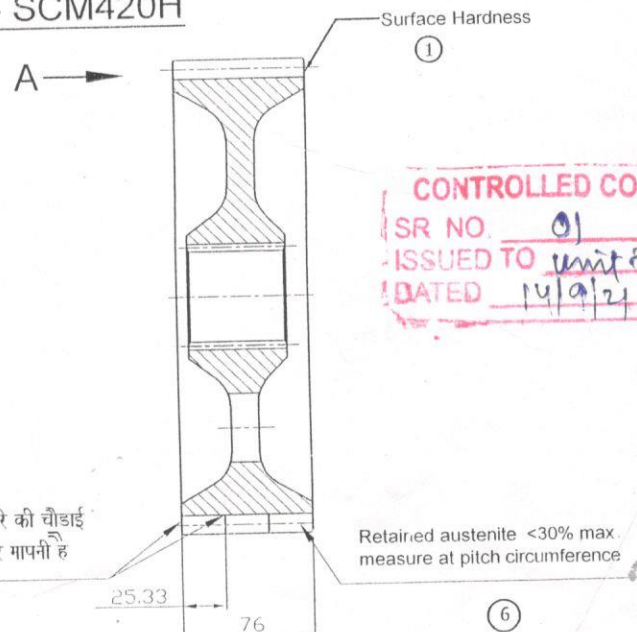Note:-
1st Measurement point at 0.025mm from the Surface, and after each indent 0.10mm interval.

Retained austenite <30% max. measure at pitch circumference

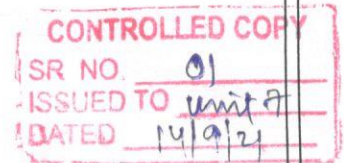

Reaction Plan: A-यदि Inspection करते समय कम्पोनेट खराब मिले तो खराब कम्पोनेट को Rejection का टैग लगाकर Rejection टेबल पर रखे और उसके बारे में Department के Incharge को बतायें।

Legends:	► Special Characteristics as Per Drawing	* Special Characteristics For Process	▲ Special Characteristics For Safety
----------	--	---------------------------------------	--------------------------------------

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change
14-01-2020	A	New Customer Drawing Received Part No KTE11248232 Rev 02 was KTE11248231 as per ECH 1429 On dated 14-01-2020	New Customer Drawing Received				