



INSPECTION STANDARD (HT LAB)


Page 01 of 01

☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)	28/01/19
Part Name:- INTERMEDIATE SHAFT		Part No.:- 1516723	Inspection Standard Number	SIP/4285/230
Customer :- TMTL		Change Level.:-00	Part Stage	HT Lab.

Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	59~63 HRC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
2.	Surface Hardness At Ø20g5	*	58 HRC (Min.)	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
3.	Surface Hardness At Ø33H6	*	58 HRC (Min.)	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
4.	ECD Measured To 550HV	*	0.60~0.90 mm	Micro Vicker/Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A
5.	Core Hardness at PCD	*	42 HRC (Max.)	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
6.	Core Hardness at RCD	*	30 HRC (Min.)	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
7.	Micro Case	*	Tempered Martensite + RA<12%, Carbide (Globular) Upto 2% Max.	Microscope	1Pc/Lot	FMT-HT-39	A
8.	Core Micro	*	LCM+Bainitic Structure, Ferrite Upto 5% Max.	Microscope	1Pc/Lot	FMT-HT-39	A
9.	IGO / NMTP	*	20 Micron Max.	Microscope	1Pc/Lot	FMT-HT-39	A

Space For Sketch:-

Material- 20MnCr5

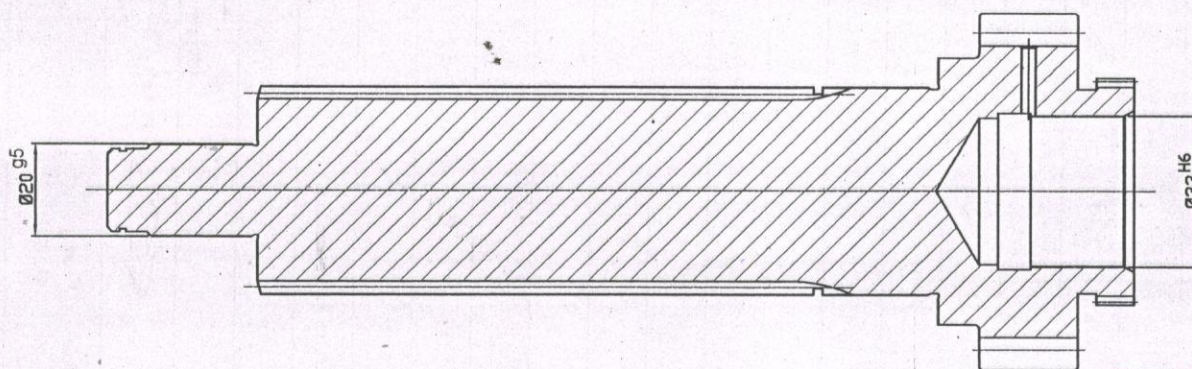

CONTROLLED COPY
SR NO. 01
ISSUED TO Ut-7
DATED 2/3/22

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing ☒ * Special Characteristics For Process ☒ Δ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change

Prepared By: *Maresh*

Checked By:

Approved By: