




INSPECTION STANDARD (HT LAB)


Page 01 of 01

☐ Prototype		☒ Pre-Launch	☐ Production	Date (Original)		30/11/2021		
Part Name:- Gear 95T			Part No.:- 006524397J01		Inspection Standard Number		SIP/2126	
Customer :- M&M			Change Level.:- 00		Part Stage		HT SIP	
Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan	
			Product Specification	Inspection Method	Inspection Frequency	Control Method		
1.	Surface Hardness at 0.1mm below the surface 500g.	*	58~63 HRC	Rockwell Hardness Tester/ Micro Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A	
2.	ECD At 513 HV1 PCD	*	0.6~1.0 mm	Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A	
3.	ECD At 513 HV1 RCD	*	0.6~1.0 mm	Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A	
4.	Core Hardness At PCD	*	36~46 HRC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A	
5.	Core Hardness At RCD (Intersection of RCD & tooth Center line)	*	34~42 HRC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A	
6.	Micro Case (100x, 500x)	*	Tempered Martensite (Min. 90%) +RA<20%	Microscope As per standard.	1Pc/Lot	FMT-HT-39	A	
7.	Micro Core (100x, 500x)	*	Tempered Martensite + Bainite. Free Ferrite,if present shall be max. 5%	Microscope As per standard.	1Pc/Lot	FMT-HT-39	A	
8.	Grain Boundary Oxidation	*	To be checked at tooth root & should not exceed 0.015mm.	Microscope As per standard.	1Pc/Lot	FMT-HT-39	A	
9.	NMTP	*	To be checked at tooth root & should not exceed 0.015mm.	Microscope As per standard.	1Pc/Lot	FMT-HT-39	A	

OPEN SKTCH

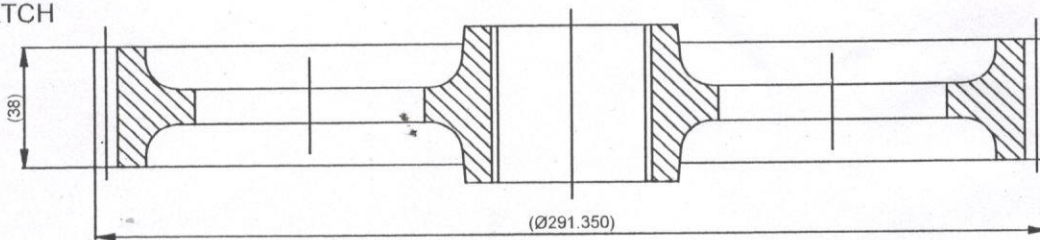

CONTROLLED COPY
SR. NO. 01
ISSUED TO unit 7
DATED 31/3/22

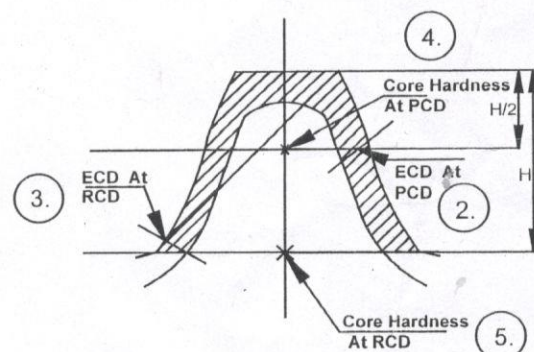

Material:-20MnCr5

Note:- Ref. M&M STD FE G 00 0587

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में

Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing ☒ Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change