




INSPECTION STANDARD (HT LAB)

Page 01 of 01


☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)	07/12/17
Part Name:- Bull Gear		Part No.:- 006502494C2 RH	Inspection Standard Number	SIP/2098/140
Customer :- M&M		Change Level.:- A	Part Stage	Hard

Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	57~63 HRC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
2.	ECD At 513 Hv	*	1.20~1.60 mm	Vicker Hardness Tester	1Pc/Lot	FMT-HT-39	A
3.	Core Hardness At RCD	*	26~36 RC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
4.	Core Hardness At PCD	*	32~40 RC	Rockwell Hardness Tester	1Pc/Lot	FMT-HT-39	A
5.	Micro Case At (X200)	*	Tempered Martensite (Min. 90%) +RA<20%	Microscope	1Pc/Lot	FMT-HT-39	A
6.	Core Micro	*	Tempered Martensite + Bainite. Free Ferrite, If Present Shell Be Max. 5%	Microscope	1Pc/Lot	FMT-HT-39	A
7.	Cut Sample Preserve period 3 Years (A)						

OPEN SKTCH

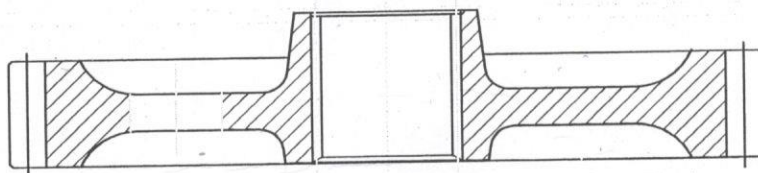

Material:-20MnCr5
Note:- Ref. M&M STD T04112

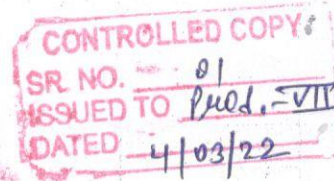

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing ☒ Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change
17-4-18	A	Cut Sample Preserve period 3 Years	Customer Requirement				