





INSPECTION STANDARD (HT LAB)

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)	04-09-2019			
Part Name:- Connecting Shaft		Part No.: N° 3796376H06		Inspection Standard Number		SIP/4323/180	
Customer :- TAFE		Change Level:-00		Part Stage		HT Lab.	
Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	58~61 HRC	Rockwell Hardness Tester	1Pc/Lot	Lab Report	A
2.	ECD Measured at Spline L1 Root HV513 @ 1.0Kg	*	0.7~1.0 mm	Micro Vicker, Vicker Hardness Tester	1Pc/Lot	Lab Report	A
2.	ECD Measured at Spline L2 Root HV513 @ 1.0Kg	*	0.7~1.0 mm	Micro Vicker, Vicker Hardness Tester	1Pc/Lot	Lab Report	A
3.	Core Hardness (Half Radius)	*	37~47 HRC	Rockwell Hardness Tester	1Pc/Lot	Lab Report	A
4.	Internal Oxidation	*	15µm Max.	Microscope	1Pc/Lot	Lab Report	A
5.	NNTP	*	15µm Max.	Microscope	1Pc/Lot	Lab Report	A
6.	Micro Case (400X)	*	Tempered Martensitic+ Retained austenite acceptable 10~30% Presence of Bainite is proscribed on First 0.40mm of the Carburized Layer. Presence of Bainite authorised between 0.40mm and 0.50 mm of the carburized layer:10% maxi. The presence of networks of Carbides (Cementite) is totally prohibited.	Microscope	1Pc/Lot	Lab Report	A
7.	Core Micro (400X)	*	LCTM + Bainitic Structure	Microscope	1Pc/Lot	Lab Report	A
8.	Surface Carbon	*	0.80 ~ 0.95%	Microscope	1Pc/Lot	Lab Report	A

Space For Sketch:-

Material-17CrNiMo6

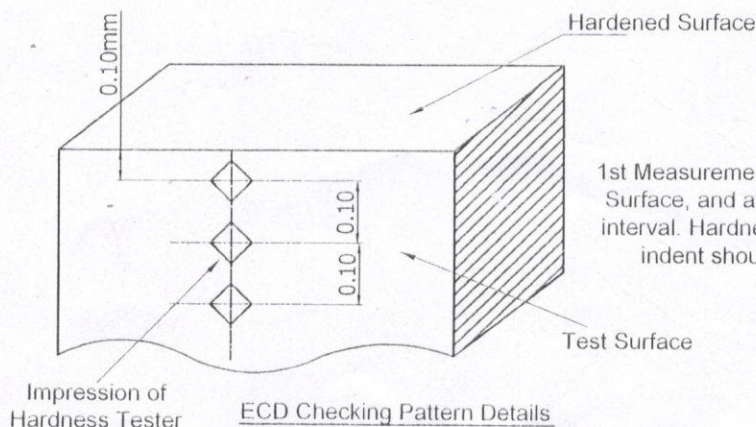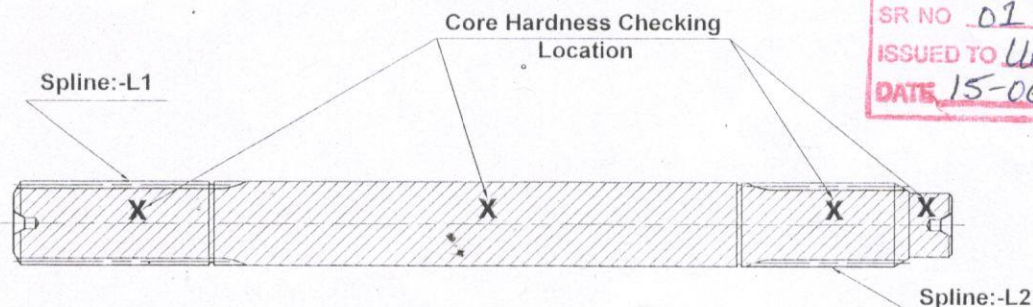

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें।

Legends: ☒ Special Characteristics as Per Drawing * Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change