







INSPECTION STANDARD (HT LAB)

Page 01 of 01

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)	28/11/2020			
Part Name:- SHAFT,BEVEL GEAR		Part No.:- KTE88012721		Inspection Standard Number		SIP/4397/150	
Customer :- ESCORTS (KUBOTA)		Change Level.:- 00		Part Stage		HT Lab.	
Sr.No	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness check at Dia D1	*	57~61 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	Effective case depth at Root of spline Z-24 1st side at 550 HV 300gf. & 10sec	*	0.5~0.8 mm	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Effective case depth at Root of spline Z-24 2nd side at 550 HV 300gf. & 10sec	*	0.5~0.8 mm	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
4.	Surface Carbon concentration Tooth Bottom (C Location)	*	0.77~0.95 %	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
5.	Internal Oxidation Layer Depth at Tooth Bottom (C Location)	*	Layer Depth Shall be 25 Microns (um) or less	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
6.	Core Hardness check at A1,A2,(d/4)		-----	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
7.	Case Micro at PCD	*	Tempered Martensite + Retained austenite 30% max.	Microscope (400x or more Magnification) see std KS-013-0003	1Pc/Lot	HT Lab Report	A
8.	Austenite Grain Size (C Location)	*	The grain size number shall be 6 or more	Microscope (Three or more visual field shall be check) see std KS-013-0035	1Pc/Lot	HT Lab Report	A
9.	Microstructure	*	Fine pearlite shall have no precipitation within 1/2 of the lower limit of effective hardend layer depth	Microscope (Three or more visual field shall be check) see std KS-013-0035	1Pc/Lot	HT Lab Report	A
10.	Core Micro check at core hardness location	*	LCTM + Baintic	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A
11.	Precipitation of Fe ₃ C (cementite) on surface at Tooth top & PCD	*	Granular form is allowable Note that the grain size shall be 5 micron or less	Microscope (400x or more Magnification)	1Pc/Lot	HT Lab Report	A

Material:- SCM420H

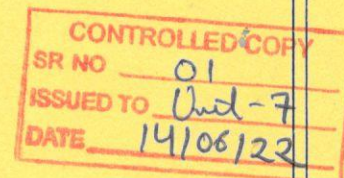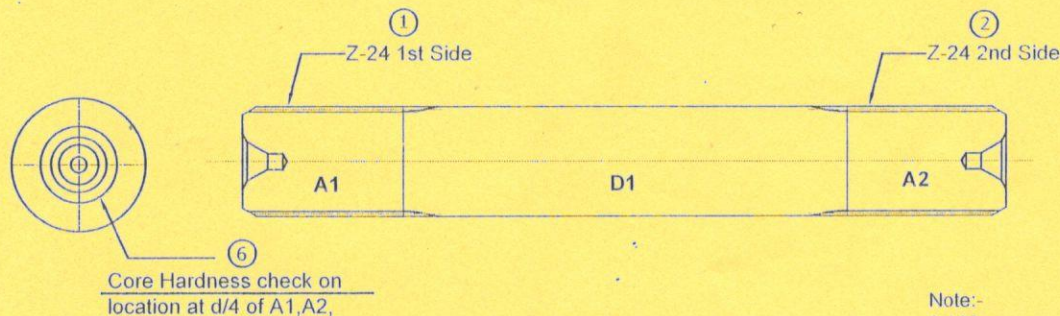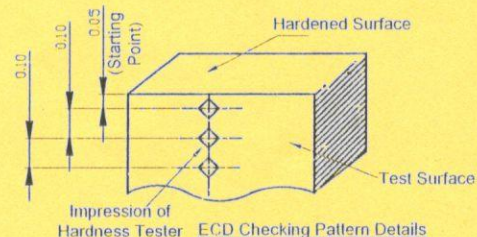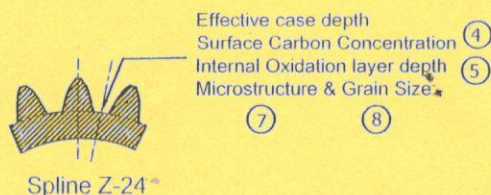

Note:-
1st Measurement point at 0.025mm from the Surface, and after each indent 0.10mm interval.

Reaction Plan: A-यदि Inspection करते समय कम्पानेंट खराब मिले तो खराब कम्पानेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें।

Legends: ☒ Special Characteristics as Per Drawing * Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change