





INSPECTION STANDARD (HT LAB)

Page 01 of 01

☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)	20/03/2024
Part Name:- Gear, Driven		Part No.:- 84069418	Inspection Standard Number	SIP/14012/320
Customer :- CNH		Change Level :- 00	Part Stage	HT Lab.


Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness at teeth	►	58 - 62 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	Effective Case Depth at teeth Sec-AA & Sec-GG (PCD) at 550HV at 1.0 kg load	►	1.40-1.70mm (Before Gear Grinding)	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Effective Case Depth at teeth Sec-AA & Sec-GG (PCD) at 550HV at 1.0 kg load	►	1.0-1.50mm (After Gear Grinding)	Micro Vicker Hardness Tester	1Pc/6th Lot	HT Lab Report	A
4.	Effective Case Depth at teeth Sec-BB & Sec-FF (RCD) at cut off 550HV at 1.0 kg load	►	0.6 mm Min.	Micro Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
5.	Core Hardness at tooth base (X)	►	(X)- 270 - 365 HV-1	Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
5a.	Core Hardness at mid tooth height (Y)	►	(Y)- 30 - 45 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
6.	Case Micro	*	Tempered Martensite + RA 20% Max. (No Carbide Networks, Continuous or discontinuous are permissible)	Microscope (500X)	1Pc/Lot	HT Lab Report	A
7.	Core Micro	*	Low Carbon Martensite Bainite & Accicular Ferrite, No Blocky Ferrite	Microscope (500X)	1Pc/Lot	HT Lab Report	A
8.	IGO At PCD	*	No IGO permitted	Microscope	1Pc/Lot	HT Lab Report	A
9.	NMTP At PCD	*	No NMTP permitted	Microscope	1Pc/Lot	HT Lab Report	A

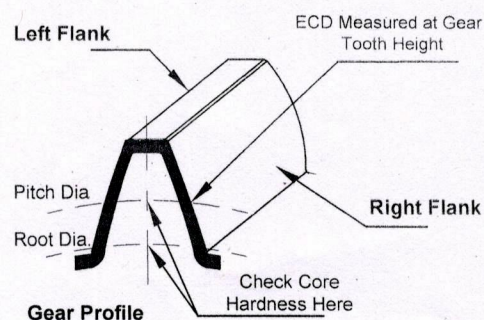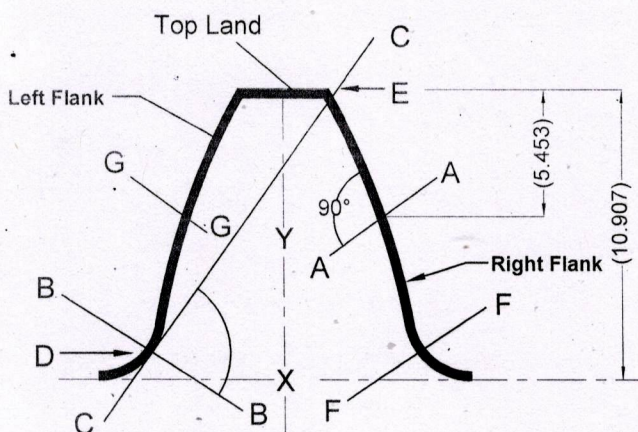

View - A
(from Step face)

"Y" CORE HARDNESS LOCATION AT TOOTH MID HEIGHT OF TEETH

"X" CORE HARDNESS LOCATION AT RCD IN TEETH

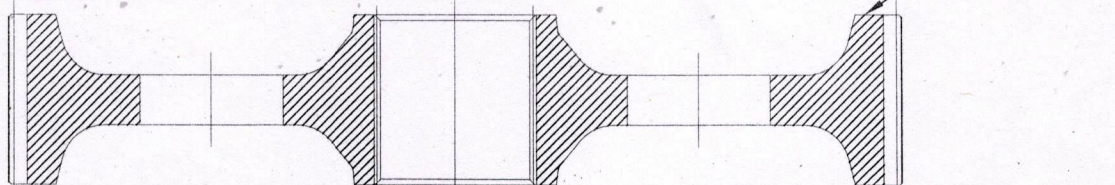

Material:- CNH MAT1052 Refer HT Standard:- MAT 4030

Reaction Plan: A-यदि Inspektion करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ► Special Characteristics as Per Drawing * Special Characteristics For Process ⚠ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change
16-04-2025	A	Modification:- Parameter S.No (2) ECD changed, 1.40-1.70 was 1.35-1.70.	