

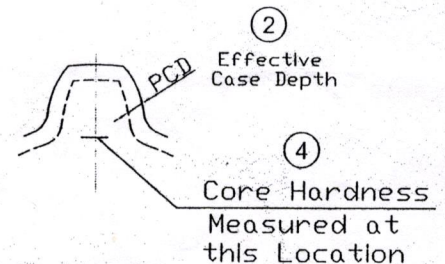
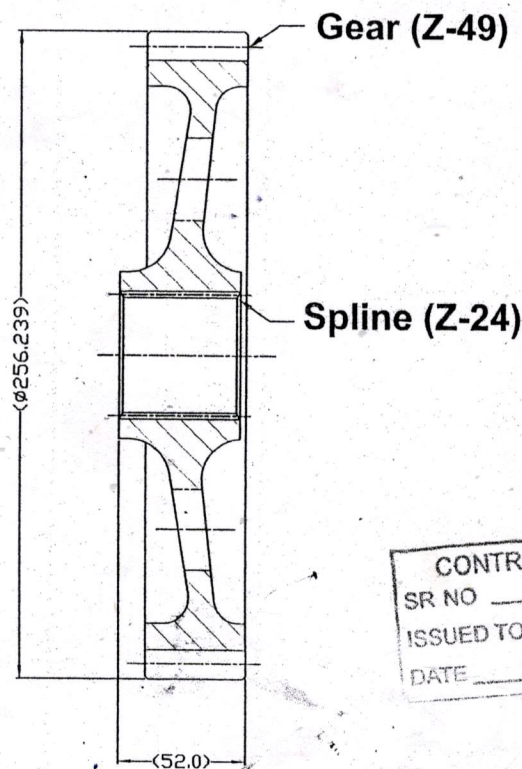
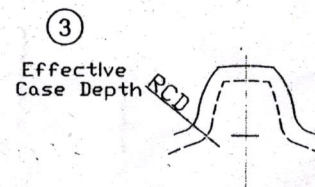
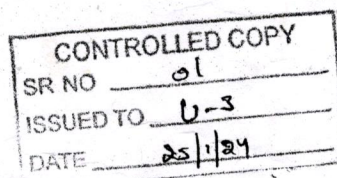


METALLURGICAL INSPECTION STANDARD (HT LAB)

Page 01 of 01

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)	14.09.2018
Part Name:- Gear Driven Final Drive Reduction (Z-49)		Part No.:- D10571680	Inspection Standard Number	SIP/2100/160
Customer :- ESCORTS		Change Level:- A	Part Stage	HT Lab

Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	►	58~62 HRC	Rockwell Hardness Tester	5% of Each Charge & Cut Piece	HT Lab Repot	A
2.	ECD (upto 513HV) at Gear PCD (Z-49)	►	0.9~1.2mm	Vicker Hardness Tester	1Pc/Lot	HT Lab Repot	A
3.	ECD At Spline RCD (Z-24)		0.6 min	Vicker Hardness Tester	1Pc/Lot	HT Lab Repot	A
4.	Core Hardness	►	32~41 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Repot	A
5.	Micro Case	►	Tempered Martensite +RA<20%	Microscope	1Pc/Lot	HT Lab Repot	A
6.	Core Micro	►	LCTM+Bainite	Microscope	1Pc/Lot	HT Lab Repot	A

Space For Sketch:-**Material -20Mn5Cr5-S****Gear (Z-49)****Spline (Z-24)**

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ► Special Characteristics as Per Drawing * Special Characteristics For Process ⚠ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change