



INSPECTION STANDARD (HT LAB)




Page 01 of 01

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)		26/04/24	
Part Name:- Bull Gear Z-65		Part No.:- P50011141B		Inspection Standard Number		SIP/26010/230
Customer :- SWARAJ (M&M)		Change Level.:-		Part Stage		HT SIP


Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	58~63 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	ECD Measured at 513 HV1 at PCD Of Gear	*	1.0~1.3 mm	Micro Vicker / Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Core Hardness at PCD	*	42 HRC Max.	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
4.	Core Hardness at RCD	*	32 HRC Min.	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
5.	Micro Case	*	Tempered Martensite + 15% Max. Retained Austenite without any carbide network	Microscope at 500x	1Pc/Lot	HT Lab Report	A
6.	Core Micro	*	LCM+Bainite+Not more than 5% Free Ferrite	Microscope at 500x	1Pc/Lot	HT Lab Report	A

COMPONENT SKTCH:-

Material:- 20MnCr5

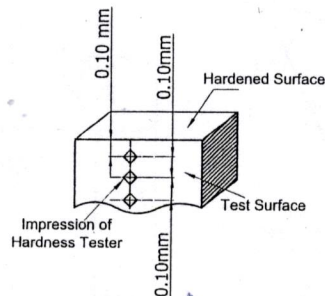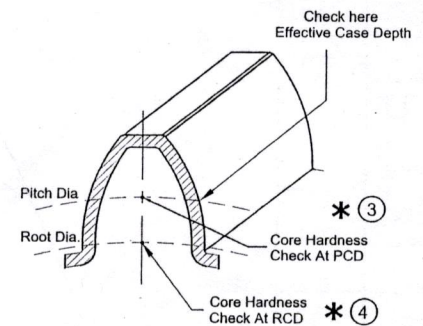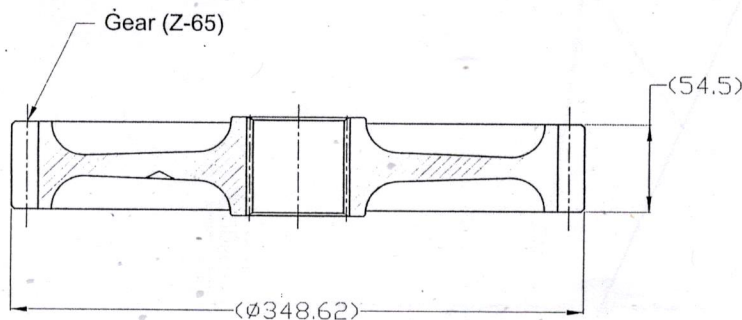

Transverse For Hardness Check
(Take Every Impression At a Distance Of 0.1mm)

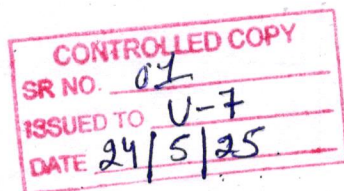

Reaction Plan: A-यदि Inspektion करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing * Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change