



INSPECTION STANDARD (HT LAB)






Page 01 of 02

☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)	29/05/2025
Part Name:- Shaft Output PTO	Part No.:- 4410C01901	Inspection Standard Number	SIP/28038/220	
Customer :- TAFE	Change Level.:-00	Part Stage	HT Lab.	

Sr.No	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	*	58 ~ 63 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	Effective Case Depth Measure To 550 HV0.3 At PCD (Z-22)	*	0.80 ~ 1.20 mm	Micro-Vicker Hardness Tester/ Vicker Hardness tester	1Pc/Lot	HT Lab Report	A
3.	Effective Case Depth Measure To 550 HV0.3 At RCD Below Root (Z-22)	*	0.56 ~ 1.20 mm	Micro-Vicker Hardness Tester/ Vicker Hardness tester	1Pc/Lot	HT Lab Report	A
4.	Effective Case Depth Measure To 550 HV0.3 at Spline RCD Below Root Z-6	*	0.56 ~ 1.20 mm	Micro-Vicker Hardness Tester/ Vicker Hardness tester	1Pc/Lot	HT Lab Report	A

Space For Sketch:

Material- 20MnCr5

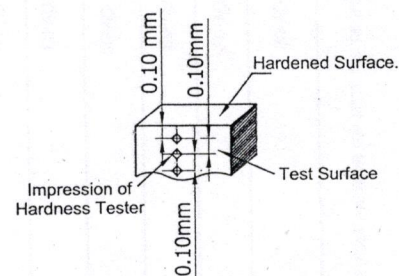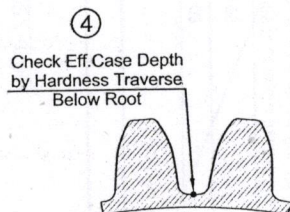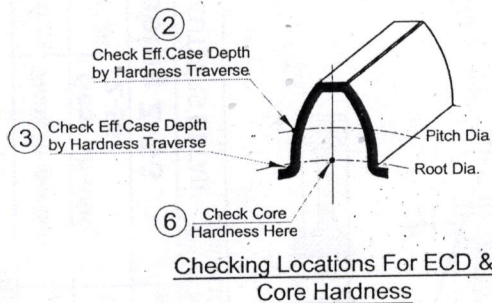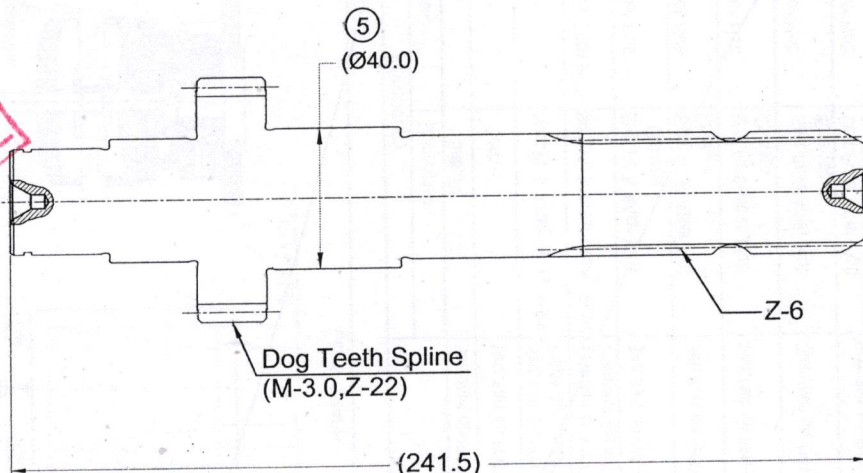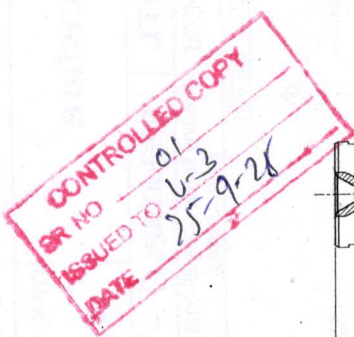

Transverse For Hardness Check
(Take Every Impression At a Distance Of 0.1mm)

Note:- Spline To Be Cut Center Of The Spline Width For Inspection.

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ☒ Special Characteristics as Per Drawing * Special Characteristics For Process ☒ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change