




# INSPECTION STANDARD (HT LAB)

Page 01 of 01


| <input type="checkbox"/> Prototype | <input checked="" type="checkbox"/> Pre-Launch    | <input type="checkbox"/> Production | Date (Original)                          | <b>17/03/2025</b>            |                      |                |               |
|------------------------------------|---------------------------------------------------|-------------------------------------|------------------------------------------|------------------------------|----------------------|----------------|---------------|
| Part Name:- <b>GEAR</b>            |                                                   | Part No.:- <b>C050502</b>           |                                          | Inspection Standard Number   |                      | SIP/40006/270  |               |
| Customer :- <b>AGCO</b>            |                                                   | Change Level.:- 00                  |                                          | Part Stage                   |                      | HT Lab.        |               |
| Sr.No.                             | Parameter                                         | Special Char. Class                 | Product Specification                    | Methods                      | Inspection Frequency | Control Method | Reaction Plan |
|                                    |                                                   |                                     |                                          | Inspection Method            |                      |                |               |
| 1.                                 | Surface Hardness                                  | ▶                                   | 58-63 HRC<br>(After Gear Grinding)       | Rockwell Hardness Tester     | 1Pc/Lot              | HT Lab Report  | A             |
| 2.                                 | Effective Case Depth 550 HV1                      | ▶                                   | 1.45 - 1.70 mm<br>(Before Gear Grinding) | Micro Vicker Hardness Tester | 1Pc/Lot              | HT Lab Report  | A             |
| 3.                                 | Effective Case Depth 550 HV1                      | ▶                                   | 1.20 - 1.50 mm<br>(After Gear Grinding)  | Micro Vicker Hardness Tester | 1Pc/Lot              | HT Lab Report  | A             |
| 4.                                 | Core Hardness at middle of tooth at root diameter | ▶                                   | 30 - 45 HRC                              | Rockwell Hardness Tester     | 1Pc/Lot              | HT Lab Report  | A             |
| 5.                                 | Case Micro Structure                              | *                                   | Tempered Martensite+RA ≤ 20% max         | Microscope (100X-500X)       | 1Pc/Lot              | HT Lab Report  | A             |
| 6.                                 | Core Micro Structure                              | *                                   | Low Carbon Martensite+Bainite            | Microscope (100X-500X)       | 1Pc/Lot              | HT Lab Report  | A             |
| 7.                                 | IGO                                               | *                                   | 0.035 Max.                               | Microscope (100X-500X)       | 1Pc/Lot              | HT Lab Report  | A             |

## Sketch:-


Z-82

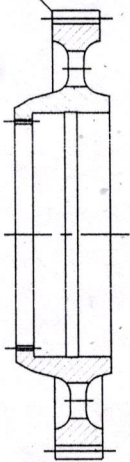

No case on threads  
(Thread should be soft  
M12×3Holes)

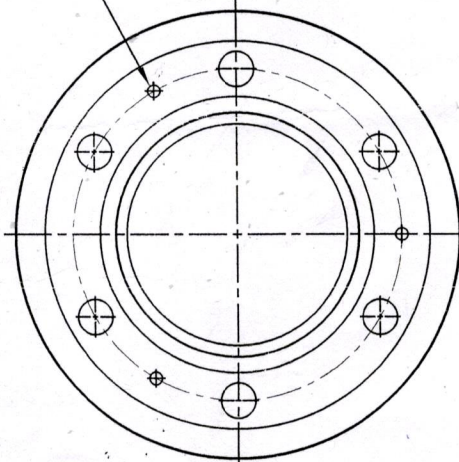

Check ECD by  
Hardness Traverse

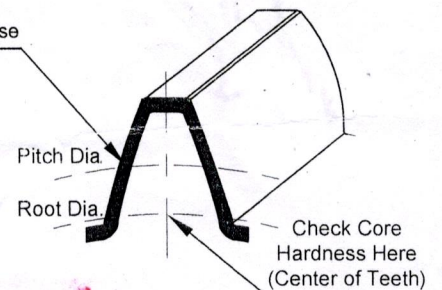

**Gear Profile**

**Material:- 20MnCr5**

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ▶ Special Characteristics as Per Drawing \* Special Characteristics For Process ▲ Special Characteristics For Safety

### Change Details

| Date | Rev. No. | Change | Reason for Change |
|------|----------|--------|-------------------|
|------|----------|--------|-------------------|

|  |  |  |  |
|--|--|--|--|
|  |  |  |  |
|  |  |  |  |
|  |  |  |  |