



INSPECTION STANDARD (HT LAB)






Page 01 of 01

☐ Prototype	☒ Pre-Launch	☐ Production	Date (Original)	11/06/2021
Part Name:- Shaft Speed Driven		Part No.:- P80001118A	Inspection Standard Number	SIP/4425/190
Customer :- M & M SWARAJ		Change Level.:-00	Part Stage	HT Lab.

Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	►	58~63 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	ECD Measured To 513HV1 check at root.	►	0.5~0.8 mm	Micro Vicker Hardness Tester/ Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Core Hardness check at below root (5.0 mm).	►	34~42 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
4.	Micro Case	►	Tempered Martensitec +RA 15% max.	Microscope	1Pc/Lot	HT Lab Report	A
5.	Core Micro	►	Bainite+Sorbide Free Ferrite<=5%	Microscope	1Pc/Lot	HT Lab Report	A

OPEN SKETCH

Material- 20MnCr5

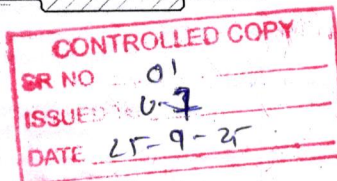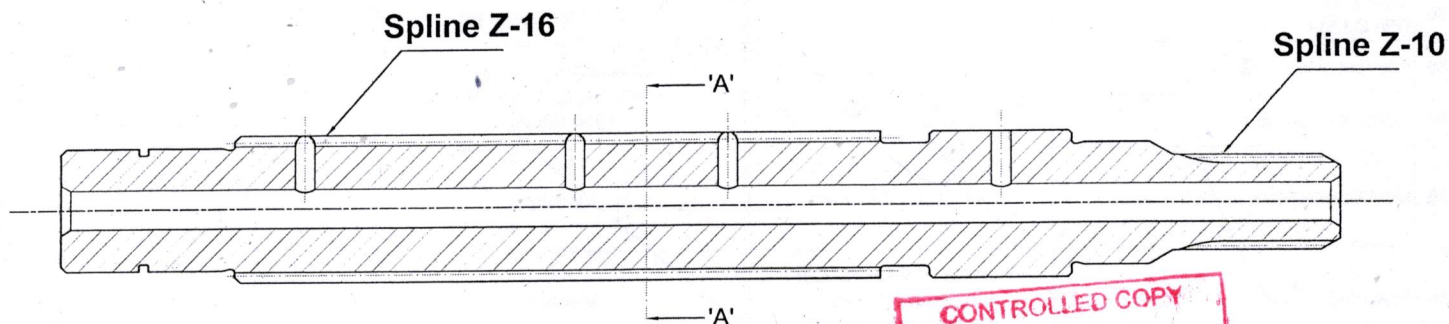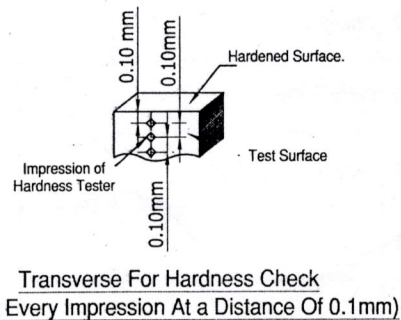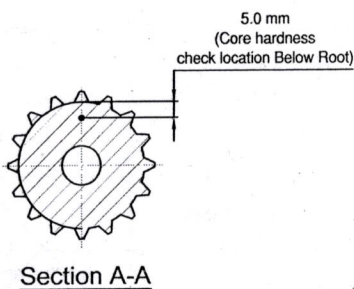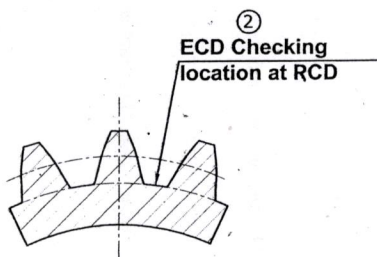

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends:		▶ Special Characteristics as Per Drawing		* Special Characteristics For Process		△ Special Characteristics For Safety	
Change Details							
Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change