



INSPECTION STANDARD (HT LAB)

Page 01 of 01



☐ Prototype	☐ Pre-Launch	☒ Production	Date (Original)	03/07/21
Part Name:- Bull Gear 71T		Part No.:- P80001106A	Inspection Standard Number	SIP/4426/130
Customer :- M&M (SWARAJ)		Change Level.:- 00	Part Stage	HT lab

Sr.No.	Parameter	Special Char. Class	Methods				Reaction Plan
			Product Specification	Inspection Method	Inspection Frequency	Control Method	
1.	Surface Hardness	►	57~63 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
2.	ECD at 513 HV	►	0.8~1.1 mm	Micro Vicker/ Vicker Hardness Tester	1Pc/Lot	HT Lab Report	A
3.	Core Hardness	►	30~39 HRC	Rockwell Hardness Tester	1Pc/Lot	HT Lab Report	A
4.	Before Shot Peening Retained Austenite in the zone 0.1~0.3mm	►	Retained Austenite 20%Min.	Microscope	1Pc/Lot	HT Lab Report	A
5.	Before Shot Peening Hardness in the zone 0.1~0.3mm	►	700HV Min. (60HRC Min.)	Vicker Hardness Tester/ Rockwell Hardness Tester/	1Pc/Lot	HT Lab Report	A
6.	After Shot Peening Hardness in the zone 0.1~0.3mm	►	740HV (62 HRC Min.)	Vicker Hardness Tester/ Rockwell Hardness Tester/	1Pc/Lot	HT Lab Report	A

COMPONENT SKTCH:-

Material:- SAE 8620

Heat Treatment
Carburizing + Carbonitriding

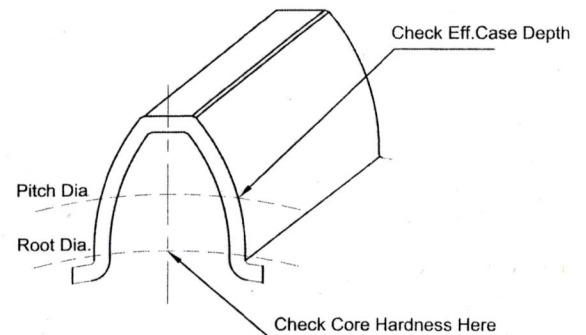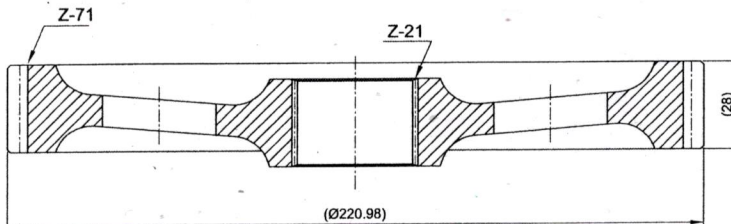

Reaction Plan: A-यदि Inspection करते समय कम्पोनेंट खराब मिले तो खराब कम्पोनेंट को Rejection का टैग लगाकर Rejection टेबल पर रखें और उसके बारे में Department के Incharge को बतायें ।

Legends: ► Special Characteristics as Per Drawing * Special Characteristics For Process ⚠ Special Characteristics For Safety

Change Details

Date	Rev. No.	Change	Reason for Change	Date	Rev. No.	Change	Reason for Change