

## AUTHOR QUERY FORM

	<p><b>Journal:</b> J. Appl. Phys.</p> <p><b>Article Number:</b> JAP21-AR-DIS2022-05281</p>	<p>Please provide your responses and any corrections by annotating this PDF and uploading it to AIP's eProof website as detailed in the Welcome email.</p>
-----------------------------------------------------------------------------------	--------------------------------------------------------------------------------------------	------------------------------------------------------------------------------------------------------------------------------------------------------------

Dear Author,

Below are the queries associated with your article; please answer all of these queries before sending the proof back to AIP.

**Article checklist:** In order to ensure greater accuracy, please check the following and make all necessary corrections before returning your proof.

1. Is the title of your article accurate and spelled correctly?
2. Please check affiliations including spelling, completeness, and correct linking to authors.
3. Did you remember to include acknowledgment of funding, if required, and is it accurate?

<b>Location in article</b>	<b>Query / Remark: click on the Q link to navigate to the appropriate spot in the proof. There, insert your comments as a PDF annotation.</b>
Q1	Please check that the author names are in the proper order and spelled correctly. Also, please ensure that each author's given and surnames have been correctly identified (given names are highlighted in red and surnames appear in blue).
Q2	In the sentence beginning "In the literature..." please check the usage of the term "second capture" in two occurrences.
Q3	We were unable to locate a digital object identifier (doi) for Refs. 40 and 68. Please verify and correct author names and journal details (journal title, volume number, page number, and year) as needed and provide the doi. If a doi is not available, no other information is needed from you. For additional information on doi's, please select this link: <a href="http://www.doi.org/">http://www.doi.org/</a> .
Q4	The resolution of Fig. 1 is low. If you are not satisfied with the way the figure appears in the proof, please provide a new figure file of higher resolution.
	<p>Please confirm ORCIDs are accurate. If you wish to add an ORCID for any author that does not have one, you may do so now. For more information on ORCID, see <a href="https://orcid.org/">https://orcid.org/</a>.</p> <p style="margin-left: 40px;"> <a href="#">O. Olikh</a>-0000-0003-0633-5429  <a href="#">V. Kostylyov</a>-0000-0002-1800-9471  <a href="#">V. Vlasiuk</a>-0000-0001-6352-0423  <a href="#">R. Korkishko</a>  <a href="#">Ya. Olikh</a>  <a href="#">R. Chupryna</a> </p>
	<p>Please check and confirm the Funder(s) and Grant Reference Number(s) provided with your submission:</p> <p style="margin-left: 40px;">National Research Foundation of Ukraine, 2020.02/0036</p> <p>Please add any additional funding sources not stated above:</p>

Thank you for your assistance.

**Dear Author,**  
**While reviewing your paper, we have identified additional changes that were necessary and have noted them on the proof. Please retain our changes and write "approve" or "reject" next to each one. Thank you.**

# <sup>1</sup> Features of FeB pair light-induced dissociation <sup>2</sup> and repair in silicon $n^+$ - $p$ - $p^+$ structures under ultrasound loading

<sup>3</sup>  
<sup>4</sup> Cite as: J. Appl. Phys. **130**, 000000 (2021); doi: [10.1063/5.0073135](https://doi.org/10.1063/5.0073135)  
<sup>5</sup> Submitted: 28 September 2021 · Accepted: 28 November 2021 ·  
<sup>6</sup> Published Online: ■■■ 2021



Q1

<sup>7</sup> **O. Olikh,<sup>1,a)</sup>** **V. Kostylyov,<sup>2</sup>** **V. Vlasiuk,<sup>2</sup>** **R. Korkishko,<sup>2</sup>** **Ya. Olikh,<sup>2</sup>** and **R. Chupryna<sup>1</sup>**

## <sup>8</sup> AFFILIATIONS

<sup>9</sup> <sup>1</sup> Physics Faculty, Taras Shevchenko National University of Kyiv, Kyiv 01601, Ukraine  
<sup>10</sup> <sup>2</sup> V. Lashkaryov Institute of Semiconductor Physics of NAS of Ukraine, Kyiv 03028, Ukraine

<sup>11</sup> **Note:** This paper is part of the Special Topic on Defects in Semiconductors.

<sup>12</sup> **a) Author to whom correspondence should be addressed:** [olegolikh@knu.ua](mailto:olegolikh@knu.ua)

<sup>13</sup>

## <sup>14</sup> ABSTRACT

<sup>15</sup> The experimental research in ultrasound impact on iron–boron pair transformation in silicon  $n^+$ - $p$ - $p^+$  structures has revealed the decrease  
<sup>16</sup> in concentration of pairs dissociated by light, as well as in the time of pair associations. The FeB pair changes were monitored by measuring  
<sup>17</sup> short circuit current kinetics. The ultrasound influence was investigated at different light intensities, temperatures, frequencies, and power of  
<sup>18</sup> acoustic waves. The possible mechanisms underlying the revealed effects were analyzed.

<sup>19</sup> *Published under an exclusive license by AIP Publishing. <https://doi.org/10.1063/5.0073135>*


## <sup>20</sup> I. INTRODUCTION

<sup>21</sup> It is of wide knowledge that the properties of semiconducting  
<sup>22</sup> crystals and structures are determined very much by their impurity  
<sup>23</sup> compositions. As a result, the methods aimed at modifying the  
<sup>24</sup> system of defects are very important for practical applications.  
<sup>25</sup> Most of these methods use irradiation, thermal treatment, or spe-  
<sup>26</sup>cific conditions of crystal growth. However, numerous experiments  
<sup>27</sup> show that ultrasound also represents a sufficiently effective instru-  
<sup>28</sup>ment to control the semiconductor defects. For example, it has  
<sup>29</sup> been found that acoustic waves cause a spatial redistribution of  
<sup>30</sup> defects,<sup>1–6</sup> transformation of metastable point defects,<sup>7–9</sup> recharging  
<sup>31</sup> of recombination centers,<sup>10,11</sup> and low temperature annealing of  
<sup>32</sup> radiation defects.<sup>12–16</sup> The effects of this kind are observed, in par-  
<sup>33</sup>ticular, in silicon, which is the basic modern material used in  
<sup>34</sup> microelectronics and solar power engineering.<sup>1,2,5,8,12,15,17,18</sup>

<sup>35</sup> The advantages of using active ultrasound (US) are the local  
<sup>36</sup> action of elastic oscillations and the possibility to adjust the exter-  
<sup>37</sup>nal impact by changing the type, polarization, or frequency of  
<sup>38</sup> acoustic waves.<sup>19</sup> However, this method of modifying defect  
<sup>39</sup> systems has not found wide application not least because of the  
<sup>40</sup> lack of appropriate experimental research. In our opinion, it is  
<sup>41</sup> most promising to use US loading (USL) as an additional factor of

<sup>42</sup> influence during various technological processes, which causes, in  
<sup>43</sup> particular, the transformations in the defect system. This assump-  
<sup>44</sup>tion is supported by the results obtained during ion implantation  
<sup>45</sup> performed in the US field.<sup>1,17,20</sup>

<sup>46</sup> Iron is an important impurity in silicon-based integrated  
<sup>47</sup> circuit and solar cell technology. Most often, iron-related defects  
<sup>48</sup> are the main recombination centers that determine the lifetime of  
<sup>49</sup> minority charge carriers; in particular, and device characteristics; in  
<sup>50</sup> general. Therefore, the methods aimed at iron gettering at various  
<sup>51</sup> stocks have practical importance. There are quite many reports  
<sup>52</sup> concerning defects of this kind. It is known that in thermal equilib-  
<sup>53</sup>rium at room temperature virtually all Fe<sub>i</sub> is present as Fe<sub>i</sub>B<sub>s</sub>  
<sup>54</sup> pairs in Si:B.<sup>21,22</sup> FeB pair dissociation can be accomplished by  
<sup>55</sup> illumination at room temperature, by minority carrier injection, or  
<sup>56</sup> by increasing the temperature.<sup>21,23,24</sup> Moreover, ultrasound vibra-  
<sup>57</sup>tions with a frequency of 25–80 kHz and acoustic lattice strain of  
<sup>58</sup>  $10^{-5}$ – $10^{-4}$  (Cz-Si<sup>25</sup>) or  $10^{-6}$ – $10^{-5}$  (poly-Si<sup>26,27</sup>) are capable of  
<sup>59</sup> destroying FeB pairs. In practice, however, the most widely used  
<sup>60</sup> technique is light-induced dissociation. The peculiarities of the dis-  
<sup>61</sup>sociation and subsequent repair are well studied.<sup>21–23,28–33</sup>  
<sup>62</sup> However, to the best of our knowledge, there are no reports about  
<sup>63</sup> the US impact on these processes.<sup>64</sup>

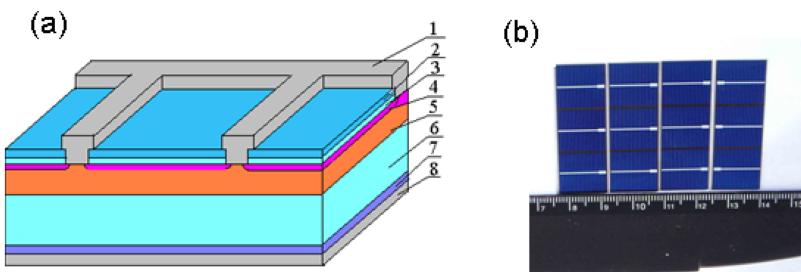

**FIG. 1.** (a) Scheme of the sample. (1) frontal Al electrode, (2)  $\text{Si}_3\text{N}_4$ , (3)  $\text{SiO}_2$ , (4) induced  $n^{++}$ -layer, (5) diffusion  $n^+$ -layer, (6) p-base region, (7) diffusion  $p^+$ -layer, and (8) rear Al electrode. (b) View of real solar cells; the photo was taken from the side of frontal metal electrode.

Our aim was to study experimentally the influence of ultrasound loading (2–30 MHz) on the processes of  $\text{FeB} \leftrightarrow \text{Fe}_i + \text{B}$  transformations in silicon solar cells (SCs). In order to prevent irreversible changes in the material properties, we used subthreshold intensity (strain  $< 2 \times 10^{-6}$ ). The obtained results can be applied for subtle acoustically controlled tuning of the processes involved in iron atom gettering.

## II. EXPERIMENTAL AND CALCULATION DETAILS

The  $n^+ - p - p^+$ -Si samples used in the experiment are shown in Fig. 1. The structure was fabricated from a  $380 \mu\text{m}$  thick p-type boron-doped Czochralski silicon wafer with [100] orientation and a resistivity of  $10 \Omega \text{ cm}$ . The  $n^+$  emitter with a sheet resistance of about  $20-30 \Omega/\square$  a thickness of  $0.7 \mu\text{m}$  was formed by phosphorus diffusion from the gas phase ( $\text{POCl}_3$ ) at  $940^\circ\text{C}$ . The anti-recombination isotype barrier was created by using  $p^+$  layer (10–20  $\Omega/\square$ ,  $0.6 \mu\text{m}$ ) formed by boron diffusion from the gas phase ( $\text{BCl}_3$ ) at  $985^\circ\text{C}$ . On the front surface, the antireflective and passivating  $\text{SiO}_2$  (40 nm) and  $\text{Si}_3\text{N}_4$  (30 nm) layers were formed. The solid grid Al contacts were formed by magnetron sputtering on the rear and front surfaces, respectively.

It has been found that some SC lots have significantly worse parameters compared to typical solar cells for this technological process. Additional experiments with thermal annealing at temperatures of 200 and  $90^\circ\text{C}$  (the procedure is described by Tayyib *et al.*<sup>34</sup>) showed that a sharp drop in the photoconversion parameters value is caused by iron impurities available in the SC base at concentrations up to  $4 \times 10^{13} \text{ cm}^{-3}$  in the SC base. It has also been found that the source of iron impurity is insufficiently pure chemicals that were used in the technological process for some SC lots. To study the effect of ultrasonic loading on the transformation of iron–boron pairs, the samples from these “bad” lots with varying degrees of iron contamination [ $(0.2 - 4) \times 10^{13} \text{ cm}^{-3}$ ] were taken. The area of the samples used in the experiment was  $1.52 \times 1.535 \text{ cm}^2$ .

To dissociate  $\text{FeB}$  pairs, the frontal side of the sample was illuminated with a halogen lamp with a radiation intensity  $W_{\text{ill}}$  of  $0.08-0.20 \text{ W/cm}^2$ . The illumination time  $t_{\text{ill}}$  was up to 30 s.

The  $\text{FeB}$  pair association was monitored by measuring the kinetics of short circuit current  $I_{\text{SC}}(t)$  after illumination by a halogen lamp—see Fig. 2.  $I_{\text{SC}}$  was measured under SC illumination by a low-intensity monochromatic light source (light-emitting diode SN-HPIR940 nm—1 W with light wavelength  $\lambda = 940 \text{ nm}$ ). The excess carrier density  $\Delta n$  induced by the LED illumination was estimated by using open-circuit voltage value according to


Sachenko *et al.*<sup>35</sup> The  $\Delta n$  value ( $< 10^{12} \text{ cm}^{-3}$ ) and duty cycle while  $I_{\text{SC}}(t)$  measuring (0.5%) evidence that LED illumination is weak and does not cause  $\text{FeB}$  dissociation. After illumination by the halogen lamp is terminated,  $\text{FeB}$  pairs are formed again and the starting value of  $I_{\text{SC}}$  is completely recovered.

In fact, in conditions of homogeneous carrier generation in the base, which is several minority carrier diffusion lengths  $L_n$ , the short circuit current can be described as follows:<sup>36,37</sup>

$$I_{\text{SC}}(t) = \frac{P_{\text{ph}}(1 - R_{\text{ph}}) q \beta \lambda}{hc} \times \frac{\alpha_{\text{ph}} \sqrt{\mu_n k T \tau(t)/q}}{1 + \alpha_{\text{ph}} \sqrt{\mu_n k T \tau(t)/q}}, \quad (1)$$

where  $\alpha_{\text{ph}} = \alpha_{\text{ph}}(T, \lambda)$  is the coefficient of light absorption,  $P_{\text{ph}}$  is the light power,  $R_{\text{ph}}$  is the coefficient of reflection,  $\beta$  is the coefficient of quantum yield,  $\mu_n$  is the electron mobility, and  $\tau$  is the minority carrier lifetime in the base. In the assumption that it is the iron-related defects that play an essential role in the recombination, the following expression can be used to estimate  $\tau$ :

$$\frac{1}{\tau(t)} = \frac{1}{\tau_i} + \frac{1}{\tau_{\text{SRH}}^{\text{Fe}_i}(t)} + \frac{1}{\tau_{\text{SRH}}^{\text{FeB}}(t)} + \frac{1}{\tau_{\text{other}}}, \quad (2)$$

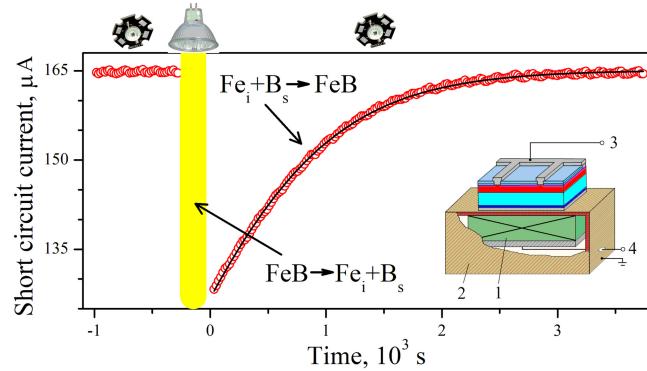

**FIG. 2.** Kinetics of short circuit current after intensive illumination. The marks are the experimental results, the line is the fitted curve using Eqs. (1)–(8). The zero of time corresponds to the moment of intensive illumination termination.  $T = 340 \text{ K}$ . Inset: Scheme of USL. (1) Piezoelectric transducer, (2) metal (Cu) foil, and (3 and 4) contact to  $I-V$  measure and to ultrasound excitation, respectively.

where  $\tau_i$  is the lifetime associated with intrinsic recombination;  $\tau_{SRH}^{Fe_i}$  and  $\tau_{SRH}^{FeB}$  are related to the recombinations at interstitial iron atoms  $Fe_i$  and at  $FeB$  pairs, accordingly;  $\tau_{other}$  describes further recombination channels (other impurities, lattice defects, surface recombination). In order to calculate  $\tau_{SRH}^{Fe_i}$  and  $\tau_{SRH}^{FeB}$ , the Shockley-Read-Hall model was used,

$$\begin{aligned}\tau_{SRH}^{Fe_i,FeB}(t) = & \frac{\tau_{p0}^{Fe_i,FeB}(t) \times (n_0 + n_1^{Fe_i,FeB} + \Delta n)}{N_A + n_0 + \Delta n} \\ & + \frac{\tau_{n0}^{Fe_i,FeB}(t) \times (N_A + p_1^{Fe_i,FeB} + \Delta n)}{N_A + n_0 + \Delta n},\end{aligned}\quad (3)$$

where  $N_A$  is the material's doping level ( $1.4 \times 10^{15} \text{ cm}^{-3}$ ),  $n_0$  is the equilibrium electron concentration given by the law of mass action, and  $n_1$  and  $p_1$  are given by

$$\begin{aligned}n_1^{Fe_i,FeB} &= N_C \exp\left(-\frac{E_C - E_t^{Fe_i,FeB}}{kT}\right), \\ p_1^{Fe_i,FeB} &= N_V \exp\left(-\frac{E_t^{Fe_i,FeB} - E_V}{kT}\right),\end{aligned}\quad (4)$$

where  $E_C$  and  $E_V$  are the energies of the conduction band and valence band edge, respectively,  $N_C$  and  $N_V$  are the densities of states in the conduction band and valence band, respectively, and  $E_t$  is the energy level of the relevant defect. The respective capture time constants of electrons and holes at the defect are given by

$$\begin{aligned}\tau_{p0}^{Fe_i,FeB}(t) &= \frac{1}{N_{Fe,FeB}(t) \sigma_p^{Fe_i,FeB} v_{th}^p}, \\ \tau_{n0}^{Fe_i,FeB}(t) &= \frac{1}{N_{Fe,FeB}(t) \sigma_n^{Fe_i,FeB} v_{th}^n},\end{aligned}\quad (5)$$

where  $N_{Fe}(t)$  and  $N_{FeB}(t)$  are the concentrations of  $Fe_i$  and  $FeB$ , respectively,  $v_{th}$  is the thermal velocity, and  $\sigma_n$  and  $\sigma_p$  are the respective capture cross sections of electrons and holes at the defect.

The time dependence of interstitial iron atom concentration after pair dissociation is described by the known expression from Refs. 38 and 39,

$$N_{Fe}(t) = (N_{Fe,0} - N_{Fe,eq}) \times \exp(-t/\tau_{ass}) + N_{Fe,eq}, \quad (6)$$

where  $\tau_{ass}$  is the characteristic time of the complex association, according to Refs. 23, 28, and 29

$$\tau_{ass} = 5.7 \times 10^5 \frac{\text{s}}{\text{K cm}^3} \times \frac{T}{N_A} \exp\left(\frac{E_m}{kT}\right), \quad (7)$$

where  $E_m$  is the energy of  $Fe_i^+$  migration,  $N_{Fe,0}$  is the concentration of interstitial iron atoms formed due to illumination, and  $N_{Fe,eq}$  is the portion of interstitial iron atoms with  $N_{Fe,0}$  that remain unpaired in the equilibrium state. According to Wijaranakula,<sup>39</sup>  $N_{Fe,eq}$  depends on temperature, doping level, and  $N_{Fe,0}$ :  $N_{Fe,eq} = N_{Fe,eq}(T, N_A, N_{Fe,0})$ . The estimations show that at 340 K  $N_{Fe,eq} \approx 0.1N_{Fe,0}$  for the samples under study.

In its turn, the iron–boron pair concentration  $N_{FeB}$ , which is formed as the result of the partial association of  $N_{Fe,0}$ , can be

estimated from

$$N_{FeB}(t) + N_{Fe}(t) = N_{Fe,0}. \quad (8)$$

In case the intensive illumination causes dissociation of all the pairs,  $N_{Fe,0}$  should be the same as the total concentration of the impurity iron in the structure  $N_{Fe,tot}$ . If the duration (or intensity) of illumination is not sufficient for total dissociation,  $N_{Fe,0} < N_{Fe,tot}$ . In the latter case,  $\tau_{other}$  will also make contribution in the recombination of the  $FeB$  pairs that have not dissociated [with concentration  $N_{Fe,tot} - N_{Fe,0} - N_{Fe,eq}(T, N_A, N_{Fe,tot} - N_{Fe,0})$ ] as well as the respective number of  $Fe_i$  [with concentration  $N_{Fe,eq}(T, N_A, N_{Fe,tot} - N_{Fe,0})$ ].

In our calculations, we took  $\beta = 1$ ,  $R_{ph} = 0.14$  (the result of calculations according to Klyui *et al.*<sup>40</sup>),  $\mu_n(T, N_A)$  from Klaassen,<sup>41</sup>  $v_{th}^n$  and  $v_{th}^p$  from Green,<sup>42</sup>  $N_C$ ,  $N_V$  from Couderc *et al.*,<sup>43</sup> the defect parameters from Rougieux *et al.*,<sup>44</sup> and  $\alpha_{ph}(T, \lambda)$  from data.<sup>45,46</sup> In calculating  $\tau_i$ , band-to-band radiation recombination and Auger recombination were taken into account, and the temperature dependence of the corresponding coefficients was calculated according to Nguyen *et al.*<sup>47</sup> and Altermatt *et al.*<sup>48</sup> We used Eqs. (1)–(8) to fit the experimental data  $I_{SC}(t)$ . As fitting parameters,  $P_{ph}$ ,  $\tau_{other}$ ,  $N_{Fe,0}$ , and  $E_m$  were taken. The fittings were performed by using the metaheuristic method EBL SHADE.<sup>49</sup>

The example of fitting results is shown in Fig. 2. In our case, the parameters determined by fitting had the following values.  $P_{ph} = (3.6 \pm 0.2) \times 10^{-4} \text{ W}$ , which agrees well with the value measured by PowerMeter Rk-5720 ( $3.5 \times 10^{-4} \text{ W}$ ).  $\tau_{other} > 100 \text{ s}$ , which testifies that the contribution of other recombination pathways can be neglected.  $N_{Fe,0} = (1.6 \pm 0.1) \times 10^{13} \text{ cm}^{-3}$ , which is close to the value obtained for the samples of the same series from  $L_n$  measuring before and after intense illumination ( $0.5 \times 10^{13} \text{ cm}^{-3}$ ). In this case,  $L_n$  was measured using spectral dependencies of short circuit current<sup>50</sup> and the iron concentration was determined by using Zoth and Bergholz<sup>24</sup> equation. Finally,  $E_m = (0.655 \pm 0.001) \text{ eV}$ . This value coincides with that well-known value,<sup>23,28,29,32</sup> which is 0.66 eV. The coincidence of the values obtained by approximation with those obtained from other sources (first of all,  $E_m$  value) proves that the investigations of  $I_{SC}(t)$  after intensive illumination can be applied for estimating the parameters of iron-related defects. Moreover, the peculiarities of pair dissociation (see Sec. III A) found in this way also correspond to those reported in the previous publications, which testifies that this approach is quite appropriate. In fact, the time of  $I_{SC}$  recovering is an indicator of how large the energy of migration is, and the amplitude with which  $I_{SC}$  changes in the result of intensive illumination is associated with the concentration of iron atoms released in the process. It should also be noted that this approach is similar to the method proposed by Herlufsen *et al.*,<sup>51</sup> in which actual concentrations of  $FeB$  pairs are estimated by the photoluminescence signal kinetics during pair association.

The measurements were carried out over a temperature range of 300–340 K. The temperature was varied by a thermoelectric cooler controlled by an STS-21 sensor and stabilized by a computer-controlled PID loop.

In the case of USL, the transverse (with frequency  $f_{US} = 0.3 \text{ MHz}$ ) or longitudinal (2–31 MHz) acoustic waves (AWs)

were applied to the samples by using a piezoelectric transducer. The US intensities  $W_{\text{US}}$  and amplitudes of strain  $\xi_{\text{US}} = \sqrt{2W_{\text{US}}/\rho_{\text{Si}}\vartheta_{\text{US}}^3}$  ( $\rho_{\text{Si}} = 2.33 \text{ g/cm}^3$  is the silicon density,  $\vartheta_{\text{US}}$  is the US velocity, 9850 and 5840 m/s in cases of longitudinal and transverse AWs, respectively) does not overcome  $1.3 \text{ W/cm}^2$  and  $2 \times 10^{-6}$ , respectively. Since the focus of our research was the influence of elastic vibrations on FeB pair transformations, to avoid the effect of the piezoelectric field, the transducer was shielded—see the inset of Fig. 2.

### III. RESULTS AND DISCUSSION

#### A. FeB dissociation

In our investigation of light-induced FeB pair dissociation processes, we illuminated the structure with a halogen lamp by varying the time of illumination  $t_{\text{ill}}$  and afterward measured the kinetics of short circuit current recovery—see Fig. 3(a). As seen from the figure, the time of short circuit current recovery does not change while the amplitude of light-induced changes depends on the time of illumination. Further approximation of the experimental curves by using the approach described in the previous section allowed us to estimate the number of pairs that dissociated in the result of illumination  $N_{\text{Fe},0}$  as a function of  $t_{\text{ill}}$ . The experiments were carried out on a series of samples at different light intensities and temperatures in conditions with and without US loading. The typical results are given in Fig. 4.

The obtained results show that as the illumination time grows the values of  $N_{\text{Fe},0}$  increase gradually until reaching saturation. This is in complete correspondence with the results of the previous research studies<sup>21,23,28</sup> that predict the exponential decrease in pair concentration with the increase in illumination time. The

saturation should correspond to the condition of complete pair dissociation. The experimentally obtained dependencies were approximated by using the following equation:

$$N_{\text{Fe},0}(t_{\text{ill}}) = A \exp(-t_{\text{ill}}/\tau_{\text{dis}}) + N_{\text{Fe},\text{fit}} \quad (9)$$

where  $\tau_{\text{dis}}$  is the characteristic time of dissociation and  $N_{\text{Fe},\text{fit}}$  is the value corresponding to saturation. The examples of approximation curves are given in Fig. 4, and the values of the parameters obtained by approximation are given in Table I.


On the other way, the equilibrium between free  $\text{Fe}_i$  and  $\text{Fe}_i\text{B}_s$  is determined by the following rate equations:




where  $R_a = \tau_{\text{ass}}^{-1}$  and  $R_d$  are the association and dissociation rates of FeB pairs, respectively. From Eq. (10), taking into account that  $N_{\text{Fe}} = N_{\text{Fe,tot}} - N_{\text{FeB}}$  and  $N_{\text{Fe}}(t_{\text{ill}} = 0) = N_{\text{Fe,eq}}$ , the time-dependent interstitial iron content during illumination can be described as follows:

$$\begin{aligned} N_{\text{Fe}}(t_{\text{ill}}) = & \left( N_{\text{Fe,eq}} - N_{\text{Fe,tot}} \frac{R_d}{R_d + R_a} \right) \exp[-(R_d + R_a)t_{\text{ill}}] \\ & + N_{\text{Fe,tot}} \frac{R_d}{R_d + R_a}. \end{aligned} \quad (11)$$

The comparison of Eqs. (9) and (11) shows that  $\tau_{\text{dis}}^{-1} = R_a + R_d$ ,  $N_{\text{Fe,fit}} = N_{\text{Fe,tot}}R_d/(R_a + R_d)$  should be noted that in our case (see Sec. III B)  $\tau_{\text{ass}} \gg \tau_{\text{dis}}$  (without USL  $\tau_{\text{ass}} \simeq 700 \text{ s}$  at 340 K and  $\tau_{\text{ass}} \simeq 13000 \text{ s}$  at 300 K). Therefore,  $R_d \gg R_a$  and  $\tau_{\text{dis}}^{-1} \simeq R_d$ ,  $N_{\text{Fe,fit}} \simeq N_{\text{Fe,tot}}$ .

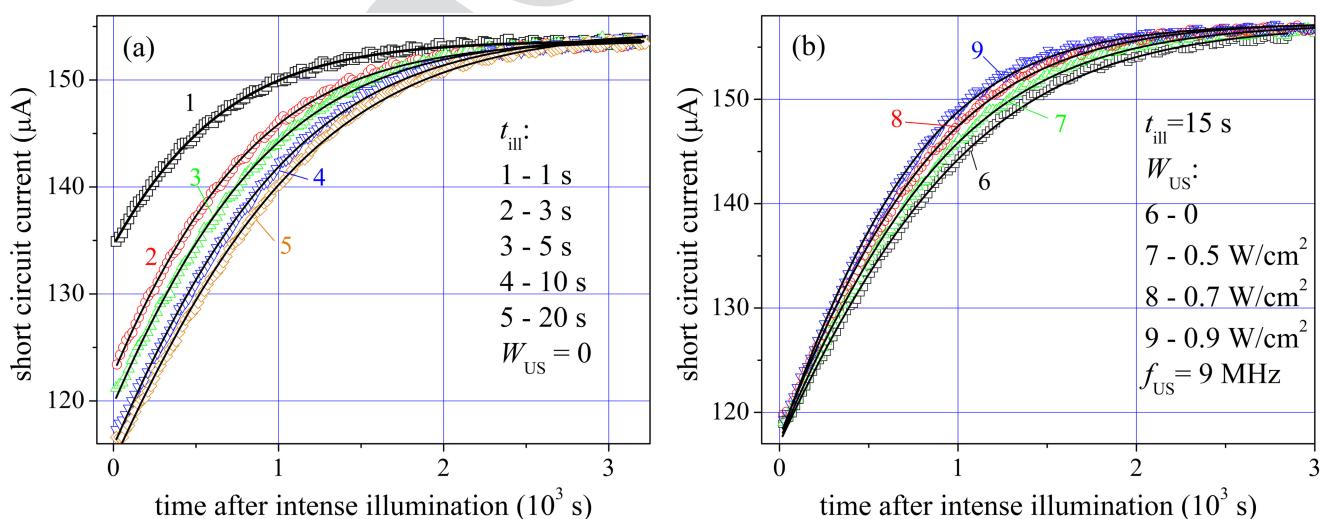

**FIG. 3.** Typical kinetics of short circuit current after intensive illumination of different duration (a) and USL intensity (b). The marks are the experimental results and the lines are the curves fitted by using Eqs. (1)–(8).  $t_{\text{ill}}$ , s: 1 (curve 1), 3 (2), 5 (3), 10 (4), 15 (6–9), 20 (5).  $W_{\text{US}}$ ,  $\text{W}/\text{cm}^2$ : 0 (1–6), 0.5 (7), 0.7 (8), 0.9 (9).  $f_{\text{US}} = 9 \text{ MHz}$ ,  $T = 340 \text{ K}$ .

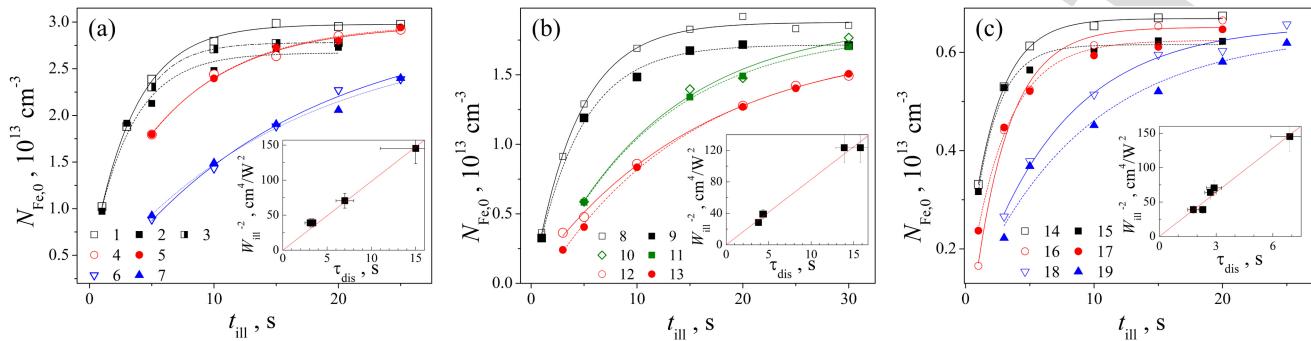

**FIG. 4.** Concentration dependence of interstitial atoms due to light-induced dissociation on illumination time. The marks are the experimental results and the lines are the curves fitted by using Eq. (9). Empty circles and solid lines are used for the case without USL, filled circles and dashed lines—for the case of USL.  $W_{ill}$ ,  $\text{W}/\text{cm}^2$ : 0.16 (curves 1–3, 8–11, 14, 15), 0.12 (4, 5, 16, 17), 0.09 (12, 13), 0.08 (6, 7, 18, 19).  $W_{US}$ ,  $\text{W}/\text{cm}^2$ : 0.9 (2, 5, 7), 0.6 (3, 9, 11, 13), 0.5 (15, 17, 19).  $f_{US}$ , MHz: 9.0 (2, 3, 5, 7), 0.3 (9, 11, 13), 5.0 (15, 17, 19); T, K: 340 (1–9, 12–19), 320 (10, 11). Samples SC350-1 (a), SC352-0 (b), and SC349-1 (c). Insets:  $\tau_{dis}$  are plotted against  $W_{ill}^{-2}$ . The lines are the curves fitted by  $\tau_{dis} = \text{constant} \times W_{ill}^{-2}$ .

As for the case without USL, we should note the following. First, for every sample  $N_{Fe,fit}$  remains constant and does not depend on illumination intensity and temperature—see Table I. This is quite expectable if we assume that in this case  $N_{Fe,fit} = N_{Fe,tot}$ . Second, the value of  $\tau_{dis}$  (last column in Table I) depends on  $W_{ill}$  and  $T$ . It is well known<sup>21,28,52</sup> that the dissociation rate of FeB pairs increases quadratically with increasing illumination intensity. In the insets of Fig. 4, the values of  $\tau_{dis}$  are plotted against  $W_{ill}^{-2}$ . The linearity of the obtained curves is in complete coincidence with the reported data and can serve as an additional proof of the suggested approach applicability in estimating iron-related defect parameters. Moreover, it is known<sup>53</sup> that the dissociation time decreases approximately twice per 20 °C increase. In our experiment,  $\tau_{dis} = (11 \pm 4)$  s for sample SC350-2 [Fig. 4(b) and Table I] at  $T = 320$  K and at 340 K, it comprised  $4.3 \pm 0.3$  s, which justifies the expectations.

Another reason why it is advisable to analyze  $I_{SC}$  kinetics is the behavior of  $\tau_{other}$  revealed in the experiments. In the case when  $t_{ill}$  corresponds to the values of  $N_{Fe,0}$  close to saturation, the other recombination channels can be neglected ( $\tau_{other} > 100$  ms). In the case when the values of  $t_{ill}$  are small,  $\tau_{other}$  changes in the range  $10^{-6}$ – $10^{-4}$  s and begins to increase as the illumination time increases. In terms of the proposed approximation, this indicates that some parts of FeB pairs have not dissociated and the value of  $\tau_{other}$  is related to recombination on iron-related defects that do not reconstruct when the sample is kept in darkness. In order to support this assumption, the quantity  $\tau_{other}^{calc}$  was estimated as follows:

$$\tau_{other}^{calc} = \left( (\tau_{SRH}^{Fe})^{-1} + (\tau_{SRH}^{FeB})^{-1} \right)^{-1},$$

where  $\tau_{SRH}^{Fe}$  and  $\tau_{SRH}^{FeB}$  were calculated by Eq. (3) for defect concentrations  $N_{Fe} = N_{Fe,eq}(N_{Fe,tot} - N_{Fe,0})$  and  $N_{FeB} = N_{Fe,tot} - N_{Fe,0} - N_{Fe}$ , accordingly. It turned out that  $\tau_{other}^{calc}$  and  $\tau_{other}$ , obtained in the same conditions, are very close: the correlation coefficient equals to 0.98 (see the supplementary material).

Paying our attention back to the impact of acoustic waves on the processes of light-induced dissociation of FeB pairs, the

following should be noted. First, USL actually does not influence the magnitude of dissociation time:  $\tau_{dis}$  values in neighboring rows are similar in the error range for all the cases in Table I. Second, some pairs do not dissociate under illumination in the USL case:

**TABLE I.** The value of maximum concentrations of light released iron atoms and characteristic dissociation time obtained by approximating experimental dependencies by Eq. (9).

Sample	$T$ (K)	$W_{ill}$ ( $\text{W}/\text{cm}^2$ )	$f_{US}$ (MHz)	$W_{US}$ ( $\text{W}/\text{cm}^2$ )	$N_{Fe, fit}$ ( $10^{13} \text{ cm}^{-3}$ )	$\tau_{dis}$ (s)
SC350-1	340	0.08	9.0	0.9	$3.0 \pm 0.3$	$15 \pm 4$
	340	0.08			$2.9 \pm 0.4$	$15 \pm 6$
	340	0.12			$2.98 \pm 0.07$	$7 \pm 1$
	340	0.12			$2.99 \pm 0.06$	$7 \pm 1$
	340	0.16			$2.98 \pm 0.02$	$3.4 \pm 0.2$
	340	0.16	9.0	0.6	$2.78 \pm 0.03$	$3.1 \pm 0.6$
	340	0.16	9.0	0.9	$2.67 \pm 0.07$	$2.9 \pm 0.6$
SC352-1	340	0.16	5.9	1.0	$4.25 \pm 0.03$	$3.8 \pm 0.2$
	340	0.16			$4.03 \pm 0.04$	$3.7 \pm 0.2$
SC350-2	340	0.09	0.3	0.6	$1.76 \pm 0.08$	$16 \pm 2$
	340	0.09			$1.72 \pm 0.05$	$14 \pm 1$
	340	0.12			$1.89 \pm 0.02$	$9 \pm 1$
	340	0.12			$1.86 \pm 0.03$	$8 \pm 2$
	340	0.16			$1.88 \pm 0.02$	$4.3 \pm 0.3$
	340	0.16			$1.72 \pm 0.02$	$4.4 \pm 0.4$
	320	0.16			$1.9 \pm 0.2$	$11 \pm 4$
	320	0.16			$1.8 \pm 0.1$	$11 \pm 1$
SC349-1	340	0.08	5.0	0.5	$0.66 \pm 0.02$	$7 \pm 1$
	340	0.08			$0.64 \pm 0.05$	$9 \pm 3$
	340	0.12			$0.65 \pm 0.01$	$2.7 \pm 0.3$
	340	0.12			$0.62 \pm 0.01$	$2.9 \pm 0.4$
	340	0.16			$0.67 \pm 0.01$	$2.3 \pm 0.2$
	340	0.16			$0.61 \pm 0.01$	$1.8 \pm 0.3$

293  $N_{\text{Fe,fit}}(W_{\text{US}} > 0) < N_{\text{Fe,fit}}(W_{\text{US}} = 0)$ . How large the portion of  
 294 these pairs is, depends on US intensity [see Figs. 4(a), Table I,  
 295  $W_{\text{ill}} = 0.16 \text{ W/cm}^2$ ; at maximum  $W_{\text{US}}$  values, this portion reaches  
 296 10%. It should be noted that this [effect] is observed only in the  
 297 case when light-induced pair dissociation is close to saturation.  
 298 If  $W_{\text{ill}}$  (or temperature), however, is that at which a part of iron  
 299 atoms stays near the substitutional boron atoms at the given illumina-  
 300 tion times, then  $N_{\text{Fe,fit}}(W_{\text{US}} > 0) \simeq N_{\text{Fe,fit}}(W_{\text{US}} = 0)$ .

### 301 B. FeB association

302 It has also been found that USL accelerates FeB pair associa-  
 303 tion, see Fig. 3(b). As seen from the figure, the main result of ultra-  
 304 sound excitation in the structure is the decrease in time of short  
 305 circuit current recovery. Since in approximating experimental  
 306 dependencies  $I_{\text{SC}}(t)$ , we assumed that pre-exponential multiplier in  
 307 Eq. (7) does not depend on USL (but relies only on the temperature  
 308 and level of base doping), in order to find numerical characteristics  
 309 of this effect, we used the change in migration energy  $\Delta E_{\text{US}}$ , i.e., it  
 310 was assumed that

$$E_m \text{ultrasound} - E_{m,0} = \Delta E_{\text{US}}, \quad (12)$$

311 where  $E_{m,0}$  is the migration energy estimated without USL and  
 312  $\Delta E_{\text{US}}$  is the acoustically induced (AI) change in migration energy.  
 313 It is seen from Fig. 3(b) that  $\Delta E_{\text{US}}$  depends on acoustic wave inten-  
 314 sity. Figure 5 presents the dependencies  $\Delta E_{\text{US}} = \Delta E_{\text{US}}(W_{\text{US}})$  at  
 315 varied US frequencies and for the samples with different iron  
 316 content (estimated by the dependencies similar to those given in  
 317 Fig. 4). The presented data show that

- 318 1.  $\Delta E_{\text{US}}$  shows a practically linear dependence on US intensity;
- 319 2. Effectiveness of AI change in migration energy decreases as the  
 320 US frequency increases; transverse waves, despite their low fre-  
 321 quency, less strongly impact the processes of iron ion diffusion;
- 322 3. the magnitude of AI effect practically does not depend on iron  
 323 concentration;
- 324 4. AI change in migration energy can be as high as 13 meV.

325  $\Delta E_{\text{US}}$  has not been found to depend on illumination intensity.

326 The data presented in Fig. 5 were obtained at 340 K. With the  
 327 decrease in temperature, the AI effect decreases—see Fig. 6.  
 328 As seen from the figure, temperature dependencies of  $\Delta E_{\text{US}}$  are  
 329 close to linear,

$$\Delta E_{\text{US}}(T) = \Delta E_{\text{US}}(0) + \alpha_{\text{US}} T, \quad (13)$$

330 where temperature coefficient  $\alpha_{\text{US}}$  depends on US frequency (see  
 331 the inset of Fig. 6), while  $\Delta E_{\text{US}}(0)$  depends also on the US intensity.

### 332 C. Possible mechanisms of ultrasound influence

333 It is obvious that the analysis of the possible reasons for US  
 334 impact should be based on the mechanisms of iron-related defect  
 335 transformation. It is suggested that FeB pair dissociation is a two-  
 336 stage process.<sup>21,23,54</sup> First, the electron capture process leads to  $\text{Fe}_i^+$   
 337 neutralization, which removes the Coulombic attraction between  $\text{Fe}_i^0$   
 338 and  $\text{B}_s^-$ . Second, the electron capture results in the deposition of dif-  
 339 fusion barrier energy and spatial dissociation of atoms. In the


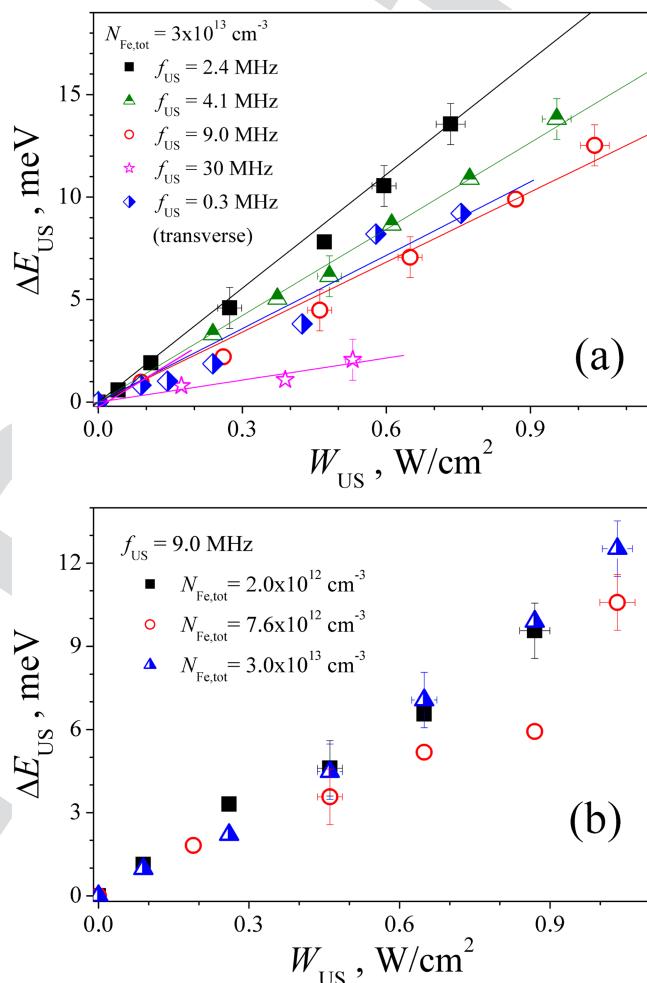


FIG. 5. Dependencies of AI change in migration energy on US intensity for various frequencies (a) and samples with different iron concentrations (b).  $T = 340 \text{ K}$ . The points were obtained by approximating experimental dependencies and the lines are the linear fitted curves.

literature, two possibilities are discussed: the second capture, which leads to a negative charge state ( $\text{Fe}_i^-$ ) and consequently to Coulombic repulsion of  $\text{Fe}_i^- \text{B}_s^-$  pair, and the second capture, which deposits the necessary  $\text{Fe}_i^0$  migration energy after recombination with a hole. The second way is known<sup>23</sup> as recombination-enhanced defect reaction (REDR) and is caused by a strong electron–lattice coupling at the defect.

As for the association, it happens due to  $\text{Fe}_i^+$  field-assisted migration to  $\text{B}_s^-$ . Therefore, a more detailed expression for  $\tau_{\text{ass}}$  takes the following form:<sup>22,23,28</sup>

$$\tau_{\text{ass}} = \frac{\epsilon \epsilon_0 k T}{q^2 D_{\text{Fe}} N_A} = \frac{\epsilon \epsilon_0 k T}{q^2 D_{0,\text{Fe}} N_A} \exp\left(\frac{E_m}{k T}\right), \quad (14)$$

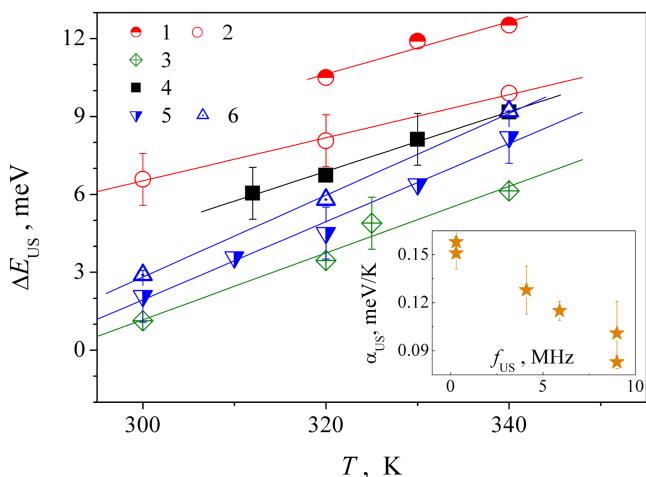

**FIG. 6.** Temperature dependencies of  $\Delta E_{\text{US}}$ .  $N_{\text{Fe,tot}} = 10^{13} \text{ cm}^{-3}$ : 3.0 (curves 1 and 2), 4.3 (3), 1.9 (4).  $f_{\text{US}}$ , MHz: 9.0 (1,2), 4.1 (3), 5.9 (4), 0.3 (5,6).  $W_{\text{US}}$ , W/cm<sup>2</sup>: 1 (1), 0.87 (2), 0.48 (3), 1.0 (4), 0.58 (5), 0.76 (6). The marks are the experimental results and the lines are the linear fitted curves. Inset: Frequency dependence of temperature coefficient  $\Delta E_{\text{US}}$ .

where iron diffusivity  $D_{\text{Fe}} = D_{0,\text{Fe}} \exp(-E_m/kT)$ , and in the general case<sup>55–57</sup>  $D_{0,\text{Fe}} = \beta v a_0^2 \exp(\delta S_{\text{Fe}}/k)$ ,  $\beta$  is the correlation factor,  $v$  is the effective vibrational (attempt) frequency,  $a_0$  is the jump distance, and  $\delta S_{\text{Fe}}$  is the migration entropy.

For non-piezoelectric materials, the main effect of acoustic waves is associated with the mechanical stresses they cause. It is reported<sup>55,58–64</sup> about several stress-related mechanisms of impurity diffusivity variation. For instance, Aziz *et al.*<sup>55,58</sup> show that due to static stresses  $\sigma_{\text{stat}}$  in the crystal, the impurity migration energy can decrease by  $\Delta E = \sigma_{\text{stat}} V^*$ , where  $V^*$  is the activation strain tensor. It is known<sup>65</sup> that as US propagates through the crystal, it causes static strain,

$$u_{\text{stat}} = \frac{\beta}{8} \left( \frac{2\pi f_{\text{US}} u_{\text{US}}}{v_{\text{US}}} \right)^2 = \frac{\beta W_{\text{US}}}{4\rho_{\text{Si}} v_{\text{US}}^3}, \quad (15)$$

where  $\beta$  is the acoustic nonlinearity parameter and  $u_{\text{US}} = \frac{1}{\pi f_{\text{US}}} \sqrt{\frac{W_{\text{US}}}{2\rho_{\text{Si}} v_{\text{US}}}}$  is the amplitude of lattice atom displacements. Therefore, the effect should be linear with respect to the US intensity, which correlates with the experimental data. It is known,<sup>58,66</sup> however, that  $V^* = (0.01 - 0.2)\Omega$ , where  $\Omega$  is the atomic volume ( $\sim 2 \times 10^{-29} \text{ m}^3$  for silicon), and the value of the multiplier depends on the kind of impurity. If we consider the propagation of longitudinal waves in direction [100] ( $\beta = 2.0003$  is assumed,<sup>67</sup>  $\sigma_{\text{stat}} = c_{11} u_{\text{stat}}$ ,  $c_{11} = 166 \text{ GPa}$ ), for  $W_{\text{US}} = 1 \text{ W/cm}^2$  we shall obtain  $\Delta E = 5 \times 10^{-11} \text{ eV}$ . Therefore, this mechanism cannot be the cause of the revealed effect.

According to the data,<sup>60–62</sup> the diffusion of impurities in US fields can occur due to elastic deformation. In particular, the energy of interaction between a single defect and the strain field is

given by

$$E_{\text{int}}(x, t) = -K\Omega_d \xi(x, t), \quad (16)$$

where  $K$  is the bulk modulus (102 GPa for Si),  $\Omega_d$  is the variation of crystal volume, in the result of point defect formation, for interstitial defect<sup>61</sup>  $\Omega_d = (1.7 - 2.2)\Omega$ , and  $\xi$  is the lattice relative deformation by the acoustic wave. The estimation of maximum interaction for  $W_{\text{US}} = 1 \text{ W/cm}^2$  yields  $E_{\text{int}} \simeq 0.1 \text{ meV}$ . Although Baransky *et al.*<sup>68</sup> state that in case of clusters containing  $N_i$  defects, a collective effect can be observed, when  $E_{\text{int}} \rightarrow N_i E_{\text{int}}$ , in our opinion, this mechanism cannot be crucial in the effect of AI acceleration of FeB pair association revealed in our research.

In turn, the most probable cause of a decrease in  $\tau_{\text{ass}}$  is the process of impurity interactions with nonequilibrium excitations of the crystal lattice described in Refs. 63 and 64, which results in the change in probability of diffusion transitions. According to Pavlovich,<sup>63</sup> the US influence is that it causes an increase in crystal effective temperature and an effective decrease in “ polaron” activation energy. The latter is related to the transfer of lattice deformation around the impurity during diffusion transition.<sup>63</sup> It should be noted that according to calculations,<sup>63</sup> this effect should depend linearly on US intensity and temperature, which correlates with experimentally found peculiarities of AI changes. In addition, according to Krevchik *et al.*,<sup>64</sup>  $\Delta E_{\text{US}} \sim t_s$ , where  $t_s$  is phonon collision time, which can account for the revealed frequency dependence of the effect.

It should be noted that the iron–boron pairs are found<sup>25–27</sup> to dissociate due to ultrasound treatment. In our opinion, the reported herein and previous results have a lot in common. In fact, according to Ostapenko *et al.*,<sup>26</sup> Fe<sub>i</sub> has to “jump” to the next nearest interstitial under ultrasound action; we state about the decrease in Fe<sub>i</sub> migration energy value as well as the enhance of Fe<sub>i</sub> diffusivity in case of ultrasound loading. Further, the efficiency of AI dissociation, as well as AI  $\tau_{\text{ass}}$  fall, increases with the rise of temperature.<sup>407</sup> The difference in the action of ultrasound (the iron–boron pairs dissociation or the enhancing of pairing) is associated with the difference in the intensity of the acoustic influence. For instance, the researchers used acoustic strain  $\xi_{\text{US}} = 10^{-5} - 10^{-4}$  was used<sup>25</sup> to dissociate FeB pairs in Cz-Si. Furthermore, Ostapenko and Bell<sup>25</sup> regarded the resonance condition of pair reorientation (first step of dissociation) and used 25–70 kHz. In our case,  $\xi_{\text{US}} < 2 \times 10^{-6}$  and  $f_{\text{US}} = 2 - 30 \text{ MHz}$  are deficient to effectively overcome the Coulombic attraction between Fe<sub>i</sub><sup>+</sup> and B<sub>s</sub><sup>-</sup>. Additionally, the presented data show that the effectiveness of acoustically induced change decreases as the ultrasound frequency increases. Besides, it should be noted that Ostapenko *et al.*<sup>27</sup> asserted that in the case of predominant dissociated pairs, the ultrasound treatment may promote the pairing reaction in contradistinction to the case of a high fraction of paired iron. In our case, the predominant dissociation was realized by intense illumination and then the ultrasound loading accelerated pairing. Thus, the reported results provided empirical evidence for the above-mentioned prediction.

As far as dissociation is concerned, it is worth paying attention to the possible US impact on the processes of charge carrier capture. For instance, it is suggested<sup>19</sup> that in conditions of USL the capture cross sections for complex defects should change

because of the change in effective distance between the components. In particular, this effect is expected to be especially substantial for the complexes whose components have  $\Omega_d$  with opposite signs. This is what is observed for FeB ( $\Omega_d(\text{Fe}_i) > 0$ ,  $\Omega_d(\text{B}_s) < 0$ ) and for this reason, the complex should be acoustically active in terms of charge carrier capture. However, in our opinion, the processes of AI changes in  $\sigma_{n(p)}$  should have influenced, first, the characteristic time of dissociation, but actually, the effects of this kind have not been revealed. AI increase of  $R_a$  should decrease  $N_{\text{Fe,fit}}$  [see Eqs. (9) and (11)]; however, this effect is leveled by the essential difference between  $\tau_{\text{dis}}$  and  $\tau_{\text{ass}}$ . Therefore, probably because of this reason, the US produces an impact on the second stage of dissociation. On the one hand, Korotchenkov and Grimmeiss<sup>11</sup> show that due to the change of impurity location concerning surrounding atoms in silicon under USL, the activation thermal energy of the carrier captured by the defect is decreased (up to about 10 meV at US intensities commensurate to those in our experiments). A similar increase in electron emission in our case should decrease the equilibrium part of negatively charged Fe ions experiencing Coulombic repulsion with  $\text{B}_s^-$ . On the other hand, it is shown<sup>69</sup> that USL of low intensity makes some part of the FeB pairs get rearranged in a metastable configuration with a different (orthorhombic) symmetry, in which the distance between the components is greater. At over threshold US intensities, the spatial separation of this kind results in a complete pair dissociation.<sup>25–27</sup> For our case, however, the important thing is that the decrease in distance weakens the Coulombic repulsion. In addition, the decrease in the concentration of pairs, which dissociate under illumination in the USL case, can be connected to a partial acoustically induced FeB dissociation. In fact, if some pairs were dissociated by ultrasound waves, which had been pre-exited in the sample with a high initial fraction of paired Fe, they cannot be dissociated under illumination. The decrease in the temperature or photon quantity leads to a reduction in the set of FeB which was modified by ultrasound or in the set of FeB which was modified by the capture of light-induced electrons, respectively. The sets cease to overlap and  $N_{\text{Fe,fit}}(W_{\text{US}} > 0) \simeq N_{\text{Fe,fit}}(W_{\text{US}} = 0)$ —see Table I. Finally, USL can be the cause of weakening the electron-lattice coupling at the defect as well as the REDR process as a whole.

Numerous publications, see, for example, Refs. 70–72, report that during such technological processes as temperature stimulated diffusion of dopants or the formation of an antireflection coating, iron atoms also undergo gettering. This is caused by Fe ions diffusion to various stocks. When performed in the US field, these processes, as the obtained results suggest, should improve the gettering effectiveness because of the greater volume from which Fe ions could be piled at the stocks.

#### IV. CONCLUSION

The experimental research of ultrasound impact on the processes of FeB pair transformation was carried out in silicon  $n^+$ - $p$ - $p^+$  structures at near room temperatures. The investigation has revealed an acoustically driven decrease in the portion of FeB pairs that dissociate under the action of light as well as the decrease in Fe ion migration energies. The latter effect depends linearly on ultrasound intensity; the temperature decrease and ultrasound

frequency increase reduce the acoustically induced change of migration energy. The analysis has shown that these phenomena are caused by the interaction of impurities with nonequilibrium excitations of a crystal lattice, and acoustically driven attenuation of Coulombic repulsion, which is caused by the increase in distance between pair components and/or change in defect's charge. Thus, ultrasound can be an effective tool for controlling silicon structure characteristics.

#### SUPPLEMENTARY MATERIAL

See the [supplementary material](#) for the lifetime associated with further recombination channels plot [ $\tau_{\text{other}}$  which was obtained by  $I_{\text{SC}}(t)$  fitting vs  $\tau_{\text{other}}^{\text{calc}}$  which was calculated from  $N_{\text{Fe,0}}$  and  $N_{\text{Fe,fit}}$  values].

#### ACKNOWLEDGMENTS

The authors would like to acknowledge the financial support by National Research Foundation of Ukraine (Project No. 2020.02/0036).

#### DATA AVAILABILITY

The data that support the findings of this study are available from the corresponding author upon reasonable request.

#### REFERENCES

- <sup>1</sup>M. Jivanescu, A. Romanyuk, and A. Stesmans, *J. Appl. Phys.* **107**, 114307 (2010).
- <sup>2</sup>A. Gorb, O. Korotchenkov, O. Olikh, A. Podolian, and R. Chupryna, *Solid State Electron.* **165**, 107712 (2020).
- <sup>3</sup>S. Ostapenko, *Appl. Phys. A* **69**, 225 (1999).
- <sup>4</sup>B. Zaveryukhin, N. Zaveryukhina, and O. M. Tursunkulov, *Tech. Phys. Lett.* **28**, 752 (2002).
- <sup>5</sup>N. Zaveryukhina, E. Zaveryukhina, S. Vlasov, and B. Zaveryukhin, *Tech. Phys. Lett.* **34**, 241 (2008).
- <sup>6</sup>I. Dirnstorfer, W. Burkhardt, B. K. Meyer, S. Ostapenko, and F. Karg, *Solid State Commun.* **116**, 87 (2000).
- <sup>7</sup>I. Buyanova, S. S. Ostapenko, A. Savchuk, and M. K. Sheinkman, in *Defects in Semiconductors 17*, Materials Science Forum Vol. 143, edited by H. Heinrich and W. Jantsch (Trans Tech Publications, 1993), pp. 1063–1068.
- <sup>8</sup>I. Ostrovskii, O. Korotchenkov, O. Olikh, A. Podolyan, R. Chupryna, and M. Torres-Cisneros, *J. Opt. A: Pure Appl. Opt.* **3**, 82 (2001).
- <sup>9</sup>T. Wosinski, A. Makosa, and Z. Witczak, *Semicond. Sci. Technol.* **9**, 2047 (1994).
- <sup>10</sup>O. Olikh, *Ultrasonics* **56**, 545 (2015).
- <sup>11</sup>O. Korotchenkov and H. Grimmeiss, *Phys. Rev. B* **52**, 14598 (1995).
- <sup>12</sup>A. O. Podolian, A. B. Nadtochiy, and O. A. Korotchenkov, *Tech. Phys. Lett.* **38**, 405 (2012).
- <sup>13</sup>Y. Olikh, M. Tymochko, and A. Dolgolenko, *Technol. Phys. Lett.* **32**, 586 (2006).
- <sup>14</sup>I. Ostrovskii, N. Ostrovskaya, O. Korotchenkov, and J. Reidy, *IEEE Trans. Nucl. Sci.* **52**, 3068 (2005).
- <sup>15</sup>P. Parchinskii, S. Vlasov, and L. Ligai, *Semiconductors* **40**, 808 (2006).
- <sup>16</sup>O. Konoreva, Y. M. Olikh, M. Pinkovska, O. Radkevych, V. Tartachnyk, and V. Shlapatska, *Superlattices Microstruct.* **102**, 88 (2017).
- <sup>17</sup>A. Romanyuk, P. Oelhafen, R. Kurps, and V. Melnik, *Appl. Phys. Lett.* **90**, 013118 (2007).
- <sup>18</sup>O. Y. Olikh, K. V. Voytenko, and R. M. Burbelo, *J. Appl. Phys.* **117**, 044505 (2015).

- <sup>538</sup> <sup>19</sup>O. Y. Olikh, A. M. Gorb, R. G. Chupryna, and O. V. Pristay-Fenenkov, *J. Appl. Phys.* **123**, 161573 (2018).
- <sup>539</sup> <sup>20</sup>A. Romanyuk, V. Spassov, and V. Melnik, *J. Appl. Phys.* **99**, 034314 (2006).
- <sup>540</sup> <sup>21</sup>L. J. Geerligs and D. Macdonald, *Appl. Phys. Lett.* **85**, 5227 (2004).
- <sup>541</sup> <sup>22</sup>D. Macdonald, T. Roth, P. N. K. Deenapanray, K. Bothe, P. Pohl, and J. Schmidt, *J. Appl. Phys.* **98**, 083509 (2005).
- <sup>542</sup> <sup>23</sup>C. Möller, T. Bartel, F. Gibaja, and K. Lauer, *J. Appl. Phys.* **116**, 024503 (2014).
- <sup>543</sup> <sup>24</sup>G. Zoth and W. Bergholz, *J. Appl. Phys.* **67**, 6764 (1990).
- <sup>544</sup> <sup>25</sup>S. S. Ostapenko and R. E. Bell, *J. Appl. Phys.* **77**, 5458 (1995).
- <sup>545</sup> <sup>26</sup>S. S. Ostapenko, L. Jastrzebski, and B. Sopori, *Semicond. Sci. Technol.* **10**, 1494 (1995).
- <sup>546</sup> <sup>27</sup>S. S. Ostapenko, L. Jastrzebski, J. Lagowski, and B. Sopori, *Appl. Phys. Lett.* **65**, 1555 (1994).
- <sup>547</sup> <sup>28</sup>N. Khelifati, H. S. Laine, V. Vähäniemi, H. Savin, F. Z. Bouamama, and D. Bouhafs, *Phys. Status Solidi A* **216**, 1900253 (2019).
- <sup>548</sup> <sup>29</sup>J. Tan, D. Macdonald, F. Rougier, and A. Cuevas, *Semicond. Sci. Technol.* **26**, 055019 (2011).
- <sup>549</sup> <sup>30</sup>K. Lauer, C. Möller, D. Debbih, M. Auge, and D. Schulze, in *Gettering and Defect Engineering in Semiconductor Technology XVI*, Solid State Phenomena Vol. 242 (Trans Tech Publications Ltd, 2016), pp. 230–235.
- <sup>550</sup> <sup>31</sup>X. Zhu, D. Yang, X. Yu, J. He, Y. Wu, J. Vanhellemont, and D. Que, *AIP Adv.* **3**, 082124 (2013).
- <sup>551</sup> <sup>32</sup>D. Macdonald, A. Cuevas, and L. J. Geerligs, *Appl. Phys. Lett.* **92**, 202119 (2008).
- <sup>552</sup> <sup>33</sup>T. Bartel, F. Gibaja, O. Graf, D. Gross, M. Kaes, M. Heuer, F. Kirscht, C. Möller, and K. Lauer, *Appl. Phys. Lett.* **103**, 202109 (2013).
- <sup>553</sup> <sup>34</sup>M. Tayyib, J. Theobald, K. Peter, J. Odden, and T. Sætre, *Energy Procedia* **27**, 21 (2012).
- <sup>554</sup> <sup>35</sup>A. V. Sachenko, Y. V. Kryuchenko, V. P. Kostylyov, A. V. Bobyl, E. I. Terukov, S. N. Abolmasov, A. S. Abramov, D. A. Andronikov, M. Z. Shvarts, I. O. Sokolovskyi, and M. Evstigneev, *J. Appl. Phys.* **119**, 225702 (2016).
- <sup>555</sup> <sup>36</sup>A. Fahrenbruch and R. Bube, *Fundamentals of Solar Cells: Photovoltaic Solar Energy Conversion* (Academic Press, 1983), p. 580.
- <sup>556</sup> <sup>37</sup>M. Razeghi and A. Rogalski, *J. Appl. Phys.* **79**, 7433 (1996).
- <sup>557</sup> <sup>38</sup>J. D. Murphy, K. Bothe, M. Olmo, V. V. Voronkov, and R. J. Falster, *J. Appl. Phys.* **110**, 053713 (2011).
- <sup>558</sup> <sup>39</sup>W. Wijaranakula, *J. Electrochem. Soc.* **140**, 275 (1993).
- <sup>559</sup> <sup>40</sup>N. Klyui, V. Kostylyov, A. Rozhin, V. Gorbulik, V. Litovchenko, M. Voronkin, and N. Zaika, *Opto-Electr. Rev.* **8**, 402 (2000).
- <sup>560</sup> <sup>41</sup>D. Klaassen, *Solid State Electron.* **35**, 953 (1992).
- <sup>561</sup> <sup>42</sup>M. A. Green, *J. Appl. Phys.* **67**, 2944 (1990).
- <sup>562</sup> <sup>43</sup>R. Couderc, M. Amara, and M. Lemiti, *J. Appl. Phys.* **115**, 093705 (2014).
- <sup>563</sup> <sup>44</sup>F. E. Rougier, C. Sun, and D. Macdonald, *Sol. Energy Mater. Sol. Cells* **187**, 581 263 (2018). 582
- <sup>564</sup> <sup>45</sup>K. Rajkanan, R. Singh, and J. Shewchun, *Solid State Electron.* **22**, 793 (1979). 583
- <sup>565</sup> <sup>46</sup>M. A. Green and M. J. Keevers, *Prog. Photovoltaics: Res. Appl.* **3**, 189 (1995). 584
- <sup>566</sup> <sup>47</sup>H. T. Nguyen, S. C. Baker-Finch, and D. Macdonald, *Appl. Phys. Lett.* **104**, 585 112105 (2014). 586
- <sup>567</sup> <sup>48</sup>P. P. Altermatt, J. Schmidt, G. Heiser, and A. G. Aberle, *J. Appl. Phys.* **82**, 587 4938 (1997). 588
- <sup>568</sup> <sup>49</sup>A. W. Mohamed, A. A. Hadi, and K. M. Jambi, *Swarm Evol. Comput.* **50**, 589 100455 (2019). 590
- <sup>569</sup> <sup>50</sup>E. D. Stokes and T. L. Chu, *Appl. Phys. Lett.* **30**, 425 (1977). 591
- <sup>570</sup> <sup>51</sup>S. Herlufsen, D. Macdonald, K. Bothe, and J. Schmidt, *Phys. Status Solidi RRL* **6**, 1 (2012). 593
- <sup>571</sup> <sup>52</sup>J. Schmidt, K. Bothe, V. V. Voronkov, and R. Falster, *Phys. Status Solidi B* **257**, 594 1900167 (2020). 595
- <sup>572</sup> <sup>53</sup>J. Lagowski, P. Edelman, A. M. Kontkiewicz, O. Milic, W. Henley, M. Dexter, 596 L. Jastrzebski, and A. M. Hoff, *Appl. Phys. Lett.* **63**, 3043 (1993). 597
- <sup>573</sup> <sup>54</sup>L. Kimerling and J. Benton, *Physica B+C* **116**, 297 (1983). 598
- <sup>574</sup> <sup>55</sup>M. J. Aziz, *Mater. Sci. Semicond. Process.* **4**, 397 (2001). 599
- <sup>575</sup> <sup>56</sup>M. Stavola, *Identification of Defects in Semiconductors* (Academic Press, 1998). 600
- <sup>576</sup> <sup>57</sup>E. Weber, *Appl. Phys. A* **30**, 1 (1983). 601
- <sup>577</sup> <sup>58</sup>M. J. Aziz, Y. Zhao, H.-J. Gossmann, S. Mitha, S. P. Smith, and D. Schiferl, *Phys. Rev. B* **73**, 054101 (2006). 602
- <sup>578</sup> <sup>59</sup>B. Ziebarth, M. Mrovec, C. Elsässer, and P. Gumbisch, *Phys. Rev. B* **92**, 115309 604 (2015). 605
- <sup>579</sup> <sup>60</sup>F. Mirzade, *J. Appl. Phys.* **110**, 064906 (2011). 606
- <sup>580</sup> <sup>61</sup>F. K. Mirzade, *J. Appl. Phys.* **103**, 044904 (2008). 607
- <sup>581</sup> <sup>62</sup>R. Peleshchak, O. Kuzyk, and O. Dan'kiv, *Ukr. J. Phys.* **61**, 741 (2016). 608
- <sup>582</sup> <sup>63</sup>V. N. Pavlovich, *Phys. Status Solidi B* **180**, 97 (1993). 609
- <sup>583</sup> <sup>64</sup>V. D. Krevchik, R. A. Muminov, and A. Y. Yafasov, *Phys. Status Solidi A* **63**, 610 K159 (1981). 611
- <sup>584</sup> <sup>65</sup>W. T. Yost and J. H. Cantrell, *Phys. Rev. B* **30**, 3221 (1984). 612
- <sup>585</sup> <sup>66</sup>M.-J. Chen and Y.-M. Sheu, *Appl. Phys. Lett.* **89**, 161908 (2006). 613
- <sup>586</sup> <sup>67</sup>J. Philip and M. A. Breazeale, *J. Appl. Phys.* **52**, 3383 (1981). 614
- <sup>587</sup> <sup>68</sup>P. Baransky, A. Belyaev, S. Komirenko, and N. Shevchenko, *Solid State Phys.* **32**, 2159 (1990). 615
- <sup>588</sup> <sup>69</sup>O. Y. Olikh and I. V. Ostrovskii, *Phys. Solid State* **44**, 1249 (2002). 617
- <sup>589</sup> <sup>70</sup>H. S. Laine, V. Vähäniemi, A. E. Morishige, J. Hofstetter, A. Haarahlitunen, B. Lai, H. Savin, and D. P. Fenning, *IEEE J. Photovoltaics* **6**, 1094 (2016). 619
- <sup>590</sup> <sup>71</sup>V. Vähäniemi, A. Haarahlitunen, H. Talvitie, M. Yli-Koski, and H. Savin, *Prog. Photovoltaics: Res. Appl.* **21**, 1127 (2013). 620
- <sup>591</sup> <sup>72</sup>T. Mchedlidze, C. Möller, K. Lauer, and J. Weber, *J. Appl. Phys.* **116**, 245701 622 (2014). 623