Microwave induced transformation of defect subsystem in SiC and GaAs

Abstract

Text of abstract Text of abstract

Keywords: Microwave, SiC, GaAs, Defect transformation

1. Introduction

It is well known (Kozlovskii et al. (2000); Schrimpf and Fleetwood (2004))

(Kitchen et al. (2014); Zohm et al. (2000); Bhunia and Bose (1998); Bacherikov et al. (2003); Pashkov et al. (1994); Boltovets et al. (2002); Milenin et al. (1994); Belyaev et al. (2002); Ashkinadze et al. (1996); Ermolovich et al. (1998); Belyayev et al. (1998); Bacherikov et al. (2008); Zayats et al. (2015); Belyayev et al. (2012).)

Kitchen et al. (2014); Zohm et al. (2000)

Kitchen et al. (2014)

Kitchen et al. (2014); Bhunia and Bose (1998)

Boltovets et al. (2002); Pashkov et al. (1994); Milenin et al. (1994); Belyaev et al. (2002); Ermolovich et al. (1998); Zayats et al. (2015); Belyayev et al. (2012)

Bacherikov et al. (2003)

Bacherikov et al. (2003); Belyayev et al. (1998); Zayats et al. (2015)

Milenin et al. (1994)

Belyayev et al. (1998)

Bacherikov et al. (2008)

Belyaev et al. (2002); Ermolovich et al. (1998); Belyayev et al. (1998)

2. Experimental details

Boltovets et al. (2002); Milenin et al. (1994); Belyaev et al. (2002); Ashkinadze et al. (1996); Ermolovich et al. (1998)

Ostrovskii et al. (1998); Ostrovskii and Olikh (1998); Gromashevskii et al. (2013); Abbate et al. (1995)

$$V_{\mathrm{TAV}}(t) = V_{\mathrm{TAV},0}\exp(-t/\tau). \quad (1)$$

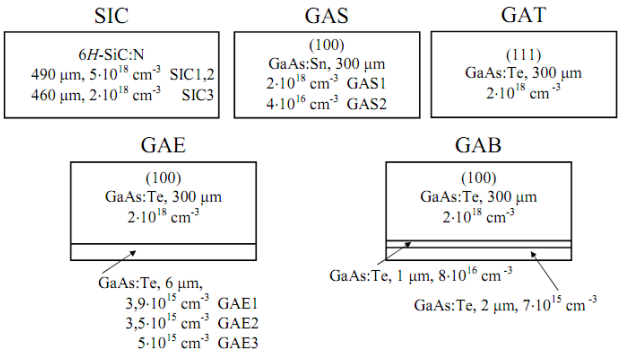

Figure 1: Structure of samples

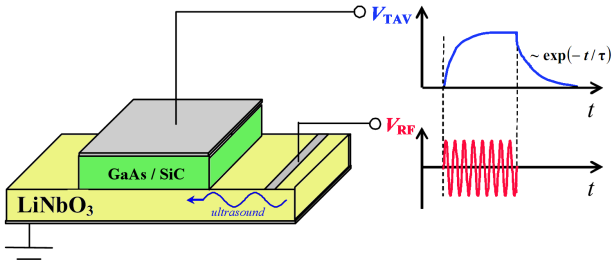

Figure 2: The scheme of TAV measurement. The time dependencies of the radio impulse V_{RF} for the excitation of ultrasound in a piezoelectric plate and the resulting TAV signal V_{TAV} are schematically shown as well.

Ostrovskii et al. (1998); Abbate et al. (1995)

$$\tau = \frac{1}{\sigma_n \, \upsilon_{\mathrm{th},n} \, N_c} \exp\left(\frac{E_c - E_t}{kT}\right). \quad (2)$$

where $\upsilon_{\mathrm{th},n}$ is the electron thermal velocity N_C is the densities of states in the conduction band.

Godwod et al. (1976)

Belyayev et al. (1998)

3. Results and discussion

Pavlović et al. (2000)

Bulyarskii et al. (2000); Makram-Ebeid and Lannoo (1982)

Stellmacher et al. (2001)

Bourgoin and De Angelis (2001)

Bourgoin and De Angelis (2001)

Bourgoin et al. (1988)

Pavlović et al. (2000)

Lebedev (1999); Anikin et al. (1991a,b)

Kuznetsov and Edmond (1997)

Lebedev (1999)

Lebedev (1999)

Anikin et al. (1991a,b)

Lebedev et al. (2000)

Lebedev et al. (2001)

Hemmingsson et al. (1999)

Lebedev et al. (2001)

Kol'chenko and Lomako (1994)

Samoylov et al. (1994)

Vaytkus et al. (1988)

Kol'chenko et al. (1989)

Ermolovich et al. (2007)

Boltovets et al. (2002); Belyayev et al. (2012)

Bacherikov et al. (2003); Pashkov et al. (1994); Boltovets et al. (2002); Milenin et al. (1994); Belyaev et al. (2002)

Zohm et al. (2000)

Fang et al. (1990)

Abbate et al. (1995); Ostrovskii and Olikh (1998); Ostrovskii et al. (1998)

Boltovets et al. (2002); Belyayev et al. (2012)

Yousefi et al. (1995); Mircea and Mitonneau (1975); Bourgoin et al. (1988); Ashby et al. (1976); Fang et al. (1987); Lefèvre and Schulz (1977); Kol'chenko et al. (1989)

References

References

Abbate, A., Ostrovskii, I.V., Han, K.J., Masini, G., Palma, F., Das, P., 1995. Transient acoustoelectric spectroscopy measurements for the characterization of GaAs epilayer structures. Semicond. Sci. Technol. 10, 965–969. doi:10.1088/0268-1242/10/7/011.

Abele, J.C., Kremer, R.E., Blakemore, J.S., 1987. Transient photoconductivity measurements in semi–insulating GaAs. ii. a digital approach. J. Appl. Phys. 62, 2432–2438. doi:10.1063/1.339476.

Anikin, M., Andreyev, A., Lebedev, A., Pyatko, S., Rastegayeva, M., Savkina, N., Strel'chuk, A., Syrkin, A., Chelnokov, V., 1991a. High temperature Schottky diode Au-SiC-6H. Fizika i tekhnika poluprovodnikov 25, 328–333. (in Russian).

Anikin, M., Zubrilov, A., Lebedev, A., Strel'chuk, A., Cherenkov, A., 1991b. Recombination processes in 6H–SiCp–n–structures and the influence of deep centers. Fizika i tekhnika poluprovodnikov 25, 479–486. (in Russian).

Ashby, A., Roberts, G., Ashen, D., Mullin, J., 1976. Non-extrinsic conduction in semi-insulating gallium arsenide. Solid State Commun. 20, 61–63. doi:10.1016/0038-1098(76)91699-9.

Ashkinadze, B., Cohen, E., Ron, A., Linder, E., Pfeiffer, L., 1996. The effects of photogenerated free carriers and microwave electron heating on exciton dynamics in gaasalgaas quantum wells. Solid-State Electron. 40, 561–565. doi:10.1016/0038-1101(95)00290-1.

Bacherikov, Y., Konakova, R., Milenin, V., Okhrimenko, O., Svetlichnyi, A., Polyakov, V., 2008. Changes in characteristics of gadolinium, titanium, and erbium oxide films on the sic surface under microwave treatment. Semiconductors 42, 868–872. doi:10.1134/S106378260807019.

Bacherikov, Y.Y., Konakova, R.V., Kocherov, A.N., Lytvyn, P.M., Lytvyn, O.S., Okhrimenko, O.B., Svetlichnyi, A.M., 2003. Effect of microwave annealing on silicon dioxide/silicon carbide structures. Technical Physics 48, 598–601. doi:10.1134/1.1576474.

Belyaev, A., Venger, E., Ermolovich, I., Konakova, R., Lytvyn, P., Milenin, V., Prokopenko, I., Svechnikov, G., Soloviev, E., Fedorenko, L., 2002. Effect of microwave and laser radiations on the parameters of semiconductor structures. Intac, Kyiv.

Table 1: The determined parameters of defects in the samples *n*–GaAs and *n*–6*H*–SiC samples

Sample	t_{MWT}, s	Level	$(E_c - E_t)$, eV	σ_n, cm^2 [a)]	R_{cur}, m	ξ_{cur}
SIC1	0	ESC1	0.33 ± 0.01	$(7 \pm 4) \cdot 10^{-18}$	∞	0
	20	ESC1	0.33 ± 0.01	$(5 \pm 3) \cdot 10^{-19}$	170.2	$8.7 \cdot 10^{-7}$
	40	ESC2	0.26 ± 0.01	$(2 \pm 1) \cdot 10^{-19}$		
	80		weak signal			-
SIC2	0	ESC1	0.33 ± 0.01	$(7 \pm 4) \cdot 10^{-18}$	> 2000	$< 1.2 \cdot 10^{-7}$
	20	ESC1	0.33 ± 0.01	$(5 \pm 3) \cdot 10^{-19}$	171.9	$1.4 \cdot 10^{-6}$
SIC3	0	ESC1	0.34 ± 0.02	$(3 \pm 2) \cdot 10^{-18}$	3.8	$6.1 \cdot 10^{-5}$
	20	ESC2	0.29 ± 0.01	$(5 \pm 3) \cdot 10^{-19}$	5.5	$4.2 \cdot 10^{-5}$
	40	ESC2	0.26 ± 0.01	$(10 \pm 7) \cdot 10^{-20}$		
	80	ESC2	0.23 ± 0.01	$(6 \pm 4) \cdot 10^{-20}$		-
GAS1	0	EGA1	0.32 ± 0.02	$(3 \pm 2) \cdot 10^{-17}$	-53.8	$-2.8 \cdot 10^{-6}$
	20	EGA1	0.31 ± 0.01	$(2 \pm 1) \cdot 10^{-17}$	22.9	$6.5 \cdot 10^{-6}$
	40		weak signal			-
GAS2	0	EGA1	0.32 ± 0.01	$(4 \pm 2) \cdot 10^{-17}$	17.2	$8.7 \cdot 10^{-6}$
	20	EGA2	0.28 ± 0.01	$(5 \pm 2) \cdot 10^{-18}$	14.7	$1.0 \cdot 10^{-5}$
	40		weak signal			
GAT	0	EGA3	0.49 ± 0.02	$(5 \pm 3) \cdot 10^{-14}$		
	20	EGA4	0.40 ± 0.02	$(2 \pm 1) \cdot 10^{-15}$		
GAE1	0	EGA5	0.24 ± 0.01	$(2 \pm 1) \cdot 10^{-18}$		
	60	EGA2	0.29 ± 0.01	$(10 \pm 6) \cdot 10^{-18}$		
GAE2	0	EGA5	0.25 ± 0.01	$(2 \pm 1) \cdot 10^{-18}$		
	60	EGA2	0.30 ± 0.01	$(2 \pm 1) \cdot 10^{-17}$		
GAE3	0	EGA6	0.43 ± 0.01	$(8 \pm 5) \cdot 10^{-17}$		-
	60	EGA6	0.46 ± 0.02	$(7 \pm 4) \cdot 10^{-16}$		
GAB1	0	EGA4	0.39 ± 0.01	$(10 \pm 7) \cdot 10^{-18}$		
	20	EGA4	0.39 ± 0.01	$(4 \pm 2) \cdot 10^{-17}$		
	40	EGA6	0.43 ± 0.02	$(10 \pm 6) \cdot 10^{-17}$		
GAB2	0	EGA4	0.40 ± 0.01	$(10 \pm 6) \cdot 10^{-17}$		
	20	EGA4	0.41 ± 0.01	$(10 \pm 6) \cdot 10^{-17}$		
	40	EGA6	0.45 ± 0.02	$(4 \pm 2) \cdot 10^{-16}$		

[a)] *at* $T = 300$ *K for SIC, GA, GAE and at* $T = 340$ *K for GAB*

Table 2: Literature data for levels closed to the location of detected levels

$(E_c - E_t)$, eV	σ_n, cm^2	configuration	method [a)]	epi–structure	Reference
		EGA1, $(E_c - E_t) = (0.31 \div 0.32)$ eV			
0.33	-	complex with V_{As}	DLTS	no	Richter et al. (2000)
0.33	-	-	DLTS	no	Neild et al. (1991)
$0.31 \div 0.33$	-	V_{As}		no	Schultz (2015)
0.33	$1 \cdot 10^{-17}$	-	TSC	no	Pavlović et al. (2000)
0.323	$1 \cdot 10^{-14}$	-	DLTS	yes	Yousefi et al. (1995)
0.334	$2 \cdot 10^{-15}$		DLTS	yes	Yousefi et al. (1995)
0.35	-	complex with V_{As}	PA	no	Kuisma et al. (1997)
$0.315 \div 0.325$	$3 \cdot 10^{-17}$	-	TSC	no	Pavlović and Desnica (1998)
0.33	-	-	TSC	no	Tomozane and Nannichi (1986)
$0.30 \div 0.33$	-	-	DLTS	no	Lang et al. (1976)
		EGA2, $(E_c - E_t) = (0.28 \div 0.30)$ eV			
0.28	$5 \cdot 10^{-18}$	$V_{As}As_i$	TSC	no	Pavlović et al. (2000)
0.26	$3.5 \cdot 10^{-15}$	-	DLTS	yes	Yousefi et al. (1995)
0.277	$5 \cdot 10^{-17}$	-	TSC	no	Pavlović and Desnica (1998)
0.284	$1 \cdot 10^{-17}$	-	TSC	no	Pavlović and Desnica (1998)
0.28	-	intrinsic	TP	no	Abele et al. (1987)
0.28	$8 \cdot 10^{-15}$	-	DLTS	yes	Mircea and Mitonneau (1975)
0.30	-	complex with Te	DLTS	no	Kol'chenko and Lomako (1994)
0.30	$6 \cdot 10^{-15}$	$V_{As}As_i$	DLTS	no	Pons and Bourgoin (1985)
		EGA3, $(E_c - E_t) = 0.49$ eV			
0.50	-	Sb_{Ga}	DLTS	no	Samoylov et al. (1994)
0.48	$4 \cdot 10^{-16}$	As_{Ga}^{++}	TSC	no	Pavlović et al. (2000)
0.485	$2 \cdot 10^{-16}$	-	TSC	no	Pavlović and Desnica (1998)
0.48	-	impurity	TP	no	Abele et al. (1987)
0.51	$1 \cdot 10^{-12}$	-	DLTS	no	Martin et al. (1977)
0.48	$3 \cdot 10^{-13}$	-	DLTS	no	Lang et al. (1976)
0.50	$1 \cdot 10^{-15}$	V_{As}, $V_{Ga}Ga_iV_{As}$	DLTS	no	Pons and Bourgoin (1985)
		EGA4, $(E_c - E_t) = (0.39 \div 0.41)$ eV			
0.42	-	-	DLTS	no	Neild et al. (1991)
0.41	-	$V_{Ga}V_{As}$	DLTS	no	Samoylov et al. (1994)
0.39	-	$V_{Ga}Ga_{As}$	TSC	no	Fang et al. (1990)
0.41	$2 \cdot 10^{-13}$	-	DLTS	yes	Bourgoin et al. (1988)
0.40	-	-	SCRC	yes	Ashby et al. (1976)
0.37	$2 \cdot 10^{-14}$	-	DLTS	yes	Fang et al. (1987)
0.40	-	$V_{Ga}Ga_{As}$	DLTS	no	Vaytkus et al. (1988)
0.387	$2 \cdot 10^{-14}$	-	DLTS	yes	Yousefi et al. (1995)
		EGA5, $(E_c - E_t) = (0.24 \div 0.25)$ eV			
0.23	-	-	DLTS	no	Neild et al. (1991)
0.23	$2 \cdot 10^{-17}$	-	TSC	no	Pavlović et al. (2000)
$0.22 \div 0.25$	$8 \cdot 10^{-19}$	-	TSC	no	Lin et al. (1976)
0.26	-	complex with V_{Ga}	TSC	no	Fang et al. (1990)
0.24	-	-	TSC	no	Tomozane and Nannichi (1986)
0.23	-	intrinsic	TP	no	Abele et al. (1987)
0.23	-	$V_{Ga}V_{As}$	DLTS	no	Morrow (1991)
0.23	$1 \cdot 10^{-14}$	$V_{Ga}V_{As}$	DLTS	no	Bourgoin et al. (1988)
0.23	$7 \cdot 10^{-15}$	-	DLTS	yes	Mircea and Mitonneau (1975)
0.22	$2 \cdot 10^{-15}$	-	DLTS	no	Fang et al. (1987)
0.258	$4 \cdot 10^{-16}$	-	DLTS	yes	Yousefi et al. (1995)
		EGA6, $(E_c - E_t) = (0.43 \div 0.46)$ eV			
0.44	$1 \cdot 10^{-14}$	$V_{As}As_i$, V_{As}	TSC	no	Pavlović et al. (2000)
0.44	$9 \cdot 10^{-15}$	-	TSC	no	Pavlović and Desnica (1998)
0.43	$7 \cdot 10^{-16}$	intrinsic	DLTS	yes	Lefèvre and Schulz (1977) Bourgoin et al. (1988)
0.44	$2 \cdot 10^{-15}$	complex with V_{As}	DLTS	yes	Kol'chenko et al. (1989)

[a)] *DLTS — deep level transient spectroscopy*

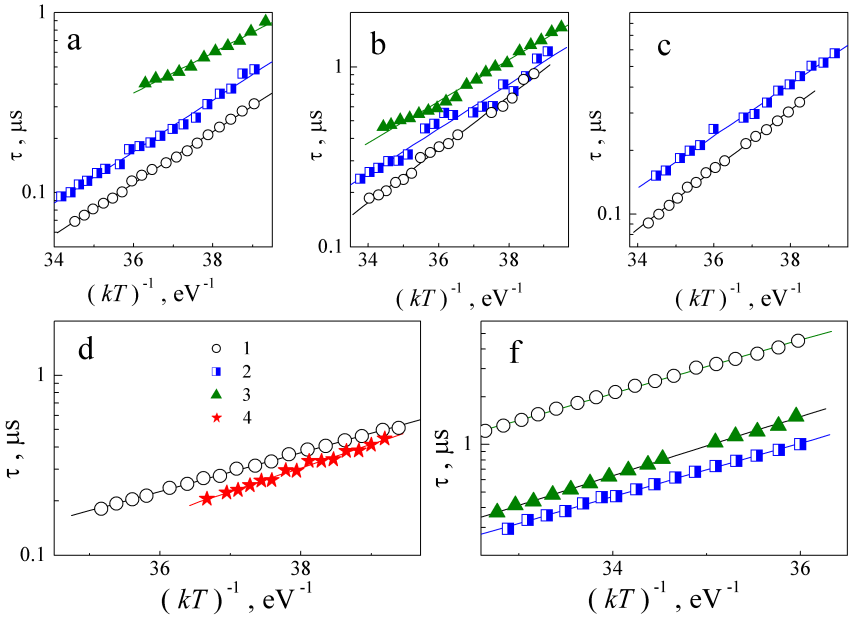

Figure 3: Dependences of TAV relaxation time on inverse temperature for samples SIC2 (a), SIC3 (b), GAS2 (c), GAE2 (d) and GAB1 (e) before and after MWT. t_{MWT}, c: 0 (curves 1), 20 (2), 40 (3), 60 (4)

Belyayev, A., Belyayev, A., Yermolovich, I., Komirenko, S., Konakova, R., Lyapin, V., Milenin, V., Solov'ev, E., Shevelev, M., 1998. Influence of microwave treatment on the electrophysical characteristics of technically important semiconductors and surface-barrier structures. Technical Physics 43, 1445–1449. doi:10.1134/1.1259222.

Belyayev, A., Sachenko, A., Boltovets, N., Ivanov, V., Konakova, R., Kudryk, Y., Matveeva, L., Milenin, V., Novitskii, S., Sheremet, V., 2012. Effect of microwave irradiation on the resistance of au–tib$_x$–ge–au–n–n$^+$–n^{++}–GaAs(InP) ohmic contacts. Semiconductors 46, 541–544. doi:10.1134/S1063782612040021.

Bhunia, S., Bose, D., 1998. Microwave synthesis, single crystal growth and characterization of znte. J. Cryst. Growth 186, 535–542. doi:10.1016/S0022-0248(97)00814-2.

Boltovets, N.S., Kamalov, A.B., Kolyadina, E.Y., Konakova, R.V., Lytvyn, P.M., Lytvyn, O.S., Matveeva, L.A., Milenin, V.V., Rengevych, O.E., 2002. Microwave-stimulated relaxation of internal strains in gaas-based device heterostructures. Technical Physics Letters 28, 154–156. doi:10.1134/1.1458520.

Bourgoin, J.C., von Bardeleben, H.J., Stiévenard, D., 1988. Native defects in gallium arsenide. J. Appl. Phys. 64, R65–R92. doi:10.1063/1.341206.

Bourgoin, J.C., De Angelis, N., 2001. The defect responsible for non–radiative recombination in GaAs materials. Semicond. Sci. Technol. 16, 497–501. doi:10.1088/0268-1242/9/2/005.

Bulyarskii, S., Grushko, N., Zhukov, A., 2000. Field dependence of the rate of thermal emission of holes from the $V_{Ga}S_{As}$ complex in gallium arsenide. Semiconductors 34, 40–44. doi:10.1134/1.1187958.

Ermolovich, I., Milenin, G., Milenin, V., Konakova, R., Red'ko, R., 2007. Modification of the defect structure in binary semiconductors under the action of microwave radiation. Technical Physics 77, 1173–1177. doi:10.1134/S1063784207090113.

Ermolovich, I.B., Venger, E.F., Konakova, R.V., Milenin, V.V., Svechnikov, S.V., Sheveljev, M.V., 1998. Photoluminescent investigations of shf irradiation effect on defect states in gaas:sn(te) and inp crystals. Proc. SPIE 3359, 265–272. doi:10.1117/12.306225.

Fang, Z., Shan, L., Schlesinger, T., Milnes, A., 1990. Study of defects in LEC–grown undoped SI–GaAs by thermally stimulated current spectroscopy. Materials Science and Engineering: B 5, 397–408. doi:10.1016/0921-5107(90)90104-J.

Fang, Z.Q., Schlesinger, T.E., Milnes, A.G., 1987. Evidence for EL6 (e_c – 0.35 eV) acting as a dominant recombination center in n–type horizontal Bridgman GaAs. J. Appl. Phys. 61, 5047–5050. doi:10.1063/1.338327.

Godwod, K., Nagy, A.T., Rek, Z., 1976. The application of the x–ray triple–crystal spectrometer for measuring the radius of curvature of bent single crystals. Phys. Status Solidi A 34, 705–710. doi:10.1002/pssa.2210340235.

Gromashevskii, V., Tatyanenko, N., Snopok, B., 2013. Application of the transverse acoustoelectric effect to studying silicon surface charging upon water adsorption. Semiconductors 47, 579–585. doi:10.1134/S106378261304009X.

Hemmingsson, C.G., Son, N.T., Janzén, E., 1999. Observation of negative–U centers in 6H silicon carbide. Appl. Phys. Lett. 74, 839–841. doi:10.1063/1.123401.

Kitchen, H.J., Vallance, S.R., Kennedy, J.L., Tapia-Ruiz, N., Carassiti, L., Harrison, A., Whittaker, A.G., Drysdale, T.D., Kingman, S.W., Gregory, D.H., 2014. Modern microwave methods in solid-state inorganic materials chemistry: From fundamentals to manufacturing. Chem. Rev. 114, 1170–1206. doi:10.1021/cr4002353.

Kol'chenko, T., Lomako, V., 1994. New metastable center in irradiated GaAs. Fizika i tekhnika poluprovodnikov 28, 857–860. (in Russian).

Kol'chenko, T., Lomako, V., Rodionov, A., Sveshnikov, Y., 1989. Features of defect formation in epitaxial gallium arsenide, which is containing isovalent indium impurity. Fizika i tekhnika poluprovodnikov 23, 626–629. (in Russian).

Kozlovskii, V.V., Kozlov, V.A., Lomasov, V.N., 2000. Modification of semiconductors with proton beams. a review. Semiconductors 34,

123–140. doi:10.1134/1.1187921.

Kuisma, S., Saarinen, K., Hautojärvi, P., Fang, Z.Q., Look, D., 1997. Microscopic nature of thermally stimulated current and electrical compensation in semi–insulating GaAs. J. Appl. Phys. 81, 3512–3521. doi:10.1063/1.364705.

Kuznetsov, N., Edmond, J., 1997. Effect of deep levels on current excitation in 6H–SiC diodes. Semiconductors 31, 1049–1052. doi:10.1134/1.1187023.

Lang, D.V., Cho, A.Y., Gossard, A.C., Ilegems, M., Wiegmann, W., 1976. Study of electron traps in n–GaAs grown by molecular beam epitaxy. J. Appl. Phys. 47, 2558–2564. doi:10.1063/1.322974.

Lebedev, A., Davydov, D., Tregubova, A., Bogdanova, E., Shcheglov, M., Pavlenko, M., 2001. Effect of structural imperfection on the spectrum of deep levels in 6H–SiC. Semiconductors 35, 1372–1374. doi:10.1134/1.1427973.

Lebedev, A., Veinger, A., Davydov, D., Kozlovskii, V., Savkina, N., Strel'chuk, A., 2000. Radiation defects in n–6H–SiC irradiated with 8 MeV protons. Semiconductors 34, 861–866. doi:10.1134/1.1188089.

Lebedev, A.A., 1999. Deep level centers in silicon carbide: A review. Semiconductors 33, 107–130. doi:10.1134/1.1187657.

Lefèvre, H., Schulz, M., 1977. Double correlation technique (DDLTS) for the analysis of deep level profiles in semiconductors. Applied physics 12, 45–53. doi:10.1007/BF00900067.

Lin, A.L., Omelianovski, E., Bube, R.H., 1976. Photoelectronic properties of high–resistivity GaAs:O. J. Appl. Phys. 47, 1852–1858. doi:10.1063/1.322904.

Makram-Ebeid, S., Lannoo, M., 1982. Quantum model for phonon–assisted tunnel ionization of deep levels in a semiconductor. Phys. Rev. B 25, 6406–6424. doi:10.1103/PhysRevB.25.6406.

Martin, G.M., Mitonneau, A., Mircea, A., 1977. Electron traps in bulk and epitaxial gaas crystals. Electronics Letters 13, 191–193. doi:10.1049/el:19770140.

Milenin, V., Konakova, R., Statov, V., Sklyarevich, V., Tkhorik, Y., Filatov, M., Shevelev, M., 1994. Physicochemical processes at the interface of contacts Au/Pt/Cr/Pt/GaAs, subjected to microwave annealing. Pis'ma v zhurnal tekhnicheskoy fiziki 20, 32–36. (in Russian).

Mircea, A., Mitonneau, A., 1975. A study of electron traps in vapour–phase epitaxial GaAs. Applied physics 8, 15–21. doi:10.1007/BF00883664.

Morrow, R.A., 1991. In–diffusing divacancies as sources of acceptors in thermally annealed GaAs. J. Appl. Phys. 69, 3396–3398. doi:10.1063/1.348519.

Neild, S.T., Skowronski, M., Lagowski, J., 1991. Signature of the gallium–oxygen–gallium defect in GaAs by deep level transient spectroscopy measurements. Appl. Phys. Lett. 58, 859–861. doi:10.1063/1.104513.

Ostrovskii, I., Olikh, O., 1998. Characterization of interface deep levels in as vapor grown epi–GaAs. Solid State Commun. 107, 341–343. doi:https://doi.org/10.1016/S0038-1098(98)00236-1.

Ostrovskii, I.V., Saiko, S.V., Walther, H.G., 1998. Determination of deep levels' parameters in epi–GaAs by a transient acoustoelectric technique. J. Phys. D: Appl. Phys. 31, 2319–2325. doi:10.1088/0022-3727/31/18/018.

Pashkov, V., Perevoshchikov, V., Skupov, V., 1994. Influence of annealing in a microwave radiation field on the residual deformation and impurity composition of near-surface silicon layers. Pis'ma v zhurnal tekhnicheskoy fiziki 20, 14–18. (in Russian).

Pavlović, M., Desnica, U.V., 1998. Precise determination of deep trap signatures and their relative and absolute concentrations in semi-insulating GaAs. J. Appl. Phys. 84, 2018–2024. doi:10.1063/1.368258.

Pavlović, M., Desnica, U.V., Gladić, J., 2000. Complete set of deep traps in semi–insulating gaas. J. Appl. Phys. 88, 4563–4570. doi:10.1063/1.1308072.

Pons, D., Bourgoin, J.C., 1985. Irradiation–induced defects in GaAs. J. Phys. C: Solid State Phys. 18, 3839–3871. doi:10.1088/0022-3719/18/20/012.

Richter, T., Kühnel, G., Siegel, W., Niklas, J.R., 2000. Activation energies of the EL6 trap and of the 0.15 eV donor and their correlation in GaAs. Semicond. Sci. Technol. 15, 1039–1044. doi:10.1088/0268-1242/15/11/305.

Samoylov, V.A., Yakusheva, N.A., Prints, V.Y., 1994. Effect of an isovalent antimony impurity on the formation of electrically active cents in *n*–GaAs obtained by liquid-phase epitaxy from a bismuth melt. Fizika i tekhnika poluprovodnikov 28, 1617–1626. (in Russian).

Schrimpf, R.D., Fleetwood, D.M., 2004. Radiation Effects and Soft Errors in Integrated Circuits and Electronic Devices. World Scientific. doi:10.1142/5607.

Schultz, P.A., 2015. The e 1—e 2 center in gallium arsenide is the divacancy. J. Phys.: Condens. Matter 27, 075801. doi:10.1088/0953-8984/27/7/075801.

Stellmacher, M., Bisaro, R., Galtier, P., Nagle, J., Khirouni, K., Bourgoin, J.C., 2001. Defects and defect behaviour in GaAs grown at low temperature. Semicond. Sci. Technol. 16, 440–446. doi:10.1088/0268-1242/16/6/304.

Tomozane, M., Nannichi, Y., 1986. Improved thermally stimulated current spectroscopy to characterize levels in semi–insulating GaAs. Japanese Journal of Applied Physics 25, L273–L275. doi:10.1143/JJAP.25.L273.

Vaytkus, Y., Storasta, Y., Pintsevichyus, A., Pyatrauskas, M., Kazhukauskas, V., 1988. Determination of the parameters of deep centers in semi-insulating GaAs from the relaxation of photoconductivity under laser excitation. Litovskiy fizicheskiy sbornik 28, 744–751. (in Russian).

Yousefi, G.H., Webb, J.B., Rousina, R., Khanna, S.M., 1995. Electron irradiation induced defects and schottky diode characteristics for metalorganic vapor phase epitaxy and molecular beam epitaxial n–GaAs. J. Electron. Mater. 24, 15–20. doi:10.1007/BF02659720.

Zayats, N.S., Konakova, R.V., Milenin, V.V., Milenin, G.V., Red'ko, R.A., Red'ko, S.N., 2015. Microwave-radiation-induced structural transformations in homo- and heterogeneous gaas-based systems. Technical Physics 60, 432–436. doi:10.1134/S1063784215030299.

Zohm, H., Kasper, E., Mehringer, P., Müller, G., 2000. Thermal processing of silicon wafers with microwave co-heating. Microelectron. Eng. 54, 247–253. doi:10.1016/S0167-9317(00)00413-5.