

A physically based predictive model of Si/SiO₂ interface trap generation resulting from the presence of holes in the SiO₂

P. M. Lenahan and J. F. Conley Jr.

Citation: [Applied Physics Letters](#) **71**, 3126 (1997); doi: 10.1063/1.120284

View online: <http://dx.doi.org/10.1063/1.120284>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/apl/71/21?ver=pdfcov>

Published by the [AIP Publishing](#)

Articles you may be interested in

[Charge trapping properties at silicon nitride/silicon oxide interface studied by variable-temperature electrostatic force microscopy](#)

J. Appl. Phys. **100**, 023711 (2006); 10.1063/1.2218025

[Characterization of multiple Si/SiO₂ interfaces in silicon-on-insulator materials via second-harmonic generation](#)

Appl. Phys. Lett. **85**, 3095 (2004); 10.1063/1.1807011

[Frequency characterization and modeling of interface traps in HfSi_xO_y/HfO₂ gate dielectric stack from a capacitance point-of-view](#)


Appl. Phys. Lett. **81**, 3392 (2002); 10.1063/1.1518561

[Oxidation-induced traps near SiO₂/SiGe interface](#)

J. Appl. Phys. **86**, 1542 (1999); 10.1063/1.370927

[Electrical and physical characterization of deuterium sinter on submicron devices](#)

Appl. Phys. Lett. **72**, 1721 (1998); 10.1063/1.121163

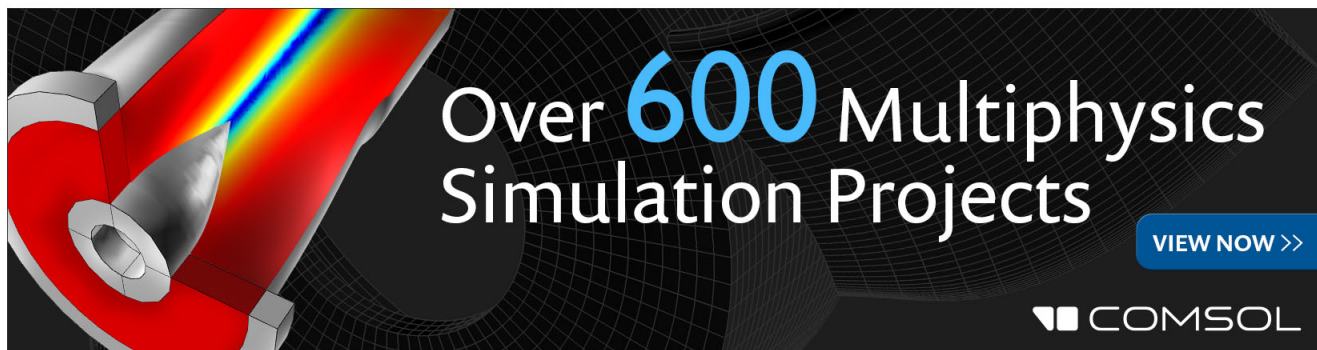The advertisement features a 3D simulation of a mechanical part with a red and yellow stress distribution. The text "Over 600 Multiphysics Simulation Projects" is prominently displayed in white and blue. A blue button with the text "VIEW NOW >>" is located to the right. The COMSOL logo is in the bottom right corner.

Over 600 Multiphysics Simulation Projects

[VIEW NOW >>](#)

COMSOL

A physically based predictive model of Si/SiO₂ interface trap generation resulting from the presence of holes in the SiO₂

P. M. Lenahan^{a)}

The Pennsylvania State University, Department of Engineering Science and Mechanics, University Park, Pennsylvania 16802

J. F. Conley, Jr.^{b)}

Dynamics Research Corporation, Commercial Systems, 19545 NW Von Neumann Drive, Suite 130, Beaverton, Oregon 97006

(Received 18 August 1997; accepted for publication 26 September 1997)

A physically based model is developed which explains apparently unrelated aspects of the Si/SiO₂ interface trap generation process; the predictions of the model are in at least semiquantitative agreement with observations previously reported in the literature. The model involves interactions between molecular hydrogen and trivalent silicon dangling bond defects in the oxide (*E'* centers) and at the Si/SiO₂ interface (*P_b* centers). Our model is primarily directed at interface trap generation caused by ionizing radiation and by hot hole injection phenomena observed in short channel transistors. © 1997 American Institute of Physics. [S0003-6951(97)03747-9]

Although the Si/SiO₂ interface trap generation phenomenon has been intensively investigated for over 30 years,^{1–8} a fundamental physical understanding of the process has yet to emerge. However, some aspects of the phenomena can be described with considerable assurance. Interface trap defects are created when charge carriers are introduced to the amorphous SiO₂ film above the silicon.^{1–8} (Holes are many orders of magnitude more effective in this process than are electrons; however electrons may also have a role under some circumstances.⁴) Many studies indicate that a hydrogen species is involved^{5–12} and that some interaction of a hole in the oxide and a hydrogen species triggers the interface trap generation process.

Electron spin resonance (ESR) measurements by several independent groups have shown that the generation of silicon “dangling bond” defects called *P_b* centers accompanies the interface trap formation process^{13–18} and that there is an approximate one-to-one correspondence between the density of *P_b* centers and the density of interface traps created during the process.^{13,15,17} Since the *P_b* centers defects are clearly interface trap defects with two broad levels in the silicon band gap,^{14,15,19,20} one may reasonably conclude that they dominate interface trap generation.

Recently, Conley *et al.*^{11,12} demonstrated a link between the interface trap generation and a second silicon dangling bond defect, this one in the oxide. The oxide defects are called *E'* centers and involve an unpaired electron residing on a dangling bond of a silicon back-bonded to three oxygens. The dangling bond orbital “points” toward a positively charged silicon. The defect is thus a hole trapped at an oxygen vacancy. ESR studies by at least four independent groups indicate that the *E'* center dominates oxide hole trapping in quite a wide variety of oxides.^{15,17,18,21–23}


Conley *et al.*^{11,12} showed that *E'* centers in oxide films on silicon react rapidly at room temperature with molecular hydrogen, H₂. In their study, about 25% of the *E'* centers

disappeared as about an equal number of hydrogen complexed *E'* centers (which we term *E'H*) appeared; the loss in *E'* density was accompanied by an approximately equivalent gain in interface trap density. No increase in interface trap density occurred with H₂ exposure if the positively charged *E'* centers were absent. It is interesting to note that Mrstik and Rendell¹⁰ have reported electrical measurements showing that an increase in interface trap density was accompanied by a roughly equivalent 25% decrease in oxide trapped holes when previously irradiated SiO₂ films were exposed to H₂ at room temperature. These observations are significant because when SiO₂ is subjected to ionizing radiation, atomic hydrogen is created; above 110 °K it very rapidly dimerizes leaving behind H₂ in the oxide.²⁴

It is well established that silicon dangling bond sites at the Si/SiO₂ interface (*P_b* centers) are passivated by hydrogen.^{25,26} We assume, as have many others, that the interface trap creation process involves the breaking of silicon-hydrogen bonds at *P_b* center precursor sites at the Si/SiO₂ interface; the precursor site will be termed *P_bH*.

The linkage between *E'* centers, *P_b* centers, and H₂ is key to understanding the interface trap generation process.

We propose a reaction of the following form:



In this reaction, H₂ plays the formal role of a catalyst. When a hole drifting to an *E'* precursor site is captured, a positively charged silicon dangling bond site (*E'* center) is created, which, as Conley *et al.*^{11,12} have shown, can react with radiolytic H₂ to form a complex which we term *E'H*. After irradiation, the H₂ is eventually dissipated, but for a short time the system will approach equilibrium. Elementary statistical mechanics tells us that, if the system were to reach equilibrium, one could write²⁷

$$\frac{[P_b][E'\text{H}]}{[P_b\text{H}][E']} = K, \quad (2)$$

$$\text{where } K = \exp\left(\frac{-\Delta G}{kT}\right). \quad (3)$$

^{a)}Electronic mail: pmlesm@engr.psu.edu

^{b)}Electronic mail: jconley@stt3.com

Here ΔG is the difference in Gibbs free energy of the reactants and products. Since expression (1) involves the transfer of a hydrogen atom from a silicon at the interface (P_b) to a silicon in the oxide (E'), one would reasonably conclude that ΔG is small. Thus, $K \approx 1$, at least within about an order of magnitude.

In order to solve Eq. (2) for ΔP_b , the concentration of P_b centers eventually generated after the interface trap formation process is complete, we define the initial (prestress) P_b concentration to be P_{bi} , the initial (prestress) P_bH concentration to be $(P_bH)_i$, and the density of E' trapped holes present immediately after irradiation (and immediately after all the holes which were not trapped are swept from the oxide) to be E'_i .

With these definitions, Eq. (2) becomes

$$\frac{[P_{bi} + \Delta P_b][\Delta P_b]}{[(P_bH)_i - \Delta P_b][E'_i - \Delta P_b]} = K. \quad (4)$$

In Eq. (4), we take the number of $E'H$ complex sites created to be equal to the number of P_b sites created.¹² Assuming it captures the essential physics of the process, Eq. (4) should allow us to predict the interface trap generation behavior in a wide range of oxides.

Suppose we first consider the technologically important situation in which we initially have an excellent Si/SiO₂ interface with a very low interface trap density and thus a very low P_b density. In this case $P_{bi} \approx 0$. At low dose $[\Delta P_b \ll (P_bH)_i]$, Eq. (4) becomes

$$\frac{[\Delta P_b][\Delta P_b]}{(P_bH)_i(E'_i - \Delta P_b)} \approx K. \quad (5)$$

This expression yields

$$\Delta P_b \approx \frac{K}{2} (P_bH)_i \{ (1 + 4E'_i/[K(P_bH)_i])^{1/2} - 1 \}. \quad (6)$$

For a low level of initial E'_i generation ΔP_b will be almost equal (always slightly less than) the initial E'_i density. Thus, if we were to flood a very good oxide with a small number of holes, suppress the interface trap generation process, measure the initial trapped hole concentration, and then allow interface trap generation to proceed, we would expect that the eventual interface trap density (each P_b has two levels) would be roughly equal to the initial trapped hole density.

The generation of interface traps *can* be suppressed for hours by lowering the temperature of the system;²⁸ warming to room temperature allows the process to proceed. Many years ago, Hu and Johnson²⁸ subjected good oxide/silicon devices to relatively low levels of hole flooding at temperatures low enough to temporarily suppress interface trap generation. Initial oxide hole densities were evaluated, then interface traps allowed to generate, and those interface trap densities were also evaluated. As Eq. (6) predicts, Hu and Johnson found that the initial oxide hole density was approximately equal to the eventual interface trap density.

There are other semiquantitative aspects of this model which are in agreement with results in the literature.^{5-10,12,18,21,29}

- (1) Expression (6) shows that ΔP_b should be sublinear in E'_i . Since E'_i generation should itself be sublinear in dose,³⁰ our model predicts a sublinear buildup of interface sites with dose. Such behavior is widely reported.²⁹
- (2) The model predicts that in devices with low initial interface trap density, the hole trapping and interface trap generation, P_b generation and E' generation would approximately scale together. This behavior (both cases) has been observed.²¹
- (3) Since the model involves interaction of a trapped hole site with molecular hydrogen triggering a reaction at a Si/SiO₂ interface P_bH site, one would expect that the time involved in interface trap generation would be significantly increased by reversing the irradiation bias from positive gate voltage to negative gate voltage. This behavior is consistently observed.⁵⁻⁸
- (4) Since the E' center precursors (oxygen vacancies) are intrinsic defects, one would expect that their number would be an exponential function of processing temperature. Thus one would expect a strong increase in interface trap generation with increasing temperature of gate oxide processing. This behavior is observed.²¹
- (5) Radiolytic, molecular hydrogen will be rapidly dissipated from the oxide; in some cases this will not allow equilibrium densities of P_b interface traps to be achieved. One would thus expect that post irradiation exposure to a molecular hydrogen ambient generally increases interface trap density. This behavior is observed.^{9,10,12}
- (6) Consider a metal-oxide-semiconductor device in which the oxide has been flooded with holes for a brief period. If a positive voltage was applied to the gate electrode, E' precursors near the Si/SiO₂ boundary would be populated with holes: if a negative voltage was applied, E' precursors near the gate (usually polycrystalline Si)/SiO₂ boundary would be similarly populated. Our model, at least to zero order, predicts a similar radiation response, in that the eventual number of P_b centers created would be the same with either sign of gate bias during irradiation. (This assumes equal E' precursor density at both interfaces.) Experimental work indeed shows this to be the case "electrically" for brief bursts of irradiation *provided* that the oxide bias is positive *after* the irradiation.⁸ (That is, the eventual interface state densities generated are approximately equal for both cases.)
- (7) Briefly consider the technologically irrelevant case of a very high initial interface trap density and a very high initial P_b density. In such a case we would expect a reaction of the following form:



Thus, the model would clearly predict an initial post irradiation *decrease* in P_b density for Si/SiO₂ structures with quite high initial P_b density. This behavior has been reported.¹⁸

A particularly useful aspect of the model is its prediction of a quantitative relationship between P_b and E' generation. Recently Lenahan and Conley developed a model which allows a quantitative prediction of E' densities based on processing parameters.³⁰

By combining the Conley/Lenahan E' model with Eq. (6) one should, on the basis of processing parameters, be able to predict *both* radiation induced interface trap densities and radiation induced oxide charging.

The portion of this work performed at The Pennsylvania State University was funded by Dynamics Research Corporation.

- ¹R. J. Powell and G. F. Derbenwick, IEEE Trans. Nucl. Sci. **18**, 99 (1971).
- ²P. S. Winokur, H. E. Boesch, Jr., J. M. McGarrity, and F. B. McLean, J. Appl. Phys. **50**, 3492 (1979).
- ³T. P. Ma, G. A. Scoggan, and R. Leone, Appl. Phys. Lett. **27**, 61 (1975).
- ⁴S. K. Lai and D. R. Young, J. Appl. Phys. **52**, 6231 (1981).
- ⁵F. B. McLean, IEEE Trans. Nucl. Sci. **27**, 1651 (1980).
- ⁶J. M. McGarrity, P. S. Winokur, H. E. Boesch, and F. B. McLean, *The Physics of SiO₂ and Its Interfaces*, edited by S. T. Pantelides (Pergamon, New York, 1978), p. 428.
- ⁷N. S. Saks and M. G. Ancona, IEEE Trans. Nucl. Sci. **34**, 1348 (1987).
- ⁸H. E. Boesch, IEEE Trans. Nucl. Sci. **35**, 1160 (1988).
- ⁹R. E. Stahlbush and B. J. Mrstik, IEEE Trans. Nucl. Sci. **37**, 1641 (1990).
- ¹⁰B. J. Mrstik and R. W. Rendell, IEEE Trans. Nucl. Sci. **38**, 1101 (1991).
- ¹¹J. F. Conley and P. M. Lenahan, Appl. Phys. Lett. **62**, 40 (1993).
- ¹²J. F. Conley and P. M. Lenahan, IEEE Trans. Nucl. Sci. **40**, 1335 (1993).
- ¹³P. M. Lenahan, K. L. Brower, P. V. Dressendorfer, and W. C. Johnson, IEEE Trans. Nucl. Sci. **28**, 4105 (1981).
- ¹⁴P. M. Lenahan and P. V. Dressendorfer, Appl. Phys. Lett. **41**, 542 (1982).
- ¹⁵P. M. Lenahan and P. V. Dressendorfer, J. Appl. Phys. **55**, 3495 (1984).
- ¹⁶R. L. Vranich, B. Henderson, and M. Pepper, Appl. Phys. Lett. **52**, 1161 (1988).
- ¹⁷H. Miki, M. Noguchi, K. Hokosawa, B. Kim, K. Asada, and T. Sugano, IEEE Trans. Electron Devices **35**, 2245 (1988).
- ¹⁸K. Awazu, K. Watanabe, and H. Kawazoe, J. Appl. Phys. **73**, 8519 (1993).
- ¹⁹E. H. Poindexter, G. J. Gerardi, M. E. Ruekel, P. J. Caplan, N. M. Johnson, and D. K. Biegelson, J. Appl. Phys. **56**, 2844 (1984).
- ²⁰P. M. Lenahan and P. V. Dressendorfer, Appl. Phys. Lett. **44**, 96 (1984).
- ²¹P. M. Lenahan and P. V. Dressendorfer, IEEE Trans. Nucl. Sci. **30**, 4602 (1983).
- ²²T. Takahashi, B. B. Triplett, K. Yokogawa, and T. Sugano, Appl. Phys. Lett. **26**, 1339 (1987).
- ²³L. Lipkin, L. Rowan, A. Reisman, and C. K. Williams, J. Electrochem. Soc. **138**, 2050 (1991).
- ²⁴K. L. Brower, P. M. Lenahan, and P. V. Dressendorfer, J. Appl. Phys. **41**, 251 (1982).
- ²⁵Y. Nishi, T. Tanaka, and A. Ohwada, Jpn. J. Appl. Phys. **11**, 85 (1972).
- ²⁶K. L. Brower, Phys. Rev. B **38**, 9657 (1988).
- ²⁷L. Pauling, *General Chemistry* (Dover, New York, 1988).
- ²⁸G. J. Hu and W. C. Johnson, J. Appl. Phys. **54**, 1441 (1983).
- ²⁹T. P. Ma and P. V. Dressendorfer, *Ionizing Radiation Effects in MOS Devices and Circuits* (Wiley, New York, 1989), and references therein.
- ³⁰P. M. Lenahan, J. F. Conley, Jr., and B. D. Wallace, J. Appl. Phys. **81**, 6824 (1997).