

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/370013229>

# A Simple and Efficient Determination of the Ideality Factor of Solar Cells and Modules from the Knee Point of the Shunt Resistance Curve

Article · April 2023

DOI: 10.1007/s13369-023-07860-3

CITATIONS

0

READS

69

2 authors, including:



Fahmi F. Muhammadsharif

Koya University

117 PUBLICATIONS 1,282 CITATIONS

SEE PROFILE

Some of the authors of this publication are also working on these related projects:



microwave sensor [View project](#)



Design and fabrication of Metamaterials [View project](#)



# A Simple and Efficient Determination of the Ideality Factor of Solar Cells and Modules from the Knee Point of the Shunt Resistance Curve

Fahmi F. Muhammadsharif<sup>1,2</sup> · Suhairul Hashim<sup>1,3</sup>

Received: 24 September 2022 / Accepted: 20 March 2023  
© King Fahd University of Petroleum & Minerals 2023

## Abstract

In this work, a simple and efficient method is proposed to determine the ideality factor of solar cells and modules using the knee point of the shunt resistance curve. The method was implemented by deriving a nonlinear empirical equation, which is a function of the shunt resistance and ideality factor, from which a peak value of the function is obtained that corresponds to the knee point of the shunt resistance. Researchers can use this simple approach to efficiently determine the ideality factor by either having the datasheet information or experimental current–voltage (I–V) data. Also, the determined ideality factor can be utilized to extract the other parameters of solar cells/modules, thereby modelling the I–V curve of these devices at different conditions. The method was validated on four different PV modules that are available on the market, namely Poly-Si, Mono-Si, thin film and multijunction (hybrid). It was found that the determination of the ideality factor by applying the proposed approach is easier and more efficient than the methods reported in the literature.

**Keywords** Solar cell · PV module · Parameter extraction · Simple approach · Datasheet information

## 1 Background and Literature Review

Solar energy has a lot of potential to meet our energy needs in the future as it can be used in various interesting ways. Photovoltaic (PV) technology involves the conversion of solar energy into usable electrical power by means of solar cells or modules [1]. Four solar cell technologies are currently available on the market that utilize monocrystalline, multicrystalline, thin film, and hybrid semiconductors [2–4]. A precise model of the current–voltage (I–V) characteristics of solar cells/modules enables effective quality control and performance analysis of these devices [5–7]. It is also essential for the prediction of energy yield, understanding solar cell defects, and assessing PV modules in different environmental conditions [8–10]. However, to carry out a successful I–V

modelling, it is imperative to determine the parameters of solar cell/module devices. These parameters include the ideality factor ( $n$ ), series resistance ( $R_s$ ), shunt resistance ( $R_{sh}$ ), photocurrent ( $I_{ph}$ ), and saturation current ( $I_o$ ), which can be described by the single-diode model (SDM) [11].

The ideality factor ( $n$ ) indicates the degree to which a solar cell resembles the characteristic of an ideal diode (for ideal diodes,  $n = 1$ ). Therefore, the ideality factor is crucial in determining the electrical response and fill factor of solar cell devices [12, 13]. The value of ideality factor for conventional solar cells is typically between one and two; however, it can be greater than two for organic and perovskite solar cells. In addition to the accurate I–V modelling of solar cells and modules, determination of ideality factor is important for the study of recombination mechanisms, solar cells/modules ageing [14–17] and understanding the effects of temperature and illumination energy on the performance of solar cells [18–22]. Furthermore, very recently, researchers used deep-learning approach to monitor the ideality factor, thereby estimating iron concentration in silicon solar cells [23]. Williams et al. revealed the importance of the ideality factor to being a key variable for the design of tandem perovskite-on-silicon solar cells, due to its strong influence over whether tandem sub-cells should be current-matched or intentional current mismatched [24]. Also, investigation of

✉ Fahmi F. Muhammadsharif  
fahmi.fariq@koyauniversity.org

<sup>1</sup> Department of Physics, Faculty of Science, Universiti Teknologi Malaysia (UTM), 81310 Skudai, Johor, Malaysia

<sup>2</sup> Department of Physics, Faculty of Science and Health, Koya University, Koya, Kurdistan Region-F.R., Iraq

<sup>3</sup> Ibnu Sina Institute for Scientific and Industrial Research (ISISIR), Universiti Teknologi Malaysia (UTM), 81310 Skudai, Johor, Malaysia



ideality factor plays an important role in understanding the electrical and microscopic properties of both light-emitting diodes and normal diodes [25, 26].

A survey of literature revealed the availability of a number of computational and analytical techniques for determining the ideality factor ( $n$ ) and the four parameters ( $R_s, R_{sh}, I_{ph}, I_o$ ) that assist researchers simulate the I–V response of solar cells and modules [27–36]. Analytical methods are not accurate due to neglecting part of the quantities in the manipulation process of equations [37–40]. Computational metaheuristic algorithms were also used to find the ideality factor and other parameters simultaneously, but they are computationally complex and less stable in locating the best value of ideality factor compared to the deterministic computational methods [41–44].

Along this line, several methods were proposed to determine the ideality factor [45, 46]. For instance, Singh et al. used special trans function theory (STFT) to determine the ideality factor of grey and blue solar cells [47]. The advanced STFT was also proposed as an alternative exact analytical approach to determine the ideality factor of solar cells [48]. However, the implementation of these methods is complex and it leads to obtain a less accurate I–V modelling, especially around the maximum power point (MPP). Moreover, Bayhan and Bayhan proposed a simple analytical technique to find the ideality factor of solar cells under illumination, which was less accurate due to considering equal approximate values of the photocurrent ( $I_{ph}$ ) and short-circuit current ( $I_{sc}$ ) in the utilized equations [49]. The methods of D.C. and A.C. electro-analytical were also reported to measure the ideality factor [43]. However, they are complex and unable to be implemented when only datasheet information of the solar cell/module is available. On the other hand, the use of analytical methods to find the ideality factor together with the  $R_s, R_{sh}, I_o$  and  $I_{ph}$  parameters leads to inaccurate estimation because approximations are carried out with all parameters to model the I–V response [50–54]. Noticeably, a trivial uncertainty in the ideality factor results in a high relative error of the I–V model [28]. Therefore, it has been inferred that deterministic computational techniques can perform better to determine the ideality factor if a right optimization algorithm is chosen. In our previous works [27–29], different deterministic approaches were proposed to extract the five parameters of solar cells and modules accurately, thereby modelling the I–V characteristics. However, accurate ideality factor had to be determined by simulating a collection of I–V curves relative to the reference I–V curve, which was relatively a complex and time-consuming operation.

## 2 Research Gaps

A comprehensive literature review revealed that there has not been a defined approach for determining the ideality factor of solar cells and modules in a simple and efficient manner (trade-off between simplicity and accuracy). Metaheuristic approaches may provide a precise estimate of the ideality factor, albeit at the expense of computational efficiency. In addition, analytical and deterministic methods can provide a straightforward estimation of the ideality factor at the expense of precision.

## 3 Research Objective

This paper proposes a simple and efficient numerical approach for determining the ideality factor of solar cells and modules. The proposed method is meant to be applicable to all types of solar cells and modules, and the ideality factor can be computed using either the datasheet information or experimental I–V measurements.

## 4 Research Contribution

The contribution of this work is to aid researchers, engineers, and end-users of solar cells and modules in determining the ideality factor with only the basic datasheet information or measured current–voltage data. This method is novel in that it employs the shunt resistance ( $R_{sh}$ ) curve at its knee point to find the ideality factor ( $n$ ) readily and efficiently.

## 5 Mathematical Formalism

The single-diode model (SDM) equation can be used to model the I–V characteristic of solar cells, which includes the five parameters ( $n, R_s, R_{sh}, I_o$  and  $I_{ph}$ ) [28]:

$$I = I_{ph} - I_o \left[ \exp \left( \frac{V + IR_s}{nV_t} \right) - 1 \right] - \frac{(V + IR_s)}{R_{sh}} \quad (1)$$

where  $V_t$  is the thermal voltage ( $k_B T / q$ ),  $k_B$  is Boltzmann's constant,  $q$  is the elementary charge, and  $T$  is the cell's temperature in Kelvin. The theoretical value of the ideality factor is assumed to be one ( $n = 1$ ), implying that the recombination of charge carriers does not occur in the p–n junction (depletion region) of the cell. However, recombination may occur

differently in various regions of the active layer, resulting in a deviation from unity of the ideality factor. Consequently, the ideality factor is a main tool used for determining the type and order of charge recombination in various types of solar cells. For a PV module, which is made from  $N$  series of connected cells, the ideality factor ( $n$ ) in Eq. 1 and the rest of derived formulas should be replaced by  $N \times a$ , where  $a$  is the ideality factor of the PV module.

### 5.1 Boundary Condition and Manipulation

Taking into account the boundary conditions at the short-circuit current ( $I_{sc}$ ), open circuit voltage ( $V_{oc}$ ), and maximum power ( $P_m$ ) in Eq. 1, it is possible to derive the following equations:

$$0 = I_{ph} - \frac{V_{oc}}{R_{sh}} + I_o \left[ 1 - \exp\left(\frac{V_{oc}}{nV_t}\right) \right] \quad (2)$$

$$I_{sc} = I_{ph} - \frac{R_s I_{sc}}{R_{sh}} + I_o \left[ 1 - \exp\left(\frac{R_s I_{sc}}{nV_t}\right) \right] \quad (3)$$

$$I_m = I_{ph} - \frac{R_s I_m}{R_{sh}} - \frac{V_m}{R_{sh}} + I_o \left[ 1 - \exp\left(\frac{V_m + R_s I_m}{nV_t}\right) \right] \quad (4)$$

The simultaneous Eqs. 2 and 3 can be used to solve for the saturation current ( $I_o$ ):

$$I_o = \frac{I_{sc} + \frac{R_s}{R_{sh}} I_{sc} - \frac{V_{oc}}{R_{sh}}}{\exp\left(\frac{V_{oc}}{nV_t}\right) - \exp\left(\frac{R_s I_{sc}}{nV_t}\right)} \quad (5)$$

The term  $\exp\left(\frac{R_s I_{sc}}{nV_t}\right)$  is small enough to be neglected [55–57], so Eqs. 3 and 5 are rewritten as follows:

$$I_{ph} = I_{sc} + \frac{R_s I_{sc}}{R_{sh}} - I_o \quad (6)$$

$$I_o = \frac{I_{sc} + \frac{R_s}{R_{sh}} I_{sc} - \frac{V_{oc}}{R_{sh}}}{\exp\left(\frac{V_{oc}}{nV_t}\right)} \quad (7)$$

It is known from the theorem of the maximum power transfer that when the internal impedance ( $Z_{in}$ ) of a power source is equal to the external impedance of the connected load ( $Z_{out}$ ), maximum power ( $P_m$ ) is delivered to the load. This can be represented by [28]:

$$\frac{V_m}{I_m} = Z_{out} = Z_{in} \quad (8)$$

The internal impedance formula can be derived from the equivalent circuit of the single-diode model and is equated

to the external impedance:

$$R_s + \frac{r_d R_{sh}}{r_d + R_{sh}} = \frac{V_m}{I_m} \quad (9)$$

where  $r_d$  is the dynamic non-ohmic resistance of the diode, which is estimated by taking the first derivative of the diode equation as follows:

$$r_d = \frac{dV_D}{dI_D} \Big|_{P_m} = \frac{nV_t}{I_o \exp\left(\frac{V_m + R_s I_m}{nV_t}\right)} \quad (10)$$

Then, substituting for  $r_d$  in Eq. 9, one can get:

$$\frac{nV_t(I_m + \frac{R_s I_m}{R_{sh}} - \frac{V_m}{R_{sh}})}{V_m - R_s I_m} = I_o \exp\left(\frac{V_m + R_s I_m}{nV_t}\right) \quad (11)$$

Also, subtracting Eq. 2 from 4 yields

$$I_o \exp\left(\frac{V_m + R_s I_m}{nV_t}\right) = I_{sc} + \frac{R_s}{R_{sh}}(I_{sc} - I_m) - \frac{V_m}{R_{sh}} - I_m \quad (12)$$

Now, the simultaneous Eqs. 11 and 12 can be solved to make  $R_{sh}$  subject as follows:

$$R_{sh} = \frac{R_s^2(I_{sc} I_m - I_m^2) + R_s(nV_t I_m - I_{sc} V_m) + V_m^2 - nV_t V_m}{V_m(I_{sc} - I_m) + R_s(I_m^2 - I_{sc} I_m) - nV_t I_m} \quad (13)$$

Another expression can be achieved from Eq. 6 and 4 as follows:

$$I_{sc} + \frac{R_s I_{sc}}{R_{sh}} = I_m + \frac{R_s I_m}{R_{sh}} + \frac{V_m}{R_{sh}} + I_o \exp\left(\frac{V_m + R_s I_m}{nV_t}\right) \quad (14)$$

Substituting for  $I_o$  in Eq. 14, another formula for the shunt resistance ( $R_{sh}$ ) can be derived, which is:


$$R_{sh} = \frac{R_s(I_{sc} A - I_{sc} + I_m) + V_m - V_{oc} A}{I_{sc}(1 - A) - I_m} \quad (15)$$

where  $A = \exp\left(\frac{V_m - V_{oc} + R_s I_m}{nV_t}\right)$ .

Finally, by equating Eqs. 13–15, a relation between the ideality factor ( $n$ ) and series resistance ( $R_s$ ) can be established:

$$R_s = \frac{nV_t V_m(2I_m - I_{sc})A^{-1} + nV_t(I_{sc} V_m - I_m V_{oc}) + V_{oc} V_m(I_{sc} - I_m) - V_m^2 I_{sc}}{I_{sc} I_m(V_{oc} - V_m) - I_m^2 V_{oc}} \quad (16)$$




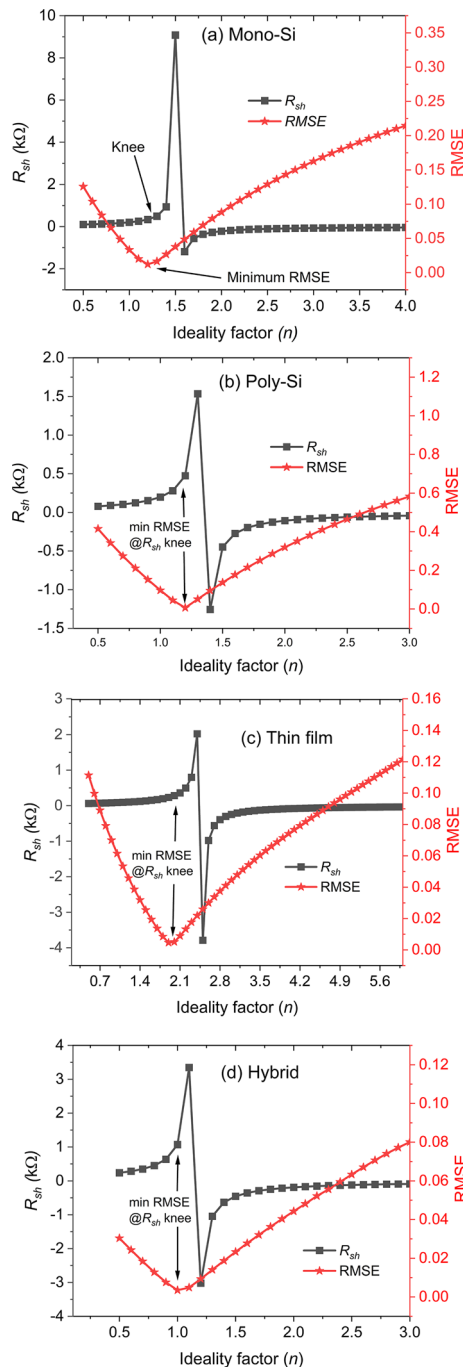

**Fig. 1** The relation between ideality factor with shunt resistance and root mean square error for PV modules made from **a** monocrystalline silicon, **b** polycrystalline silicon, **c** thin film, and **d** hybrid active layers

## 5.2 Proposed Method

This study was inspired by a number of experimental investigations conducted on the modelling of I–V characteristics of solar cells and modules, with the intention of showing an intriguing relationship between shunt resistance ( $R_{sh}$ ) and ideality factor ( $n$ ). It was determined that the most accurate

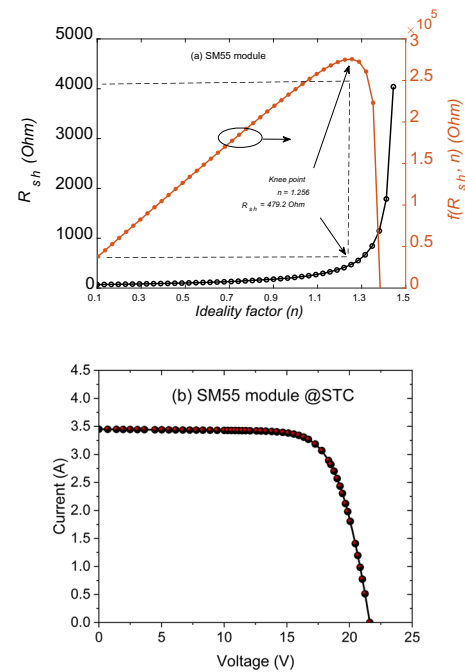

**Fig. 2 a** Determination of the ideality factor where Eq. 17 shows its highest value at the knee point of  $R_{sh}$ - $n$ , and **b** the I–V curve of a sample module (SM55) which is opposite to the shape of  $R_{sh}$ - $n$  curve

I–V model (the one with the minimum error) is obtained when the ideality factor corresponds to the knee point of the nonlinear curve of  $R_{sh}$ . Equation 15 can be used to draw this nonlinear curve of  $R_{sh}$  as a function of the ideality factor. To justify this finding, plots of  $R_{sh}$  versus root mean square error (RMSE) of the I–V modelling were drawn for the four types of solar cell technologies (monocrystalline, polycrystalline, thin film and hybrid), as shown in Fig. 1. As can be seen, the best I–V model is at the knee point of the positive values of  $R_{sh}$  curve. Therefore, the ideality factor at the knee point represents the most accurate value.

To develop an algorithm for extracting the ideality factor at the knee point of the  $R_{sh}$  curve, we have transformed the curve so that the knee point corresponds to a maximum point (vertex) on the new curve, as shown in Fig. 2a. The new curve was produced as follows; each single value of  $R_{sh}$  was subtracted from its maximum value, i.e.  $(R_{sh\_max} - R_{sh})$ , where  $R_{sh\_max}$  is the maximum value beyond the knee point. Later, the function was multiplied by the ideality factor to obtain:

$$f(R_{sh}, n) = (R_{sh\_max} - R_{sh}) \times n \quad (17)$$

where  $f(R_{sh}, n)$  is the new curve function having a maximum point which corresponding to the knee point of  $R_{sh}$ . Figure 3 shows the pseudocode used to execute the algorithm through which the ideality factor was determined at the knee point of the  $R_{sh}$  curve.

```

1. Initialize  $V_{oc}$ ,  $I_{sc}$ ,  $V_m$ ,  $I_m$ ,  $V_t$ ,  $N$ 
2. For  $a = 0.5$  to  $5$  (step size 0.002)
3.    $n = a \times N$ 
4.   Calculate  $R_s$  from Eq. 16
5.   Calculate  $R_{sh}$  from Eq. 15
6. End for
7. Find  $R_{sh\_max} = \max(R_{sh})$ 
8. Find  $a = a_{max}$  at  $R_{sh\_max}$ 
9. For  $a = 0.5$  to  $a_{max}$ 
10.  Calculate  $f = (R_{sh\_max} - R_{sh}) \times n$ 
11. End for
12. Find  $f_{max} = \max(f)$ 
13. Find  $a = \text{ideality factor at } f_{max}$ 

```

**Fig. 3** The MATLAB coding steps of the proposed method to determine the ideality factor

## 6 Results and Discussion

The proposed method was validated on four types of PV modules that are available on the market, including monocrystalline-Si (SM55), polycrystalline-Si (KC200GT), thin film (ST40) and hybrid (CTJ30), whose datasheet extracted I–V data can be found elsewhere [27, 58, 59]. The photovoltaic parameters and number of cells of the PV modules at standard test condition (STC), which are reported in the manufacturer's datasheet, are shown in Table 1.

The accuracy of the proposed method to determine the ideality factor was assessed by finding the percentage relative error (RE%) between the calculated I–V and measured I–V data. This is because there are no benchmark ideality factors for the PV modules to be compared with the calculated ones. Consequently, the five intrinsic parameters of the PV modules

were determined and utilized to generate the calculated I–V data. Interestingly, the percentage relative error (RE%) was found to be low enough, from 1 to 2.9%, when the proposed method was used to simulate the I–V curve of the PV modules at STC, as shown in Table 2.

As shown in Table 3, the uncertainty of the ideality factor estimated for the PV modules by the proposed method was compared to those determined by other techniques reported in the literature. Notably, the proposed method was found to be more accurate (lower RE%, as shown in bold inside parenthesis) than the previous approaches in determining the ideality factor. In addition, the two approaches developed by Zaimi et al. [60] and El-Achouby et al. [61] exhibited high errors when used to determine the ideality factor and other parameters of the thin film PV modules, but they performed better for the mono-Si and poly-Si modules. It is worth mentioning that despite the higher accuracy of the proposed method, the methodology process is much simpler than the methods reported earlier.

The competence of the proposed method was further demonstrated by estimating the ideality factor of several PV modules at varying temperatures and irradiance levels. Figure 4 shows the effect of temperature and irradiance on the ideality factor of the investigated PV modules using the proposed method. One can notice that for the monocrystalline PV module, the ideality factor was relatively increased and decreased with the increase of temperature and irradiance, respectively. This result was found to be in agreement with the previously reported experimental investigations [18, 50]. However, the ideality factor change for the polycrystalline and thin film PV modules was observed to follow a reverse trend with the increase in temperature and irradiance [28]. Comparably, the change in the ideality factor was found by

**Table 1** Photovoltaic parameters of four types of PV modules at STC extracted from their datasheets

PV module	PV parameters				
	$V_{oc}$ (V)	$I_{sc}$ (A)	$V_m$ (V)	$I_m$ (A)	$N$
Mono-Si (SM55)	21.7	3.45	17.4	3.15	36
Poly-Si (KC200GT)	32.9	8.21	26.3	7.61	54
Thin film (ST40)	23.3	2.68	16.6	2.41	36
Hybrid/Multijunction (CTJ30)	2.610	0.473	2.314	0.452	3

**Table 2** Intrinsic parameters of different PV modules extracted by the proposed method at STC


PV module	Module parameters					
	$n$	$R_s$ ( $\Omega$ )	$R_{sh}$ ( $\Omega$ )	$I_o$ (A)	$I_{ph}$ (A)	RE%
Mono-Si (SM55)	1.256	0.381	479.2	2.816E-8	3.453	1.04
Poly-Si (KC200GT)	1.192	0.212	388.6	1.675E-8	8.184	1.87
Thin film (ST40)	1.992	0.899	278.2	6.519E-6	2.687	1.66
Hybrid/multijunction (CTJ30)	1.028	0.055	425.1	2.83E-15	0.473	2.85






**Table 3** The determined ideality factor of different PV modules using the proposed method in comparison to those estimated by other researchers

PV module	Ideality factor ( $n$ ) ( $RE$ )		
	This work	Ref. [60–62]	Ref. [63]
Mono-Si (SM55)	1.256 ( <b>1.04%</b> )	1.036 (1.53%)	1.64 (1.41%)
Poly-Si (KC200GT)	1.192 ( <b>1.87%</b> )	1.043 (2.34%)	1.22 (2.19%)
Thin film (ST40)	1.992 ( <b>1.66%</b> )	1.148 (2.21%)	1.38 (1.73%)
Hybrid/Multijunction (CTJ30)	1.028 (2.85%)	NA	NA

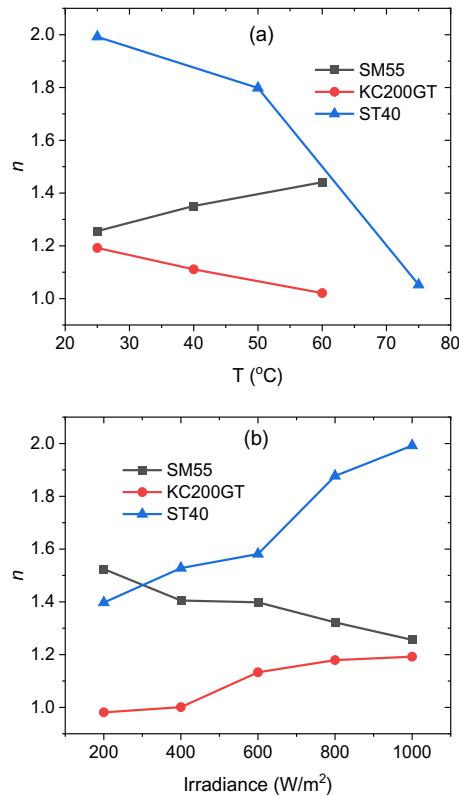**Fig. 4** The simulated I–V curve of thin film (ST40) PV module at **a** different irradiances and **b** temperatures compared to those reported in the datasheet and literature

other researchers to be insignificant with the increase in temperature and irradiance [64].

Additionally, in order to observe the fitness quality of the simulated I–V curves at different irradiances and temperatures, the determined ideality factors were used to calculate the I–V data at each condition. The results of this simulation is shown in Fig. 5 for the thin film (ST40), as a representative PV module. It was found that the proposed method has well fitted the datasheet I–V at different environmental conditions. Noticeably, there has been less deviation of the calculated curves from those of the measured ones at low temperatures and high irradiances, implying an efficient response of the proposed method compared to those reported in the literature. It was observed that the proposed method is

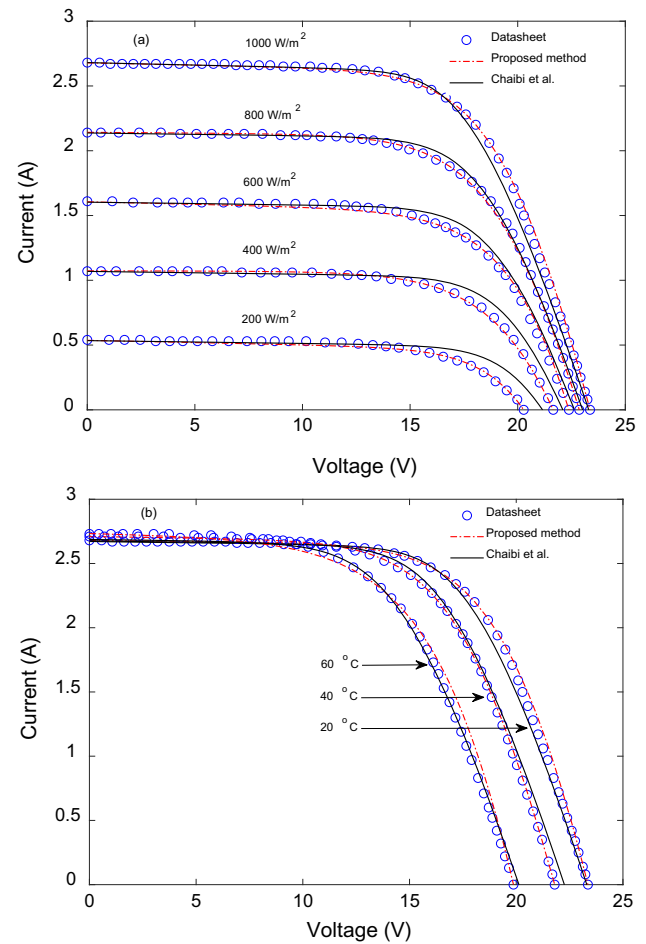**Fig. 5** The simulated I–V curve of thin film (ST40) PV module at **a** different irradiances and **b** temperatures compared to those reported in the datasheet and literature

more efficient at the maximum power point (MPP) and at the voltages beyond  $V_m$  (see Fig. 5) compared to that reported by Chaibi's et al. [63].

## 7 Conclusions

A new simple and efficient numerical method was successfully implemented to extract the ideality factor of solar cells and modules from the knee point of the shunt resistance

curve. The ideality factor of mono-Si (SM55) was determined to be 1.256, while that for poly-Si (KC200GT), thin film (ST40) and hybrid (CTJ30) were found to be 1.192, 1.992 and 1.028, respectively. The relative error percentage in the ideality factors estimated by the suggested method was found to be lower than those reported by previous methods. Noteworthy, the relative errors in the ideality factor of mono-Si (SM55), poly-Si (KC200GT), thin film (ST40) and hybrid (CTJ30) were calculated to be 1.04%, 1.87%, 1.66% and 2.85%, respectively. Importantly, the proposed method can use either the datasheet information or experimental current–voltage (I–V) data to extract the ideality factor, through which the other four parameters of solar cells/modules can also be determined. This allows for the correct modelling of I–V characteristics under diverse scenarios. It was determined that the proposed method for obtaining the ideality factor is simpler and more effective than the methods described in the literature. The proposed method can help researchers, engineers, and end-users of solar cells and modules in determining the ideality factor with only the basic datasheet information or measured current–voltage data.

**Acknowledgements** Fahmi F. Muhammadsharif is thankful to the Islamic Development Bank for their support under IDB Merit Scholarship Program. The authors thank Assoc. Prof. Dr. Yassine Chaibi at Moroccan School of Engineering Sciences for providing some datasets used to validate this work.

**Data availability** The data and material are available within the manuscript.

## Declarations

**Conflict of interest** The author declares that there is no conflict of interest regarding the publication of this paper.

## References

1. Luque, A.; Hegedus, S.: *Handbook of Photovoltaic Science and Engineering*. Wiley, New York (2011)
2. Zurita, A.; Castillejo-Cuberos, A.; García, M.; Mata-Torres, C.; Simsek, Y.; García, R.; Antonanzas-Torres, F.; Escobar, R.A.: State of the art and future prospects for solar PV development in Chile. *Renew. Sustain. Energy Rev.* **92**, 701–727 (2018). <https://doi.org/10.1016/j.rser.2018.04.096>
3. Thopil, G.A.; Sachse, C.E.; Lalk, J.; Thopil, M.S.: Techno-economic performance comparison of crystalline and thin film PV panels under varying meteorological conditions: A high solar resource southern hemisphere case. *Appl. Energy*. **275**, 115041 (2020). <https://doi.org/10.1016/j.apenergy.2020.115041>
4. Ghaleb, B.; Asif, M.: Assessment of solar PV potential in commercial buildings. *Renew. Energy*. **187**, 618–630 (2022). <https://doi.org/10.1016/j.renene.2022.01.013>
5. Xiao, W.; Edwin, F.F.; Spagnuolo, G.; Jatskevich, J.: Efficient approaches for modeling and simulating photovoltaic power systems. *IEEE J. Photovolt.* **3**, 500–508 (2013). <https://doi.org/10.1109/JPHOTOV.2012.2226435>
6. Banik, A.; Shrivastava, A.; Manohar Potdar, R.; Kumar Jain, S.; Gopal Nagpure, S.; Soni, M.: Design, modelling, and analysis of novel solar PV system using MATLAB. *Mater. Today Proc.* **51**, 756–763 (2022). <https://doi.org/10.1016/j.matpr.2021.06.226>
7. Pendem, S.R.; Mikkili, S.: Modelling and performance assessment of PV array topologies under partial shading conditions to mitigate the mismatching power losses. *Sol. Energy*. **160**, 303–321 (2018). <https://doi.org/10.1016/j.solener.2017.12.010>
8. Gholami, A.; Ameri, M.; Zandi, M.; Gavagsaz Ghoachani, R.: A single-diode model for photovoltaic panels in variable environmental conditions: investigating dust impacts with experimental evaluation. *Sustain. Energy Technol. Assess.* **47**, 101392 (2021). <https://doi.org/10.1016/j.seta.2021.101392>
9. Chen, Z.; Chen, Y.; Wu, L.; Cheng, S.; Lin, P.; You, L.: Accurate modeling of photovoltaic modules using a 1-D deep residual network based on I–V characteristics. *Energy Convers. Manag.* **186**, 168–187 (2019). <https://doi.org/10.1016/j.enconman.2019.02.032>
10. Patel, H.; Agarwal, V.: MATLAB-based modeling to study the effects of partial shading on PV array characteristics. *IEEE Trans. Energy Convers.* **23**, 302–310 (2008). <https://doi.org/10.1109/TEC.2007.914308>
11. Abdulrazzaq, A.K.; Bognár, G.; Plesz, B.: Evaluation of different methods for solar cells/modules parameters extraction. *Sol. Energy*. **196**, 183–195 (2020). <https://doi.org/10.1016/j.solener.2019.12.010>
12. Caprioglio, P.; Wolff, C.M.; Sandberg, O.J.; Armin, A.; Rech, B.; Albrecht, S.; Neher, D.; Stolterfoht, M.: On the origin of the ideality factor in perovskite solar cells. *Adv. Energy Mater.* **10**, 2000502 (2020). <https://doi.org/10.1002/aenm.202000502>
13. Hu, Z.; Nomoto, K.; Song, B.; Zhu, M.; Qi, M.; Pan, M.; Gao, X.; Protasenko, V.; Jena, D.; Xing, H.G.: Near unity ideality factor and Shockley–Read–Hall lifetime in GaN-on-GaN p–n diodes with avalanche breakdown. *Appl. Phys. Lett.* **107**, 243501 (2015). <https://doi.org/10.1063/1.4937436>
14. Almora, O.; Cho, K.T.; Aghazada, S.; Zimmermann, I.; Matt, G.J.; Brabec, C.J.; Nazeeruddin, M.K.; Garcia-Belmonte, G.: Discerning recombination mechanisms and ideality factors through impedance analysis of high-efficiency perovskite solar cells. *Nano Energy* **48**, 63–72 (2018). <https://doi.org/10.1016/j.nanoen.2018.03.042>
15. Hameiri, Z.; McIntosh, K.; Xu, G.: Evaluation of recombination processes using the local ideality factor of carrier lifetime measurements. *Sol. Energy Mater. Sol. Cells*. **117**, 251–258 (2013). <https://doi.org/10.1016/j.solmat.2013.05.040>
16. Calado, P.; Burkitt, D.; Yao, J.; Troughton, J.; Watson, T.M.; Carnie, M.J.; Telford, A.M.; O'Regan, B.C.; Nelson, J.; Barnes, P.R.F.: Identifying dominant recombination mechanisms in perovskite solar cells by measuring the transient ideality factor. *Phys. Rev. Appl.* **11**, 044005 (2019). <https://doi.org/10.1103/PhysRevApplied.11.044005>
17. Duan, L.; Yi, H.; Xu, C.; Upama, M.B.; Mahmud, M.A.; Wang, D.; Shabab, F.H.; Uddin, A.: Relationship between the diode ideality factor and the carrier recombination resistance in organic solar cells. *IEEE J. Photovolt.* **8**, 1701–1709 (2018). <https://doi.org/10.1109/JPHOTOV.2018.2870722>
18. Ahmed, D.R.; Abdullah, H.M.; Muhammadsharif, F.F.: Utilization of device parameters to assess the performance of a monocrystalline solar module under varied temperature and irradiance. *Energy Syst.* (2021). <https://doi.org/10.1007/s12667-021-00472-6>
19. Babbe, F.; Choubrac, L.; Siebentritt, S.: The optical diode ideality factor enables fast screening of semiconductors for solar cells. *Sol. RRL* **2**, 1800248 (2018). <https://doi.org/10.1002/solr.201800248>
20. Ahmed, D.R.; Mohammed, I.R.; Abdullah, H.M.; Muhammadsharif, F.F.; Sulaiman, K.; Alsoufi, M.S.; Bawazeer, T.M.: The correlation of device parameters with illumination energy to explore the performance of a monocrystalline silicon solar module.





- SILICON **14**, 1439–1445 (2022). <https://doi.org/10.1007/s12633-021-00966-z>
21. Yordanov, G.H.; Midtgård, O.-M.; Saetre, T.O.: PV modules with variable ideality factors. In: 2012 38th IEEE Photovoltaic Specialists Conference, pp. 002362–002367 (2012)
  22. Velilla, E.; Jaramillo, F.; Mora-Seró, I.: High-throughput analysis of the ideality factor to evaluate the outdoor performance of perovskite solar minimodules. *Nat. Energy*. **6**, 54–62 (2021). <https://doi.org/10.1038/s41560-020-00747-9>
  23. Olikh, O.; Lozitsky, O.; Zavorodnii, O.: Estimation for iron contamination in Si solar cell by ideality factor: deep neural network approach. *Prog. Photovolt. Res. Appl.* **30**, 648–660 (2022)
  24. Williams, B.; Daiber, B.; Case, C.: Importance of ideality factors in perovskite/Si tandem solar cell design. In: 2022 IEEE 49th Photovoltaics Specialists Conference (PVSC). pp. 0328–0328. IEEE (2022)
  25. Shin, D.-S.; Shim, J.-I.: Understanding microscopic properties of light-emitting diodes from macroscopic characterization: ideality factor, S-parameter, and internal quantum efficiency. *Phys. Status Solidi A*. **219**, 2200042 (2022)
  26. Myeong, G.; Shin, W.; Sung, K.; Kim, S.; Lim, H.; Kim, B.; Jin, T.; Park, J.; Lee, T.; Fuhrer, M.S.: Dirac-source diode with sub-unity ideality factor. *Nat. Commun.* **13**, 1–6 (2022)
  27. Muhammadsharif, F.F.: A new simplified method for efficient extraction of solar cells and modules parameters from datasheet information. *SILICON* **14**, 3059–3067 (2022). <https://doi.org/10.1007/s12633-021-01097-1>
  28. Muhammadsharif, F.F.; Hashim, S.; Hameed, S.S.; Ghoshal, S.K.; Abdullah, I.K.; Macdonald, J.E.; Yahya, M.Y.: Brent's algorithm based new computational approach for accurate determination of single-diode model parameters to simulate solar cells and modules. *Sol. Energy*. **193**, 782–798 (2019). <https://doi.org/10.1016/j.solener.2019.09.096>
  29. Muhammad, F.F.; Sangawi, A.W.K.; Hashim, S.; Ghoshal, S.K.; Abdullah, I.K.; Hameed, S.S.: Simple and efficient estimation of photovoltaic cells and modules parameters using approximation and correction technique. *PLoS ONE* **14**, e0216201 (2019). <https://doi.org/10.1371/journal.pone.0216201>
  30. Chen, Z.; Yu, H.; Luo, L.; Wu, L.; Zheng, Q.; Wu, Z.; Cheng, S.; Lin, P.: Rapid and accurate modeling of PV modules based on extreme learning machine and large datasets of I-V curves. *Appl. Energy*. **292**, 116929 (2021). <https://doi.org/10.1016/j.apenergy.2021.116929>
  31. Boutana, N.; Mellit, A.; Haddad, S.; Rabhi, A.; Pavan, A.M.: An explicit I-V model for photovoltaic module technologies. *Energy Convers. Manag.* **138**, 400–412 (2017). <https://doi.org/10.1016/j.enconman.2017.02.016>
  32. Pandiarajan, N.; Muthu, R.: Mathematical modeling of photovoltaic module with Simulink. In: 2011 1st International Conference on Electrical Energy Systems. pp. 258–263 (2011)
  33. Khatib, T.; Ghareeb, A.; Tamimi, M.; Jaber, M.; Jaradat, S.: A new offline method for extracting I-V characteristic curve for photovoltaic modules using artificial neural networks. *Sol. Energy*. **173**, 462–469 (2018). <https://doi.org/10.1016/j.solener.2018.07.092>
  34. Ma, X.; Huang, W.-H.; Schnabel, E.; Köhl, M.; Brynjarsdóttir, J.; Braid, J.L.; French, R.H.: Data-driven \$IS\$–\$VS\$ feature extraction for photovoltaic modules. *IEEE J. Photovolt.* **9**, 1405–1412 (2019). <https://doi.org/10.1109/JPHOTOV.2019.2928477>
  35. Tao, Y.; Bai, J.; Pachauri, R.K.; Sharma, A.: Parameter extraction of photovoltaic modules using a heuristic iterative algorithm. *Energy Convers. Manag.* **224**, 113386 (2020). <https://doi.org/10.1016/j.enconman.2020.113386>
  36. Ben Hmamou, D.; Elyaqouti, M.; Hanafi, A.E.; Saadaoui, D.; Lidaighbi, S.; Chaoufi, J.; Ibrahim, A.; Aql, R.; El Fatmi, D.; Obukhov, S.: A novel hybrid numerical with analytical approach for parameter extraction of photovoltaic modules. *Energy Convers. Manag.* **14**, 100219 (2022). <https://doi.org/10.1016/j.ecmx.2022.100219>
  37. Ibrahim, H.; Anani, N.: Evaluation of analytical methods for parameter extraction of PV modules. *Energy Procedia*. **134**, 69–78 (2017). <https://doi.org/10.1016/j.egypro.2017.09.601>
  38. Abdulrazzaq, A.K.; Bognár, G.; Plesz, B.: Accurate method for PV solar cells and modules parameters extraction using I-V curves. *J. King Saud Univ. Eng. Sci.* **34**, 46–56 (2022). <https://doi.org/10.1016/j.jksues.2020.07.008>
  39. Oulcaid, M.; El Fadil, H.; Ammeh, L.; Yahya, A.; Giri, F.: Parameter extraction of photovoltaic cell and module: analysis and discussion of various combinations and test cases. *Sustain. Energy Technol. Assess.* **40**, 100736 (2020). <https://doi.org/10.1016/j.seta.2020.100736>
  40. Elkholy, A.; Abou El-Ela, A.A.: Optimal parameters estimation and modelling of photovoltaic modules using analytical method. *Heliyon* **5**, e02137 (2019). <https://doi.org/10.1016/j.heliyon.2019.e02137>
  41. Li, S.; Gong, W.; Gu, Q.: A comprehensive survey on meta-heuristic algorithms for parameter extraction of photovoltaic models. *Renew. Sustain. Energy Rev.* **141**, 110828 (2021). <https://doi.org/10.1016/j.rser.2021.110828>
  42. Merchaoui, M.; Sakly, A.; Mimouni, M.F.: Particle swarm optimisation with adaptive mutation strategy for photovoltaic solar cell/module parameter extraction. *Energy Convers. Manag.* **175**, 151–163 (2018). <https://doi.org/10.1016/j.enconman.2018.08.081>
  43. Hachana, O.; Hemsas, K.E.; Tina, G.M.; Ventura, C.: Comparison of different metaheuristic algorithms for parameter identification of photovoltaic cell/module. *J. Renew. Sustain. Energy*. **5**, 053122 (2013). <https://doi.org/10.1063/1.4822054>
  44. Nguyen, T.T.; Nguyen, T.T.; Tran, T.N.: Parameter estimation of photovoltaic cell and module models relied on metaheuristic algorithms including artificial ecosystem optimization. *Neural Comput. Appl.* (2022). <https://doi.org/10.1007/s00521-022-07142-3>
  45. Bashahu, M.; Nkundabakura, P.: Review and tests of methods for the determination of the solar cell junction ideality factors. *Sol. Energy*. **81**, 856–863 (2007). <https://doi.org/10.1016/j.solener.2006.11.002>
  46. Cotfas, D.T.; Cotfas, P.A.; Ursutiu, D.; Samoila, C.: The methods to determine the series resistance and the ideality factor of diode for solar cells-review. In: 2012 13th International Conference on Optimization of Electrical and Electronic Equipment (OPTIM). pp. 966–972 (2012)
  47. Santakrus Singh, N.; Jain, A.; Kapoor, A.: Determination of the solar cell junction ideality factor using special trans function theory (STFT). *Sol. Energy Mater. Sol. Cells*. **93**, 1423–1426 (2009). <https://doi.org/10.1016/j.solmat.2009.03.013>
  48. Perovich, S.M.; Djukanovic, M.D.J.; Dlabac, T.; Nikolic, D.; Calasan, M.P.: Concerning a novel mathematical approach to the solar cell junction ideality factor estimation. *Appl. Math. Model.* **39**, 3248–3264 (2015). <https://doi.org/10.1016/j.apm.2014.11.026>
  49. Bayhan, H.; Bayhan, M.: A simple approach to determine the solar cell diode ideality factor under illumination. *Sol. Energy*. **85**, 769–775 (2011). <https://doi.org/10.1016/j.solener.2011.01.009>
  50. Cuce, E.; Cuce, P.M.; Karakas, I.H.; Bali, T.: An accurate model for photovoltaic (PV) modules to determine electrical characteristics and thermodynamic performance parameters. *Energy Convers. Manag.* **146**, 205–216 (2017). <https://doi.org/10.1016/j.enconman.2017.05.022>
  51. Gulkowski, S.; Muñoz Diez, J.V.; Aguilera Tejero, J.; Nofuentes, G.: Computational modeling and experimental analysis of heterojunction with intrinsic thin-layer photovoltaic module under different environmental conditions. *Energy* **172**, 380–390 (2019). <https://doi.org/10.1016/j.energy.2019.01.107>



52. Shinong, W.; Qianlong, M.; Jie, X.; Yuan, G.; Shilin, L.: An improved mathematical model of photovoltaic cells based on datasheet information. *Sol. Energy.* **199**, 437–446 (2020). <https://doi.org/10.1016/j.solener.2020.02.046>
53. Maouhoub, N.: Photovoltaic module parameter estimation using an analytical approach and least squares method. *J. Comput. Electron.* **17**, 784–790 (2018). <https://doi.org/10.1007/s10825-017-1121-5>
54. Nassar-eddine, I.; Obbadi, A.; Errami, Y.; El Fajri, A.; Agunaou, M.: Parameter estimation of photovoltaic modules using iterative method and the Lambert W function: a comparative study. *Energy Convers. Manag.* **119**, 37–48 (2016). <https://doi.org/10.1016/j.enconman.2016.04.030>
55. Lineykin, S.; Averbukh, M.; Kuperman, A.: An improved approach to extract the single-diode equivalent circuit parameters of a photovoltaic cell/panel. *Renew. Sustain. Energy Rev.* **30**, 282–289 (2014). <https://doi.org/10.1016/j.rser.2013.10.015>
56. Zhang, C.; Zhang, J.; Hao, Y.; Lin, Z.; Zhu, C.: A simple and efficient solar cell parameter extraction method from a single current-voltage curve. *J. Appl. Phys.* **110**, 064504 (2011). <https://doi.org/10.1063/1.3632971>
57. Tong, N.T.; Pora, W.: A parameter extraction technique exploiting intrinsic properties of solar cells. *Appl. Energy.* **176**, 104–115 (2016). <https://doi.org/10.1016/j.apenergy.2016.05.064>
58. Chaibi, Y.; Allouhi, A.; Malvoni, M.; Salhi, M.; Saadani, R.: Solar irradiance and temperature influence on the photovoltaic cell equivalent-circuit models. *Sol. Energy.* **188**, 1102–1110 (2019). <https://doi.org/10.1016/j.solener.2019.07.005>
59. Chaibi, Y.; Malvoni, M.; Allouhi, A.; Mohamed, S.: Data on the I-V characteristics related to the SM55 monocrystalline PV module at various solar irradiance and temperatures. *Data Brief.* **26**, 104527 (2019). <https://doi.org/10.1016/j.dib.2019.104527>
60. Zaimi, M.; El Achouby, H.; Ibral, A.; Assaid, E.M.: Determining combined effects of solar radiation and panel junction temperature on all model-parameters to forecast peak power and photovoltaic yield of solar panel under non-standard conditions. *Sol. Energy.* **191**, 341–359 (2019). <https://doi.org/10.1016/j.solener.2019.09.007>
61. El Achouby, H.; Zaimi, M.; Ibral, A.; Assaid, E.M.: New analytical approach for modelling effects of temperature and irradiance on physical parameters of photovoltaic solar module. *Energy Convers. Manag.* **177**, 258–271 (2018). <https://doi.org/10.1016/j.enconman.2018.09.054>
62. Villalva, M.G.; Gazoli, J.R.; Filho, E.R.: Comprehensive approach to modeling and simulation of photovoltaic arrays. *IEEE Trans. Power Electron.* **24**, 1198–1208 (2009). <https://doi.org/10.1109/TPEL.2009.2013862>
63. Chaibi, Y.; Allouhi, A.; Salhi, M.: A simple iterative method to determine the electrical parameters of photovoltaic cell. *J. Clean. Prod.* **269**, 122363 (2020). <https://doi.org/10.1016/j.jclepro.2020.122363>
64. Fébba, D.M.; Rubinger, R.M.; Oliveira, A.F.; Bortoni, E.C.: Impacts of temperature and irradiance on polycrystalline silicon solar cells parameters. *Sol. Energy.* **174**, 628–639 (2018). <https://doi.org/10.1016/j.solener.2018.09.051>

Springer Nature or its licensor (e.g. a society or other partner) holds exclusive rights to this article under a publishing agreement with the author(s) or other rightsholder(s); author self-archiving of the accepted manuscript version of this article is solely governed by the terms of such publishing agreement and applicable law.

