
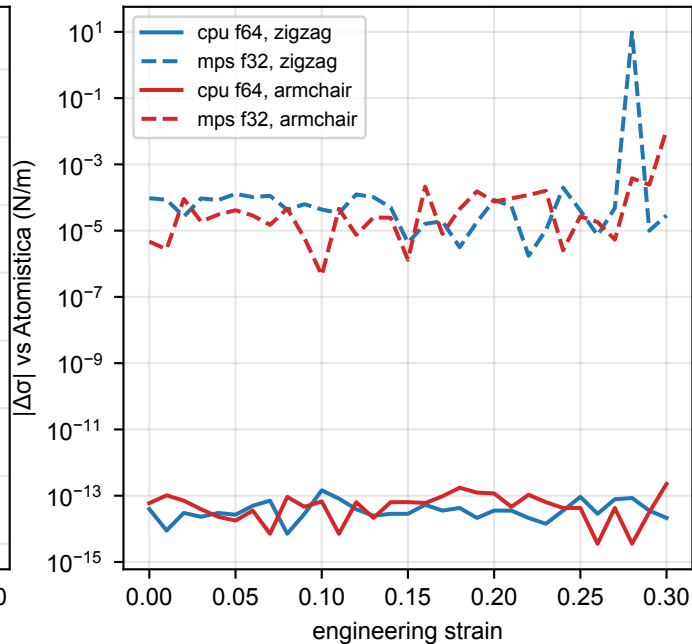


homogeneous tensile response (relaxed internal coordinates)

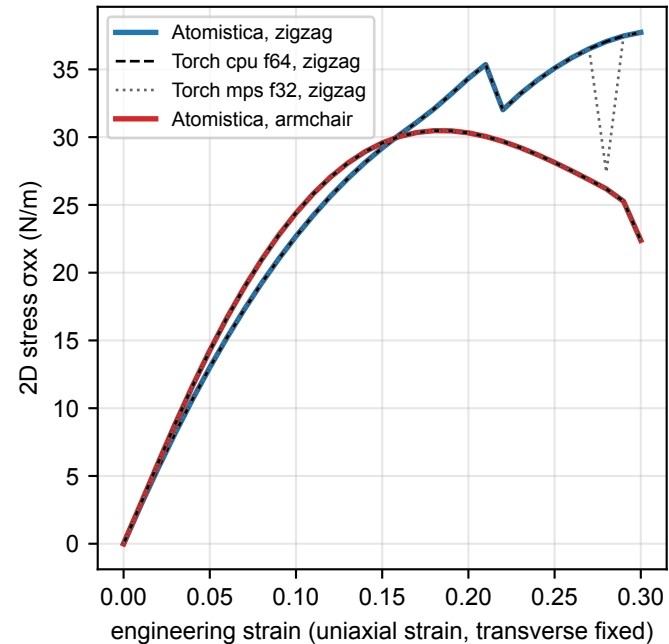

Atomistica	$a_0=2.460177 \text{ \AA}$	bond=1.420384 $\text{\AA}$	$E_{coh}=-7.395110 \text{ eV}$
Torch cpu f64	$a_0=2.460177 \text{ \AA}$	bond=1.420384 $\text{\AA}$	$E_{coh}=-7.395110 \text{ eV}$
Torch mps f32	$a_0=2.460591 \text{ \AA}$	bond=1.420623 $\text{\AA}$	$E_{coh}=-7.395117 \text{ eV}$

Atomistica	$C_{11}=289.53$	$C_{12}=113.46$	$Y_{2D}=245.07 \text{ N/m}$	$\nu=0.3919$
Torch cpu f64	$C_{11}=289.53$	$C_{12}=113.46$	$Y_{2D}=245.07 \text{ N/m}$	$\nu=0.3919$
Torch mps f32	$C_{11}=289.39$	$C_{12}=113.54$	$Y_{2D}=244.88 \text{ N/m}$	$\nu=0.3922$

experiment (Lee 2008): $Y_{2D} \approx 340 \text{ N/m}$, $\sigma_{max} \approx 42 \text{ N/m}$; $\nu(\text{graphene}) \approx 0.17$
 (REB02 underestimates Y_{2D} and overestimates ν – a documented limitation of the published potential, not of the port)