

BS EN ISO 11666:2010



BSI Standards Publication

Non-destructive testing of welds — Ultrasonic testing — Acceptance levels (ISO 11666:2010)

National foreword

This British Standard is the UK implementation of EN ISO 11666:2010. It supersedes BS EN 1712:1997 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/46, Non-destructive testing.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 55535 0

ICS 25.160.40

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2011.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Non-destructive testing of welds - Ultrasonic testing -
Acceptance levels (ISO 11666:2010)

Contrôle non destructif des assemblages soudés - Contrôle
par ultrasons - Niveaux d'acceptation (ISO 11666:2010)

Zerstörungsfreie Prüfung von Schweißverbindungen -
Ultraschallprüfung von Schweißverbindungen -
Zulässigkeitsgrenzen (ISO 11666:2010)

This European Standard was approved by CEN on 14 December 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 11666:2010) has been prepared by Technical Committee CEN/TC 121 "Welding", the secretariat of which is held by DIN, in collaboration with Technical Committee ISO/TC 44 "Welding and allied processes".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2011, and conflicting national standards shall be withdrawn at the latest by June 2011.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 1712:1997.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Measurement of indication length	1
4 Sensitivity setting and levels	2
5 Acceptance levels	2
5.1 General	2
5.2 Longitudinal indications	3
5.3 Transverse indications	3
5.4 Grouping of indications	3
5.5 Cumulative length of acceptable indications	4
Annex A (normative) Levels	5
Annex B (normative) Fixed amplitude level technique	17

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11666 was prepared by the European Committee for Standardization (CEN) Technical Committee TC 121, *Welding*, Subcommittee SC 5, *Testing of welds*, in collaboration with ISO Technical Committee TC 44, *Welding and allied processes*, Subcommittee SC 5, *Testing and inspection of welds*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

Requests for official interpretations of any aspect of this International Standard should be directed to the Secretariat of ISO/TC 44/SC 5 via your national standards body. A complete listing of these bodies can be found at www.iso.org.

Non-destructive testing of welds — Ultrasonic testing — Acceptance levels

1 Scope

This International Standard specifies ultrasonic acceptance levels 2 and 3 for full penetration welded joints in ferritic steels, which correspond to ISO 5817 quality levels B and C. An acceptance level corresponding to ISO 5817 quality level D is not included in this International Standard as ultrasonic testing is generally not requested for this weld quality.

These acceptance levels are applicable to testing carried out in accordance with ISO 17640.

This International Standard applies to the examination of full penetration ferritic steel welds, with thicknesses from 8 mm to 100 mm. It can also be used for other types of welds, materials and thicknesses above 100 mm, provided the examinations have been performed with necessary consideration of the geometry and acoustic properties of the component, and an adequate sensitivity can be employed to enable the acceptance levels of this International Standard to be applied. The nominal frequency of probes used in this International Standard is between 2 MHz and 5 MHz unless attenuation or requirements for higher resolution call for other frequencies. The use of these acceptance levels in conjunction with frequencies outside this range needs to be considered carefully.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5817, *Welding — Fusion-welded joints in steel, nickel, titanium and their alloys (beam welding excluded) — Quality levels for imperfections*

ISO 17635, *Non-destructive testing of welds — General rules for metallic materials*

ISO 17640, *Non-destructive testing of welds — Ultrasonic testing — Techniques, testing levels, and assessment*

ISO 23279, *Non-destructive testing of welds — Ultrasonic testing — Characterization of indications in welds*

3 Measurement of indication length

The length of an indication shall be determined by measuring the distance along the length over which the echo amplitude is above the evaluation level, using the fixed amplitude level technique specified in Annex B.

Alternative techniques for measuring indication length may be used when specified.

4 Sensitivity setting and levels

The sensitivity setting may be performed by one of the following techniques. For sensitivity setting and the subsequent examinations, the same technique shall be used:

- a) technique 1: based on 3 mm diameter side-drilled holes;
- b) technique 2: based on distance gain size (DGS) curves for flat-bottom holes (disk-shaped reflectors);
- c) technique 3: using a distance-amplitude-corrected (DAC) curve of a rectangular notch of 1 mm depth and 1 mm width;
- d) technique 4: using the tandem technique with reference to a 6 mm diameter flat-bottom hole (disk-shaped reflector).

Four levels as defined in ISO 17640 are used in this International Standard:

- 1) reference level;
- 2) evaluation level;
- 3) recording levels (for two acceptance levels, reference levels are derived from the relevant acceptance level minus 4 dB);
- 4) acceptance levels (for two quality levels).

All levels are linked to the reference reflectors specified in Table A.1.

Annex A specifies levels.

5 Acceptance levels

5.1 General

The relationship between acceptance levels, testing levels and quality levels is given in ISO 17635. See also Table 1.


Table 1 — Ultrasonic pulse echo technique (UT)

Quality level in accordance with ISO 5817	Testing technique and level in accordance with ISO 17640 ^a	Acceptance level in accordance with this International Standard
B	at least B	2
C	at least A	3
D	at least A	3 ^b
^a When characterization of indications is required, ISO 23279 shall be applied.		
^b UT is not recommended but can be defined in a specification (with the same requirements as quality level C).		

The acceptance levels in this International Standard are valid for all testing levels and for all techniques as defined in ISO 17640, including tests with straight beam probes.

If characterization has been specified in accordance with ISO 23279, planar indications are not acceptable and for non-planar indications, the acceptance levels in this International Standard apply.

If characterization has not been specified, the acceptance levels in this International Standard apply to all indications.

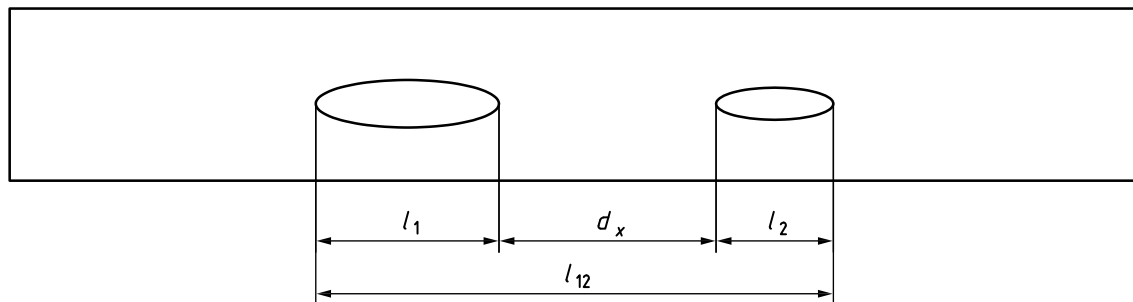


Key

- d_x distance in the x -direction
 l_1, l_2 individual indications
 l_{12} combined length

Figure 2 — Length of a group of indications

5.5 Cumulative length of acceptable indications

The cumulative length of all individually acceptable indications above recording level is given as the sum of lengths of both single indications and linearly aligned indications of combined length within a given section of weld length.

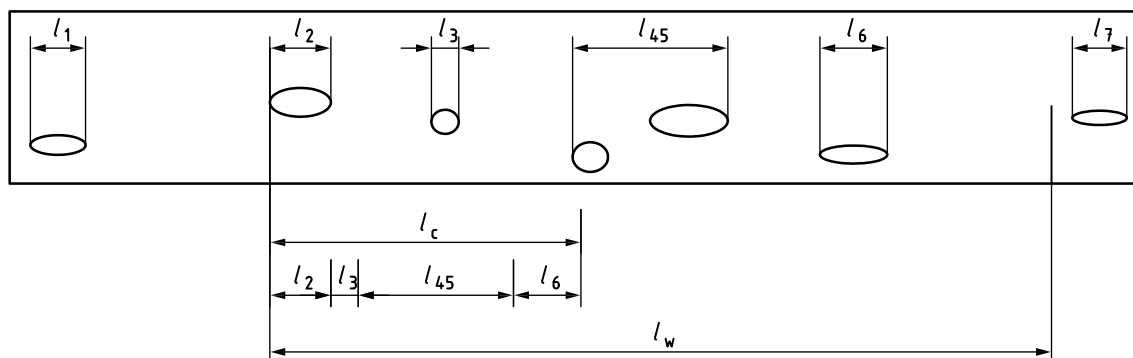

Key


- l_c cumulative length
 $l_c = l_2 + l_3 + l_{45} + l_6$
 l_w weld length
 l_n where $n = 1 \dots 7$, individual indications

Figure 3 — Cumulative length of indications

For any section of weld length, l_w , the maximum cumulative length of all individually acceptable indications above the recording level shall not exceed 20 % of this length for acceptance level 2, or 30 % of this length for acceptance level 3, where $l_w = 6t$ for $t < 15$ mm and $l_w = 100$ mm for $t \geq 15$ mm.

Annex A (normative)


Levels

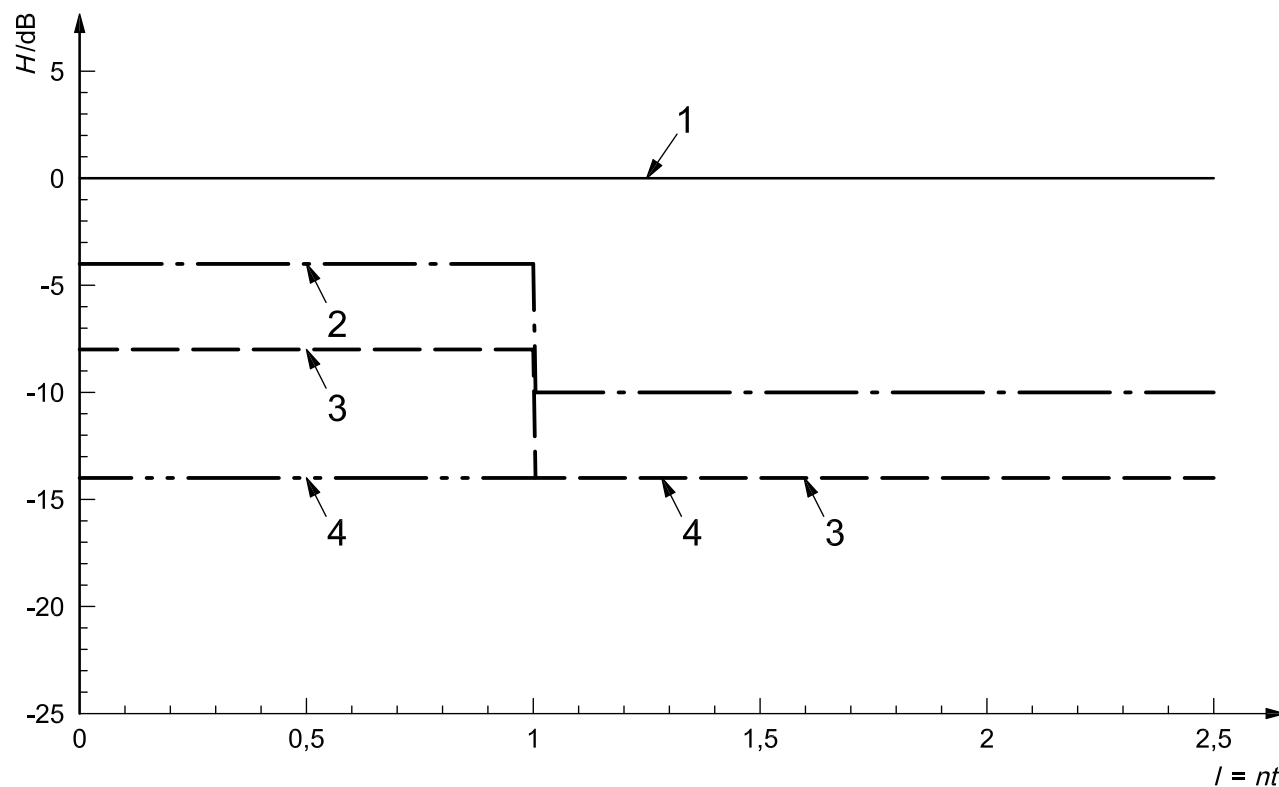

Key

- 1 reference level
- 2 acceptance level 2
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.1 — Levels for techniques 1 and 3 for thicknesses 8 mm to 15 mm — Acceptance level 2

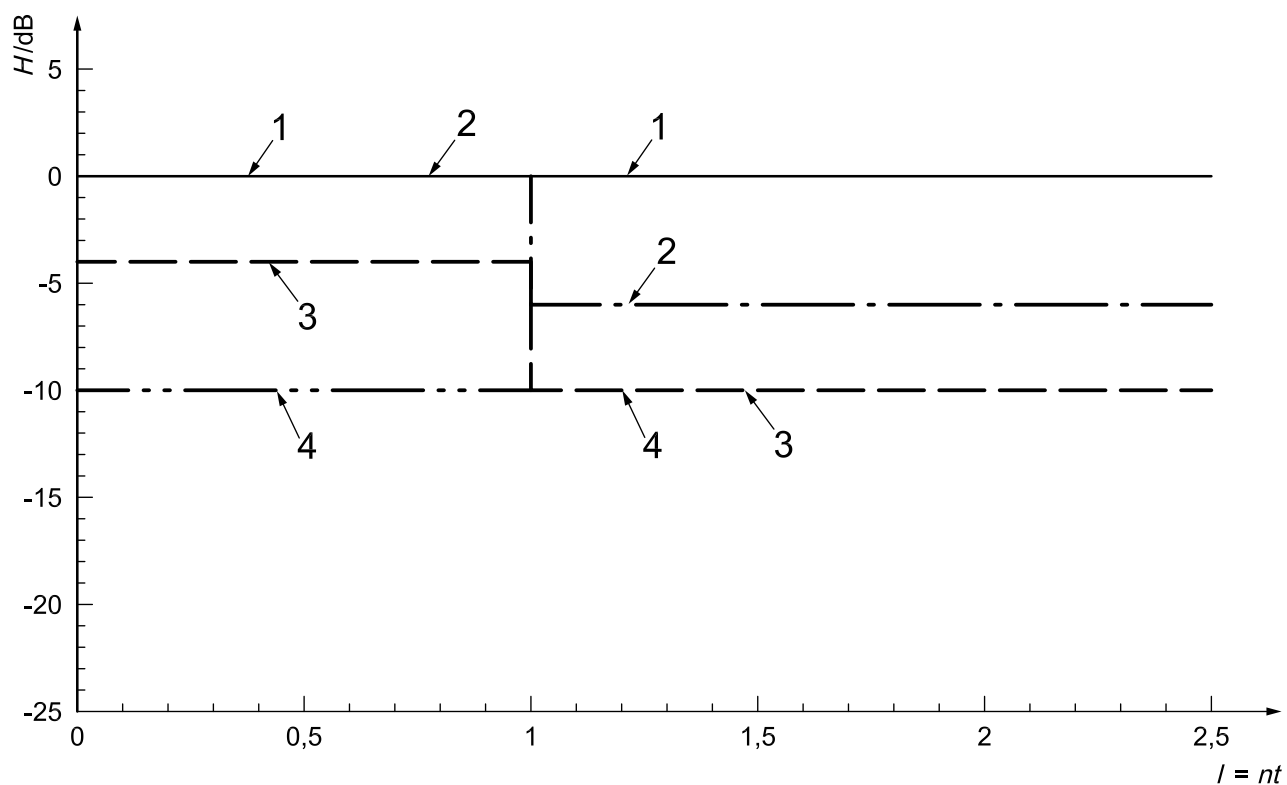

Key

- 1 reference level
- 2 acceptance level 3
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.2 — Levels for techniques 1 and 3 for thicknesses 8 mm to 15 mm — Acceptance level 3

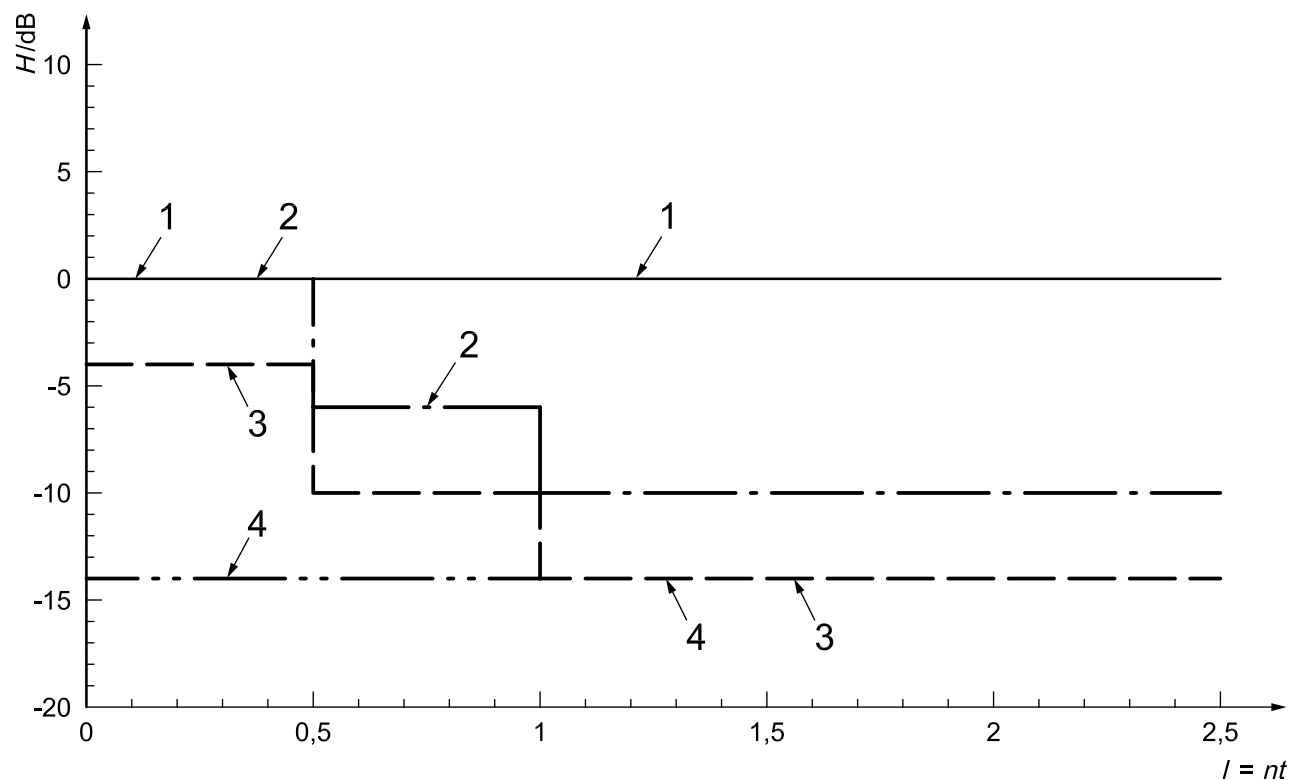

Key

- 1 reference level
- 2 acceptance level 2
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.3 — Levels for technique 1 for thicknesses 15 mm to 100 mm — Acceptance level 2

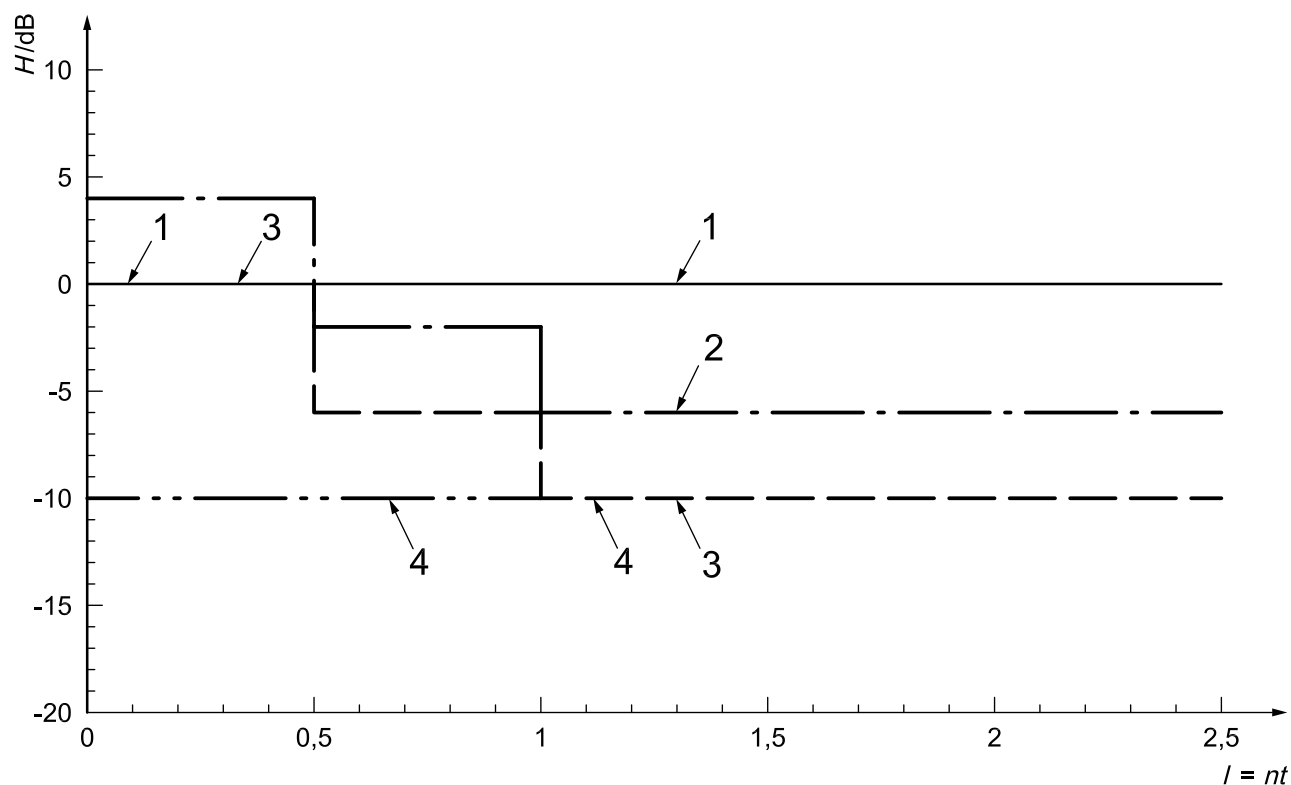

Key

- 1 reference level
- 2 acceptance level 3
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.4 — Levels for technique 1 for thicknesses 15 mm to 100 mm — Acceptance level 3

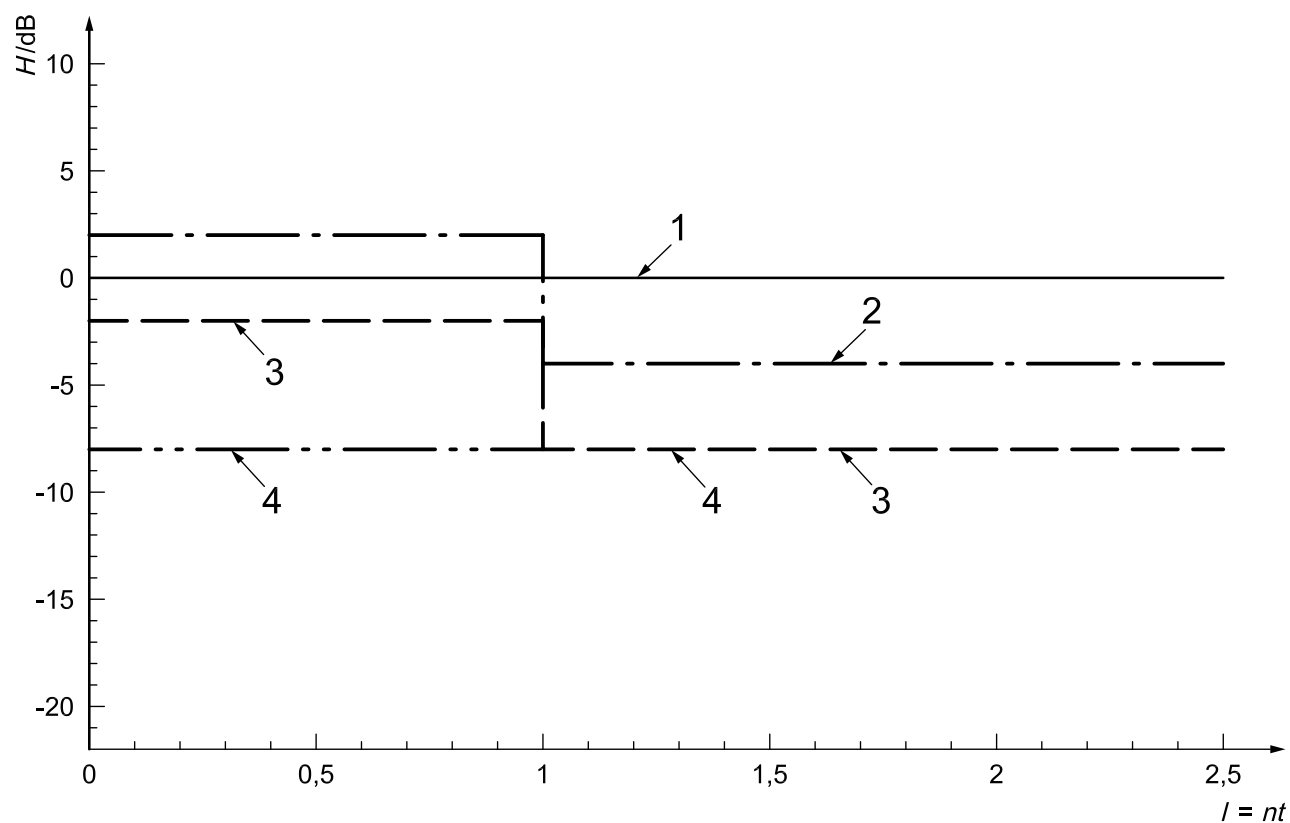

Key

- 1 reference level
- 2 acceptance level 2
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.5 — Levels for technique 2 for thicknesses 8 mm to 15 mm — Acceptance level 2

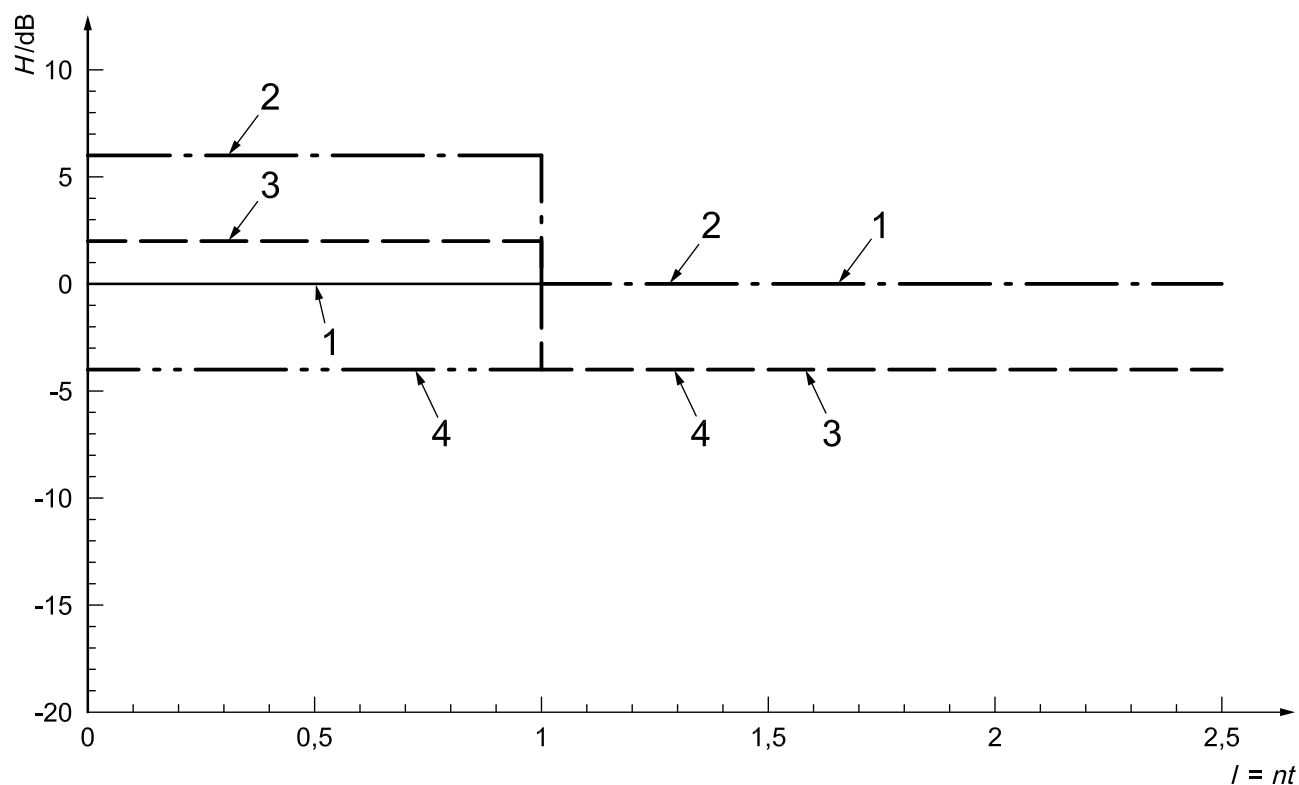

Key

- 1 reference level
- 2 acceptance level 3
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.6 — Levels for technique 2 for thicknesses 8 mm to 15 mm — Acceptance level 3

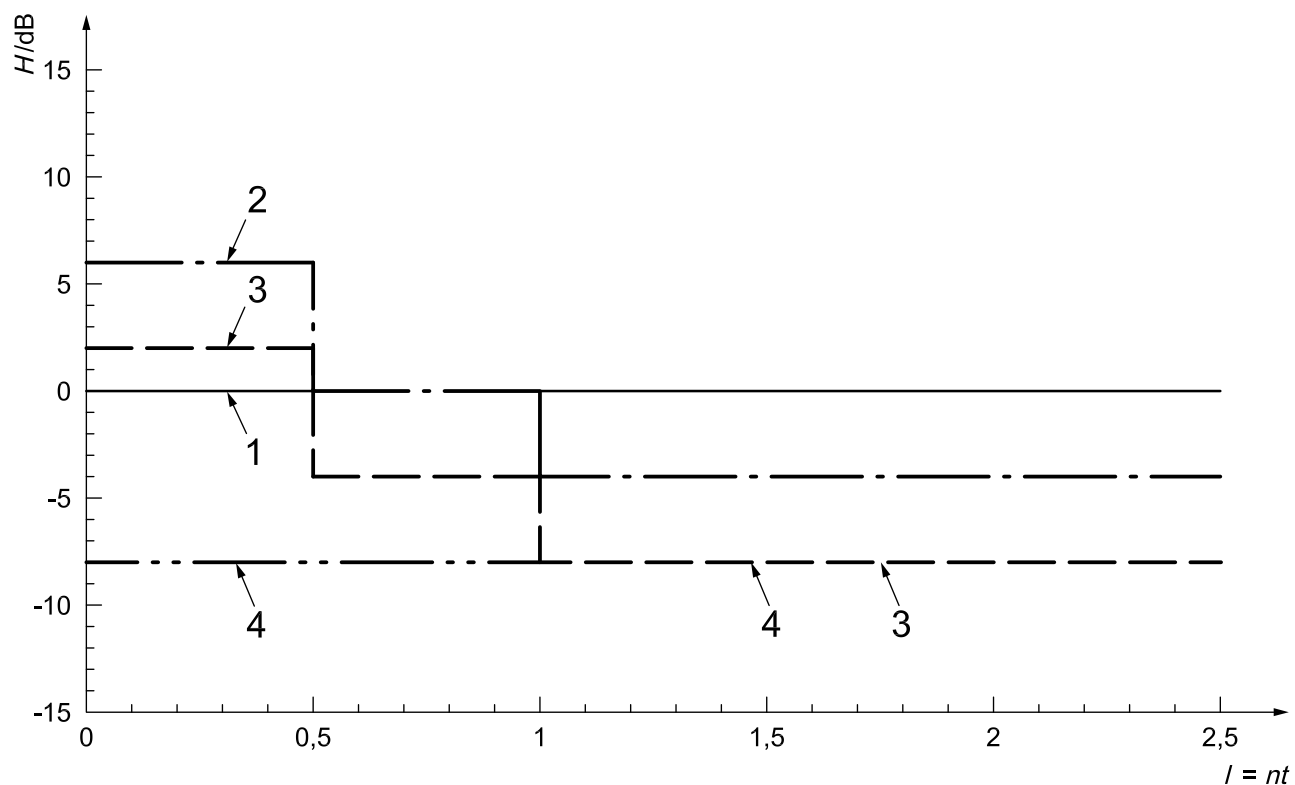

Key

- 1 reference level
- 2 acceptance level 2
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.7 — Levels for technique 2 for thicknesses 15 mm to 100 mm — Acceptance level 2

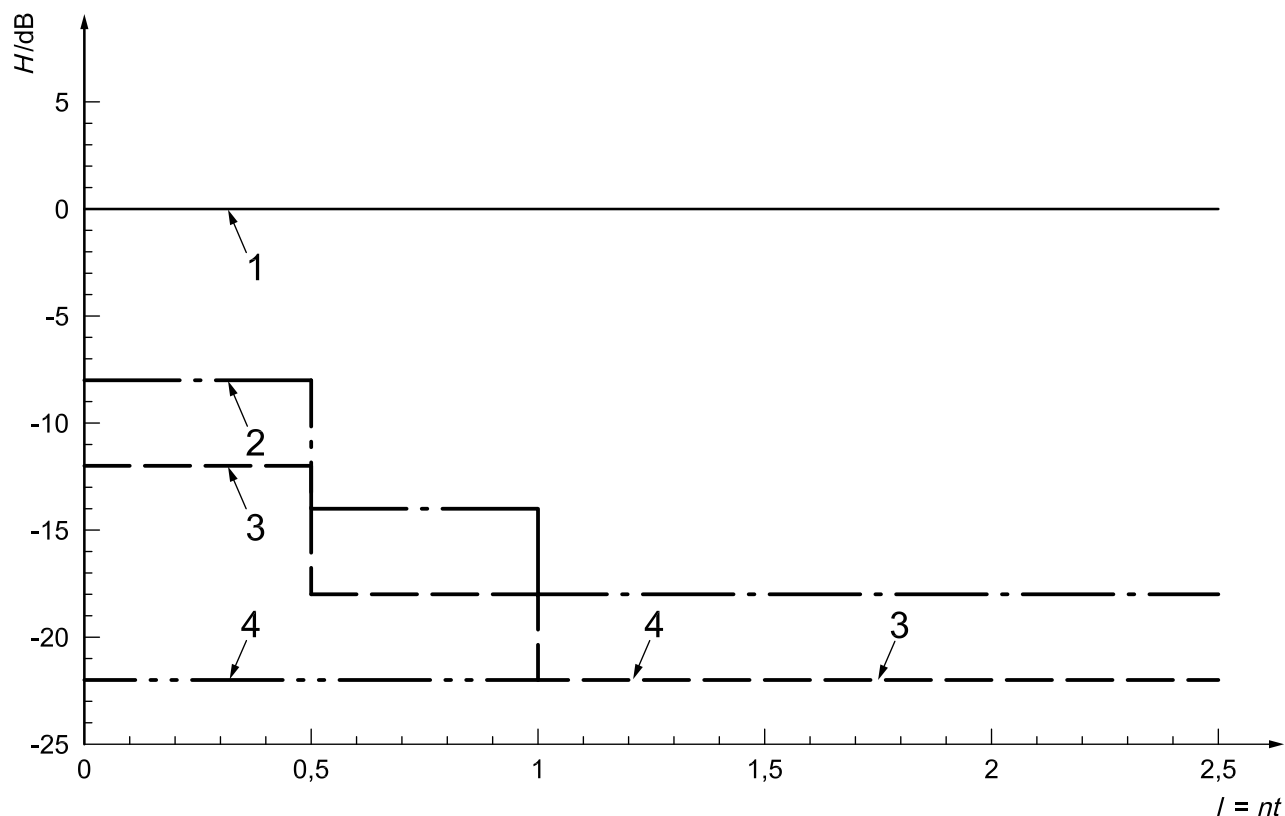

Key

- 1 reference level
- 2 acceptance level 2
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness


Figure A.8 — Levels for technique 4 for thicknesses 15 mm to 100 mm — Acceptance level 2

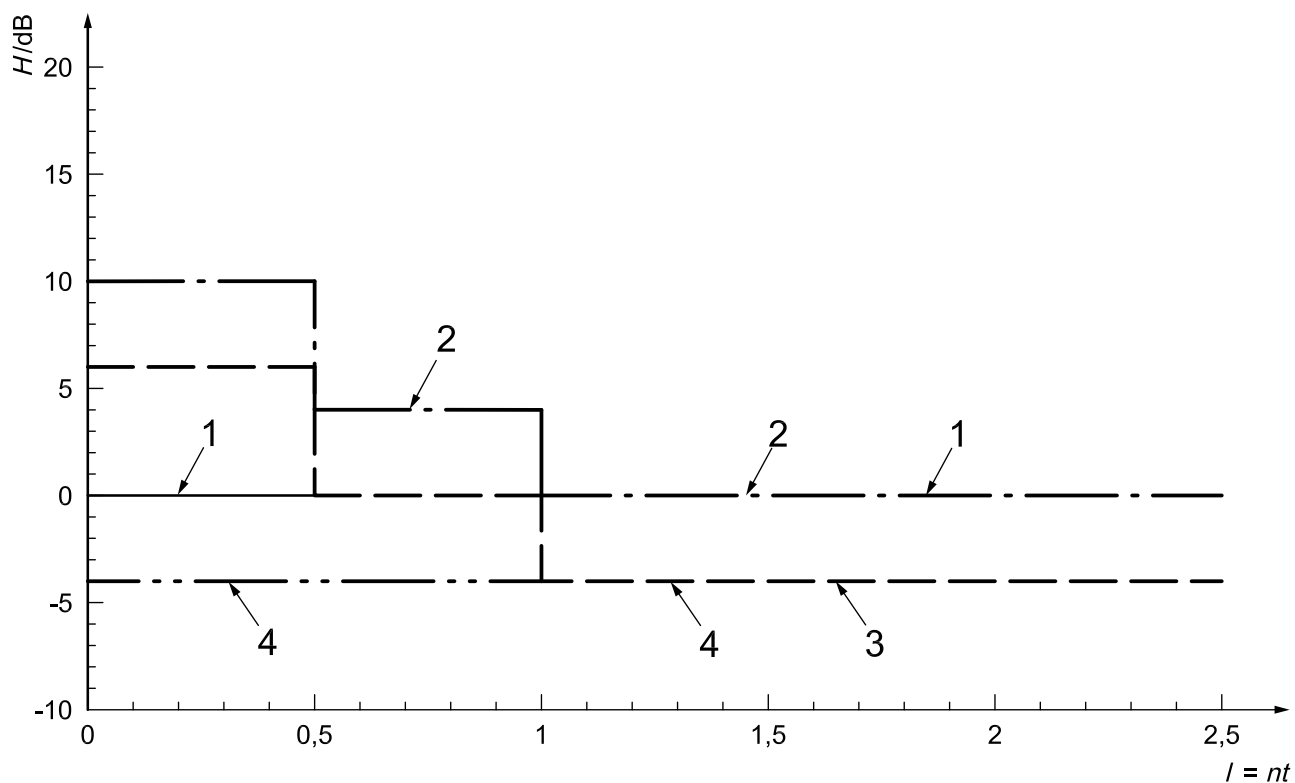

Key

- 1 reference level
- 2 acceptance level 3
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness

Figure A.9 — Levels for technique 2 for thicknesses 15 mm to 100 mm — Acceptance level 3

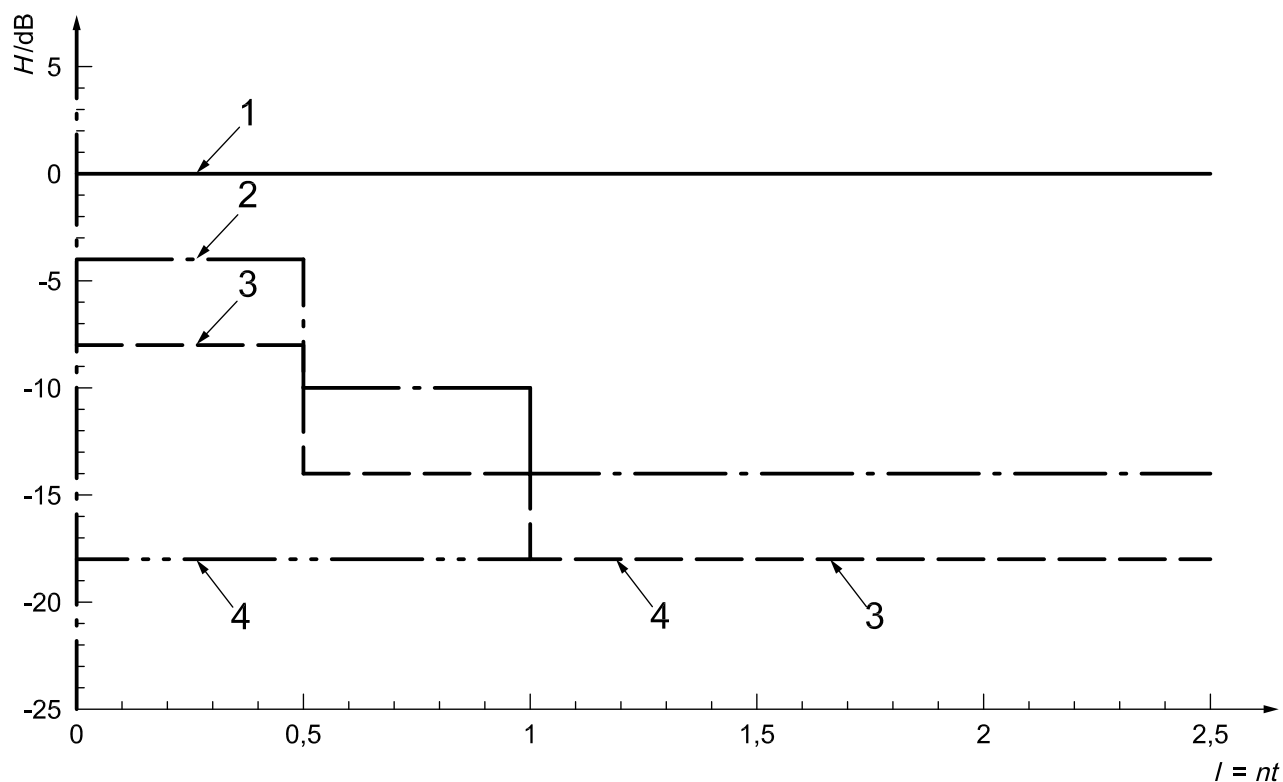

Key

- 1 reference level
- 2 acceptance level 3
- 3 recording level
- 4 evaluation level
- H amplitude
- l indication length
- n multiplier of t
- t thickness

Figure A.10 — Levels for technique 4 for thicknesses 15 mm to 100 mm — Acceptance level 3

Table A.1 — Acceptance levels 2 and 3 for techniques 1, 2, 3, and 4

Technique (according to ISO 17640)	Evaluation level		Acceptance level 2 (AL 2)		Acceptance level 3 (AL 3)	
	for AL 2	for AL 3	8 mm ≤ <i>t</i> < 15 mm	15 mm ≤ <i>t</i> < 100 mm	8 mm ≤ <i>t</i> < 15 mm	15 mm ≤ <i>t</i> < 100 mm
1 (side-drilled holes)	$H_0 - 14$ dB	$H_0 - 10$ dB	For $l \leq t$: $H_0 - 4$ dB For $l > t$: $H_0 - 10$ dB	For $l \leq 0,5 t$: H_0 For $0,5 t < l \leq t$: $H_0 - 6$ dB For $l > t$: $H_0 - 10$ dB	For $l \leq t$: H_0 For $l > t$: $H_0 - 6$ dB	For $l \leq 0,5 t$: $H_0 + 4$ dB For $0,5 t < l \leq t$: $H_0 - 2$ dB For $l > t$: $H_0 - 6$ dB
2 [flat-bottom holes (disk-shaped reflectors)]	$H_0 - 8$ dB in accordance with Table A.2 or A.3	$H_0 - 4$ dB in accordance with Table A.2 or A.3	For $l \leq t$: $H_0 + 2$ dB For $l > t$: $H_0 - 4$ dB	For $l \leq 0,5 t$: $H_0 + 6$ dB For $0,5 t < l \leq t$: H_0 For $l > t$: $H_0 - 4$ dB	For $l \leq t$: $H_0 + 6$ dB For $l > t$: H_0	For $l \leq 0,5 t$: $H_0 + 10$ dB For $0,5 t < l \leq t$: $H_0 + 4$ dB For $l > t$: H_0
3 (rectangular notch)	$H_0 - 14$ dB	$H_0 - 10$ dB	For $l \leq t$: $H_0 - 4$ dB For $l > t$: $H_0 - 10$ dB	—	For $l \leq t$: H_0 For $l > t$: $H_0 - 6$ dB	—
4 (tandem technique)	$H_0 - 22$ dB	$H_0 - 18$ dB	—	For $l \leq 0,5 t$: $H_0 - 8$ dB For $0,5 t < l \leq t$: $H_0 - 14$ dB For $l > t$: $H_0 - 18$ dB	—	For $l \leq 0,5 t$: $H_0 - 4$ dB For $0,5 t < l \leq t$: $H_0 - 10$ dB For $l > t$: $H_0 - 14$ dB
Recording levels are 4 dB below the corresponding acceptance levels. H_0 is the reference level.						

Table A.2 — Reference levels for acceptance levels 2 and 3 for technique 2 using angle beam scanning with transverse waves

Nominal probe frequency MHz	Thickness of parent material, t					
	8 mm $\leq t < 15$ mm		15 mm $\leq t < 40$ mm		40 mm $\leq t < 100$ mm	
1,5 to 2,5	AL 2	AL 3	AL 2	AL 3	AL 2	AL 3
3,0 to 5,0	—	—	$D_{\text{DSR}} = 2,5$ mm	$D_{\text{DSR}} = 2,5$ mm	$D_{\text{DSR}} = 3,0$ mm	$D_{\text{DSR}} = 3,0$ mm
	$D_{\text{DSR}} = 1,5$ mm	$D_{\text{DSR}} = 1,5$ mm	$D_{\text{DSR}} = 2,0$ mm	$D_{\text{DSR}} = 2,0$ mm	$D_{\text{DSR}} = 3,0$ mm	$D_{\text{DSR}} = 3,0$ mm
D_{DSR} is the diameter of the disk-shaped reflector.						

Table A.3 — Reference levels for acceptance levels 2 and 3 for technique 2 using straight beam scanning with longitudinal waves

Nominal probe frequency MHz	Thickness of parent material, t					
	8 mm $\leq t < 15$ mm		15 mm $\leq t < 40$ mm		40 mm $\leq t < 100$ mm	
1,5 to 2,5	AL 2	AL 3	AL 2	AL 3	AL 2	AL 3
3,0 to 5,0	—	—	$D_{\text{DSR}} = 2,5$ mm	$D_{\text{DSR}} = 2,5$ mm	$D_{\text{DSR}} = 3,0$ mm	$D_{\text{DSR}} = 3,0$ mm
	$D_{\text{DSR}} = 2,0$ mm	$D_{\text{DSR}} = 2,0$ mm	$D_{\text{DSR}} = 2,0$ mm	$D_{\text{DSR}} = 2,0$ mm	$D_{\text{DSR}} = 3,0$ mm	$D_{\text{DSR}} = 3,0$ mm
D_{DSR} is the diameter of the disk-shaped reflector.						


Annex B (normative)

Fixed amplitude level technique

The technique measures the lateral dimensions of an indication over which the echo is equal to or greater than the evaluation level.

To make a measurement, the beam is scanned over the indications, and the probe position and beam path range, at which the echo has fallen to the evaluation level, are noted (positions 1 and 2 in Figure B.1).

The lateral dimension, l , is then determined by the distance between the positions 1 and 2.

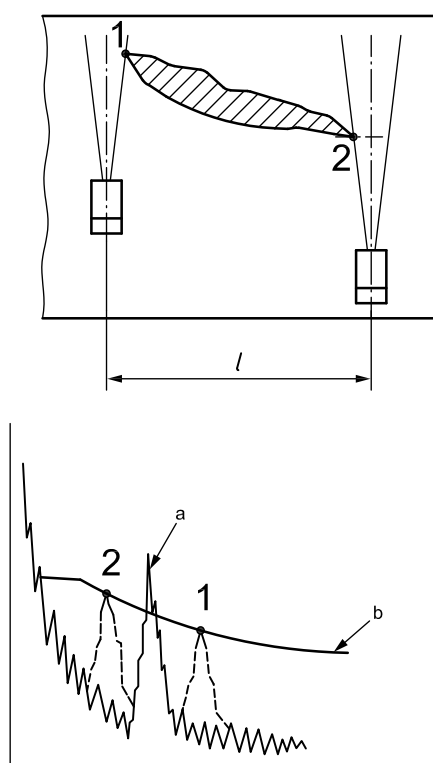

Key

- l measured lateral dimension of indication
- 1, 2 positions where indication amplitudes are equal to the evaluation level
- a Maximum echo.
- b Evaluation level.

Figure B.1 — Fixed amplitude level technique using the beam axis

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com