

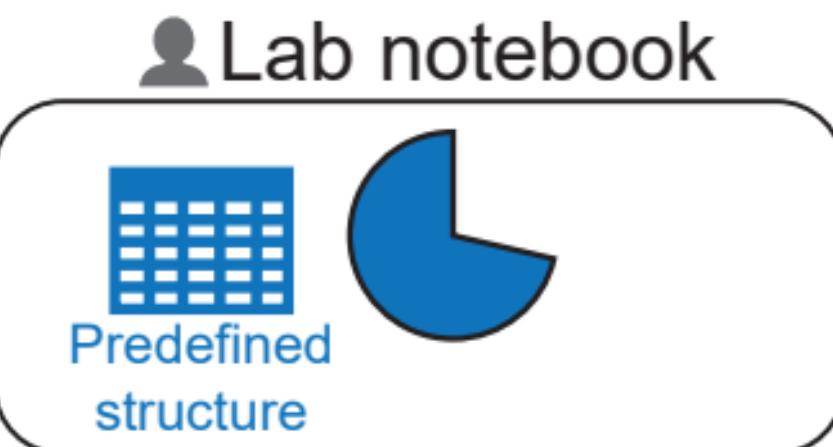


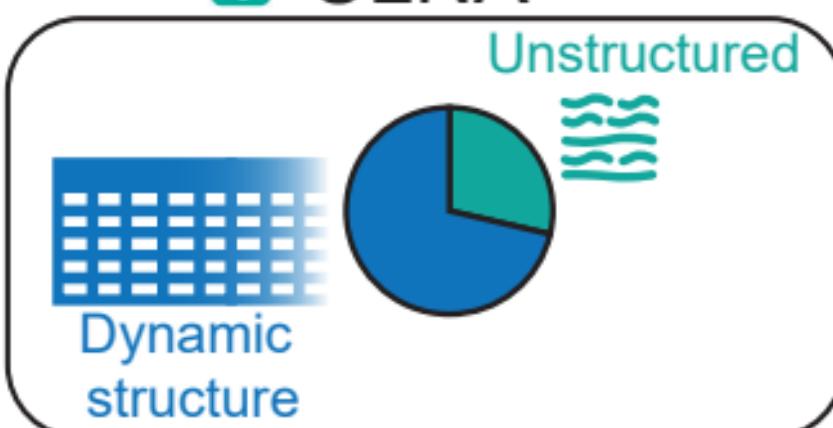

ULNA

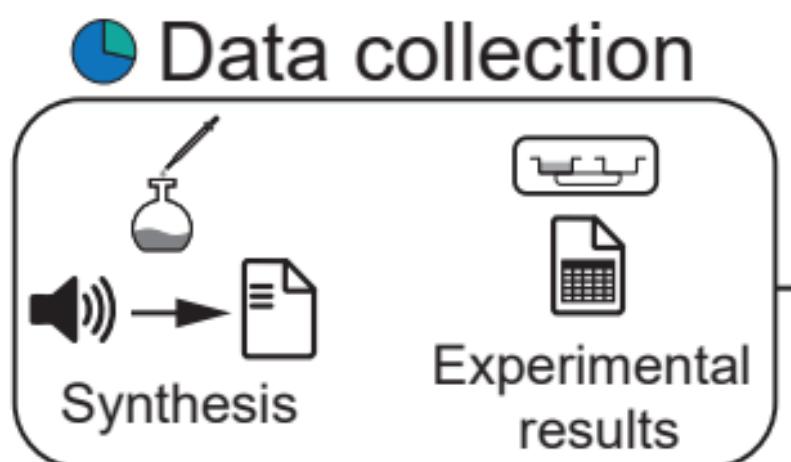

Predefined structure

- “Fuzzy” trends**
5. Mixing/solubility quality — poor dispersion depresses enthalpy (COD)
 - COD with visible particles/insolubility (Exps 2, 3, 10): mean 152.1 J/g (n=3).
 - COD clear/fully dissolved (Exps 1, 4–9): mean 287.3 J/g (n=7).
⇒ Poor dissolution corresponds to ≈ -135 J/g on average.
 6. Delay/aging before DSC — lowers enthalpy (DCPD example)
 - Same DCPD/M204/TBP~1.0 regime, both 7 °C/min:
 - Exp 16 (prompt run): 337.6 J/g.
 - Exp 14 ("left on bench before DSC"): 251.5 J/g.
⇒ Bench time before the run cost ≈ -86 J/g here.

