

Aluminium-Water Combustion for Zero Carbon Marine Shipping: Masters Proposal

Md Nadim Ahmed

May 22, 2026

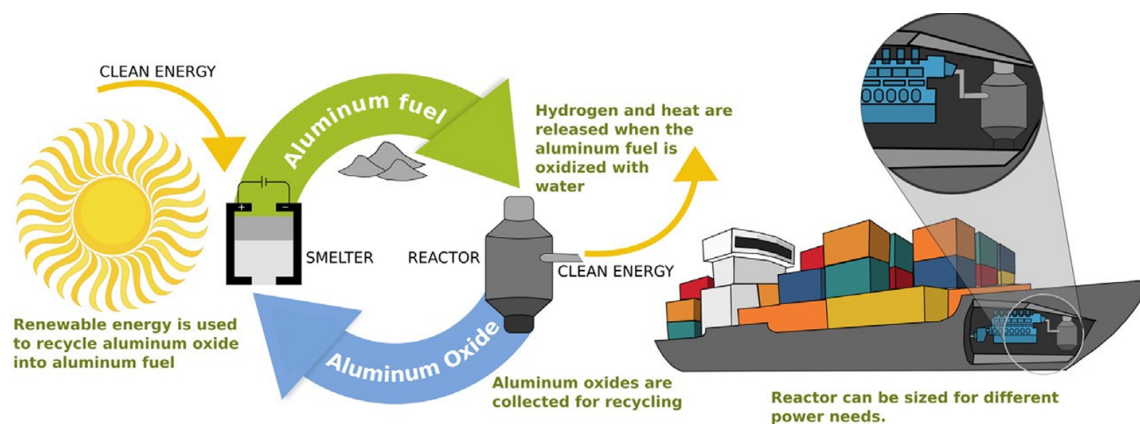


Figure 1: Aluminium powder as maritime shipping fuel (Energy Life-cycle). Adapted from [1]

Abstract

Table of Contents

List of Tables	4
List of Figures	4
1 Research Background	6
1.1 Preliminary Analysis of Electro-Fuels Options	6
1.1.1 High Level Energy Density Analysis	10
1.1.2 Effective Energy Density Analysis	13
1.2 Aluminium-Water Combustion	14
1.3 Reactor Design	15
1.3.1 Low Temperature Metal-Water Reactors	17
1.3.2 High Temperature Metal-Water Reactor	18
1.3.3 Summary Tables	21
1.4 Economics of Aluminium Fuel	22
1.4.1 The Long Term Trends	22
1.4.2 The Emerging Green Aluminium Supply Chain	23
1.5 Technology Development Pathway	25
1.5.1 Barriers to Entry in Container Shipping	25
1.5.2 Luxury Yachts and Superyachts as an Ideal Beachhead	25
1.5.3 Regulatory Pathway and Certification Advantages	27
1.5.4 Pathway to Broader Adoption	27
2 Research Questions	28
2.1 System Requirements for Yacht Applications	28
2.2 Metal-Water Reactor Design	29
3 Methodology	35
3.1 Industry Research	35
3.2 Metal-Water Reactor Design	37
4 Proposed Project Time-line	43
5 References	44
A Laboratory Safety Protocols and Experimental Plan Verification	50
A.1 Safety Protocols	50
A.2 Experimental Plan Verification and University Approval	52

List of Tables

1	Comparison of different Al–H ₂ O by-product scenarios. Adapted from [2, 3, 4, 5, 6, 1]	19
2	Volumetric Energy Densities of different Al–H ₂ O combustion scenarios. Adapted from [2, 3, 7, 8, 9, 10, 11]	19
3	Comparison of Low Temperature Metal-Water Reactors (LT-MWR) and High Temperature Metal-Water Reactors (HT-MWR)	21
4	Scope boundary for the metal-water reactor research and its relation to future work.	31

List of Figures

1	Aluminium powder as maritime shipping fuel (Energy Life-cycle). Adapted from [1]	1
2	Falling cost of solar electricity vs Fossil Fuels [12]	6
3	Falling cost of lithium ion battery packs [13]	7
4	High Level Process Diagram for synthetic hydrocarbon production from renewable electricity [14]	8
5	Metal based electro-fuels as secondary energy carriers [15]	9
6	Simplified Energy Density Analysis. Data Analysis can be found in the Appendix. Adapted from [16]	10
7	Proposed bunkering procedure for metal fuels (iron powder in this specific case) [17]	11
8	Effective Energy Density Analysis. Data Analysis can be found in the Appendix. Adapted from [16]	12
9	Simplified Overview of Metal-Water Propulsion System[4]	15
10	Schematic of the three reaction stages of aluminium with water at low temperatures, including a sketch of the initial dry particle for reference. Also sketched is the characteristic hydrogen-production curve showing the induction, rapid oxidation, and quenching stages [6] . . .	16
11	Al–H ₂ O reaction transition diagram extrapolated to 10 MPa. Labels E1-E4 show conditions used for experimental validation [18]	20
12	Aluminium fuel vs other electrofuels and diesel (The bars show the price of energy derived from low-carbon energy carriers, if the input electricity price were set to \$36/MWh (dark blue) or \$26/MWh (light blue). The pale region at the top of each bar represents the uncertainty related to the required inputs.) [1]	22

13	Modern Electric Yachts with Integrated Solar Panels [19]	26
14	The Gotland Horizon X By Austal Panels [20]	26

1 Research Background

Overview

Maritime shipping plays a crucial role in global trade, facilitating around 80% of all commerce [21]. This makes it essential for globalization, economic development, and maintaining living standards. However, the sector also contributes significantly to global greenhouse gas emissions, accounting for 2-3% of global emissions and approximately 10% of all transport-related emissions [22, 21].

In response, the International Maritime Organization (IMO) has set ambitious targets to curb emissions from international shipping. By 2030, the IMO aims to reduce annual greenhouse gas emissions by 20-30% compared to 2008 levels, with a more aggressive target of 70-80% reduction by 2040 [23].

1.1 Preliminary Analysis of Electro-Fuels Options

Overview

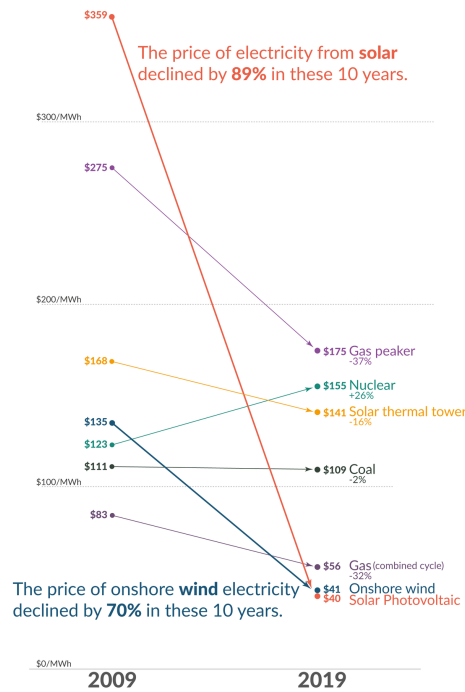


Figure 2: Falling cost of solar electricity vs Fossil Fuels [12]

Recent years have witnessed a dramatic decline in the cost of low-carbon electricity sources, particularly solar and wind power, as illustrated in Figure 2. This cost reduction has significantly enhanced the viability of transitioning to a low-carbon economy, yet substantial challenges persist in the so-called hard-to-abate sectors, among which marine shipping features prominently.

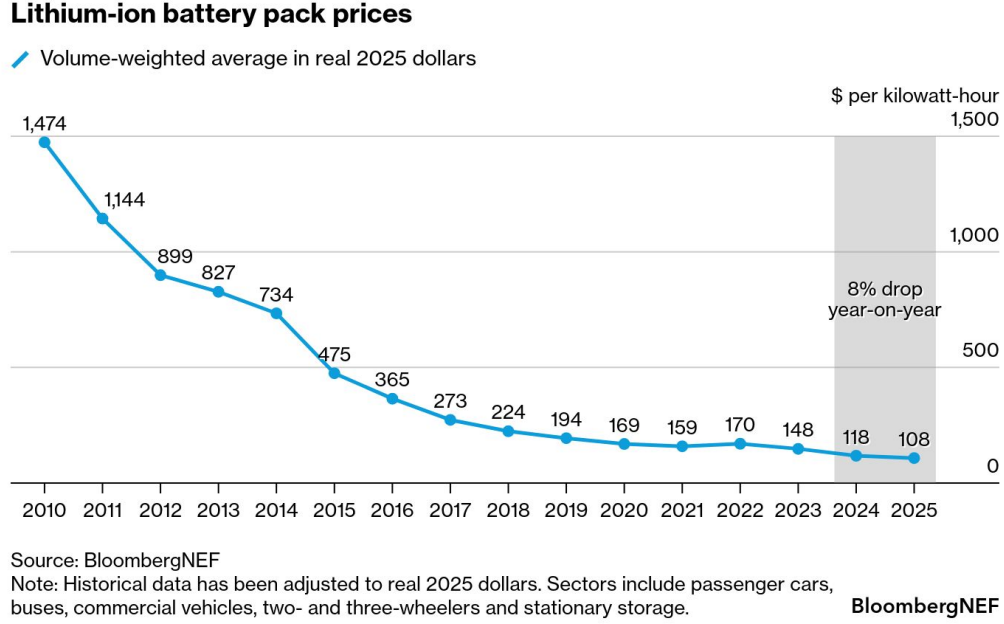


Figure 3: Falling cost of lithium ion battery packs [13]

The predominant method for storing electrical energy remains electrochemical batteries, with lithium-ion technology leading the charge. These batteries have increasingly displaced fossil fuels in passenger vehicles and, more recently, have begun penetrating short and medium-distance trucking applications [24]. This transformation has been driven largely by the precipitous decline in lithium battery prices, as demonstrated in Figure 3. The technology’s reach has even extended to inland shipping routes, where standardized and swappable battery packs are being deployed in China [25]. Major battery manufacturers such as CATL are making substantial investments in these markets, signaling confidence in the technology’s continued expansion [26].

However, despite remarkable advances in both price and energy density, lithium-ion batteries remain largely impractical for deep-sea shipping, which accounts for approximately 70% of marine shipping emissions [27]. The fundamental constraint lies in the current energy density limitations of lithium-ion technology, which ranges from 0.1 to 0.5 kWh/kg [2, 3]—substantially lower than gasoline, which can exceed 10 kWh/kg [6]. This considerable disparity in energy density presents a formidable barrier to the electrification of long-distance maritime transport.

In response to the energy density limitations of lithium-ion batteries, researchers and policymakers have increasingly explored the use of abundant and inexpensive solar electricity to produce alternative fuels, primarily through electrolysis. This approach has given rise to a diverse landscape of electro-fuel options, which can be systematically organized into four broad classifications:

- **Simple electro-fuels** - hydrogen and ammonia, which represent the most straightforward products of electrolytic processes

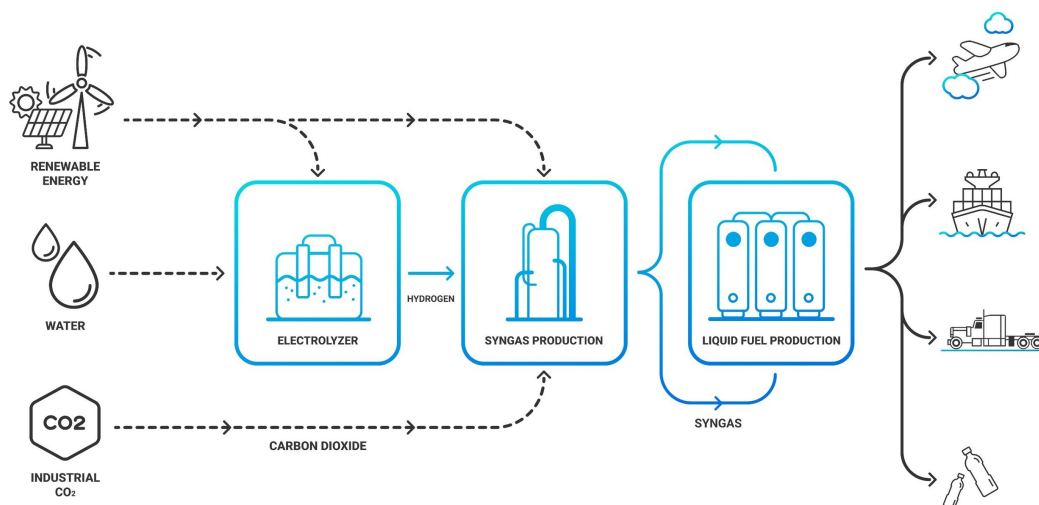


Figure 4: High Level Process Diagram for synthetic hydrocarbon production from renewable electricity [14]

- **Synthetic hydrocarbons** - primarily methane and methanol, whose production pathways are illustrated in Figure 4, which depicts the high-level process for synthesizing these fuels from low-carbon electricity

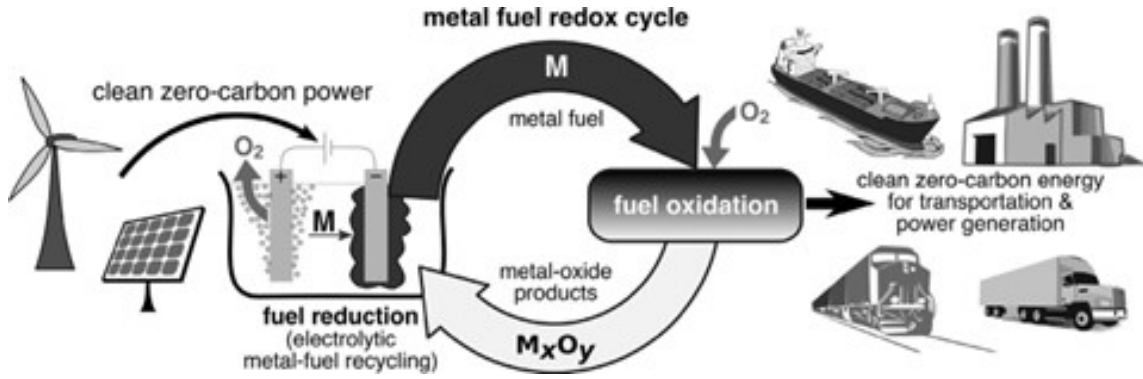


Figure 5: Metal based electro-fuels as secondary energy carriers [15]

- **Metal-based electro-fuels** - including iron, aluminium, magnesium, silicon, and boron. Figure 5 demonstrates the high-level process by which these metal-based electro-fuels can function as recyclable secondary energy carriers, offering a distinctive closed-loop energy storage paradigm
- **Metal hydrides (hydrogen carriers)** - such as MgH₂, AlH₃, LiBH₄, and NaAlH₄, providing an alternative means of storing and transporting hydrogen in a more dense and stable form than its gaseous state

In the following subsections, a preliminary analysis is conducted to compare the mass energy and volumetric energy densities of these various electro-fuel options in order to understand their viability for marine shipping applications.

1.1.1 High Level Energy Density Analysis

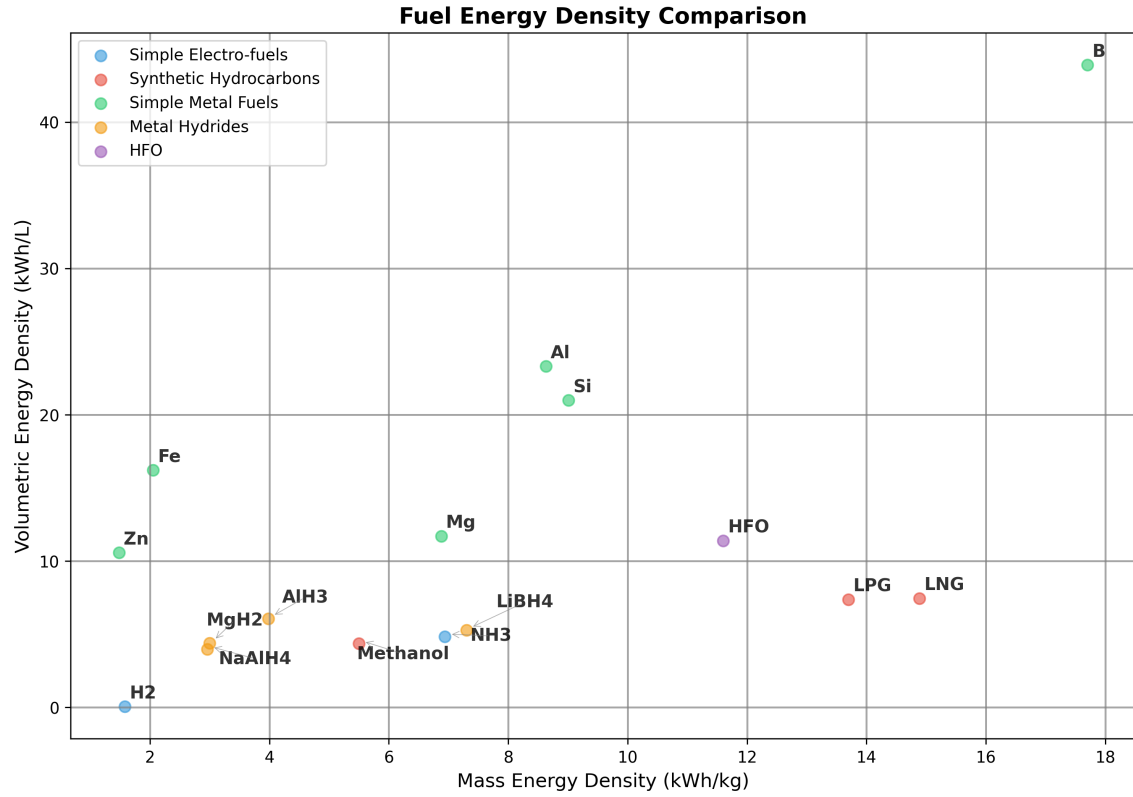


Figure 6: Simplified Energy Density Analysis. Data Analysis can be found in the Appendix. Adapted from [16]

Note: 1) Pressure Cylinder H2 is 25°Celsius 500 bar

2) Liquid NH3 is -33°Celsius 1 bar. Energy needed for cracking for NH3 to H2 is ignored in this table and all subsequent calculations.

Figure 6 presents the fuel energy density calculations for the various electro-fuel options currently under investigation for marine applications. Heavy Fuel Oil (HFO) serves as the reference fuel in these comparisons, as it remains the dominant fuel source for global marine shipping due to its low cost and widespread availability.

Hydrogen, which is being explored as a potential solution for several hard-to-decarbonise sectors including shipping and aviation, requires pressurisation at approximately 500 bar. This compression requirement drastically diminishes the fuel’s energy density, presenting significant challenges for practical implementation. Even methanol, which is considered a relatively straightforward drop-in replacement for marine shipping and has garnered substantial support from major shipping companies such as Maersk [28], exhibits significantly lower mass and volumetric energy densities compared to HFO.

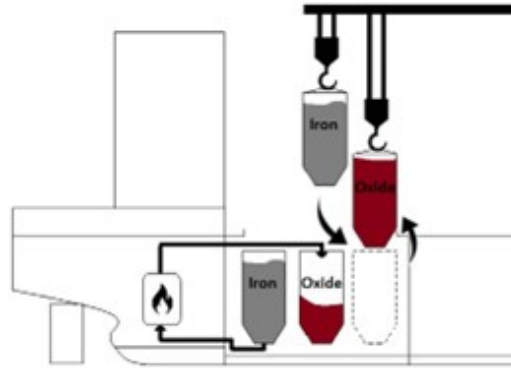


Figure 7: Proposed bunkering procedure for metal fuels (iron powder in this specific case) [17]

As illustrated in Figure 6, metal fuels demonstrate considerable promise in terms of both mass and volumetric energy densities, despite the relatively limited research effort devoted to their development. All metal fuels examined display higher volumetric energy densities than HFO, with boron demonstrating superior performance across all available electro-fuel options and surpassing even HFO itself. However, metal fuels present numerous complications that must be addressed for practical deployment. To make metal fuels economically viable, the metal oxide by-products generated during combustion cannot simply be discharged into the ocean. Instead, these by-products must be retained onboard the vessel and offloaded at ports for subsequent recycling using renewable energy sources, as shown in Fig 5. The bunkering procedure for a metal fuels system is depicted in Figure 7. It is crucial to recognise that energy density calculations which fail to account for the mass and volume of the metal oxide by-products can be highly misleading and do not reflect the true practical performance of these fuel systems.

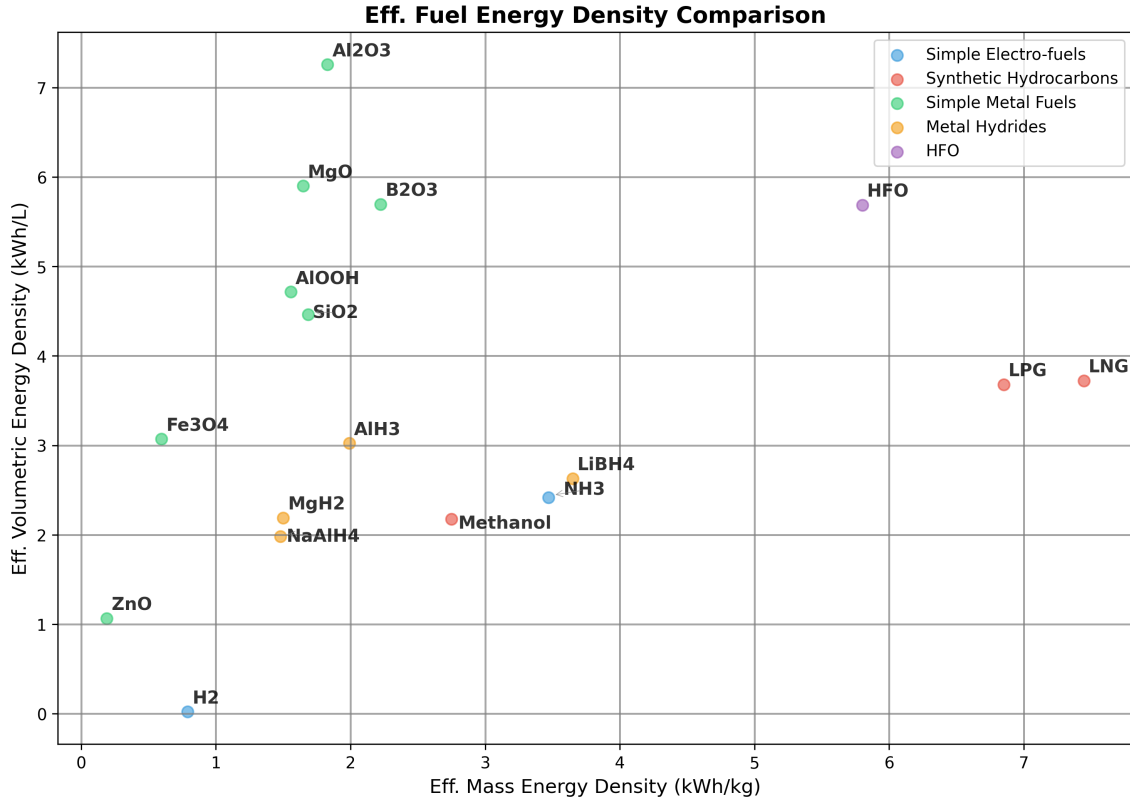


Figure 8: Effective Energy Density Analysis. Data Analysis can be found in the Appendix. Adapted from [16]

Note: 1) Pressure Cylinder H₂ is 25°Celsius 500 bar

2) Liquid NH₃ is -33°Celsius 1 bar. Energy needed for cracking for NH₃ to H₂ is ignored in this table and all subsequent calculations.

3) The engine efficiency for hydrogen and hydrocarbon combustion is assumed to be around 50%

4) The engine efficiency for the metal fuels is assumed to be 40%. This number is theoretically as no such system currently exists for marine shipping. More information about the metal combustion will be discussed in the following sections.

5) For the metal hydrides, the energy needed to free the stored hydrogen is not considered in this calculation.

1.1.2 Effective Energy Density Analysis

To gain a more comprehensive understanding of the practicality of the different electro-fuel options, an analysis of effective energy densities must be conducted. Effective energy density is defined as the energy density after accounting for engine efficiency, but in the case of metal fuels, it additionally incorporates the weight and volume associated with carrying the metal oxide by-products post-combustion. Figure 8 presents the results from the effective energy density analysis for the various electro-fuel options available. For metal fuels, the effective energy density represents the worst-case scenario of continuously carrying the by-products post-combustion throughout the voyage. In practice, the effective energy density for metal fuels will likely be higher than these calculations suggest, since the by-products can be partially offloaded at ports for collection and subsequent processing at metal reduction facilities.


It should be noted that this is a highly simplified analysis, as the mass and volume of the engines and metal reactors have been deliberately excluded from consideration. Furthermore, there is currently no real-world commercially available marine engine that utilises metal fuels, and therefore an efficiency of approximately 40% has been assumed for these calculations. The complete methodology and detailed calculations for the effective energy density analysis can be found in the Appendix.

As demonstrated in Figure 8, metal fuels remain competitive with the energy density of HFO even after accounting for the metal oxide by-products, particularly with respect to volumetric energy density. Although the mass energy density of the most promising metal fuel candidates, such as aluminium and silicon, remains lower than that of methanol, it is still substantially higher than commercially available electrochemical batteries. The superior volumetric energy densities are of particular significance, given that in practice the metal fuel system will necessitate two sets of storage tanks—one for storing the fuel and another for storing the by-products. This characteristic is also likely to prove advantageous for marine applications where space is at a premium, such as yachts, cruise ships, and container shipping. In later sections, the viability of using aluminium as a marine fuel is discussed in detail, given its promising performance following the effective energy density calculations.

1.2 Aluminium-Water Combustion

Using the energy density analysis from the previous sub-section, aluminium metal emerges as the most promising candidate for use in marine applications. Although it cannot match HFO and other fossil fuels in terms of mass energy density, it demonstrates competitive performance with respect to volumetric energy density. The higher volumetric energy density of aluminium fuel is particularly advantageous for marine applications where space is at a premium, such as yachts, cruise ships, and container ships. Additionally, in practice, the vessel will utilise two storage tanks—one for storing the aluminium powder fuel and another for storing the aluminium oxide by-product, which can be collected later at ports or refuelling stations for recycling.

Aluminium offers several other significant advantages that make it an attractive fuel candidate. It is the third most abundant metal in the Earth’s crust, ensuring long-term availability and resource security [1, 29]. Furthermore, aluminium production is already a massive global industry, as the metal’s properties make it exceptionally useful across numerous applications. There exists a well-established electrochemical process for producing aluminium from aluminium oxide, known as the Hall-Héroult process. This industrial process can be rendered entirely zero-carbon if the electricity is sourced from renewable energy and the electrolyzers make use of inert anodes, thereby eliminating carbon emissions from the production cycle [30].



Equation 1 demonstrates how aluminium reacts with water to produce heat and hydrogen gas. Equation 2 subsequently shows how this hydrogen gas can then be combusted to produce water and additional heat. Together, these equations reveal that to utilise the full chemical energy potential of the aluminium-water system, both the heat generated from the metal-water reaction and the heat produced from the hydrogen combustion must be harnessed. This metal-water reaction, also known as wet cycle combustion, has already found application in several specialized domains, including ALICE rockets developed for NASA [31] and underwater propulsion applications employed by the American and Russian militaries [32].

1.3 Reactor Design

Overview

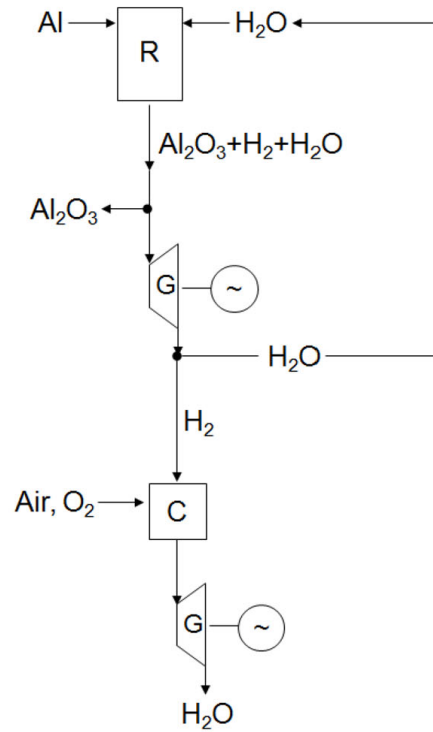


Figure 9: Simplified Overview of Metal-Water Propulsion System[4]

Note: R = metal-water reactor, G = steam generator, C = hydrogen combustion chamber

The metal-water propulsion system, as illustrated in Fig 9, demonstrates a novel approach to maritime propulsion. In this system, seawater from the ocean is mixed with aluminium powder from the fuel tank within a specialized metal-water reactor. The resulting reaction generates three key outputs: hydrogen, thermal heat, and aluminium oxide by-product, with the latter being separated into a dedicated storage tank. The system harnesses energy through two pathways: the thermal heat is utilized to drive a steam engine, while the produced hydrogen can be combusted in a separate chamber to generate high-temperature steam for powering an additional steam engine.

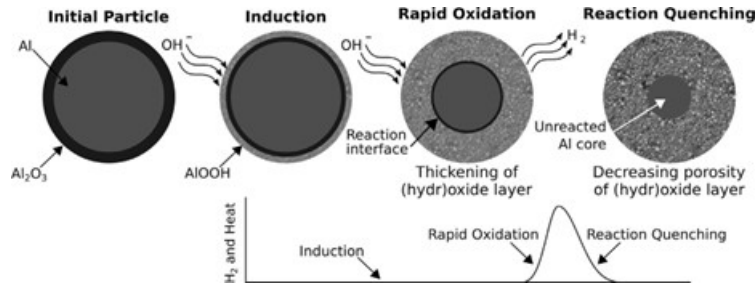


Figure 10: Schematic of the three reaction stages of aluminium with water at low temperatures, including a sketch of the initial dry particle for reference. Also sketched is the characteristic hydrogen-production curve showing the induction, rapid oxidation, and quenching stages [6]

Fig 10 illustrates the reaction pathway for the low temperature aluminium-water reaction, depicting an aluminium particle encased by a thin, inert aluminium oxide coating that must be overcome to facilitate metal-water oxidation. The metal-water reactor design requires careful optimization to achieve appropriate reaction rates for marine propulsion applications, while simultaneously maximizing hydrogen yield to enhance both the efficiency and mass energy density of the aluminium fuel.

The reaction rate and hydrogen yield can be enhanced through:

- Increased temperature and/or pressure conditions
- Reduced aluminium powder particle size
- Reduced aluminium powder to water ratio
- Implementation of various catalysts (detailed in following sub-section) [6, 4, 33]

1.3.1 Low Temperature Metal-Water Reactors

The aluminium-water reaction pathway for hydrogen generation has garnered significant international research attention, with most approaches focusing on nano-sized aluminium powder combined with catalysts at low temperatures. This approach involves reducing the aluminium powder to nano-sized particles and employing various catalytic methods such as alkaline solutions and ball milling the aluminium powder with other metals such as lithium and gallium, or salts such as NaCl. The primary aim of these methods is to increase the exposed surface area of the aluminium particles and prevent the protective layer of aluminium oxide from stopping or slowing down the reaction [34, 33]. This enables the metal-water reaction to take place below 120°C. Companies such as Found Energy are working to facilitate the metal-water reaction at room temperature and pressure [35].

This metal-water reactor design comes with both advantages and disadvantages. One advantage is that the reaction takes place quickly and enables the system to rapidly increase or decrease energy output to meet shifting load demands. However, this design also presents significant disadvantages:

- **High fuel production costs:** The production of nano-sized particles that also need to be ball milled with catalyst metals or salts requires an entire production chain and is likely to increase fuel costs substantially [36].
- **Elevated transport and handling costs:** The high reactivity of the nano-sized particles with water is likely to make transport and handling costs very high, as the metal reacts with water to produce hydrogen, which is a highly combustible gas and can independently contribute to climate change [37]. The higher production and handling costs for the fuel are likely to damage the economic case for this technology, since fuel costs constitute a large percentage of the operating costs for marine shipping, which is also a low-margin industry.

- **Low-grade heat output and reduced energy density:** As discussed in the previous sections, approximately half of the chemical potential energy of the aluminium metal is released as heat when reacted with water (as shown in equations 1 and 2). To maximise the round-trip efficiency of the metal-water reactor, this heat energy must be utilised for engine power. However, in these low-temperature reactors, the heat output is low-grade and unsuitable for use in traditional and high-efficiency steam engines [34]. The low-grade heat could be used by Stirling engines, but these engines have low power-to-weight ratios and have not been mass-produced so far like other heat engines such as diesel or gas turbines have [38]. The low-grade heat could also perhaps be upgraded using heat pumps and used in conjunction with Organic Rankine Cycle engines, but this increases the system complexity and the technology risks for the entire system [39]. The inability to utilise the low-grade heat also reduces the effective mass and volumetric energy density of the metal fuel by half.

Although the low-grade heat cannot be used for engine power, it can be used for other heating applications such as hot water production or indoor spas [40]. These applications are particularly useful in the yacht and cruise ship markets.

1.3.2 High Temperature Metal-Water Reactor

High-temperature metal-water reactors operate at 250–400°C and 15–25 MPa for optimal reaction rates [36]. These reactors can use micron-sized particles instead of nano-sized particles as in the case of low-temperature metal-water reactors. Although high-temperature metal-water reactors have garnered less research focus relative to low-temperature reactors, they come with some significant advantages, especially relating to marine shipping applications:

- **Lower fuel production costs:** Micron-sized particles are much cheaper and simpler to produce industrially compared to nano-sized particles [36, 4, 34].
- **Improved fuel handling and transport:** The micron-sized particles are also inert at room temperature and pressure, as opposed to nano-sized particles which can readily react with water at room temperature (depending on the catalytic process that is being used). Because of the fuel’s inert nature, it makes them easier to transport and handle, which further improves the economic case for these reactors.

- **High-grade heat output and improved energy efficiency:** High-temperature reactors produce high-grade heat output in the form of a steam and hydrogen mixture. This high-grade heat can be used to power high-efficiency steam engines, which nearly doubles the round-trip energy efficiency of aluminium as a secondary energy carrier [34]. It also increases the mass and volumetric energy densities of the aluminium fuel as more useful energy can be created using the same kilogram of fuel.

Fuel Type	Fuel Mass Density (kWh/kg)	Engine Efficiency	By-Product to Fuel Weight Ratio	Final Energy Density (kWh/kg)
Al powder (ref.)	8.61	0.40 (ass.)	x	3.44
Al(OH) ₃ by-product	8.61	0.40 (ass.)	2.89	1.19
AlOOH by-product	8.61	0.40 (ass.)	2.22	1.55
Al ₂ O ₃ by-product	8.61	0.40 (ass.)	1.89	1.82

Table 1: Comparison of different Al–H₂O by-product scenarios. Adapted from [2, 3, 4, 5, 6, 1]

Fuel Type	Volume Density (kg/L)	Final Volumetric Energy Density (kWh/L)
Al powder (ref.)	2.7	9.30
Al(OH) ₃ by-product	2.42	2.88
AlOOH by-product	3.03	4.70
Al ₂ O ₃ by-product	3.97	7.23

Table 2: Volumetric Energy Densities of different Al–H₂O combustion scenarios. Adapted from [2, 3, 7, 8, 9, 10, 11]

- **Superior metal oxide by-product:** The aluminium-water reaction can produce three main by-products: Al(OH)₃, AlOOH, and Al₂O₃. The by-product produced can change the effective mass energy density of the fuel system. The lowest energy density happens with Al(OH)₃, while the highest is with Al₂O₃, as shown in Tables 1 and 2. In Fig 11 we can see that as temperature and pressure increase, the probability of producing Al₂O₃ instead of Al(OH)₃ increases, thus further increasing the effective mass and volumetric energy density of the aluminium fuel system. Al₂O₃ can also be used directly as the input in the Hall–Héroult process, as opposed to Al(OH)₃, which needs to be processed into Al₂O₃ first [40].

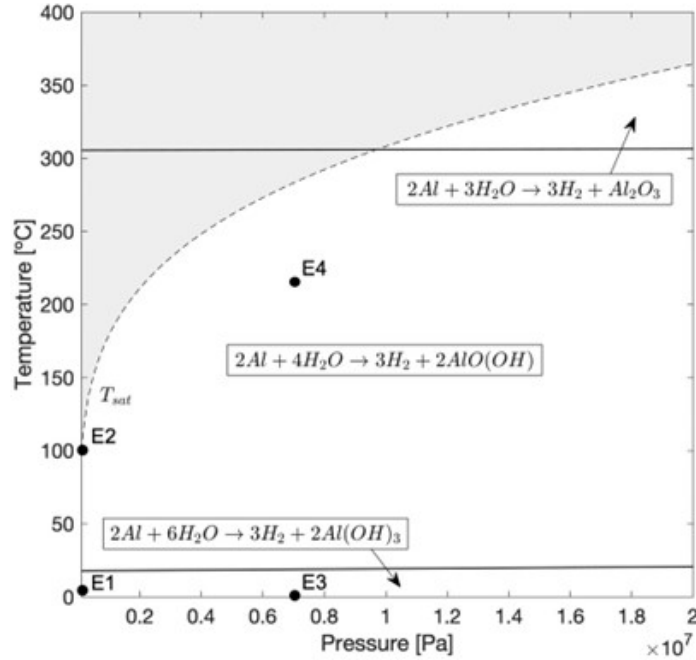


Figure 11: Al–H₂O reaction transition diagram extrapolated to 10 MPa. Labels E1-E4 show conditions used for experimental validation [18]

However, high-temperature reactors come with their own disadvantages:

- **Extended reactor start-up time:** It could take some time for the reactor to heat up, which can be up to 15–30 minutes depending on the size of the reactor. This problem can be mitigated by the use of hybrid electric propulsion using electrochemical batteries that work as a buffer storage system as the reactor heats up. Hybrid electric systems can mitigate the impact on performance and manoeuvrability caused by the longer start-up time. These hybrid electric systems have been widely used in the automotive sector for decades and have already been gaining traction in the marine shipping sector [41]. Hybrid electric designs were also used to manage the longer start-up time for aluminium powder powered submarine and UUV systems that were researched by the American military [32].
- **Higher reactor manufacturing costs:** The reactor for the high-temperature system is likely to be more expensive since it needs to handle the higher temperature and pressure.

1.3.3 Summary Tables

Parameter	LT-MWR	HT-MWR
Particle Size	Nano-sized particles	Micron-sized particles
Catalysts	Range of special alloys (Li, Ga, Hg, etc.)	No catalysts
Temperature and Pressure	Below 120°C (can operate at room temperature depending on catalyst)	250–400°C and 15–25 MPa
Metal By-product	Al(OH) ₃ or AlOOH	AlOOH or Al ₂ O ₃
Worst Case Mass Energy Density	0.60 or 0.78 kWh/kg	1.55 or 1.82 kWh/kg
Worst Case Volumetric Energy Density	1.44 or 2.35 kWh/L	4.70 or 7.23 kWh/L
Thermal Heat Utilization	Difficult due to low temperature	Possible with simple steam turbines
Fuel Production Costs	Higher (smaller particles and ball milling alloys)	Lower (larger particles and low catalysts)
Round-trip Energy Eff.	11–13% (if no heat is utilized)	23–25%
Fuel Transport Costs	Higher (very reactive at room temp.)	Lower (mostly inert at room temperature)
Fuel Handling Safety	Lower	Higher
Reactor Costs	Lower	Higher (to withstand high temperature & pressure)
Reactor Start-up Time	Lower (ability to load follow)	15–30 minutes (better for baseloads)

Table 3: Comparison of Low Temperature Metal-Water Reactors (LT-MWR) and High Temperature Metal-Water Reactors (HT-MWR)

1.4 Economics of Aluminium Fuel

1.4.1 The Long Term Trends

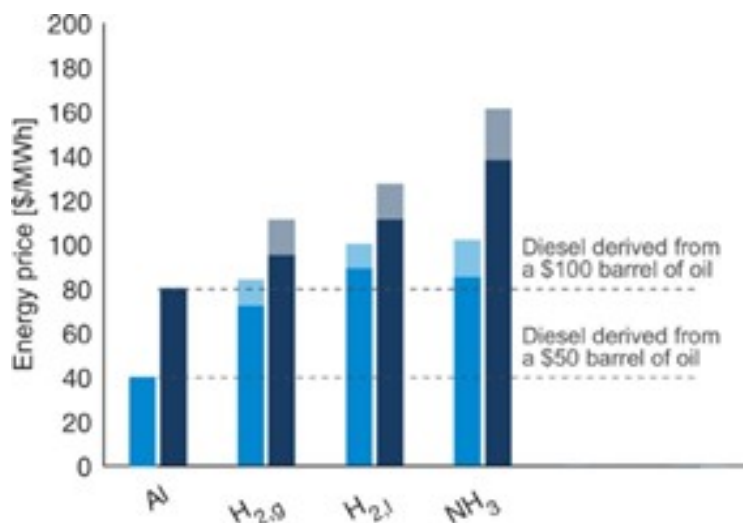


Figure 12: Aluminium fuel vs other electrofuels and diesel (The bars show the price of energy derived from low-carbon energy carriers, if the input electricity price were set to \$36/MWh (dark blue) or \$26/MWh (light blue). The pale region at the top of each bar represents the uncertainty related to the required inputs.) [1]

According to researchers at McGill University, Canada, if both the heat and hydrogen from the aluminium-water reaction are utilized for power generation at 40% efficiency, aluminium’s round-trip efficiency as an electro-fuel reaches approximately 23-25%, making it comparable to hydrogen [42] and superior to ammonia [43].

The cost of electro-fuels like aluminium can be estimated based on electricity prices, while diesel is tied to crude oil prices. As shown in Figure 12, aluminium becomes cost-competitive with diesel when electricity prices fall between \$26-36/MWh and oil prices range from \$50-100 per barrel.

Aluminium also holds a cost advantage over rival electro-fuels such as hydrogen (both gas and liquefied forms) and ammonia. In OECD countries, industrial electricity rates range from \$45-143/MWh, with an average of \$100/MWh [44]. In regions with abundant renewable energy, such as Norway and Quebec, where rates are as low as \$45/MWh and \$27/MWh, aluminium becomes even more competitive in these markets [45].

1.4.2 The Emerging Green Aluminium Supply Chain

The economic case for aluminium as a recyclable energy carrier depends not only on electricity prices and round-trip efficiency, but also on the carbon intensity of aluminium production itself. For decades, the conventional Hall-Héroult process has been highly carbon-intensive for two fundamental reasons:

- **Very high electricity consumption** – Primary aluminium smelting typically requires 14–16 MWh of electricity per tonne of metal produced. In coal-dependent grids, this translates into a large carbon footprint.
- **Consumable carbon anodes** – The anodes used in conventional cells are made of baked carbon. During normal operation, these anodes oxidise to release carbon dioxide directly from the process, not just from the electricity source.

Together, these factors have made virgin aluminium one of the most emission-heavy industrial metals. Furthermore, the Hall-Héroult process was traditionally thought to require stable, inflexible baseload electricity. Aluminium smelters were designed to run continuously at a fixed power draw, making them a poor match for variable renewable electricity from solar and wind power.

However, several recent projects are challenging these long-held assumptions, pointing toward a future green aluminium supply chain that is both low-carbon and grid-interactive.

Photovoltaic direct-current (DC) aluminium smelting in Yunnan, China

A novel DC-powered smelting system has been demonstrated that directly integrates photovoltaic generation with aluminium electrolysis. Key achievements include:

- DC power supply efficiency of at least **98%**, a significant improvement over the $\sim 80\%$ efficiency of traditional AC-coupled photovoltaic systems [46].
- Stabilisation of the electrolytic process by controlling current fluctuations on the DC bus to within $\pm 1.5\%$, overcoming a major technical barrier to direct solar-powered smelting [46].

This technology has already been deployed at **eight plant sites**, with a total installed capacity of **252 MW**, demonstrating that direct solar-powered aluminium production is scaling beyond the laboratory [47].

The EnPot process from New Zealand

The EnPot system provides, for the first time, dynamic control of the heat balance of aluminium smelting pots across an entire potline. Key capabilities include:

- Energy consumption and aluminium production can be increased or decreased by as much as $\pm 30\%$ **almost instantaneously** [48].
- Smelters can reduce power draw during periods of grid stress or low renewable output, and increase draw when surplus renewable electricity is available.
- This transforms the smelter from a passive end-user of power into a “**virtual battery**” for the electricity network, enabling deeper penetration of wind and solar generation [48].

Crucially, the EnPot process is no longer a theoretical concept. It is being deployed in **real-world projects in Germany and China**, proving that flexible aluminium smelting can operate alongside heavy industrial demand and variable renewable grids [49].

Ceramic-based inert anodes

Perhaps the most transformative development is the ongoing commercialisation of inert anodes (ceramic or metal-based) to replace the century-old consumable carbon anodes. Inert anodes do not oxidise during electrolysis, eliminating the direct CO_2 emissions from the anode reaction. When paired with renewable electricity, the entire Hall-Héroult process becomes **completely zero-carbon** [30]. Several consortia (including Rusal, Alcoa, and Rio Tinto’s ELYSIS partnership) are now scaling this technology [50].

Taken together, these three innovations – DC photovoltaic smelting, EnPot’s load-flexible potlines, and inert anodes – are rapidly removing the historical carbon penalty from aluminium production. For the aluminium-water propulsion system proposed in this work, an emerging green aluminium supply chain means that the fuel can be truly low-carbon from well-to-wake, not only during onboard combustion. This strengthens both the environmental and economic case for aluminium as a marine fuel, particularly as renewable electricity becomes cheaper and more widespread.

1.5 Technology Development Pathway

1.5.1 Barriers to Entry in Container Shipping

The maritime shipping industry has historically been conservative in its adoption of new propulsion technologies. This reluctance stems from the sector’s high capital costs and persistently low operating margins, which leave little room for experimental or unproven systems. Consequently, any novel engine or fuel system must first obtain certification from the International Maritime Organization (IMO), a process that typically requires extensive operational data and can take up to a decade. This lengthy and expensive approval pathway presents a formidable barrier to the introduction of a completely new fuel–engine combination, even in scenarios where high carbon taxes or stringent emissions regulations might otherwise favour low-carbon alternatives.

Given these challenges, a direct assault on the container shipping market with aluminium-water propulsion is unlikely to succeed in the near term. Moreover, while solar and battery costs are falling sharply, a robust green aluminium production industry has yet to emerge. Realistic projections suggest that at least 10–15 years will be required for this supply chain to mature and for aluminium fuel to reach cost parity with heavy fuel oil (HFO) and other hydrocarbons. Therefore, a beachhead market must be identified—one in which the technology can be developed, demonstrated, and refined through a “learning by doing” process, while generating the operational track record needed for eventual IMO certification. [51]

1.5.2 Luxury Yachts and Superyachts as an Ideal Beachhead

The most promising initial market for aluminium-water propulsion systems is the luxury yacht and superyacht segment. These vessels are typically purchased by Ultra-High-Net-Worth Individuals (UHNWIs), defined as individuals with a net worth of US\$30 million or more. The global UHNWI population is expected to grow by approximately 33% between 2025 and 2030 [52], driving strong demand for bespoke, high-end vessels.

Unlike container shipping, which is a commoditised market driven almost exclusively by cost per tonne-mile, the superyacht market places a premium on product differentiation, innovation, and environmental stewardship. UHNWIs are also more likely to tolerate a significant green premium during the early years of technology development, while the aluminium-water propulsion system is being refined and while green aluminium fuel has yet to reach cost parity with conventional fuels. This tolerance for higher upfront costs provides a critical financial bridge for the technology.



Figure 13: Modern Electric Yachts with Integrated Solar Panels [19]



Figure 14: The Gotland Horizon X By Austal Panels [20]

Indeed, several green yachting options already exist, including fully battery-electric yachts powered by integrated solar panels (as shown in Fig 13). Furthermore, Austal—Australia’s largest shipbuilder—is developing a catamaran ferry called the Gotland Horizon X (as shown in Fig 14), which features a lightweight “green aluminium” hull and can be powered entirely by green hydrogen [20]. These developments indicate a strong and growing appetite for low-carbon, novel vessel designs within the premium marine segment.

1.5.3 Regulatory Pathway and Certification Advantages

Equally important are the regulatory differences between commercial shipping and the superyacht sector. IMO certification for container shipping follows a rigid, top-down process that demands extensive pre-approved data. In contrast, superyacht certification is handled primarily by private classification societies such as Registro Italiano Navale (RINA), Lloyd’s Register (LR), and DNV. These societies employ a flexible, bottom-up, risk-based approach, often engaging in bespoke negotiations with builders and owners. They are specifically equipped to approve novel systems and one-off builds, making them far more accommodating to innovative propulsion technologies [53, 54].

1.5.4 Pathway to Broader Adoption

If aluminium-water combustion systems can be successfully commercialised in the luxury yacht market, the operational data generated will greatly simplify the subsequent IMO certification process for container shipping applications. This strategy mirrors the path taken by Tesla in the automotive industry: the original Tesla Roadster—a high-performance, low-volume sports car—served as a beachhead to develop battery and electric drivetrain technology, generate real-world data, and build brand credibility before moving into mass-market vehicles [55, 51]. By targeting yachts and superyachts as the initial product development segment, the aluminium fuel system can follow an analogous learning-by-doing trajectory, ultimately paving the way for large-scale deployment in deep-sea shipping.

2 Research Questions

2.1 System Requirements for Yacht Applications

While deep-sea shipping remains the ultimate decarbonisation target, accounting for approximately 70% of the industry’s fuel consumption and carbon emissions [27], the luxury yacht and superyacht segment offers an ideal beachhead for the development of aluminium-water propulsion systems. This market allows for iterative technology refinement, real-world operational data collection, and the establishment of flexible regulatory pathways.

However, the performance requirements for an aluminium-water reactor vary significantly across the different classes of superyachts that are popular in the market today. These include motor yachts, sailing superyachts, explorer yachts, and pocket superyachts (24–40 metres). To guide engineering design effectively, the following technical parameters must be systematically determined for each class:

- Minimum mass energy density
- Minimum volumetric energy density
- Power demand profile (minimum, maximum, and average power)
- Minimum range
- Total energy demand between refuelling stops
- Detailed energy demand profile for marine engine operations

2.2 Metal-Water Reactor Design

Based on the analysis presented in Section 1.3, this research explicitly adopts the high-temperature metal-water reactor (HT-MWR) as the design architecture under investigation. The case for this choice over low-temperature alternatives rests on four compounding advantages:

1. **Lower fuel production costs.** The HT-MWR operates with micron-sized aluminium particles, which are substantially cheaper and simpler to produce industrially than the nano-sized particles required by low-temperature designs.
2. **Safer and cheaper fuel transport and handling.** Micron-sized particles are inert at room temperature and pressure, unlike nano-sized particles, which can react readily with ambient moisture. This inert character significantly reduces transport and handling costs and improves the overall economic case for aluminium as a marine fuel.
3. **Higher round-trip energy efficiency.** The HT-MWR produces high-grade thermal output—heat at temperatures suitable for use in steam engines and other external heat engines. Harnessing this thermal output alongside the hydrogen combustion effectively doubles the round-trip energy efficiency of the aluminium fuel cycle, and correspondingly increases its effective mass and volumetric energy density, as demonstrated in Section 1.3.
4. **Superior by-product for recycling.** At the elevated temperatures and pressures of the HT-MWR, the aluminium-water reaction preferentially produces Al_2O_3 rather than $\text{Al}(\text{OH})_3$ or AlOOH . As shown in Tables 1 and 2, Al_2O_3 gives the most favourable effective energy density of any by-product scenario. Crucially, it can also be fed directly into the Hall–Héroult recycling process with minimal pre-processing, which reduces costs and complexity across the entire aluminium fuel supply chain.

Scope of This Research

The overarching research question this project addresses is:

Can a high-temperature aluminium-water reactor be designed and operated to provide reliable propulsion power for superyachts, and under what conditions does it do so safely and efficiently?

However, given the timeframe of a Master’s research programme, the scope must be carefully bounded. Table 4 formalises what falls within and outside the scope of this study, and identifies how the outputs of this work will directly enable each downstream research activity.

Research Activity	Ac-	In Scope	Out of Scope	How This Study Enables Future Work
Industry requirements matrix		Yes	—	Defines power, range, and energy density targets that bound all downstream reactor design
Reaction parameter characterisation (T, P, particle size, fuel-to-water ratio)		Yes	—	Produces the experimental dataset for reactor geometry and operating point selection
By-product composition analysis (Al(OH) ₃ , AlOOH, Al ₂ O ₃)		Yes	—	Determines achievable effective energy density and recycling compatibility under real operating conditions
Seawater vs. distilled water reactant comparison		Yes	—	Establishes whether onboard seawater can be used directly, and specifies any pre-treatment or filtration requirements
Reactor start-up time and transient load characterisation		Yes	—	Defines the battery buffer specification and informs control system design required for hybrid-electric integration

Continued on next page...

Research tivity	Ac-	In Scope	Out Scope	of	How This Study Enables Future Work
Marine safety protocols (bunkering, dust control, emergency re- sponse)		Yes	—		Provides the safety evidential basis for future certification submissions to RINA, LR, and DNV
Reactor geometry and material selection		Yes (lab-scale, indicative)	Full-scale design		Lab-scale findings provide the basis for scaled engineering design in future work
Preliminary cost estimation (reactor and aluminium fuel)		Yes (indicative, order-of-magnitude)	Final production costs		High-level estimates inform the economic feasibility case and identify where further cost refinement is needed
Engine and turbine selection and integration		—	Yes		Steam output conditions characterised here define turbine inlet specifications for future work
Battery sizing for hybrid-electric buffer		—	Yes		Reactor transient data from this study directly bounds the battery energy and power requirements
Control system development		—	Yes		Reactor transient data and power modulation results from this study provide the input requirements for control system design
Full-scale stress testing and classification society approval		—	Yes		Experimental safety protocols and datasets developed here form the evidential basis for future certification submissions

Table 4: Scope boundary for the metal-water reactor research and its relation to future work.

Two points in the scope boundary deserve particular emphasis. First, the preliminary cost estimates for the lab-scale reactor and aluminium powder fuel are intended to give an indicative, order-of-magnitude picture of economic viability, not final production costs. These numbers will need to be refined substantially once a full-scale commercial system has been designed. Second, the reactor designed and built in this project is a laboratory-scale prototype intended for systematic parameter testing. It is not directly equivalent to the system that would eventually be deployed aboard a commercial superyacht, and should not be interpreted as such.

Reactor Research Deliverables

With this scope established, the research decomposes into the following primary questions:

1. Reaction parameter optimisation How do temperature (250–400°C), pressure (up to 25 MPa), aluminium particle size, and fuel-to-water ratio individually and jointly influence hydrogen yield and thermal heat output? The target thermal output is a steam-hydrogen mixture at 400–500°C—the temperature range required to drive external heat engines such as steam turbines. The goal of this investigation is to identify the combination of parameters that delivers stable, controllable output at this temperature while maximising hydrogen yield.

2. Aluminium particle size characterisation The reaction rate of the aluminium-water system increases as particle size decreases, but smaller particles are more expensive to produce and more difficult to handle safely. This investigation will therefore identify the coarsest particle size that still achieves the reaction rates and thermal output required to meet the power demand profile of the target superyacht class identified in Section 2.1, since this coarsest viable size defines the most commercially attractive operating point.

3. By-product composition analysis The by-product produced by the aluminium-water reaction—whether $\text{Al}(\text{OH})_3$, AlOOH , or Al_2O_3 —has a major impact on the practical performance of the fuel system, for two reasons. First, the yacht must carry the by-product in a dedicated storage tank throughout the voyage, so the mass and volume of the by-product directly affects the effective energy density available for propulsion, as shown in Tables 1 and 2. Second, delivering Al_2O_3 rather than $\text{Al}(\text{OH})_3$ to recycling facilities eliminates an intermediate processing step before the Hall–Héroult process, reducing cost and complexity across the supply chain.

This investigation will therefore identify the specific temperature and pressure conditions under which the reaction shifts from producing $\text{Al}(\text{OH})_3$ or AlOOH toward Al_2O_3 as the dominant by-product, and will characterise how fuel-to-water ratio and particle size interact with this shift.

4. Seawater reactant characterisation For a vessel operating at sea, seawater is the naturally available reactant. The ability to use seawater directly as the oxidiser would deliver significant operational and maintenance benefits for aluminium-powered marine vessels. However, seawater introduces chemical variables that distilled water experiments cannot capture:

- Dissolved chloride ions and sulphates, which may modify the passivation behaviour of the aluminium oxide layer and alter the induction, rapid oxidation, and quenching stages of the reaction
- Magnesium and sodium salts, which could affect by-product composition
- Biological matter and suspended particulates, which may affect reactor internals and feed systems over time

This investigation will compare the hydrogen yield and thermal output of the aluminium-water reaction using distilled water versus seawater. Any filtration or pre-treatment required for the seawater intake will be identified and documented, since this information is essential for a proper cost-benefit analysis of seawater as the operational oxidiser.

5. Reactor start-up time and transient load characterisation Much of the existing research on high-temperature aluminium-water reactors—including work conducted at McGill University—is directed at baseload electricity generation for remote communities or mining operations, where the reactor reaches a steady state and holds it. A marine propulsion system operates in a fundamentally different environment: power demand changes continuously as the vessel manoeuvres, accelerates, cruises, and docks.

This investigation will characterise the reactor’s power modulation capability and compare the results against the power demand profiles established for the target superyacht class in Section 2.1. This characterisation is explicitly scoped to describe the reactor’s transient behaviour, not to design the battery buffer system that will bridge the gap during start-up and load transitions—battery sizing is identified in Table 4 as future work. However, the data produced here will be the primary input that enables future researchers and engineers to correctly specify that buffer, design appropriate control systems, and select compatible engine configurations.

6. Marine safety systems Aluminium powder introduces a set of hazards that are not commonly encountered in conventional marine fuel systems and are not fully addressed by existing maritime fuel codes:

- **Fire and explosion risk** from highly combustible aluminium dust clouds
- **Hydrogen liberation** from the exothermic reaction of aluminium powder with moisture, presenting both a fire risk and a potential contribution to climate change if vented
- **Chronic inhalation risk**—prolonged exposure to aluminium dust can cause pulmonary fibrosis (aluminosis)
- **Special extinguishing requirements**—water-based extinguishing agents are prohibited in areas where aluminium powder is present; Class D agents and inert atmospheres are required

The development and validation of safety protocols covering bunkering procedures, leak detection, dust control, and emergency response constitutes a distinct research deliverable of this study. These protocols will be developed in consultation with Registro Italiano Navale (RINA), Lloyd’s Register (LR), and DNV, to ensure that the procedures adopted are consistent with the risk-based certification frameworks that will govern eventual onboard deployment, and that the documentation generated is structured to support future certification submissions.

Trade-offs and Design Decisions

As with any engineering system, the experimental results from this research will surface trade-offs that cannot all be optimised simultaneously. All such trade-offs will be transparently documented and justified as part of this study, providing future engineers with the information they need to make informed design decisions as the metal-water propulsion system is developed further toward commercial deployment.

3 Methodology

3.1 Industry Research

To develop a robust understanding of system requirements for the superyacht market, this research will involve structured outreach to key industry participants, including yacht builders, classification societies (Registro Italiano Navale, Lloyd’s Register, and DNV), naval architects, and vessel owners (Ultra-High-Net-Worth Individuals). Semi-structured interviews will be conducted with each group and, with consent, recorded for later transcription and thematic analysis.

The interviews will capture the following quantitative and qualitative information:

- Typical energy demand profiles for different superyacht classes (motor yachts, sailing yachts, explorer yachts, and pocket superyachts)
- Minimum and maximum power output requirements during various operational phases (docking, cruising, manoeuvring)
- Expected refuelling costs and maximum acceptable refuelling time per stop
- Total energy demand between planned refuelling stops
- Minimum mass and volumetric energy density targets derived from onboard storage constraints
- Tolerance for novel technology risks and willingness to pay a green premium

Interviews with classification societies will also clarify the regulatory pathway for safety certification of a novel aluminium-fuel propulsion system, addressing:

- The documentation required for prototype approval
- The operational data thresholds needed to move from one-off builds to broader certification
- Specific safety concerns related to aluminium powder handling, hydrogen production, and high-temperature/pressure reactor operation

Understanding these regulatory requirements early will shape the project’s data collection and documentation strategy, ensuring experimental results are recorded in a way that directly supports future certification.

Crucially, conversations with both classification societies and potential customers will help identify which superyacht market segments offer the greatest promise for initial large-scale deployment of this low-carbon fuel system. Factors such as regulatory flexibility, typical cruising ranges, risk tolerance, and willingness to accept a green premium vary considerably across motor yachts, sailing yachts, explorer yachts, and pocket superyachts. By analysing these segment-specific characteristics, the research will prioritise one or more classes as the first target for deployment. This prioritisation then directly narrows the system requirements for the metal-water reactor:

- If explorer yachts emerge as the lead segment, the design will emphasise maximum range and total energy between refuelling stops.
- If pocket superyachts are prioritised, volumetric energy density and compact reactor packaging become paramount.

The insights from all interviews will be synthesised into a formal requirements matrix that will guide the subsequent design and experimental validation of the metal-water reactor.

3.2 Metal-Water Reactor Design

This section describes the experimental programme for the high-temperature metal-water reactor (HT-MWR) component of this research. The programme is structured to address each of the six research deliverables identified in Section 2.2, building on the system requirements established through the industry research in Section 3.1.

Reactor Vessel and Instrumentation

The central piece of experimental equipment is a laboratory-scale high-pressure reactor vessel designed to operate at temperatures of 250–400°C and pressures up to 25 MPa. The reactor body will be constructed from SS316L stainless steel, which provides the required tensile strength, corrosion resistance in high-temperature steam environments, and wide commercial availability of pressure-rated fittings. All pressurised components will be specified with pressure ratings exceeding 300 bar at 450°C. For seawater experiments, reactor sections in contact with the fluid will be constructed from or lined with Hastelloy C-276 or Inconel 625 to resist chloride-induced stress corrosion cracking. The reactor will be heated externally using a resistance heater, with thermal insulation applied along its full length to minimise heat loss. The following instrumentation will be installed as standard across all experiments:

- **Temperature:** Four K-type thermocouples distributed axially along the reactor exterior, with the average reading used as the representative reactor temperature, consistent with the approach of Vlaskin et al. [36]
- **Pressure:** Two calibrated high-pressure transducers — one on the pump inlet and one measuring direct reactor pressure — with continuous high-frequency data logging
- **Real-time gas flow:** A thermal mass flow controller on the gas outlet line, providing continuous volumetric measurement of gas leaving the reactor
- **Hydrogen concentration:** An electrochemical hydrogen sensor positioned in the gas outlet stream and exhaust ventilation line, serving both as a safety monitor and a supplementary yield measurement
- **Slurry injection:** A variable-speed high-pressure plunger pump with remote speed control, enabling precise and adjustable mass flow rates of aluminium–water slurry into the reactor

All sensor outputs will be logged centrally from a remote data acquisition console outside the reactor enclosure.

Aluminium Powder Characterisation

Seven discrete particle size grades will be tested, spanning the 10–500 micrometre range, with target nominal sizes of approximately 10, 25, 50, 100, 200, 350, and 500 μm . These will be selected from commercially available aluminium powder products, covering the size range studied in prior high-temperature aluminium–water research in Russia [36] and Canada [56]. Before use in any reaction experiment, each powder batch will be characterised using:

- **Laser diffraction particle size analysis:** To verify actual size distributions (D10, D50, and D90 values) against nominal supplier specifications
- **Scanning electron microscopy (SEM):** To inspect particle morphology, surface condition, and the native aluminium oxide passivation layer
- **Inductively coupled plasma optical emission spectroscopy (ICP-OES):** To quantify elemental impurities, particularly silicon and iron content

Silicon content will be screened carefully, as Boudreau et al. [56] demonstrated that increasing silicon mass fraction from 0.06% to 0.54% reduced aluminium oxidation rate by an order of magnitude under supercritical water conditions. Only powders with silicon content below 0.1% by mass will be used in the primary parameter optimisation experiments.

Reaction Parameter Optimisation

Experiments will systematically vary temperature (250–400°C), pressure (saturated vapour pressure at each temperature, with supplementary runs up to 25 MPa), water-to-aluminium mass ratio (5, 7, 9, and 12), and all seven particle size grades. Each parameter combination will be repeated a minimum of three times to establish repeatability. The primary measured outputs are:

1. **Hydrogen yield:** Calculated from reactor pressure rise using the ideal gas law and cross-validated against the mass flow controller reading on the gas outlet
2. **Thermal heat output:** Derived from the reactor temperature–time curves recorded by the four thermocouples

The target output condition is a steam–hydrogen mixture at 400–500°C. The coarsest particle size that still achieves this target while meeting the power demand requirements of the superyacht class from Section 3.1 will be identified as the most commercially attractive operating point.

By-product Composition Analysis

Following each experiment, solid products will be extracted, cooled, and vacuum-dried before analysis using two complementary methods:

- **Powder X-ray diffraction (PXRD):** To identify and quantify the crystalline phases present — specifically $\text{Al}(\text{OH})_3$, AlOOH , and the Al_2O_3 polymorphs — with phase proportions quantified by Rietveld refinement of the diffraction patterns
- **Thermogravimetric analysis (TGA):** As a complementary method to cross-validate phase composition based on characteristic mass loss temperatures

Residual unreacted aluminium will also be quantified by PXRD, providing a direct conversion degree measurement alongside the hydrogen yield calculations. By-product phase data will be mapped against the temperature and pressure conditions of each experiment to identify the threshold conditions required to shift the reaction toward Al_2O_3 as the dominant product.

Seawater Reactant Characterisation

Rather than a simple binary comparison between distilled water and seawater, this research defines four distinct water treatment categories to isolate which components of seawater affect the reaction:

- **Category A — Distilled water:** The baseline case
- **Category B — Synthetic seawater:** Distilled water with dissolved salts at open-ocean concentration (≈ 35 g/L, ASTM D1141), isolating ionic effects from biological and particulate contamination
- **Category C — Coarse-filtered natural seawater:** Natural seawater passed through a $50\text{ }\mu\text{m}$ filter, removing organisms and macro-particulates while retaining dissolved ions and fine particles
- **Category D — Fine-filtered natural seawater:** Natural seawater passed through a $50\text{ }\mu\text{m}$ pre-filter followed by a $1\text{ }\mu\text{m}$ membrane filter, removing virtually all suspended particulates while retaining dissolved ions

Natural seawater samples for Categories C and D will be collected at both open-ocean (≈ 35 g/L) and coastal (≈ 15 g/L) salinities. The hydrogen yield, thermal output, and by-product composition for each water type will be compared against the distilled water baseline. The filtration complexity and estimated cost of each category will be documented, enabling a cost-benefit analysis of onboard seawater pre-treatment for a deployed marine system.

Reactor Start-up and Transient Load Characterisation

This is the most novel component of the experimental programme. Prior high-temperature aluminium–water reactor research — including work conducted at McGill University — has focused on baseload electricity generation for stationary applications where the reactor reaches a steady state and holds it. No prior work has characterised HT-MWR behaviour under the dynamic load-following conditions required for marine propulsion, where power demand changes continuously as the vessel manoeuvres, accelerates, cruises, and docks.

The reactor’s output will be characterised across four discrete power settings that reflect the operational modes of a marine propulsion system:

- **Off:** No aluminium injection; reactor held at thermal standby temperature
- **Low:** Approximately 25% of rated hydrogen output, corresponding to harbour manoeuvring and low-speed transit conditions
- **Medium:** Approximately 50% of rated hydrogen output, corresponding to moderate cruising
- **High:** 100% of rated hydrogen output, corresponding to full cruising speed

The absolute output targets for each level will be derived from the superyacht power demand profiles established in Section 3.1.

Real-time hydrogen yield will be measured continuously throughout all transient experiments using two simultaneous methods:

1. **Pressure–time derivative method:** The rate of pressure change (dP/dt) from the high-frequency pressure transducer, combined with the known gas space volume, gives the instantaneous molar hydrogen production rate via a modified ideal gas equation, consistent with the computational procedure of Vlaskin et al. [36]. This provides high temporal resolution.

2. **Mass flow controller method:** The gas outlet thermal mass flow controller provides a direct real-time volumetric measurement of gas leaving the reactor, cross-validated against hydrogen concentration from the in-line electrochemical sensor.

Both measurement streams will be logged with timestamps synchronised to the pump control input signals, enabling direct calculation of the lag time between a control input change and the corresponding output change — the primary dataset required by future engineers designing control systems for this reactor.

Three power modulation techniques will be investigated, each chosen for its relevance to real-world continuous marine propulsion rather than the batch operation characterised in prior research:


1. **Slurry injection rate modulation:** Adjusting the pump speed to change the aluminium mass flow rate entering the reactor. This is the most direct analogue to fuel injection control in a conventional engine and is expected to produce the fastest dynamic response, making it the most commercially viable approach for a deployed marine system.
2. **Fuel-to-water ratio modulation:** Adjusting the aluminium slurry and water supply rates independently to tune the fuel-to-water ratio while holding total throughput approximately constant. This may help maintain reactor pressure stability during load transitions without requiring large changes in total flow rate.
3. **Temperature modulation:** Varying heater power to shift the reactor operating temperature within the 250–400°C range, exploiting the strong temperature-dependence of aluminium oxidation kinetics. This method has the slowest response time due to reactor thermal mass, but may serve as a coarse power adjustment complementing injection rate control.

Each technique will be tested independently, and promising combinations will be tested together. For each transition between power settings, the response lag, rise time, steady-state output, and any overshoot or undershoot in hydrogen production will be recorded and reported. The results will be compared directly against the superyacht power demand profiles from Section 3.1, and will form the primary dataset enabling future researchers and engineers to design control systems, size battery buffers, and select engine configurations for this propulsion architecture.

Safety, Verification, and Approval

The experimental programme involves concurrent hazards from aluminium powder handling, continuous hydrogen gas production, and high-pressure and high-temperature reactor operation. A comprehensive safety protocol addressing each risk category, together with the plan for independent peer review and formal university approval of the experimental design, is provided in full in [Appendix A](#). In summary, all experimental work will be conducted in a dedicated ventilated enclosure with Class D fire suppression, continuous hydrogen monitoring with automatic equipment interlocks, and a minimum of two researchers present at all times. A detailed laboratory experimental proposal incorporating the full safety protocol, risk register, and reactor specifications will be submitted for independent review by experienced academics and for formal approval by the university's laboratory safety committee. No high-pressure or high-temperature experimental work will commence before this approval is granted. This comprehensive proposal and its approval will be completed by the **end of the first quarter** of the research project.

4 Proposed Project Time-line

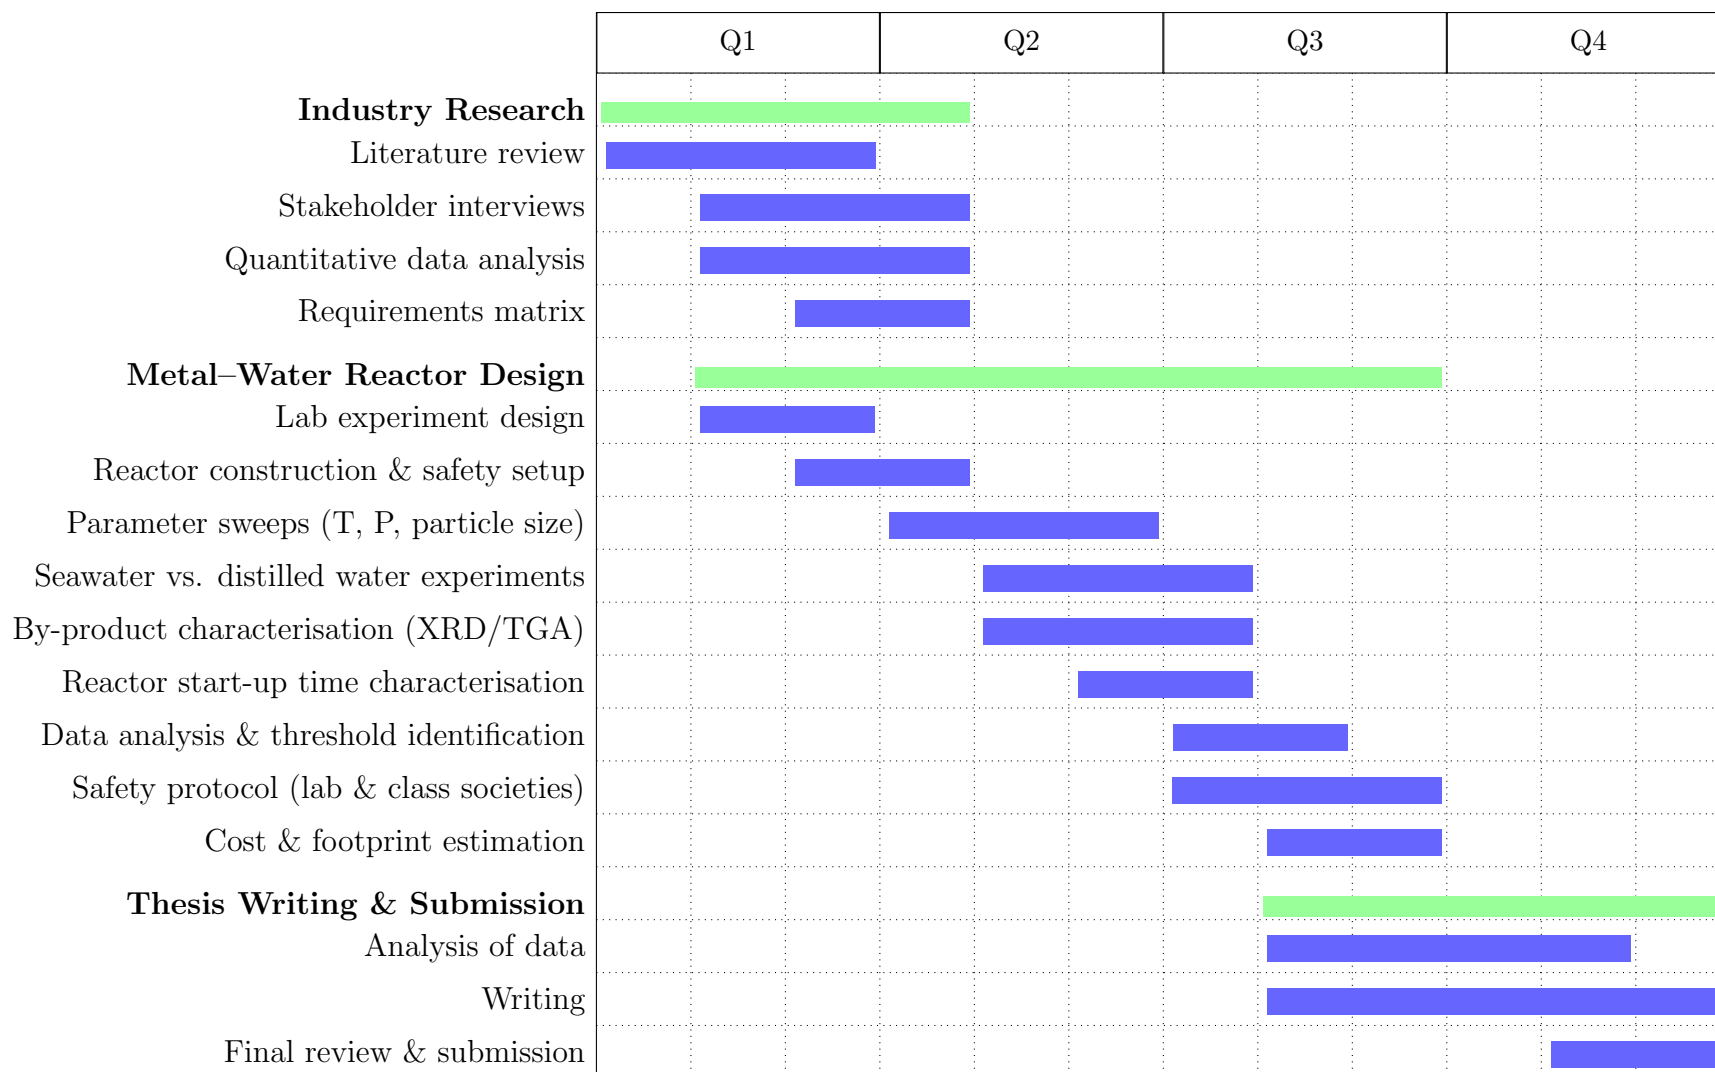

5 References

- [1] K. A. Trowell, S. Goroshin, D. L. Frost, and J. M. Bergthorson, “Aluminum and its role as a recyclable, sustainable carrier of renewable energy,” *Appl. Energy*, vol. 275, p. 115112, Oct. 2020.
- [2] B. Dunn, H. Kamath, and J.-M. Tarascon, “Electrical energy storage for the grid: a battery of choices,” *Science*, vol. 334, pp. 928–935, Nov. 2011.
- [3] F. T. Wagner, B. Lakshmanan, and M. F. Mathias, “Electrochemistry and the future of the automobile,” *J. Phys. Chem. Lett.*, vol. 1, pp. 2204–2219, July 2010.
- [4] M. S. Vlaskin, G. E. Valyano, A. Z. Zhuk, and E. I. Shkolnikov, “Oxidation of coarse aluminum in pressured water steam for energy applications,” *Int. J. Energy Res.*, vol. 44, pp. 8689–8715, Sept. 2020.
- [5] “Energy Density of some Combustibles — The Geography of Transport Systems — transportgeography.org.” <https://transportgeography.org/contents/chapter4/transportation-and-energy/combustibles-energy-content/>. [Accessed 25-11-2024].
- [6] J. M. Bergthorson, “Recyclable metal fuels for clean and compact zero-carbon power,” *Prog. Energy Combust. Sci.*, vol. 68, pp. 169–196, Sept. 2018.
- [7] PubChem, “Density, gasoline (nominal: 0.7429 g/ml @ 15 degrees c).” <https://pubchem.ncbi.nlm.nih.gov/substance/483747003>. Accessed: 2024-11-26.
- [8] PubChem, “Aluminum.” <https://pubchem.ncbi.nlm.nih.gov/compound/5359268>. Accessed: 2024-11-26.
- [9] PubChem, “Aluminum hydroxide.” <https://pubchem.ncbi.nlm.nih.gov/compound/10176082>. Accessed: 2024-11-26.
- [10] D. Barthelmy, “Boehmite mineral data.” <http://webmineral.com/data/Boehmite.shtml>. Accessed: 2024-11-26.
- [11] PubChem, “Aluminum oxide.” <https://pubchem.ncbi.nlm.nih.gov/compound/9989226>. Accessed: 2024-11-26.
- [12] M. Roser, “Why did renewables become so cheap so fast?,” *Our World in Data*, 2020. <https://ourworldindata.org/cheap-renewables-growth>.

- [13] M. Maisch, “BNEF: Lithium-ion battery pack prices fall to \$108/kWh, stationary storage becomes lowest price segment - Energy Storage — ess-news.com.” <https://www.ess-news.com/2025/12/09/bnef-lithium-ion-battery-pack-prices-fall-to-108-kwh-stationary-storage-becomes-lowest-price-segment/#pid=1>. [Accessed 12-12-2025].
- [14] Infinium, “Infinium™ Enters into Strategic Alliance with Denbury for Ultra-Low Carbon Fuels Projects in Texas, Continuing Development Momentum — prnewswire.com.” <https://www.prnewswire.com/news-releases/infinium-enters-into-strategic-alliance-with-denbury-for-ultra-low-carbon-fuels-projects-in-texas-continuing-development-momentum-301489124.html>. [Accessed 13-01-2025].
- [15] J. M. Bergthorson, S. Goroshin, M. J. Soo, P. Julien, J. Palecka, D. L. Frost, and D. J. Jarvis, “Direct combustion of recyclable metal fuels for zero-carbon heat and power,” *Appl. Energy*, vol. 160, pp. 368–382, Dec. 2015.
- [16] “Combustion of Fuels - Carbon Dioxide Emission — engineeringtoolbox.com.” https://www.engineeringtoolbox.com/co2-emission-fuels-d_1085.html. [Accessed 10-01-2025].
- [17] J. de Kwant, R. Hekkenberg, A. Souflis-Rigas, and A. A. Kana, “Exploring the potential of iron powder as fuel on the design and performance of container ships,” *Int. Shipbuild. Prog.*, vol. 70, pp. 3–28, June 2023.
- [18] P. Godart, J. Fischman, K. Seto, and D. Hart, “Hydrogen production from aluminum-water reactions subject to varied pressures and temperatures,” *Int. J. Hydrogen Energy*, vol. 44, pp. 11448–11458, May 2019.
- [19] “® OFFICIAL Silent Yachts — Solar powered yachts — silent-yachts.com.” <https://silent-yachts.com/>. [Accessed 14-05-2026].
- [20] “Austal in LOI for 130-meter Gotland Horizon X hydrogen-fueled cat - Maritime and Salvage Wolrd News - Latest Ship Technologies — marine-salvage.net.” <https://marine-salvage.net/en/maritime-news/austal-in-loi-for-130-meter-gotland-horizon-x-hydrogen-fueled-cat/>. [Accessed 14-05-2026].
- [21] H. Ritchie, “Cars, planes, trains: where do co2 emissions from transport come from?,” *Our World in Data*, 2020. <https://ourworldindata.org/co2-emissions-from-transport>.

- [22] H. Ritchie, “Sector by sector: where do global greenhouse gas emissions come from?,” *Our World in Data*, 2020. <https://ourworldindata.org/ghg-emissions-by-sector>.
- [23] “2023 IMO Strategy on Reduction of GHG Emissions from Ships — imo.org.” <https://www.imo.org/en/OurWork/Environment/Pages/2023-IMO-Strategy-on-Reduction-of-GHG-Emissions-from-Ships.aspx>. [Accessed 24-10-2024].
- [24] C. McKerracher, “China’s Clean-Truck Surprise Defies the EV Slowdown Narrative — BloombergNEF — about.bnef.com.” <https://about.bnef.com/insights/clean-transport/chinas-clean-truck-surprise-defies-the-ev-slowdown-narrative/>. [Accessed 12-12-2025].
- [25] M. Barnard, “And So It Begins: 1,000-Kilometer Route Yangtze Container Ship With Swappable Batteries - CleanTechnica — cleantechnica.com.” <https://cleantechnica.com/2023/07/31/and-so-it-begins-1000-kilometer-route-yangtze-container-ship-with-swappable-batteries/>. [Accessed 12-12-2025].
- [26] M. P. Release, “Maersk and CATL Forge Global Strategic Partnership in Supply Chain Electrification and International Logistics — maersk.com.” <https://www.maersk.com/news/articles/2025/10/10/maersk-and-catl-forge-global-strategic-partnership-in-supply-chain>. [Accessed 12-12-2025].
- [27] “The New Energy Trade: Harnessing Australian renewables for global development — superpowerinstitute.com.au.” <https://www.superpowerinstitute.com.au/work/the-new-energy-trade>. [Accessed 26-11-2024].
- [28] “Maersk orders six methanol powered vessels — maersk.com.” <https://www.maersk.com/news/articles/2023/06/26/maersk-orders-six-methanol-powered-vessels>. [Accessed 13-01-2025].
- [29] N. Klopčič, I. Grimmer, F. Winkler, M. Sartory, and A. Trattner, “A review on metal hydride materials for hydrogen storage,” *J. Energy Storage*, vol. 72, p. 108456, Nov. 2023.
- [30] H. Kvande and W. Haupin, “Inert anodes for Al smelters: Energy balances and environmental impact,” *JOM (1989)*, vol. 53, pp. 29–33, May 2001.

- [31] G. Risha, T. Connell, R. Yetter, V. Yang, T. Wood, M. Pfeil, T. Pourpoint, and S. Son, “Aluminum-ICE (ALICE) propellants for hydrogen generation and propulsion,” in *45th AIAA/ASME/SAE/ASEE Joint Propulsion Conference & Exhibit*, (Reston, Virginia), American Institute of Aeronautics and Astronautics, Aug. 2009.
- [32] D. F. Waters and C. P. Cadou, “Modeling a hybrid rankine-cycle/fuel-cell underwater propulsion system based on aluminum–water combustion,” *J. Power Sources*, vol. 221, pp. 272–283, Jan. 2013.
- [33] A. Bolt, I. Dincer, and M. Agelin-Chaab, “A review of unique aluminum–water based hydrogen production options,” *Energy Fuels*, vol. 35, pp. 1024–1040, Jan. 2021.
- [34] J. M. Bergthorson, Y. Yavor, J. Palecka, W. Georges, M. Soo, J. Vickery, S. Goroshin, D. L. Frost, and A. J. Higgins, “Metal-water combustion for clean propulsion and power generation,” *Appl. Energy*, vol. 186, pp. 13–27, Jan. 2017.
- [35] “Technology Works; Found Energy — found.energy.” <https://found.energy/technology-works/>. [Accessed 12-01-2026].
- [36] M. S. Vlaskin, E. I. Shkolnikov, and A. V. Bersh, “Oxidation kinetics of micron-sized aluminum powder in high-temperature boiling water,” *Int. J. Hydrogen Energy*, vol. 36, pp. 6484–6495, June 2011.
- [37] T. Sun, E. Shrestha, S. P. Hamburg, R. Kupers, and I. B. Ocko, “Climate impacts of hydrogen and methane emissions can considerably reduce the climate benefits across key hydrogen use cases and time scales,” *Environmental Science & Technology*, vol. 58, no. 12, pp. 5299–5309, 2024. PMID: 38380838.
- [38] K. Wang, S. R. Sanders, S. Dubey, F. H. Choo, and F. Duan, “Stirling cycle engines for recovering low and moderate temperature heat: A review,” *Renew. Sustain. Energy Rev.*, vol. 62, pp. 89–108, Sept. 2016.
- [39] D. M. van de Bor, C. A. Infante Ferreira, and A. A. Kiss, “Low grade waste heat recovery using heat pumps and power cycles,” *Energy (Oxf.)*, vol. 89, pp. 864–873, Sept. 2015.
- [40] M. Y. Haller, D. Amstad, M. Dudita, A. Englert, and A. Häberle, “Combined heat and power production based on renewable aluminium-water reaction,” *Renew. Energy*, vol. 174, pp. 879–893, Aug. 2021.

- [41] M. Kolodziejski and I. Michalska-Pozoga, “Battery energy storage systems in ships’ hybrid/electric propulsion systems,” *Energies*, vol. 16, p. 1122, Jan. 2023.
- [42] A. Escamilla, D. Sánchez, and L. García-Rodríguez, “Assessment of power-to-power renewable energy storage based on the smart integration of hydrogen and micro gas turbine technologies,” *Int. J. Hydrogen Energy*, vol. 47, pp. 17505–17525, May 2022.
- [43] S. Giddey, S. P. S. Badwal, C. Munnings, and M. Dolan, “Ammonia as a renewable energy transportation media,” *ACS Sustain. Chem. Eng.*, vol. 5, pp. 10231–10239, Nov. 2017.
- [44] “World energy statistics (edition 2018),” Mar. 2019. Title of the publication associated with this dataset: IEA World Energy Statistics and Balances.
- [45] “Electricity rates for business customers — hydroquebec.com.” <https://www.hydroquebec.com/business/customer-space/rates/>. [Accessed 24-10-2024].
- [46] L. Wu, Q. Huo, Q. Liu, J. Yin, and J. Yang, “Multi-time-scale optimization and control method for high-penetration photovoltaic electrolytic aluminum plants,” *Energies*, vol. 18, p. 5840, Nov. 2025.
- [47] S. M. Market, “Yunnan aluminum: Pv power generation dc integration into aluminum production power supply technology is an industry first.” <https://news.metal.com/es/newscontent/103901603-SMM-PV-Yunnan-Aluminum-PV-Power-Generation-DC-Integration-into-Aluminum-Production-Power-Supply-Technology-Is-an-Industr>, 2026. [Accessed 17-05-2026].
- [48] M. Dorreen, L. Wright, G. Matthews, P. Patel, and D. S. Wong, “Transforming the way electricity is consumed during the aluminium smelting process,” in *The Minerals, Metals & Materials Series*, The Minerals, Metals & Materials Series, pp. 15–25, Cham: Springer International Publishing, 2017.
- [49] “EnPot demonstrates power flexibility in China smelter trials » EnPot — enpot.com.” <https://enpot.com/media/news/video>. [Accessed 17-05-2026].
- [50] “ELYSIS achieves breakthrough with commercial-size cell: a first in aluminium production using the inert anode technology — riotinto.com.” <https://www.riotinto.com/en/can/news/releases/2025/elysis-achieves-breakthrough-with-commercial-size-cell>. [Accessed 17-05-2026].

- [51] J. Coelen, “What makes a great beachhead market? — doctormarket.fit.” <https://www.doctormarket.fit/p/what-makes-a-great-beachhead-market>. [Accessed 14-05-2026].
- [52] BERNAMA, “GLOBAL UHNW POPULATION SET TO RISE 33 PCT BY 2030, REPORT FINDS — bernama.com.” <https://bernama.com/tv/news.php/news.php/?id=2556029>. [Accessed 14-05-2026].
- [53] “Practical guide for approval of ammonia- or hydrogen-fuelled ships — Hellenic Shipping News Worldwide — hellenicshippingnews.com.” <https://www.hellenicshippingnews.com/practical-guide-for-approval-of-ammonia-or-hydrogen-fuelled-ships-2/>. [Accessed 14-05-2026].
- [54] “Why class societies are not just box tickers — boatinternational.com.” https://www.boatinternational.com/boat-presents/rina-classification-society-class-rules?j=586935&jb=6&l=55_{H}{T}{M}{L}&mid=500009995&sfmc_id=417830332&sfmc_sub=417830332&u=13972977&utm_campaign={B}oat+{B}riefing+251124&utm_id=586935&utm_medium=email&utm_source=sfmc&utm_term={W}hy+class+societies+are+not+just+box+tickers+{B}{P}+{A}{R}{T}{I}{C}{L}{E}+{I}{M}{A}{G}{E}. [Accessed 14-05-2026].
- [55] “New case study takes up Tesla’s entry into the auto industry — MIT Sloan — mitsloan.mit.edu.” <https://mitsloan.mit.edu/ideas-made-to-matter/new-case-study-takes-teslas-entry-auto-industry>. [Accessed 14-05-2026].
- [56] P. Boudreau, F. Osorio-MacCready, J. Blanchet, and J. M. Bergthorson, “Reactivity of commercial aluminum alloys in high-temperature water for hydrogen and heat generation,” *Fuel (Lond.)*, vol. 407, p. 137278, Mar. 2026.

A Laboratory Safety Protocols and Experimental Plan Verification

A.1 Safety Protocols

The experimental programme involves three concurrent categories of hazard that must each be addressed before any laboratory work begins.

Aluminium Powder Hazards

Micron-sized aluminium powder presents four distinct hazards in a laboratory environment. First, aluminium dust clouds are highly combustible and can detonate if ignited above the minimum ignition energy threshold. All powder transfers will therefore be conducted inside a dedicated enclosed glove box maintained under a dry nitrogen atmosphere, with strict prohibition of open flames, electrical sparks, and non-antistatic equipment within five metres of all powder handling areas. Second, aluminium reacts exothermically with ambient moisture, liberating flammable hydrogen gas. All powder handling operations will be conducted under inert atmosphere or with active humidity control maintained below 30% relative humidity, and the reactor will be nitrogen-purged before each loading operation. Third, chronic inhalation of aluminium dust causes pulmonary fibrosis (aluminosis). P100 full-face respirators are mandatory during all powder handling operations; an enclosed handling system is preferred wherever practicable, and post-experiment reactor cleaning will be conducted under wet-suppression conditions to prevent dust re-entrainment. Fourth, standard water-based fire extinguishers are strictly prohibited in any area where aluminium powder is present, as water reacts with aluminium to produce hydrogen. Class D dry-powder extinguishers — copper powder or sodium chloride type — will be stationed at all powder handling positions.

Hydrogen Gas Hazards

Hydrogen has a lower explosive limit (LEL) of 4% in air. A dedicated forced-ventilation exhaust hood will be installed over the reactor gas outlet, maintaining hydrogen concentration below 1% (25% of LEL) at all monitoring points. Electrochemical hydrogen sensors will be positioned in the gas outlet stream and at multiple points within the reactor enclosure, with audible alarms activating at 1% hydrogen concentration and automatic equipment shutdown interlocks engaging at 2%. All equipment will be bonded and earthed to prevent static discharge ignition, antistatic flooring will be installed throughout the reactor area, and synthetic clothing will be prohibited during experiments. All gas line connections will be made with pressure-rated compression fittings rated to at least twice operating pressure, and a nitrogen leak check will be performed before every experiment. All hydrogen produced during experiments that is not captured for measurement will be routed through a catalytic oxidiser before venting to atmosphere, eliminating both the ignition risk and the indirect climate impact of hydrogen release.

High-Pressure and High-Temperature Hazards

All pressurised components will be rated to a minimum of twice the maximum operating pressure (≥ 50 MPa). The reactor vessel will undergo third-party hydrostatic pressure testing annually. A spring-loaded pressure relief valve set at $1.25\times$ operating pressure will be installed, with an independent secondary burst disc as a redundant protection layer. The reactor will be operated from behind a rated polycarbonate blast shield at all times. All reactor external surfaces will be thermally insulated, and heat-resistant gloves and a face shield are mandatory during setup and any access to the reactor area during operation. A formal cooldown and pressure equalisation protocol will be documented and followed before any reactor valve is opened; an interlock will prevent opening any reactor valve while internal pressure exceeds 0.5 MPa. All steam outlet lines will be thermally insulated, labelled with appropriate warning markings, and routed through a condensate trap before reaching the gas measurement instruments.

General Laboratory Controls

A minimum of two researchers must be present during all experimental sessions. A dedicated safety observer role will be assigned for each session, responsible for monitoring all sensor readings in real time and activating the emergency shutdown procedure if any parameter exceeds its safe operating limit. Emergency shutdown procedures will be formally documented and prominently displayed within the laboratory. All researchers involved in the project will complete formal training on these procedures before participating in any experimental work.

A.2 Experimental Plan Verification and University Approval

The experimental programme described in Section 3.2 represents the high-level research plan appropriate for a Master’s proposal. Before any laboratory work begins, this plan must undergo two independent layers of review.

Internal Peer Review

Following completion of the industry research phase in the first six to eight weeks of the project, the detailed experimental design — including the reactor vessel specification, instrumentation layout, full experimental sequences, and safety protocol — will be submitted for review to a panel of at least two independent academics from the university’s mechanical and chemical engineering departments with direct experience in high-pressure reactor systems. This review is intended to identify blind spots in experimental design, instrumentation, and safety provisions that may not be apparent from within the research team. All reviewer comments will be formally documented and the experimental plan revised accordingly before being finalised.

University Laboratory Safety Approval

A comprehensive laboratory experimental proposal — incorporating the full safety protocol, risk register, emergency response procedures, chemical waste disposal plan, and detailed reactor specifications — will be formally submitted to the university’s laboratory safety committee and the relevant departmental review body. This submission will include evidence of compliance with applicable pressure vessel standards and will reference the safety framework developed in consultation with Registro Italiano Navale (RINA), Lloyd’s Register (LR), and DNV as described in Section 2.2. No high-pressure or high-temperature experimental work will commence before this approval is formally granted. The comprehensive proposal and its associated university approval will be completed by the **end of the first quarter** of the research project.