

ORIGINAL ARTICLE

Integrated Soft Ionotronic Skin with Stretchable and Transparent Hydrogel–Elastomer Ionic Sensors for Hand-Motion Monitoring

Guoying Gu,^{1,2} Haipeng Xu,¹ Sai Peng,³ Ling Li,¹ Sujie Chen,³ Tongqing Lu,⁴ and Xiaojun Guo³

Abstract

Skin-like stretchable sensors with the flexible and soft inorganic/organic electronics have many promising potentials in wearable devices, soft robotics, prosthetics, and health monitoring equipment. Hydrogels with ionic conduction, akin to the biological skin, provide an alternative for soft and stretchable sensor design. However, fully integrated and wearable sensing skin with ionically conductive hydrogel for hand-motion monitoring has not been achieved. In this article, we report a wearable soft ionotronic skin (iSkin) system integrating multichannel stretchable and transparent hydrogel–elastomer hybrid ionic sensors and a wireless electronic control module. The ionic sensor is of resistive type and fabricated by curing ionic hydrogel precursor on a benzophenone-treated preshaped elastomer to form a hydrogel–elastomer hybrid structure. The hydrogel–elastomer hybrid iSkin is highly stretchable ($\sim 300\%$ strain), transparent ($\sim 95\%$ transmittance in the visible light range), and lightweight (<22 g). Experiments demonstrate that the fully integrated iSkin system can conformably attach onto the dexterous hands for recognizing the joint proprioception and hand gesture, and understanding the sign language. Our iSkin system would also provide a test bed for customized material selection and construction in a variety of applications.

Keywords: ionotronic skin, ionic sensor, hydrogel–elastomer hybrid, soft and stretchable sensor, hand-motion monitoring

Introduction

SKIN PLAYS AN IMPORTANT ROLE for humans to feel the world.¹ Achieving skin's sensing capability in wearable devices and robotics is a long-lasting challenge. Although many skin-inspired wearable or implantable sensors have been developed for motion detection and health monitoring, they are generally made of rigid and brittle electronic materials without high enough stretchability, resulting in fundamental mismatch and uncomfortable in mechanics with human bodies.^{2–5} Human skin not only has powerful sensory organs but also is soft and stretchable to adapt the body motions. Development of soft and stretchable sensors is of significance in the realm of wearable sensing skins and has

the advantages of higher flexibility, better adaptability, and conformal integration over their rigid counterparts.⁶

Over the years, intensive efforts have been made in skin-inspired stretchable sensors. One clever concept is to exploit inorganic semiconductor materials in the unconventional deterministic thin architectures (such as micropatterned, wavy, or buckled geometries).^{7–10} However, such semiconductor sensors are flexible but not intrinsic stretchable, and complicated structures and fabrication techniques are required for stretchable sensing system design. To support soft and stretchable functionality, the majority of stretchable electronics have been proposed by using the soft conductive electrodes with intrinsic stretchable substrates (such as silicone rubbers).^{11–15} The choice of conductive electrodes

¹Soft Robotics and Biodesign Lab, Robotics Institute, School of Mechanical Engineering, Shanghai Jiao Tong University, Shanghai, China.

²State Key Laboratory of Mechanical System and Vibration, Shanghai Jiao Tong University, Shanghai, China.

³School of Electronics, Information and Electrical Engineering, Shanghai Jiao Tong University, Shanghai, China.

⁴State Key Lab for Strength and Vibration of Mechanical Structures, Department of Engineering Mechanics, Xi'an Jiaotong University, Xi'an, China.

includes conductive fabrics and polymers,^{16–19} organic semiconductor nanocomposites,^{20–22} carbon nanotube films,^{3,23–26} and liquid metals.^{27–30} These conductive electrodes transmit the sensing signals using electrons, whereas sensors in our skin transmit signals using ions.³¹ Alternatively, stretchable ionotronics using the soft ionic conductors have been becoming another promising technology for wearable sensing skins.^{32,33} Hydrogel is one attractive selection as ionic conductors owing to its distinctive attributes, including inherent softness (with the modulus of ~ 8 kPa), high stretchability (beyond ~ 20 times the initial length), transparency, biocompatibility, and/or biodegradability.^{34–40} Currently, various ionic hydrogel conductors have been reported, for instance, ionic cables,^{41,42} strain/pressure sensors,^{43–46} touch panels,⁴⁷ self-healing sensors,^{48,49} and hybrid circuits.^{50,51} These studies have well demonstrated the capability of ionic hydrogel conductors to sense body motions like human fingers. However, efforts to incorporate the multichannel ionic hydrogel sensors into fully integrated and untethered wearable sensing skins for hand joint proprioception and gesture recognition have not been achieved.

In this study we report a highly stretchable transparent wearable soft ionotronic skin (iSkin) system integrating 10-channel hydrogel–elastomer hybrid ionic sensors and a wireless electronic control module (Fig. 1), which conformably attaches onto our hand and monitors the real-time hand motions. The ionic sensor is of resistive type and fabricated by curing hydrogels on a benzophenone-treated preshaped elastomer to form the hydrogel–elastomer hybrid structure. The integrated iSkin system with 10 ionic sensors covers the metacarpophalangeal joint and proximal-interphalangeal joint of each finger for joint proprioception and hand gesture monitoring, which is highly stretchable ($\sim 300\%$ strain),

transparent ($\sim 95\%$ transmittance in the visible light range), and lightweight (<22 g). For ease of usability, we further integrate the iSkin system with a wireless electronic control module consisting of digitizers, a microcontroller, a Bluetooth transceiver, and a cell battery. Flexibly wavy circuit interconnects are used to connect the ionic sensors to the control module. In this sense, the real-time hand motions can be detected by our integrated wireless iSkin system and displayed in distal devices (such as a mobile phone). By experiments, we demonstrate that the integrated wireless iSkin system exhibits the ability to identify various hand motions, including the joint bending, hand posture, gesture, and sign language. The stretchability, transparency, wearability, and soft interaction make our integrated wireless iSkin system promising in various applications such as soft robotics, prosthetics, and wearable medical devices.

Materials and Methods

Synthesis of the ionic hydrogel

The ionic hydrogels are the polyacrylamide (PAAm) hydrogel containing lithium chloride (LiCl). The PAAm–LiCl hydrogels are synthesized by using the acrylamide (AAM; J&K) as the monomer, *N,N'*-methylenebisacrylamide (MBAA; Molbase) as the crosslinker, LiCl monohydrate ($\text{LiCl} \cdot \text{H}_2\text{O}$; Sinopharm Chemical Reagent) as the ionic conductive medium, and 2-ketoglutaric acid (Adamas) as the photoinitiator. The synthesis steps are described as follows. The monomer solution is prepared by mixing AAM, $\text{LiCl} \cdot \text{H}_2\text{O}$, and deionized water at the weight ratio of 9.98%:16.16%:73.86%. MBAA solution is dissolved in deionized water with a weight ratio of 1.2%. Then, the monomer



FIG. 1. Overview of the soft iSkin system integrating 10-channel hydrogel–elastomer hybrid ionic sensors and a wireless electronic control module. iSkin, ionotronic skin. Color images are available online.

solution, MBAA solution, and 2-ketoglutaric acid are mixed with the weight ratio of 96.67%:1.13%:2.20% to form the hydrogel precursor ink for further fabrication. We may mention that LiCl is contained into the hydrogels, not only serving as conductive medium but also as one kind of hygroscopic salts.⁵² To further avoid the dehydration problem of ionic hydrogels, we will encapsulate them with the elastomer layers, which will be detailed in the following development.

Fabrication of hydrogel–elastomer hybrid iSkin

To prevent the dehydration of ionic hydrogels and achieve the robust strain sensing, we fabricate the iSkin with the hydrogel–elastomer hybrid structure. The used elastomer is made of polydimethylsiloxane (PDMS) elastomer (Silpuran film; Wacker), which has good breathability and biocompatibility.⁵³ As shown in Figure 2A, the ionic hydrogel is sandwiched by two PDMS elastomer films to form anti-dehydration structure. To alleviate oxygen inhibition effect and activate elastomer surfaces for the robust bond with ionic hydrogels, benzophenone is used to modify the PDMS elastomer surface.⁴² As shown in Figure 2B to D, we can see that the fabricated hydrogel–elastomer hybrid ionic sensor is highly stretchable ($\sim 300\%$ strain) and transparent ($\sim 95\%$ transmittance in the visible light range).

In Figure 2E, we provide a schematic illustration of the fabrication process for the iSkin system with 10 ionic sensors and the wireless control module. (i) A thin PDMS elastomer film ($100\ \mu\text{m}$) is used as the sensor substrate, and a laser cut mold array for the ionic hydrogel sensors is arranged onto the

substrate according to the distribution of metacarpophalangeal joints and proximal-interphalangeal joints of human hands. After the surface treatment with the benzophenone, the hydrogel precursor ink is injected into the mold through a needle tubing. (ii) Ultraviolet light with 500 W and 365 nm wavelength is applied to initiate the crosslinking for about 20 min. (iii) The mold array is peeled off and electrical circuits including the flexible interconnects and portable control module are integrated onto the elastomer substrate. Notably, the flexible interconnects are made of serpentine shape copper wires for a better stretchability.⁴⁰ (iv) The integrated system is cut into a hand-like shape and packaged by assembling another thin PDMS elastomer film ($100\ \mu\text{m}$), where the pre-elastomer resin (DowCorning Sylgard 184) is used as the adhesive between the two thin PDMS films. Notably, the integrated iSkin system will be further cured for about 1 h under room temperature.

Description of the control module

The wireless electronic control module used in the iSkin system consists of an analog interface with two 8-channel analog switches (NX3L4051; NXP) for multiplexing, a 32-bit microcontroller (STM32L152RC; ST Microelectronics) integrating a 12-bit analog-to-digital converter (ADC), and a Bluetooth transceiver (BC-04-B; Cambridge Silicon Radio). The multiplexing analog interface can read 16 channel inputs in maximum. The 12-bit ADC in the microcontroller converts the analog inputs to digital signals by a series connected load

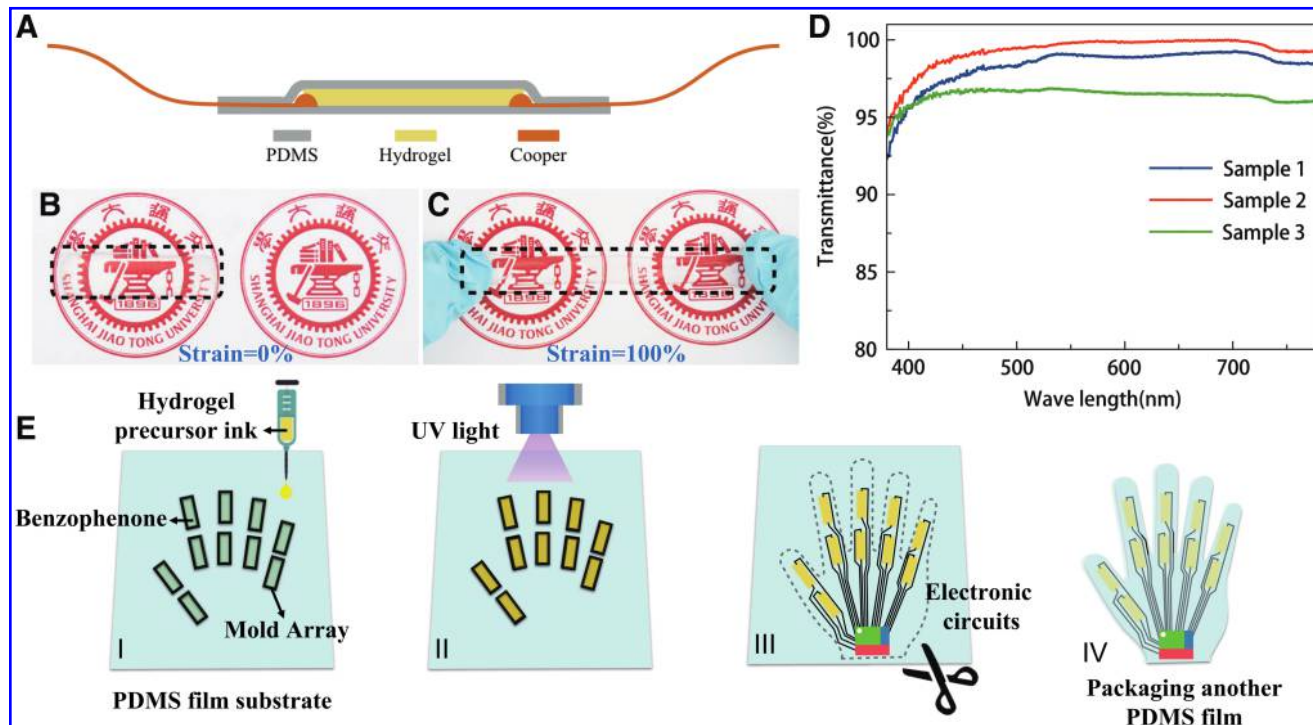


FIG. 2. Fabrication of the soft ionic sensor and iSkin system. (A) Schematic illustration of the ionic sensor in the sandwiched hydrogel–elastomer hybrid structure. The ionic hydrogel layer is strongly bonded to the PDMS films through the benzophenone treatment. (B) The ionic sensor with 0% strain. (C) The ionic sensor with 100% strain. Since the hydrogel ionic sensor is transparent, the black dotted box indicates the real size of the ionic sensors. (D) The transmittance of ionic sensor. (E) Schematic illustration of the fabrication process of our integrated iSkin system as listed from I to IV. PDMS, polydimethylsiloxane. Color images are available online.

resistor with a sampling time of 3 ms for further processing. The Bluetooth module is used to build wireless communications with the mobile phone that can transmit a robust signal up to 10 m. The whole transceiver is powered by a 3.3 V rechargeable Li-ion battery. A software developed in Android is run in the mobile phone to process, store, and display the data.

Results and Discussions

Sensor performance characterization

To thoroughly characterize the performance of our hydrogel–elastomer hybrid ionic sensor, a series of performance indicators are introduced and characterized, including the sensitivity, hysteresis, repeatability, durable stability, and detection limit.¹³

The gauge factor (GF) is used to define the sensitivity

$$GF = \frac{\Delta R/R_0}{\varepsilon},$$

where ΔR is the relative resistance change with respect to the nominal resistance R_0 at zero strain and ε denotes the strain of the sensor. Figure 3A plots $\Delta R/R_0$ as a function of ε by performing cyclic loading up to 100% strain at a frequency of 30 Hz. The GF is ~ 0.7762 , with linearity of $R^2 = 0.9944$ in both loading and unloading directions. The results also show that the hysteresis of our ionic sensor is very low, by comparing with the carbon–grease-based strain sensor.¹⁹ This may be attributed to the robust hydrogel–elastomer hybrid structure for a more uniform resistive distribution during stretching.

Extended use of the sensors is to characterize the repeatability by performing cyclic loading up to 100% strain for 50 cycles. The results indicate that the sensor signals are stable and repeatable (Fig. 3B). Further cyclic tests are performed to show the durable stability of our sensor up to 7 days (Fig. 3C). The experimental data demonstrate that the sensor responses agree well among days and the sensor is still sensitive at the end of the experiment, showing the capability for long time use.

To identify its segment retentivity, we stretch and then hold the sensor for 10 s at increasing strains of 20%, 40%, 60%, 80%, and 100%. The real-time data $\Delta R/R_0$ are plotted as a function of time in Figure 3D. We can see that the segment strains are well distinguished and there is slight signal creep when holding it at the strained state. By putting the sensor on metacarpophalangeal joint of an index finger, we can clearly identify the bending angle of the joint at the increasing angles of 0°, 30°, 60°, and 90° (Fig. 3E). From the results in Figure 3D and E, we can see some fluctuation of the ionic sensors. This may be caused by the following: (i) the motion of the finger is generally dynamic, which cannot be fully steady and (ii) the soft materials, including the PDMS and hydrogels, have the inherent viscoelasticity, which needs certain time to stabilize the responses. To further demonstrate its static stability, we used a linear-guide platform to hold the ionic sensor with a certain strain (i.e., 50%), and the measured results are shown in Figure 3F. It can be seen that the resistance of the sensor is relatively static after the viscoelastic response, which will not influence its sensitivity.

We have also performed tests to show the temperature effects on the sensor in Figure 3G and H. The results dem-

onstrate that around the room temperature (i.e., 27°C in our test), the resistance of the hydrogel sensor is almost steady. However, with the increase of the temperature, the resistance of the sensor slightly changes (for instance, the change will be <0.06 when the temperature increases from 17°C to 30°C).

Finally, we demonstrate that the strain limit of the ionic sensor is $\sim 300\%$ (Fig. 3I), which is higher than stretchability of our skin.⁹ By the experimental characterization, our ionic sensor with the hydrogel–elastomer hybrid structure demonstrates the robust performance over large strains and cyclic loadings, which can satisfy the requirements of a variety of potential applications.

Integrated iSkin system

Next, we fabricate the soft iSkin to adhere to the hand using a kind of water-borne adhesive (Romantic Angel RL-7030) for commercial cosmetics and monitor the hand motions. Since the moduli of the PDMS (~ 10 kPa) and the hydrogel sensors (~ 8 kPa) are much smaller than our skin (between 0.42 and 0.85 MPa⁵⁴), our iSkin system can provide conformal contact with human hands. As shown in Figure 2E, the iSkin system contains 10 embedded hydrogel ionic sensors that cover the metacarpophalangeal joint and proximal interphalangeal joint of each finger. When a finger joint bends, the located sensor accommodates the bending strain, causing correspondingly change in the electrical signal; when the finger straightens, the sensor also recovers to its initial resistance (Fig. 3E). To be a wearable device, we integrate our iSkin with the portable electronic control module using the flexible wavy circuit interconnects.⁴⁰ The control module captures the sensor signals and wirelessly transmits the signals to a mobile phone through the Bluetooth transceiver protocol. The signals can then be real-time displayed in the virtual interface of the remote mobile phone.

The functionality of our iSkin system is demonstrated by a series of tests. In these tests, the fingers sequentially move through multiple finger gestures. Figure 4A shows the real-time responses recorded from the corresponding 10 sensors of our iSkin system. As can be seen, every slight movement of the metacarpophalangeal joint and proximal interphalangeal joint on each finger can be fast and accurately detected, showing the electrical and mechanical robustness of the integrated iSkin system. By the combination of different sensor signals, we can monitor the hand gesture to recognize the digits 0–9 of the American Sign Language and display them in the virtual interface of the mobile phone (Supplementary Movie S1). Figure 4B also shows that our iSkin system can automatically recognize the gestures of the letters S, J, T, and U of the international sign language to composite into SJTU (abbreviation of Shanghai Jiao Tong University) (Supplementary Movie S2). Since the iSkin system is soft, stretchable, wearable, and biocompatible, it is flexible for multiple users.

Applications of the integrated iSkin system

We next demonstrate the potential applications with our integrated iSkin system in daily life. Figure 5A shows the example to control the brake of a bike using the index finger and middle finger of a hand. It can be seen that the iSkin system can monitor the isochronous motions of two fingers while cyclically opening and closing the index and middle fingers to brake. In contrast, when using a mouse, the index

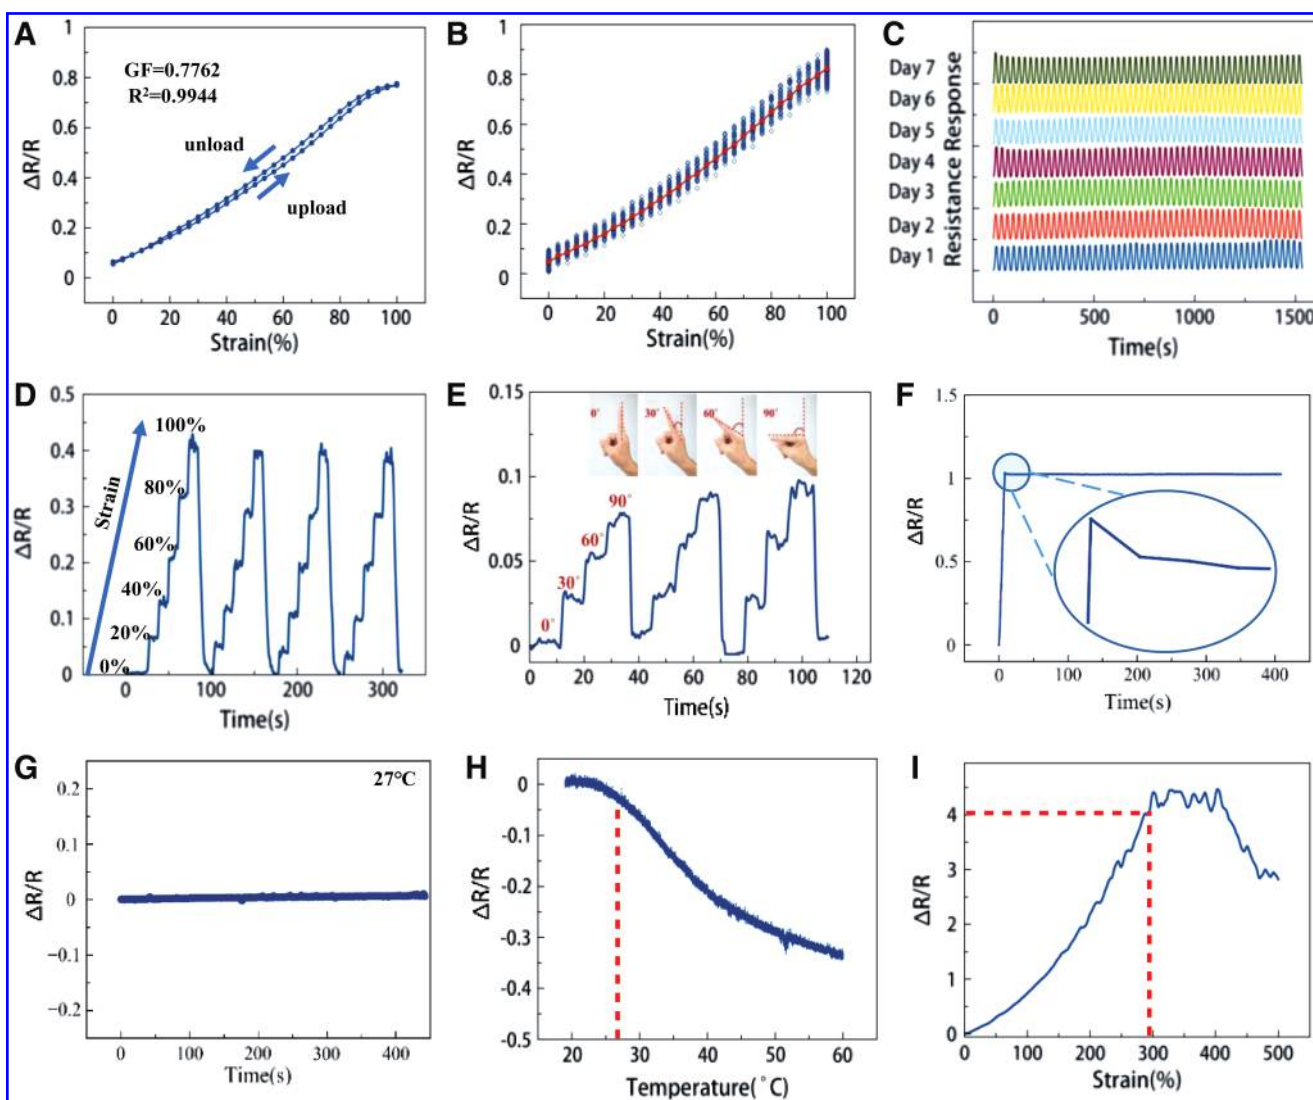


FIG. 3. The performance of a single hydrogel sensor. (A) $\Delta R/R_0$ is plotted as a function of ϵ by performing cyclic loading up to 100% strain. (B) $\Delta R/R_0$ is plotted as a function of ϵ by performing cyclic loading up to 100% strain with 50 cycles. (C) Measured resistances of an ionic sensor are plotted as a function of time at 7 days, respectively. (D) $\Delta R/R_0$ is plotted as a function of time with increasing strains of 20%, 40%, 60%, 80%, and 100%. (E) $\Delta R/R_0$ is plotted as a function of time with increasing bending angles of 0°, 30°, 60°, and 90°. (F) $\Delta R/R_0$ is plotted as a function of time when the sensor is kept with a specific strain. (G) $\Delta R/R_0$ is plotted as a function of time maintained around room temperature (i.e., 27°C in our test). (H) $\Delta R/R_0$ is plotted as a function of temperature from 17°C to 60°C. (I) The strain limit test of the ionic sensor. Color images are available online.

finger frequently slid the roller while middle finger generally keeps motionless, leading to different motion states of two fingers, which can also be differentiated by our iSkin system (Fig. 5B). The ability of a spatially resolved strain-sensitive wearable iSkin system would be used to provide proprioception feedback for potential applications in soft robotics, prosthetics, and virtual/augmented reality interaction.

As a proof of concept, we can also use the iSkin system to communicate with the sign language. Bending/straightening of each finger is captured and wirelessly transmitted from the iSkin system to a virtual device (i.e., a mobile phone). Then, the remote virtual device can translate the information into words. Figure 6 and Supplementary Movie S3 provide an example that one gesticulates “HELLO SJTUER” and the mobile phone understands the information. Therefore, with

our iSkin system, a deaf-mute person may successfully communicate with the persons who do not understand the sign language. Our integrated iSkin system thus provides the potential to be a smart “glove” and has advantages over conventional glove systems based on the optical fibers and metal-strain gauges in terms of high stretchability, transparency, fabrication cost, and simplicity.¹³

Conclusions

In this article, we present a fully integrated highly stretchable transparent wearable untethered iSkin system for hand-motion monitoring, which is composed of multiple hydrogel-elastomer hybrid ionic sensors and a wireless electronic control module. We provide an efficient and

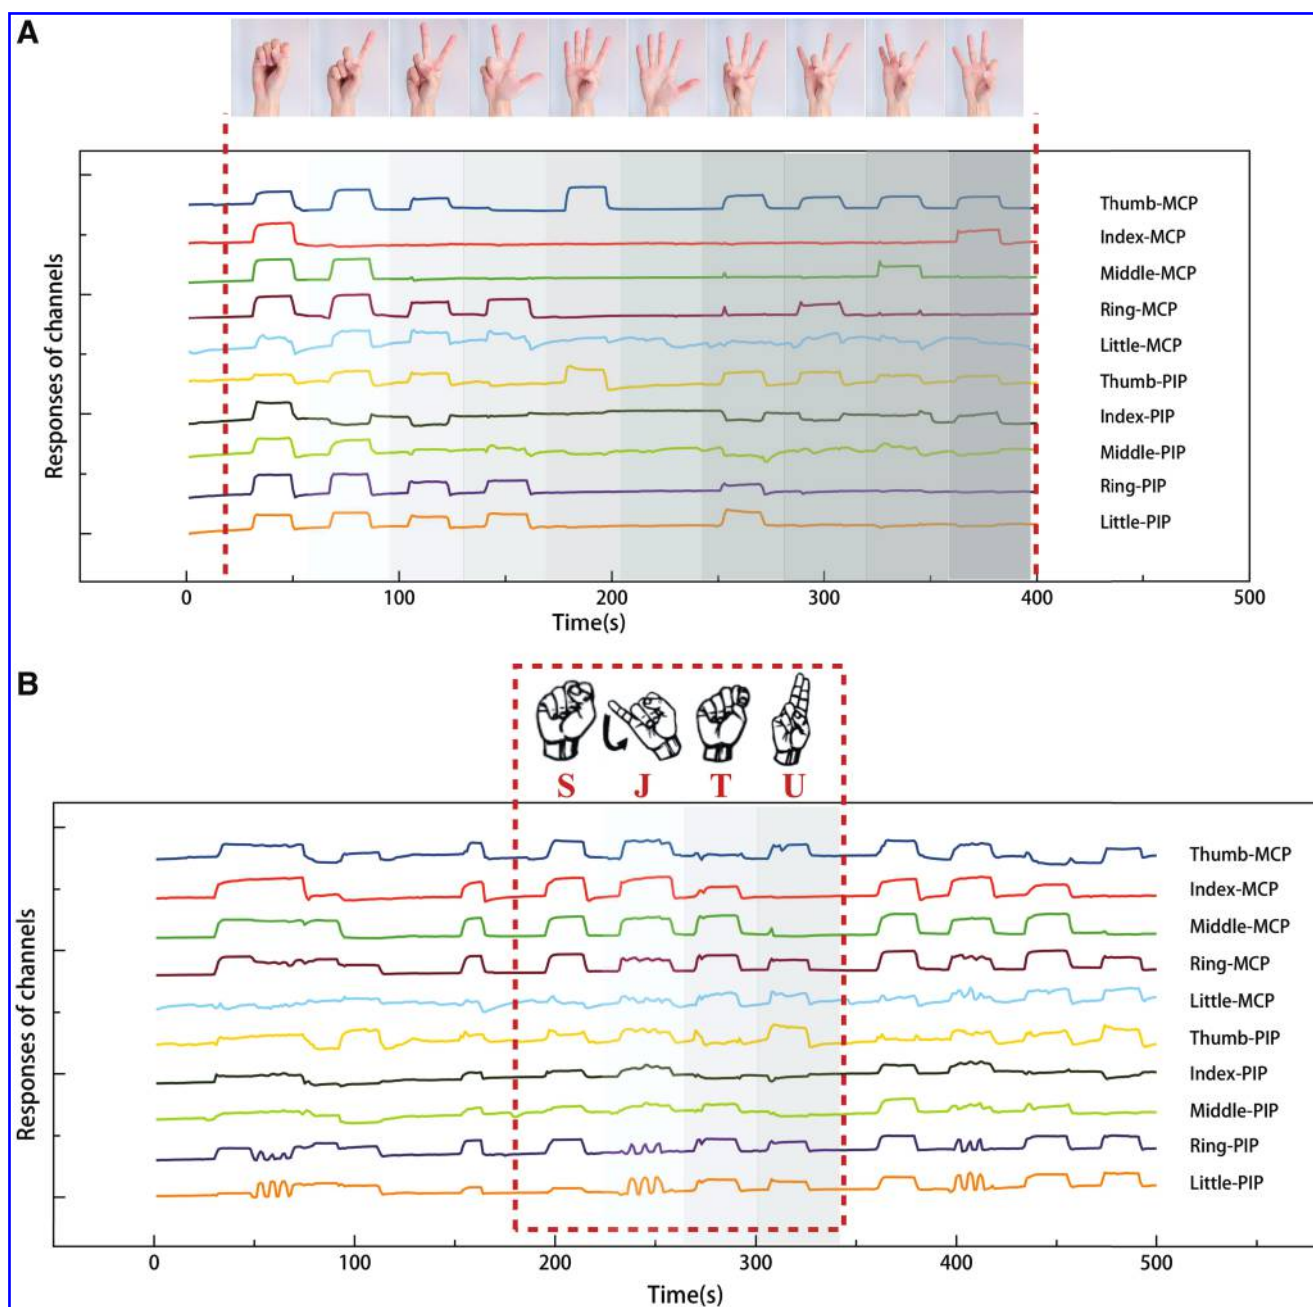


FIG. 4. Demonstrations of hand gesture recognition and sign language identifying with the integrated iSkin system. **(A)** The real-time responses recorded from the corresponding 10 sensors of our iSkin system when the subject gesticulates the digits 0–9 of the American Sign Language. **(B)** The real-time responses recorded from the corresponding 10 sensors of our iSkin system when the subject gesticulates the letters S, J, T, and U in international sign language. Color images are available online.

practical method to fabricate these robust hydrogel–elastomer hybrid ionic sensors. The adopted materials are all based on commonly available commercial products. The hydrogel–elastomer hybrid structure enables robust interface and durable sensitivity of the iSkin system. We characterize the performance of the ionic sensor with high stretchability, good sensitivity, small hysteresis, high repeatability, and durable stability. After being tested for 7 days, no significant change is observed in the sensing performance. We also demonstrate the capability of the integrated iSkin system to

monitor the joint bending and hand gesture, and communicate with the sign language. This work paves the way for practical design and integrates hydrogel–elastomer hybrid ionic sensors for highly stretchable wearable sensing skins in various applications, such as prosthetics, robotics, and human–robot interfaces. In future work, we will explore fabricating a fully transparent multifunctional iSkin system that can monitor the hand movement and detect the pressure and temperature with a better performance of precision, flexibility, adaptability, and comfortability.

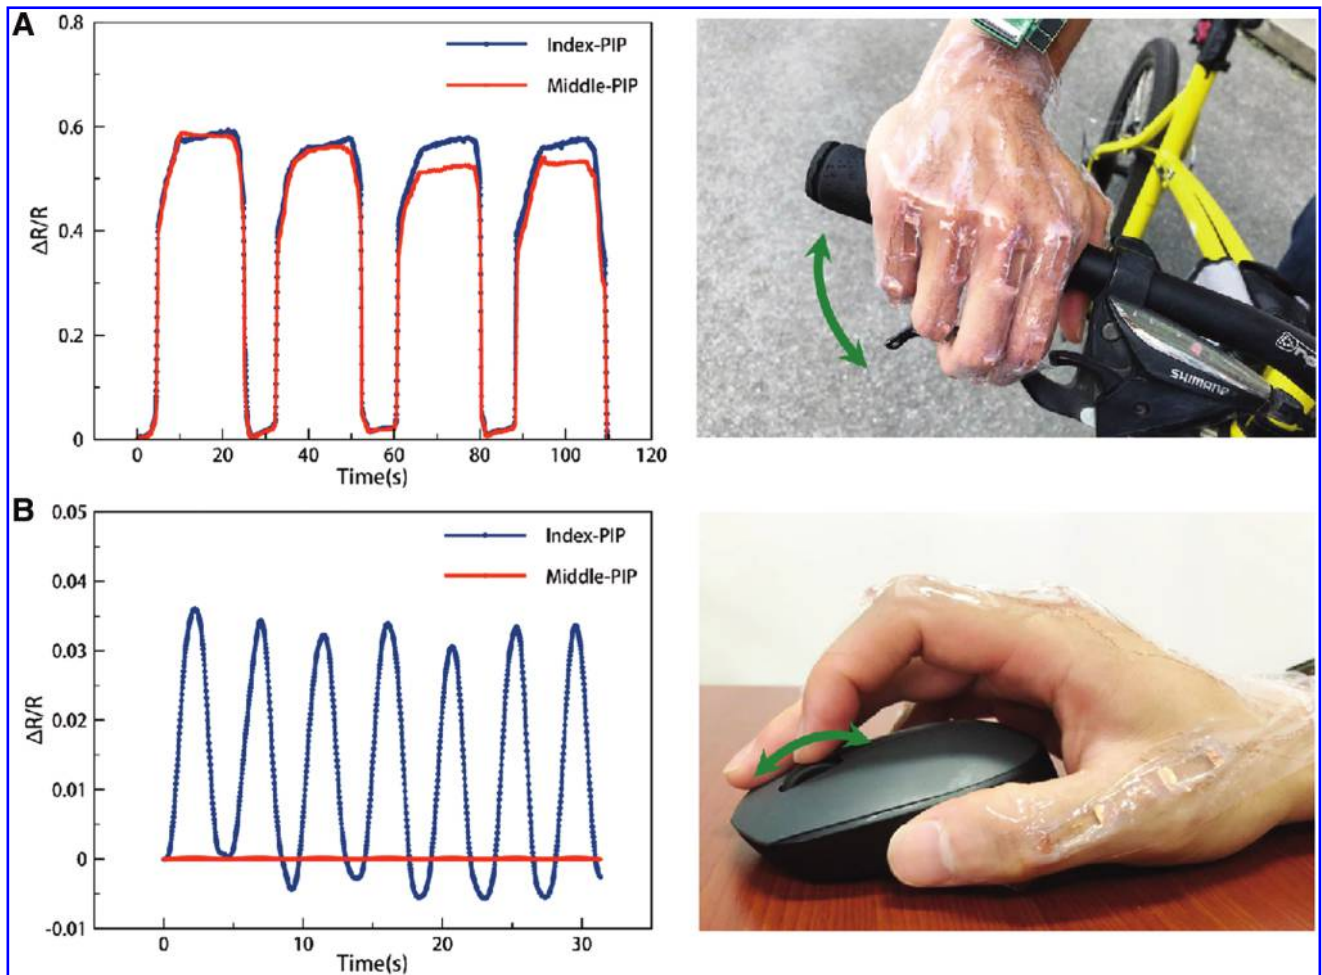


FIG. 5. (A) Application of the integrated iSkin system when braking a bike. (B) Application of the integrated iSkin system when sliding a mouse. Color images are available online.

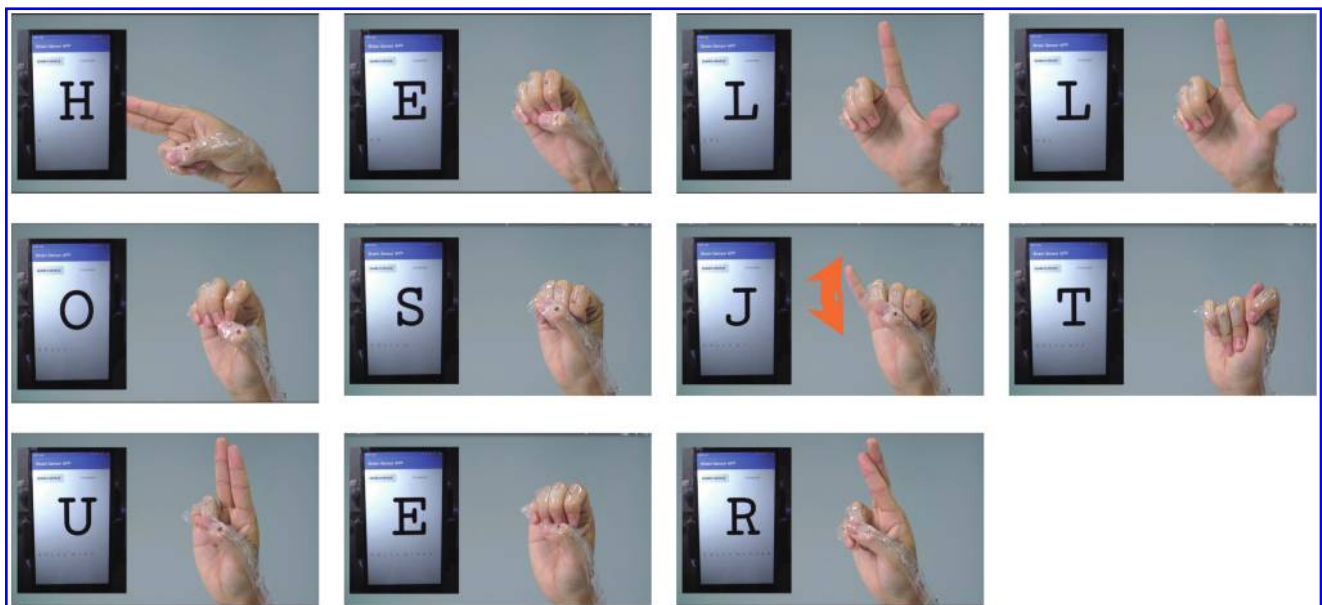


FIG. 6. A subject wearing the integrated wireless iSkin system gesticulates the sign language (i.e., "HELLO SJTUER"), which is understood by the remote virtual device (i.e., a mobile phone). Color images are available online.

Acknowledgments

This study was supported by the National Natural Science Foundation of China (Grant Nos. 51622506 and 91848204) and the Science and Technology Commission of Shanghai Municipality (Grant No. 16JC1401000). We would like to thank Baoyang Lu and Nannan Jian for transmittance measurement of ionic hydrogels.

Author Disclosure Statement

No competing financial interests exist.

Supplementary Material

Supplementary Movie S1

Supplementary Movie S2

Supplementary Movie S3

References

1. Chortos A, Liu J, Bao Z. Pursuing prosthetic electronic skin. *Nat Mater* 2016;15:937.
2. Rogers JA, Someya T, Huang Y. Materials and mechanics for stretchable electronics. *Science* 2010;327:1603–1607.
3. Son D, Kang J, Vardoulis O, *et al.* An integrated self-healable electronic skin system fabricated via dynamic reconstruction of a nanostructured conducting network. *Nat Nanotechnol* 2018;13:1057–1065.
4. Bauer S, Bauer-Gogonea S, Graz I, *et al.* 25th anniversary article: a soft future: from robots and sensor skin to energy harvesters. *Adv Mater* 2014;26:149–162.
5. Berntha JE, Ho V, Liu H. Morphological computation in haptic sensation and interaction: from nature to robotics. *Adv Robotics* 2018;32:340–362.
6. Hu L, Chen Y, Wang S, Chen Z. A fast, lightweight and accurate activity recognition model for mini-wearable devices. *Pervasive Mob Comput* 2014;15:200–214.
7. Kim DH, Lu N, Ma R, *et al.* Epidermal electronics. *Science* 2011;333:838–843.
8. Lu N, Kim DH. Flexible and stretchable electronics paving the way for soft robotics. *Soft Robot* 2014;1:53–62.
9. Liu Y, Norton J, Qazi R, *et al.* Epidermal mechano-acoustic sensing electronics for cardiovascular diagnostics and human-machine interfaces. *Sci Adv* 2016;2:e1601185.
10. Jang KI, Li K, Chung HU, *et al.* Self-assembled three dimensional network designs for soft electronics. *Nat Commun* 2017;8:15894.
11. Wagner S, Bauer S. Materials for stretchable electronics. *MRS Bull* 2012;37:207–213.
12. Hammock ML, Chortos A, Tee B, *et al.* 25th anniversary article: the evolution of electronic skin (e-skin): a brief history, design considerations, and recent progress. *Adv Mater* 2013;25:5997–6038.
13. Amjadi M, Kyung KU, Park I, *et al.* Stretchable, skin-mountable, and wearable strain sensors and their potential applications: a review. *Adv Funct Mater* 2016;26:1678–1698.
14. Chen D, Pei Q. Electronic muscles and skins: a review of soft sensors and actuators. *Chem Rev* 2017;117:11239–11268.
15. Kim HJ, Sim K, Thukral A, *et al.* Rubbery electronics and sensors from intrinsically stretchable elastomeric composites of semiconductors and conductors. *Sci Adv* 2017;3:e1701114.
16. Muth JT, Vogt DM, Truby RL, *et al.* Embedded 3d printing of strain sensors within highly stretchable elastomers. *Adv Mater* 2014;26:6307–6312.
17. Bartlett MD, Markvicka EJ, Majidi C. Rapid fabrication of soft, multilayered electronics for wearable biomonitoring. *Adv Funct Mater* 2016;26:8496–8504.
18. O'Connor TF, Fach ME, Miller R, *et al.* The Language of Glove: wireless gesture decoder with low-power and stretchable hybrid electronics. *PLoS One* 2017;12:e0179766.
19. Li L, Jiang S, Shull PB, *et al.* Skingest: artificial skin for gesture recognition via filmy stretchable strain sensors. *Adv Robot* 2018;32:1112–1121.
20. Wang S, Xu J, Wang W, *et al.* Skin electronics from scalable fabrication of an intrinsically stretchable transistor array. *Nature* 2018;555:83.
21. Kim HJ, Thukral A, Yu C. Highly sensitive and very stretchable strain sensor based on a rubbery semiconductor. *ACS Appl Mater Interfaces* 2018;10:5000–5006.
22. Kim HJ, Thukral A, Sharma S, *et al.* Biaxially stretchable fully elastic transistors based on rubbery semiconductor nanocomposites. *Adv Mater Technol* 2018;3:1800043.
23. Yamada T, Hayamizu Y, Yamamoto Y, *et al.* A stretchable carbon nanotube strain sensor for human-motion detection. *Nat Nanotechnol* 2011;6:296.
24. Li Q, Li J, Tran D, *et al.* Engineering of carbon nanotube/polydimethylsiloxane nanocomposites with enhanced sensitivity for wearable motion sensors. *J Mater Chem C* 2017;5:11092–11099.
25. Hu N, Itoi T, Akagi T, *et al.* Ultrasensitive strain sensors made from metal-coated carbon nanofiller/epoxy composites. *Carbon* 2013;51:202–212.
26. Wang C, Sim K, Chen J, *et al.* Soft ultrathin electronics innervated adaptive fully soft robots. *Adv Mater* 2018;30:1706695.
27. Park Y, Chen B, Wood RJ. Design and fabrication of soft artificial skin using embedded microchannels and liquid conductors. *IEEE Sens J* 2012;12:2711–2718.
28. Lu T, Finkenauer L, Wissman J, *et al.* Rapid prototyping for soft-matter electronics. *Adv Funct Mater* 2014;24:3351–3356.
29. Markvicka EJ, Bartlett MD, Huang X, *et al.* An autonomously electrically self-healing liquid metal-elastomer composite for robust soft-matter robotics and electronics. *Nat Mater* 2018;17:618–624.
30. Gao Y, Ota H, Schaler EW, *et al.* Wearable microfluidic diaphragm pressure sensor for health and tactile touch monitoring. *Adv Mater* 2017;29:1701985.
31. Sun JY, Keplinger C, Whitesides GM, *et al.* Ionic skin. *Adv Mater* 2014;26:7608–7614.
32. Yang C, Suo Z. Hydrogel ionotronics. *Nat Rev Mater* 2018;3:125–142.
33. Lee HR, Kim CC, Sun JY. Stretchable ionics-a promising candidate for upcoming wearable devices. *Adv Mater* 2018;30:e1704403.
34. Sun JY, Zhao X, Illeperuma W, *et al.* Highly stretchable and tough hydrogels. *Nature* 2012;489:133.
35. Keplinger C, Sun JY, Foo CC, *et al.* Stretchable, transparent, ionic conductors. *Science* 2013;341:984–987.
36. Lipomi DJ, Vosgueritchian M, Tee CK, *et al.* Skin-like pressure and strain sensors based on transparent elastic films of carbon nanotubes. *Nat Nanotechnol* 2011;6:788–792.
37. Ramuz M, Tee B, Tok J, *et al.* Transparent, optical, pressure-sensitive artificial skin for large-area stretchable electronics. *Adv Mater* 2012;24:3223–3227.
38. Kim J, Lee M, Jeon S, *et al.* Highly transparent and stretchable field-effect transistor sensors using graphene-nanowire hybrid nanostructures. *Adv Mater* 2015;27:3292–3297.

39. Zhao X. Multi-scale multi-mechanism design of tough hydrogels: building dissipation into stretchy networks. *Soft Matter* 2014;10:672–687.
40. Lin S, Yuk H, Zhang T, *et al.* Stretchable hydrogel electronics and devices. *Adv Mater* 2016;28:4497–4505.
41. Yang C, Chen B, Lu J, *et al.* Ionic cable. *Extreme Mech Lett* 2015;3:59–65.
42. Yuk H, Zhang T, Parada GA, *et al.* Skin-inspired hydrogel-elastomer hybrids with robust interfaces and functional microstructures. *Nat Commun* 2016;7:12028.
43. Larson C, Peele B, Li S, *et al.* Highly stretchable electroluminescent skin for optical signaling and tactile sensing. *Science* 2016;351:1071–1074.
44. Tian K, Bae J, Bakarich SE, *et al.* 3D printing of transparent and conductive heterogeneous hydrogel-elastomer systems. *Adv Mater* 2017;29:1604827.
45. Kim SH, Jung S, Yoon IS, *et al.* Ultrastretchable conductor fabricated on skin-like hydrogel-elastomer hybrid substrates for skin electronics. *Adv Mater* 2013;30:1800109.
46. Qiu Z, Wan Y, Zhou W, *et al.* Ionic skin with biomimetic dielectric layer templated from calathea zebrine leaf. *Adv Funct Mater* 2018;28:1802343.
47. Kim CC, Lee HH, Oh KH, *et al.* Highly stretchable, transparent ionic touch panel. *Science* 2016;353:682–687.
48. Cai G, Wang J, Qian J, *et al.* Extremely stretchable strain sensors based on conductive self-healing dynamic cross-links hydrogels for human-motion detection. *Adv Sci* 2017;4:1600190.
49. Lei Z, Wang Q, Sun S, *et al.* A bioinspired mineral hydrogel as a self-healable, mechanically adaptable ionic skin for highly sensitive pressure sensing. *Adv Mater* 2017;29:1700321.
50. Wirthl D, Pichler R, Drack M, *et al.* Instant tough bonding of hydrogels for soft machines and electronics. *Sci Adv* 2017;3:e1700053.
51. Shay T, Velev OD, Dickey MD. Soft electrodes combining hydrogel and liquid metal. *Soft Matter* 2018;14:3296–3303.
52. Bai Y, Chen B, Xiang F, *et al.* Transparent hydrogel with enhanced water retention capacity by introducing highly hydratable salt. *Appl Phys Lett* 2014;105:151903.
53. Wacker. Silpuran. Available at: https://www.wacker.com/cms/en/products/brands_3/silpuran/silpuran.jsp (accessed February 21, 2019).
54. Pawlaczyk M, Lelonkiewicz M, Wieczorowski M. Age-dependent biomechanical properties of the skin. *Adv Dermatol* 2013;30:302–306.

Address correspondence to:

Guoying Gu
 Soft Robotics and Biodesign Lab
 Robotics Institute
 School of Mechanical Engineering
 Shanghai Jiao Tong University
 Shanghai 200240
 China

E-mail: guguoqing@sjtu.edu.cn

This article has been cited by:

1. Junli Shi, Yuan Dai, Yu Cheng, Sai Xie, Gang Li, Yuan Liu, Jingxiao Wang, Ruirui Zhang, Ningning Bai, Minkun Cai, Yuan Zhang, Yifei Zhan, Zhengyou Zhang, Cunjiang Yu, Chuan Fei Guo. 2023. Embedment of sensing elements for robust, highly sensitive, and cross-talk-free iontronic skins for robotics applications. *Science Advances* 9:9. . [[Crossref](#)]
2. Francisco R. Avila, Rickey E. Carter, Christopher J. McLeod, Charles J. Bruce, Davide Giardi, Gunel Guliyeva, Antonio J. Forte. 2023. Accuracy of Wearable Sensor Technology in Hand Goniometry: A Systematic Review. *HAND* 18:2, 340-348. [[Crossref](#)]
3. Fengdi Li, Giao T. M. Nguyen, Cédric Vancaeyzeele, Frédéric Vidal, Cédric Plesse. 2023. Vitriimer ionogels towards sustainable solid-state electrolytes. *RSC Advances* 13:10, 6656-6667. [[Crossref](#)]
4. Meiling Peng, Xiang Li, Yinfeng Liu, Jianwen Chen, Xiaohua Chang, Yutian Zhu. 2023. Flexible multisensory sensor based on hierarchically porous ionic liquids/thermoplastic polyurethane composites. *Applied Surface Science* 610, 155516. [[Crossref](#)]
5. Xiangnan He, Jianxiang Cheng, Zhenqing Li, Haitao Ye, Xinfeng Wei, Honggeng Li, Rong Wang, Yuan-Fang Zhang, Hui Ying Yang, Chuanfei Guo, Qi Ge. 2023. Multimaterial Three-Dimensional Printing of Ultraviolet-Curable Ionic Conductive Elastomers with Diverse Polymers for Multifunctional Flexible Electronics. *ACS Applied Materials & Interfaces* 15:2, 3455-3466. [[Crossref](#)]
6. Kaixiang Shen, Kai Xu, Mengyuan Zhang, Jing Yu, Yuxuan Yang, Xiaodan Zhao, Qiang Zhang, Youshen Wu, Yangfeng Zhang, Yilong Cheng. 2023. Multiple hydrogen bonds reinforced conductive hydrogels with robust elasticity and ultra-durability as multifunctional ionic skins. *Chemical Engineering Journal* 451, 138525. [[Crossref](#)]
7. Yufei Hao, Shixin Zhang, Bin Fang, Fuchun Sun, Huaping Liu, Haiyuan Li. 2022. A Review of Smart Materials for the Boost of Soft Actuators, Soft Sensors, and Robotics Applications. *Chinese Journal of Mechanical Engineering* 35:1. . [[Crossref](#)]
8. Antonia Georgopoulou, Joost Brancart, Seppe Terryn, Anton W. Bosman, Sophie Norvez, Guy Van Assche, Fumiya Iida, Bram Vanderborght, Frank Clemens. 2022. Soft self-healing resistive-based sensors inspired by sensory transduction in biological systems. *Applied Materials Today* 29, 101638. [[Crossref](#)]
9. Tiantong Wang, Yunbiao Zhao, Qining Wang. A Flexible Iontronic Capacitive Sensing Array for Hand Gesture Recognition Using Deep Convolutional Neural Networks. *Soft Robotics*, ahead of print. [[Abstract](#)] [[Full Text](#)] [[PDF](#)] [[PDF Plus](#)]
10. Liyan Mo, Daohui Zhang, Dezhen Xiong, Kai Li, Xingang Zhao. A Highly Flexible Optical Waveguide Sensor with Rectangular Structure for Muscle Contraction Signals Detection 6815-6820. [[Crossref](#)]
11. Shan Xia, Ming Wang, Guanghui Gao. 2022. Preparation and application of graphene-based wearable sensors. *Nano Research* 15:11, 9850-9865. [[Crossref](#)]
12. Heyuan Huang, Xuanjia Zhang, Zhicheng Dong, Xin Zhao, Baolin Guo. 2022. Nanocomposite conductive tough hydrogel based on metal coordination reinforced covalent Pluronic F-127 micelle network for human motion sensing. *Journal of Colloid and Interface Science* 625, 817-830. [[Crossref](#)]
13. Suresh Kumar Chittibabu, Krishnamoorthi Chintagumpala, Arunkumar Chandrasekhar. 2022. Porous dielectric materials based wearable capacitance pressure sensors for vital signs monitoring: A review. *Materials Science in Semiconductor Processing* 151, 106976. [[Crossref](#)]
14. Claude Huniade, Daniel Melling, Cédric Vancaeyzeele, Giao T.-M. Nguyen, Frédéric Vidal, Cédric Plesse, Edwin W. H. Jager, Tariq Bashir, Nils-Krister Persson. 2022. Ionofibers: Ionically Conductive Textile Fibers for Conformal i-Textiles. *Advanced Materials Technologies* 7:10, 2101692. [[Crossref](#)]
15. Wenbin Sun, Zilong Guo, Zhiqiang Yang, Yizhou Wu, Weixia Lan, Yingjie Liao, Xian Wu, Yuanyuan Liu. 2022. A Review of Recent Advances in Vital Signals Monitoring of Sports and Health via Flexible Wearable Sensors. *Sensors* 22:20, 7784. [[Crossref](#)]
16. Yinping Liu, Lulu Wang, Yuanyuan Mi, Sisi Zhao, Simeng Qi, Meng Sun, Bo Peng, Quan Xu, Yingchun Niu, Yang Zhou. 2022. Transparent stretchable hydrogel sensors: materials, design and applications. *Journal of Materials Chemistry C* 10:37, 13351-13371. [[Crossref](#)]
17. Seok Hee Han, Min-Ah Oh, Taek Dong Chung. 2022. Iontronics: Aqueous ion-based engineering for bioinspired functionalities and applications. *Chemical Physics Reviews* 3:3, 031302. [[Crossref](#)]
18. . Is 4D Printing Disruptive or Incremental, or a Bit of Both? 1-115. [[Crossref](#)]
19. Zequn Shen, Zhilin Zhang, Ningbin Zhang, Jinhao Li, Peiwei Zhou, Faqi Hu, Yu Rong, Baoyang Lu, Guoying Gu. 2022. High-Stretchability, Ultralow-Hysteresis ConductingPolymer Hydrogel Strain Sensors for Soft Machines. *Advanced Materials* 34:32, 2203650. [[Crossref](#)]
20. Hao Wang, Yang Yue, Wenze Zou, Yang Pan, Xiaogang Guo. 2022. The stretchable carbon black-based strain fiber with a remarkable linearity in a wide sensing range. *International Journal of Smart and Nano Materials* 13:3, 529-541. [[Crossref](#)]

21. Burebi Yiming, Zhaoxin Zhang, Yuchen Lu, Xingang Liu, Costantino Creton, Shuze Zhu, Zheng Jia, Shaoxing Qu. 2022. Molecular Mechanism Underpinning Stable Mechanical Performance and Enhanced Conductivity of Air-Aged Ionic Conductive Elastomers. *Macromolecules* **55**:11, 4665-4674. [[Crossref](#)]
22. Zhihui Xie, Zhuo Chen, Xiangshu Hu, Hao-Yang Mi, Jian Zou, Heng Li, Yuejun Liu, Zhi Zhang, Yinghui Shang, Xin Jing. 2022. Ultrastretchable, self-healable and adhesive composite organohydrogels with a fast response for human-machine interface applications. *Journal of Materials Chemistry C* **10**:21, 8266-8277. [[Crossref](#)]
23. Linan Deng, Yi Shen, Yang Hong, Yunlong Dong, Xin He, Ye Yuan, Zhi Li, Han Ding. Sen-Glove: A Lightweight Wearable Glove for Hand Assistance with Soft Joint Sensing 5170-5175. [[Crossref](#)]
24. Zhenhui Jin, Fujunzhu Zhao, Yanlin Lei, Yi-Cheng Wang. 2022. Hydrogel-based triboelectric devices for energy-harvesting and wearable sensing applications. *Nano Energy* **95**, 106988. [[Crossref](#)]
25. Binbin Ying, Runze Zuo, Yilun Wan, Xinyu Liu. 2022. An Ionic Hydrogel-Based Antifreezing Triboelectric Nanogenerator. *ACS Applied Electronic Materials* **4**:4, 1930-1938. [[Crossref](#)]
26. Huai Xiao, Jundong Wu, Wenjun Ye, Yawu Wang. 2022. Dynamic modeling of dielectric elastomer actuators based on thermodynamic theory. *Mechanics of Advanced Materials and Structures* **29**:11, 1543-1552. [[Crossref](#)]
27. Chun Zhao, Yanjie Wang, Gangqiang Tang, Jie Ru, Zicai Zhu, Bo Li, Chuan Fei Guo, Lijie Li, Denglin Zhu. 2022. Ionic Flexible Sensors: Mechanisms, Materials, Structures, and Applications. *Advanced Functional Materials* **32**:17, 2110417. [[Crossref](#)]
28. Hritwick Banerjee, Manivannan Sivaperuman Kalairaj, Ting-Hsiang Chang, Fanfan Fu, Po-Yen Chen, Hongliang Ren. 2022. Highly Stretchable Flame-Retardant Skin for Soft Robotics with Hydrogel-Montmorillonite-Based Translucent Matrix. *Soft Robotics* **9**:1, 98-118. [[Abstract](#)] [[Full Text](#)] [[PDF](#)] [[PDF Plus](#)] [[Supplementary Material](#)]
29. Harika Dechiraju, Manping Jia, Le Luo, Marco Rolandi. 2022. Ion-Conducting Hydrogels and Their Applications in Bioelectronics. *Advanced Sustainable Systems* **6**:2, 2100173. [[Crossref](#)]
30. Yuying Si, Sujie Chen, Ming Li, Siying Li, Yisen Pei, Xiaojun Guo. 2022. Flexible Strain Sensors for Wearable Hand Gesture Recognition: From Devices to Systems. *Advanced Intelligent Systems* **4**:2, 2100046. [[Crossref](#)]
31. Shuai Hao, Tianci Li, Xuemeng Yang, Hongzan Song. 2022. Ultrastretchable, Adhesive, Fast Self-Healable, and Three-Dimensional Printable Photoluminescent Ionic Skin Based on Hybrid Network Ionogels. *ACS Applied Materials & Interfaces* **14**:1, 2029-2037. [[Crossref](#)]
32. Sudheer Kumar, Sukhila Krishnan, Smita Mohanty. Applications of elastomer blends and composites 305-329. [[Crossref](#)]
33. Philipp Ruppel, Norman Hendrich, Jianwei Zhang. 2022. Elastic Tactile Sensor Skin on Double-Curved Surfaces for Robots and Wearables. *IEEE Access* **10**, 91103-91118. [[Crossref](#)]
34. Shuo Jiang, Peiqi Kang, Xinyu Song, Benny Lo, Peter Shull. 2022. Emerging Wearable Interfaces and Algorithms for Hand Gesture Recognition: A Survey. *IEEE Reviews in Biomedical Engineering* **15**, 85-102. [[Crossref](#)]
35. Balaji Dontha, Kyoung Swearingen, Scott Swearingen, Susan E. Thrane, Asimina Kiourti. 2022. Wearable Sensors Based on Force-Sensitive Resistors for Touch-Based Collaborative Digital Gaming. *Sensors* **22**:1, 342. [[Crossref](#)]
36. Fengjin Xie, Xinpei Gao, Yang Yu, Fei Lu, Liqiang Zheng. 2021. Dually cross-linked single network poly(ionic liquid)/ionic liquid ionogels for a flexible strain-humidity bimodal sensor. *Soft Matter* **17**:48, 10918-10925. [[Crossref](#)]
37. Hongcheng Xu, Libo Gao, Haitao Zhao, Hanlin Huang, Yuejiao Wang, Gang Chen, Yuxin Qin, Ningjuan Zhao, Dandan Xu, Ling Duan, Xuan Li, Siyu Li, Zhongbao Luo, Weidong Wang, Yang Lu. 2021. Stretchable and anti-impact iontronic pressure sensor with an ultrabroad linear range for biophysical monitoring and deep learning-aided knee rehabilitation. *Microsystems & Nanoengineering* **7**:1. . [[Crossref](#)]
38. Ming Li, Yisen Pei, Yu Cao, Sujie Chen, Xiaojun Guo. 2021. Flexible strain sensors: from devices to array integration. *Flexible and Printed Electronics* **6**:4, 043002. [[Crossref](#)]
39. Jiang Zou, Miao Feng, Ningyuan Ding, Peinan Yan, Haipeng Xu, Dezhi Yang, Nicholas X Fang, Guoying Gu, Xiangyang Zhu. 2021. Muscle-fiber array inspired, multiple-mode, pneumatic artificial muscles through planar design and one-step rolling fabrication. *National Science Review* **8**:10. . [[Crossref](#)]
40. Shuyu Wang, Zhaojia Sun, Yuliang Zhao, Lei Zuo. 2021. A highly stretchable hydrogel sensor for soft robot multi-modal perception. *Sensors and Actuators A: Physical* **331**, 113006. [[Crossref](#)]
41. Zequn Shen, Xiangyang Zhu, Carmel Majidi, Guoying Gu. 2021. Cutaneous Ionogel Mechanoreceptors for Soft Machines, Physiological Sensing, and Amputee Prostheses. *Advanced Materials* **33**:38, 2102069. [[Crossref](#)]
42. Yang Gao, Yuanrui Wang, Shan Xia, Guanghui Gao. 2021. An environment-stable hydrogel with skin-matchable performance for human-machine interface. *Science China Materials* **64**:9, 2313-2324. [[Crossref](#)]

43. Yu Cheng, Runzhi Zhang, Wenpei Zhu, Hua Zhong, Sicong Liu, Juan Yi, Liyang Shao, Wenping Wang, James Lam, Zheng Wang. 2021. A Multimodal Hydrogel Soft-Robotic Sensor for Multi-Functional Perception. *Frontiers in Robotics and AI* 8. . [\[Crossref\]](#)
44. Guoying Gu, Ningbin Zhang, Haipeng Xu, Shaoting Lin, Yang Yu, Guohong Chai, Lisen Ge, Houle Yang, Qiwen Shao, Xinjun Sheng, Xiangyang Zhu, Xuanhe Zhao. 2021. A soft neuroprosthetic hand providing simultaneous myoelectric control and tactile feedback. *Nature Biomedical Engineering* 10. . [\[Crossref\]](#)
45. Guangyu Bao, Ran Huo, Zhenwei Ma, Mitchell Strong, Amin Valiei, Shuaibing Jiang, Shiyu Liu, Luc Mongeau, Jianyu Li. 2021. Ionotronic Tough Adhesives with Intrinsic Multifunctionality. *ACS Applied Materials & Interfaces* 13:31, 37849–37861. [\[Crossref\]](#)
46. Jing Cong, Zhiwei Fan, Shaoshan Pan, Jie Tian, Weizhen Lian, Shan Li, Sijie Wang, Dongchang Zheng, Chunguang Miao, Weiping Ding, Taolin Sun, Tianzhi Luo. 2021. Polyacrylamide/Chitosan-Based Conductive Double Network Hydrogels with Outstanding Electrical and Mechanical Performance at Low Temperatures. *ACS Applied Materials & Interfaces* 13:29, 34942–34953. [\[Crossref\]](#)
47. Xin Jing, Zhenping Ma, Maxwell Fordjour Antwi-Afari, Lin Wang, Heng Li, Hao-Yang Mi, Pei-Yong Feng, Yuejun Liu. 2021. Synthesis and Fabrication of Supramolecular Polydimethylsiloxane-Based Nanocomposite Elastomer for Versatile and Intelligent Sensing. *Industrial & Engineering Chemistry Research* 60:28, 10419–10430. [\[Crossref\]](#)
48. Runze Zuo, Zhanfeng Zhou, Binbin Ying, Xinyu Liu. A Soft Robotic Gripper with Anti-Freezing Ionic Hydrogel-Based Sensors for Learning-Based Object Recognition 12164–12169. [\[Crossref\]](#)
49. Chenrun Feng, C.P. Hemantha Rajapaksha, Antal Jákli. 2021. Ionic Elastomers for Electric Actuators and Sensors. *Engineering* 7:5, 581–602. [\[Crossref\]](#)
50. Yue Jiao, Kaiyue Lu, Ya Lu, Yiyi Yue, Xinwu Xu, Huining Xiao, Jian Li, Jingquan Han. 2021. Highly viscoelastic, stretchable, conductive, and self-healing strain sensors based on cellulose nanofiber-reinforced polyacrylic acid hydrogel. *Cellulose* 28:7, 4295–4311. [\[Crossref\]](#)
51. Jiye Qiu, Xiangwei Wang, Yong Ma, Zhiwei Yu, Tingxi Li. 2021. Stretchable Transparent Conductive Films Based on Ag Nanowires for Flexible Circuits and Tension Sensors. *ACS Applied Nano Materials* 4:4, 3760–3766. [\[Crossref\]](#)
52. Xin Li, Jiajie Guo, Xingxing Ma, Luye Yang, Kok-Meng Lee, Caihua Xiong. 2021. Flexible Capacitive Curvature Sensor with One-Time Calibration for Amphibious Gait Monitoring. *Soft Robotics* 8:2, 164–174. [\[Abstract\]](#) [\[Full Text\]](#) [\[PDF\]](#) [\[PDF Plus\]](#) [\[Supplementary Material\]](#)
53. Linlin Yuan, Weiye Qi, Kaiyu Cai, Chunhua Li, Qiuping Qian, Yunlong Zhou. 2021. Gesture recognition device based on cross reticulated graphene strain sensors. *Journal of Materials Science: Materials in Electronics* 32:7, 8410–8417. [\[Crossref\]](#)
54. Zhijian Ren, Masoud Zarepoor, Xiaonan Huang, Andrew P. Sabelhaus, Carmel Majidi. 2021. Shape Memory Alloy (SMA) Actuator With Embedded Liquid Metal Curvature Sensor for Closed-Loop Control. *Frontiers in Robotics and AI* 8. . [\[Crossref\]](#)
55. Zexing Deng, Rui Yu, Baolin Guo. 2021. Stimuli-responsive conductive hydrogels: design, properties, and applications. *Materials Chemistry Frontiers* 5:5, 2092–2123. [\[Crossref\]](#)
56. Yu Chang, Liu Wang, Ruya Li, Zhichao Zhang, Qi Wang, Junlong Yang, Chuan Fei Guo, Tingrui Pan. 2021. First Decade of Interfacial Iontronic Sensing: From Droplet Sensors to Artificial Skins. *Advanced Materials* 33:7, 2003464. [\[Crossref\]](#)
57. Xiangsheng Han, Wenyu Lu, Wenfan Yu, Hang Xu, Shuyan Bi, Hongzhen Cai. 2021. Conductive and adhesive gluten ionic skin for eco-friendly strain sensor. *Journal of Materials Science* 56:5, 3970–3980. [\[Crossref\]](#)
58. XinJun Sheng, Zhun Qin, HaiPeng Xu, XiaoKang Shu, GuoYing Gu, XiangYang Zhu. 2021. Soft ionic-hydrogel electrodes for electroencephalography signal recording. *Science China Technological Sciences* 64:2, 273–282. [\[Crossref\]](#)
59. Zhiguang Xing, Jun Lin, David McCoul, Dapeng Zhang, Jianwen Zhao. 2020. Inductive Strain Sensor With High Repeatability and Ultra-Low Hysteresis Based on Mechanical Spring. *IEEE Sensors Journal* 20:24, 14670–14675. [\[Crossref\]](#)
60. Xiao Chen, Zhixin Zhan, Qimin Liu, Tao Wu. 2020. Modeling the response characteristics of photo-sensitive hydrogel electrolytes in Hofmeister salt solution for the development of smart energy storage devices. *Sustainable Energy & Fuels* 4:12, 6112–6124. [\[Crossref\]](#)
61. Canhui Yang, Sibao Cheng, Xi Yao, Guodong Nian, Qihan Liu, Zhigang Suo. 2020. Ionotronic Luminescent Fibers, Fabrics, and Other Configurations. *Advanced Materials* 32:47, 2005545. [\[Crossref\]](#)
62. Zequn Shen, Feifei Chen, Xiangyang Zhu, Ken-Tye Yong, Guoying Gu. 2020. Stimuli-responsive functional materials for soft robotics. *Journal of Materials Chemistry B* 8:39, 8972–8991. [\[Crossref\]](#)
63. Hui Tang, Jingxian Sun, Xin Shu, Yingying Zhao, Jun Nie, Xiaoqun Zhu. 2020. Fabrication of a Surface Adhesion Layer for Hydrogel Sensors via Photografting. *ACS Applied Polymer Materials* 2:9, 4140–4148. [\[Crossref\]](#)
64. Ming Li, Sujie Chen, Boyu Fan, Bangyuan Wu, Xiaojun Guo. 2020. Printed Flexible Strain Sensor Array for Bendable Interactive Surface. *Advanced Functional Materials* 30:34, 2003214. [\[Crossref\]](#)

65. Hailong Huang, Lu Han, Xiaobin Fu, Yanling Wang, Zhongli Yang, Likun Pan, Min Xu. 2020. Multiple Stimuli Responsive and Identifiable Zwitterionic Ionic Conductive Hydrogel for Bionic Electronic Skin. *Advanced Electronic Materials* 6:7, 2000239. [[Crossref](#)]
66. HaiPeng Xu, ZeQun Shen, GuoYing Gu. 2020. Performance characterization of ionic-hydrogel based strain sensors. *Science China Technological Sciences* 63:6, 923-930. [[Crossref](#)]
67. Qiwen Shao, Ningbin Zhang, Zequn Shen, Guoying Gu. A Pneumatic Soft Gripper with Configurable Workspace and Self-sensing 36-43. [[Crossref](#)]
68. Hailong Huang, Lu Han, Junfeng Li, Xiaobin Fu, Yanling Wang, Zhongli Yang, Xingtao Xu, Likun Pan, Min Xu. 2020. Super-stretchable, elastic and recoverable ionic conductive hydrogel for wireless wearable, stretchable sensor. *Journal of Materials Chemistry A* 8:20, 10291-10300. [[Crossref](#)]
69. Hao Chen, Yang Gao, Xiuyan Ren, Guanghui Gao. 2020. Alginate fiber toughened gels similar to skin intelligence as ionic sensors. *Carbohydrate Polymers* 235, 116018. [[Crossref](#)]
70. Gyowook Shin, Byungjun Jeon, Yong-Lae Park. 2020. Direct printing of sub-30 μ m liquid metal patterns on three-dimensional surfaces for stretchable electronics. *Journal of Micromechanics and Microengineering* 30:3, 034001. [[Crossref](#)]
71. Shuqiang Peng, Yuewei Li, Lixin Wu, Jie Zhong, Zixiang Weng, Longhui Zheng, Zhi Yang, Jia-Tao Miao. 2020. 3D Printing Mechanically Robust and Transparent Polyurethane Elastomers for Stretchable Electronic Sensors. *ACS Applied Materials & Interfaces* 12:5, 6479-6488. [[Crossref](#)]
72. Jiajun Xu, Rining Jin, Xiuyan Ren, Guanghui Gao. 2019. Cartilage-inspired hydrogel strain sensors with ultrahigh toughness, good self-recovery and stable anti-swelling properties. *Journal of Materials Chemistry A* 7:44, 25441-25448. [[Crossref](#)]
73. Bowen Yang, Weizhong Yuan. 2019. Highly Stretchable, Adhesive, and Mechanical Zwitterionic Nanocomposite Hydrogel Biomimetic Skin. *ACS Applied Materials & Interfaces* 11:43, 40620-40628. [[Crossref](#)]
74. Yuan-Fang Zhang, Colin Ju-Xiang Ng, Zhe Chen, Wang Zhang, Sahil Panjwani, Kavin Kowsari, Hui Ying Yang, Qi Ge. 2019. Miniature Pneumatic Actuators for Soft Robots by High-Resolution Multimaterial 3D Printing. *Advanced Materials Technologies* 4:10, 1900427. [[Crossref](#)]