

Omnisoot: a process design package for gas-phase synthesis of carbonaceous nanoparticles

by
Mohammad Adib

A thesis submitted to the Faculty of Graduate and Postdoctoral Affairs
in partial fulfillment of the requirements for the degree of

Doctor of Philosophy
in
Mechanical Engineering

Carleton University
Ottawa, Canada

© 2026
Mohammad Adib

I would like to dedicate this thesis to my loving parents . . .

Declaration

I hereby declare that except where specific reference is made to the work of others, the contents of this dissertation are original and have not been submitted in whole or in part for consideration for any other degree or qualification in this, or any other university. This dissertation is my own work and contains nothing which is the outcome of work done in collaboration with others, except as specified in the text and Acknowledgements. This dissertation contains fewer than 65,000 words including appendices, bibliography, footnotes, tables and equations and has fewer than 150 figures.

Mohammad Adib
2026

Acknowledgements

And I would like to acknowledge ...

Abstract

This is where you write your abstract ...

Table of contents

List of figures	xiii
List of tables	xxi
Nomenclature	xxiii
1 Introduction	1
1.1 Motivation	1
1.2 Background	2
1.2.1 Soot inception and surface growth	2
1.3 Coagulation and agglomeration	8
1.4 Soot maturity and its optical properties	10
1.5 Oxidation	12
1.6 Research objectives	14
2 Theoretical Model	17
2.1 Assumptions and conventions	17
2.2 Reactors	20
2.2.1 Constant Volume Reactor (CVR)	21
2.2.2 Imposed Pressure Reactor	22
2.2.3 Perfectly Stirred Reactor (PSR)	23
2.2.4 Plug Flow Reactor (PFR)	24
2.3 Particle Dynamics	25
2.3.1 Common Features	26
2.3.2 Sectional Population Balance Model	29
2.3.3 Monodisperse Population Balance Model	35
2.4 PAH growth models	36
2.4.1 Irreversible Dimerization	38
2.4.2 Reactive Dimerization	40

2.4.3	Dimer Coalescence	43
2.4.4	E-Bridge Modified	45
2.4.5	Summary of features	47
2.5	Surface reactions model	48
2.6	Gas scrubbing rates	51
3	Code Validation	53
3.1	Validation of Collision Frequency	53
3.2	Coagulation	54
3.3	Elemental and Energy Balance	57
3.3.1	Constant Volume Reactor	57
3.3.2	Imposed Pressure Reactor	58
3.3.3	Perfectly Stirred Reactor	60
3.3.4	Plug Flow Reactor	61
4	Results	63
4.1	Fundamental analysis of PAH growth models	63
4.1.1	Uncertainties in gas chemistry	64
4.1.2	Methane pyrolysis in shock tube	66
4.1.3	Ethylene pyrolysis in a flow reactor	73
4.1.4	Ethylene combustion in a perfectly stirred reactor	76
4.1.5	Conclusions	80
4.2	Identifying stages of carbon black evolution	81
4.2.1	Experimental methods	82
4.2.2	Numerical model	84
4.2.3	Precursor chemistry	85
4.2.4	Stages of CB formation	86
4.2.5	The effect of temperature	90
4.2.6	Conclusions	96
	References	99
	Appendix A Supplementary results	115
A.1	Fundamental analysis of PAH growth models	115
A.2	Identifying stages of carbon black formation	118

List of figures

1.1	The TEM images of Carbon black (a & c) [161] and soot (b & d) [175, 100] that shows soot and CB has similar morphology and structure	3
1.2	Standard enthalpy (ΔH) and entropy ($T\Delta S$) contributions to Gibbs function of reaction ΔG at 1600 K for carbon formation from propane(reprinted from Ref. [182])	5
1.3	The range of time and length scales of the processes involved in soot formation from molecular reactions to particle-fluid interaction in flames	6
1.4	The HRTEM image of (a) a nascent soot primary particle with disordered internal nanostructure juxtaposed with that of (b) a mature soot primary particle with well-organized cluster near the shell sampled from soot generated by pyrolysis of ethanol at 1250 and 1650, respectively. Reprinted from Ref.[174]	11
1.5	The conceptual structure of developed process design tool that account for gas mixture properties, and soot chemistry involving inception, surface growth and oxidation as well as its coagulation leading to the fractal-like morphology of soot particles	13
2.1	The structure of Omnisoot that illustrates the coupling with Cantera and sub-models including reactors, particle dynamic models, PAH growth models and surface reactions models	18
2.2	The schematics of constant volume reactor (a), constant pressure reactor (b) perfectly stirred reactor (c), and plug flow reactor (d)	21
2.3	The comparison of temperature and soot mobility diameter, d_m (a) and the mole fraction of methane, CH_4 , and benzene, A1 in the simulation of the pyrolysis of 30% CH_4 -Ar when soot sensible energy is considered (labeled as "WSSE") and neglected (labeled as "W/OSSE"). The CVR is used along with Caltech mechanism [21], Reactive Dimerization and MPBM	22

2.4	The schematics of a soot agglomerates with 12 primary particles ($n_p = 12$). Primary particle, d_p , mobility d_m , and gyration d_g , diameters are shown.	27
2.5	The illustration of sections in SPBM. The mass of sections grows progressively by the scale factor of SF. Inception introduces new particles to the first section that propagate to the upper section via coagulation and surface growth and return to lower sections by oxidation. Carbon and hydrogen pass from gas to solid phase through inception and surface growth and goes back via oxidation.	30
2.6	The temperature dependence of inception flux, I_{inc} , predicted using various PAH growth models. I_{inc} of each model is normalized with its maximum to facilitate the comparison.	48
3.1	The comparison of collision frequency, β , obtained by Omnisoot using harmonic mean (red solid line) and Fuchs interpolations (blue dashed line) with DEM results (symbols) [63].	54
3.2	The schematic of the agglomeration process in the coagulation test case where initially spherical particles collide and form agglomerates	55
3.3	The number concentration of agglomerates and primary particles (a), and mobility and gyration diameters (b) obtained by Omnisoot using MPBM and SPBM in the free-molecular regime, which are in close agreement with the DEM results [94] indicating the validity of the coagulation sub-models.	56
3.4	The non-dimensional particle size distribution at different residence times in the free-molecular (a) and continuum regimes (b) overlaps after the initial transient phase, indicating the attainment of a self-preserving size distribution, which is also in good agreement with DEM results [63].	56
3.5	Standard deviation of the mobility diameter, σ_g , in the free-molecular regime obtained by SPBM is in close agreement with DEM results [94].	57
3.6	The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted against residence time during pyrolysis of 30% $\text{CH}_4\text{-N}_2$ at 2455 K and 3.47 atm in the constant volume reactor simulated using different PAH growth models along with MPBM (solid line) and SPBM (dashed line).	58

3.7	The pressure time history (black line) measured by the Stanford group for pyrolysis of 5%CH ₄ at T ₅ = 2355 K and P ₅ = 4.64 atm, and filtered (red line) with reduced fluctuations used to specify the pressure of the reactor	59
3.8	The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted against residence time during pyrolysis of 5% CH ₄ -Ar at post-reflected-shock temperature and pressure of T ₅ = 2355 K and P ₅ = 4.64 atm with an imposed pressure profile simulated using different PAH growth models along with MPBM (solid line) and SPBM (dashed line)	60
3.9	The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted in simulation time during adiabatic combustion of C ₂ H ₄ -air with $\phi = 2$ at 1 atm simulated using different combinations of PAH growth models and particle dynamics models: MPBM (solid line) and SPBM (dashed line).	61
3.10	The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted against reactor length (cm) in the adiabatic flow reactor during pyrolysis of 30% CH ₄ -N ₂ at 2100 K and 1 atm simulated using different PAH growth models and MPBM (solid line) and SPBM (dashed line) .	62
4.1	The mole fraction of CH ₄ (a), C ₂ H ₄ and C ₂ H ₂ (c) during pyrolysis of 5% CH ₄ -Ar predicted using different reaction mechanisms and compared with measurements [58].	65
4.2	The maximum soot volume fraction predicted using Irreversible Dimerization and different reaction mechanisms during pyrolysis of 5% CH ₄ -Ar was compared with measurements [58]. The shaded area represents the uncertainty in the reported experimental data.	65
4.3	The relative error of CY normalized by the maximum value at $t = 1.5$ ms for 5% CH ₄ -Ar obtained using Caltech mechanism and all PAH growth models. Each cell is annotated with its corresponding normalized relative error expressed in percent.	68
4.4	The bell-shaped temperature profile of carbon mass fraction of soot precursors (A2 and larger) combined and C ₂ H ₂ at $t = 1.5$ ms during pyrolysis of 5% CH ₄ -Ar obtained using Caltech mechanism without considering soot.	69

4.5	The soot carbon yield, CY, at $t = 1.5$ ms (a) and primary particle diameter, d_p (b) obtained using the default soot precursors (denoted by solid line and labeled as "Default") compared with the same results when five-membered ring PAHs excluded from soot precursors (denoted by dashed line and labeled as "NoFive"). Both cases were obtained using Caltech mechanism and the same equal adjustment factors. The black dashed line was added to show the trend in the measurements [4].	69
4.6	The CY (a) and primary particle diameter, d_p , (b) at $t = 1.5$ ms during the pyrolysis of 5% CH ₄ -Ar obtained using equal adjustment factors to minimize the prediction error with extinction measurements [4]. The dashed line was added to show the trend in the measurements.	71
4.7	The variation of θ , defined as soot carbon mass from inception, PAH adsorption and HACA normalized by total soot carbon mass at $t = 1.5$ ms during the pyrolysis of 5% CH ₄ -Ar.	71
4.8	The temperature dependence of total number of agglomerates, N_{agg} (a), number of primary particles per agglomerate, n_p (b) at $t = 1.5$ ms during the pyrolysis of 5% CH ₄ -Ar.	72
4.9	The comparison of CY and d_p at $t = 1.5$ ms for 5% CH ₄ -Ar when the minimum inception (solid lines) and the minimum PAH adsorption adjustment factors were applied to minimize the prediction error. The dashed line was added to show the trend in the measurements.	72
4.10	The centerline temperature along the reactor for $Q = 8, 11$, and 12 L/min interpolated from the thermocouple measurements [115].	73
4.11	The particle size distribution at the end of PFR, and the total number of agglomerates, N_{agg} , and inception flux, I_{inc} along the PFR for $Q = 8$ (a, d), 11 (b, e), and 12 L/min (c, f) obtained using KAUST mechanism, SPBM and different inception models calibrated to match the predictions with measurement [115].	75
4.12	The variation of θ , defined as soot carbon mass from inception, PAH adsorption and HACA normalized by total soot carbon mass for $Q = 8$ L/min along with d_p and d_m obtained using KAUST mechanism, SPBM and different inception models.	76

4.13	The particle size distribution at the end of PFR, and the mole fraction of A2R5, and inception flux, I_{inc} along the PFR for $\phi = 1.9$ (a, d), 2.0 (b, e), and 2.1 (c, f) obtained using KAUST mechanism, SPBM and different inception models calibrated to match the predictions with the PSD measurements [109].	77
4.14	The primary particle diameter, d_p , the total surface growth rate by HACA and PAH adsorption, and the soot volume fraction, f_v along the PFR for $\phi = 1.9$ (a, d), 2.0 (b, e), and 2.1 (c, f) obtained using KAUST mechanism, SPBM and different inception models calibrated to match the predictions with the PSD measurements [109].	79
4.15	Samples of TEM images collected for $T_5=2203$ K. Red circles represent the identified primary particles used to measure d_p	83
4.16	The comparison of (a) pressure (b) temperature (c) CB volume fraction for simulations with constant and imposed pressure trace at $T_5=1984$ K.	84
4.17	The time history of (a) CH_4 and (b) C_2H_2 predicted using CRECK mechanisms in close agreement with the laser absorption measurements. The shaded area represents the uncertainty in the measurements.	86
4.18	The four stages of CB formation demonstrated at $T_5=1984$ K for (a) CB volume fraction, f_v , and carbon yield, CY (b) surface growth rate, I_{gr} , via HACA and PAH adsorption, and inception flux; (c) the carbon mass fraction, CMF, of C_2H_2 and CB precursors combined, and primary particle diameter, d_p , and mobility diameter d_m , of CB agglomerates. Panel (a) depicts the light extinction measurements at $\lambda = 1064$ nm with the shaded area representing the uncertainty from the variability in $E(m)$	88
4.19	The time histories of normalized CB volume fraction, $f_v/f_{v,m}$ and normalized surface growth, $I_{gr}/I_{gr,m}$ at various temperatures. The measurements are from light extinction at $\lambda = 1064$ nm with the shaded area representing the uncertainty from the variability in $E(m)$	89
4.20	The time histories of average primary particle diameter, d_p compared with TEM measurement. The shaded area, and error bar represents the d_p arithmetic standard deviation from the simulations and measurements, respectively. The dashed line specifies the time when d_p reaches 99% of its final value.	91

4.21	The predicted CB induction time, τ_{ind} , compared with light extinction measurements at 633 nm and 1064 nm, and with the data from Agafonov et al. [5]. The dashed line is the Arrhenius fit to the measurements.	92
4.22	The CB volume fraction, f_v , from light extinction at $\lambda = 633$ nm sampled at 2 ms (a), 3 ms (b), 4 ms (c), and 5 ms and compared with the simulation results for $T_5 = 1875, 1984, 2132, 2203, 2247, 2355$ K. Errors bars indicate experimental uncertainty due to variability in $E(m)$, and the dashed line is added to show the trends.	94
4.23	The final primary particle diameter, d_p , from TEM measurements compared with the model predictions.	95
4.24	The evolution of (a) maturity index, β , obtained from extinction measurements at 633 nm and 1064 nm, and (b) the predicted H/C ratio of CB particles at various T_5	96
A.1	The comparison of CY (a) and primary particle diameter, d_p , at $t = 1.5$ ms obtained using MPBM and SPBM models for the case optimized using equal adjustment factors to minimize the prediction error.	115
A.2	The temperature dependence of total number of agglomerates, N_{agg} (a), number of primary particles per agglomerate, n_p (b), at $t = 1.5$ ms obtained using MPBM and SPBM models for the case optimized using equal adjustment factors to minimize the prediction error.	116
A.3	The non-dimensional particle size distribution during 5%CH ₄ -Ar at $T_5 = 2200$ K that evolves from 1 ms to 2.5 ms indicating SPSPD is not attained yet.	116
A.4	The particle size distribution at the end of PFR for $Q = 8$ (a), 11 (b), and 12 L/min (c) obtained using Caltech mechanism, SPBM and different inception models calibrated to match the predictions with measurement [115].	117
A.5	The surface growth by HACA and PAH adsorption combined along the PFR for $Q = 8$ (a), 11 (b), and 12 L/min (c) obtained using KAUST mechanism, SPBM and different inception models. The yellow area represents the hot zone ($T > 0.9T_{max}$).	117
A.6	The measured pressure trace and the filtered profile imposed in the model for the entire temperature range	118
A.7	The number of hydrogenated sites, $\chi_{soot-H} = H_{tot}/A_{tot}$ normalized by its nominal value of $\chi_{soot-H}^{nom} = 2.3 \times 10^{19}$ sites/m ²	118
A.8	The effect on carbonization on CB induction time.	119

A.9	The carbon mass fraction of CB precursors at 0.5 ms	119
A.10	The final primary particle diameter, d_p , considering the additional carbon mass from condensation of benzene and larger species on CB compared with d_p from TEM measurements and the model predictions at 7.5 ms.	120
A.11	The size distribution of primary particles from TEM measurements compared with the model predictions.	121
A.12	The CB mass from inception, PAH adsorption and HACA normalized by total carbon mass at $t=5$ ms	122
A.13	Samples of TEM images collected for $T_5=1875$ K that shows a compact carbonaceous lump with not clear boundaries between primary particles.	122

List of tables

2.1	The names, symbols, chemical formula and molecular weight of the soot precursors used by Omnisoot.	20
2.2	Rate coefficients for the monomer de-/hydrogenation reaction of E-bridge formation in Arrhenius form $k = AT^n \cdot e^{-E/RT}$ [54].	46
2.3	The summary of key features of PAH growth models.	48
2.4	Arrhenius rate coefficients of the surface reactions in HACA [8], $k = AT^n \cdot e^{-E/RT}$	50
4.1	The value of adjustment factors used in the simulation of 5% CH ₄ -Ar pyrolysis.	70
4.2	The value of adjustment factors used in the simulation of ethylene pyrolysis in the flow reactor.	74
4.3	The value of adjustment factors used in the simulation of ethylene oxidation in the perfectly stirred reactor.	77
4.4	The geometric mean mobility diameter, $d_{m,g}$, and the geometric mobility standard deviation, $\sigma_{m,g}$, obtained using different inception models compared with the value calculated from the measured PSD [109].	78
4.5	The post-reflected-shock pressure (P_5) and temperature (T_5) of the executed shock-tube tests.	83
4.6	The primary particle diameter measurements from TEM images. d_p is arithmetic mean, $d_{p,g}$ geometric mean, σ_p arithmetic standard deviation, and $\sigma_{p,g}$ geometric standard deviation.	92

Nomenclature

Acronyms

CFD Computational Fluid Dynamics

DEM Discrete Element Modelling

HACA H-abstraction-C₂H₂/Carbon-addition

MPBM Monodisperse Population Balance Model

SPBM Sectional Population Balance Model

Constants

Av Avogadro's number $6.02214076 \times 10^{23}$ 1/mol

k_B Boltzmann constant $1.3806488 \times 10^{-23}$ J/K

R Global gas constant 8.314 J/mol

English symbols

A Surface area.....m²

c_p Heat capacity at constant pressure.....J/kgK

c_v Heat capacity at constant volume.....J/kgK

c_{soot} Heat capacity of soot J/kgK

C_{tot} Total carbon content of soot particles (per section).....mol/kg

D Diffusion coefficient of particles m²/s

d	Diameter	m
d_c	Collision diameter	m
d_g	Gyration diameter	m
D_H	Duct hydraulic diameter	m
d_m	Mobility diameter	m
d_p	Primary particle diameter	m
e	Internal energy	J/kg
$E(m)$	Absorption function of soot	—
f	Friction factor	—
f_v	Soot volume fraction based on gas volume	m ³ /m ³
h	Enthalpy	J/kg
H_{tot}	Total hydrogen content of soot particles (per section)	mol/kg
I	Partial source terms for soot variables	mol/(kg · s)
k	Reaction rate constant	m ³ /(mol · s)
k_{dep}	Deposition velocity	m/s
Kn	Knudsen number	—
m	Mass	kg
n_p	Number of primary particles of per agglomerate	
N_{agg}	Number density of agglomerates	mol/kg
N_{pri}	Number density of primary particles	mol/kg
p	Pressure	Pa
P_c	Wetted perimeter of the flow reactor	m
R_H	Duct hydraulic radius	m
Re	Reynolds number	—

S	Source terms for soot variables.....	mol/(kg · s)
Sc	Schmidt number	—
SF	Sectional spacing factor	—
Sh	Sherwood number.....	—
T	Temperature	K
u	Velocity.....	m/s
V	Volume	m ³
W	Molecular weight	kg/mol
Y	Mass fraction of gaseous species	—

Greek symbols

β	Collision frequency.....	m ³ /s
δ_a	Mean distance of particles.....	m
ϵ	Wall roughness.....	m
η_{ads}	PAH adsorption adjustment factor	—
η_{inc}	Inception adjustment factor	—
λ	Mean free path	m
λ_a	Mean stopping distance of particles	m
μ	Gas dynamic viscosity	Pa · s
ω	The rate of production of gaseous species.....	mol/m ³ s
ρ	Density.....	kg/m ³
τ_w	Wall shear stress	Pa
τ_{psr}	Nominal residence time of perfectly stirred reactor.....	Pa
φ	Soot volume fraction based on reactor volume	kg/m ³

ζ Collision efficiency.....—

Subscripts

ads Adsorption

agg Agglomerate

coag Coagulation

cont Continuum

f Forward

fm Free molecular

grow Surface growth

inc Inception

ox Oxidation

pri Primary particle

r Reverse

reac Reactive

Chapter 1

Introduction

1.1 Motivation

Carbonaceous nanoparticles, such as Carbon Black (CB) and soot, are widely encountered in nature and engineering. Every year, nearly 9.5 megatons of soot (black carbon) is emitted into the atmosphere from anthropogenic activities and natural sources such as wildfires and volcanoes [128]. The wide light absorption range of soot reduces the albedo of snow-covered area and alters the radiative forcing balance in the atmosphere making soot the third strongest contributor to climate change after methane and carbon dioxide [128]. Also, exposure to combustion-generated soot could promote respiratory and cardiovascular diseases [138]. So, strict regulations are targeting combustion engines to limit environmental and health risks from soot formation [43]. Accurate and affordable models are essential for the prediction of soot composition and morphology in combustion devices and the reduction of emissions in engines. They can also provide better understanding of soot optical properties that are major indicator of soot environmental effects.

On the other hand, CB with a similar synthesis process and structure to soot but higher elemental carbon to hydrogen ratios ($>97\%$) [189] is commercially produced and sold in large scales. In fact, CB is the largest industrially produced nanomaterial by value and volume (~ 15 megatons per year with a value of \$17B) with applications as a reinforcing agent in rubber and tire industries [10], and conductive additive in lithium-ion batteries [139]. CB is primarily manufactured by the so-called furnace process in which about 50% of heavy fuel oil is partially combusted to convert the rest of it into CB [144]. This process suffers from low mass yield and excessive emission, generating 4 tons of CO_2 per each ton of product on average [12]. Plasma reactor is an emerging alternative production method with distinct advantages over flame-based

methods: They can achieve 100% carbon yields with no direct CO₂ emission or other pollutants [31], and the energy required for pyrolysis is supplied by an electric arc that does not depend on the feedstock composition. Controlling CB properties such as its specific surface area (or primary particle diameter), hard agglomerate size (or gyration diameter of agglomerates with primary particles connected to each other by strong chemical bonds), and composition (or particle carbon to hydrogen ratio) is important to make the process economical and to achieve specific grades of CB for different target applications. However, this is a challenging task because of the complexity of CB formation and mass growth processes and its coupling with gas phase chemistry, dependence on local temperature and pressure. This requires accurate process design and optimization tools built on physics of CB formation and evolution to inform manufacturers' decisions for production of CB with desired grades [141].

The term "*soot*" usually refers to the unwanted particulate matter formed during incomplete combustion of any carbon-containing material from jet and diesel fuel to wood, heavy oil, and plastics with variable organic content and a large variation in C/H ratio [189], but this research focuses on soot particles generated under controlled laboratory conditions from fuels with known compositions. The mature soot formed in methane and ethylene premixed flame can reach 95% elemental C/H ratio [150], which is close to CB composition. The comparison of transmission electron microscopy (TEM) images of industrially produced CB [161] with soot sampled from diesel fuel [175, 100] shown in Fig.1.1 indicates similarity of their morphology and structure. Hereafter, soot will be used to collectively refer to carbonaceous nanoparticles produced in flame/reactor during combustion/pyrolysis processes.

1.2 Background

1.2.1 Soot inception and surface growth

Soot formation involves concurrent processes with different time and length scales starting from the breakdown of hydrocarbon molecules to formation of intermediate species and radicals that transition into soot particles and grow via heterogeneous reactions on the surface as well as coagulation [41]. The TEM analysis of soot sampled from flames [100], reactors [137], and engines [190] with different fuels and process conditions revealed a common fractal-like morphology, often characterized as agglomerates of primary particles. High resolution transmission electron microscopy (HRTEM) of soot primary particles showed clusters of precondensed Polycyclic Aromatic

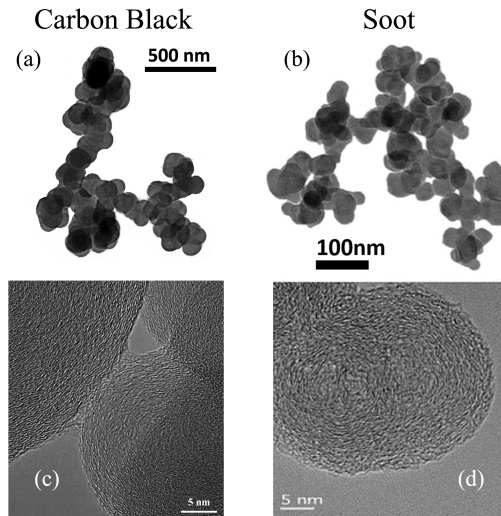


Fig. 1.1 The TEM images of Carbon black (a & c) [161] and soot (b & d) [175, 100] that shows soot and CB has similar morphology and structure

Hydrocarbons (PAHs) [7] pointing to PAHs as main soot precursors. This hypothesis was also supported by thermodynamic stability of PAHs enabling them to resist dissociation at high flame temperatures [165].

However, the transition of PAHs (soot precursors) to incipient soot, known as *soot inception* has not been well understood at the level of pathways and elementary reactions [182] primarily due to uncertainties in PAH (precursor) chemistry. The formation of carbonaceous particles is kinetically controlled and known to be an entropy-driven process [182]. Wang [182] uses the pyrolysis of propane at 1600 K to highlight how thermodynamics of soot formation is distinct from synthesis of inorganic nanomaterials. As shown in Fig. 1.2, acetylene is highly endothermic, but it is accompanied with drastic increase in entropy due to hydrogen release resulting in overall decrease of Gibbs free energy, which explains acetylene (C_2H_2) being the dominant hydrocarbon species. The growth of PAHs from acetylene does not undergo a significant enthalpy release or entropy increase, so the path is driven by a gradual reduction in Gibbs free energy. As a result, the kinetics of PAH growth into subsequent soot particles can be highly reversible hence sensitive to local temperature, pressure and intermediate species concentration.

The growth of PAHs beyond first ring (benzene) is predominantly driven by so-called hydrogen abstraction carbon (acetylene) addition (HACA) mechanism [50] where a hydrogen radical abstracts an hydrogen atom at the edge of PAH, providing a reactive site for acetylene addition. The kinetic reversibility of HACA opens the door for

competing pathways such as chain reactions of resonance-stabilized radical (RSR). Propargyl is a prominent example of these radicals, whose combination is known as a major contributor to benzene formation [46]. Built on this hypothesis, Johansson et al. [80] proposed a radical-driven growth mechanism by addition of vinyl (C_2H_3) starting from cyclopentadienyl (C_5H_5) to larger hydrocarbon radicals that can survive long enough in high temperatures to react with other radicals, PAHs and unsaturated aliphatic species, through radical chain reactions. However, low concentrations of these radicals limit the growth rate through RSR pathways [54]. Moreover, some of the intermediate steps for radical regeneration such as formation of vinylcyclopentadienyl were shown to be kinetically unfavorable [54] compared to HACA. Regardless of their mechanistics, these sequential growth mechanisms, termed as *chemical growth* cannot account for rapid soot formation [50] and its nanostructure [52].

There is abundant but mostly indirect experimental and computational evidence pointing to an alternative collision-based mechanism for soot inception. HRTEM images of nascent and mature soot shows disordered PAH clusters highlighting the role of PAH collisions. The bimodality of particle size distribution (PSD) of nascent soot particles in premixed flames [202] indicates that the kinetics of inception is second order in precursor concentration [1]. The time-of-flight mass spectrometry (TOFMS) experiments in a 13 kPa acetylene-oxygen flame showed a series of peaks with a periodicity of 500 amu [68].

It is not clear how PAH clusters form and what forces allow the binding occur and resist dissociation at flames temperatures ($T \geq 1600$ K). Frenklach [50] described clustering of PAHs as an irreversible process where two PAHs collide and stick upon collision forming dimers held together by Van der Waals (vdW). Herdman and Miller [73] found that the binding energy of PAHs dimers due to dispersive and electrostatic forces increases linearly with molecular mass and reaches the limit of exfoliation energy for graphite. However, the entropy barrier of dimerization increases with PAH size making them unfavorable under equilibrium conditions. So, PAHs as large as circumcoronene ($C_{54}H_{18}$) can only form dimer to survive flame temperatures [182]. However, the concentration of large PAHs are too low to account for the observed number density of soot particles in flames [170].

There is also the possibility of PAH clustering governed by non-equilibrium kinetics. PAH molecules can form rovibrationally excited dimer with long enough life-time [191] to react with H atoms forming covalent bonds. There is another possibility for these clusters to be joined by aliphatic linkages. Micro-FT-IR spectroscopy analysis by Cain et al. [25] showed the ratio of aliphatic-to-aromatic C-H bonds can exceed unity at the

flame temperature. Using these findings, they suggested that the aliphatic components in the form of alkyl and alkenyl can covalently bound to aromatic units in soot particles. Although such a mechanism is viable near the flame region, it cannot explain persistent soot inception in the post-flame zone [203] where the H atom concentration is too low to initiate H abstraction reactions that produce those radicals.

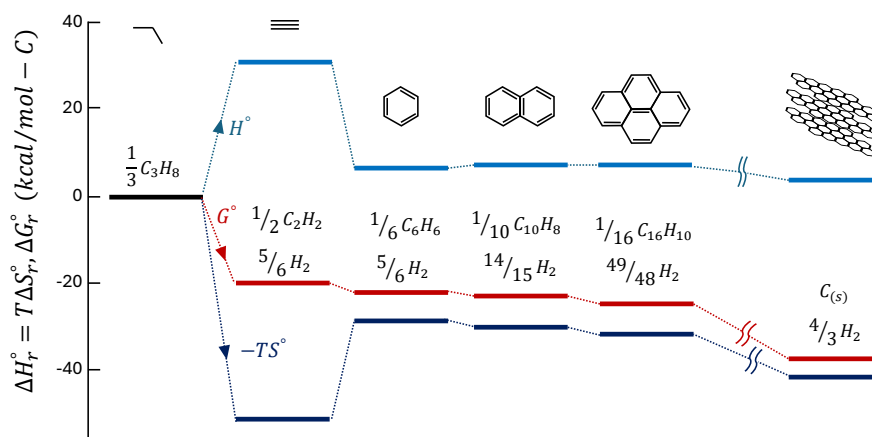


Fig. 1.2 Standard enthalpy (ΔH) and entropy ($T\Delta S$) contributions to Gibbs function of reaction ΔG at 1600 K for carbon formation from propane(reprinted from Ref. [182])

There are other complicating factors that hinders the fundamental understanding of soot inception such as lack of a decisive criterion to distinguish gaseous molecules from particles [41], and the overlap of inception with surface growth and agglomeration [111]. Measurement techniques have limited capability in soot detection due to short time and length scales of soot inception and surface growth ranging from pico- to milliseconds and micro- to millimeter [179]. Fig. 1.3 demonstrates the length and time scales relevant to different stages of soot formation from PAH precursors to incipient, nascent and mature soot in flames. Moreover, the collected data from measurements might not be true representatives of soot formed at the probed location of the studied process. For example, intrusive diagnostic methods based on thermophoresis or dilution have a sampling probe that can perturb flow dynamics or alter structure and composition of soot [92]. Non-intrusive techniques such as optical methods also rely on assumptions about light absorption and scattering of soot [158] and its morphology [39].

Despite the gaps in fundamental understanding of soot formation and limitations of diagnostics methods, models have been developed describe the soot inception and growth. These models have been formulated as a set of clear pathways that explain soot inception based on collisions of PAH molecules. They have to be consistent with current knowledge of soot inception, feasible to be coupled with chemistry and particle

dynamics models, and able to predict soot mass, PSD and morphology observed in flames and reactors.

The classic description of soot inception relies on PAH dimerization where collision of two PAH molecules (monomers in this context) forms a dimer held together by Van der Waals forces [55]. The dimerization is a irreversible process with an efficiency that accounts for the reversibility or dissociation of dimers. The theory postulates that PAH growth continues by sequential addition of a monomer (PAH molecule) forming stacks of dimers, trimers, tetramers and so on to reach a certain mass threshold that marks the emergence of incipient soot [55], but for practical purposes, a dimer is usually considered as an incipient soot. Here, we call this model *Irreversible Dimerization*. Irreversible Dimerization has been used to predict soot formation in burner-stabilized premixed [155, 37], counterflow diffusion flames [187, 196], coflow diffusion flames [96, 178]. A collision efficiency factor ranging between 10^{-6} to 1 is also employed to adjust the inception flux and PAH adsorption rates to achieve desired soot mass and size distribution. PAHs of moderate sizes such as pyrene (4 rings) to coronene (7 rings) have been considered as the starting point of inception due to their thermodynamic instability that justifies the irreversibility at high temperatures [55]. However, the theoretical calculations [125] and experiments [151] indicated that PAH dimerization is highly reversible in flame conditions.

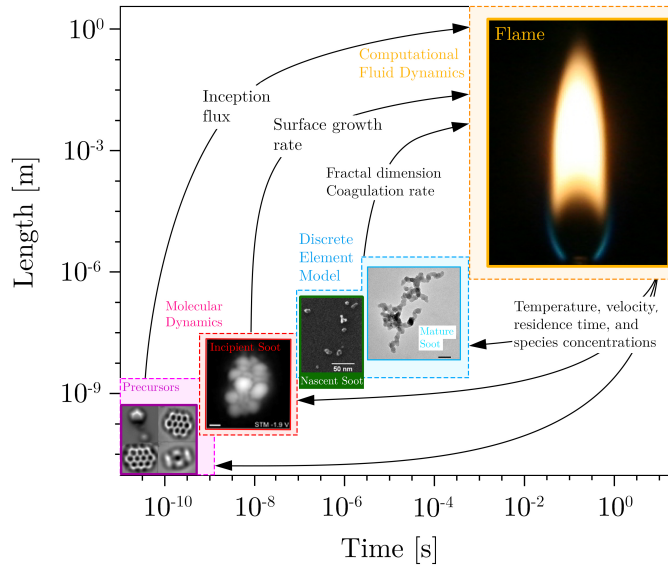


Fig. 1.3 The range of time and length scales of the processes involved in soot formation from molecular reactions to particle-fluid interaction in flames

The inception flux of irreversible dimerization is determined from collision of PAHs, which is proportional to $\sqrt{T}$, so new particles can be formed at low temperatures (even less than 500 K) [131] despite experimental evidence for termination of inception below 1200 K [156, 30]. Moreover, the arbitrary selection of efficiency factors alters the distribution of mass between inception of surface growth could significantly change soot mass, PSD, and morphology [152]. Miller [123] used equilibrium constant for PAH dimerization to calculate the net dimerization rate and demonstrated that the collision of PAHs larger than circumvalene (~ 800 amu) could last long enough grow into incipient soot. However, the concentration of PAHs drops rapidly with size [182]. The entropy barrier of dimerization is significant for larger PAHs [59].

Eaves et al. [42] relaxed the irreversibility assumption, and developed a reversible clustering model to simulate inception using an array of PAHs from naphthalene to benzo-pyrene. Building on that work, Kholghy et al. [93] emphasized on the necessity of chemical bond formation after physical PAH clustering for accurate prediction of volume fraction, primary particle diameter and PSD in ethylene coflow diffusion flames. Later, Kholghy et al. [95] proposed the "*Reactive Dimerization*" model which starts with reversible collision of PAHs leading to physical dimers held with vdW forces that are graphitized and form chemically-bonded dimers that serve as soot nuclei grow via surface reactions. They also performed a systematic analysis on the contribution of different PAHs, and concluded that one- and two-ring aromatics account for almost all of inception flux in the so-called "*sooting flame*" [37]. However, Frenklach and Mebel [54] pointed out that an inception model that initiated with a highly reversible step similar to Reactive Dimerization [95] cannot produce sufficient flux of particles to match measurements of the benchmark burner-stabilized stagnation flame [1]. Instead, they proposed a HACA-driven mechanism where addition of monomer molecule to its radical activated by hydrogen abstraction for a stable dimer via an E-Bridge bond formation, and this sequential process continues to form trimers, tetramers, and larger PAH clusters.

The gas-phase chemistry of aromatics can be extended to account for chemical growth of incipient soot via surface reactions [50]. This hypothesis, known as "chemical similarity" postulates that the reactions occurring on the soot surface are similar to those involving large molecules of PAHs in the gas phase. It also provides means to describe the rates of surface growth and particle oxidation in terms of elementary chemical reactions. In other words, it is assumed that the surface of soot particles is made up of lateral faces of large PAHs covered with C-H bonds. This is the basis for HACA mechanism [55, 8] that assumes the soot surface to consist of hydrogenated sites

with a predefined density. Mass growth on soot surface requires H-abstraction to form a radical site, followed by acetylene attack similar to growth of PAH molecules in the gas-phase. The reactivity of these sites changes with time and temperature [192, 35], described as soot aging. For modelling purposes, a temperature-dependent multiplier, usually represented by α , was introduced to account for these effects. Appel et al. [8] showed α changes with temperature and particle size.

Adsorption of PAHs on the surface of soot particles is also a viable growth mechanism [55], more specifically called physisorption or chemisorption depending on the mechanisms driving the adsorption process [120]. There is still debate over the stability of adsorbed PAH molecules on soot surface [135]. Following the hypothesis that PAHs are building blocks of soot particles, a mechanism similar to inception is often used to describe PAH-soot growth.

1.3 Coagulation and agglomeration

In typical soot formation processes such as those occurring in flames and reactor, soot particles are formed at high number concentrations (10^{12} 1/cm³), and inception and surface growth are relatively short compared to the total residence time of soot particles. As a result, coagulation becomes dominant rapidly attaining both [64] self-preserving size distribution (SPSD) [99] and asymptotic fractal-like structure [126]. The evolving fractal-like structure of agglomerates quantified by their mobility diameter normalized by primary particle, d_m/d_p , and gyration, d_m/d_g , diameters can be described with power laws derived from mesoscale simulations [85]. The collision frequency of agglomerates depends on their evolving fractal-like morphology. Also, polydisperse agglomerates collide more frequently than monodisperse ones. The enhancement in their collision frequency reaches an asymptotic value of 35% [64] or 82% [83] in the free molecular or transition regimes, respectively at PSD regardless of the polydispersity in their constituent primary particles. Particle morphology formed by inception, surface growth and agglomeration can be tracked precisely by mesoscale simulations, such as Discrete Element Modeling (DEM) [84] where each agglomerate is tracked separately. However, they are computationally expensive and interfacing them with chemical kinetics in computational fluid dynamics (CFD) is not trivial [89]. This limits their application in simulation of realistic flames and reactors. So, sectional population balance models (SPBM) are often used to track agglomerate and primary particle size distribution [194], morphology [140], and composition [96] in complex laminar [96] and turbulent flows [157]. Using the SPBMs coupled with relations for agglomerate fractal-

like structure [112] and collision frequency [36], particle size distribution, morphology and composition can be tracked accurately. However, the computational cost of SPBMs increases exponentially with the number of sections [194] and particle properties [96] tracked. Thus, one property (e.g. agglomerate mass) is typically tracked with SPBMs to reduce computational cost. This does not allow to account for agglomerate fractal-like structure [162, 11] which limits SPBM accuracy in predicting surface growth and coagulation rate of agglomerates and their size distribution.

Alternatively, particle dynamics can be tracked by the method of moments (MOM) [82] or monodisperse population balance models (MPBM) [98]. Such models only track average particle properties (e.g. moment ratios) and their accuracy could be limited if unrealistic assumptions (e.g. approximating agglomerates as monodisperse and perfect spheres) are used. However, when inception and surface growth are short [164] and high particle (number) concentrations are formed [85], they lead to rapid attainment of self-preserving size distributions (SPSD) and agglomerates having asymptotic structure [64]. In this case a MPBM or MOM can be assembled on a firm scientific basis with accuracy on par with DEM [84], SPBM [86] and experimental data [2, 108, 26]. Such models can be readily interfaced with CFD simulations [66] without significant computational cost, making them ideal for three-dimensional and even turbulent flame simulations.

The MOM tracks moments of the PSD and estimates average particle properties such as mass [143], surface area [23], the number of constituent primary particles per agglomerate, n_p [82], or even particle composition [22] using the ratio of the moments. The MOM with four equations was used to describe synthesis of optical fibers by simultaneous reaction, diffusion, coagulation and thermophoresis of SiO_2 in laminar flow reactors assuming a lognormal PSD [97]. The MOM with interpolative closure (MOMIC) was developed to predict simultaneous nucleation, surface growth and coagulation of soot agglomerates and estimate its PSD with six equations [82]. To calculate source terms of the transported moments, additional moments that are not tracked are needed preventing the closure of the system of differential equations with the MOM [143, 53]. Thus, often the PSD shape is assumed a priori [143] or extra equations are solved to estimate it [98].

The MPBMs do not have the closure problem and calculate average particle properties by tracking their total concentration, mass [98] and area [172, 106]. Leung et al. [104] used a 2-equation MPBM to track soot concentration and mass in (non-premixed) flames assuming spherical particles. Good agreement was achieved for measured soot mass. However, the specific surface area [106] and coagulation frequency

of spheres are significantly smaller compared to that of agglomerates with the same mass underestimating their oxidation rate [86] and overestimating their concentration [98]. Kruis et al. [98] proposed a 3-equation MPBM to account for the fractal-like structure of nanoparticle agglomerates during coagulation and sintering. Agglomerate volume and area were used to obtain their equivalent primary particle diameter, d_p , and n_p . Then, agglomerate collision diameter, i.e. d_g , was calculated by D_f , d_p and n_p to account for their fractal-like structure that affects their collision frequency. Tsantilis and Pratsinis [172] extended the MPBM to predict hard-(chemically-bonded) and soft-(physically-bonded) agglomerates during synthesis of SiO_2 and TiO_2 [65] nanoparticles with simultaneous reaction, surface growth, coagulation and sintering. Such a MPBM applies best at high concentrations when inception and surface growth are short [164] resulting in the dominance of coagulation where particles rapidly reach their SPSPD and asymptotic fractal-like structure. This is often the case for soot emitted from a variety of combustion devices or CB reactors where inception and surface growth are limited to only a few milliseconds when temperature is very high (i.e. $T \geq 1500\text{K}$) [95].

1.4 Soot maturity and its optical properties

The maturity level of soot is described as the evolution of physical and chemical properties from incipient to graphite-like mature soot [118]. It involves the growth of the graphitic crystallite fine structure of soot within, and perpendicular to, the aromatic layers. [49, 71], known as graphitization, followed by increase in the size of the crystallite-layer planes and decrease of the interlayer spacing [7]. This process is accompanied by the pyrolytic conversion of hydrocarbon species and substituted hydrocarbons toward elemental carbon and increase in the carbon-to-hydrogen (C/H) ratio, known as carbonization. Soot maturity is closely associated with reactivity of surface sites [27]. Fig. 1.4 compares nanostructure of nascent soot composed of disoriented PAH clusters with that of mature soot with a core-shell pattern where disordered core is surrounded by concentrically oriented graphitic layers [68]. The core-shell nanostructure of mature soot strongly depends on process conditions such as pressure, fuel identity, temperature and residence time of the particles.

Evolution of soot maturity and morphology impacts its optical properties. Incipient and nascent soot absorb shorter wave lengths ($\lambda < 600 \mu\text{m}$) as opposed to mature soot particles that are broad-band light absorbers [76]. Non-intrusive optical diagnostic methods such as light extinction (absorption and scattering) [114] and Laser Induced Incandescence (LII) [158] are widely utilized to measure soot volume fraction, f_v using

extinction coefficient and the absorption function, $E(m)$ that depends on soot refractive index, m , soot composition and morphology [38].

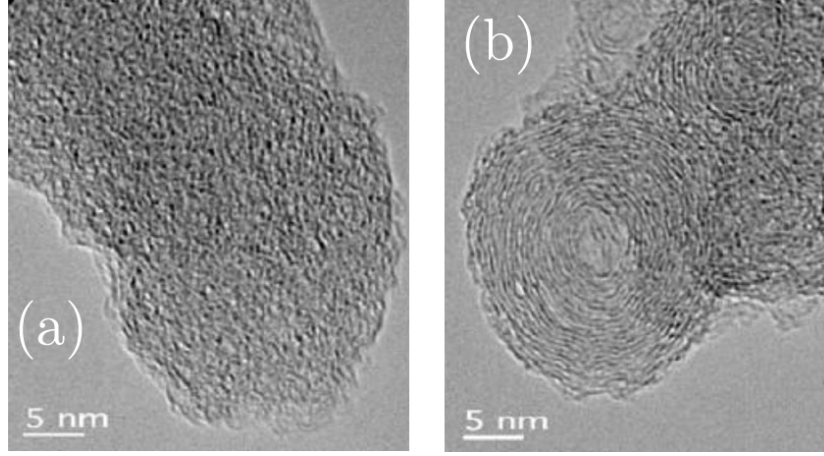


Fig. 1.4 The HRTEM image of (a) a nascent soot primary particle with disordered internal nanostructure juxtaposed with that of (b) a mature soot primary particle with well-organized cluster near the shell sampled from soot generated by pyrolysis of ethanol at 1250 and 1650, respectively. Reprinted from Ref.[174]

However, the effects of soot composition, and morphology on its refractive index, and absorption function are not fully understood yet. $E(m)$ of soot at $\lambda = 1064$ nm measured by two-color LII measurements increases from 0.193 to 0.349, and 0.226 to 0.340 for ethylene premixed flames with equivalence ratio of $\phi = 2.1$ and $\phi = 2.3$, respectively when height above burner (HAB) changes from 8 to 14 mm [136]. During acetylene pyrolysis in a shock tube, $E(m)$ of soot particles increases from 0.05 to 0.25 as their primary particle diameter, d_p , grows to 20 nm within 1.6 ms [44]. Using m and $E(m)$ of mature spherical soot [34] at different HABs neglecting the impact of soot morphology and composition on m [199] can overestimate soot volume fraction by 100% [88]. So, accurate estimation of the evolving optical properties of soot is essential to close the carbon mass balance in the measurements [88], and analyze reaction kinetics for soot inception [95] surface growth [8] and oxidation [145] that are essential for development and validation of aerosol dynamics models coupled with chemistry to predict soot formation.

The dependence of soot m on its morphology and composition can be quantified by soot optical band gap, E_g [24]. The optical band gap concept was originally proposed by Tauc et al. [169] for semi-conductors and later developed for amorphous carbon [148], and it can be used to describe the crystalline character of PAH clusters in soot [148]. Incipient flame-made soot with diameters less than 20 nm exhibit quantum

dot behavior [107] with $0.7 < E_g < 2$ eV that is larger than E_g of graphitized soot, 0.12 eV [107]. Optical band gap of organic carbon coated on soot remains nearly constant (1.8-1.9 eV) over soot evolution [101]. In contrast, Russo et al. [149] measured soot optical band gap using ex-situ and in-situ methods and showed that E_g drops from 0.7 eV at HAB= 8 mm to 0.2 eV at HAB=14 mm in an ethylene premixed flame with $\phi=2.3$ as particles grow and become more mature by carbonization. Kelesidis and Pratsinis [87] correlated the evolving refractive index of soot with its E_g obtained from quantum confinement theory (QCT) [107] for wavelengths of $\lambda= 532$ and 1064 nm [87] by linear interpolations between that of nascent and mature soot. The proposed relations were then used with soot morphologies obtained from Discrete Element Modeling (DEM) simulations to obtain the evolving Mass Absorption Cross-section (MAC), $E(m)$, and the absorption function ratio of soot ($E(\lambda=532\text{nm})/ E(\lambda=1024\text{nm})$) and compared with measurements [15, 121, 33]. Employing the relation in laser diagnostics to reprocess light extinction measurement data resulted in accurate prediction of f_v in moderate ($\phi=2.34$) [88] and rich ($\phi > 3$) ethylene premixed flames [116], and f_v along the centerline of a coflow ethylene diffusion flame [90] which is necessary to close the carbon mass balance in soot generating processes.

1.5 Oxidation

Soot oxidation is described as the removal of soot mass by reaction of molecular oxygen (O_2), oxygen radical (O), and hydroxyl radical (OH) from soot surface. Because of its heterogeneous reaction kinetics and mechanisms, oxidation is expected to be sensitive to surface structure and composition. So, oxidation mechanisms depend on soot maturity and temperature-time history. In near stoichiometric and fuel-rich conditions, the contribution of OH radical to soot oxidation is predominant [134] compared to that of O radicals [105]. Fenimore and Jones [48] investigated soot oxidation rate for low oxygen partial pressures and temperatures from 1530 to 1890 K, highlighted the importance of OH as a major oxidation agent, and attributed the faster rates compared to those predicted by Lee et al. [102], to OH oxidation. One approach for describing OH oxidation is by introducing collision efficiency representing the fraction of collisions of OH with soot particles that resulted in the removal of a carbon atom [134]. Scanning Mobility Particle Sizer (SMPS) with a two-stage burner also showed a collision efficiency of 0.13 [13].

The empirical relation of Nagle and Strickland-Constable (NSC) [129] originally developed for oxidation of pyrolytic graphite have been widely used to describe soot

oxidation by O_2 . It describes O_2 oxidation rates based on partial pressure of O_2 and the fraction of reactive edge sites to less reactive basal planes using the graphite analogy for soot. The dominance of edge sites in typical combustion conditions accounts for the relatively small reactivity of soot and basal planes become reactive at high temperature (>2500 K) [105]. O_2 oxidation kinetics was also described with a power-law kinetics [102], and shown to be first order in oxygen concentration [133]. Alternatively, soot oxidation can be explained based on chemical similarity using HACA mechanism assuming that active sites are attacked by O_2 and OH leading to loss of carbon and release of CO.

A different oxidation regime has been identified for soot at low temperatures ($T < 1000$ K) where O_2 diffuses and reacts with bulk soot accounting for most of soot mass consumption [108]. Internal oxidation compacts the pore network of soot resulting in hollow CB [91], diesel [77] and biodiesel [163] soot particles and increases their SSA up to a factor of four [77]. Oxidation can cause fragmentation of soot particles affecting their morphology. The increase in number concentration and the change of soot morphology in lean premixed flames [195] and in the oxidation region of diffusion flames [146] was attributed to fragmentation. Such a change in agglomerate morphology has not been observed in fuel-rich conditions, so fragmentation was linked to O_2 oxidation.

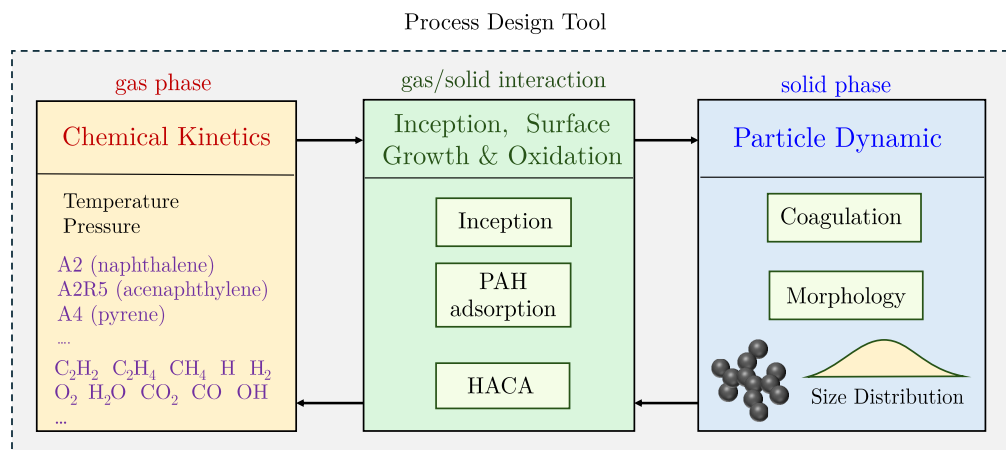


Fig. 1.5 The conceptual structure of developed process design tool that account for gas mixture properties, and soot chemistry involving inception, surface growth and oxidation as well as its coagulation leading to the fractal-like morphology of soot particles

1.6 Research objectives

The purpose of this project is developing a process design tool to predict the yield, morphology, composition and size distribution of soot particles in industrial flames and reactors under different temperatures, pressures and residence times. Integrating gas chemistry, all existing inception and surface growth models and particle dynamics in a single package provides a fully coupled soot description from breakdown of fuel to agglomeration and oxidation of particles that enables sensitivity analysis to shed light on key pathways for soot inception and surface growth in various targets. This tool can also be used for rate constant optimization and mechanism reduction under soot forming conditions. The conceptual structure of this tool is shown in Fig 1.5 that includes a chemical kinetics unit coupled with Cantera [62] to compute thermal and physical properties of gas mixture such as temperature, pressure, density, and enthalpy based on ideal equation of state for the gas mixture. The chemistry of gas mixture is quantified using detail reaction mechanisms that enables tracking concentration of fuel, intermediate species such as C_2H_2 and H_2 essential to surface growth, and PAHs such as benzene (A1), naphthalene (A2) and pyrene (A4) known as building blocks of soot. The second unit accounts for soot inception and surface growth via PAH adsorption and HACA as well as surface oxidation. It accommodates the four inception models widely used in literature. The third unit deals with particle dynamics using a MPBM and SPBM to describe the coagulation of soot particles that results in the fractal-like structure of particle with an evolving size distribution. A multi-step validation procedure is followed to assess reliability of each sub-model that entails the comparison of collision frequency kernels and agglomerate morphology of different particle dynamics models with those of detailed DEM simulations and establishing energy and elemental carbon, and hydrogen balances for all combinations of particle dynamics and inception models with reactors and flames. This tool can be applied to a variety of experimental targets with different temperature- and pressure-time-histories, residence times, and fuel compositions.

As the first step, methane pyrolysis in shock-tube will be simulated using a constant volume reactor. The species measurements will be used to assess the reaction mechanism and examine carbon conversion flux from fuel to smaller intermediates and larger hydrocarbons. The inception flux and surface growth rates of the soot model strongly depend on the reaction mechanism employed to track the concentration of soot precursors. The performance of inception models will be analyzed by comparing the predicted soot volume fraction, f_v and primary particle diameter, d_p , with data collected from extinction and TEM measurements. A sensitivity analysis will

be conducted on model parameters to identify the determining factors that control both f_v and d_p in the framework of shock-tube simulations with short residence time ($t \approx 2$ ms) and high temperatures (≥ 2000 K). Then, the optimization of inception models will be performed by adjusting the rate constants within their physical limit (maximum collision rate of molecules) to minimize the prediction error for yield and morphology. This shows the range of inception flux that ensures the accurate prediction of soot yield and morphology represented by f_v and d_p , respectively in good agreement with measurements. Then, the optimized rates will be applied to shock-tube in a wide temperature range, and the f_v predictions will be compared with data. The measurement on shock-tube pyrolysis of methane with different H_2 concentrations will be used to investigate the effect of hydrogen on pyrolysis chemistry as well as soot yield and morphology. A main focus will be finding the reaction mechanism that describes methane decomposition rate and acetylene and PAH concentrations in good agreement with the data from absorbance measurements. The inception flux and surface growth rate that results in accurate prediction of soot yield and morphology will be estimated and compared with cases without hydrogen. A similar investigation will be conducted for flow reactors using plug flow reactor model of omnisoot at lower temperatures and longer residence times and then the range of expected inception flux will be compared with those of shock-tubes.

In the next step, a reactor network model based on omnisoot will be developed to enable building a series of plug flow reactors (PFR) and perfectly stirred reactor (PSR) models with multiple gas sources to more accurately represent complex industrial reactors. A set of tests will be developed to ensure gas and solid mass and energy balance during the development process. The connections between elements will be developed in a way that recognizes upstream and downstream flows. Moreover, safeguards will be put in place for the network to avoid faulty designs that can result in cyclical flows and detached networks. The performance of the reactor network will be evaluated using benchmark data from literature [109].

The flame solver of omnisoot will be developed from its current experimental stage to a functional level. After validation of the coagulation and surface growth sub-models and ensuring the conservation of carbon and hydrogen mass, and energy balances, the flame solver will be applied to a variety of counterflow diffusion [60, 61] and burner-stabilized premixed flames[1] with stagnation plate [26] at atmospheric and elevated pressures. The reaction mechanism study will be performed to reduce the uncertainty in tracking gas chemistry by comparing the model predictions of species concentration with measurements. The performance of the soot model will be evaluated by comparing

the predicted soot volume fraction, agglomerate number concentration, PSD, mobility and primary particle diameters with those obtained from light extinction measurement, scanning mobility particle sizer (SMPS), and TEM samples, and the comparisons will be use to estimated the range of inception flux and surface growth rates that can predict soot mass, morphology and size distribution with minimum error compared to data.

Chapter 2

Theoretical Model

The mathematical basis for *Omnisoot* is explained in the top-to-bottom hierarchical order. First, the governing equations for constant volume, constant pressure, perfectly stirred and plug flow reactor models are reviewed in Sections 2.2.1-2.2.4. These equations differ from pure gas-phase transport formulation as they consider the solid phase. The transport equations of “soot variables” include the source terms that account for change in each soot variable due to inception, surface growth, oxidation and coagulation. Then, particle dynamics models are explained in Sections 2.3 that entails description of size distribution and morphology of soot particles and their collision rate, which is used to determine the coagulation source term. Section 2.4 focuses on the “*PAH growth model*”s that take care of inception and adsorption from designated precursors and calculates the corresponding source terms. Similarly, the “*surface reactions*” model are detailed in Section 2.5 that elaborates on the surface growth and oxidation rates based on HACA mechanism. Figure 2.1 illustrates the general structure of *Omnisoot* and the sub-models.

2.1 Assumptions and conventions

Here, the main conventions and assumptions used in the derivation of the mathematical models are listed below.

1. f_v and φ denote the volume of soot particles normalized by the gas volume and reactor volume, respectively. Their relationship can be expressed as:

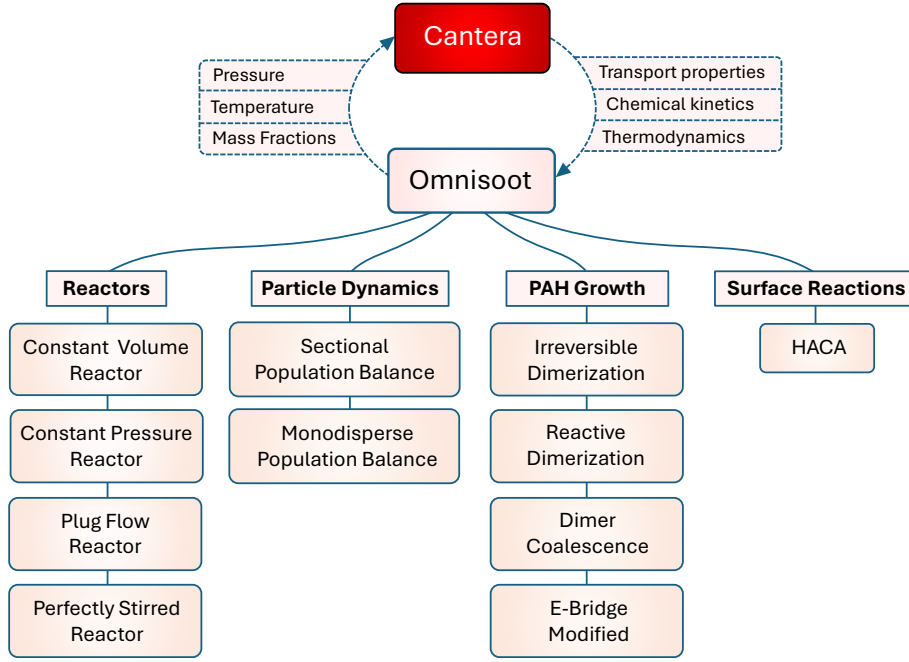


Fig. 2.1 The structure of Omnisoot that illustrates the coupling with Cantera and sub-models including reactors, particle dynamic models, PAH growth models and surface reactions models

$$\begin{aligned}
 f_v &= \frac{V_{soot}}{V_{gas}}, \\
 \varphi &= \frac{V_{soot}}{V_{gas} + V_{soot}}, \\
 \varphi &= \frac{f_v}{1 + f_v}.
 \end{aligned} \tag{2.1}$$

2. $\dot{s}_k$ denotes the rate production/consumption of k_{th} gaseous species (i.e., gas scrubbing) due to soot inception, surface growth and oxidation. It is positive when the species is released to the gas mixture.
3. Each soot agglomerate consists of monodisperse spherical primary particles, which are in point contact. So, the model does not consider formation of necking (or sintering) in soot agglomerates by surface growth.
4. The word “particle” refers to soot both in spherical and agglomerate shape.

5. The density of soot is assumed constant at the value of 1800 kg/m^3 . Soot density changes with its maturity level, which is often linked to the elemental C/H ratio of soot particles [119]. Here, the considered value represents an average between density of mature soot with high C/H ratios ($\rho = 2000 \text{ kg/m}^3$) and that of nascent soot with low C/H ratios ($\rho = 1600 \text{ kg/m}^3$) [78, 119].
6. The incipient soot particles are 2 nm in diameter, so the model does not allow particles with a primary particle diameter smaller than 2 nm. The number of carbon atoms in the incipient soot particle, $n_{c,min}$, is calculated from the mass of a sphere with a diameter of $d_{p,min} = 2 \text{ nm}$ assuming pure carbon content, which results in:

$$n_{c,min} = \frac{\pi}{6} \rho_{soot} d_{p,min}^3 \frac{1}{W_{carbon}} \approx 378. \quad (2.2)$$

7. The specific heat, internal energy and enthalpy of soot are approximated by those of pure graphite, and are employed to close the energy balance in the system [113].
8. Soot particles and gas are in thermal equilibrium during soot formation processes, and there is no temperature gradient within each agglomerate.
9. ψ denotes a *soot variable* that represents a mean property of soot particles in each section tracked in Omnisoot by solving transport equations for the total concentration of agglomerates, N_{agg} and primary particles, N_{pri} , and the total carbon, C_{tot} and hydrogen content, H_{tot} of soot. S_ψ is the source term of the soot variable, ψ , which appears in soot equations.
10. *PAH growth* is a sub-model of Omnisoot with a set of pathways that determine the rate of inception and adsorption from PAHs (designated as soot precursors) in the gas mixture.
11. *Surface reactions* is a sub-model of Omnisoot that describes the addition of acetylene to soot surface, and removal of carbon via oxidation by OH and O₂ following the HACA scheme. The model does not consider soot oxidation with CO₂, H₂O and NO_x.
12. The single superscript i denotes the section number of a soot variable or a derived property. For example, d_p^i represents the primary particle diameter of section i . The double superscript ij indicates a property related to two sections; for

Table 2.1 The names, symbols, chemical formula and molecular weight of the soot precursors used by Omnisoot.

Species name	Symbol	Chemical formula	W [kg/mol]
Naphthalene	A2	C ₁₀ H ₈	0.128
Phenanthrene	A3	C ₁₄ H ₁₀	0.178
Pyrene	A4	C ₁₆ H ₁₀	0.202
Acenaphthylene	A2R5	C ₁₂ H ₈	0.152
Acephenanthrylene	A3R5	C ₁₆ H ₁₀	0.202
Cyclopentapyrene	A4R5	C ₁₈ H ₁₀	0.226

example, β^{ij} denotes the collision frequency between sections i and j . In the case of the monodisperse model, the section number can be omitted because it is equivalent to the sectional model with only one section.

13. The computation of morphological parameters is done similarly in both particle dynamics models, but they are explained separately in Section 2.3.1.
14. *precursors* refer to the PAHs larger than naphthalene used for inception and PAH adsorption. The list of precursors with their chemical formula and molecular mass is provided in Table 2.1. It should be noted that the precursors can be dynamically changed by Omnisoot's user interface.

2.2 Reactors

The governing equations of reactor models implemented in Omnisoot are briefly presented in the following sections. The control volume encompasses the gas mixture and soot particles, as illustrated in Figure 2.2. The equations ensure conservation of total mass and energy of the gas and particle system, which can also receive or lose heat through the reactor walls.

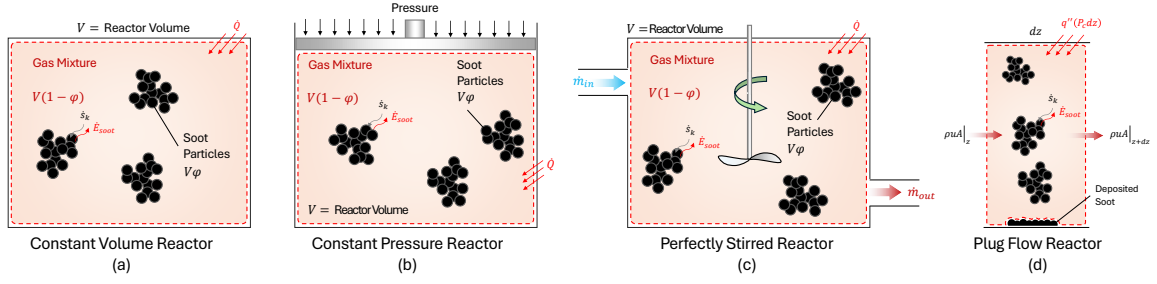


Fig. 2.2 The schematics of constant volume reactor (a), constant pressure reactor (b) perfectly stirred reactor (c), and plug flow reactor (d)

2.2.1 Constant Volume Reactor (CVR)

As shown in Figure 2.2a, CVR represents a closed system constant volume where chemical reactions converts part of the gas mixture to soot particles. The mass balance equation is written as:

$$\frac{d}{dt}(m) = (1 - \varphi)V \sum_i \dot{s}_i W_i, \quad (2.3)$$

where m is the mass of the gas mixture. The rate of change of m is equal to the rate of production of soot mass. Similarly, the species equation for species k is expressed as:

$$\frac{dY_k}{dt} = \frac{1}{\rho} (\dot{\omega}_k + \dot{s}_k) W_k - \frac{1}{\rho} Y_k \sum_i \dot{s}_i W_i. \quad (2.4)$$

The transport equation for a generic soot variable, ψ , can be written as:

$$\frac{d\psi}{dt} = S_\psi - \frac{\psi}{\rho} \sum_i \dot{s}_i W_i. \quad (2.5)$$

The second term on RHS of Equations (2.4) and (2.5) denotes the change in Y_k and ψ , respectively, due to the removal or addition of gas mass by soot-related processes. The energy conservation for the gas mixture is written in terms of the rate of change of temperature. An external heat source of $\dot{Q}$ is considered to account for possible heat loss/gain of the reactor.

$$\begin{aligned} \frac{dT}{dt} = \frac{1}{\rho c_v + \rho_{soot} f_v c_{soot}} & \left[- \sum_k e_k (\dot{\omega}_k + \dot{s}_k) W_k \right. \\ & \left. + e_{soot} \sum_k \dot{s}_k W_k + \frac{\dot{Q}}{V(1 - \varphi)} \right], \end{aligned} \quad (2.6)$$

where $\rho_{soot} f_v c_{soot}$ and $e_{soot} \sum_k \dot{s}_k W_k$ represent the formation and sensible energy of soot, respectively. We investigated the effect of considering soot formation and sensible energy on gas and soot properties by simulating the pyrolysis of 30% CH₄-Ar with and without considering the above mentioned term. As shown in Figure 2.3a, neglecting soot sensible energy results in the overprediction of temperature by nearly 150 K and mobility diameter by a factor of 3 during the 80 ms of the simulation. The overprediction of temperature changes gas chemistry, leading to a noticeable decrease in the residual methane and benzene (Figure 2.3b).

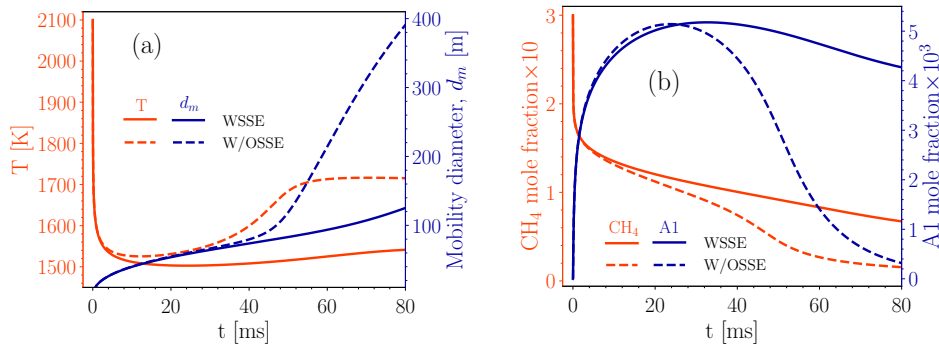


Fig. 2.3 The comparison of temperature and soot mobility diameter, d_m (a) and the mole fraction of methane, CH₄, and benzene, A1 in the simulation of the pyrolysis of 30%CH₄-Ar when soot sensible energy is considered (labeled as “WSSE”) and neglected (labeled as “W/OSSE”). The CVR is used along with Caltech mechanism [21], Reactive Dimerization and MPBM

2.2.2 Imposed Pressure Reactor

As show in Figure 2.2b, this reactor is a closed system similar to CVR with a main difference that the boundary can move and change the volume of the system due to an external pressure that can stay constant or vary with time. In either case, the pressure is known a priori in this model. The heat transfer can occur through reactor walls, which changes the internal energy of the gas-particle system.

The equations of mass, species, and soot variables in IPR are the same as those in CVR, but the energy equation is written based on enthalpy, h , instead of internal energy, e , as:

$$\frac{dT}{dt} = \frac{1}{\rho c_p + \rho_{soot} f_v c_{soot}} \left[- \sum_k h_k (\dot{\omega}_k + \dot{s}_k) W_k + h_{soot} \sum_k \dot{s}_k W_k + \frac{dP}{dt} + \frac{\dot{Q}}{V(1-\varphi)} \right]. \quad (2.7)$$

where dP/dt represents the effect of variable pressure on the gas temperature, which is zero when the pressure is constant throughout the process.

2.2.3 Perfectly Stirred Reactor (PSR)

In this reactor, gas enters with a mass flow rate, composition, and temperature of $\dot{m}_{in}$, Y_{in} , and T_{in} , respectively, and homogeneously reacts with the mixture inside the reactor. The reacting gas reaches a spatially uniform temperature and composition described by T and Y . It is assumed that temperature, composition and soot properties of the outflow are the same as the mixture inside reactor. Without soot formation, the inlet and outlet mass flow rates are equal (i.e. $\dot{m}_{in} = \dot{m}_{out}$), but when soot is formed, $\dot{m}_{out}$ is slightly less than $\dot{m}_{in}$. The nominal residence time of PSR is calculated as:

$$\tau_{psr} = \frac{\rho V}{\dot{m}_{in}}. \quad (2.8)$$

The conservation of mass of PSR can be written by considering the mass flux of in- and outflow, and the removal of mass due to soot formation as:

$$\frac{dm}{dt} = \dot{m}_{in} - \dot{m}_{out} + V(1-\varphi) \sum_i \dot{s}_i W_i. \quad (2.9)$$

Gas composition is obtained by solving the species transport equations as:

$$\frac{dY_k}{dt} = \frac{\dot{m}_{in}}{\rho V (1-\varphi)} (Y_{k,in} - Y_k) + \frac{1}{\rho} \left[(\dot{\omega}_k + \dot{s}_k) W_k - Y_k \sum_i \dot{s}_i W_i \right]. \quad (2.10)$$

The soot transport equations can also be expressed as:

$$\frac{d\psi}{dt} = \frac{\dot{m}_{in}}{\rho V (1-\varphi)} (\psi_{in} - \psi) + S_\psi - \frac{1}{\rho} \psi \sum_i \dot{s}_i W_i. \quad (2.11)$$

The energy equation for this reactor is written as:

$$\frac{dT}{dt} = \frac{1}{\rho c_p + \rho_{soot} c_{p,soot} f_v} \left[\frac{\dot{m}_{in}}{V(1-\varphi)} (h_{in} - h) - \frac{\dot{m}_{in}}{V(1-\varphi)} \sum_k (Y_{k,in} - Y_k) h_k - \sum_k (\dot{\omega}_k + \dot{s}_k) W_k h_k + \sum_i \dot{s}_i W_i h_{soot} + \frac{\dot{Q}}{V(1-\varphi)} \right]. \quad (2.12)$$

2.2.4 Plug Flow Reactor (PFR)

PFR is an ideal representation of a channel or duct where the temperature, composition, and soot properties of a steady-state one-dimensional flow evolve along the reactor. There is no spatial gradient over cross-section due to strong mixing. The diffusion along reactor is negligible.

The continuity equation for PFR is written as:

$$\frac{d\dot{m}}{dz} = (1-\varphi)A \sum_i \dot{s}_i W_i. \quad (2.13)$$

The momentum equation can also be established as:

$$u(1-f_v) \sum_i \dot{s}_i W_i + \rho u(1-\varphi) \frac{du}{dz} = -\frac{d}{dz}(p(1-\varphi)) - \frac{\tau_w}{R_H}, \quad (2.14)$$

where τ_w , and R_H are the wall shear stress and hydraulic radius of the reactor. τ_w can be determined from the friction factor, f , as:

$$\tau_w = \frac{1}{2} \rho u^2 f, \quad (2.15)$$

where f can be accurately calculated over the entire range of Reynolds numbers, from laminar to turbulent flow, using the explicit formula provided by Haaland [67]:

$$\frac{1}{f^{1/2}} = -1.8 \log \left(\frac{6.9}{Re} + \left[\frac{\epsilon/D_H}{3.7} \right]^{1.11} \right), \quad (2.16)$$

where ϵ and D_H are the wall roughness and the hydraulic radius of the reactor. The species equation can be expressed as:

$$\frac{dY_k}{dz} = \frac{1}{\rho u} \left[(\dot{\omega}_k + \dot{s}_k) W_k - Y_k \sum_i \dot{s}_i W_i \right]. \quad (2.17)$$

The soot transport equations can also be written as:

$$\frac{d\psi}{dz} = \frac{S_\psi}{u} - \frac{\psi}{\rho u} \sum_i \dot{s}_i W_i - \frac{4}{D_H} \frac{k_{dep}^i \psi}{u}, \quad (2.18)$$

where k_{dep}^i is the deposition velocity of soot particles of section i , which is calculated as:

$$k_{dep} = \frac{Sh \cdot D^i}{D_H}, \quad (2.19)$$

where $Sh = 3.66$ for laminar flows, and it calculated using the Berger and Hau correlation [17] for the turbulent flow as:

$$Sh = 0.0165 Re^{0.86} Sc^{1/3}. \quad (2.20)$$

The energy equation can be expressed as:

$$\begin{aligned} \frac{dT}{dz} = \frac{1}{\rho u c_p + \rho_{soot} u f_v c_{p,soot}} & \left[- \sum_k h_k (\dot{\omega}_k + \dot{s}_k) W_k \right. \\ & \left. + h_{soot} \sum_k \dot{s}_k W_k + q'' \frac{P_c}{A} \right], \end{aligned} \quad (2.21)$$

where q'' is the wall heat flux of the reactor.

2.3 Particle Dynamics

Population balance models rely on the Eulerian description of particles where average properties of particle population such as number density, mass or surface area are treated as continuous quantities and tracked by solving scalar transport equations. These methods are computationally cheaper compared with mesoscale models such as DEM, and can be easily interfaced with chemical kinetics in CFD solvers to simulate soot formation in laminar and turbulent configurations. Here, we use two particle dynamics models: a monodisperse population balance model (MPBM), which tracks four variables and results in four transport equations, and a fixed sectional population balance model (SPBM), which tracks three variables per section. In the SPBM approach, the total number of transport equations equals the number of tracked variables multiplied by the number of sections.

Having the total number concentration of agglomerates and primary particles and total carbon content of soot enables the model to describe evolving fractal-like morphology and surface area of soot agglomerates, which is essential to compute their collision frequency [127] as well as oxidation and surface growth rates [86]. Tracking hydrogen content of soot allows capturing the soot composition, thereby its maturity [96], and surface reactivity [22].

The common features of implemented particle dynamics models are reviewed in Section 2.3.1. The composition (H/C), diffusion coefficient, and morphology of soot particles are calculated in the same manner for MPBM and each section in SPBM. However, particle dynamics models differ in terms of the calculation of coagulation, and the processing of the contributions from inception, surface growth, and coagulation to generate the source terms of soot variables, S_φ , incorporated into the transport equations.

2.3.1 Common Features

Soot Morphology

The evolving fractal-like structure of agglomerates is quantified by their mobility diameter normalized by primary particle diameter, d_m/d_p , and gyration diameter, d_m/d_g , that can be described with power-laws derived from mesoscale simulations. Incipient soot is initially a sphere formed of PAHs that grows in size by surface reactions and forms agglomerates by coagulation. The collision frequency of particles depends on their evolving fractal-like structure [127]. Mobility and gyration diameters are calculated using power-laws developed to describe the morphology of soot from premixed [2], diffusion [197] flames, and diesel engines [147]. Figure 2.4 shows the schematic of a soot agglomerate composed of 12 primary particles, with d_p , d_m , and d_g annotated.

n_p^i is the number of primary particles per agglomerate of the i^{th} section that can be obtained by dividing the number concentration of primary particles in the i^{th} section by that of agglomerates in that section as:

$$n_p^i = \frac{N_{pri}^i}{N_{agg}^i}. \quad (2.22)$$

The primary particle diameter, d_p^i , is determined from the total carbon content and the number density of primary particles using:

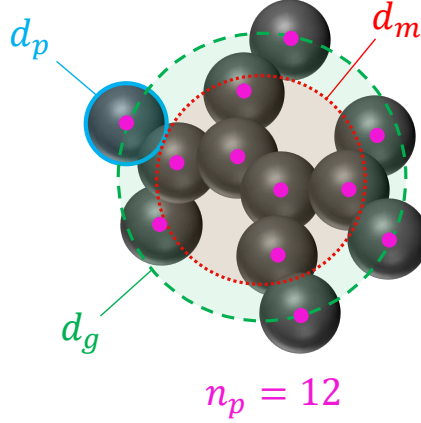


Fig. 2.4 The schematics of a soot agglomerates with 12 primary particles ($n_p = 12$). Primary particle, d_p , mobility d_m , and gyration d_g , diameters are shown.

$$d_p^i = \left(\frac{6}{\pi} \frac{C_{tot}^i \cdot W_{carbon}}{\rho_{soot}} \frac{1}{N_{pri}^i \cdot Av} \right)^{1/3}. \quad (2.23)$$

The DEM-derived power-laws [85] relate d_m^i and d_g^i to d_p^i and n_p^i as:

$$d_m^i = d_p^i \cdot n_p^{i 0.45}, \quad (2.24)$$

$$d_g^i = \begin{cases} d_m^i / (n_p^{i -0.2} + 0.4), & \text{if } n_p^i > 1.5 \\ d_m^i / 1.29 & \text{if } n_p^i \leq 1.5 \end{cases} \quad (2.25)$$

The collision diameter, d_c^i , is the maximum of d_m^i and d_g^i :

$$d_c^i = \max(d_m^i, d_g^i). \quad (2.26)$$

The volume equivalent diameter, d_v^i , is the diameter of the sphere with the same mass as the agglomerate, and it is obtained as:

$$d_v^i = d_p^i \cdot n_p^{i 1/3}. \quad (2.27)$$

The primary particle surface area is calculated from d_p^i assuming spherical primary particles as:

$$A_p^i = \pi d_p^{i 2}. \quad (2.28)$$

A_{tot}^i (for each section) is defined as the total surface area of soot particles per unit mass of gas mixture obtained as:

$$A_{tot}^i = N_{pri}^i \cdot Av \cdot A_p^i. \quad (2.29)$$

Mass of each agglomerate, m_{agg}^i is expressed as:

$$m_{agg}^i = \frac{C_{tot}^i \cdot W_{carbon}}{N_{agg}^i \cdot Av}. \quad (2.30)$$

Soot Composition

The composition of soot characterized by their elemental carbon to hydrogen ratio (C/H) is a measure of soot maturity and increases from $C/H < 2$ for incipient soot [32] to $2 < C/H < 10$ for nascent soot [19] and $C/H > 20$ for mature soot [118]. The soot agglomerates are assumed to have pure carbon graphitic core [96] with all hydrogen atoms on the surface [22]. C/H ratio can be obtained from the total carbon and the hydrogen content as:

$$\left(\frac{C}{H}\right)^i = \frac{C_{tot}^i}{H_{tot}^i}. \quad (2.31)$$

The carbon content of each agglomerate is a predefined parameter in the SPBM (depending on the section the agglomerate is placed), but it can be calculated from dividing C_{tot} by N_{agg} for the MPBM. The hydrogen content of each agglomerate is calculated for both particle dynamics models as:

$$H_{agg}^i = \frac{H_{tot}^i}{N_{agg}^i}. \quad (2.32)$$

Diffusion of soot particles

The diffusion coefficient of soot particle, D^i , is calculated as:

$$D^i = \frac{k_B T}{f^i}, \quad (2.33)$$

where f^i is the friction factor of particles in the gas mixture, and it is calculated as:

$$f^i = \frac{3\pi\mu d_m^i}{C^i(d_m^i)}, \quad (2.34)$$

where C^i is the Cunningham correction factor for the particle friction factor that accounts for non-continuum effects in the transition and free molecular regimes. C^i is calculated for a given diameter, d , as:

$$C^i(d) = 1 + \frac{2\lambda}{d} \left(1.21 + 0.4 \exp\left(\frac{-0.78d}{\lambda}\right) \right), \quad (2.35)$$

where λ is the mean free path of gas given as:

$$\lambda = \frac{\mu}{\rho} \sqrt{\frac{\pi W_{gas}}{2k_B A v T}}. \quad (2.36)$$

Note that λ is a property of the gas mixture that does not depend on particle mass and morphology.

2.3.2 Sectional Population Balance Model

A SPBM with fixed pivots is used to describe particle dynamics [193]. The mass range of particles is divided into discrete sections each of which includes agglomerates of the same mass. Figure 2.5 illustrates the interaction between the gas phase and mass sections, as well as the mechanisms by which particles move between sections. Inception introduces new particles to the first section with the mass corresponding to the incipient particle. The particles of each section can migrate to upper sections by gaining mass via surface growth and coagulation, and return to lower sections when they lose mass through oxidation without breaking into smaller particles (i.e., fragmentation is not considered). Particles attach at point contact without coalescence. The mass of sections is determined by a geometric progression that has an initial value equal to the mass of incipient soot particle, and a common ratio of SF, known as sectional spacing factor. The mass of each section is approximated by the carbon content of agglomerates in moles as:

$$C_{agg}^i = \frac{n_{c,min}}{A_v} \cdot SF^{(i-1)}, \quad (2.37)$$

where $(i - 1)$ represents the exponent of SF. The mass of hydrogen is ignored in the placement of agglomerates in the sections. The total number density of agglomerates, N_{agg}^i , and primary particles, N_{pri}^i , and the hydrogen content, H_{tot} , are tracked for each section. The mass of each section is fixed, so C_{tot} , for each section can be easily calculated by knowing the number of agglomerates; that is, $C_{tot} = N_{agg}^i \cdot A_v \cdot C_{agg}^i$.

Morphological parameters for each section are determined according to the equations provided in Section 2.3.1.

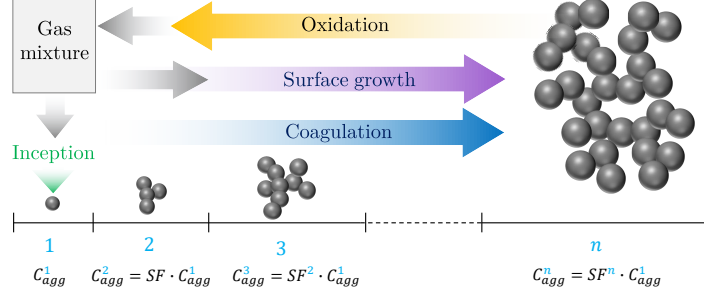


Fig. 2.5 The illustration of sections in SPBM. The mass of sections grows progressively by the scale factor of SF. Inception introduces new particles to the first section that propagate to the upper section via coagulation and surface growth and return to lower sections by oxidation. Carbon and hydrogen pass from gas to solid phase through inception and surface growth and goes back via oxidation.

New particles formed by coagulation are assigned to an upper section, with a total mass equal to the sum of the masses of the colliding particles. If the mass of resulting particle falls between two consecutive sections, the mass is distributed between them proportionally. In some cases, the mass of the newly formed particle may exceed the upper bound of the last section, causing it to fall outside the tracked mass range. This leads to potential mass loss, which is a known limitation of the fixed pivot sectional model [200]. However, this issue can be mitigated by choosing an appropriate number of sections and a suitable spacing factor to ensure the uppermost sections remain unoccupied during the simulation. In the SPBM, the source terms of tracked soot variables (which appear in Equations 2.5, 2.11, and 2.18) are split into four parts showing the contribution of inception, surface growth, oxidation and coagulation. The effect of HACA and PAH adsorption are combined (denoted by the subscript *haca,ads*) because they are similar mass-gaining mechanisms. The source terms for section *i* are given as:

$$S_{N_{agg}}^i = (S_{N_{agg}}^i)_{inc} + (S_{N_{agg}}^i)_{haca,ads} + (S_{N_{agg}}^i)_{ox} + (S_{N_{agg}}^i)_{coag}, \quad (2.38)$$

$$S_{N_{pri}}^i = (S_{N_{pri}}^i)_{inc} + (S_{N_{pri}}^i)_{haca,ads} + (S_{N_{pri}}^i)_{ox} + (S_{N_{pri}}^i)_{coag}, \quad (2.39)$$

$$S_{H_{tot}}^i = (S_{H_{tot}}^i)_{inc} + (S_{H_{tot}}^i)_{haca,ads} + (S_{H_{tot}}^i)_{ox} + (S_{H_{tot}}^i)_{coag}. \quad (2.40)$$

Coagulation Source Term

Coagulation redistributes the total number of agglomerates and primary particles as well as hydrogen atoms among the sections. The partial coagulation source terms for N_{agg}^i , N_{pri}^i and H_{tot}^i can be calculated as:

$$\left(S_{N_{agg}}^i\right)_{coag} = \sum_{k=1}^{n_{sec}} \sum_{j=k}^{n_{sec}} \left(1 - \frac{\delta_{jk}}{2}\right) \eta_{ijk} \zeta^{jk} \beta^{jk} N_{agg}^j N_{agg}^k - N_{agg}^i \sum_{m=1}^{n_{sec}} \zeta^{im} \beta^{im} N_{agg}^m, \quad (2.41)$$

$$\left(S_{N_{pri}}^i\right)_{coag} = \sum_{k=1}^{n_{sec}} \sum_{j=k}^{n_{sec}} \left(1 - \frac{\delta_{jk}}{2}\right) \eta_{p,ijk} \eta_{ijk} \zeta^{jk} \beta^{jk} N_{agg}^j N_{agg}^k - N_{pri}^i \sum_{m=1}^{n_{sec}} \zeta^{im} \beta^{im} N_{agg}^m, \quad (2.42)$$

$$\left(S_{H_{tot}}^i\right)_{coag} = \sum_{k=1}^{n_{sec}} \sum_{j=k}^{n_{sec}} \left(1 - \frac{\delta_{jk}}{2}\right) \eta_{h,ijk} \eta_{ijk} \zeta^{jk} \beta^{jk} N_{agg}^j N_{agg}^k - H_{tot}^i \sum_{m=1}^{n_{sec}} \zeta^{im} \beta^{im} N_{agg}^m. \quad (2.43)$$

where δ_{jk} is the Kronecker delta defined as:

$$\delta_{jk} = \begin{cases} 1, & \text{if } j = k \\ 0, & \text{if } j \neq k \end{cases} \quad (2.44)$$

The collision frequency between sections j and k (β^{jk}) can be obtained from the harmonic mean of the values in the continuum (β_{cont}^{jk}) and free molecular (β_{fm}^{jk}) regimes as:

$$\beta^{jk} = \frac{\beta_{fm}^{jk} \cdot \beta_{cont}^{jk}}{\beta_{fm}^{jk} + \beta_{cont}^{jk}}, \quad (2.45)$$

$$\beta_{fm}^{jk} = \sqrt{\frac{\pi k_B T}{2} \left(\frac{1}{m_{agg}^j} + \frac{1}{m_{agg}^k} \right) (d_c^j + d_c^k)^2}, \quad (2.46)$$

$$\beta_{cont}^{ij} = \frac{2k_B T}{3\mu} \left(\frac{C^j}{d_m^j} + \frac{C^k}{d_m^k} \right) (d_c^j + d_c^k)^2. \quad (2.47)$$

The collision frequency can also be determined from the Fuchs interpolation as:

$$\beta^{jk} = \beta_{cont}^{ij} \left[\frac{d_c^j + d_c^k}{d_c^j + d_c^k + 2 + \delta_r^{jk}} + \frac{8(D^j + D^k)}{\bar{c}_r^{jk} (d_c^j + d_c^k)} \right]^{-1}, \quad (2.48)$$

where δ_r^{jk} and $\bar{c}_r^{jk}$ are the mean square root of mean distance and velocity of particles, respectively, and they are obtained as:

$$\delta_r^{jk} = \sqrt{\delta_a^{j2} + \delta_a^{k2}}, \quad (2.49)$$

$$\bar{c}_r^{jk} = \sqrt{c^j{}^2 + c^k{}^2}. \quad (2.50)$$

The mean velocity, c^i , and mean stop distance of particles, λ_a^i , can be calculated as:

$$c^i = \sqrt{\frac{8k_B T}{\pi m_{agg}^i}}, \quad (2.51)$$

$$\delta_a^i = \frac{1}{d_c^i \lambda_a^i} \left[(d_c^i + \lambda_a^i)^3 - (d_c^{i2} + \lambda_a^{i2})^{3/2} \right] - d_c^i, \quad (2.52)$$

λ_a^i is the agglomerate stopping distance defined as:

$$\lambda_a^i = \frac{8D^i}{\pi c^i}. \quad (2.53)$$

In Equation (2.41), η_{ijk} assigns newly formed agglomerates to the two consecutive sections in order to conserve mass during coagulation [140].

$$\eta_{ijk} = \begin{cases} \frac{C_{agg}^{i+1} - C_{agg}^{jk}}{C_{agg}^{i+1} - C_{agg}^i}, & \text{if } C_{agg}^i \leq C_{agg}^{jk} < C_{agg}^{i+1} \\ \frac{C_{agg}^i - C_{agg}^{jk}}{C_{agg}^i - C_{agg}^{i-1}}, & \text{if } C_{agg}^{i-1} \leq C_{agg}^{jk} < C_{agg}^i \\ 0, & \text{else} \end{cases} \quad (2.54)$$

where $C_{agg}^{jk} = C_{agg}^j + C_{agg}^k$. Similarly, $\eta_{p,ijk}$ in Equation (2.42) and $\eta_{h,ijk}$ in Equation (2.43) adjust the number of primary particles and hydrogen atoms added to consecutive sections based on their mass, respectively.

$$\eta_{p,ijk} = \frac{C_{agg}^i}{C_{agg}^{jk}} (n_p^j + n_p^k), \quad (2.55)$$

$$\eta_{h,ijk} = \frac{C_{agg}^i}{C_{agg}^{jk}} (H_{agg}^j + H_{agg}^k). \quad (2.56)$$

In Equation (2.41), ζ^{jk} is the coagulation efficiency of soot particles in sections j and k . A value of $\zeta^{jk} = 1$ indicates that every collision between two soot particles

successfully results in the formation of a new agglomerate. However, numerical models [130] and experimental evidence [40] have shown that coagulation efficiency drastically decreases for particles smaller than 10 nm in the free-molecular regime ($\text{Kn} \gg 10$), due to their high kinetic energy exceeding the magnitude of attractive forces [183]. The coagulation efficiency between two colliding particles can be described by [130]:

$$\zeta^{ij} = 1 - \left(1 + \frac{\Phi_0^{ij}}{k_B T}\right) \exp\left(-\frac{\Phi_0^{ij}}{k_B T}\right), \quad (2.57)$$

where Φ_0 is the potential well depth, i.e., the minimum interaction energy between two colliding particles. Hou et al. [75] calculated Φ_0 for soot particles ranging from 1 to 15 nm by considering the attractive and repulsive interactions between constituent carbon and hydrogen atoms, and proposed an equation based on the reduced diameter, d_r^{jk} , of colliding particles as:

$$\Phi_0^{ij} = -6.6891 \times 10^{-23} (d_r^{jk})^3 + 1.1244 \times 10^{-21} (d_r^{jk})^2 + 1.1394 \times 10^{-20} d_r^{jk} - 5.5373 \times 10^{-21}, \quad (2.58)$$

$$d_r^{jk} = \frac{d_c^i \cdot d_c^j}{d_c^i + d_c^j}. \quad (2.59)$$

Equation (2.58) is valid for d_r^{jk} between 1 and 7 nm, and ζ^{ij} is assumed as unity for particles with a reduced diameter larger than 7 nm.

Other Source terms

Inception introduces equal number of agglomerates and primary particles to the first section.

$$(S_{N_{agg}}^i)_{inc} = \begin{cases} \frac{1}{Av} \frac{I_{N,inc}}{C_{agg}^i}, & \text{if } i = 1 \\ 0.0, & \text{else} \end{cases} \quad (2.60)$$

$$(S_{N_{pri}}^i)_{inc} = \begin{cases} \frac{1}{Av} \frac{I_{N,inc}}{C_{agg}^i}, & \text{if } i = 1 \\ 0.0, & \text{else} \end{cases} \quad (2.61)$$

$$(S_{H_{tot}}^i)_{inc} = \begin{cases} I_{H,inc}, & \text{if } i = 1 \\ 0.0. & \text{else} \end{cases} \quad (2.62)$$

Surface growth and PAH adsorption increase both the carbon mass and hydrogen content of agglomerates, transferring them to higher sections. The rate at which agglomerates are removed from the original section and added to the target section is calculated to ensure mass conservation. Specifically, it is determined by dividing the mass growth rate by the difference in mass of adjacent sections as:

$$\left(S_{N_{agg}}^i\right)_{haca,ads} = \frac{1}{Av} \begin{cases} -\frac{I_{C_{tot},haca}^i + I_{C_{tot},ads}^i}{C_{agg}^{i+1} - C_{agg}^i}, & \text{if } i = 1 \\ \frac{I_{C_{tot},haca}^{i-1} + I_{C_{tot},haca}^{i-1}}{C_{agg}^i - C_{agg}^{i-1}} - \frac{I_{C_{tot},haca}^i + I_{C_{tot},ads}^i}{C_{agg}^{i+1} - C_{agg}^i}, & \text{if } 1 < i < n_{sec} \\ \frac{I_{C_{tot},haca}^{i-1} + I_{C_{tot},ads}^{i-1}}{C_{agg}^i - C_{agg}^{i-1}}. & \text{if } i = n_{sec} \end{cases} \quad (2.63)$$

As agglomerates move up/down through sections, they carry the number of primary particles as well as hydrogen atoms, so the transfer rate of agglomerates is multiplied by n_p^i and H_{agg}^i , respectively.

$$\left(S_{N_{pri}}^i\right)_{haca,ads} = \frac{1}{Av} \begin{cases} -\frac{I_{C_{tot},haca}^i + I_{C_{tot},ads}^i}{C_{agg}^{i+1} - C_{agg}^i}, & \text{if } i = 1 \\ \frac{I_{C_{tot},haca}^{i-1} + I_{C_{tot},ads}^{i-1}}{C_{agg}^i - C_{agg}^{i-1}} n_p^{i-1} - \frac{I_{C_{tot},haca}^i + I_{C_{tot},ads}^i}{C_{agg}^{i+1} - C_{agg}^i} n_p^i, & \text{if } 1 < i < n_{sec} \\ \frac{I_{C_{tot},haca}^{i-1} + I_{C_{tot},ads}^{i-1}}{C_{agg}^i - C_{agg}^{i-1}} n_p^{i-1}, & \text{if } i = n_{sec} \end{cases} \quad (2.64)$$

$$\left(S_{H_{tot}}^i\right)_{haca,ads} = \frac{1}{Av} \begin{cases} -\frac{I_{C_{tot},haca}^i + I_{C_{tot},ads}^i}{C_{agg}^{i+1} - C_{agg}^i} H_{agg}^i + I_{H_{tot},haca}^i + I_{H_{tot},ads}^i, & \text{if } i = 1 \\ \frac{I_{C_{tot},haca}^{i-1} + I_{C_{tot},ads}^{i-1}}{C_{agg}^i - C_{agg}^{i-1}} H_{agg}^{i-1} - \frac{I_{C_{tot},haca}^i + I_{C_{tot},ads}^i}{C_{agg}^{i+1} - C_{agg}^i} H_{agg}^i + I_{H_{tot},haca}^i + I_{H_{tot},ads}^i, & \text{if } 1 < i < n_{sec} \\ \frac{I_{C_{tot},haca}^{i-1} + I_{C_{tot},ads}^{i-1}}{C_{agg}^i - C_{agg}^{i-1}} H_{agg}^{i-1} + I_{H_{tot},haca}^i + I_{H_{tot},ads}^i. & \text{if } i = n_{sec} \end{cases} \quad (2.65)$$

Similarly, the agglomerates lose carbon mass by oxidation, and descend to the lower sections carrying primary particle and hydrogen.

$$(S_{N_{agg}}^i)_{ox} = \frac{1}{Av} \begin{cases} \frac{I_{C_{tot},ox}^{i+1}}{C_{agg}^{i+1} - C_{agg}^i} - \frac{I_{C_{tot},ox}^i}{C_{agg}^i}, & \text{if } i = 1 \\ \frac{I_{C_{tot},ox}^{i+1}}{C_{agg}^{i+1} - C_{agg}^i} - \frac{I_{C_{tot},ox}^i}{C_{agg}^i - C_{agg}^{i-1}}, & \text{if } 1 < i < n_{sec} \\ -\frac{I_{C_{tot},ox}^i}{C_{agg}^i - C_{agg}^{i-1}}, & \text{if } i = n_{sec} \end{cases} \quad (2.66)$$

$$(S_{N_{pri}}^i)_{ox} = \frac{1}{Av} \begin{cases} \frac{I_{C_{tot},ox}^{i+1}}{C_{agg}^{i+1} - C_{agg}^i} n_p^{i+1} - \frac{I_{C_{tot},ox}^i}{C_{agg}^i}, & \text{if } i = 1 \\ \frac{I_{C_{tot},ox}^{i+1}}{C_{agg}^{i+1} - C_{agg}^i} n_p^{i+1} - \frac{I_{C_{tot},ox}^i}{C_{agg}^i - C_{agg}^{i-1}} n_p^i, & \text{if } 1 < i < n_{sec} \\ -\frac{I_{C_{tot},ox}^i}{C_{agg}^i - C_{agg}^{i-1}} n_p^i, & \text{if } i = n_{sec} \end{cases} \quad (2.67)$$

$$(S_{H_{tot}}^i)_{ox} = \frac{1}{Av} \begin{cases} \frac{I_{C_{tot},ox}^{i+1}}{C_{agg}^{i+1} - C_{agg}^i} H_{agg}^{i+1} - \frac{I_{C_{tot},ox}^i}{C_{agg}^i} H_{agg}^i + I_{H_{tot},ox}^i, & \text{if } i = 1 \\ \frac{I_{C_{tot},ox}^{i+1}}{C_{agg}^{i+1} - C_{agg}^i} H_{agg}^{i+1} - \frac{I_{C_{tot},ox}^i}{C_{agg}^i - C_{agg}^{i-1}} H_{agg}^i + I_{H_{tot},ox}^i, & \text{if } 1 < i < n_{sec} \\ -\frac{I_{C_{tot},ox}^i}{C_{agg}^i - C_{agg}^{i-1}} H_{agg}^i + I_{H_{tot},ox}^i, & \text{if } i = n_{sec} \end{cases} \quad (2.68)$$

2.3.3 Monodisperse Population Balance Model

The MPBM used in this study is based on the monodisperse model presented in [94], and it tracks N_{pri} , N_{agg} , C_{tot} and H_{tot} . The coagulation model follows the same principles as the SPBM, but the calculations are greatly simplified due to the monodispersity assumption. This approach has been shown to achieve accuracy comparable to that of DEM and SPBM when applied with well-justified assumptions [84, 86]. The rate of decay of agglomerates is simply described as:

$$I_{coag} = -\frac{1}{2} \zeta \beta N_{agg}^2, \quad (2.69)$$

where ζ is the collision efficiency of agglomerates calculated using Equation (2.57), and β is the collision frequency of agglomerates for the free-molecular ($Kn > 10$) to continuum regimes ($Kn < 0.1$). The value of β in the transition regime ($0.1 < Kn < 10$) can be

calculated from the harmonic mean of the continuum (β_{cont}) and free-molecular (β_{fm}) regime values. Additionally, an enhancement factor of 1.82 is applied to take into account the effect of polydispersity [83] as:

$$\beta = 1.82 \frac{\beta_{fm} \cdot \beta_{cont}}{\beta_{fm} + \beta_{cont}}, \quad (2.70)$$

$$\beta_{fm} = 4 \sqrt{\frac{\pi k_B T}{m_{agg}}} d_c^2, \quad (2.71)$$

$$\beta_{cont} = 8\pi d_m D, \quad (2.72)$$

where d_c , D , and m_{agg} are calculated using Equations (2.26), (2.33), and (2.30), respectively. Alternatively, β can be obtained using Fuchs interpolation [56] as:

$$\beta = \beta_{cont} \left(\frac{d_c}{d_c + 2\sqrt{2}\delta} + \frac{8D}{\sqrt{2}cd_c} \right)^{-1}, \quad (2.73)$$

where c (mean velocity of particles) and δ (mean stop distance of particles) are calculated using Equations (2.51) and (2.52). The source terms of tracked variables combines the effect of the inception, surface growth, oxidation and coagulation.

$$S_{N_{agg}} = \frac{I_{N,inc}}{n_{c,min}} + I_{coag}, \quad (2.74)$$

$$S_{N_{pri}} = \frac{I_{N,inc}}{n_{c,min}}, \quad (2.75)$$

$$S_{C_{tot}} = I_{C_{tot},inc} + I_{C_{tot},haca} + I_{C_{tot},ads} - I_{C_{tot},ox}, \quad (2.76)$$

$$S_{H_{tot}} = I_{H_{tot},inc} + I_{H_{tot},haca} + I_{H_{tot},ads} - I_{H_{tot},ox}. \quad (2.77)$$

2.4 PAH growth models

Four different PAH growth models are implemented in Omnisoot to describe the conversion of PAHs into incipient particles and their adsorption onto existing agglomerates. In other words, these models explain the calculation of $I_{\varphi,inc}$ and $I_{\varphi,ads}^i$. The implemented models are: Irreversible Dimerization [55], Reactive Dimerization [95], Dimer Coalescence [23], and E-Bridge Modified [54]. All models are based on PAH collision, as supported by ample evidence in the literature [202, 1, 68], but they differ in terms of reversibility, temperature dependence, and the number of steps involved. The

collision frequency of gaseous species including PAH molecules and polymers depends on their mass and diameter, and it is obtained as:

The collision frequency of gaseous species, including PAH molecules and polymers, depends on their mass and diameter and is calculated as:

$$\beta_{dim_{jk}} = 2.2 \cdot d_r^2 \sqrt{\frac{8\pi k_B T}{m_r}}, \quad (2.78)$$

where 2.2 is the vdW enhancement factor [95]. d_r and m_r are reduced diameter and mass for two PAH molecules/dimers, respectively, calculated as:

$$d_r = \frac{d_{PAH_k} \cdot d_{PAH_j}}{d_{PAH_k} + d_{PAH_j}}, \quad (2.79)$$

$$m_r = \frac{m_{PAH_k} \cdot m_{PAH_j}}{m_{PAH_k} + m_{PAH_j}}, \quad (2.80)$$

where m_{PAH_j} and d_{PAH_j} are the mass and equivalent diameter of the j^{th} PAH molecule, respectively, and are obtained as:

$$m_{PAH_j} = \frac{W_{PAH_j}}{Av}, \quad (2.81)$$

$$d_{PAH_j} = \left(\frac{6 \cdot m_{PAH_j}}{\pi \cdot \rho_{PAH_j}} \right)^{1/3}, \quad (2.82)$$

where ρ_{PAH_j} is the equivalent density of PAH estimated using the relation proposed by Johansson et al. [81] as:

$$\rho_{PAH_j} = 171943.5197 \frac{W_{carbon} \cdot n_{C,PAH_j} + W_{hydrogen} \cdot n_{H,PAH_j}}{n_{C,PAH_j} + n_{H,PAH_j}}, \quad (2.83)$$

where n_{C,PAH_j} and n_{H,PAH_j} denote the number of carbon and hydrogen atoms in the j^{th} PAH molecule, respectively. The collision frequency of PAH_j and soot agglomerates in each section can be determined for the entire regime by harmonic mean of the collision frequencies in the free-molecular and continuum regimes as:

$$\beta_{ads_j}^i = \frac{\beta_{fm,ads}^i \cdot \beta_{cont,ads}^i}{\beta_{fm,ads}^i + \beta_{cont,ads}^i}, \quad (2.84)$$


$$\beta_{fm,ads_j}^i = 2.2 \sqrt{\frac{\pi k_B T}{2} \left(\frac{1}{m_{agg}^i} + \frac{1}{m_{PAH_j}} \right) (d_g^i + d_{PAH_j})^2}, \quad (2.85)$$

$$\beta_{cont,ads_j}^i = \frac{2k_B T}{3\mu} \left[\frac{C^i(d_m)}{d_g^i} + \frac{C^i(d_{PAH_j})}{d_{PAH_j}} \right] (d_g + d_{PAH_j}), \quad (2.86)$$

where C^i is the Cunningham correction factor calculated using Equation (2.35).

2.4.1 Irreversible Dimerization

The Irreversible Dimerization is based on the collision of a pair of PAH molecules forming a dimer. The sequential growth continues leading formation of trimers and tetramers until the PAH cluster mass reaches a threshold that can be considered a solid particle. For practical purposes, a dimer is usually considered as an incipient particle that grows by surface growth and coagulation. A single-step collision of two similar PAHs forms a new dimer as:



Similarly, the adsorption of each PAH molecule on soot particles is described by the irreversible collision of soot and PAH_j as:



The forward rate of dimerization, k_{f,dim_j} , and adsorption, k_{f,ads_j} , in Reactions (R.2.1) and (R.2.2) are calculated as:

$$k_{f,dim_j} = \gamma_{inc} \cdot \beta_{jj,PAH} \cdot Av, \quad (2.87)$$

$$k_{f,ads_j}^i = \gamma_{ads_j} \cdot \beta_{j,ads}^i \cdot Av, \quad (2.88)$$

where $\beta_{jk,PAH}$ and $\beta_{j,ads}^i$ are computed using Equations (2.78) and (2.84), respectively, and γ_{inc} and γ_{ads} are the collision efficiencies for dimerization and adsorption, respectively. Their values range from 10^{-7} to 1 and are typically chosen to match the predicted soot properties with experimental data. The dimerization rate of PAH_j is then calculated as:

$$\omega_{dim_j} = \eta_{inc} k_{f,dim_j} [PAH_j][PAH_j]. \quad (2.89)$$

The partial source terms of inception are calculated as:

$$I_{N,inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 2\omega_{dim_j} n_{PAH_j,C}, \quad (2.90)$$

$$I_{C_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 2\omega_{dim_j} n_{PAH_j,C}. \quad (2.91)$$

$$I_{H_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 2\omega_{dim_j} n_{PAH_j,H}. \quad (2.92)$$

The rate of PAH adsorption for each section is obtained as:

$$\omega_{ads_j}^i = \eta_{ads} k_{f,ads_j}^i [\text{soot}^i] [\text{PAH}_j]. \quad (2.93)$$

The contribution of PAH adsorption to the source terms are expressed as:

$$I_{C_{tot},ads}^i = \frac{1}{\rho} \sum_{j=1}^{n_{PAH_j}} \omega_{ads_j}^i n_{PAH_j,C}, \quad (2.94)$$

$$I_{H_{tot},ads}^i = \frac{1}{\rho} \sum_{j=1}^{n_{PAH_j}} \omega_{ads_j}^i (n_{PAH_j,H} - 2). \quad (2.95)$$

Note that PAH adsorption is a mass growth phenomenon that only changes C_{tot} and H_{tot} but does not affect number of N_{agg} and N_{pri} . Each PAH molecule loses one H atom becoming a radical that forms bonds with a dehydrogenated site on soot surface, so two H atoms are released during adsorption that is taken into account in Equation (2.95).

The formation of a dimer consumes two PAH molecules, and during adsorption one PAH molecule is removed from the gas mixture, so the total rate of removal of PAH_j by Irreversible Dimerization is obtained as:

$$\left(\frac{d[\text{PAH}_j]}{dt} \right)_{inc} = -2\omega_{dim_j}, \quad (2.96)$$


$$\left(\frac{d[\text{PAH}_j]}{dt} \right)_{inc} = - \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i. \quad (2.97)$$

Moreover, one H_2 is released to the gas mixture as a result of the adsorption process.

$$\left(\frac{d[\text{H}_2]}{dt} \right)_{ads} = \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i. \quad (2.98)$$

2.4.2 Reactive Dimerization

This model was built on Irreversible Dimerization with a main difference: The first step of dimerization and adsorption is reversible forming physically bonded dimers followed by a irreversible carbonization that leads to chemical bond formation in dimers [95]. This approach allows the formation of homo- and hetero-dimers. The dimerization of PAH_j and PAH_k is described as:



where Dimer_{jk}^* and Dimer_{jk} are physically and chemically bonded dimers, respectively, from PAH_j and PAH_k . The forward rate of physical dimerization, $k_{f,dim_{jk}}$, is calculated as:

$$k_{f,dim_{jk}} = p'' \cdot \beta_{jk,PAH} \cdot Av, \quad (2.99)$$

where $\beta_{jk,PAH}$ is calculated using Equation (2.78), and $p'' = 0.1$ accounts for the probability of PAH-PAH collisions occurring in the "FACE" configuration that result in successful van der Waals (vdW) bond formation [124]. The reverse rate of physical dimerization, $k_{r,dim_{jk}}$, is obtained from the dimerization equilibrium constant [123] as:

$$k_{r,dim_{jk}} = \frac{k_{f,dim_{jk}}}{K_{eq}}, \quad (2.100)$$

$$\log_{10} K_{eq} = a \frac{\epsilon_{jk}}{RT} + b, \quad (2.101)$$

$$\epsilon_{jk} = cW_{jk} - d, \quad (2.102)$$

$$W_{jk} = \frac{W_j \cdot W_k}{W_j + W_k}, \quad (2.103)$$

where $a = 0.115$ (obtained from pyrere dimerization data [151]) and $b = 1.8$ [95], $c = 933420 \text{ J/kg}$, and $d = 34053 \text{ J/mol}$ [95].

The rate constant of chemical bond formation, k_{reac} , is defined in the Arrhenius form [131] as

$$k_{reac} = 5 \times 10^6 \cdot e^{(-96232/RT)}. \quad (2.104)$$

Assuming a steady state condition for physical dimers, i.e., $\partial[\text{Dimer}_{jk}^*]/\partial t = 0$, the rate of formation of chemically-bonded dimers can be obtained as:

$$\omega_{dim_{jk}} = k_{reac} \frac{k_{f,dim_{jk}} [\text{PAH}_j] [\text{PAH}_k]}{k_{r,dim_{jk}} + k_{reac}}. \quad (2.105)$$

The contribution of dimer formation to the partial source terms is evaluated by looping over all combinations of PAH precursors as:

$$I_{N,inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} \sum_{k=j}^{n_{PAH}} \omega_{dim_{kj}} (n_{PAH_j,C} + n_{PAH_k,C}), \quad (2.106)$$

$$I_{C_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} \sum_{k=j}^{n_{PAH}} \omega_{dim_{kj}} (n_{PAH_j,C} + n_{PAH_k,C}), \quad (2.107)$$

$$I_{H_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} \sum_{k=j}^{n_{PAH}} \omega_{dim_{kj}} (n_{PAH_j,H} + n_{PAH_k,H}). \quad (2.108)$$

Similarly, PAH adsorption is described by a two-step process where the collision of PAH_j with soot agglomerates leads to a physically bonded Soot-PAH_j^* that is carbonized and forms a chemically bonded Soot-PAH_j on soot surface.



The forward and reverse rate of PAH-soot collision are calculated as:

$$k_{f,ads_j}^i = \beta_{j,ads}^i \cdot Av, \quad (2.109)$$

$$k_{r,ads_j}^i = k_{f,ads_j}^i \cdot 10^{-b} e^{-a\epsilon_{soot,j}^i \ln(10)/(RT)}, \quad (2.110)$$

$$\epsilon_{soot,j}^i = cW_{soot,j}^i - d, \quad (2.111)$$

where $\beta_{j,ads}^i$ is calculated using Equation (2.84). The values of a , b , c , and d are the same as those explained in the inception part. Computing $\epsilon_{soot,j}^i$ also requires the equivalent soot molecular weight, W_{soot}^i , which is estimated from carbon mass of each agglomerate as:

$$W_{soot}^i = \frac{C_{tot}^i W_{carbon}}{N_{agg}^i}. \quad (2.112)$$

The rate constant of carbonization of Soot-PAH_j^{*} is defined as in an Arrhenius form similar to the inception formulation (Equation (2.104)). The pre-exponential factor is adjusted by matching the numerical PSD [131] with measurements in the ethylene pyrolysis in a flow reactor [9].

$$k_{c,ads} = 2 \times 10^{10} \cdot e^{(-96232/RT)}. \quad (2.113)$$

The total adsorption rate can be calculated assuming a steady-state concentration for the physically adsorbed PAH on soot, i.e., $\partial[\text{Soot-PAH}_j^*]/\partial t = 0$, calculated in a similar way to the inception flux (Equation (2.105)) as:

$$\omega_{ads_j}^i = k_{c,ads} \frac{k_{f,ads_j} [\text{soot}^i] [\text{PAH}_j]}{k_{r,ads_j} + k_{c,ads_j}}, \quad (2.114)$$

The contribution of PAH adsorption rate to the partial source terms can be expressed as:

$$I_{C_{tot},ads}^i = \frac{1}{\rho} \sum_{i=1}^{n_{PAH}} \omega_{ads_j}^i n_{C,PAH_j}, \quad (2.115)$$

$$I_{H_{tot},ads}^i = \frac{1}{\rho} \sum_{i=1}^{n_{PAH}} \omega_{ads_j}^i (n_{H,PAH_j} - 2). \quad (2.116)$$

The rate of removal of PAH from the gas mixture due to inception and PAH adsorption is given as:

$$\left(\frac{d[\text{PAH}_j]}{dt} \right)_{inc} = - \sum_{k=1}^{n_{PAH}} \omega_{dim_{jk}}, \quad (2.117)$$


$$\left(\frac{d[\text{PAH}_j]}{dt} \right)_{ads} = - \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i. \quad (2.118)$$

Additionally, during the PAH adsorption process one H₂ is released to the gas mixture changing the concentration of H₂ as:

$$\left(\frac{d[\text{H}_2]}{dt} \right)_{ads} = \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i. \quad (2.119)$$

2.4.3 Dimer Coalescence

The Dimer Coalescence model is a multi-step irreversible model proposed by Blanquart and Pitsch [23] where self-collision of PAH molecules forms dimers, which are an intermediate state between gaseous PAH molecules and solid soot particles. The dimers can either form incipient soot particles through self-coalescence or adsorb on the surface of existing soot particles and contribute to their surface growth. The following equations describing the inception and surface growth in Dimer Coalescence adopted from the work of Sun et al. [168].



The rate constant of dimerization, k_{dim_j} , and inception, k_{inc_j} , are calculated from the collision rate of PAHs as:

$$k_{dim_j} = \gamma_{dim_j} \cdot \beta_{jj,PAH} \cdot Av, \quad (2.120)$$

$$k_{inc_j} = \beta_{jj,dimer} \cdot Av, \quad (2.121)$$

where $\beta_{jj,PAH}$, $\beta_{jj,dimer}$ are both calculated using Equation (2.78). γ_{dim_j} is the dimerization efficiency assumed to scale with the fourth power of the PAH molecular weight [22] as:

$$\gamma_{dim_j} = C_{N,j} \cdot W_{PAH_j}^4. \quad (2.122)$$

Blanquart and Pitsch [23] estimated the constant $C_{N,j}$ in Equation (2.122) by comparing the profiles of several PAH species with the experimental measurements in a single premixed benzene flame [171], and provide $C_{N,j}$ values for various PAHs, which are listed in Table 1 in [22]. The rate of dimer collision is expressed as:

$$\omega_{dim_j} = \eta_{inc} k_{inc_j} [\text{Dimer}_j] [\text{Dimer}_j]. \quad (2.123)$$

Similarly, the rate of adsorption of dimers on soot particles is obtained as:

$$\omega_{ads_j}^i = \eta_{ads} k_{ads_j}^i [\text{soot}^i] [\text{Dimer}_j], \quad (2.124)$$

$$k_{ads_j}^i = \beta_{ads_j}^i \cdot Av. \quad (2.125)$$

Assuming fast dimer consumption leads to the steady-state concentration of dimers, which can be determined by solving a quadratic equation [22] as:

$$a_{inc_j}[\text{Dimer}_j]^2 + b_{ads_j}[\text{Dimer}_j] = \omega_{dim,j}, \quad (2.126)$$

$$[\text{Dimer}_j] = \begin{cases} \frac{-b_{ads_j} + \sqrt{\Delta_j}}{2a_{inc_j}}, & \text{if } \Delta_j \geq 0, \\ 0 & \text{if } \Delta_j < 0 \end{cases}, \quad (2.127)$$

$$\Delta_j = b_{ads_j}^2 + 4a_{inc_j}\omega_{dim,j}, \quad (2.128)$$

where $a_{inc_j} = k_{inc_j}$ and b_{ads_j} is calculated by summing the adsorption rate of dimers for all sections as:

$$b_{ads_j} = \sum_{i=1}^{n_{sec}} k_{ads_j}^i [\text{soot}^i] \quad (2.129)$$

After determining the concentration of each dimer, the contributions of inception and PAH adsorption to the source terms of the tracked soot variables can be calculated in a manner similar to previous inception models, by accounting for the number of carbon and hydrogen atoms involved in the process as:

$$I_{N,inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 4\omega_{inc_j} n_{PAH_j,C}, \quad (2.130)$$

$$I_{C_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 4\omega_{inc_j} n_{PAH_j,C}, \quad (2.131)$$

$$I_{H_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 4\omega_{inc_j} n_{PAH_j,H}, \quad (2.132)$$

$$I_{C_{tot},ads}^i = \frac{1}{\rho} \sum_{i=1}^{n_{PAH}} 2\omega_{ads_j}^i n_{C,PAH_j}, \quad (2.133)$$

$$I_{H_{tot},ads}^i = \frac{1}{\rho} \sum_{i=1}^{n_{PAH}} 2\omega_{ads_j}^i (n_{H,PAH_j} - 1). \quad (2.134)$$

The rate of removal of PAHs and release of H₂ molecule due to PAH adsorption is calculated as:



$$\left(\frac{d[\text{PAH}_j]}{dt}\right)_{inc} = -4 \sum_{k=1}^{n_{PAH}} \omega_{inc_j}, \quad (2.135)$$

$$\left(\frac{d[\text{PAH}_j]}{dt}\right)_{ads} = -2 \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i, \quad (2.136)$$

$$\left(\frac{d[\text{H}_2]}{dt}\right)_{ads} = \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i. \quad (2.137)$$

2.4.4 E-Bridge Modified

The E-Bridge model was originally proposed by Frenklach and Mebel [54] to describe soot inception using a HACA-like scheme that starts with the dehydrogenation of PAH monomers, often pyrene, which forms the monomer radicals and continues with the sequential addition of the radicals that form dimers, trimers and larger polymers until the PAH structure reaches a mass threshold and the clustering process becomes irreversible [54]. Here, a modified version of this model, called E-Bridge Modified, is used where dimers are considered as incipient soot, and monomer radicals are adsorbed on soot agglomerates. This PAH growth model is described using the following set of pathways:



The rate constants of Reactions (R 2.10) and (R 2.11) are listed in Table 2.2. k_{inc_j} and k_{ads_j} are the rate constants of dimer production and PAH adsorption, respectively, which are calculated as:

$$k_{inc_j} = \beta_{jj,PAH} \cdot Av, \quad (2.138)$$

$$k_{ads_j}^i = \beta_{ads_j}^i \cdot Av, \quad (2.139)$$

Table 2.2 Rate coefficients for the monomer de-/hydrogenation reaction of E-bridge formation in Arrhenius form $k = AT^n \cdot e^{-E/RT}$ [54].

Reaction		A [m ³ /mol · s]	n	E/R [K]
(R 2.10)	f	$98 \times n_{C,PAH_j}$	1.8	7563.519
	r	1.6×10^{-2}	2.63	2145.346
(R 2.11)	f	4.8658×10^7	0.13	0.0

where $\beta_{jj,PAH}$ and $\beta_{ads_j}^i$ are obtained using Equations (2.78) and (2.84), respectively. The rate of dimer formation and adsorption is calculated as:

$$\omega_{dim_j} = k_{inc_j} [\cdot PAH_j]^2, \quad (2.140)$$

$$\omega_{ads_j}^i = k_{ads_j}^i [soot^i] [P\dot{A}H_j]. \quad (2.141)$$

The calculation of rate of inception and PAH adsorption from PAH_j requires the concentration of $P\dot{A}H_j$, which can be determined by applying the steady-state assumption for $P\dot{A}H_j$, i.e., $d[P\dot{A}H_j]/dt = 0$, resulting in a quadratic equation as:

$$a_{inc_j} [P\dot{A}H_j]^2 + b_{ads_j} [P\dot{A}H_j] + c_j = 0, \quad (2.142)$$

$$a_{inc_j} = k_{inc_j} \quad (2.143)$$

$$b_{ads_j} = k_{r,d_j} [H_2] + k_{f,h_j} [H] + \sum_{i=1}^{n_{sec}} k_{ads_j}^i [Soot]^i \quad (2.144)$$

$$c_{inc_j} = k_{f,d_j} [PAH_j] [H] \quad (2.145)$$

Solving the quadratic equation for each PAH gives the concentration of $P\dot{A}H_j$ as:

$$[P\dot{A}H_j] = \begin{cases} \frac{-b_{ads_j} + \sqrt{\Delta_j}}{2a_{inc_j}}, & \text{if } \Delta_j \geq 0 \\ 0 & \text{if } \Delta_j < 0 \end{cases} \quad (2.146)$$

$$\Delta_j = b_{ads_j}^2 - 4a_{inc_j} c_j \quad (2.147)$$

The partial source terms of inception, $I_{\varphi,inc}$, are calculated in the E-Bridge Modified model as:

$$I_{N,inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 2\omega_{inc_j} n_{PAH_j,C}, \quad (2.148)$$

$$I_{C_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} 2\omega_{inc_j} n_{PAH_j,C}, \quad (2.149)$$

$$I_{H_{tot},inc} = \frac{1}{\rho} \sum_{j=1}^{n_{PAH}} \omega_{inc_j} (n_{PAH_j,H} - 2), \quad (2.150)$$

The partial source terms of PAH adsorption, $I_{\varphi,ads}^i$, are calculated for each section in this PAH growth model as:

$$I_{C_{tot},ads}^i = \frac{1}{\rho} \sum_{i=1}^{n_{PAH}} \omega_{ads_j}^i n_{C,PAH_j}, \quad (2.151)$$

$$I_{H_{tot},ads}^i = \frac{1}{\rho} \sum_{i=1}^{n_{PAH}} \omega_{ads_j}^i (n_{H,PAH_j} - 2). \quad (2.152)$$

The rate of removal of each PAH involved in soot inception and PAH adsorption, and release of H₂ to the gas mixture can be expressed as:

$$\left(\frac{d[PAH_j]}{dt} \right)_{inc} = -2 \sum_{k=1}^{n_{sec}} \omega_{inc_j}, \quad (2.153)$$

$$\left(\frac{d[PAH_j]}{dt} \right)_{ads} = - \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i, \quad (2.154)$$

$$\left(\frac{d[H_2]}{dt} \right)_{inc} = \sum_{i=1}^{n_{sec}} \omega_{ads_j}^i. \quad (2.155)$$

2.4.5 Summary of features

The comparison of key features of the implemented PAH growth models is provided in Table 2.3. As shown in Fig. 2.6 the inception flux predicted by the Reactive Dimerization and E-Bridge Modified models increases exponentially with temperature (that is, decreases with its inverse), whereas the Irreversible Dimerization and Dimer Coalescence models show only about a factor-of-two increase over the range 500-2500 K.

Table 2.3 The summary of key features of PAH growth models.

Name	Reversibility	Temperature dependence	The sequence of steps in inception mechanism
Irrev.Dim. [55]	Irreversible	Weak, $\propto \sqrt{T}$	$[\text{PAH}] \xrightarrow{\text{collision}} [\text{Dim.}]$
Reac.Dim. [95]	Reversible	Strong, $\propto e^{-E/(RT)}$	$[\text{PAH}] \xrightleftharpoons{\text{collision}} [\text{Phy.Dim.}] \xrightarrow{\text{carbonization}} [\text{Chem.Dim.}]$
Dim.Coal. [22]	Irreversible	Weak, $\propto \sqrt{T}$	$[\text{PAH}] \xrightarrow{\text{collision}} [\text{Dim.}] \xrightarrow{\text{collision}} [\text{Tetra.}]$
EBri.Mod. [54]	Reversible	Strong, $\propto e^{-E/(RT)}$	$[\text{PAH}] \xrightleftharpoons{\text{dehydrogenation}} [\text{Rad.}]$ $\xrightarrow{\text{collision}} [\text{Chem.Dim.}]$

Dim. denotes PAH dimers. Phy.Dim. and Chem.Dim. represent physically- and chemically-bonded dimers, respectively. Rad. and Tetra. refer to a PAH radical and a tetramer, respectively.

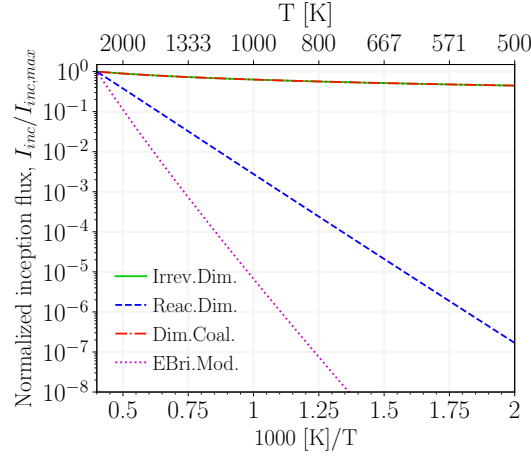


Fig. 2.6 The temperature dependence of inception flux, I_{inc} , predicted using various PAH growth models. I_{inc} of each model is normalized with its maximum to facilitate the comparison.

2.5 Surface reactions model

Heterogeneous surface reactions are described by HACA. The soot growth in HACA scheme is based on a sequential process similar to PAH growth. The hydrogenated armchair sites ($C_{\text{soot}} - H$) on the edge of aromatic rings are dehydrogenated by H abstraction forming C_{soot}° that bonds with C_2H_2 resulting in an additional aromatic ring with hydrogenated sites. These sites can also be attacked by O_2 or OH leading to removal of carbon from soot particles by oxidation. The elementary reactions that

describe this sequential process are listed in Table 2.4. The rate of mass growth by HACA is obtained from the reaction of C_2H_2 with dehydrogenated sites as:

$$\omega_{gr}^i = \alpha^i k_{f4} [C_2H_2] [C_{soot^\circ}^i], \quad (2.156)$$

where k_{f4} denotes the forward rate of Reaction (R.2.17) in Table 2.4, and $[C_{soot^\circ}^i]$ is obtained by multiplying the surface density of dehydrogenated sites, $C_{soot^\circ}^i$ by the total surface area of soot (per unit of mass of gas mixture) of each section as:

$$[C_{soot^\circ}^i] = \frac{\rho}{A_v} A_{tot}^i \cdot \chi_{soot^\circ}, \quad (2.157)$$

where χ_{soot° is the surface density of dehydrogenated sites, and is calculated by assuming the steady-state for $[C_{soot^\circ}]$ in the system of reactions in Table 2.4 as:

$$\chi_{soot^\circ} = \frac{k_{f1}[H] + k_{f2}[OH]}{k_{r1}[H_2] + k_{r2}[H_2O] + k_{f3}[H] + k_{f4}[C_2H_2] + k_{f5}[O_2]} \chi_{soot-H}, \quad (2.158)$$

where χ_{soot-H} is the surface density of hydrogenated sites estimated based on the assumption that soot "surface is assumed to be composed of outwardlooking PAH edges with PAH molecular moieties assembled into turbostratic structures" [51]. Considering the layer spacing of $3.15\text{\AA}$ and two C-H bonds per benzene ring length, χ_{soot-H} is calculated to be $0.23\text{site}/\text{\AA}^2 = 2.3 \times 10^{19} \text{ site}/\text{m}^2$, which gives the maximum theoretical limit of the reaction sites.

In Equation (2.156), α^i is the surface reactivity factor between 0 and 1 that represents the decline of reaction sites from the theoretical limit due to PAH layer orientation, particle aging, growth and maturity [70, 69], and it has been observed to depend on temperature-time history [74, 35]. The value of α has been described using constant target-specific values as well as empirical equations based on particle size and flame temperature. A detailed review of these can be found in Chapter 4 of [177]. Here, the empirical equation proposed by Appel et al. [8] is used to calculate α^i as:

$$\alpha^i = \tanh \left(\frac{12.56 - 0.00563T}{\log_{10} \left(\frac{\rho_{soot} \cdot A_v}{W_{carbon}} \frac{\pi}{6} d_p^3 \right)} - 1.38 + 0.00068T \right). \quad (2.159)$$

Alternatively, α^i can be related to the H/C ratio of soot particles by assuming that all hydrogen atoms reside on the particle surface [23] as:

$$\alpha^i = \frac{H_{tot}^i}{C_{tot}^i}. \quad (2.160)$$

Table 2.4 Arrhenius rate coefficients of the surface reactions in HACA [8], $k = AT^n \cdot e^{-E/RT}$.

No.	Reaction		A [m ³ /mol · s]	n	E/R [K]
(R 2.14)	$C_{\text{soot-H}} + H \xrightleftharpoons[k_{r,1}]{k_{f,1}} C_{\text{soot}^\circ} + H_2$	f	4.17×10^7	0	6542.52
		r	3.9×10^6	0	5535.98
(R 2.15)	$C_{\text{soot-H}} + OH \xrightleftharpoons[k_{r,2}]{k_{f,2}} C_{\text{soot}^\circ} + H_2O$	f	10^4	0.734	719.68
		r	3.68×10^2	1.139	8605.94
(R 2.16)	$C_{\text{soot}^\circ} + H \xrightarrow{k_{f,3}} C_{\text{soot-H}}$	f	10^4	0.734	719.68
(R 2.17)	$C_{\text{soot}^\circ} + C_2H_2 \xrightarrow{k_{f,4}} C_{\text{soot-H}} + H$	f	80	1.56	1912.43
(R 2.18)	$C_{\text{soot}^\circ} + O_2 \xrightarrow{k_{f,5}} 2 CO + \text{product}$	f	2.2×10^6	0	3774.53
(R 2.19)	$C_{\text{soot-H}} + OH \xrightarrow{k_{f,6}} CO + \text{product}$	f	$\gamma_{OH} = 0.13$		

The contribution of HACA to growth source terms can be computed from HACA rates considering the number of carbon atoms in C_2H_2 and number of arm-chair and zig-zag hydrogenated sites on soot particle [22] using

$$I_{C_{tot},haca}^i = 2\omega_{gr}^i/\rho, \quad (2.161)$$

$$I_{H_{tot},haca}^i = 0.25\omega_{gr}^i/\rho. \quad (2.162)$$

The rates of concentration change of C_2H_2 and H radical due to HACA are written as:

$$\left(\frac{d[C_2H_2]}{dt}\right)_{gr} = -\sum_{i=1}^{n_{sec}} \omega_{gr}^i, \quad (2.163)$$

$$\left(\frac{d[H]}{dt}\right)_{gr} = 1.75 \sum_{i=1}^{n_{sec}} \omega_{gr}^i. \quad (2.164)$$

The carbons on the surface of soot are oxidized via reaction with O_2 (Reaction (R 2.18)) and OH (Reaction (R 2.19)). As a result, oxidation decreases the total carbon of soot and releases CO and H_2 to the gas mixture. The O_2 and OH oxidation rates are calculated as:

$$\omega_{ox,O_2}^i = \alpha^i k_{f5}[O_2][C_{soot^\circ}^i], \quad (2.165)$$

$$\omega_{ox,OH}^i = \gamma_{OH} \beta_{OH}^i Av[OH][soot^i], \quad (2.166)$$

where $\gamma_{OH} = 0.13$ is the reaction probability of OH radicals with soot particles [8]. β_{OH} is the collision frequency of OH and soot particles calculated based on the kinetic theory of gases as:

$$\beta_{OH}^i = \sqrt{\frac{\pi k_B T}{2} \left(\frac{1}{m_{agg}^i} + \frac{1}{m_{OH}} \right) (d_c^i + d_{OH})^2}, \quad (2.167)$$

where $m_{OH} = 2.824 \times 10^{-26}$ kg, and $d_{OH} = 0.3$ nm [160] are the mass and equivalent diameter of a OH radical, respectively. Then, the oxidation source term is calculated considering the number of carbon atoms removed from soot through each oxidation pathway as:

$$I_{C_{tot},ox}^i = (2\omega_{ox,O_2}^i + \omega_{ox,OH}^i)/\rho. \quad (2.168)$$

The rate of change of concentration of CO, O₂ and OH by oxidation is calculates as:

$$\left(\frac{d[CO]}{dt} \right)_{ox} = 2 \sum_{i=1}^{n_{sec}} \omega_{ox,O_2}^i, \quad (2.169)$$

$$\left(\frac{d[O_2]}{dt} \right)_{ox} = - \sum_{i=1}^{n_{sec}} \omega_{ox,O_2}^i, \quad (2.170)$$

$$\left(\frac{d[OH]}{dt} \right)_{ox} = - \sum_{i=1}^{n_{sec}} \omega_{ox,OH}^i, \quad (2.171)$$

$$\left(\frac{d[H]}{dt} \right)_{ox} = \sum_{i=1}^{n_{sec}} \omega_{ox,OH}^i. \quad (2.172)$$

2.6 Gas scrubbing rates

The rate of production/destruction of species involved in soot formation must be taken into account to preserve the mass and energy balance in reactive systems. In order to do that, the production rate of gaseous species calculated by Cantera must be corrected for the rate of release/consumption due to PAH growth and surface reaction models.

$$\left(\frac{d[\text{PAH}_j]}{dt}\right)_{tot} = \left(\frac{d[\text{PAH}_j]}{dt}\right)_{gas} + \left(\frac{d[\text{PAH}_j]}{dt}\right)_{inc} + \left(\frac{d[\text{PAH}_j]}{dt}\right)_{ads}. \quad (2.173)$$

H_2 is released to the gas mixture due to inception, PAH adsorption as well as oxidation.

$$\left(\frac{d[\text{H}_2]}{dt}\right)_{tot} = \left(\frac{d[\text{H}_2]}{dt}\right)_{gas} + \left(\frac{d[\text{H}_2]}{dt}\right)_{inc} + \left(\frac{d[\text{H}_2]}{dt}\right)_{ads} + \left(\frac{d[\text{H}_2]}{dt}\right)_{ox}. \quad (2.174)$$

Surface growth consumes C_2H_2 and adds H_2 to the gas mixture.

$$\left(\frac{d[\text{C}_2\text{H}_2]}{dt}\right)_{tot} = \left(\frac{d[\text{C}_2\text{H}_2]}{dt}\right)_{gas} + \left(\frac{d[\text{C}_2\text{H}_2]}{dt}\right)_{gr}. \quad (2.175)$$

$$\left(\frac{d[\text{H}]}{dt}\right)_{tot} = \left(\frac{d[\text{H}]}{dt}\right)_{gas} + \left(\frac{d[\text{H}]}{dt}\right)_{gr}. \quad (2.176)$$

Oxidation uses O_2 and OH to remove carbon from soot particles and generates H_2 and CO .

$$\left(\frac{d[\text{CO}]}{dt}\right)_{tot} = \left(\frac{d[\text{CO}]}{dt}\right)_{gas} + \left(\frac{d[\text{CO}]}{dt}\right)_{ox}. \quad (2.177)$$

$$\left(\frac{d[\text{O}_2]}{dt}\right)_{tot} = \left(\frac{d[\text{O}_2]}{dt}\right)_{gas} + \left(\frac{d[\text{O}_2]}{dt}\right)_{ox}. \quad (2.178)$$

$$\left(\frac{d[\text{OH}]}{dt}\right)_{tot} = \left(\frac{d[\text{OH}]}{dt}\right)_{gas} + \left(\frac{d[\text{OH}]}{dt}\right)_{ox}. \quad (2.179)$$

Chapter 3

Code Validation

A set of simulations was performed to evaluate the accuracy and reliability of Omnisoot in predicting soot formation. The aerosol dynamics models were validated by comparing the results of the population balance models implemented in Omnisoot with DEM simulations reported in the literature. In addition, carbon and hydrogen mass and energy balances were rigorously assessed to ensure that residuals remain within the bounds of acceptable numerical error.

3.1 Validation of Collision Frequency

The collision frequency function determines the rate at which two particles collide, which results in the reduction of the total number of agglomerates and the increase in particle size. In the absence of strong flow shear or external forces, Brownian motion is the main driving force for particle coagulation. As explained in Sections 2.3.2 and 2.3.3, Omnisoot employs harmonic mean and Fuchs interpolations to calculate collision frequency of agglomerates from free-molecular ($\text{Kn} \geq 10$) to continuum ($\text{Kn} \leq 0.1$) regimes based on the gas mean free path and the particle size.

The test case for validation of collision frequency is based on the DEM simulation of 2000 monodisperse spherical particles with the density of 2200 kg/m^3 in a cubic cell with the constant temperature of 298 K and pressure of 1 atm [63]. Figure 3.1 depicts the collision frequency plotted against Knudsen number ($\text{Kn} = 2\lambda/d_m$) obtained by Omnisoot using harmonic mean (red solid line) and Fuchs interpolation (blue dashed line) and the DEM results of Goudeli et al. [63]. The Fuchs interpretation perfectly matches DEM data over the free-molecular regime to the continuum regime. Harmonic mean is also in good agreement with the DEM results in the free-molecular and

continuum regimes, but slightly underpredicts the collision frequency in the transition regime with relative errors less than 16%.

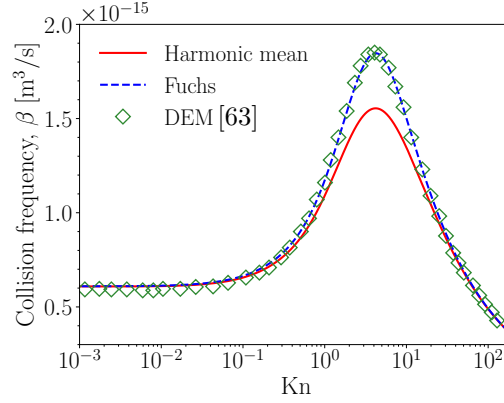


Fig. 3.1 The comparison of collision frequency, β , obtained by Omnisoot using harmonic mean (red solid line) and Fuchs interpolations (blue dashed line) with DEM results (symbols) [63].

3.2 Coagulation

Two test cases were set up to validate the coagulation sub-model of MPBM and SPBM in the free-molecular¹ and continuum² regimes. An adiabatic CVR with a volume of 1 m³ was populated with 2.6261×10^{18} spherical particles with the initial diameters of 2 nm and 668 nm for the free-molecular and continuum cases, respectively. The initial temperature in the free-molecular and continuum simulations are 1800 K and 300 K, respectively.

Figure 3.2 illustrate the schematics of the designed test in which the particles collide and grow in size through coagulation in both simulations, without inception, surface growth, or oxidation. Figure 3.3 demonstrates the evolution of N_{agg} , N_{pri} , d_m , and d_g as predicted by MPBM and SPBM in the free-molecular regime, which are in good agreement with DEM results [94]. N_{pri} is conserved during coagulation, resulting in identical flat trends for both models. In contrast, N_{agg} decreases over time, with a faster decay observed in SPBM due to its treatment of agglomerate polydispersity, which leads to a higher collision frequency compared to MPBM. Therefore, d_m and d_g predicted by SPBM, shown in Figure 3.3b, are slightly larger than those predicted by MPBM.

¹https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/validations/coagulation/free_molecular

²<https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/validations/coagulation/continuum>

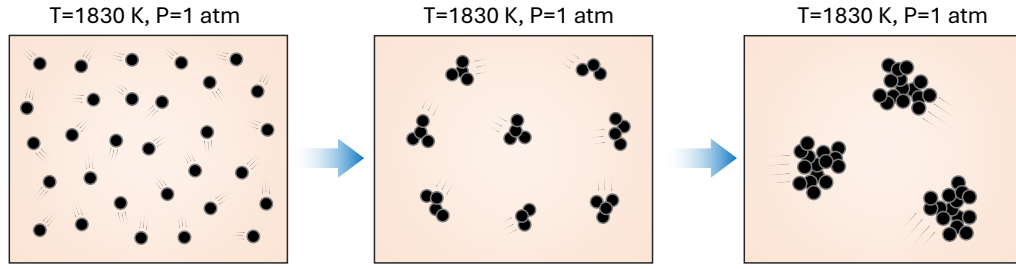


Fig. 3.2 The schematic of the agglomeration process in the coagulation test case where initially spherical particles collide and form agglomerates

The MPBM model cannot resolve the PSD due to the monodispersity assumption. In contrast, the SPBM tracks the number concentration of particles in discrete sections, which allows the construction of an evolving PSD, and the assessment of the size distribution spread. Figure 3.4 shows the evolution of the non-dimensional PSD from $t = 1$ ms to 500 ms for the free-molecular and continuum simulations. The PSD is plotted as a function of the normalized concentration, $\Psi = \bar{v}n_{agg}(v, t)/N_{agg, \infty}$ and dimensionless volume, $\eta = v/\bar{v}$, where $n_{agg}(v, t)$ is the size distribution function of agglomerate, v is the particle volume, $\bar{v}$ is the mean particle volume, $N_{agg, \infty}$ is the total number concentration of agglomerates. After the initial transient ($t > 22$ ms), the PSD rapidly evolves into a full bell curve and remains unchanged, indicating the attainment of a SPSP. This behavior is in good agreement with DEM results and confirms the capability of the SPBM implemented in Omnisoot to capture the SPSP for soot agglomerates in the free-molecular and continuum regimes, a characteristic outcome of Brownian-driven particle coagulation.

Figure 3.4a shows the standard deviation of the mobility diameter, σ_g , predicted by SPBM in the free-molecular regime, which is in close agreement with DEM results. Initially, $\sigma_g = 1$, indicating a monodisperse population, and it gradually increases, reaching a final value of 2.03, which corresponds to the characteristic standard deviation for the free-molecular regime [176].

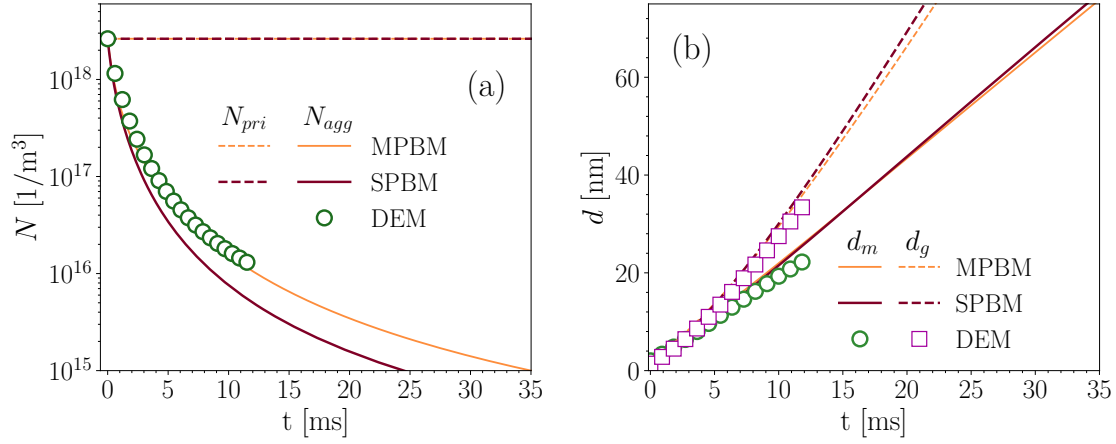


Fig. 3.3 The number concentration of agglomerates and primary particles (a), and mobility and gyration diameters (b) obtained by Omnisoot using MPBM and SPBM in the free-molecular regime, which are in close agreement with the DEM results [94] indicating the validity of the coagulation sub-models.

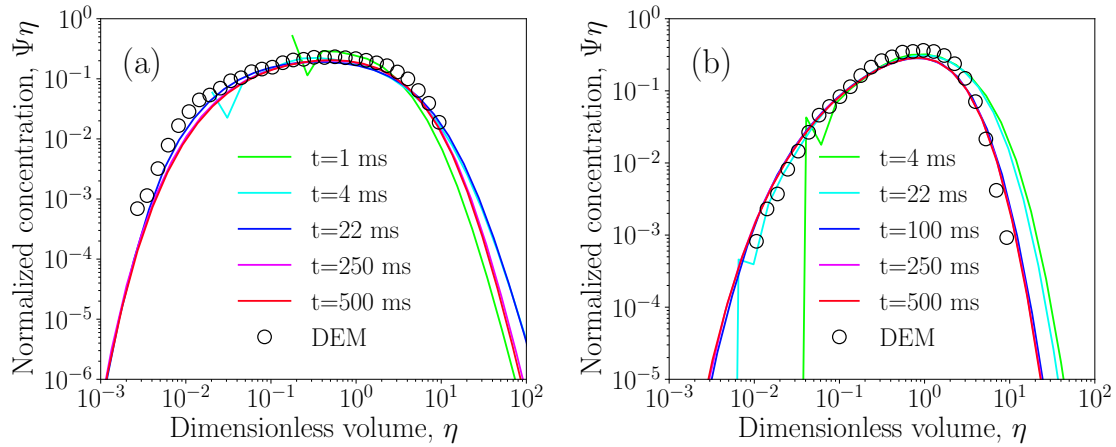


Fig. 3.4 The non-dimensional particle size distribution at different residence times in the free-molecular (a) and continuum regimes (b) overlaps after the initial transient phase, indicating the attainment of a self-preserving size distribution, which is also in good agreement with DEM results [63].

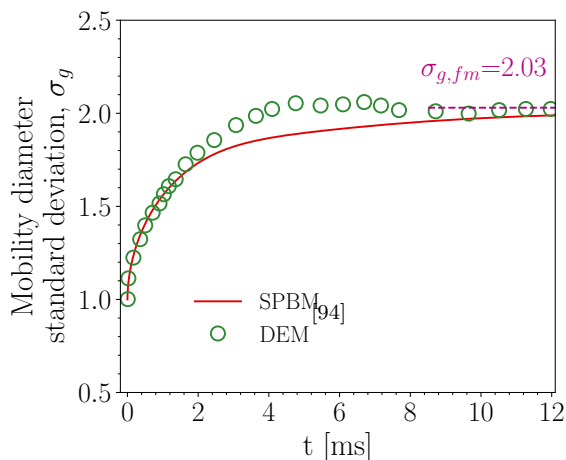


Fig. 3.5 Standard deviation of the mobility diameter, σ_g , in the free-molecular regime obtained by SPBM is in close agreement with DEM results [94].

3.3 Elemental and Energy Balance

To ensure the accuracy and reliability of the simulations, the conservation of elemental mass and energy was assessed across all reactor models implemented in Omnisoot. The elemental balances of carbon, hydrogen, and the total energy (internal or enthalpy depending on the reactor type) of the gas-particle system were evaluated during soot formation processes under various pyrolysis and combustion conditions. A set of simulations³ was performed using different combinations of PAH growth and particle dynamics models, and the relative errors in elemental and energy balances were monitored over time or reactor length. The relative error of total carbon, hydrogen and energy are calculated for CVR, CPR, PSR, and PFR using different combinations of particle dynamics and inception models. The residuals for all reactor configurations remained within acceptable limits (typically below 10^{-10}), confirming that Omnisoot accurately preserves mass and energy during the coupled evolution of gas-phase and soot particles.

3.3.1 Constant Volume Reactor

The pyrolysis of 30% CH_4 diluted in N_2 with the initial temperature and pressure of 2455 K and 3.47 atm, respectively, was simulated using CVR with a residence time of 40 ms. The combination of available PAH growth and particle dynamics models

³https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/validations/mass_energy

results in eight different cases, which were simulated to verify conservation of mass and energy. Here, we focus on the total elemental balance of carbon and hydrogen, as they are key elements involved in soot formation. Figure 3.6 shows the relative errors in total carbon, hydrogen, and energy for the different PAH growth and particle dynamics models. In all cases, the errors fall below 10^{-10} , confirming that CVR satisfies mass and energy conservation.

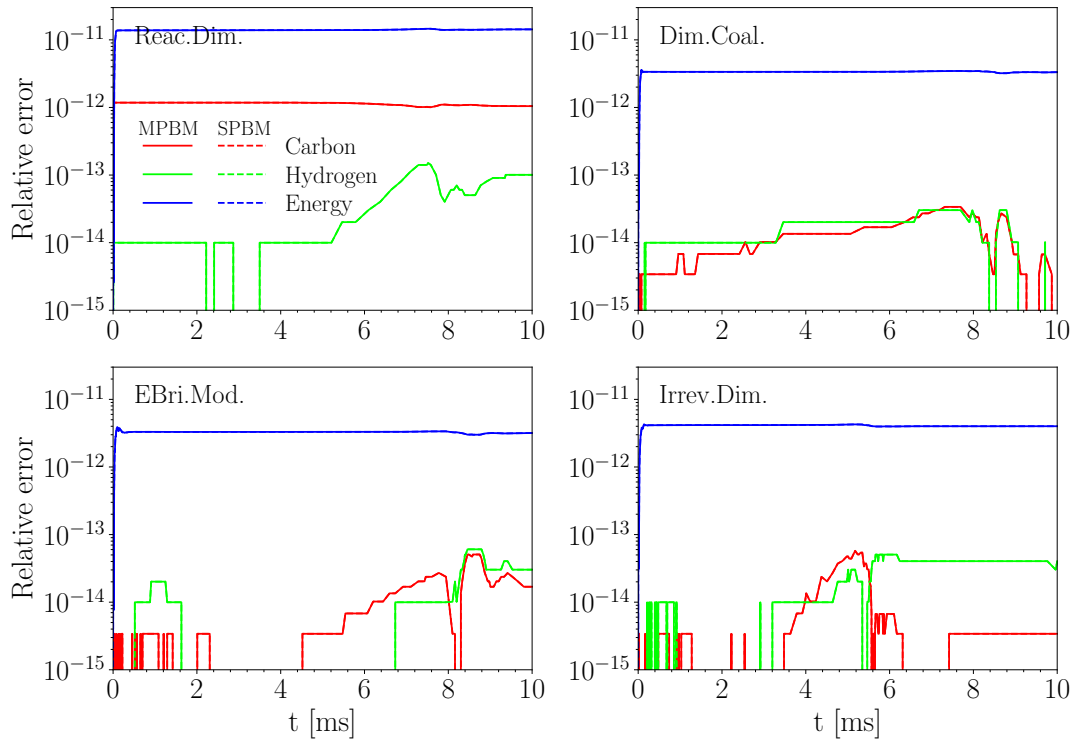


Fig. 3.6 The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted against residence time during pyrolysis of 30% $\text{CH}_4\text{-N}_2$ at 2455 K and 3.47 atm in the constant volume reactor simulated using different PAH growth models along with MPBM (solid line) and SPBM (dashed line).

3.3.2 Imposed Pressure Reactor

The pyrolysis of 5% CH_4 in a shock-tube at post-reflected-shock temperature and pressure of $T_5 = 2355$ K and $P_5 = 4.64$ atm was simulated using IPR model. The pressure was measured using an end-wall sensor by the Hanson Research Group at Stanford University. The measured pressure signal was smoothed using the Savitzky–Golay filter in SciPy[180] to reduce fluctuations in the raw signal and make it suitable for the

numerical solver. The residual of carbon and hydrogen mass are less than 10^{-12} , while the energy residual reaches up to 10^{-6} for energy by the end of the simulation. The relatively higher energy residual is attributed to pressure work.

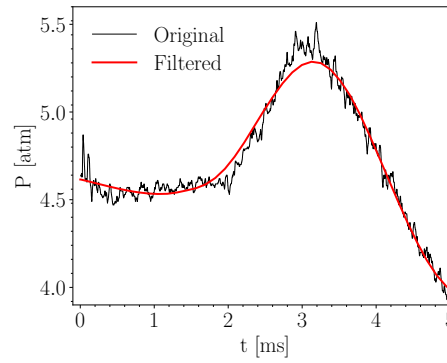


Fig. 3.7 The pressure time history (black line) measured by the Stanford group for pyrolysis of 5%CH₄ at $T_5 = 2355$ K and $P_5 = 4.64$ atm, and filtered (red line) with reduced fluctuations used to specify the pressure of the reactor

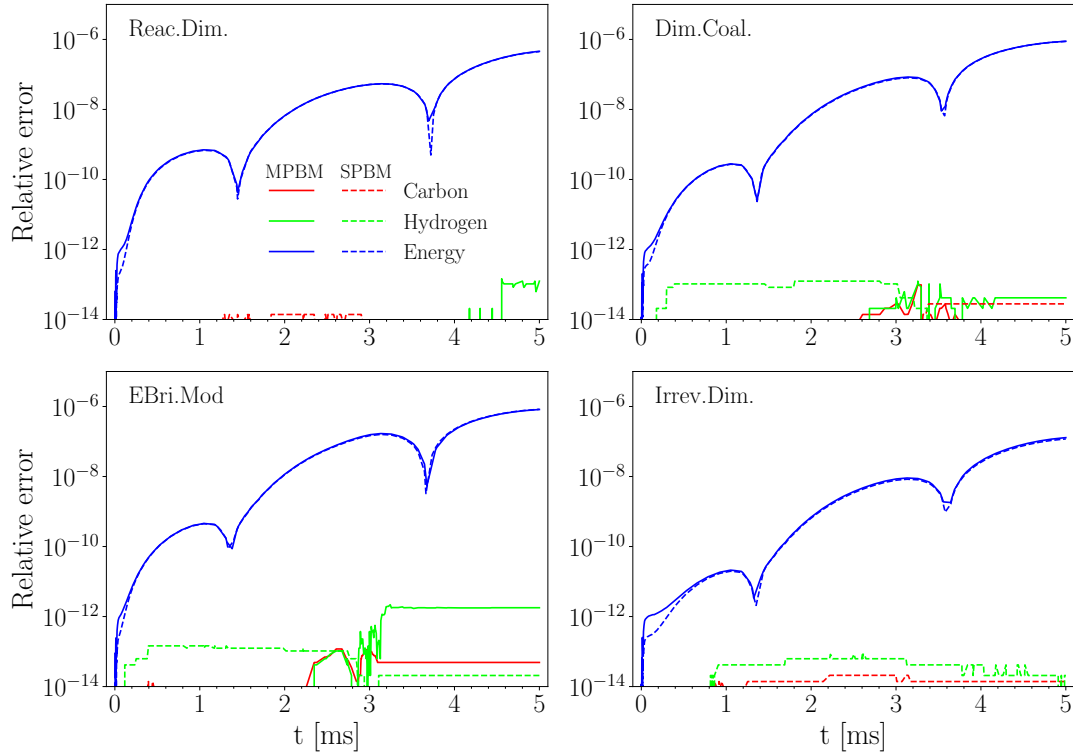


Fig. 3.8 The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted against residence time during pyrolysis of 5% CH_4 -Ar at post-reflected-shock temperature and pressure of $T_5 = 2355$ K and $P_5 = 4.64$ atm with an imposed pressure profile simulated using different PAH growth models along with MPBM (solid line) and SPBM (dashed line)

3.3.3 Perfectly Stirred Reactor

The mass and energy balance are investigated for soot formation during ethylene-air oxidation at equivalence ratio of $\phi = 2$ in a perfectly stirred reactor. The simulation conditions were chosen based on the combustor implemented and utilized by Stouffer et al. [166]. The reactants enter the reactor with the volume of 250 ml at 300 K and atmospheric pressure. The simulation is initialized from a high temperature (≈ 2000 K) to avoid trivial solution (cold reactant leaving the reactor with no chemical reactions) and to ensure the model captures a sustained combustion. The residence time of products in the reactor is 8.5 ms. Figure 3.9 shows the relative error of total elemental carbon and hydrogen mass and total enthalpy of gas and soot, which is less than 10^{-6} for all combinations of particle dynamics and PAH growth models.

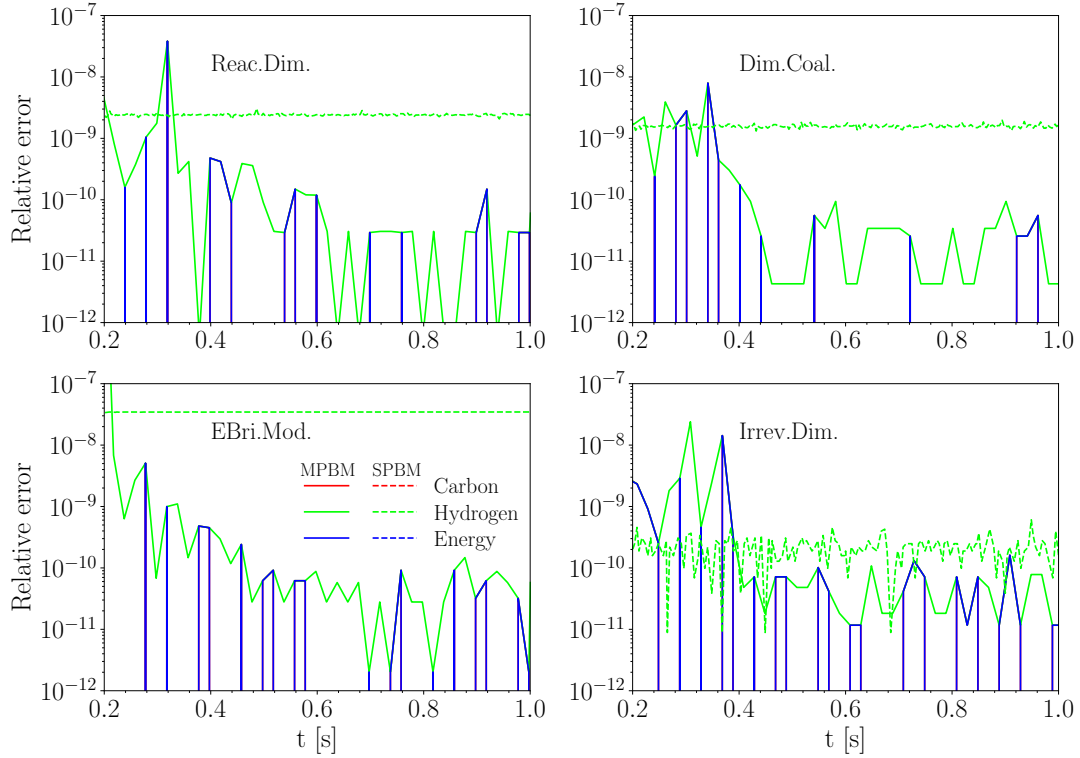


Fig. 3.9 The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted in simulation time during adiabatic combustion of C_2H_4 -air with $\phi = 2$ at 1 atm simulated using different combinations of PAH growth models and particle dynamics models: MPBM (solid line) and SPBM (dashed line).

3.3.4 Plug Flow Reactor

Methane pyrolysis in an adiabatic PFR was used to assess the conservation of elemental carbon, hydrogen, and energy. The inlet stream 30% CH_4 diluted in N_2 with an initial temperature of 2100 K and pressure of 1 atm. Figure 3.10 shows the residuals of total elemental carbon, hydrogen, and energy along the reactor length, up to 40 cm, for all combinations of PAH growth and particle dynamics models. The residuals remain below 10^{-11} , confirming that the PFR model in Omnisoot satisfies mass and energy conservation.

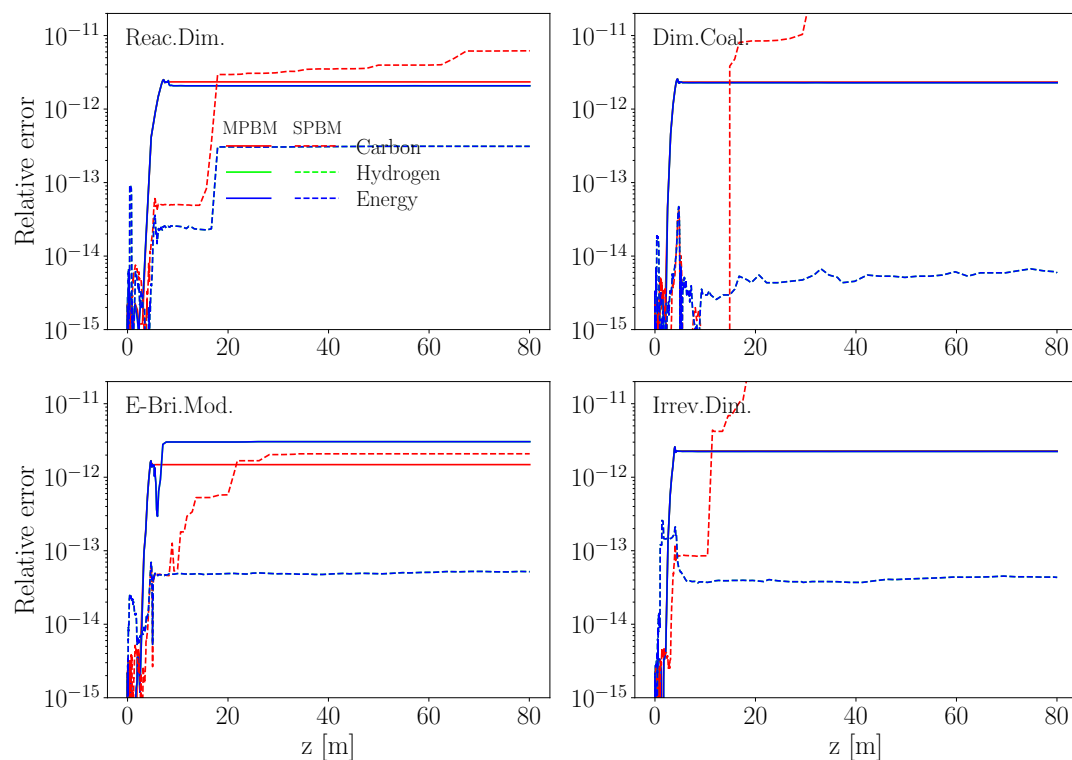


Fig. 3.10 The relative error of total carbon (red line) and hydrogen (green line) mass, and total internal energy residual of gas and soot (blue line) plotted against reactor length (cm) in the adiabatic flow reactor during pyrolysis of 30% $\text{CH}_4\text{-N}_2$ at 2100 K and 1 atm simulated using different PAH growth models and MPBM (solid line) and SPBM (dashed line)

Chapter 4

Results

This chapter shows the application of Omnisoot in various use-cases. Each section of the chapter represents a paper, in which Omnisoot was used for predicting soot yield, morphology and size distribution. The uncertainties from gas-phase chemistry and empirically-derived inception pathways were highlighted and discussed. The carbon flux from gas to solid via inception, HACA and PAH adsorption were investigated to understand their effect on soot properties. A special attention was paid to methane pyrolysis in shock-tubes with different compositions, and temperatures, and pressures because temperature and pressure ranges achieved in shock-tube experiments can reach 2300 K and 5 atm that are relevant to CB synthesis in industrial plasma reactors [57], which is a major motivations for developing Omnisoot. Additionally, a unique experimental data-set were compiled and processed in a joint program between Carleton-Monolith-Stanford. The shock-tube experimental campaign cover a wide range of high methane loadings (5%, 10%, and 30%) and temperature sweep of 1800 K-2500 K, and it provides simultaneous species and particulate measurements.

4.1 Fundamental analysis of PAH growth models

This section presents an extended version of the paper titled “*Omnisoot: a process design package for gas-phase synthesis of carbonaceous nanoparticles*” published in *Combustion and Flame*¹. In the paper, we introduced Omnisoot as an integrated platform for modeling soot formation using 0D reactors. Theoretical foundation and governing equations were discussed in Chapter 2. The results and discussion in the paper focused on (i) understanding the uncertainties in predicted soot properties due to

¹<https://doi.org/10.1016/j.combustflame.2025.114758>

gas-phase chemistry caused by the variability of reaction pathways and rate constants implemented in kinetic mechanisms (ii) the physio-chemical differences in PAH growth models when inception and PAH adsorption rates were adjusted by varying η_{inc} and η_{ads} to closely reproduce the experimental results.

4.1.1 Uncertainties in gas chemistry

Prior studies have shown that the predicted concentrations of large PAHs can vary by orders of magnitude depending on the reaction mechanism used [185]. This variation introduces substantial uncertainty in the predicted rates of soot inception and surface growth. As a result, the reliability of soot simulations depends more on the accuracy of upstream chemical kinetics than on the rate constants of the inception models.

To illustrate the impact of chemical mechanism selection on predict soot properties, a series of simulations² were performed using the CPR model of Omnisoot (with soot formation disabled) for the pyrolysis of 5% CH₄-Ar mixture at $T_5 = 2203$ K and $P_5 = 4.9$ atm [58]. Six widely used chemical mechanisms were evaluated: ABF [8], Caltech [21], KAUST [186], CRECK [153], ITV [72], and FFCM2 [201].

Fig. 4.1 shows the large variability in the predicted mole fraction of CH₄, C₂H₄, and C₂H₂ across different reaction mechanisms. The mole fraction of CH₄ serves as a useful indicator of carbon flux from the fuel to small and large intermediates. The CRECK and KAUST mechanisms significantly underpredict methane mole fraction compared to the measurements, but ABF and FFCM2 provide more accurate prediction considering the uncertainty of the experimental data. The carbon flux analysis by Wang et al. [185] highlighted the major role of C₂H₄ in the production of C₂H₂ via vinyl radical (C₂H₃). The overall trend of C₂H₄ mole fraction is captured by all mechanisms. After the rapid initial jump, C₂H₄ reaches its peak, which is underpredicted by ITV and overpredicted by KAUST. The subsequent decline was overestimated by all mechanisms that predict the final value of $\simeq 10^{-4}$ below the measurements. A similar variability is observed in the prediction of C₂H₂ mole fraction: it is best captured by FFCM2, overpredicted by CRECK, and slightly underpredicted by the ITV and Caltech mechanisms. Among all, FFCM2 shows the best overall agreement with the measurements; however, this mechanism only includes C₁-C₄ species and excludes benzene and larger PAHs, so it cannot be coupled with the soot models considered in this study.

Next, we examine the maximum possible soot yield predicted by the selected mechanisms (excluding FFCM2) during 5% CH₄ pyrolysis at $T_5 = 2203$ K and

²https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/examples/pressure/mechanism_comparison

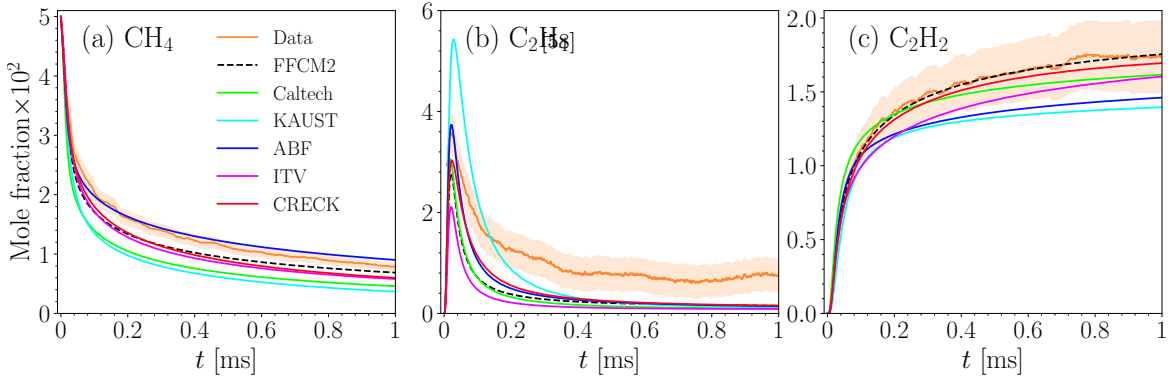


Fig. 4.1 The mole fraction of CH_4 (a), C_2H_4 and C_2H_2 (c) during pyrolysis of 5% CH_4 -Ar predicted using different reaction mechanisms and compared with measurements [58].

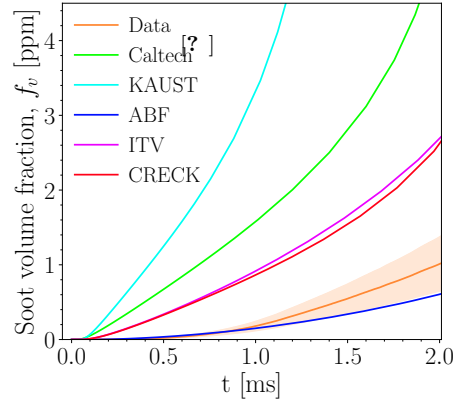


Fig. 4.2 The maximum soot volume fraction predicted using Irreversible Dimerization and different reaction mechanisms during pyrolysis of 5% CH_4 -Ar was compared with measurements [58]. The shaded area represents the uncertainty in the reported experimental data.

$P_5 = 4.9$ atm. To do so, the Irreversible Dimerization model is employed with 100% efficiency for both inception and PAH adsorption (i.e., all collisions lead to inception or surface growth). As shown in Fig. 4.2, the maximum possible f_v predicted by the mechanisms shows greater relative variation than that observed for CH_4 and C_2H_2 . Furthermore, the f_v predicted by the ABF mechanism is lower than the measured value, even when accounting for the reported uncertainty. The same analysis was performed for other data points with a different T_5 in [58], and similar results were observed indicating that ABF mechanism cannot provide enough precursors under pyrolysis conditions in these simulations. In contrast, the maximum possible f_v predicted by other mechanisms is significantly larger than the measurements, which presents the possibility of predicting f_v close to the measurements using more realistic assumptions

(i.e., lower dimerization efficiencies). Caltech and KAUST mechanisms are used in the simulations of this study for description of gas chemistry as they provide the highest carbon flux to soot precursors, and they are still computationally more affordable than ITV and CRECK mechanisms for parametric studies.

In the rest of the results, the inception and PAH adsorption rates of PAH growth models are adjusted by calibrating η_{inc} and η_{ads} to match predict soot properties with available measurements. Note that, this approach does not resolve the mechanistic uncertainties of soot formation. Instead, it allows the model to calculate effective carbon fluxes from the gas phase into the particle phase that are consistent with measured soot properties. Our analysis showed that all PAH growth models require different sets of η_{inc} and η_{ads} to capture the measured soot properties in the studied conditions. The lack of universal factors highlights the uncertainties in concentration of gaseous species, potential missing inception and surface growth pathways, and unknown sensitivities to temperature and fuel composition.

4.1.2 Methane pyrolysis in shock tube

The pyrolysis of a 5% CH₄-Ar mixture was studied using the CPR model over a post-shock temperature range of $T_5 = 1800\text{-}3000$ K and a pressure range of $P_5 = 4.7\text{-}7.1$ bar. Since P_5 was not specified for individual experiments (each defined by a given T_5), a linear dependence of P_5 on T_5 was assumed within the stated range [4]. The simulations were performed using the KAUST and Caltech mechanisms, and the model predictions were compared with the CY measurements. The bell-shaped profile of CY was captured using both mechanisms; however, the T_5 corresponding to the peak CY was overpredicted by all inception models using KAUST by more than 100 K, in contrast to the Caltech mechanism, which shows closer agreement with the measurements. Therefore, the gas-phase chemistry was described using the Caltech mechanism for the rest of simulations in for the shock-tube pyrolysis of methane. Inception and PAH adsorption rates were adjusted using η_{inc} and η_{ads} , respectively, to match the predicted Carbon Yield (CY) at $t = 1.5$ ms with light extinction measurements at $\lambda = 632$ nm across the studied T_5 and P_5 ranges [4]. The experimental CY was extracted from the reported product of CY and the absorption function, $E(m)$. However, this approach introduces uncertainty due to variability in $E(m)$. It is common to assume the $E(m)$ of mature soot, which may not be valid in shock tube experiments with short residence times (≈ 2 ms) that involve initial stages of soot formation, as $E(m)$ increases with particle size, composition, and maturity. For instance, during acetylene pyrolysis, $E(m)$ can vary from 0.05 to 0.25 as d_p reaches 20

nm within 1.6 ms. We considered the reported variability of $E(m)$ in the literature, ranging from 0.174 [103] to 0.37 [6].

A parametric study was conducted on η_{inc} and η_{ads} using a grid search approach. Each factor was varied across 11 logarithmically spaced values from 10^{-4} to 1, resulting in 121 simulation cases per data point and 847 simulations in total. Each η_{inc} and η_{ads} pair was ranked based on the average relative error of CY across all data points in the studied T_5 range, in order to identify the set of adjustment factors that minimized the CY prediction error.

To reduce the computational load of the parametric study, simulations were performed using MPBM for all inception models. The comparison of results obtained using SPBM and MPBM in Fig. A.1 shows that CY and d_p are not sensitive to the choice of particle dynamics model, indicating that MPBM results can be reliably used for CY error analysis. However, N_{agg} and n_p , shown in Fig. A.2, differ significantly between SPBM and MPBM because the central assumption of the monodisperse model is the rapid attainment of SPSD, which is not valid at short residence times near 1.5 ms. For example, the non-dimensional PSD at $T_5 = 2200$ K, shown in Fig. A.3, significantly changes from 1.0 ms to 2.5 ms for all inception models.

Fig. 4.3 shows a heat map of the mean relative error, normalized by the maximum value, for all inception models. The largest error occurs for the combination of maximum inception ($\eta_{inc} = 1$ or $\log_{10}(\eta_{inc}) = 0$) and minimum adsorption ($\eta_{ads} = 10^{-4}$ or $\log_{10}(\eta_{ads}) = -4$). The region of lowest normalized error (less than 5%), outlined in blue in Fig. 4.3, includes a broad set of adjustment factor combinations that enable the model to accurately predict CY. However, accurate prediction of CY does not necessarily imply accurate prediction of other properties, such as primary particle diameter or mobility diameter. The availability of data on other soot parameters or intermediate gaseous species, and including them as optimization targets, could help narrow down the range of optimal adjustment factors.

To highlight the variability in soot morphology across the low-error region of the heat map, we focus on three representative combinations of η_{inc} and η_{ads} : (i) minimum inception flux ($\eta_{inc} = 10^{-4}$), (ii) minimum PAH adsorption rate ($\eta_{ads} = 10^{-4}$), and (iii) equally scaled inception flux and PAH adsorption rate ($\eta_{inc} = \eta_{ads}$). It is important to note that soot CY and morphology are closely coupled to gas-phase chemistry under the short residence times studied. Therefore, a set of simulations was performed without soot to isolate gas-phase chemistry and examine the temperature dependence of soot precursors and C_2H_2 . Subsequently, inception models were optimized using equal

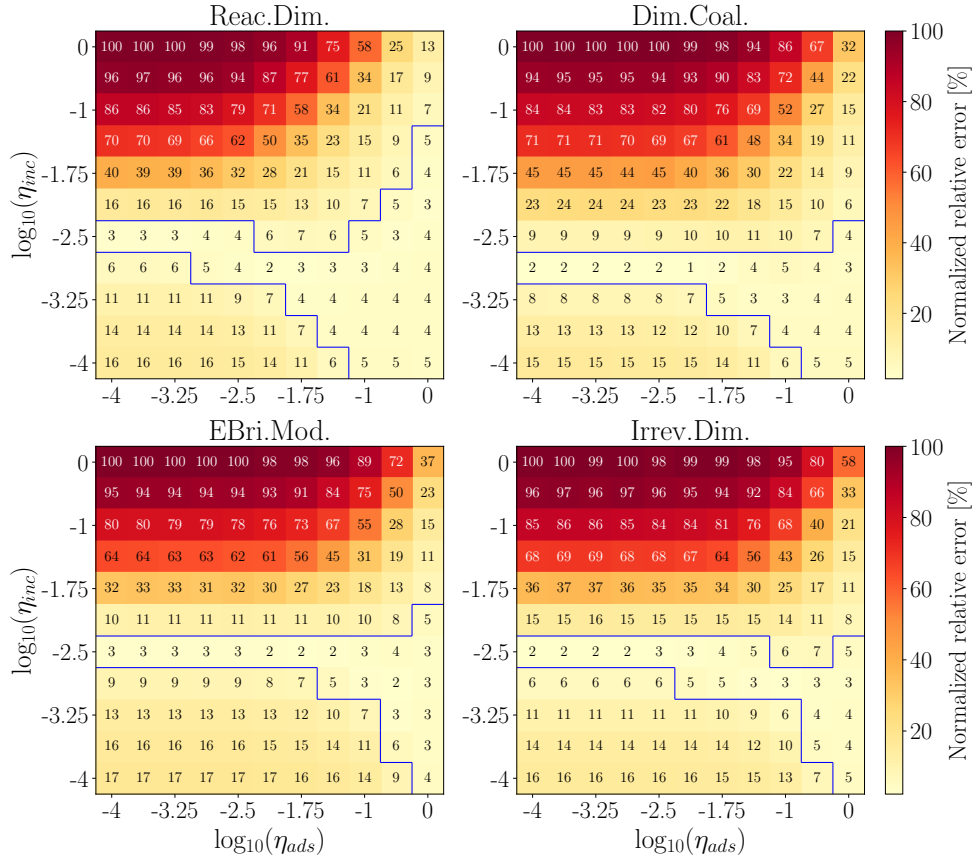


Fig. 4.3 The relative error of CY normalized by the maximum value at $t = 1.5$ ms for 5% CH_4 -Ar obtained using Caltech mechanism and all PAH growth models. Each cell is annotated with its corresponding normalized relative error expressed in percent.

adjustment factors³ ($\eta_{inc} = \eta_{ads}$), and separate optimizations were carried out for the minimum adsorption case ($\eta_{ads} = 10^{-4}$) and the minimum inception case ($\eta_{inc} = 10^{-4}$), denoted as *Min-Ads* and *Min-Inc*, respectively.

Fig. 4.4a shows the CMF of soot precursors (individual PAHs and total) and C_2H_2 at 1.5 ms across the studied temperature range, with the soot model deactivated. The CMF is defined as the ratio of the carbon mass contained in a given species to the total carbon mass in the system. While PAH precursors exhibit a bell-shaped profile, the CMF of C_2H_2 increases linearly with temperature and plateaus near 85% at $T_5 \approx 2400$ K. Among the considered PAHs, A2, A2R5, and A4R5 account for most of the carbon and are likely major contributors to soot inception and surface growth. The strong variation in PAH CMF highlights the impact of precursor selection on inception flux, surface growth rates, and their temperature dependence. Fig. 4.5 illustrates the

³https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/examples/pressure/methane_pyrolysis

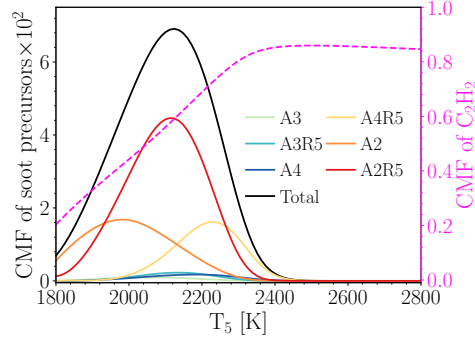


Fig. 4.4 The bell-shaped temperature profile of carbon mass fraction of soot precursors (A2 and larger) combined and C_2H_2 at $t = 1.5$ ms during pyrolysis of 5% CH_4 -Ar obtained using Caltech mechanism without considering soot.

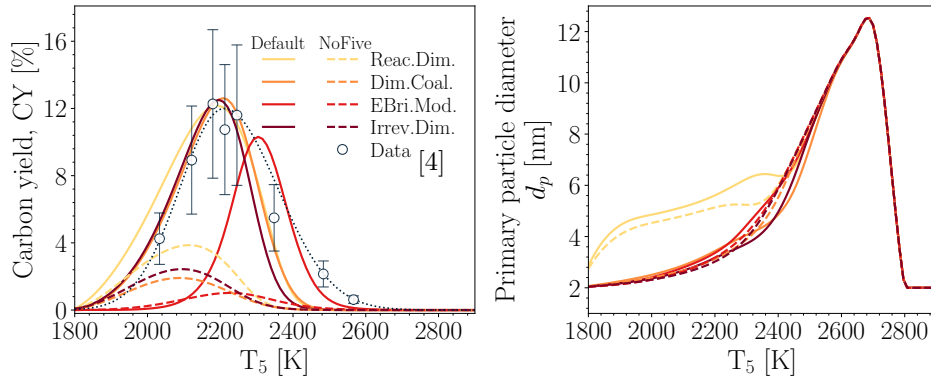


Fig. 4.5 The soot carbon yield, CY, at $t = 1.5$ ms (a) and primary particle diameter, d_p (b) obtained using the default soot precursors (denoted by solid line and labeled as “Default”) compared with the same results when five-membered ring PAHs excluded from soot precursors (denoted by dashed line and labeled as “NoFive”). Both cases were obtained using Caltech mechanism and the same equal adjustment factors. The black dashed line was added to show the trend in the measurements [4].

effect of excluding five-membered ring PAHs (A2R5, A3R5, and A4R5) from the soot precursors on the CY and d_p . As expected, excluding these species reduces CY for all inception models, potentially highlighting the significant contribution of five-membered rings PAHs.

Next set of simulations were conducted by using equal adjustment factors ($\eta_{inc} = \eta_{ads}$) to minimize the prediction error of CY. Table 4.1 lists the adjustment factors used for each inception model. Note that the efficiencies of inception (γ_{inc} in Equation (2.87)) and PAH adsorption (γ_{ads} in Equation (2.88)) for Irreversible Dimerization were set to 10^{-4} and 10^{-3} , respectively [131], so η_{inc} and η_{ads} values greater than unity do not result in collision rates exceeding the theoretical limit of kinetic theory. Fig. 4.6a compares

Table 4.1 The value of adjustment factors used in the simulation of 5% CH₄-Ar pyrolysis.

	Reac.Dim.	Dim.Coal.	EBri.Mod.	Irrev.Dim.
η_{inc}	0.17	0.21	0.36	2.3
η_{ads}	0.17	0.21	0.36	2.3

CY from various inception models with experimental data [4]. A skew exponential curve (black dotted line) was fitted to the data to highlight the CY trend and its peak near 12%. Soot CY follows a bell-shaped profile similar to that of soot precursors, as inception flux and PAH adsorption rate directly depend on precursor concentrations. Reactive Dimerization model predicts a higher CY at lower temperatures due to stronger PAH adsorption rates, while E-Bridge Modified model shifts the peak to higher temperatures compared to the other models because in this model, inception is initiated and controlled by the dehydrogenation rate of PAH molecules, which is strongly depends on temperature and the concentration of H radicals. In contrast, the other models begin with physical PAH collision, which is primarily a function of PAH concentration.

As shown in Fig. 4.6b, the predicted d_p increases with T_5 , reaching a maximum of 11 nm at 2700 K, where yield is very low ($\approx 10^{-7}$), and then drops to the model's minimum allowed value of 2 nm. The differences between inception models in predicting d_p is overall negligible except for Reactive Dimerization model, which predicts a larger d_p in $T_5 < 2500$ K. The d_p trends can be better understood by examining Equation (4.5) indicating that d_p is proportional to the third-root of C_{tot}/N_{pri} . C_{tot} describes total carbon mass converted to soot through inception and surface growth while N_{pri} is only determined by inception flux. As a result, d_p is controlled by the ratio of total surface growth rate (via HACA and PAH adsorption) to inception flux. Here, we define the parameter θ as the ratio of carbon mass gained via each pathway to the total soot carbon mass. As shown in Fig. 4.7, PAH adsorption is the dominant soot mass growth pathway for Reactive Dimerization model in $T_5 < 2000$ K (Fig. 4.7a), which results in larger C_{tot}/N_{pri} and d_p values, but inception is dominant for the other inception models. The contribution of inception decreases with temperature for all inception models while the contribution of HACA becomes dominant up to 2700 K leading to higher d_p (Fig. 4.6b). This is due to the decrease of precursor concentration and the increase of C₂H₂ CMF. Beyond 2700 K, the contribution of inception rapidly increases with temperature leading to the decrease of d_p (Fig. 4.6b).

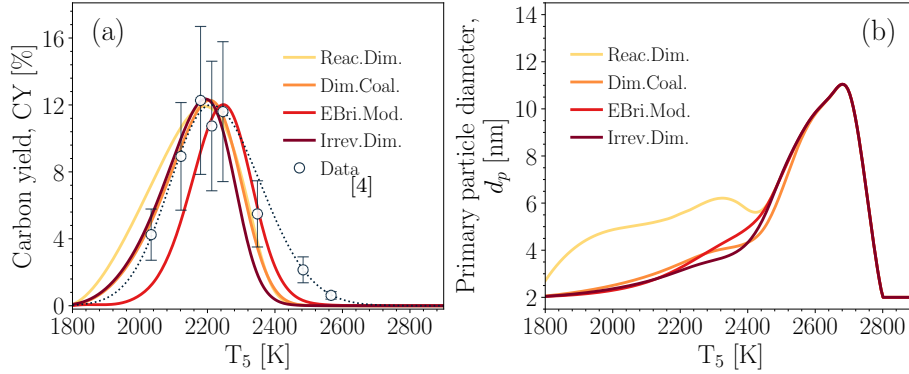


Fig. 4.6 The CY (a) and primary particle diameter, d_p , (b) at $t = 1.5$ ms during the pyrolysis of 5% CH_4 -Ar obtained using equal adjustment factors to minimize the prediction error with extinction measurements [4]. The dashed line was added to show the trend in the measurements.

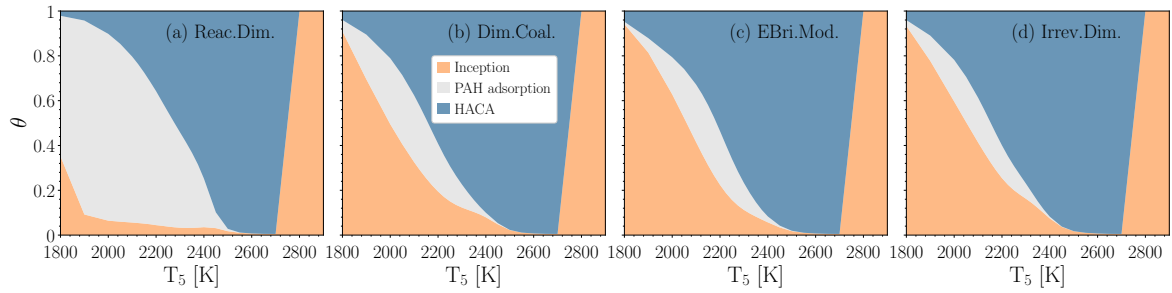


Fig. 4.7 The variation of θ , defined as soot carbon mass from inception, PAH adsorption and HACA normalized by total soot carbon mass at $t = 1.5$ ms during the pyrolysis of 5% CH_4 -Ar.

Fig. 4.8a shows that N_{pri} peaks near 2200 K, aligning with the peak in CY. This is expected because N_{pri} depends solely on the inception flux, which is the highest when PAH concentrations peak. Increased coagulation rates reduce N_{agg} in the 2000-2500 K range. Reactive Dimerization model yields the fewest particles (N_{pri} and N_{agg}) because more precursors are directed toward PAH adsorption. Consequently, n_p is lowest for Reactive Dimerization model. Differences between inception models are more evident in n_p than in d_p , influencing predicted particle morphology.

Fig. 4.9a and Fig. 4.9b shows that the optimized models with minimum η_{inc} and η_{ads} yield similar CY across inception models, except E-Bridge Modified model, which shifts slightly toward higher temperatures. The Min-Ads case has a higher peak and narrower profile compared with the Min-Inc case. As shown in Fig. 4.9c, d_p predicted in Min-Ads mode is smaller and less sensitive to the selection of inception model compared with Min-Inc mode. Two peaks can be seen in Min-Inc mode for all inception models:

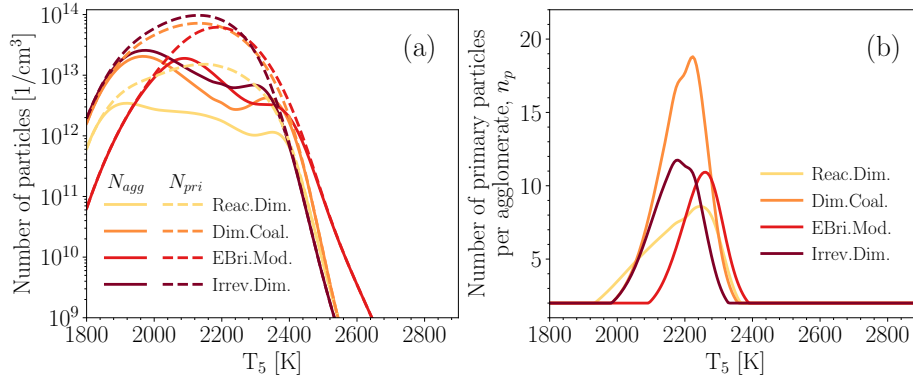


Fig. 4.8 The temperature dependence of total number of agglomerates, N_{agg} (a), number of primary particles per agglomerate, n_p (b) at $t = 1.5$ ms during the pyrolysis of 5% CH_4 -Ar.

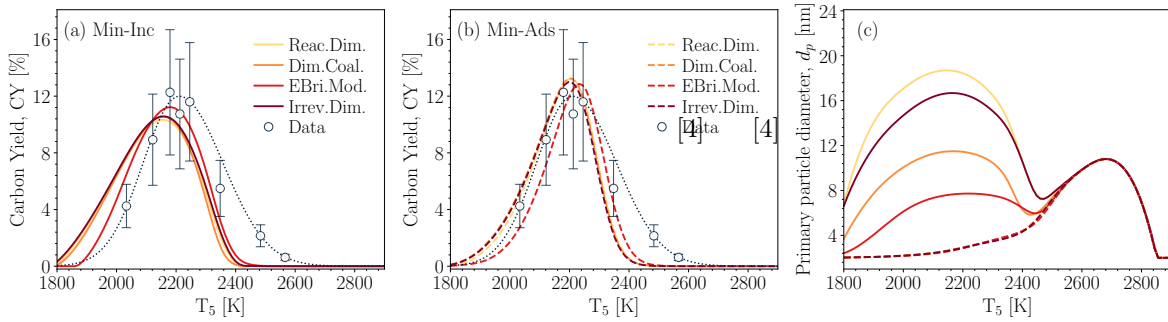


Fig. 4.9 The comparison of CY and d_p at $t = 1.5$ ms for 5% CH_4 -Ar when the minimum inception (solid lines) and the minimum PAH adsorption adjustment factors were applied to minimize the prediction error. The dashed line was added to show the trend in the measurements.

The first peak occurs due to high PAH adsorption rates at the temperature range close to the peak of CMF of soot precursors (Fig. 4.4a); the second peak which occurs around $T_5 = 2700$ K and $d_p = 12$ nm, which is very similar to d_p trends predicted using equal adjustment factors (Fig. 4.6b). Reactive Dimerization model has the largest variation at the peak from 2 to 19 nm between Min-Ads and Min-Inc modes. The existence of such a variation highlights the need for characterizing primary particle size in the experiment to reduce the uncertainty in the soot model and restrict the range of expected inception and surface growth rates required to accurately predict soot yield and morphology.

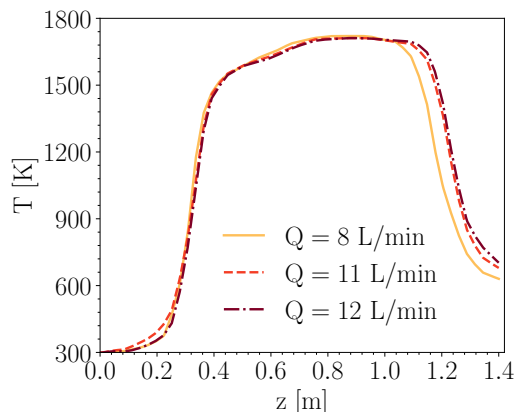


Fig. 4.10 The centerline temperature along the reactor for $Q = 8, 11$, and 12 L/min interpolated from the thermocouple measurements [115].

4.1.3 Ethylene pyrolysis in a flow reactor

The PFR model was used to simulate⁴ the pyrolysis of 0.6% C_2H_4 - N_2 in a 1.4 m long, and 16 mm diameter flow reactor. Fig. 4.10 shows the axial temperature profile used in the simulations. The maximum temperature, $T_{\max} = 1673$ K, was imposed on the model based on thermocouple measurements reported in [115] for various flow rates along the reactor centerline. The temperature increases from 300 K at the reactor inlet to the hot zone, where it reaches a value within 10% of $T_{\max}$. The length of the hot zone varies with flow rate due to advection, ranging from 0.71 m at $Q = 8$ L/min to 0.76 m at $Q = 12$ L/min. Near the reactor outlet, the temperature drops to approximately 650 K.

The inception and PAH adsorption adjustment factors were varied to match the predicted PSD with Scanning Mobility Particle Sizer (SMPS) measurements conducted on centerline at the reactor exit for the flow rates of 8, 11, and 12 L/min [115], as shown in Fig. 4.11. The parametric analysis revealed that each inception model requires a unique set of adjustment factors to minimize the PSD prediction error across different flow rates. The KAUST mechanism [186] was used to describe gas-phase chemistry because it provided better agreement with the measured PSDs than the Caltech mechanism, shown in Fig. A.4. Nevertheless, the choice of reaction mechanism does not change the findings about the differences between the inception models because they are primarily due to their reversibility and sensitivity to temperature, which is not affected by the base kinetic mechanism. Table 4.2 indicates the adjustment factors

⁴https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/examples/plug_flow/sectional

Table 4.2 The value of adjustment factors used in the simulation of ethylene pyrolysis in the flow reactor.

	Reac.Dim.	Dim.Coal.	EBri.Mod.	Irrev.Dim.
η_{inc}	0.01	0.004	0.01	0.08
η_{ads}	0.001	0.01	0.1	1

used with the KAUST mechanism for simulations of ethylene pyrolysis in the studied flow reactor.

A bimodal size distribution can be observed for $Q = 8$ L/min (Fig. 4.11a) that was attributed to the continuous inception [202]. The comparison of simulations with measurements reveals different temperature dependence of inception models. Irreversible Dimerization and Dimer Coalescence models capture the bimodality of PSD in good agreement with the measurements, but the other two models predict a nearly unimodal PSD. Specifically, the number concentration of the first section is lower by more than three orders of magnitude for the Reactive Dimerization and E-Bridge Modified models indicating the lack of active inception at the sampling location due to the temperature drop near the end of reactor that suppresses soot inception.

All inception models capture the disappearance of the PSD shoulder at flow rates of 11 and 12 L/min. In these cases, the shorter particle residence time limits coagulation, preventing formation of a second peak. However, Reactive Dimerization and E-Bridge Modified models still underpredict the number concentration of nascent particles by approximately one order of magnitude compared to the irreversible models (Irreversible Dimerization and Dimer Coalescence).

As shown in Fig. 4.11d-f, all inception models predict nearly the same N_{agg} up to $z \approx 1.1$ m, corresponding to the end of the hot zone. Beyond this point, N_{agg} continues to increase for the Irreversible Dimerization and Dimer Coalescence models, which allows soot inception to proceed in cooler downstream regions. These models agree well with experimental data at 8 and 11 L/min but tend to overpredict N_{agg} at 12 L/min.

Soot inception flux rises sharply as the gas enters the hot zone. The axial location where the flux exceeds 10^7 cm⁻³ s⁻¹ is similar across all inception models, as it is primarily determined by PAH chemistry. However, this location shifts downstream with increasing flow rate due to reduced residence time. Within the hot zone, differences among the inception models are minimal. Outside the hot zone, Irreversible Dimerization and Dimer Coalescence models maintain high inception flux, while Reactive Dimerization and E-Bridge Modified models predict a rapid decrease of more than three

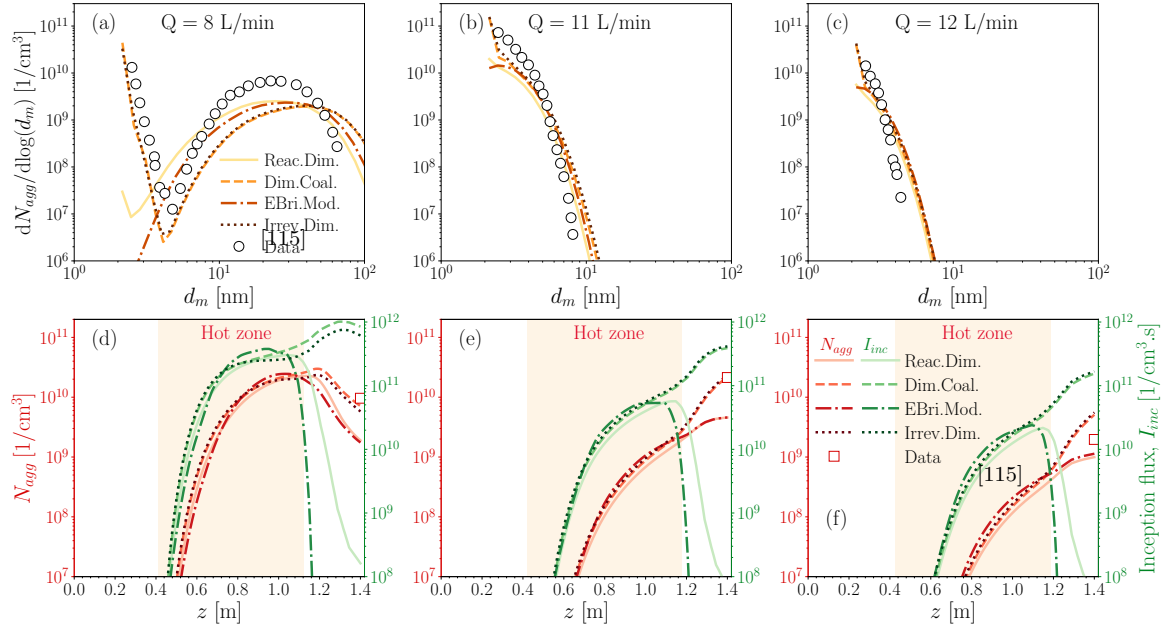


Fig. 4.11 The particle size distribution at the end of PFR, and the total number of agglomerates, N_{agg} , and inception flux, I_{inc} along the PFR for $Q = 8$ (a, d), 11 (b, e), and 12 L/min (c, f) obtained using KAUST mechanism, SPBM and different inception models calibrated to match the predictions with measurement [115].

orders of magnitude due to cooling. The difference between the models is primarily due to their temperature dependence as indicated in Table. 2.3 and illustrated in Fig. 2.6. The Arrhenius rates embedded in the carbonization step in Reactive Dimerization and the dehydrogenation in E-Bridge cause an exponential decay in these models with the temperature drops for $z > 1.1$ m. Fig. 4.12 demonstrates the contribution of each pathway to total carbon mass of soot along the reactor, which elucidates the link between particle morphology and the balance of inception and surface growth. The relative contribution of inception decreases from 100% to less than 5% by $z = 1.1$ m for all inception models leading to a gradual increase in d_p and d_m . Irreversible Dimerization and Dimer Coalescence models predict an increase in the contribution of inception beyond $z > 1.1$ m resulting in the decline of d_p while Reactive Dimerization and E-Bridge Modified models predict a nearly constant d_p close to 5 nm. The final increase in d_m beyond the end of the hot zone near $z = 1.1$ m is more pronounced for the Reactive Dimerization and E-Bridge Modified models. This is because the inception rate and surface growth rate (Fig. A.5) rapidly decrease in these models, and soot morphology becomes primarily governed by coagulation, which conserves d_p and increases d_m .

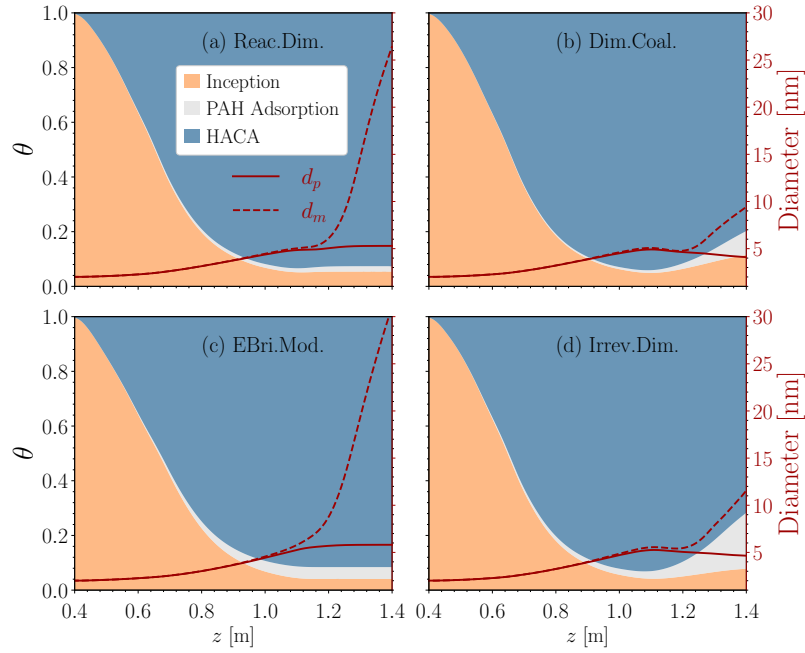


Fig. 4.12 The variation of θ , defined as soot carbon mass from inception, PAH adsorption and HACA normalized by total soot carbon mass for $Q = 8$ L/min along with d_p and d_m obtained using KAUST mechanism, SPBM and different inception models.

4.1.4 Ethylene combustion in a perfectly stirred reactor

The PSR model of Omnisoot⁵ was used to simulate ethylene combustion at different equivalence ratios, $\phi = 1.9, 2.0$, and 2.1 in a perfectly stirred reactor connected to a flow reactor [109]. PSD measurements were conducted at the end of the flow reactor using a Nano-Differential Mobility Analyzer (Nano-DMA). The volume (V) and nominal residence time (τ_{psr}) of the PSR are 250 ml and 11 ms, respectively [109]. The flow reactor is 70 cm long with an inner diameter of 5.1 cm. The reactants enter the adiabatic PSR at 300 K with an inlet mass flow rate of $\dot{m}_{in} = \rho V / \tau_{psr}$, where ρ was calculated at the reactor temperature of 1723 K [?]. The PSR simulation was continued until a steady-state condition was reached for all the solution variables. The final gas composition, temperature, and soot properties from the PSR were used as inlet conditions for the PFR simulations, yielding an average axial velocity of 14.5 m/s in the PFR, which is consistent with the values reported in [109].

The KAUST mechanism was used to describe the gas-phase chemistry. The inception and PAH adsorption adjustment factors were varied for each PAH growth model to match the predicted PSD with the measurements as closely as possible for all three

⁵https://github.com/mohammadadib-cu/omnisoot-cv/tree/main/examples/psr_pfr

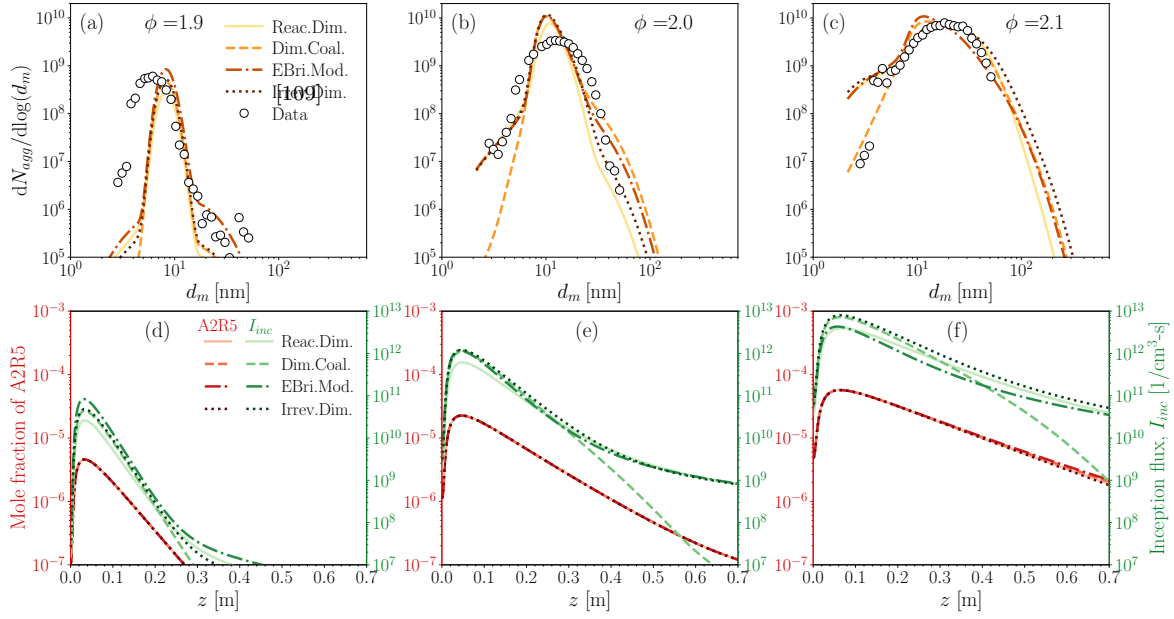


Fig. 4.13 The particle size distribution at the end of PFR, and the mole fraction of A2R5, and inception flux, I_{inc} along the PFR for $\phi = 1.9$ (a, d), 2.0 (b, e), and 2.1 (c, f) obtained using KAUST mechanism, SPBM and different inception models calibrated to match the predictions with the PSD measurements [109].

Table 4.3 The value of adjustment factors used in the simulation of ethylene oxidation in the perfectly stirred reactor.

	Reac.Dim.	Dim.Coal.	EBri.Mod.	Irrev.Dim.
η_{inc}	0.0005	0.001	0.0002	0.01
η_{ads}	0.01	0.01	0.01	1

equivalence ratios. A similar match could not be reached using the Caltech mechanism because the number concentration of particles was underestimated by at least four orders of magnitude even with $\eta_{inc} = \eta_{ads} = 1$. Table 4.3 lists the adjustment factors used with the KAUST mechanism for simulations of ethylene oxidation in the studied perfectly stirred reactor.

As shown in Fig. 4.13, all inception models capture the peak number concentration and the unimodal shape of the PSD, indicating that particle inception has ceased and coagulation is the dominant mechanism for agglomerate size growth. As reported in Table 4.4, the geometric mean mobility diameter, $d_{m,g}$, and the geometric mobility standard deviation, $\sigma_{m,g}$, obtained using all inception models are in good agreement with the values calculated from the measured PSD [109]. As shown in Fig. 4.13a-b, the

Table 4.4 The geometric mean mobility diameter, $d_{m,g}$, and the geometric mobility standard deviation, $\sigma_{m,g}$, obtained using different inception models compared with the value calculated from the measured PSD [109].

	$\phi = 1.9$		$\phi = 2.0$		$\phi = 2.1$	
	$d_{m,g}$ [nm]	$\sigma_{m,g}$	$d_{m,g}$ [nm]	$\sigma_{m,g}$	$d_{m,g}$ [nm]	$\sigma_{m,g}$
Data [109]	6.04	1.25	12.40	1.49	17.66	1.64
Reactive Dimerization	8.27	1.14	11.10	1.21	16.88	1.58
Dimer Coalescence	8.18	1.14	10.76	1.24	16.99	1.68
E-Bridge Modified	8.27	1.15	11.02	1.27	14.56	1.58
Irreversible Dimerization	8.19	1.14	10.96	1.25	18.44	1.78

spread of the predicted PSD is narrower than that of the measurements for $\phi = 1.9$ and 2.0, corresponding to an underprediction of $\sigma_{m,g}$ for these equivalence ratios.

All inception models underpredict the number concentration of small particles ($d_m < 6$ nm) at $\phi = 1.9$. The discrepancy decreases at $\phi = 2.0$, and the model predictions align well with the measurements except for Dimer Coalescence model that underpredicts the number concentration of small particles ($d_m < 5$ nm). In the simulation results, the number concentration of the smallest particles with a diameter of 2 nm is strongly affected by the equivalence ratio, as the precursor production rate increases with ϕ . This behavior can be better understood by comparing the acenaphthylene (A2R5) mole fraction at different ϕ values, as shown in Fig. 4.13d-f. The inlet mole fraction of A2R5 at $z = 0$ m corresponds to the value obtained from the PSR, which increases by factors of 10 and 4 when ϕ is increased incrementally from 1.9 to 2.0, and from 2.0 to 2.1, respectively. This relative increase is nearly the same across all inception models. The jump in A2R5 mole fraction leads to a substantial increase in the inception flux, which explains the sensitivity of the smallest particle concentrations to the equivalence ratio. The strong similarity between the A2R5 mole fraction profiles and the soot inception profiles along the reactor highlights the dominant role of A2R5 in soot inception. Another important observation is that the A2R5 mole fraction is not affected by the choice of inception model.

As shown in Fig. 4.14a-c, d_p along the PFR is nearly identical for all inception models at $\phi = 1.9$, but the differences become more noticeable at higher ϕ values. The Reactive Dimerization model predicts the largest final d_p because it channels more PAH mass into PAH adsorption rather than inception, which is consistent with the

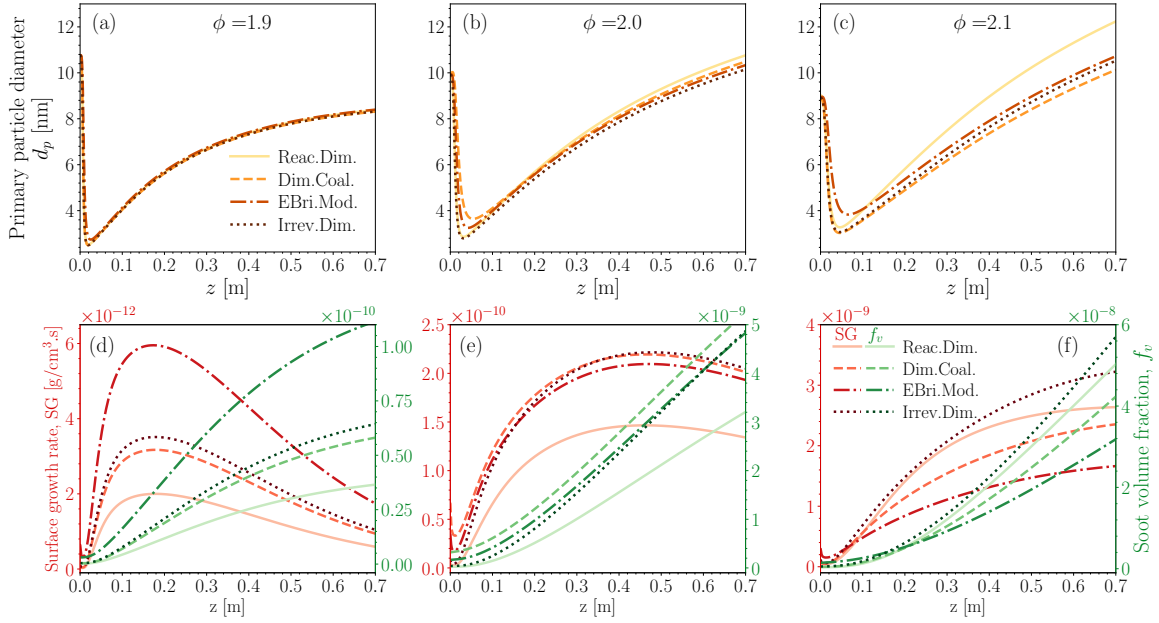


Fig. 4.14 The primary particle diameter, d_p , the total surface growth rate by HACA and PAH adsorption, and the soot volume fraction, f_v along the PFR for $\phi = 1.9$ (a, d), 2.0 (b, e), and 2.1 (c, f) obtained using KAUST mechanism, SPBM and different inception models calibrated to match the predictions with the PSD measurements [109].

lower peak number concentration observed in Fig. 4.13. The value of d_p decreases rapidly at the beginning of the reactor due to a surge in the production of incipient particles (spherical particles with a diameter of 2 nm), which lowers the mean d_p . It then increases toward the end of the reactor as surface growth becomes dominant. Although the final d_p increases slightly with ϕ , the overall range remains similar across ϕ values, indicating a comparable balance between inception and surface growth.

As shown in Fig. 4.14, the surface growth rate (HACA and PAH adsorption combined) and the soot volume fraction, however, are highly sensitive to ϕ , which can be attributed to the strong influence of ϕ on precursor production, inception flux, and the number of particles. An analysis of surface growth rates at the end of the PFR revealed that more than 95% of the soot mass is acquired through the HACA mechanism. The apparent difference in f_v between the inception models originates from the different PAH adsorption rate predicted by the inception models. For example, at $\phi = 1.9$, the E-Bridge Modified model predicts the highest surface growth rate and soot volume fraction due to a higher number of agglomerates (as shown in Fig. 4.13a), which leads to a larger total surface area, which is the key factor in calculating the HACA growth rate.

4.1.5 Conclusions

Omnisoot was employed to elucidate differences among inception models in shock tubes, flow reactors, and perfectly stirred reactors. Global adjustment factors were applied to inception and surface growth rates to accurately reproduce experimental data for each target scenario across a range of parameters, including temperature, pressure, composition, and flow rates. The performance of inception models was evaluated based on soot yield, morphology, size distribution, inception and surface growth rates, and carbon mass source analysis. Although different inception models predicted similar carbon yields that closely matched experimental observations, they produced varying morphological characteristics. This highlights the importance of characterizing soot morphology to better constrain inception flux and surface growth rate predictions.

Simulations of ethylene pyrolysis in a flow reactor demonstrated the temperature sensitivity of inception models. Irreversible models (Irreversible Dimerization and Dimer Coalescence) effectively captured the bimodal PSD resulting from high inception flux in the lower-temperature region near the reactor exit due to their weak dependence. However, the Reactive Dimerization and E-Bridge models generated nearly unimodal distributions due to their exponential temperature dependence, causing a significant drop in inception flux in the same region.

The PSD sampled at the outlet of a flow reactor downstream of a perfectly stirred reactor showed good agreement with experimental measurements across three equivalence ratios. Simulations indicated that active inception and surface growth primarily occur at high temperatures within the perfectly stirred reactor and at the entrance region of the flow reactor, far upstream of the sampling location. Under these conditions, the particle size distribution, morphology, and inception flux predictions were largely consistent across all inception models, although notable differences were observed in soot volume fraction due to variations in predicted HACA growth rate.

4.2 Identifying stages of carbon black evolution

This section presents the paper titled “*Yield, morphology and maturity of carbon black made by methane pyrolysis in a shock tube*” and submitted to **Carbon journal**, and it is focused on using Omnisoot to identify different stages of CB formation during methane pyrolysis in a shock-tube.

Despite extensive studies on the chemical kinetics of methane pyrolysis (Refs. in [47]), the mechanisms governing CB formation remain poorly understood. This limitation arises from incomplete knowledge of the pathways leading to CB inception and from uncertainties in existing kinetic mechanisms [4]. These uncertainties originate with methane dissociation reactions [181] and propagate through key intermediates such as methyl (CH_3) [184], ethylene (C_2H_4), and acetylene (C_2H_2) [154]. The uncertainty is further amplified for polycyclic aromatic hydrocarbons (PAHs) [132], which are widely accepted as the primary precursors to soot and CB [7]. Previous studies have shown that predicted concentrations of large PAHs can vary by orders of magnitude depending on the kinetic mechanism employed [185]. This variability underscores the need for time-resolved measurements of gas-phase species and particulate properties under well-controlled conditions to improve quantitative understanding of methane conversion, intermediate formation, and carbon flux to CB through inception and surface growth.

Shock tubes are powerful tools for this purpose because a wide range of temperatures (1700-3000 K [4]) and pressures (1-100 atm [159]) can be achieved by adjusting the pre-shock pressure ratio; the instant heating of the mixture behind the reflected shock creates a nearly isothermal and isobaric condition over a short test time (1-3 ms) with minimal diffusion and mixing [45], which is an ideal setting for kinetic studies of pyrolysis pathways and CB inception and surface growth.

Capturing the rapid decomposition of methane and the subsequent formation of intermediates can be achieved with the high temporal resolution offered by continuous-wave (CW) laser absorption spectroscopy [142]. In this technique, the attenuation of light in an absorbing medium is related to the gas density through the Beer–Lambert law, provided that the absorption cross-section is known. Accurate application, however, is complicated by the strong dependence of the absorption cross-section on temperature, pressure, and gas composition. CB yield and volume fraction can also be quantified with good accuracy from light extinction measurements based on the same principle, as long as the particles remain in the Rayleigh limit and the particle volume fraction is below 10 ppm [45]. This approach requires prior knowledge of the optical properties of CB, represented by the absorption function $E(m)$.

While a constant $E(m)$ value of mature CB is commonly used to retrieve volume fractions from extinction data [36, 4, 173], the optical properties are noticeably different for incipient and mature CB [119]. During maturation, CB particles undergo structural and chemical changes that result in the reduction of hydrogen-to-carbon ratio (H/C) due to carbonization [96] that increases the density and specific heat [119]. The maturity level of CB is linked to the spectral dependence of absorption [18] quantified by the ratio of $E(m)$ at two different wavelengths [198] that approaches unity for mature CB; therefore, performing extinction measurements at multiple wavelengths can reduce the uncertainties of $E(m)$ and provide a good measure of CB maturity.

This section deals with simultaneous measurements of gaseous species and carbon black (CB) during the pyrolysis of 5% CH₄ at post-reflected-shock pressures near 5 atm and temperatures between 1800 and 2500 K. In that work, a computational framework coupling detailed gas-phase chemistry with CB inception, surface growth, and coagulation is developed to describe methane-to-CB conversion, successfully reproducing the measured time histories of key gas-phase species and CB volume fraction, as well as the final primary particle diameter. A detailed analysis of the simulation results, complemented by experimental measurements, is conducted to delineate distinct stages of CB formation based on the time evolution of f_v and carbon yield. Within each stage, the evolution of inception flux and surface growth mechanisms is examined to elucidate their influence on f_v , yield, and morphology, as well as their coupling with gas-phase chemistry. The deviation of model predictions from f_v , d_p , and induction time measurements are discussed in detail. Particular emphasis is placed on the role of carbonization in describing CB maturity, its effect in limiting surface growth rates, and its connection to the spectral dependence of CB particles characterized through multi-wavelength light extinction.

4.2.1 Experimental methods

A brief overview of the employed experimental techniques is presented here. Mole fraction time histories of methane (CH₄), acetylene (C₂H₂), and ethylene (C₂H₄) were captured using CW laser absorption at 3.365 μm , 2.998 μm , and 10.532 μm , respectively [167, 142, 28]. CB volume fraction was measured using laser light extinction at $\lambda=633$ nm and 1064 nm:

$$f_v = \frac{1}{L} \frac{\ln(I_0/I_t)\lambda}{6\pi E(m)}, \quad (4.1)$$

where $L=14.12$ cm is the absorption path length, equal to the inner diameter of the shock tube. λ is the absorption wavelength, and I_0 and I_t are the incident and

Table 4.5 The post-reflected-shock pressure (P_5) and temperature (T_5) of the executed shock-tube tests.

	(1)	(2)	(3)	(4)	(5)	(6)	(7)
T_5 [K]	1875	1984	2132	2203	2247	2322	2355
P_5 [atm]	4.45	4.30	4.17	4.90	4.51	4.55	4.64

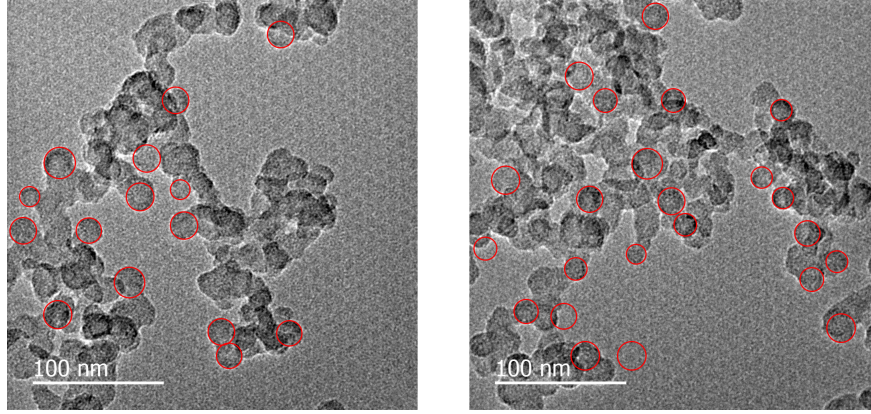


Fig. 4.15 Samples of TEM images collected for $T_5=2203$ K. Red circles represent the identified primary particles used to measure d_p .

transmitted intensities, respectively. Table 4.5 indicates the conditions of the shock-tube tests with $1800 \text{ K} < T_5 < 2400 \text{ K}$ and $P_5 = 4.5 \pm 0.5 \text{ atm}$. f_v was determined from the measured extinction at 633 nm and 1064 nm, considering the reported variability of $E(m)$ in the literature, ranging from 0.174 [103] to 0.26 [34] for 633 nm and from 0.2 to 0.3 for 1064 nm [20].

Additionally, CB samples were collected onto imaging stubs mounted in the shock-tube endwall. Samples were extracted from the interior surface of the shock tube endwall after each experiment to allow for imaging and analysis of the particulates. TEM images were recorded with a FEI Tecnai G2 F20 X-TWIN microscope and Gatan SC200 camera for all test cases. Primary particle diameter, d_p , was obtained by visually identifying the smallest circumscribed circle enclosing each primary particle in the TEM images and calculating the arithmetic and geometric means. A minimum of 200 primary particles were measured for each condition. Fig. 4.15 depicts representative TEM images collected for the test at $T_5=2203$ K, with identified primary particles shown as superimposed red circles.

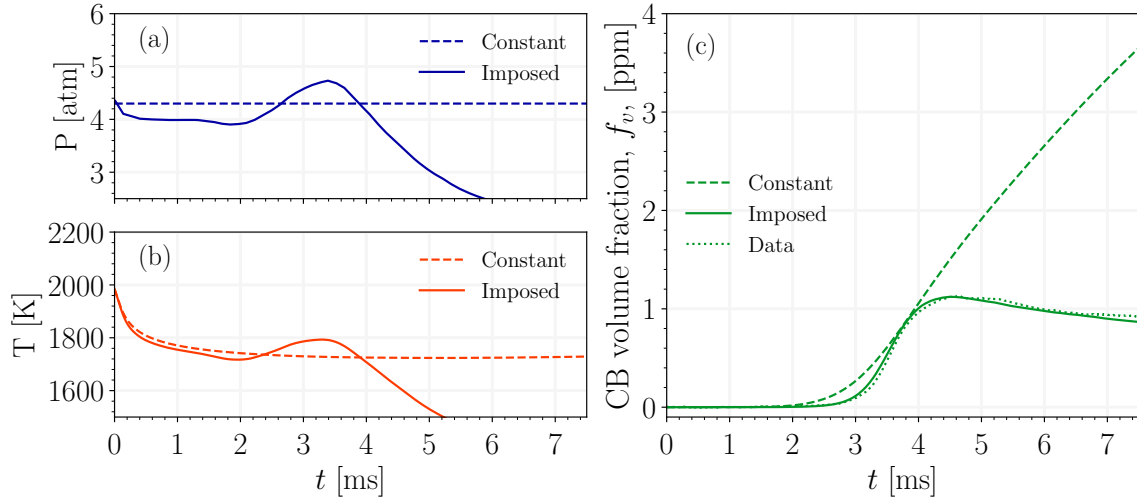


Fig. 4.16 The comparison of (a) pressure (b) temperature (c) CB volume fraction for simulations with constant and imposed pressure trace at $T_5=1984$ K.

4.2.2 Numerical model

The 0-D imposed-pressure reactor (IPR) model of Omnisoot [3] was used to simulate CB formation coupled with chemical kinetics during the pyrolysis process under post-reflected-shock conditions in the shock tube. IPR incorporates a sectional population balance model (SPBM) to describe the evolving size distribution of CB agglomerates by tracking the number of agglomerates, N_{agg} , primary particles, N_{pri} , total carbon, C_{tot} , and hydrogen content, H_{tot} .

The measured pressure trace was filtered to reduce noise and fluctuations, and then imposed on the model. The measured pressure remains within 10% of the initial value until 2 ms for all tests. Fig. 4.16a highlights the deviation of the (filtered) pressure time history from the initial pressure of $P_5=4.30$ atm at $T_5=1984$ K. The pressure starts to rise at ≈ 2.2 ms, reaches its peak at ≈ 3.1 ms, and drops towards the end of the test time due to the arrival of the expansion wave. Fig. 4.16b shows a similar deviation in the predicted temperature. The analysis of species mole fractions showed that the imposed pressure results in lower CH_4 conversion and C_2H_2 yield, thereby reducing PAH formation and CB inception flux. As shown in Fig. 4.16c, f_v values predicted using constant and imposed pressure are close until 3.9 ms, but the discrepancy grows after that, where only the simulation with the imposed pressure captures the experimental time trends.

Soot precursors considered in this study include naphthalene (A2), phenanthrene (A3), pyrene (A4), acenaphthylene (A2R5), acephenanthrylene (A3R5), and cyclopent-

tapylene (A4R5), due to extensive support in the literature for their role in the initial steps of CB formation [117, 110]. The E-Bridge Modified model is used to describe the dimerization and adsorption of precursors that contribute to CB inception and surface growth, respectively. The general formulation of the model is based on the inception model proposed by Frenklach and Mebel [54], with some modifications detailed in [3]. Two scaling factors, η_{inc} and η_{ads} , between 0 and 1 are used to adjust the inception and PAH adsorption rates, respectively [3].

The surface growth is described by the H-abstraction- C_2H_2 /Carbon-addition (HACA) scheme [8], but the surface density of hydrogenated sites, χ_{soot-H} , is dynamically calculated as the ratio of hydrogen content to the surface area of agglomerates, i.e., $\chi_{soot-H} = H_{tot}/A_{tot}$ [22]. An Arrhenius equation is used to account for the loss of hydrogen by the carbonization of CB particles as [14]:

$$k_{carb} = A_{carb} \cdot \exp\left(\frac{-E_{carb}}{RT}\right), \quad (4.2)$$

$$\left(\frac{dH_{tot}}{dt}\right)_{carb} = -k_{carb} \cdot H_{tot}, \quad (4.3)$$

where A_{carb} and E_{carb} are the exponential prefactor and activation energy for carbonization, respectively. H_{tot}/A_{tot} depends on the relative contributions of PAH adsorption and HACA, and the carbonization rate. The comparison of χ_{soot-H} with its nominal value of 2.3×10^{19} sites/ m^2 used in the original HACA formulation [55] shows that the dynamic method strongly depends on the temperature time history, and it predicts an overall larger number of reaction sites for $T_5 < 2300$ K (Fig. A.7).

4.2.3 Precursor chemistry

A detailed discussion of the time histories of measured species was presented in our previous work [58]. The performance analysis of six kinetic mechanisms indicated that FFCM2 [201] provides the best agreement across the entire temperature range, especially for CH_4 conversion and C_2H_2 yield, but it does not include PAH chemistry necessary for inception and surface growth, so it cannot be used for soot modeling. As shown in Fig. 4.17a and b, the CRECK mechanism predicts CH_4 and C_2H_2 mole fractions in close agreement with the measurements, considering their uncertainty range. CRECK includes the PAH chemistry necessary for CB inception and surface growth. Fig. 4.17c and d depict the mole fractions of A2 and A2R5, which similarly increase with time. For $T_5 > 2200$ K, the mole fraction of PAHs reaches its peak and

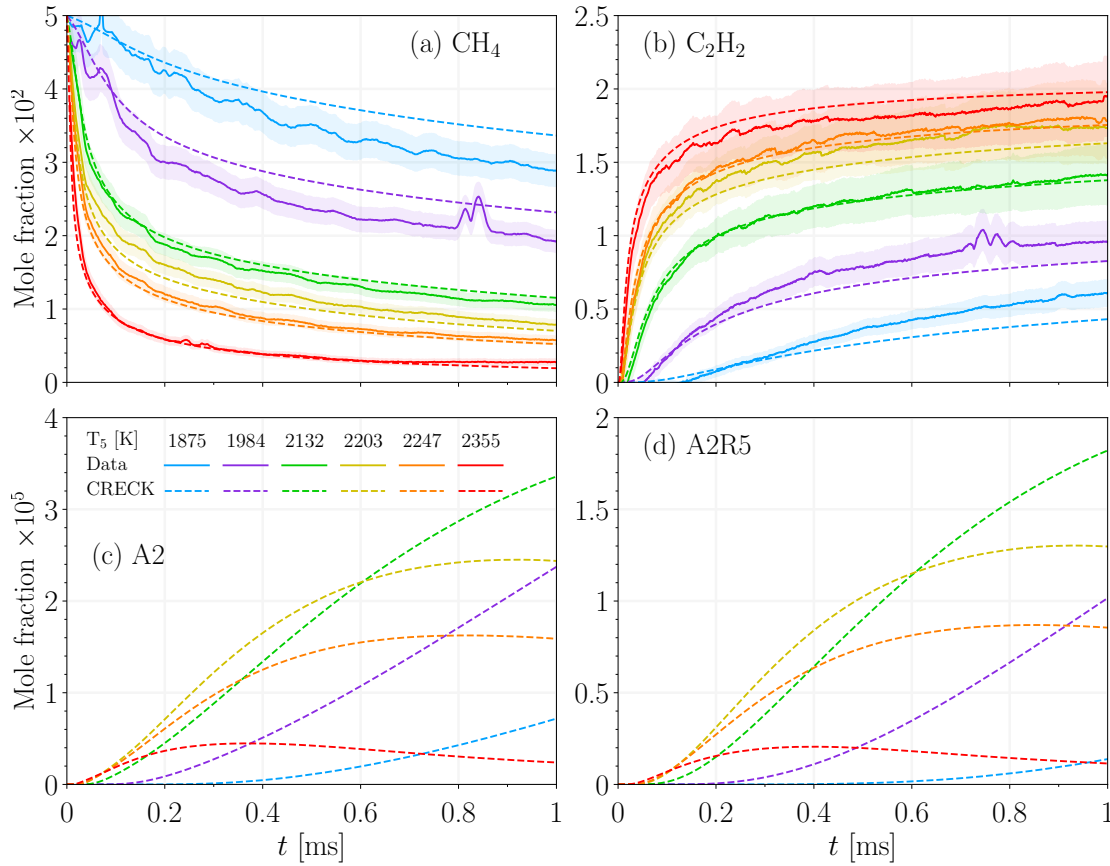


Fig. 4.17 The time history of (a) CH_4 and (b) C_2H_2 predicted using CRECK mechanisms in close agreement with the laser absorption measurements. The shaded area represents the uncertainty in the measurements.

gradually decreases within 1 ms, primarily due to conversion to C_2H_2 rather than CB inception. The mole fraction of A2 and A2R5 sampled at 1 ms follows the well-known bell-shaped behavior with the peak near 2200 K. The analysis of the carbon mass fraction (CMF) of precursors over the studied T_5 range indicated that A2 and A2R5 are the major contributors to CB inception due to their larger CMFs compared to the other precursors. The initial composition of CB is dictated by the H/C ratio of constituent precursors, which changes within a narrow range, slightly decreasing from 0.8 at 1875 K to 0.67 at 2355 K.

4.2.4 Stages of CB formation

As shown in Fig. 4.18a, the optimized model reproduces the time evolution of f_v measured using 1064 nm light extinction at 1984 K. The reported f_v measurements are the average of values calculated using the min and max $E(m)$ of each wavelength. The

predicted f_v profile exhibits four distinct stages: (I) an initial period with negligible CB mass due to low inception and surface growth, known as the CB induction time, which is slightly overestimated by the model (≈ 2.3 ms) compared to the measurements (≈ 1.9 ms). A detailed discussion of induction time over the entire T_5 range is provided in Section 4.2.5. In stage (II), rapid growth occurs in f_v , driven by increasing PAH adsorption and HACA. The end of stage (II) signifies the inflection point in f_v , where both surface growth mechanisms reach their peak, as shown in Fig. 4.18b. At 1984 K, PAH adsorption is the dominant surface growth, accounting for nearly 79% of total CB mass by 7.5 ms, and the rest ($\approx 21\%$) originates from HACA. Inception is mainly active in stages (I) and (II), and its contribution to total CB mass remains less than 0.3%. In stage (III), the increase of f_v slows down due to the decline in both surface growth mechanisms. The time histories of f_v and carbon yield, CY, are similar in the first two stages, but f_v deviates from CY in stage (III). While f_v gradually decreases at $t \approx 4.6$ ms, CY gradually increases to reach 14.3%. The decline of $f_v = V_{CB}/V_{gas}$ at ≈ 4.56 ms is attributed to gas-phase expansion caused by the arrival of the expansion wave at the endwall, reducing pressure (Fig. 4.16a) and increasing V_{gas} while V_{CB} remains constant.

In stage (IV), surface growth rates become negligible, and CB agglomerates are chemically frozen, growing primarily through Brownian coagulation. As shown in Fig. 4.18c, CB morphology undergoes a corresponding transition. Here, d_p and d_m denote the average primary particle diameter and mobility diameter, respectively. These diameters remain identical until approximately 3 ms, near the peak of inception in stage (II), when most CB particles are spherical. Beyond 3 ms, the growth of d_p slows and reaches 99% of its terminal value of 14.4 nm before the end of stage (II) at approximately 5.89 ms, while d_m continues to increase due to ongoing coagulation.

The rapid decline in inception rates (Fig. 4.18b) is primarily driven by the consumption of precursors through PAH adsorption, as evidenced by a factor of 2.3 decrease in their CMF between approximately 3 ms and 4.5 ms (Fig. 4.18c). Beyond 4.5 ms, PAH adsorption decreases as the temperature falls below 1600 K, which suppresses PAH dehydrogenation in the E-Bridge Modified model [3] and reduces the availability of PAH radicals for adsorption onto CB particles. Consequently, the CMF of precursors continues to decline after 4.5 ms and approaches 0.172 by the end of stage (III).

The reduction in HACA rates during stage (III) is mainly caused by a temperature-driven decrease in H radical concentration, which lowers the number of dehydrogenated surface sites, χ_{soot° , in the HACA formulation [8]. In addition, depletion of hydrogenated surface sites due to CB carbonization suppresses HACA rates throughout the simulation.

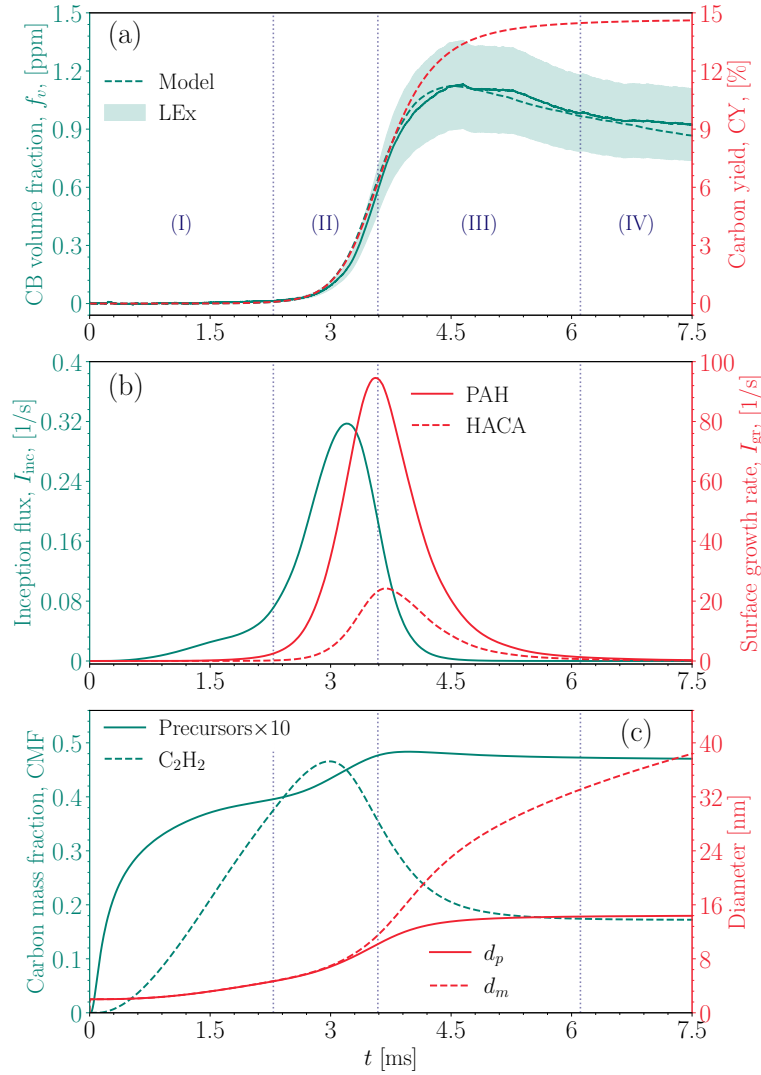


Fig. 4.18 The four stages of CB formation demonstrated at $T_5 = 1984$ K for (a) CB volume fraction, f_v , and carbon yield, CY (b) surface growth rate, I_{gr} , via HACA and PAH adsorption, and inception flux; (c) the carbon mass fraction, CMF, of C_2H_2 and CB precursors combined, and primary particle diameter, d_p , and mobility diameter d_m , of CB agglomerates. Panel (a) depicts the light extinction measurements at $\lambda = 1064$ nm with the shaded area representing the uncertainty from the variability in $E(m)$.

Simulations performed without carbonization indicate an overprediction of the peak HACA rate by a factor of 2.4 and an overestimation of the final carbon yield by 46%. While carbonization reduces the magnitude of the HACA rate, it does not affect the timing of its peak. Accordingly, the four stages identified in Fig. 4.18 remain unchanged by carbonization.

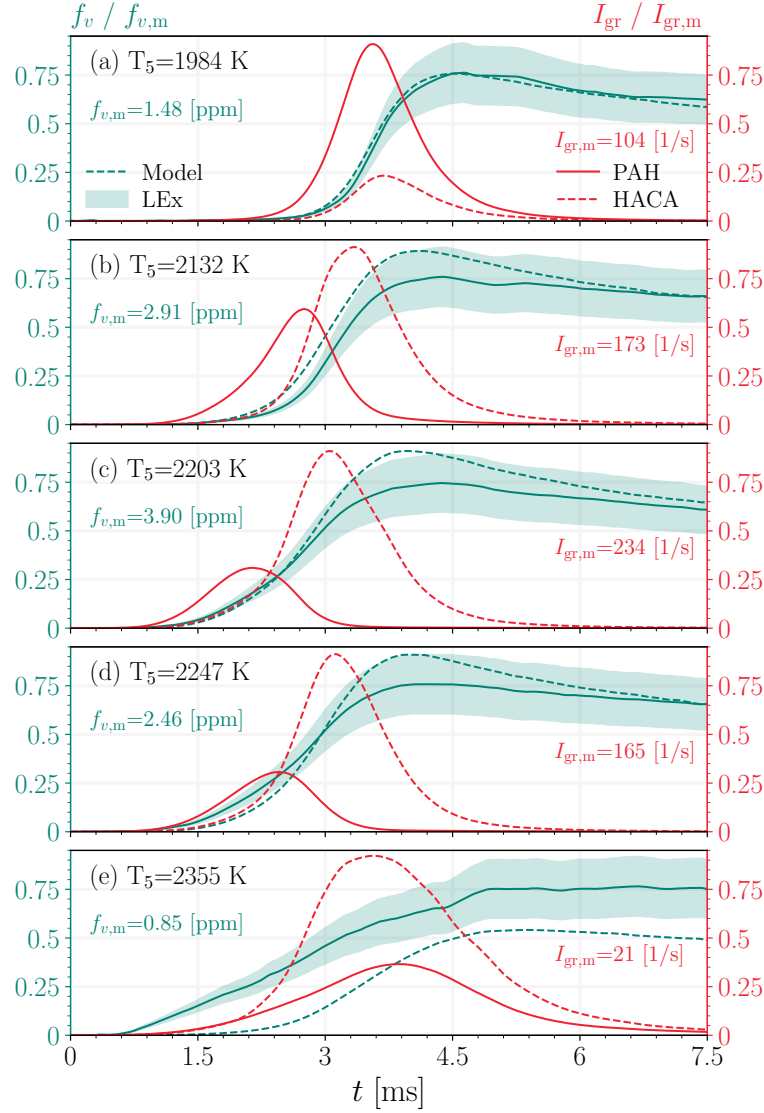


Fig. 4.19 The time histories of normalized CB volume fraction, $f_v/f_{v,m}$ and normalized surface growth, $I_{gr}/I_{gr,m}$ at various temperatures. The measurements are from light extinction at $\lambda = 1064$ nm with the shaded area representing the uncertainty from the variability in $E(m)$.

Fig. 4.19 depicts the normalized CB volume fraction, $f_v/f_{v,m}$, and surface growth rate $I_{gr}/I_{gr,m}$ for the entire studied T_5 range. The time history of f_v is predicted by the model for the entire T_5 range in good agreement with light extinction measurements, considering the sensitivity of f_v to the pressure trace. The measured f_v demonstrates that the onset of CB formation occurs earlier for higher T_5 . In other words, stage (I) becomes shorter with increasing T_5 . The model captures this shift from 1984 K to 2203 K, but noticeably predicts longer CB induction times at 2247 K and 2355 K

compared to the measurements. The behavior of the model is dictated by precursor chemistry. PAH concentration has a bell-shaped temperature dependence with the peak at $T_5=2203$ K. Therefore, the inception and PAH adsorption rates decrease when T_5 increases to 2247 K and 2355 K.

HACA becomes the dominant surface growth mechanism for $T_5 > 1984$ K, as indicated by its higher peak compared to PAH adsorption. The analysis of integrated surface growth rates indicates that the contribution of HACA to the total carbon mass of CB increases from 21% at 1984 K to 64% at 2132 K and 77% at 2203 K due to the increase in the inception flux producing more particles (active growth sites) and higher C_2H_2 concentration (Fig. 4.17b). However, the contribution of HACA slightly decreases to 75% and 69% for 2247 K and 2355 K, respectively, because the suppression of HACA by carbonization increases with temperature. Without carbonization, carbon yield reaches $\approx 100\%$ for $T_5 \geq 2132$ K with HACA accounting for more than 90% of carbon mass.

As shown in Fig. 4.20, d_p starts from 2 nm, which is the diameter of incipient CB defined in the model, increases through surface growth, and asymptotically approaches its final value, $d_{p,\infty}$. The characteristic time $\tau_{d_{p,\infty}}$, defined as the time at which d_p reaches 99% of $d_{p,\infty}$, remains below 6 ms for all T_5 . These results indicate that no significant evolution of the primary particle diameter occurs beyond $\tau_{d_{p,\infty}}$. Therefore, d_p measured from collected TEM samples provides a representative measure of CB morphology within the studied time window. The predicted $d_{p,\infty}$ is in close agreement with the measurement, except for a noticeable underprediction at $T_5=1984$ K. $d_{p,\infty}$ varies in a narrow range of 14-21 nm across various conditions. Primary particles have a relatively narrow size distribution; the standard deviation of d_p increases due to persistent inception and surface growth, reaches a maximum of 3.8 nm, and finally converges to ≈ 1.5 nm. Table 4.6 lists arithmetic and geometric means and their corresponding standard deviations for the primary particle diameter computed from TEM measurements and model predictions. The difference between arithmetic (d_p) and geometric ($d_{p,g}$) remains less than 0.8% across various conditions.

4.2.5 The effect of temperature

The CB induction time (τ_{ind}) is defined as the time extinction level exceeds the noise floor, and it provides a measure of the earliest detectable CB mass and avoid effects of pressure gradients at later times. The noise floor is $f_v E(m) = 2 \times 10^{-9}$, or $f_v \approx 8$ ppb (set by beam steering effects). Fig. 4.21 demonstrates the predicted τ_{ind} along with the measurements at 1064 nm and 633 nm that closely follow an Arrhenius-like behavior,

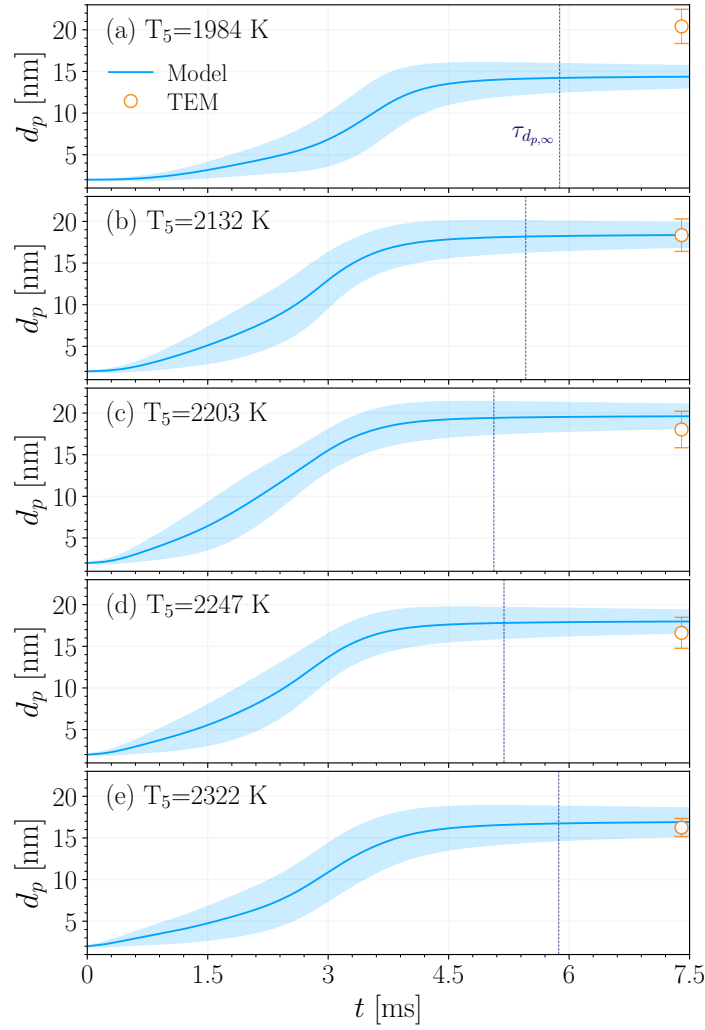


Fig. 4.20 The time histories of average primary particle diameter, d_p compared with TEM measurement. The shaded area, and error bar represents the d_p arithmetic standard deviation from the simulations and measurements, respectively. The dashed line specifies the time when d_p reaches 99% of its final value.

expressed as $\tau_{ind} = A_{ind} \exp(E_{ind}/RT)$ [5], where E_{ind} is defined as the activation energy of CB inception. The value of E_{ind} is ≈ 130 kJ for both wavelengths, consistent with the range suggested in the literature [45], but 1064 nm measurements result in longer induction times. τ_{ind} obtained from 633 nm measurements are in agreement with the measurements by Agafonov et al. [5] for 5% CH_4 using the same wavelength. The observed difference in τ_{ind} between two wavelengths is due to higher absorbance at 633 nm, which has been attributed to the non-negligible contribution of large PAHs to absorption at 633 nm [199]. In fact, Migliorini et al. [122] showed that the absorption

Table 4.6 The primary particle diameter measurements from TEM images. d_p is arithmetic mean, $d_{p,g}$ geometric mean, σ_p arithmetic standard deviation, and $\sigma_{p,g}$ geometric standard deviation.

	d_p [nm]		$d_{p,g}$ [nm]		σ_p [nm]		$\sigma_{p,g}$	
T_5 [K]	TEM	Model	TEM	Model	TEM	Model	TEM	Model
1984	20.4	14.4	20.3	14.3	2.1	1.3	1.10	1.10
2132	18.3	18.4	18.3	18.3	2.0	1.5	1.11	1.08
2203	18.0	19.6	17.9	19.6	2.2	1.5	1.13	1.08
2247	16.6	18.0	16.5	17.9	1.9	1.4	1.12	1.08
2322	16.3	16.9	16.2	16.8	1.1	1.7	1.07	1.11

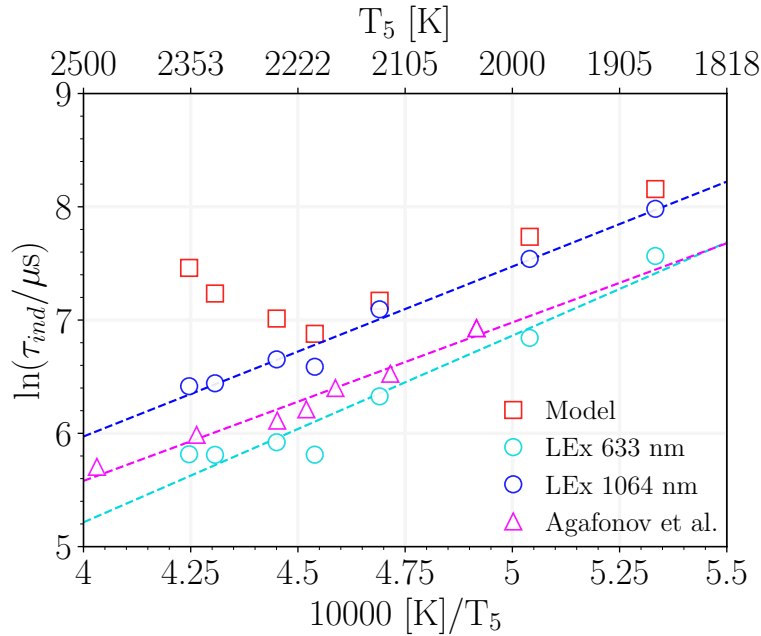


Fig. 4.21 The predicted CB induction time, τ_{ind} , compared with light extinction measurements at 633 nm and 1064 nm, and with the data from Agafonov et al. [5]. The dashed line is the Arrhenius fit to the measurements.

of gaseous species extends up to 700 nm. However, PAHs smaller than circumcoronene ($C_{54}H_{10}$) are not likely to absorb in wavelengths above 550 nm [16].

The model closely reproduces the experimental trends in the low-to-mid temperature range (1800 K-2200 K), but deviates from the measurements for $T_5 > 2200$ K. In fact, the model predicts an inverse temperature dependence for τ_{ind} relative to PAH concentration, reaching a minimum near the temperature of maximum PAH abundance (≈ 2200 K) and increasing at higher temperatures where PAH concentrations decline.

The carbon yield at τ_{ind} is close to 0.1% for $T_5 \geq 1984$ K. The analysis of simulations results at τ_{ind} suggests that inception accounts for 4.5%-6.7% of total CB mass, while the contribution of PAH adsorption decreases from 88% at $T_5 = 1875$ K and 1984 K to 50% at 2355 K. Therefore, the majority of carbon mass at τ_{ind} originates from precursors that exhibit a bell-shaped temperature dependence. Further analysis suggests that carbonization prolongs the induction time by suppressing HACA rates, but does not alter the temperature dependence of τ_{ind} (Fig. A.8). Additional simulations were conducted to assess the sensitivity of τ_{inc} to precursor selection, in which individual PAHs in the CRECK mechanism were treated separately as the sole precursor. All PAHs produced a similar inverted bell-shaped temperature dependence of τ_{inc} , as shown in Fig. 4.21.

As shown in Fig. 4.22, a bell-shaped temperature dependence of f_v is observed in the light extinction measurements at 633 nm and 1064 nm at 2, 3, 4, and 5 ms. As discussed earlier, larger f_v values are inferred at 633 nm across the studied T_5 range due to stronger absorption at this wavelength compared to 1064 nm. The temperature dependence of f_v is primarily governed by that of CB precursors (Fig. A.9) and evolves with time without significant changes in its overall shape, with the peak remaining consistently at $T_5 = 2203$ K. The model reproduces this temperature dependence in close agreement with the measurements. However, at 2 ms, the model noticeably underpredicts f_v for $T_5 > 2203$ K, consistent with the overestimation of induction time in this temperature range. This discrepancy may be attributed to missing chemical pathways for PAH formation at high temperatures, which would otherwise accelerate inception and PAH adsorption [188].

Fig. 4.23 reveals a significant discrepancy between the predicted and measured temperature dependence of d_p . While the TEM measurements exhibit a decreasing trend with increasing T_5 , the model predicts a bell-shaped profile similar to that of f_v , with a peak at 2203 K. No data point was obtained for TEM at $T_5 = 1875$ K because the collected particles appear as compact carbonaceous lumps with poorly defined boundaries between primary particles rather than chain-like aggregates (Fig. A.13), which makes the identification of individual primary particles by visual inspection highly uncertain. Nevertheless, some identifiable structures are close to 30 nm, supporting the consistently decreasing trend in d_p inferred from the TEM measurements.

The significant underprediction of d_p at 1984 K, despite the close agreement in the predicted and measured f_v time histories (Fig. 4.18a), can be attributed to the coalescence of primary particles, which increases d_p but is not accounted for in the model. Higher temperatures promote the formation of turbostratic graphite-like order,

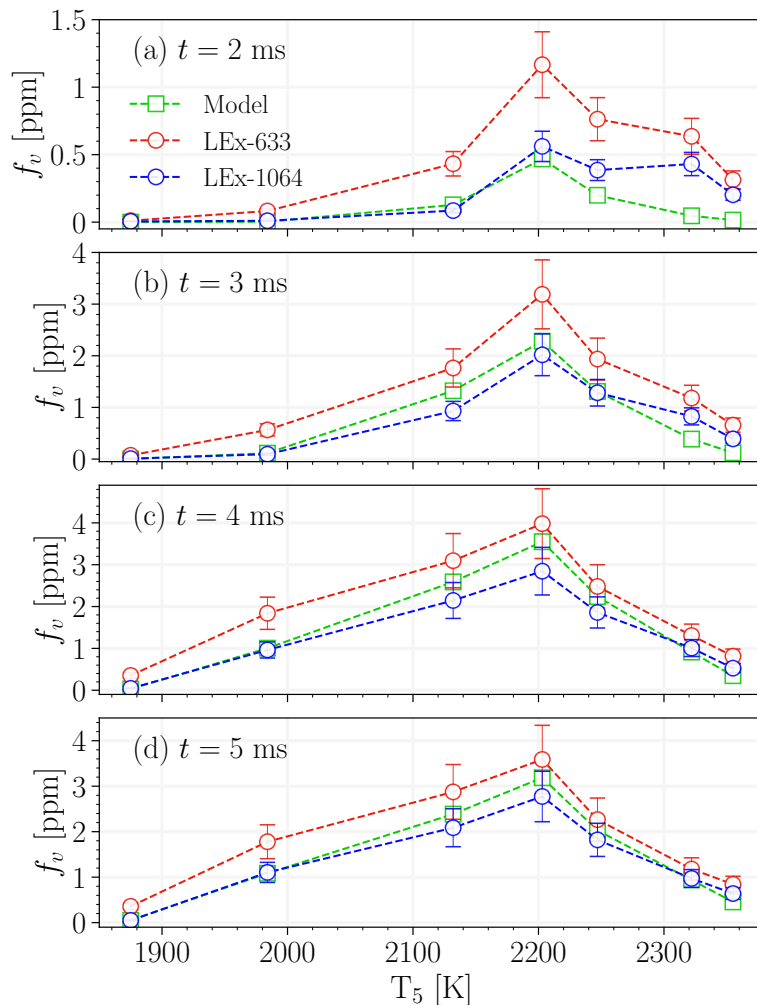


Fig. 4.22 The CB volume fraction, f_v , from light extinction at $\lambda = 633$ nm sampled at 2 ms (a), 3 ms (b), 4 ms (c), and 5 ms and compared with the simulation results for $T_5 = 1875, 1984, 2132, 2203, 2247, 2355$ K. Errors bars indicate experimental uncertainty due to variability in $E(m)$, and the dashed line is added to show the trends.

which inhibits complete merging of particles [79]. At the same time, coalescence alters particle surface area and therefore affects surface growth via HACA, which in turn influences f_v predictions.

In addition, condensation of residual aromatic species beyond 7.5 ms may further contribute to larger primary particle sizes. An upper limit for the increase in d_p was estimated for all conditions by assuming that (i) all residual species containing six or more carbon atoms, equivalent to benzene and larger species, are converted to CB and (ii) the total number of primary particles (N_{pri}) remains constant. The revised d_p was calculated as [3]:

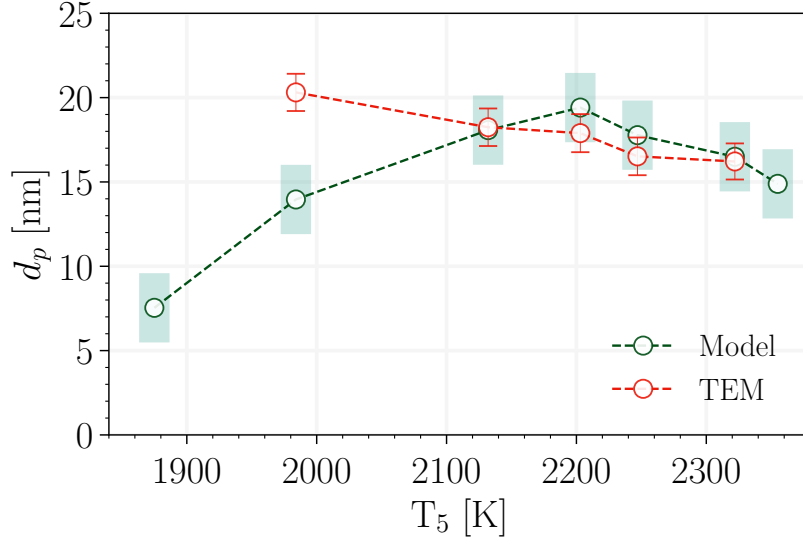


Fig. 4.23 The final primary particle diameter, d_p , from TEM measurements compared with the model predictions.

$$d_p = \left(\frac{6W_{carbon}}{\pi\rho_{soot}} \frac{C_{tot} + C_{6\geq}}{N_{pri} \cdot Av} \right)^{1/3}, \quad (4.4)$$

where C_{tot} is the total carbon mass of CB gained through surface growth mechanisms, and $C_{6\geq}$ is the total carbon mass in benzene and larger species. Under these assumptions, d_p increases to 25.6 nm at 1875 K from 7.5 nm and to 16.6 nm at 1984 K from 14 nm, whereas the increase at higher T_5 remains below 1 nm (Fig. A.10) resulting in a decreasing temperature dependence similar to the profile obtained from TEM measurements.

Fig. 4.24a depicts the maturity index, β , inferred from the extinction ratio at 633 nm and 1064 nm [198] as

$$\beta = \ln \left(\frac{E(m, \lambda_{633})}{E(m, \lambda_{1064})} \right) / \ln \left(\frac{\lambda_{1064}}{\lambda_{633}} \right). \quad (4.5)$$

The progression from high to low β with increasing time reflects the transformation of CB from disordered PAH clusters to particles with concentric graphitic layers. This structural evolution is accompanied by chemical carbonization, manifested as a decrease in the Hydrogen-to-Carbon (H/C) ratio due to dehydrogenation [29]. As shown in Fig. 4.24b, β exhibits strong qualitative agreement with the predicted H/C ratio of CB particles in both time history and temperature dependence. In all cases, both quantities show an initial rapid decline whose rate increases with T_5 , followed by a slower decrease

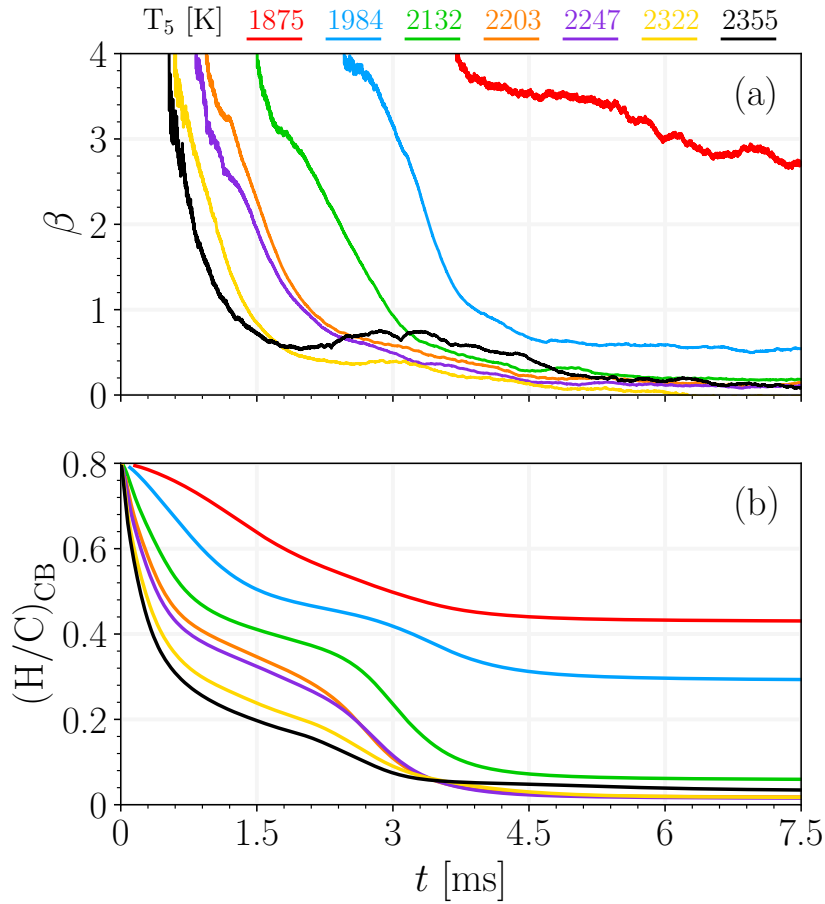


Fig. 4.24 The evolution of (a) maturity index, β , obtained from extinction measurements at 633 nm and 1064 nm, and (b) the predicted H/C ratio of CB particles at various T_5 .

toward asymptotic values ≈ 0 , indicating increasing CB maturity and weak spectral dependence. Notably, the β and H/C profiles at 1875 K and 1984 K converge to higher final values than those at $T_5 \geq 2132$ K, indicating incomplete carbonization and lower structural ordering under these conditions. In contrast, the higher- T_5 cases approach similar late-time values, suggesting that once a threshold temperature is exceeded, CB maturity becomes relatively insensitive to further increases in T_5 within the studied range.

4.2.6 Conclusions

The present work provides a combined numerical and experimental investigation of CB formation during shock-tube pyrolysis of 5% CH_4 in argon at a post-reflected-shock pressure of $P_5 = 4.5 \pm 0.5$ atm and temperatures spanning $1800 \text{ K} < T_5 < 2500 \text{ K}$. Multi-wavelength laser diagnostics were employed to measure the time-resolved mole

fractions of CH_4 , C_2H_4 , and C_2H_2 . The CB volume fraction, f_v , was determined using light extinction at 633 nm and 1064 nm, while collected TEM images were analyzed to extract the primary particle diameter, d_p , as a quantitative measure of CB morphology. Simulations using the CRECK mechanism accurately reproduced methane conversion and acetylene yields. The gas-phase chemistry solver was coupled with a sectional population balance model that accounts for CB inception, surface growth, and the reduction in H/C due to carbonization.

Simultaneous calibration of the model using both f_v and d_p provided strong constraints on inception, PAH adsorption, HACA surface growth, and carbonization rates, highlighting the importance of morphology data in avoiding non-unique calibrations based solely on f_v . The model reproduced the time history of f_v and the final d_p in good agreement with the measurements. Four stages of CB evolution were identified: (I) an induction period dominated by precursor formation, (II) rapid increase in f_v driven by rising surface growth rates, (III) transition toward final yield, composition, and d_p as surface growth wanes, and (IV) a coagulation-dominated stage in which primary particle diameters are chemically frozen while the agglomerate mobility diameter continues to increase.

The analysis showed that PAH adsorption dominates CB mass growth at lower temperatures and early times, whereas HACA becomes the primary contributor with increasing T_5 . The model reproduced the bell-shaped temperature dependence of f_v but overpredicted induction times at $T_5 > 2200$ K, suggesting the presence of missing high-temperature PAH formation pathways that would accelerate inception and PAH adsorption. TEM measurements revealed a decreasing trend in primary particle diameter with increasing T_5 , while the model predicted a bell-shaped dependence. The discrepancy at 1984 K was attributed to possible late-time condensation of residual aromatics.

The maturity index, β , inferred from the extinction ratio at 633 nm and 1064 nm, exhibited strong similarities to the predicted H/C ratio of CB particles, which is used in the model as a measure of surface reactivity. Both β and H/C decrease rapidly at early times before approaching near-asymptotic values, with the rate of the initial decline increasing with T_5 .

References

- [1] Abid, A. D., Camacho, J., Sheen, D. A., and Wang, H. (2009). Quantitative measurement of soot particle size distribution in premixed flames—the burner-stabilized stagnation flame approach. *Combustion and Flame*, 156(10):1862–1870.
- [2] Abid, A. D., Heinz, N., Tolmachoff, E. D., Phares, D. J., Campbell, C. S., and Wang, H. (2008). On evolution of particle size distribution functions of incipient soot in premixed ethylene–oxygen–argon flames. *Combustion and Flame*, 154(4):775–788.
- [3] Adib, M., Kazemi, S., and Kholghy, M. R. (2026). Omnisoot: a process design package for gas-phase synthesis of carbonaceous nanoparticles. *Combustion and Flame*, 285:114758.
- [4] Agafonov, G., Biler, I., Vlasov, P., Zhil'tsova, I., Kolbanovskii, Y. A., Smirnov, V., and Tereza, A. (2016). Unified kinetic model of soot formation in the pyrolysis and oxidation of aliphatic and aromatic hydrocarbons in shock waves. *Kinetics and Catalysis*, 57:557–572.
- [5] Agafonov, G., Borisov, A., Smirnov, V., Troshin, K. Y., Vlasov, P., and Warnatz, J. (2008). Soot formation during pyrolysis of methane and rich methane/oxygen mixtures behind reflected shock waves. *Combustion science and technology*, 180(10-11):1876–1899.
- [6] Agafonov, G., Vlasov, P., and Smirnov, V. (2011). Soot formation in the pyrolysis of benzene, methylbenzene, and ethylbenzene in shock waves. *Kinet. Catal.*, 52:358–370.
- [7] Alfè, M., Apicella, B., Barbella, R., Rouzaud, J.-N., Tregrossi, A., and Ciajolo, A. (2009). Structure–property relationship in nanostructures of young and mature soot in premixed flames. *Proceedings of the Combustion Institute*, 32(1):697–704.
- [8] Appel, J., Bockhorn, H., and Frenklach, M. (2000). Kinetic modeling of soot formation with detailed chemistry and physics: laminar premixed flames of c2 hydrocarbons. *Combustion and flame*, 121(1-2):122–136.
- [9] Araki, Y., Matsukawa, Y., Saito, Y., Matsushita, Y., Aoki, H., Era, K., and Aoki, T. (2021). Effects of carrier gas on the properties of soot produced by ethylene pyrolysis. *Fuel Processing Technology*, 213:106673.
- [10] Association, I. C. B. et al. (2016). Carbon black user’s guide. *available at www.carbon-black.org*.

- [11] Aubagnac-Karkar, D., El Bakali, A., and Desgroux, P. (2018). Soot particles inception and pah condensation modelling applied in a soot model utilizing a sectional method. *Combustion and Flame*, 189:190–206.
- [12] Bansal, R. C., Wang, M.-J., and Donnet, J. (1993). Carbon black. *Science and Technology*, 133.
- [13] Bartok, W. and Sarofim, A. F. (1991). Fossil fuel combustion: a source book.
- [14] Basile, G., Rolando, A., D’Alessio, A., D’Anna, A., and Minutolo, P. (2002). Coagulation and carbonization processes in slightly sooting premixed flames. *Proceedings of the Combustion Institute*, 29(2):2391–2397.
- [15] Bejaoui, S., Batut, S., Therssen, E., Lamoureux, N., Desgroux, P., and Liu, F. (2015). Measurements and modeling of laser-induced incandescence of soot at different heights in a flat premixed flame. *Applied Physics B*, 118:449–469.
- [16] Bejaoui, S., Mercier, X., Desgroux, P., and Therssen, E. (2014). Laser induced fluorescence spectroscopy of aromatic species produced in atmospheric sooting flames using uv and visible excitation wavelengths. *Combustion and Flame*, 161(10):2479–2491.
- [17] Berger, F. and Hau, K.-F.-L. (1977). Mass transfer in turbulent pipe flow measured by the electrochemical method. *International Journal of Heat and Mass Transfer*, 20(11):1185–1194.
- [18] Bescond, A., Yon, J., Ouf, F.-X., Rozé, C., Coppalle, A., Parent, P., Ferry, D., and Laffon, C. (2016). Soot optical properties determined by analyzing extinction spectra in the visible near-uv: Toward an optical speciation according to constituents and structure. *Journal of Aerosol Science*, 101:118–132.
- [19] Betrancourt, C., Liu, F., Desgroux, P., Mercier, X., Faccinetto, A., Salamanca, M., Ruwe, L., Kohse-Höinghaus, K., Emmrich, D., Beyer, A., et al. (2017). Investigation of the size of the incandescent incipient soot particles in premixed sooting and nucleation flames of n-butane using lii, him, and 1 nm-smgs. *Aerosol Science and Technology*, 51(8):916–935.
- [20] Bladh, H., Johnsson, J., Olofsson, N.-E., Bohlin, A., and Bengtsson, P.-E. (2011). Optical soot characterization using two-color laser-induced incandescence (2c-lii) in the soot growth region of a premixed flat flame. *Proceedings of the Combustion Institute*, 33(1):641–648.
- [21] Blanquart, G., Pepiot-Desjardins, P., and Pitsch, H. (2009). Chemical mechanism for high temperature combustion of engine relevant fuels with emphasis on soot precursors. *Combustion and Flame*, 156(3):588–607.
- [22] Blanquart, G. and Pitsch, H. (2009a). Analyzing the effects of temperature on soot formation with a joint volume-surface-hydrogen model. *Combustion and Flame*, 156(8):1614–1626.

- [23] Blanquart, G. and Pitsch, H. (2009b). A joint volume-surface-hydrogen multivariate model for soot formation. *Combustion generated fine carbonaceous particles*, pages 437–463.
- [24] Bond, T. C. and Bergstrom, R. W. (2006). Light absorption by carbonaceous particles: An investigative review. *Aerosol science and technology*, 40(1):27–67.
- [25] Cain, J. P., Camacho, J., Phares, D. J., Wang, H., and Laskin, A. (2011). Evidence of aliphatics in nascent soot particles in premixed ethylene flames. *Proceedings of the Combustion Institute*, 33(1):533–540.
- [26] Camacho, J., Liu, C., Gu, C., Lin, H., Huang, Z., Tang, Q., You, X., Saggese, C., Li, Y., Jung, H., et al. (2015a). Mobility size and mass of nascent soot particles in a benchmark premixed ethylene flame. *Combustion and Flame*, 162(10):3810–3822.
- [27] Camacho, J., Tao, Y., and Wang, H. (2015b). Kinetics of nascent soot oxidation by molecular oxygen in a flow reactor. *Proceedings of the Combustion Institute*, 35(2):1887–1894.
- [28] Cassady, S. J., Choudhary, R., Pinkowski, N. H., Shao, J., Davidson, D. F., and Hanson, R. K. (2020). The thermal decomposition of ethane. *Fuel*, 268:117409.
- [29] Cepeda, F., Nobakht, A., Verdugo, I., Fuentes, A., Dworkin, S. B., and Karatas, A. E. (2025). The effect of pressure up to 6 atm over soot maturity in laminar ethylene flames. *Combustion and Flame*, 274:113977.
- [30] Cho, S., Lee, S., Lee, W., and Park, S. (2016). Synthesis of primary-particle-size-tuned soot particles by controlled pyrolysis of hydrocarbon fuels. *Energy & Fuels*, 30(8):6614–6619.
- [31] Cho, W., Lee, S.-H., Ju, W.-S., Baek, Y., and Lee, J. K. (2004). Conversion of natural gas to hydrogen and carbon black by plasma and application of plasma carbon black. *Catalysis Today*, 98(4):633–638.
- [32] Ciajolo, A., Barbella, R., Tregrossi, A., and Bonfanti, L. (1998). Spectroscopic and compositional signatures of pah-loaded mixtures in the soot inception region of a premixed ethylene flame. In *Symposium (International) on Combustion*, volume 27, pages 1481–1487. Elsevier.
- [33] Cléon, G., Amodeo, T., Faccinetto, A., and Desgroux, P. (2011). Laser induced incandescence determination of the ratio of the soot absorption functions at 532 nm and 1064 nm in the nucleation zone of a low pressure premixed sooting flame. *Applied Physics B*, 104(2):297–305.
- [34] Dalzell, W. and Sarofim, A. (1969). Optical constants of soot and their application to heat-flux calculations.
- [35] Dasch, C. J. (1985). The decay of soot surface growth reactivity and its importance in total soot formation. *Combustion and flame*, 61(3):219–225.

- [36] De Iuliis, S., Chaumeix, N., Idir, M., and Paillard, C.-E. (2008). Scattering/extinction measurements of soot formation in a shock tube. *Experimental thermal and fluid science*, 32(7):1354–1362.
- [37] Desgroux, P., Faccinnetto, A., Mercier, X., Mouton, T., Karkar, D. A., and El Bakali, A. (2017). Comparative study of the soot formation process in a “nucleation” and a “sooting” low pressure premixed methane flame. *Combustion and Flame*, 184:153–166.
- [38] Desgroux, P., Mercier, X., and Thomson, K. A. (2013). Study of the formation of soot and its precursors in flames using optical diagnostics. *Proceedings of the Combustion Institute*, 34(1):1713–1738.
- [39] Doner, N. and Liu, F. (2017). Impact of morphology on the radiative properties of fractal soot aggregates. *Journal of Quantitative Spectroscopy and Radiative Transfer*, 187:10–19.
- [40] D’Alessio, A., Barone, A., Cau, R., D’Anna, A., and Minutolo, P. (2005). Surface deposition and coagulation efficiency of combustion generated nanoparticles in the size range from 1 to 10 nm. *Proceedings of the Combustion Institute*, 30(2):2595–2603.
- [41] D’Anna, A. (2009). Combustion-formed nanoparticles. *Proceedings of the Combustion Institute*, 32(1):593–613.
- [42] Eaves, N., Dworkin, S., and Thomson, M. (2015). The importance of reversibility in modeling soot nucleation and condensation processes. *Proceedings of the Combustion Institute*, 35(2):1787–1794.
- [43] EPA., U. (2019). Integrated science assessment (isa) for particulate matter (final report, dec 2019).
- [44] Eremin, A., Gurentsov, E., Popova, E., and Priemchenko, K. (2011). Size dependence of complex refractive index function of growing nanoparticles. *Applied Physics B*, 104:285–295.
- [45] Eremin, A. V. (2012). Formation of carbon nanoparticles from the gas phase in shock wave pyrolysis processes. *Progress in energy and combustion science*, 38(1):1–40.
- [46] Fahr, A. and Stein, S. (1989). Reactions of vinyl and phenyl radicals with ethyne, ethene and benzene. In *Symposium (International) on Combustion*, volume 22, pages 1023–1029. Elsevier.
- [47] Fau, G., Gascoin, N., Gillard, P., and Steelant, J. (2013). Methane pyrolysis: Literature survey and comparisons of available data for use in numerical simulations. *Journal of Analytical and Applied Pyrolysis*, 104:1–9.
- [48] Fenimore, C. P. and Jones, G. W. (1967). Oxidation of soot by hydroxyl radicals. *The Journal of physical chemistry*, 71(3):593–597.
- [49] Franklin, R. E. (1951). Crystallite growth in graphitizing and non-graphitizing carbons. *Proceedings of the Royal Society of London. Series A. Mathematical and Physical Sciences*, 209(1097):196–218.

- [50] Frenklach, M. (2002). Reaction mechanism of soot formation in flames. *Physical chemistry chemical Physics*, 4(11):2028–2037.
- [51] Frenklach, M. (2019). New form for reduced modeling of soot oxidation: Accounting for multi-site kinetics and surface reactivity. *Combustion and Flame*, 201:148–159.
- [52] Frenklach, M. and Ebert, L. B. (1988). Comment on the proposed role of spheroidal carbon clusters in soot formation. *The Journal of Physical Chemistry*, 92(2):561–563.
- [53] Frenklach, M. and Harris, S. J. (1987). Aerosol dynamics modeling using the method of moments. *Journal of colloid and interface science*, 118(1):252–261.
- [54] Frenklach, M. and Mebel, A. M. (2020). On the mechanism of soot nucleation. *Physical Chemistry Chemical Physics*, 22(9):5314–5331.
- [55] Frenklach, M. and Wang, H. (1991). Detailed modeling of soot particle nucleation and growth. In *Symposium (International) on Combustion*, volume 23, pages 1559–1566. Elsevier.
- [56] Fuchs, N. A., Daisley, R., Fuchs, M., Davies, C., and Straumanis, M. (1965). The mechanics of aerosols.
- [57] Fulcheri, L., Rohani, V.-J., Wyse, E., Hardman, N., and Dames, E. (2023). An energy-efficient plasma methane pyrolysis process for high yields of carbon black and hydrogen. *International Journal of Hydrogen Energy*, 48(8):2920–2928.
- [58] Gibson, C., Adib, M., Li, C., Rault, T. M., Streicher, J. W., Kholghy, R., and Hanson, R. K. (2025). Carbon black and hydrogen co-production from methane pyrolysis: measured and modeled insights from integrated gas-phase and particulate diagnostics in shock tubes. *in preparation*.
- [59] Giordana, A., Maranzana, A., and Tonachini, G. (2011). Theoretical investigation of soot nanoparticle inception via polycyclic aromatic hydrocarbon coagulation (condensation): Energetic, structural, and electronic features. *The Journal of Physical Chemistry C*, 115(5):1732–1739.
- [60] Gleason, K., Carbone, F., and Gomez, A. (2021). Paths controlling soot nucleation in 0.101–0.811 mpa ethylene counterflow diffusion flames. *Combustion and Flame*, 227:384–395.
- [61] Gleason, K. and Gomez, A. (2023). Soot nucleation in diffusion flames and the role of aromatic hydrocarbons. *Combustion and Flame*, 255:112899.
- [62] Goodwin, D. G., Moffat, H. K., Schoegl, I., Speth, R. L., and Weber, B. W. (2022). Cantera: An object-oriented software toolkit for chemical kinetics, thermodynamics, and transport processes. <https://www.cantera.org>. Version 2.6.0.
- [63] Goudeli, E., Eggersdorfer, M. L., and Pratsinis, S. E. (2015). Coagulation–agglomeration of fractal-like particles: Structure and self-preserving size distribution. *Langmuir*, 31(4):1320–1327.

- [64] Goudeli, E., Eggersdorfer, M. L., and Pratsinis, S. E. (2016). Coagulation of agglomerates consisting of polydisperse primary particles. *Langmuir*, 32:9276–9285.
- [65] Grass, R. N., Tsantilis, S., and Pratsinis, S. E. (2006). Design of high-temperature, gas-phase synthesis of hard or soft tio₂ agglomerates. *AIChE Journal*, 52(4):1318–1325.
- [66] Gröhn, A. J., Pratsinis, S. E., and Wegner, K. (2012). Fluid-particle dynamics during combustion spray aerosol synthesis of zro₂. *Chemical Engineering Journal*, 191:491–502.
- [67] Haaland, S. E. (1983). Simple and explicit formulas for the friction factor in turbulent pipe flow.
- [68] Happold, J., Grotheer, H.-H., and Aigner, M. (2009). Soot precursors consisting of stacked pericondensed pahs. *Combustion generated fine carbonaceous particles*, pages 275–285.
- [69] Harris, S. J. and Weiner, A. M. (1985). Chemical kinetics of soot particle growth. *Annual Review of Physical Chemistry*, 36(1):31–52.
- [70] Haynes, B. and Wagner, H. G. (1982). The surface growth phenomenon in soot formation. *Zeitschrift für Physikalische Chemie*, 133(2):201–213.
- [71] Haynes, B. S. and Wagner, H. G. (1981). Soot formation. *Progress in energy and combustion science*, 7(4):229–273.
- [72] Hellmuth, M., Langer, R., Meraviglia, A., Beeckmann, J., and Pitsch, H. (2024). The role of c3 and c4 species in forming naphthalene in counterflow diffusion flames. *Proc. Combust. Inst.*, 40:105620.
- [73] Herdman, J. D. and Miller, J. H. (2008). Intermolecular potential calculations for polynuclear aromatic hydrocarbon clusters. *The Journal of Physical Chemistry A*, 112(28):6249–6256.
- [74] Homann, K. (1985). Formation of large molecules, particulates and ions in premixed hydrocarbon flames; progress and unresolved questions. In *Symposium (International) on Combustion*, volume 20, pages 857–870. Elsevier.
- [75] Hou, D., Zong, D., Lindberg, C. S., Kraft, M., and You, X. (2020). On the coagulation efficiency of carbonaceous nanoparticles. *Journal of Aerosol Science*, 140:105478.
- [76] Hurt, R. H., Crawford, G. P., and Shim, H.-S. (2000). Equilibrium nanostructure of primary soot particles. *Proceedings of the Combustion Institute*, 28(2):2539–2546.
- [77] Ishiguro, T., Suzuki, N., Fujitani, Y., and Morimoto, H. (1991). Microstructural changes of diesel soot during oxidation. *Combustion and Flame*, 85(1-2):1–6.
- [78] Jensen, K. A., Suo-Anttila, J. M., and Blevins, L. G. (2007). Measurement of soot morphology, chemistry, and optical properties in the visible and near-infrared spectrum in the flame zone and overfire region of large jp-8 pool fires. *Combustion science and technology*, 179(12):2453–2487.

- [79] Johansson, K., El Gabaly, F., Schrader, P., Campbell, M., and Michelsen, H. (2017). Evolution of maturity levels of the particle surface and bulk during soot growth and oxidation in a flame. *Aerosol Science and Technology*, 51(12):1333–1344.
- [80] Johansson, K., Head-Gordon, M., Schrader, P., Wilson, K., and Michelsen, H. (2018). Resonance-stabilized hydrocarbon-radical chain reactions may explain soot inception and growth. *Science*, 361(6406):997–1000.
- [81] Johansson, K. O., Dillstrom, T., Monti, M., El Gabaly, F., Campbell, M. F., Schrader, P. E., Popolan-Vaida, D. M., Richards-Henderson, N. K., Wilson, K. R., Violi, A., et al. (2016). Formation and emission of large furans and oxygenated hydrocarbons from flames. *Proceedings of the National Academy of Sciences*, 113(30):8374–8379.
- [82] Kazakov, A. and Frenklach, M. (1998). Dynamic modeling of soot particle coagulation and aggregation: Implementation with the method of moments and application to high-pressure laminar premixed flames. *Combustion and flame*, 114(3-4):484–501.
- [83] Kelesidis, G. A. and Goudeli, E. (2021). Self-preserving size distribution and collision frequency of flame-made nanoparticles in the transition regime. *Proceedings of the Combustion Institute*, 38(1):1233–1240.
- [84] Kelesidis, G. A., Goudeli, E., and Pratsinis, S. E. (2017a). Flame synthesis of functional nanostructured materials and devices: Surface growth and aggregation. *Proc Combust Inst.*, 36:29–50.
- [85] Kelesidis, G. A., Goudeli, E., and Pratsinis, S. E. (2017b). Morphology and mobility diameter of carbonaceous aerosols during agglomeration and surface growth. *Carbon*, 121:527–535.
- [86] Kelesidis, G. A. and Pratsinis, S. E. (2019a). Estimating the internal and surface oxidation of soot agglomerates. *Combustion and Flame*, 209:493–499.
- [87] Kelesidis, G. A. and Pratsinis, S. E. (2019b). Soot light absorption and refractive index during agglomeration and surface growth. *Proceedings of the Combustion Institute*, 37(1):1177–1184.
- [88] Kelesidis, G. A. and Pratsinis, S. E. (2021a). Determination of the volume fraction of soot accounting for its composition and morphology. *Proceedings of the Combustion Institute*, 38(1):1189–1196.
- [89] Kelesidis, G. A. and Pratsinis, S. E. (2021b). A perspective on gas-phase synthesis of nanomaterials: Process design, impact and outlook. *Chemical Engineering Journal*, 421:129884.
- [90] Kelesidis, G. A. and Pratsinis, S. E. (2022). Santoro flame: The volume fraction of soot accounting for its morphology & composition. *Combustion and Flame*, 240:112025.
- [91] Kelesidis, G. A., Rossi, N., and Pratsinis, S. E. (2022). Porosity and crystallinity dynamics of carbon black during internal and surface oxidation. *Carbon*, 197:334–340.

- [92] Kholghy, M. R., Afarin, Y., Sediako, A. D., Barba, J., Lapuerta, M., Chu, C., Weingarten, J., Borshanpour, B., Chernov, V., and Thomson, M. J. (2017). Comparison of multiple diagnostic techniques to study soot formation and morphology in a diffusion flame. *Combustion and Flame*, 176:567–583.
- [93] Kholghy, M. R., Eaves, N. A., Veshkini, A., and Thomson, M. J. (2019). The role of reactive pah dimerization in reducing soot nucleation reversibility. *Proceedings of the Combustion Institute*, 37(1):1003–1011.
- [94] Kholghy, M. R. and Kelesidis, G. A. (2021). Surface growth, coagulation and oxidation of soot by a monodisperse population balance model. *Combustion and Flame*, 227:456–463.
- [95] Kholghy, M. R., Kelesidis, G. A., and Pratsinis, S. E. (2018). Reactive polycyclic aromatic hydrocarbon dimerization drives soot nucleation. *Physical Chemistry Chemical Physics*, 20(16):10926–10938.
- [96] Kholghy, M. R., Veshkini, A., and Thomson, M. J. (2016). The core-shell internal nanostructure of soot—a criterion to model soot maturity. *Carbon*, 100:508–536.
- [97] Kim, K.-S. and Pratsinis, S. E. (1988). Manufacture of optical waveguide preforms by modified chemical vapor deposition. *AIChE journal*, 34(6):912–921.
- [98] Kruis, F. E., Kusters, K. A., Pratsinis, S. E., and Scarlett, B. (1993). A simple model for the evolution of the characteristics of aggregate particles undergoing coagulation and sintering. *Aerosol science and technology*, 19(4):514–526.
- [99] Lai, F., Friedlander, S., Pich, J., and Hidy, G. (1972). The self-preserving particle size distribution for brownian coagulation in the free-molecule regime. *Journal of Colloid and Interface Science*, 39(2):395–405.
- [100] Lapuerta, M., Barba, J., Sediako, A. D., Kholghy, M. R., and Thomson, M. J. (2017). Morphological analysis of soot agglomerates from biodiesel surrogates in a coflow burner. *Journal of Aerosol Science*, 111:65–74.
- [101] Le, K. C., Russo, C., Török, S., Apicella, B., Tregrossi, A., Bengtsson, P.-E., and Ciajolo, A. (2019). Soot optical band gap evaluated through in-situ and ex-situ measurements as tracer of soot evolution in premixed flames: Soot optical band gap evaluated through in-situ and ex-situ measurements as tracer of soot evolution in premixed flames.
- [102] Lee, K., Thring, M., and Beer, J. (1962). On the rate of combustion of soot in a laminar soot flame. *Combustion and Flame*, 6:137–145.
- [103] Lee, S. and Tien, C. (1981). Optical constants of soot in hydrocarbon flames. In *Symposium (international) on combustion*, volume 18, pages 1159–1166. Elsevier.
- [104] Leung, K. M., Lindstedt, R. P., and Jones, W. P. (1991). A simplified reaction mechanism for soot formation in nonpremixed flames. *Combustion and flame*, 87(3-4):289–305.

- [105] Lighty, J., Romano, V., and Sarofim, A. (2009). Soot oxidation. In *Combustion generated fine carbonaceous particles (proceedings of an international workshop held in Villa Orlandi, Anacapri, May 13e16, 2007)*. KIT Scientific Publishing, pages 523–36.
- [106] Lindstedt, P. R. (1994). Simplified soot nucleation and surface growth steps for non-premixed flames. In *Soot formation in combustion: mechanisms and models*, pages 417–441. Springer.
- [107] Liu, C., Singh, A. V., Saggese, C., Tang, Q., Chen, D., Wan, K., Vinciguerra, M., Commoco, M., De Falco, G., Minutolo, P., et al. (2019). Flame-formed carbon nanoparticles exhibit quantum dot behaviors. *Proceedings of the National Academy of Sciences*, 116(26):12692–12697.
- [108] Ma, X., Zangmeister, C., and Zachariah, M. (2013). Soot oxidation kinetics: a comparison study of two tandem ion-mobility methods. *The Journal of Physical Chemistry C*, 117(20):10723–10729.
- [109] Manzello, S. L., Lenhert, D. B., Yozgatligil, A., Donovan, M. T., Mulholland, G. W., Zachariah, M. R., and Tsang, W. (2007). Soot particle size distributions in a well-stirred reactor/plug flow reactor. *Proceedings of the Combustion Institute*, 31(1):675–683.
- [110] Martin, J. W., Hou, D., Menon, A., Pascazio, L., Akroyd, J., You, X., and Kraft, M. (2019). Reactivity of polycyclic aromatic hydrocarbon soot precursors: implications of localized π -radicals on rim-based pentagonal rings. *The Journal of Physical Chemistry C*, 123(43):26673–26682.
- [111] Martin, J. W., Salamanca, M., and Kraft, M. (2022). Soot inception: Carbonaceous nanoparticle formation in flames. *Progress in Energy and Combustion Science*, 88:100956.
- [112] Matsoukas, T. and Friedlander, S. K. (1991). Dynamics of aerosol agglomerate formation. *Journal of Colloid and Interface Science*, 146(2):495–506.
- [113] McBride, B. J. (1993). *Coefficients for calculating thermodynamic and transport properties of individual species*, volume 4513. National Aeronautics and Space Administration, Office of Management
- [114] McEnally, C. S., Köylü, Ü. Ö., Pfefferle, L. D., and Rosner, D. E. (1997). Soot volume fraction and temperature measurements in laminar nonpremixed flames using thermocouples. *Combustion and Flame*, 109(4):701–720.
- [115] Mei, J., Wang, M., You, X., and Law, C. K. (2019). Quantitative measurement of particle size distributions of carbonaceous nanoparticles during ethylene pyrolysis in a laminar flow reactor. *Combust. Flame*, 200:15–22.
- [116] Mei, J., Zhou, Y., You, X., and Law, C. K. (2021). Formation of nascent soot during very fuel-rich oxidation of ethylene at low temperatures. *Combustion and Flame*, 226:31–41.

- [117] Mercier, X., Carrivain, O., Irimiea, C., Faccinetto, A., and Therssen, E. (2019). Dimers of polycyclic aromatic hydrocarbons: the missing pieces in the soot formation process. *Physical Chemistry Chemical Physics*, 21(16):8282–8294.
- [118] Michelsen, H. A. (2017). Probing soot formation, chemical and physical evolution, and oxidation: A review of in situ diagnostic techniques and needs. *Proceedings of the Combustion Institute*, 36(1):717–735.
- [119] Michelsen, H. A. (2021). Effects of maturity and temperature on soot density and specific heat. *Proceedings of the Combustion Institute*, 38(1):1197–1205.
- [120] Michelsen, H. A., Colket, M. B., Bengtsson, P.-E., D’anna, A., Desgroux, P., Haynes, B. S., Miller, J. H., Nathan, G. J., Pitsch, H., and Wang, H. (2020). A review of terminology used to describe soot formation and evolution under combustion and pyrolytic conditions. *ACS nano*, 14(10):12470–12490.
- [121] Michelsen, H. A., Schrader, P. E., and Goulay, F. (2010). Wavelength and temperature dependences of the absorption and scattering cross sections of soot. *Carbon*, 48(8):2175–2191.
- [122] Migliorini, F., Thomson, K., and Smallwood, G. (2011). Investigation of optical properties of aging soot. *Applied Physics B*, 104(2):273–283.
- [123] Miller, J. H. (1991). The kinetics of polynuclear aromatic hydrocarbon agglomeration in flames. In *Symposium (International) on Combustion*, volume 23, pages 91–98. Elsevier.
- [124] Miller, J. H., Mallard, W. G., and Smyth, K. C. (1984). Intermolecular potential calculations for polycyclic aromatic hydrocarbons. *The Journal of Physical Chemistry*, 88(21):4963–4970.
- [125] Miller, J. H., Smyth, K. C., and Mallard, W. G. (1985). Calculations of the dimerization of aromatic hydrocarbons: Implications for soot formation. In *Symposium (International) on Combustion*, volume 20, pages 1139–1147. Elsevier.
- [126] Mountain, R. D., Mulholland, G. W., and Baum, H. (1986). Simulation of aerosol agglomeration in the free molecular and continuum flow regimes. *Journal of Colloid and Interface Science*, 114(1):67–81.
- [127] Mulholland, G. W., Samson, R., Mountain, R., and Ernst, M. (1988). Cluster size distribution for free molecular agglomeration. *Energy & Fuels*, 2(4):481–486.
- [128] Myhre, G., Shindell, D., and Pongratz, J. (2014). Anthropogenic and natural radiative forcing.
- [129] Nagle, J. and Strickland-Constable, R. (1962). Oxidation of carbon between 1000–2000 c. In *Proceedings of the fifth conference on carbon*, pages 154–164. Elsevier.
- [130] Narsimhan, G. and Ruckenstein, E. (1985). The brownian coagulation of aerosols over the entire range of knudsen numbers: Connection between the sticking probability and the interaction forces. *Journal of colloid and interface science*, 104(2):344–369.

- [131] Naseri, A., Kholghy, M. R., Juan, N. A., and Thomson, M. J. (2022). Simulating yield and morphology of carbonaceous nanoparticles during fuel pyrolysis in laminar flow reactors enabled by reactive inception and aromatic adsorption. *Combustion and Flame*, 237:111721.
- [132] Nativel, D., Shu, B., Herzler, J., Fikri, M., and Schulz, C. (2019). Shock-tube study of methane pyrolysis in the context of energy-storage processes. *Proceedings of the Combustion Institute*, 37(1):197–204.
- [133] Neeft, J. P., Nijhuis, T. X., Smakman, E., Makkee, M., and Moulijn, J. A. (1997). Kinetics of the oxidation of diesel soot. *Fuel*, 76(12):1129–1136.
- [134] Neoh, K., Howard, J., and Sarofim, A. (1981). Soot oxidation in flames. *Particulate carbon: formation during combustion*, pages 261–282.
- [135] Obolensky, O., Semenikhina, V., Solov'Yov, A., and Greiner, W. (2007). Interplay of electrostatic and van der waals forces in coronene dimer. *International Journal of Quantum Chemistry*, 107(6):1335–1343.
- [136] Olofsson, N.-E., Simonsson, J., Török, S., Bladh, H., and Bengtsson, P.-E. (2015). Evolution of properties for aging soot in premixed flat flames studied by laser-induced incandescence and elastic light scattering. *Applied Physics B*, 119:669–683.
- [137] Ono, K., Dewa, K., Matsukawa, Y., Saito, Y., Matsushita, Y., Aoki, H., Era, K., Aoki, T., and Yamaguchi, T. (2017). Experimental evidence for the sintering of primary soot particles. *Journal of Aerosol Science*, 105:1–9.
- [138] Organization, W. H. et al. (2013). Health effects of particulate matter: Policy implications for countries in eastern europe, caucasus and central asia.
- [139] Palomares, V., Goñi, A., Muro, I. G. D., Meatza, I. D., Bengoechea, M., Cantero, I., and Rojo, T. (2010). Conductive additive content balance in li-ion battery cathodes: Commercial carbon blacks vs. in situ carbon from lifepo4/c composites. *J. Power Sources*, 195:7661–7668.
- [140] Park, S., Rogak, S., Bushe, W., Wen, J., and Thomson, M. (2005a). An aerosol model to predict size and structure of soot particles. *Combustion Theory and Modelling*, 9(3):499–513.
- [141] Park, S.-J., Seo, M.-K., and Nah, C. (2005b). Influence of surface characteristics of carbon blacks on cure and mechanical behaviors of rubber matrix compoundings. *Journal of colloid and interface science*, 291(1):229–235.
- [142] Pinkowski, N. H., Ding, Y., Johnson, S. E., Wang, Y., Parise, T. C., Davidson, D. F., and Hanson, R. K. (2019). A multi-wavelength speciation framework for high-temperature hydrocarbon pyrolysis. *Journal of Quantitative Spectroscopy and Radiative Transfer*, 225:180–205.
- [143] Pratsinis, S. E. (1988). Simultaneous nucleation, condensation, and coagulation in aerosol reactors. *Journal of colloid and interface science*, 124(2):416–427.

- [144] Pratsinis, S. E. (2011). History of manufacture of fine particles in high-temperature aerosol reactors. *Aerosol science and technology: History and reviews*, pages 475–507.
- [145] Puduppakkam, K. V., Modak, A. U., Naik, C. V., Camacho, J., Wang, H., and Meeks, E. (2014). A soot chemistry model that captures fuel effects. In *Turbo Expo: Power for Land, Sea, and Air*, volume 45691, page V04BT04A055. American Society of Mechanical Engineers.
- [146] Puri, R., Richardson, T., Santoro, R., and Dobbins, R. (1993). Aerosol dynamic processes of soot aggregates in a laminar ethene diffusion flame. *Combustion and flame*, 92(3):320–333.
- [147] Rissler, J., Messing, M. E., Malik, A. I., Nilsson, P. T., Nordin, E. Z., Bohgard, M., Sanati, M., and Pagels, J. H. (2013). Effective density characterization of soot agglomerates from various sources and comparison to aggregation theory. *Aerosol Science and Technology*, 47(7):792–805.
- [148] Robertson, J. and O’reilly, E. (1987). Electronic and atomic structure of amorphous carbon. *Physical Review B*, 35(6):2946.
- [149] Russo, C., Apicella, B., Tregrossi, A., Ciajolo, A., Le, K. C., Török, S., and Bengtsson, P.-E. (2020). Optical band gap analysis of soot and organic carbon in premixed ethylene flames: comparison of in-situ and ex-situ absorption measurements. *Carbon*, 158:89–96.
- [150] Russo, C., Tregrossi, A., and Ciajolo, A. (2015). Dehydrogenation and growth of soot in premixed flames. *Proceedings of the Combustion Institute*, 35(2):1803–1809.
- [151] Sabbah, H., Biennier, L., Klippenstein, S. J., Sims, I. R., and Rowe, B. R. (2010). Exploring the role of pahs in the formation of soot: Pyrene dimerization. *The Journal of Physical Chemistry Letters*, 1(19):2962–2967.
- [152] Saffaripour, M., Veshkini, A., Kholghy, M., and Thomson, M. J. (2014). Experimental investigation and detailed modeling of soot aggregate formation and size distribution in laminar coflow diffusion flames of jet a-1, a synthetic kerosene, and n-decane. *Combustion and Flame*, 161(3):848–863.
- [153] Saggese, C., Ferrario, S., Camacho, J., Cuoci, A., Frassoldati, A., Ranzi, E., Wang, H., and Faravelli, T. (2015). Kinetic modeling of particle size distribution of soot in a premixed burner-stabilized stagnation ethylene flame. *Combustion and Flame*, 162(9):3356–3369.
- [154] Sajid, M. B., Javed, T., and Farooq, A. (2016). Shock tube/laser absorption measurements of methane, acetylene and ethylene during the pyrolysis of n-pentane and iso-pentane. *Combustion and Flame*, 164:1–9.
- [155] Salenbauch, S., Cuoci, A., Frassoldati, A., Saggese, C., Faravelli, T., and Hasse, C. (2015). Modeling soot formation in premixed flames using an extended conditional quadrature method of moments. *Combustion and Flame*, 162(6):2529–2543.

- [156] Sanchez, N. E., Callejas, A., Millera, A., Bilbao, R., and Alzueta, M. U. (2012). Polycyclic aromatic hydrocarbon (pah) and soot formation in the pyrolysis of acetylene and ethylene: effect of the reaction temperature. *Energy & fuels*, 26(8):4823–4829.
- [157] Schiener, M. and Lindstedt, R. (2019). Transported probability density function based modelling of soot particle size distributions in non-premixed turbulent jet flames. *Proceedings of the Combustion Institute*, 37(1):1049–1056.
- [158] Shaddix, C. R. and Smyth, K. C. (1996). Laser-induced incandescence measurements of soot production in steady and flickering methane, propane, and ethylene diffusion flames. *Combustion and flame*, 107(4):418–452.
- [159] Shao, J., Ferris, A. M., Choudhary, R., Cassady, S. J., Davidson, D. F., and Hanson, R. K. (2020). Shock-induced ignition and pyrolysis of high-pressure methane and natural gas mixtures. *Combustion and Flame*, 221:364–370.
- [160] Shepherd, R. H., King, M. D., Rennie, A. R., Ward, A. D., Frey, M. M., Brough, N., Eveson, J., Del Vento, S., Milsom, A., Pfrang, C., et al. (2022). Measurement of gas-phase oh radical oxidation and film thickness of organic films at the air–water interface using material extracted from urban, remote and wood smoke aerosol. *Environmental Science: Atmospheres*, 2(4):574–590.
- [161] Singh, M. and Vander Wal, R. L. (2018). Nanostructure quantification of carbon blacks. *C*, 5(1):2.
- [162] Smooke, M., Long, M., Connelly, B., Colket, M., and Hall, R. (2005). Soot formation in laminar diffusion flames. *Combustion and Flame*, 143(4):613–628.
- [163] Song, J., Alam, M., Boehman, A. L., and Kim, U. (2006). Examination of the oxidation behavior of biodiesel soot. *Combustion and flame*, 146(4):589–604.
- [164] Spicer, P. T., Chaoul, O., Tsantilis, S., and Pratsinis, S. E. (2002). Titania formation by ticl₄ gas phase oxidation, surface growth and coagulation. *J. Aerosol Sci.*, 33:17–34.
- [165] Stein, S. E. and Fahr, A. (1985). High-temperature stabilities of hydrocarbons. *The Journal of Physical Chemistry*, 89(17):3714–3725.
- [166] Stouffer, S., Striebich, R., Zelina, J., and Frayne, C. (2002). Combustion particulates mitigation investigation using a well-stirred reactor. In *38th AIAA/ASME/SAE/ASEE Joint Propulsion Conference & Exhibit*, page 3723.
- [167] Stranic, I. and Hanson, R. K. (2014). Laser absorption diagnostic for measuring acetylene concentrations in shock tubes. *Journal of Quantitative Spectroscopy and Radiative Transfer*, 142:58–65.
- [168] Sun, B., Rigopoulos, S., and Liu, A. (2021). Modelling of soot coalescence and aggregation with a two-population balance equation model and a conservative finite volume method. *Combustion and Flame*, 229:111382.

- [169] Tauc, J., Grigorovici, R., and Vancu, A. (1966). Optical properties and electronic structure of amorphous germanium. *physica status solidi (b)*, 15(2):627–637.
- [170] Totton, T. S., Misquitta, A. J., and Kraft, M. (2012). A quantitative study of the clustering of polycyclic aromatic hydrocarbons at high temperatures. *Physical chemistry chemical physics*, 14(12):4081–4094.
- [171] Tregrossi, A., Ciajolo, A., and Barbella, R. (1999). The combustion of benzene in rich premixed flames at atmospheric pressure. *Combustion and flame*, 117(3):553–561.
- [172] Tsantilis, S. and Pratsinis, S. E. (2004). Soft-and hard-agglomerate aerosols made at high temperatures. *Langmuir*, 20(14):5933–5939.
- [173] Utsav, K., Beshir, M., and Farooq, A. (2017). Simultaneous measurements of acetylene and soot during the pyrolysis of ethylene and benzene in a shock tube. *Proceedings of the Combustion Institute*, 36(1):833–840.
- [174] Vander Wal, R. L. and Tomasek, A. J. (2004). Soot nanostructure: dependence upon synthesis conditions. *Combustion and Flame*, 136(1-2):129–140.
- [175] Vander Wal, R. L., Yezerets, A., Currier, N. W., Kim, D. H., and Wang, C. M. (2007). Hrtm study of diesel soot collected from diesel particulate filters. *Carbon*, 45(1):70–77.
- [176] Vemury, S. and Pratsinis, S. E. (1995). Self-preserving size distributions of agglomerates. *Journal of Aerosol Science*, 26(2):175–185.
- [177] Veshkini, A. (2015). *Understanding Soot Particle Growth Chemistry and Particle Sizing Using a Novel Soot Growth and Formation Model*. University of Toronto (Canada).
- [178] Veshkini, A., Dworkin, S. B., and Thomson, M. J. (2016). Understanding soot particle size evolution in laminar ethylene/air diffusion flames using novel soot coalescence models. *Combustion Theory and Modelling*, 20(4):707–734.
- [179] Violi, A., Voth, G. A., and Sarofim, A. F. (2005). The relative roles of acetylene and aromatic precursors during soot particle inception. *Proceedings of the Combustion Institute*, 30(1):1343–1351.
- [180] Virtanen, P., Gommers, R., Oliphant, T. E., Haberland, M., Reddy, T., Cournapeau, D., Burovski, E., Peterson, P., Weckesser, W., Bright, J., van der Walt, S. J., Brett, M., Wilson, J., Millman, K. J., Mayorov, N., Nelson, A. R. J., Jones, E., Kern, R., Larson, E., Carey, C. J., Polat, İ., Feng, Y., Moore, E. W., VanderPlas, J., Laxalde, D., Perktold, J., Cimrman, R., Henriksen, I., Quintero, E. A., Harris, C. R., Archibald, A. M., Ribeiro, A. H., Pedregosa, F., van Mulbregt, P., and SciPy 1.0 Contributors (2020). SciPy 1.0: Fundamental Algorithms for Scientific Computing in Python. *Nature Methods*, 17:261–272.
- [181] Vlasov, P., Akhunyanov, A., and Smirnov, V. (2022). Experimental studies and simulation of methane pyrolysis and oxidation in reflected shock waves accompanied by soot formation. *Kinetics and Catalysis*, 63(2):141–156.

- [182] Wang, H. (2011). Formation of nascent soot and other condensed-phase materials in flames. *Proc Combust Inst.*, 33:41–67.
- [183] Wang, H.-C. and Kasper, G. (1991). Filtration efficiency of nanometer-size aerosol particles. *Journal of Aerosol Science*, 22(1):31–41.
- [184] Wang, S., Davidson, D. F., and Hanson, R. K. (2016). Improved shock tube measurement of the $\text{CH}_4 + \text{Ar} = \text{CH}_3 + \text{H} + \text{Ar}$ rate constant using uv cavity-enhanced absorption spectroscopy of CH_3 . *The Journal of Physical Chemistry A*, 120(28):5427–5434.
- [185] Wang, Y., Han, W., Zirwes, T., Attili, A., Cai, L., Bockhorn, H., Yang, L., and Chen, Z. (2023). A systematic analysis of chemical mechanisms for ethylene oxidation and pah formation. *Combust. Flame*, 253:112784.
- [186] Wang, Y., Raj, A., and Chung, S. H. (2013). A pah growth mechanism and synergistic effect on pah formation in counterflow diffusion flames. *Combustion and flame*, 160(9):1667–1676.
- [187] Wang, Y., Raj, A., and Chung, S. H. (2015). Soot modeling of counterflow diffusion flames of ethylene-based binary mixture fuels. *Combustion and Flame*, 162(3):586–596.
- [188] Wang, Z.-M., Zhang, X., Lei, J.-M., Jin, K.-R., Tian, Z.-Y., et al. (2024). Revisit the pah and soot formation in high-temperature pyrolysis of methane. *Journal of Analytical and Applied Pyrolysis*, 182:106668.
- [189] Watson, A. Y. and Valberg, P. A. (2001). Carbon black and soot: two different substances. *AIHAJ-American Industrial Hygiene Association*, 62(2):218–228.
- [190] Wei, J., Zeng, Y., Pan, M., Zhuang, Y., Qiu, L., Zhou, T., and Liu, Y. (2020). Morphology analysis of soot particles from a modern diesel engine fueled with different types of oxygenated fuels. *Fuel*, 267:117248.
- [191] Wong, D., Whitesides, R., Schuetz, C., and Frenklach, M. (2009). Molecular dynamics simulations of pah dimerization. *Combustion Generated Fine Carbonaceous Particles*, pages 247–257.
- [192] Woods, I. and Haynes, B. (1991). Soot surface growth at active sites. *Combustion and flame*, 85(3-4):523–525.
- [193] Wu, J. J. and Flagan, R. C. (1988). A discrete-sectional solution to the aerosol dynamic equation. *Journal of Colloid and interface Science*, 123(2):339–352.
- [194] Xiong, Y. and Pratsinis, S. E. (1993). Formation of agglomerate particles by coagulation and sintering—part i. a two-dimensional solution of the population balance equation. *J. Aerosol Sci.*, 24:283–300.
- [195] Xu, F., Sunderland, P., and Faeth, G. (1997). Soot formation in laminar premixed ethylene/air flames at atmospheric pressure. *Combustion and Flame*, 108(4):471–493.

-
- [196] Xu, L., Yan, F., Zhou, M., and Wang, Y. (2021). An experimental and modeling study on sooting characteristics of laminar counterflow diffusion flames with partial premixing. *Energy*, 218:119479.
- [197] Yon, J., Bescond, A., and Ouf, F.-X. (2015). A simple semi-empirical model for effective density measurements of fractal aggregates. *Journal of Aerosol Science*, 87:28–37.
- [198] Yon, J., Cruz, J. J., Escudero, F., Morán, J., Liu, F., and Fuentes, A. (2021). Revealing soot maturity based on multi-wavelength absorption/emission measurements in laminar axisymmetric coflow ethylene diffusion flames. *Combustion and Flame*, 227:147–161.
- [199] Zerbs, J., Geigle, K. P., Lammel, O., Hader, J., Stirn, R., Hadeff, R., and Meier, W. (2009). The influence of wavelength in extinction measurements and beam steering in laser-induced incandescence measurements in sooting flames. *Applied Physics B*, 96:683–694.
- [200] Zhang, Q. (2010). *Detailed modeling of soot formation/oxidation in laminar coflow diffusion flames*. PhD thesis.
- [201] Zhang, Y., Dong, W., Vandewalle, L., Xu, R., Smith, G., and Wang, H. (2023). Foundational Fuel Chemistry Model Version 2.0 (FFCM-2).
- [202] Zhao, B., Yang, Z., Johnston, M. V., Wang, H., Wexler, A. S., Balthasar, M., and Kraft, M. (2003). Measurement and numerical simulation of soot particle size distribution functions in a laminar premixed ethylene-oxygen-argon flame. *Combustion and Flame*, 133(1-2):173–188.
- [203] Zhao, B., Yang, Z., Li, Z., Johnston, M. V., and Wang, H. (2005). Particle size distribution function of incipient soot in laminar premixed ethylene flames: effect of flame temperature. *Proceedings of the Combustion Institute*, 30(1):1441–1448.

Appendix A

Supplementary results

This chapter includes the supplementary results mentioned in the thesis but are the central part of discussions.

A.1 Fundamental analysis of PAH growth models

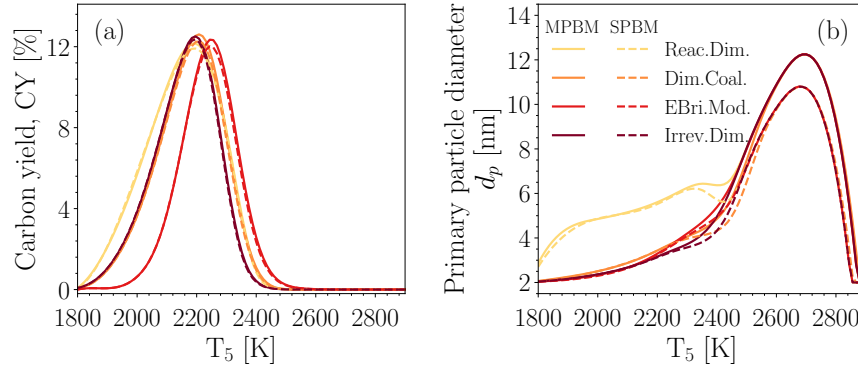


Fig. A.1 The comparison of CY (a) and primary particle diameter, d_p , at $t = 1.5$ ms obtained using MPBM and SPBM models for the case optimized using equal adjustment factors to minimize the prediction error.

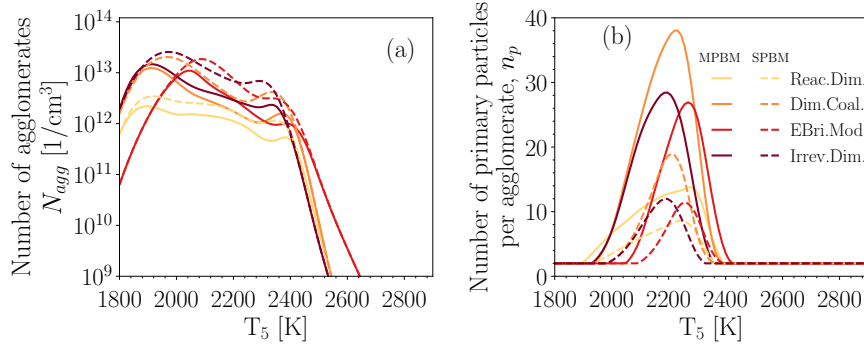


Fig. A.2 The temperature dependence of total number of agglomerates, N_{agg} (a), number of primary particles per agglomerate, n_p (b), at $t = 1.5$ ms obtained using MPBM and SPBM models for the case optimized using equal adjustment factors to minimize the prediction error.

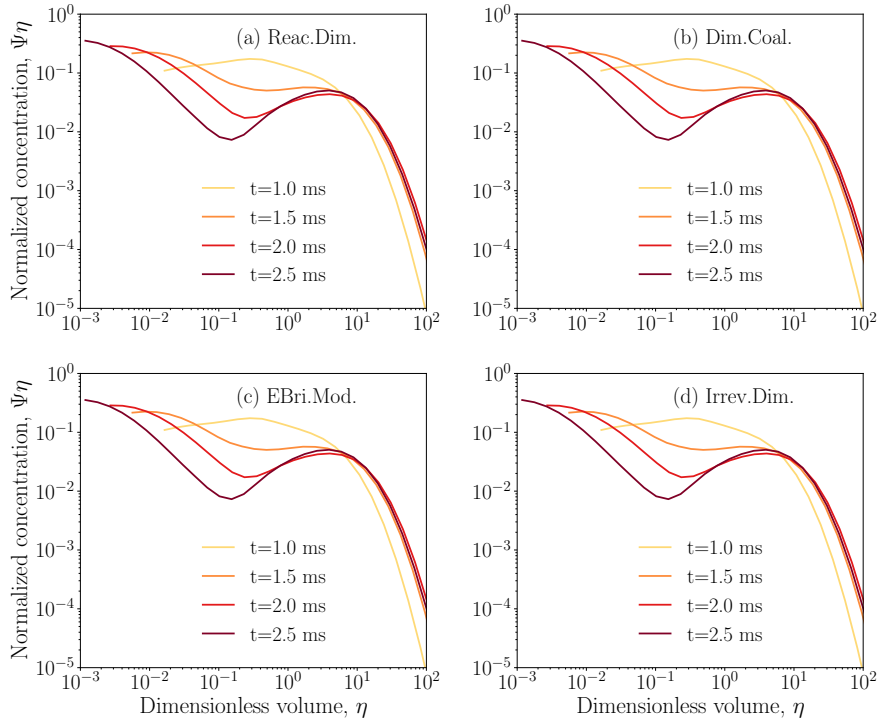


Fig. A.3 The non-dimensional particle size distribution during 5%CH₄-Ar at $T_5 = 2200$ K that evolves from 1 ms to 2.5 ms indicating SPSPD is not attained yet.

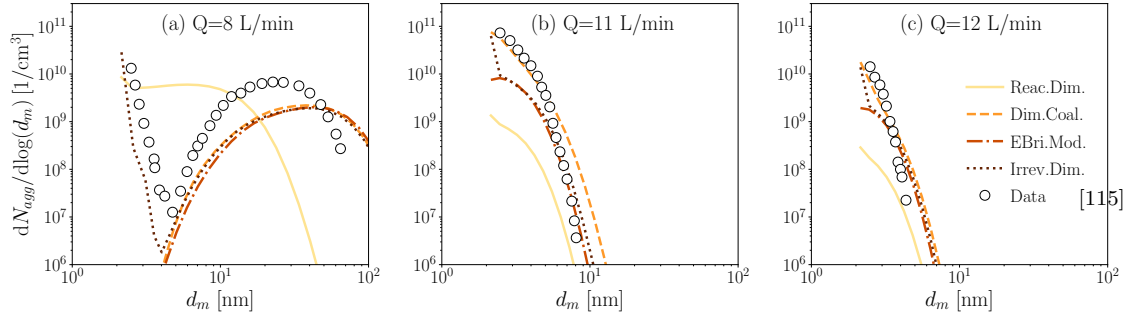


Fig. A.4 The particle size distribution at the end of PFR for $Q = 8$ (a), 11 (b), and 12 L/min (c) obtained using Caltech mechanism, SPBM and different inception models calibrated to match the predictions with measurement [115].

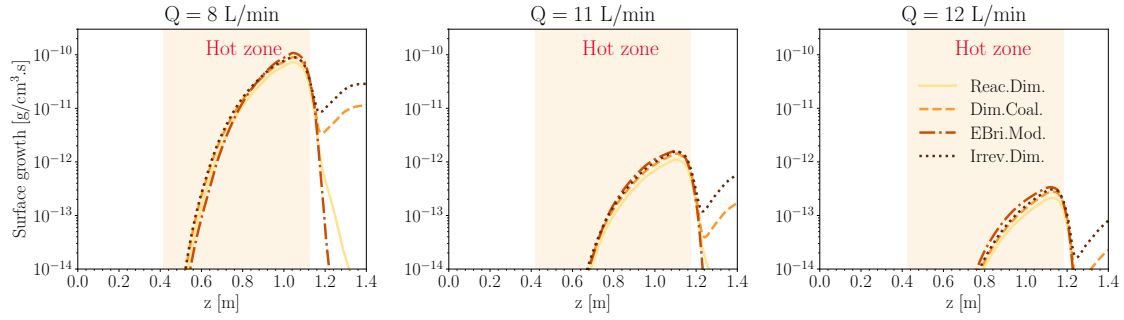


Fig. A.5 The surface growth by HACA and PAH adsorption combined along the PFR for $Q = 8$ (a), 11 (b), and 12 L/min (c) obtained using KAUST mechanism, SPBM and different inception models. The yellow area represents the hot zone ($T > 0.9T_{\max}$).

A.2 Identifying stages of carbon black formation

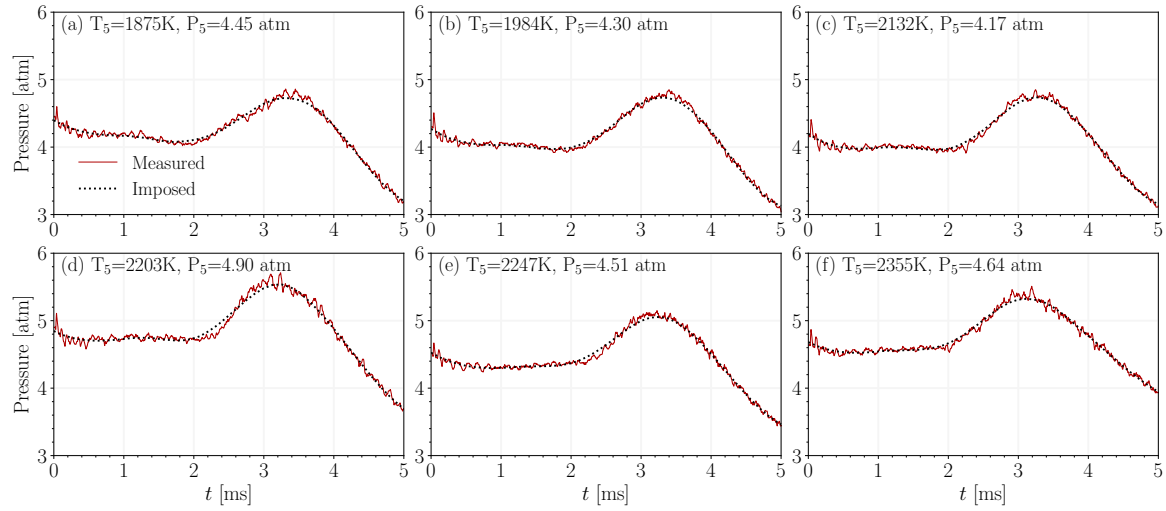


Fig. A.6 The measured pressure trace and the filtered profile imposed in the model for the entire temperature range

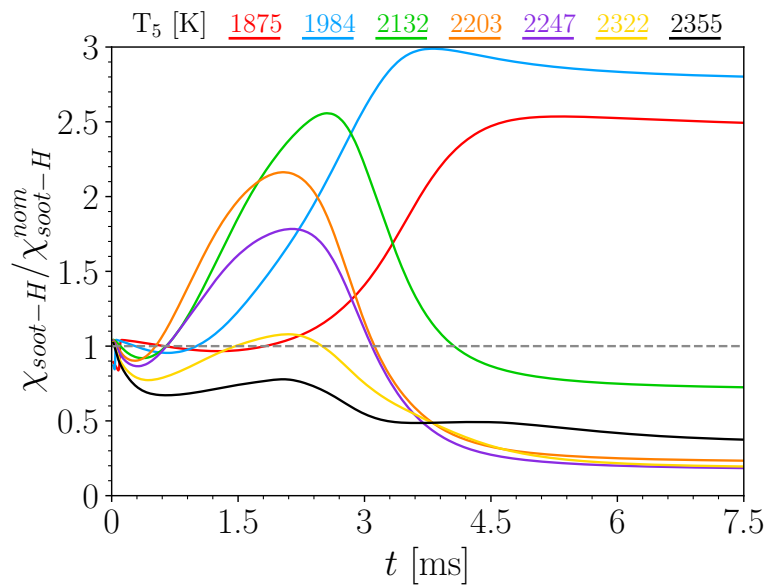


Fig. A.7 The number of hydrogenated sites, $\chi_{soot-H} = H_{tot}/A_{tot}$ normalized by its nominal value of $\chi_{soot-H}^{nom} = 2.3 \times 10^{19}$ sites/m².

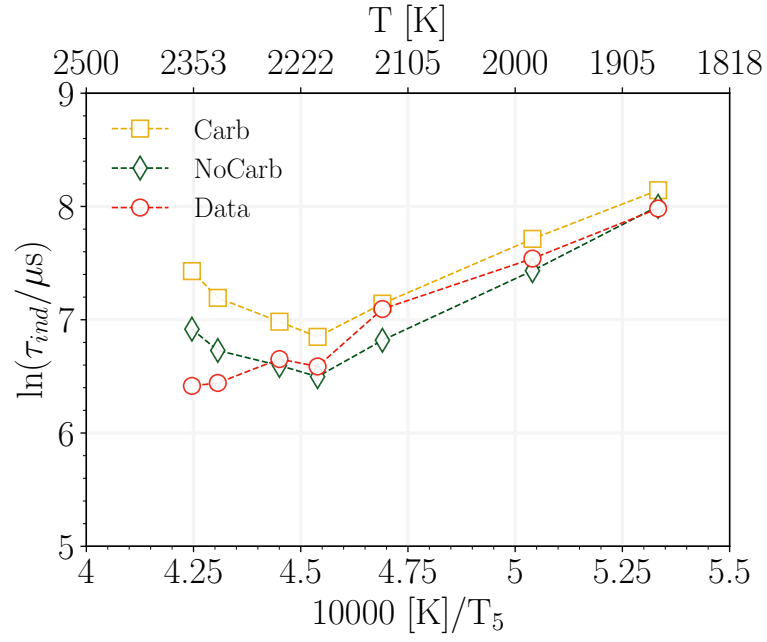


Fig. A.8 The effect on carbonization on CB induction time.

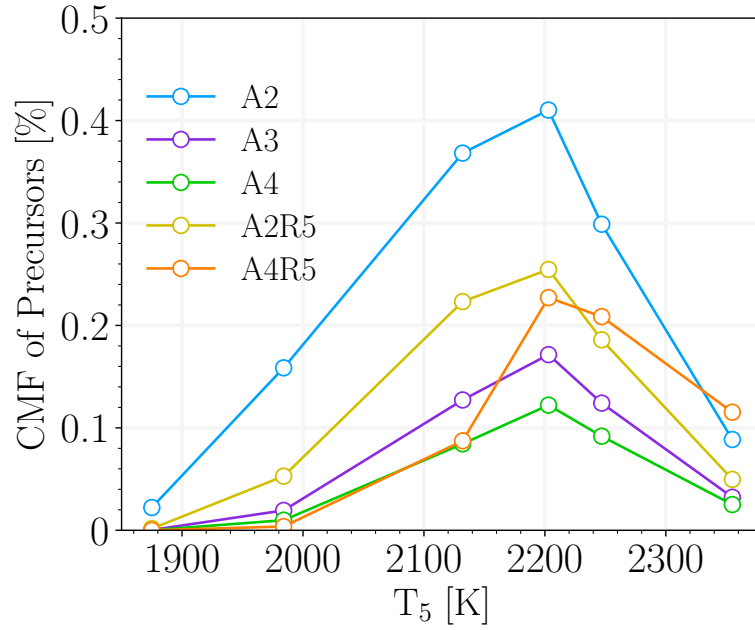


Fig. A.9 The carbon mass fraction of CB precursors at 0.5 ms

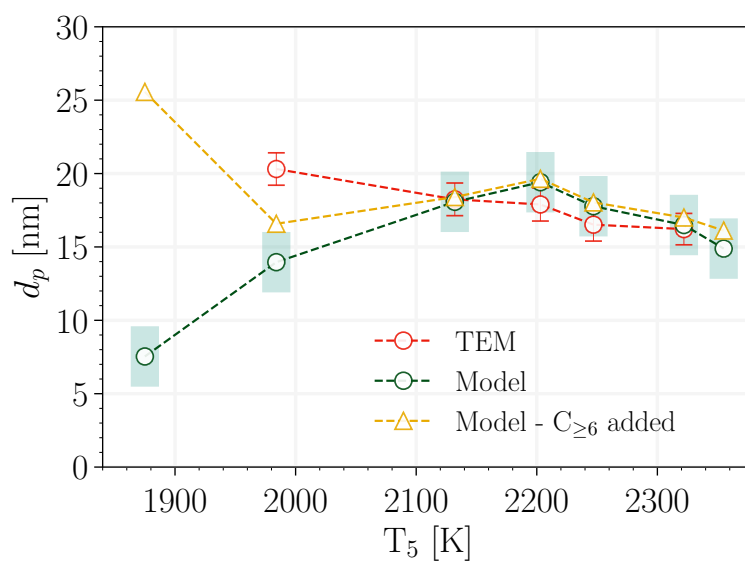


Fig. A.10 The final primary particle diameter, d_p , considering the additional carbon mass from condensation of benzene and larger species on CB compared with d_p from TEM measurements and the model predictions at 7.5 ms.

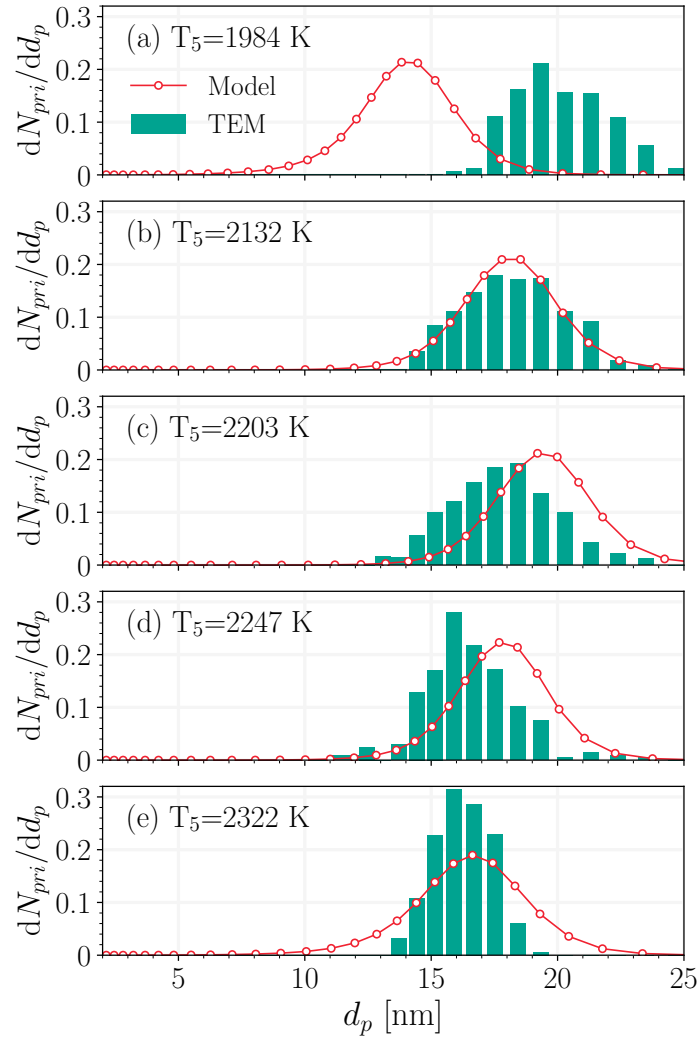


Fig. A.11 The size distribution of primary particles from TEM measurements compared with the model predictions.

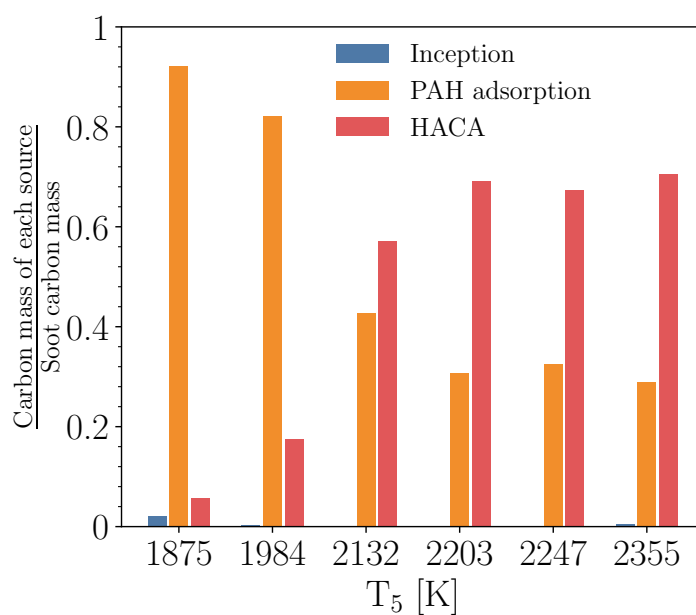


Fig. A.12 The CB mass from inception, PAH adsorption and HACA normalized by total carbon mass at $t=5$ ms

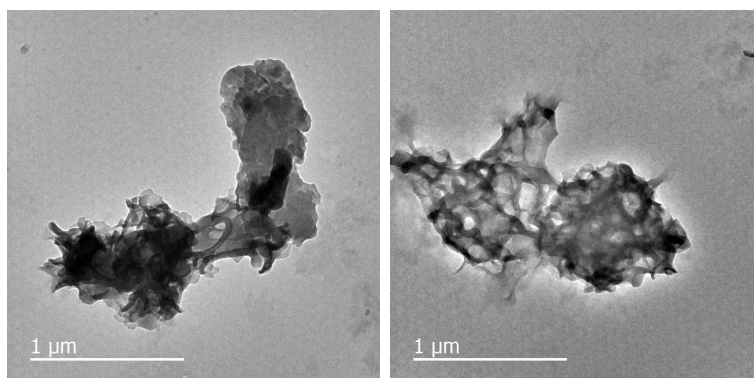


Fig. A.13 Samples of TEM images collected for $T_5=1875$ K that shows a compact carbonaceous lump with not clear boundaries between primary particles.