

OPTICAL FORCES GENERATED BY PLASMONIC NANOSTRUCTURES

by

MATTHEW MOOCARME

A dissertation submitted to the Graduate Faculty in Physics in partial fulfillment of the requirements for the degree of Doctor of Philosophy, The City University of New York

2017

© 2017

MATTHEW MOOCARME

All Rights Reserved

This manuscript has been read and accepted by the Graduate Faculty in Physics in satisfaction of the dissertation requirement for the degree of Doctor of Philosophy.

**Professor L.T.Vuong**

---

Date Chair of Examining Committee

**Professor Igor Kuskovsky**

---

Date Executive Officer

**Professor Vinod Menon**

**Professor Azriel Genack**

**Professor Harry Gafney**

**Dr Aaron Stein**

Supervisory Committee

## Abstract

### OPTICAL FORCES GENERATED BY PLASMONIC NANOSTRUCTURES

by

MATTHEW MOOCARME

Adviser: Professor L.T. Vuong

For millennia, scientists have sought to uncover the secrets what holds the world together. From which, the field of optics has been at the forefront, unravelling material properties through light-matter interactions. As the field has progressed, the smallest unit at which can be probed and manipulated has become smaller and smaller, as such the resulting field of sub-field of optics, nanophotonics, reflecting the processing of light at the nanoscale, has blossomed into a vast design space for both applied and theoretical researchers. This thesis reflects the advancement of just a few small subtopics of the field and is divided into an introduction followed by four chapters:

**Chapter 2** investigates magneto-plasmonics in gold nanoparticles, a designation generally associated with ferromagnetic-plasmonic materials because such optical responses from nonmagnetic materials alone are considered weak. This chapter shows that there exists a transition between linear and nonlinear magneto-optical behaviors in noble-metal nanocolloids that is observable at ultra-low illumination intensities and direct-current magnetic fields. The response is attributed to polarization-dependent nonzero-time-averaged plasmonic loops, vortex power flows, and nanoparticle magnetization. This chapter identifies significant mechanical effects that arise via magnetic-dipole interactions, exhibited via changes in the transmission spectra.

**Chapter 3** shows that mechanical forces associated with surface currents that have been widely overlooked point to a new family of plasmonically-driven processes. This chapter investigates the action of the Lorentz force on a free electron gas that is bound to the surface of a nanowire. Appreciable mechanical forces are produced by wavelength illuminations between longitudinal and transverse absorption resonances via the excitation of chiral hybrid plasmon modes. The plasmonic activity is associated as the underlying mechanism for nanowire rotation, which explains prior experimental results. The presence of chiral hybrid plasmon modes yield larger net translation and torque forces than either transverse or longitudinal plasmon modes. The asymmetric plasmon behavior affects the complex nonlinear dynamics of plasmonic nonspherical nanoparticles in fluids.

**Chapter 4** investigates the phenomenon that when plane waves diffract through fractal-patterned apertures, the resulting far-field profiles or diffractals also exhibit iterated, self-similar features. The chapter explores that this specific family of architectures enable robust signal processing and spatial multiplexing: arbitrary parts of a diffractal contain sufficient information to recreate the entire original sparse signal.

**Chapter 5** explores the response of an individual meta-atom is often generalized to explain the collective response of a metasurface in a manner that neglects the interactions between meta-atoms. A metasurface is studied that is composed of tilted achiral meta-atoms with no spatial variation of the unit-cell that derives appreciable optical chirality solely from the asymmetric interactions between meta-atoms. It is shown that interactions between meta-atoms can be modelled as the Lorentz force that arise from the Larmor radiation of adjacent plasmonic resonators because their inclusion accurately predicts the bonding/anti-bonding modes that are measured experimentally. Experimentally observed are the emergence of multiple polarization eigenmodes, among other polarization-dependent responses, which cannot

be modeled with the transmission matrix formalism. The results are essential for the precise characterization and design of metasurfaces.

For my parents.

# Acknowledgments

To my father whose competence and independence embodies the spirit of a physicist. To my mother whose support I couldn't have accomplished this Ph.D without.

Heartfelt thanks my adviser Prof. Luat Vuong for unlimited guidance and ideas. To my committee members. Professor Viond Menon, whose intuition and knowledge in the field of nanophotonics is extraordinary. Professor Azi Genack, whose humble guidance and understanding on light scattering is truly remarkable. Professor Harry Gafney, for his ability to transform the mood of the room for the positive and his wealth of knowledge and information. And finally, Dr Stein for brilliant support at Brookhaven National Laboratory.

To fellow lab mate, Nicolas Proscia, whose valuable discussions and emotional support have been truly vital in this journey. To other graduate students, Xiaojun Cheng, Haojie Ji, Siddarth Dhomkar, Zhou Shi, Parbatee Jagassar, Harish Krishnamoorthy, Xiaoze Liu, Rahul Deshmukh, and Roger Chang for fruitful discussions over theories and assistance with experiments. To Ryan Abrahams, Matt Grasser, Tom Proctor, and Zhibai Zhang for making homeworks and late nights in the Graduate Center entertaining. To Howard Rose and Noel Evans, whose lessons I will carry with me for a long time. To Tony, the janitor, whose outlook on life is a reminder to appreciate the important things in life. To Daniel Moy who has always been a pleasure to work with. To my friends Avinash Lalwani, Abhishek Jha, Brian Taylor, Karan Mehra, Shalini Israni, and Kahlua for accepting nothing less than me. To fellow graduate student Arpita Biswas, whose common ground we will always share.

Contents from chapter 2 is reproduced with permission from [Moocarme, M., Dominguez-Juarez, J. L., and Vuong, L. T. (2014a). Ultralow-intensity magneto-optical and mechanical effects in metal nanocolloids. *Nano Letters*, 14(3):1178–1183] 2014 Copyright American Chemical Society. Contents from chapter 3 and 4 are reproduced with permission from [Moocarme, M. and Vuong, L. T. (2015). Robustness and spatial multiplexing via diffractal architectures. *Optics Express*, 23(22):28471–28478, Moocarme, M., Kusin, B., and Vuong, L. T. (2014c). Plasmon-induced lorentz forces of nanowire chiral hybrid modes. *Optical Materials Express*, 4(11):2355–2367] 2014, 2015 Copyright Optical Society of America.

# Contents

<b>Contents</b>	<b>x</b>
<b>List of Figures</b>	<b>xiv</b>
<b>Nomenclature</b>	<b>xx</b>
<b>1 Introduction</b>	<b>1</b>
1.1 Overview of the dissertation . . . . .	1
1.2 Light and Polarization . . . . .	2
1.3 Surface plasmon polaritons . . . . .	3
<b>2 Ultra-low-intensity magneto-optical and mechanical effects in metal nanocolloids</b>	<b>13</b>
2.1 Introduction . . . . .	13
2.2 Linear dynamics . . . . .	15
2.2.1 Addition of magnetic fields to equations of motion . . . . .	15
2.3 Nonlinear dynamics . . . . .	17
2.3.1 Nonlinear current density . . . . .	17
2.3.2 Nonlinear magnetization . . . . .	18
2.4 Numerical predictions . . . . .	18
2.4.1 Finite-element simulation results . . . . .	18

<i>CONTENTS</i>	<i>xi</i>
2.5 Experimental observation . . . . .	20
2.5.1 Observation of transition from linear to nonlinear dynamics . . . . .	20
2.6 Discussion . . . . .	23
2.6.1 Magnetization magnitudes . . . . .	23
2.6.2 Time-dependent response . . . . .	24
2.7 Conclusion . . . . .	26
2.8 Experimental difficulties and future work . . . . .	26
<b>3 Plasmon-induced Lorentz forces of nanowire chiral hybrid modes</b>	<b>28</b>
3.1 Introduction . . . . .	28
3.2 Setup and simulations of 2D dynamics . . . . .	31
3.2.1 Calculation of electromagnetic fields . . . . .	31
3.2.2 Calculation of Lorentz force . . . . .	34
3.2.3 Calculation of torque forces . . . . .	35
3.3 Translation and compressive plasmonic forces . . . . .	37
3.3.1 Force visualized for various illumination wavelengths . . . . .	37
3.3.2 Momentum transfer via scattering . . . . .	40
3.4 Torque in 3-dimensions . . . . .	42
3.4.1 Torque visualized for various illumination wavelengths . . . . .	42
3.4.2 Phase diagram illustrations . . . . .	43
3.5 Conclusion . . . . .	45
3.6 Future work . . . . .	46
<b>4 Robustness and spatial multiplexing via diffractal architectures</b>	<b>47</b>
4.1 Introduction . . . . .	47
4.2 Theoretical description . . . . .	49
4.2.1 Spatial multiplexing of the diffractal . . . . .	49

<b>CONTENTS</b>	xii
4.2.2 Robust reconstruction of a blocked diffractal signal . . . . .	51
4.3 Experimental results . . . . .	55
4.4 Discussion of applications . . . . .	56
4.5 Conclusion . . . . .	60
4.6 Experimental difficulties and future work . . . . .	60
<b>5 Meta-optical chirality and emergent eigen-polarization modes via plasmon interactions</b>	<b>62</b>
5.1 Introduction . . . . .	62
5.2 The coupling force . . . . .	66
5.3 Coupled equations of motion . . . . .	68
5.4 Mode hybridization and optical chirality . . . . .	71
5.5 Emergent polarization eigenmodes . . . . .	75
5.6 Discussion . . . . .	77
5.7 Conclusion . . . . .	78
5.8 Fabrication methods and measurement . . . . .	78
5.8.1 Development . . . . .	80
5.8.2 Recipe . . . . .	82
5.8.3 Transmission measurement setup . . . . .	85
5.8.4 Polarization measurement setup . . . . .	85
5.9 Experimental difficulties and future work . . . . .	86
<b>6 Summary and Outlook</b>	<b>88</b>
6.1 What has been done . . . . .	88
6.2 What is left to do . . . . .	90
<b>Previously Published Materials</b>	<b>93</b>

*CONTENTS*

xiii

**Bibliography****94**

# List of Figures

1.1	Dispersion relation of surface plasmon modes in aluminium with water ( $\epsilon_d = 1.77$ ) as the surrounding dielectric. Dashed line represents the light line. . . . .	7
1.2	Surface plasmon polariton at a dielectric-metal interface. . . . .	10
2.1	Relative MO shift of bulk gold when external fields are varied. (a) Real and (b) imaginary parts of the refractive index as a function of wavelength under illumination of $1 \text{ W/cm}^2$ RHCP when magnetic fields are varied. . . . .	16
2.2	(a) Surface plots of the nonlinear current density of an aqueous 80-nm gold nanosphere when illuminated by LHCP, linearly-polarized and RHCP light in the $\hat{z}$ direction at the plasmon resonance, 540 nm, at $1 \text{ W/cm}^2$ . (b) Volume-averaged relative change in azimuthal component of the conductivity as a function of wavelength when illumination intensity is varied for RHCP or LHCP. . . . .	19
2.3	(Continued on the following page.) . . . . .	21

2.3 (Previous page.) Normalized MO changes in transmission for aqueous gold nanocolloid at (a) low magnetic fields (b) intermediate magnetic fields and (c) higher magnetic fields. Theoretical MO change in transmission of aqueous 80-nm gold nanospheres in the (d) linear and (f) nonlinear analyses. Theoretical MO changes that combine the linear and nonlinear analyses are shown in (e) for intermediate magnetic fields. In all plots the illumination is 1 W/cm <sup>2</sup> and RHCP. . . . .	22
2.4 Numerically calculated (a) amplitude and (b) phase of the longitudinal component of the electric field, $E_z$ , with 540-nm 1 W/cm <sup>2</sup> RHCP illumination intensity. (c) Volume-averaged magnetization as a function of wavelength when illumination intensities are varied. All plots are for an aqueous 80-nm gold nanoparticle. . . . .	23
2.5 Numerically calculated relative change in magnetization (a) of a 80-nm gold dimer nanocluster as a function of angle of rotation, and (b) ellipsoidal gold nanoparticle rotated from minimal to maximal surface area as a function of aspect ratio, illuminated with 540-nm 1 W/cm <sup>2</sup> RHCP. . . . .	25
3.1 (a) System geometry: a gold nanowire (75-nm diameter, rounded-cap, 1025-nm length) is aligned about spherical coordinates $\theta$ and $\phi$ , and a $y$ -polarized electromagnetic wave (1 W/cm <sup>2</sup> ) travels in the $-z$ direction. (b) The electric field profile surrounding a nanowire resulting from superposed angular momentum modes $m = 0, \pm 1$ with propagation lengths $k_{\parallel}z = 0, \pi/2$ , and $\pi$ . . . . .	32

3.2 Characteristics of a nanowire in the $x$ - $y$ plane for varying orientation angle $\phi$ with $\theta = 90^\circ$ . (a) Absorption cross-section. (b) Scattering cross-section, ((a), (b) spectra offset for clarity). (c) Net longitudinal force in the direction of light propagation, $-F_z$ , associated with the plasmonic Lorentz force. (d) In-plane torque $T_z$ produced by plasmons $\mathbf{f}_M$ (solid lines) and the induced electric dipole $\mathbf{f}_E$ (dashed lines). . . . .	36
3.3 Forces on the nanowire surface produced by the surface currents (red arrows) and the norm of the surface magnetic field (surface colormap) for oblique geometries that excite the chiral hybrid plasmonic mode, where (a) $\theta = 15^\circ, \phi = 90^\circ$ (b) $\theta = 30^\circ, \phi = 75^\circ$ (c) $\theta = 60^\circ, \phi = 60^\circ$ at $\lambda = 1071\text{nm}$ . . . . .	38
3.4 Net (volume-integrated) Lorentz forces associated with nanowire surface currents $\mathbf{f}_M$ in (a) $x$ -direction, (b) $y$ -direction, and (c) $z$ -directions for illuminating wavelengths $\lambda =$ (i) 441nm (ii) 517nm (iii) 625nm (iv) 790nm (v) 1071nm. . . . .	39
3.5 Far-field radiation patterns for a nanowire aligned (a) in the $x$ - $z$ plane with $\theta = 75^\circ, \phi = 0^\circ$ , (b) $\theta = 60^\circ, \phi = 60^\circ$ for wavelengths $\lambda = 441\text{nm}, 517\text{nm}, 625\text{nm}, 790\text{nm}$ , and $1071\text{nm}$ . . . . .	40
3.6 Torque around the (a) $x$ -axis, (b) $y$ -axis, and (c) $z$ -axis at (i) 441nm, (ii) 535nm, (iii) 625nm, (iv) 790nm, and (v) 1071nm. . . . .	42
3.7 Phase portrait of the torque forces calculated at $\lambda = 1071\text{nm}$ . Arrows in the $x$ and $y$ directions indicate torque that rotates the nanowire in the $\phi$ and $\theta$ directions respectively. . . . .	44

4.1 a) Signal patterns, or fractalized signals (FS) of orders $n = 1, 3$ , and $5$ . b) Corresponding Fourier transforms of signals on logarithm scale, or diffractal signals (DS). c) Reconstructed Fourier-transforms (RFS) from the 1% black- outlined subset, the blocked diffractal signal (BDS). d) Enlargement of a por- tion of the $n = 5$ diffractal, which illustrates similar patterns at different length scales. . . . .	52
4.2 The peak signal-to-noise ratio (PSNR) of RFS to FS for various fractal orders as a function of the fractional BDS size. . . . .	54
4.3 a) Light from a $\lambda = 632.8\text{-}nm$ wavelength laser is spatially filtered, expanded, and collimated and illuminates the full area of a 800x600 pixel spatial light modulator (SLM). The 4- $f$ system is composed of 2 5- $cm$ lenses placed after the SLM. The first lens Fourier transforms the fractal signal (FS) at the focal plane. An aperture is placed off-center at the focal plane and only transmits a portion of the diffractal (BDS). The second lens reconstructs the SLM image with the light that is transmitted through the aperture. b) The Sierpinski carpet hologram of order $n= 5$ , CCD image in the focal plane of the hologram after the lens, and the reconstructed image. A circle denotes the area utilized to reconstruct the image. . . . .	56

5.1	(a) Model representation: an array of plasmonic resonators (rod-shaped apertures) tilted at $\theta_s$ relative to the base of the unit meta-atom where we separate the resonators into <i>m</i> - and <i>n</i> -type. The interaction force on <i>m</i> -type resonators results from the 4 nearest <i>n</i> -type resonators and vice-versa. (b) The interaction Lorentz force that arises from Larmor radiation [Eq. 5.1] for various $\theta_s$ when resonators oscillate in the <i>x</i> -direction, as a function of time. (c) The interaction force in the parallel ( <i>x</i> ), and perpendicular ( <i>y</i> ) directions when the resonators oscillate in the <i>x</i> -direction, as a function of $\theta_s$ . . . . .	65
5.2	(i) The original array with tilt angle, $\theta_s = 22.5^\circ$ . (ii) Reflection along the vertical axis. (iii) Rotation by $45^\circ$ . (iv) Superposition of the original array with the modified array. . . . .	69
5.3	(a) A top-view scanning electron microscope image of the metasurface. (b) The transmission spectra associated with different linear polarization angles, where we observe the presence of bonding and anti-bonding modes. (c) Shift in the wavelengths of the bonding and anti-bonding modes as a function of polarization angle. (d) Interaction forces parallel and perpendicular to the polarization axis experienced by the resonators from Eq. 5.4 as a function of polarization angle. . . . .	72
5.4	(a) The optical rotation (OR) and change in the elliptical component as a function of input polarization at 660nm. Inset: the relationship between $E_x$ and $E_y$ OR and change in the elliptical on the polarization ellipse. (b) OR and circular dichroism (CD) calculated from a transmission (T-)matrix approach (dashed). Overlaid is the experimental measurements of OR (measured at $\psi = +30^\circ$ ), and the CD (solid). . . . .	73

5.5 Eigen-polarization modes of the system at 660nm are shown on (a), the Poincaré sphere, where solid circles represent eigen-polarization states on the near surface of the sphere and hollow circles represent states on the far surface. (b) illustrates the eigen-polarization states measured in the $x - y$ plane. . . . .	76
5.6 Electron beam lithography pattern, nanoapertures measure 80nm by 160nm in a square lattice with periodicity between the structures measuring 375nm. . . . .	79
5.7 Spin curve for ZEP-520A. Image: <a href="https://ebeam.mff.uw.edu/ebeamweb/process/process/zep520a.html">https://ebeam.mff.uw.edu/ebeamweb/process/process/zep520a.html</a> . . . . .	81
5.8 Recipe to fabricate nanoapertures. i) Glass substrate, ii) gold layer is deposited, iii) ZEP 520a electron beam resist is deposited, iv) pattern is written via electron beam lithography, v) pattern is developed, vi) resist and gold is milled away . . . . .	84
5.9 The schematic diagram for (a) transmission measurements and (b) polarization measurements. . . . .	85

# Nomenclature

## Chapter 1

$\chi$  Material Susceptibility

$\epsilon$  Material Permittivity

$\epsilon_0$  Permittivity of Free Space

$\epsilon_d$  Permittivity of Dielectric

$\epsilon_m$  Permittivity of Metal

$\gamma$  Decay/Damping rate

$\nabla$  Differential Operator

$\omega_0$  Angular Frequency Associated with Harmonic Restorative Force

$\omega_p$  Plasma Frequency

$\partial_x$  Partial Derivative with respect to x

$\phi$  Phase

$c$  Speed of Light

$D$  Displacement Field

$E$  Electric Field

$e$  Electric Charge of Electron

$E_d$  Electric Field in Dielectric

$E_m$  Electric Field in Metal

$H$  Auxiliary Field

$H_d$  Auxiliary Field in Dielectric

$H_m$  Auxiliary Field in Metal

$k$  Wave-Vector

$k_0$  Wave-Vector in Free Space

$k_d$  Wave-Vector in Dielectric

$k_m$  Wave-Vector in Metal

$k_{SP}$  Wave-Vector of Surface Plasmon

$m$  Mass

$m_e$  Reduced Mass

$n_e$  Free Carrier Density

$P$  Polarization Density

$r$  Displacement

$t$  Time

DC Direct Current

LSP Localized Surface Plasmon

SPP Surface Plasmon Polariton

## Chapter 2

$\epsilon$  Material Permittivity

$\epsilon_0$  Permittivity of Free Space

$\eta$  Electron Density

$\gamma$  Decay/Damping Rate

$\langle \rangle$  Time-Average

$\omega$  Angular Frequency

$\omega_0$  Angular Frequency Associated with Harmonic Restorative Force

$\omega_c$  Cyclotron Frequency

$\omega_p$  Plasma Frequency

$\sigma$  Material Conductivity

$B$  Magnetic Field

$E$  Electric Field

$j$  Current Density

$k$  Restoring Force Constant

$M$  Magnetization

$m^*$  Reduced Mass

$q$  Electric Charge

$r$  Spatial Coordinate

$t$  Time

DC Direct Current

LHCP Left-Handed Circular-Polarization

MO Magneto Optical

RHCP Right-Handed Circular-Polarization

### Chapter 3

$\epsilon$  Dielectric Constant

$\epsilon_0$  Permittivity of Free Space

$\lambda$  Wavelength

$\rho$  Charge Density

$A$  Torque Vectors in Spherical Coordinate System

$B$  Magnetic Field

$c.c.$  Complex Conjugate

$E$  Electric Field

$f$  Lorentz Force

$H_m$  Hankel Function of the  $m^{th}$  Kind

$J$  Current Density

$J_m$  Bessel Function of the  $m^{th}$  Kind

$k$  Wave-Vector

$P$  Polarization Density

$q$  Electric Charge

$T$  Torque

$v$  Velocity

UV Ultra-Violet

## Chapter 4

$\delta$  Delta Function

$\lambda$  Wavelength

$i_c$   $\sqrt{-1}$

$k$  Wave-Vector

$n$  Fractal Order

$r$  Relative Scaling Factor

$T$  Transmission Function

BDS Blocked Diffractal Signal

DS Diffractal Signal

FS Fractalized Signal

OS Original Signal

PSNR Peak Signal-to-Noise Ratio

RFS Reconstructed Fourier-Transformed Signal

ROS Reconstructed Original Signal

SLM Spatial Light Modulator

## Chapter 5

$\beta$  Ratio of Speed to the Speed of Light

$\chi$  Elliptical Component of Polarization

$\delta$  Perturbation Parameter

$\epsilon$  Material Permittivity

$\epsilon_0$  Permittivity of Free Space

$\Gamma$  Non-Locality Parameter

$\gamma$  Damping Rate

$\lambda$  Wavelength

$\langle \rangle$  Time-Average

$\omega$  Angular Frequency

$\omega_0$  Angular Frequency Associated with Harmonic Restorative Force

$\psi$  Azimuthal Component of Polarization

$\theta_s$  Aperture Tilt

$a$  Metasurface Periodicity

$c$  Speed of Light

$E$  Electric Field

$F$  Force

$F^{int}$  Interaction Force

$k$  Wave-Vector

$k_e$  Coulombs Constant

$L$  Layer Thickness

$M$  Mass

$MR$  Milling Rate

$N_0$  Free Charge Carrier Density

$P$  Polarization Density

$q$  Electric Charge

$R$  Lattice Distance

$r$  Spatial Coordinate

$S$  Screening Factor

$t$  Time

$T_{LCP}$  Transmission of Left Circular Polarization

$T_{RCP}$  Transmission of Right Circular Polarization

$x_h/y_h$  Homogeneous Solution in the  $x/y$  direction

CD Circular Dichroism

OA Optical Activity

OR Optical Rotation

PMMA Electron Beam Resist

SEM Scanning Electron Microscope

ZEP High Performance Electron Beam Resist

# Chapter 1

## Introduction

### 1.1 Overview of the dissertation

This dissertation covers a variety of ways in which nanophotonics can harness the physics of light, from manipulating optical forces at the nanoscale, to developing efficient ways to encode information in the patterns light. The focus of the thesis will be on understanding the optical forces that are generated on nanoparticles. There has been a lot of recent interest in the development of 3D (metamaterials) and 2D (metasurface) geometries that possess optical properties not found in nature. While there has been much advancement in the field, from negative index materials [Padilla et al. (2006); Dolling et al. (2007); Shelby et al. (2001)] to perfect lenses [Khorasaninejad et al. (2016b); Yang et al. (2014); Khorasaninejad et al. (2016a)] to materials with permittivity close to zero [Park et al. (2015); Alù et al. (2007)], many of these materials are limited to a small sample area as well as other pitfalls of top-down processing. Complete understanding of the optical forces generated on metallic nanoparticles leads the way bottom-up processing of metasurfaces and metamaterials suitable for large-scale production.

In chapter 2 of this thesis, the development of magneto-optical responses in plasmonic

materials, that explores the magnetization of nanoparticles via the illumination of circularly-polarized light. This phenomenon offers a new degree of control over the Lorentz force exerted on plasmonic nanoparticles. As described in the third chapter, Lorentz forces influence the motion of nanoparticles with a degree of asymmetry, namely nanowires illuminated at oblique incidences, and the non-intuitive motion that subsequently results. The following chapter (chapter 4) illustrates an efficient way to spatially encode information with fractal architecture. Finally, in chapter 5 polarization properties are explored for a metasurface composed of non-chiral sub-structures, the phenomenon of which is derived from the Lorentz force that occurs between substructures that are measured in the polarization properties as light passes through the material.

Ultimately, it is hoped that this work furthers the research on how metasurfaces and metamaterials are fabricated, but also the applications of these materials in various architectures.

## 1.2 Light and Polarization

Electromagnetic waves are derived from non-zero solutions of Maxwell's equations in vacuum in absence of electric charges [Jackson (1999); Landau and Lifshitz (1960)]. Polarization refers to the direction of the electromagnetic field vectors in space. The polarization in the most general sense, can be described by elliptical motion, with special cases linear or circular. The polarization is a fundamental property of light such as color or intensity. There are many light matter interactions that are fundamentally dependent on the incident polarization, for example the strength of reflections, absorption or scattering [van de Hulst (1958)]. Following conventions, we can consider the electric field of an electromagnetic wave travelling in the

$z$ -direction in Cartesian coordinates  $(x, y, z)$ :

$$\mathbf{E}(t, z) = \mathbf{E}_0 \cos(\omega t - kz - \phi), \quad (1.1)$$

where  $\mathbf{E}_0$  is the magnitude of the electric field,  $\omega$  is the angular frequency,  $t$  refers to time,  $k$  is the wave-vector, and  $\phi$  denotes some arbitrary phase. The electric field vector is perpendicular to the direction of propagation,  $z$ , so we can decompose the electric fields into  $x$  and  $y$  components:

$$\begin{aligned} E_x(t) &= E_{x0} \cos(\omega t - kz - \phi_x), \\ E_y(t) &= E_{y0} \cos(\omega t - kz - \phi_y), \end{aligned} \quad (1.2)$$

where  $\phi_x$  and  $\phi_y$  refer to the phase associated with the electric field in their respective direction. Special cases of elliptical polarization occur when  $\phi_x = \phi_y$ , referring to linear polarization, and  $|\phi_x - \phi_y| = \pi/2$  refers to circular polarization.

The use of the polarization to achieve additional functionality that cannot be realized with any other optical technology is an exciting prospect to be exploited. Traditionally, the polarization of light can be manipulated through interaction with uniaxial or biaxial materials, such as calcite or quartz. However, if the light-matter interaction is understood fundamentally at the nanoscale, polarization-dependent interactions can be artificially crafted through the precise design of the structure.

### 1.3 Surface plasmon polaritons

Plasmonics [Barnes et al. (2003)] named after the electron density waves that propagate along the interface of a metal and a dielectric is a blossoming sub-field of optics. In particular there has been a tremendous amount of progress in the fabrication and manipulation methods of nanometer-sized objects in the last few decades that has allowed us to make significant

leaps and bounds in the field of optics.

Certain promises in the sub-field of plasmonics are responsible for the surge in the research field, for example a new generation of ultra-fast computing [Atwater (2007)], new possibilities to treat cancer and HIV/AIDS [Kumar et al. (2011)], topological insulators [Deshko et al. (2016)] or the ability fabricate negative-refraction materials and perfect lenses [Urbas et al. (2016)]. This could be made possible because plasmonics bridges the microscopic with the nanoscopic by confining light on sub-wavelength volumes. Plasmonic structures are typically composed of metallic nanoparticles, in particular noble metals due to their high electron density, though colloidal nanoparticles, or thin metal films may support plasmonic resonances.

## Coupling to plasmons

In the visible portion of the electromagnetic spectrum, the frequency of electromagnetic waves coincide with the natural oscillation of free electrons in noble metals; when light is incident on noble metals the free electrons oscillate in resonance. The plasma frequency of the metal is given by the relation:

$$\omega_p = \sqrt{\frac{n^2 e}{m^* \epsilon_0}} \quad (1.3)$$

where  $n$  is the free carrier density in the material,  $e$  is the charge of an electron,  $m^*$  is the effective mass of the electrons, and  $\epsilon_0$  is the permittivity of free space.

If one treats the conducting electrons as a free electron gas the equations of motion can be used to study the displacement as a function of time,  $r(t)$ , in the presence of an electric field,  $E$ . A velocity dependent damping force,  $\gamma$ , and a spring-like restoring force with resonant frequency  $\omega_0$  are also included:

$$m\ddot{r} + m\gamma\dot{r} - m\omega_0^2 r = -eE \quad (1.4)$$

where  $e$  is the charge on an electron, and  $m$  is its mass. The dot formalism refers to time derivatives, such that  $\dot{r} = \frac{dr}{dt}$  and  $\ddot{r} = \frac{d^2r}{dt^2}$ . Assuming a time-harmonic response of the motion,  $r(t) = r_0 e^{-i\omega t}$ , to the time-harmonic driving field,  $E(t) = E_0 e^{-i\omega t}$ . This leads to a Lorentz-oscillator form of the motion of the charge density [Vial et al. (2005)]:

$$r(t) = \frac{r_0 e}{m(\omega - \omega_0 + i\gamma\omega)} E(t) \quad (1.5)$$

The displacement of the charge density leads to changes in the macroscopic polarization by the relation  $P = -ner$ .

$$P(t) = -\frac{ne^2}{m(\omega - \omega_0 + i\gamma\omega)} E \quad (1.6)$$

The effective permittivity,  $\epsilon$ , of the material results from the relation linking the macroscopic fields with the polarization:

$$\begin{aligned} D &= \epsilon_0 E + P, \\ D &= \epsilon_0 \epsilon E \end{aligned} \quad (1.7)$$

where  $D$  is the displacement field such that

$$D = \epsilon_0 \left(1 - \frac{\omega_p^2}{\omega^2 - \omega_0^2 + i\gamma\omega}\right) E \quad (1.8)$$

The frequency-dependent relative permittivity of the material becomes

$$\epsilon(\omega) = 1 - \frac{\omega_p^2}{\omega^2 - \omega_0^2 + i\gamma\omega} \quad (1.9)$$

The real and imaginary components of the complex dielectric function  $\epsilon(\omega) = \epsilon_r(\omega) + i\epsilon_i(\omega)$  are defined as follows:

$$\begin{aligned}\epsilon_r(\omega) &= 1 - \frac{\omega_p^2}{\omega^2 - \omega_0^2 + \gamma^2} \\ \epsilon_i(\omega) &= \frac{\omega_p^2 \gamma}{\omega(\omega^2 - \omega_0^2 + \gamma^2)}\end{aligned}\tag{1.10}$$

The modified dielectric constant gives rise to a number of interesting properties including changes to the refractive index and conductivity of the material.

The dispersion relation for a plasma is given by the relation  $\omega^2 = \omega_p^2 + c^2 k^2$  which results in an asymptotically linear behaviour. As an example Fig. 1.1 shows an example of the dispersion relation of aluminium.

Surface plasmon modes are oscillations of plasma and their properties can be derived from Maxwell's equations. Interestingly, when these equations are solved with the appropriate boundary conditions between a noble metal and a dielectric the surface plasmon mode produced can have a larger momentum than the free-space photon that produced it ( $k_{SP} > k_0$ ), where the frequency-dependent surface plasmon wave-vector is given by the relation [Sambles et al. (1991)]:

$$k_{SP} = k_0 \sqrt{\frac{\epsilon_d \epsilon_m}{\epsilon_d + \epsilon_m}}\tag{1.11}$$

where  $\epsilon_d$  is the dielectric constant of the surrounding dielectric and  $\epsilon_m$  is the dielectric constant of the metal calculated from Eq. 1.10. A detailed derivation of Eq. 1.11 is included in the Supplemental Information section. This leads to a dispersion relation as seen in Fig 1.1. The high wave vectors of surface plasmons lead to greatly-enhanced light-matter interactions [Todorov et al. (2009)].

In general mode-matching conditions are satisfied by either using a prism to couple light into the interface [Kretschmann and Raether (1968)], through defects on the surface [Hecht et al. (1996)] or via diffraction with periodic surface structures such as gratings [Ritchie et al.

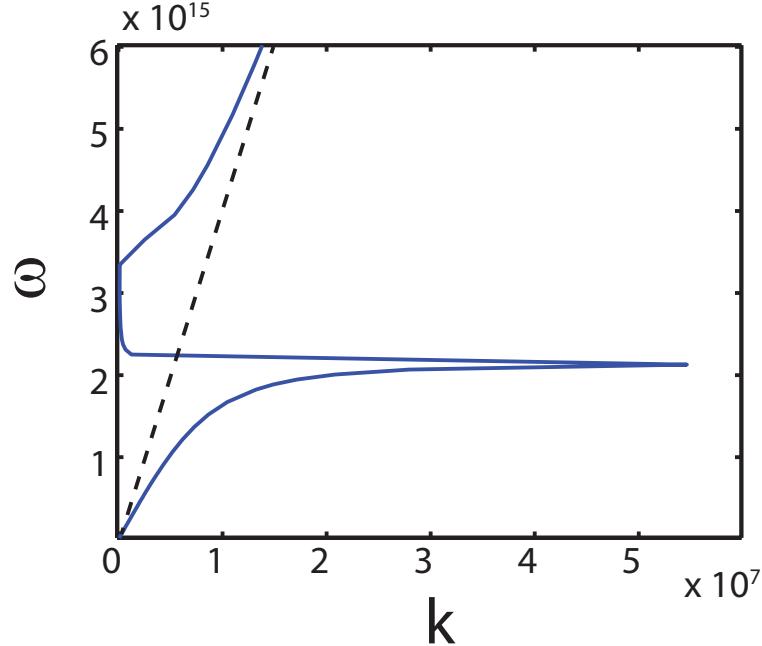


Figure 1.1: Dispersion relation of surface plasmon modes in aluminium with water ( $\epsilon_d = 1.77$ ) as the surrounding dielectric. Dashed line represents the light line.

(1968)].

Surface plasmons are commonly separated into two kinds, surface plasmon polaritons (SPPs) and localized surface plasmons (LSPs) [Maier (2007b)]. SPPs are commonly excited by 2D periodic grating structures as the periodic structure is able to provide the necessary in-plane wave-vector matching conditions. LSP resonances are a localized resonances of the charge density around nanostructures smaller than the wavelength of light. The resonance is highly dependent on the size, shape, material and surrounding environment of the nanostructure [Link and El-Sayed (2000)].

## Derivation of the surface plasmon dispersion

We consider a TM excitation wave travelling in the  $x - z$  plane incident on a metal dielectric interface at  $z = 0$ , in which  $E_y = 0$ ,  $H_x = H_z = 0$ , where  $E$  and  $H$  represent the electric and magnetic fields respectively and subscripts denote the relative direction. From this we can write the electric and magnetic fields in the metal and dielectric:

$$\begin{pmatrix} E_{xd} \\ 0 \\ E_{zd} \end{pmatrix} \exp[i(k_{xd} + k_{zd} - \omega t)], \quad \begin{pmatrix} 0 \\ H_{yd} \\ 0 \end{pmatrix} \exp[i(k_{xd} + k_{zd} - \omega t)]; \quad (1.12)$$

$$\begin{pmatrix} E_{xm} \\ 0 \\ E_{zm} \end{pmatrix} \exp[i(k_{xm} + k_{zm} - \omega t)], \quad \begin{pmatrix} 0 \\ H_{ym} \\ 0 \end{pmatrix} \exp[i(k_{xm} + k_{zm} - \omega t)]; \quad (1.13)$$

where  $k$  is the wave-vector,  $\omega$  is the angular velocity and  $t$  refers to time. The boundary conditions at the metal-dielectric interface are as follows:

$$\begin{aligned} \epsilon_m E_{zm} &= \epsilon_d E_{zd} \\ E_{xm} &= E_{xd} \\ H_{ym} &= H_{yd} \end{aligned} \quad (1.14)$$

where  $\epsilon$  refers to the dielectric constant. The last of the two boundary conditions lead to the equivalence of in-plane wave-vector,  $k_x$ :

$$k_{xm} = k_{xd} \quad (1.15)$$

Solving Maxwell's equations,  $\nabla \times \mathbf{H} = \frac{\epsilon}{c} \partial_t \mathbf{E}$ :

$$\begin{pmatrix} \partial_x \\ \partial_y \\ \partial_z \end{pmatrix} \times \begin{pmatrix} 0 \\ H_y \\ 0 \end{pmatrix} = \frac{\epsilon}{c} \partial_t \begin{pmatrix} E_x \\ 0 \\ E_z \end{pmatrix} \quad (1.16)$$

$$\begin{pmatrix} -\partial_z H_y \\ 0 \\ \partial_x H_y \end{pmatrix} = \frac{\epsilon \omega}{c} \begin{pmatrix} E_x \\ 0 \\ E_z \end{pmatrix} \quad (1.17)$$

$$\begin{aligned} (I) : -k_{zm} H_y m &= \frac{\epsilon_m \omega}{c} E_x m \\ (II) : k_{zd} H_y d &= \frac{\epsilon_d \omega}{c} E_x d \\ (I)/(II) : \frac{k_{zm}}{k_{zd}} \frac{H_{ym}}{H_{yd}} &= -\frac{\epsilon_m}{\epsilon_d} \frac{E_{xm}}{E_{xd}}, \end{aligned} \quad (1.18)$$

where region (I) represents the metal and region (II) represents the dielectric. Using the boundary condition  $E_{xm} = E_{xd}$  and  $H_{ym} = H_{yd}$  and the general relation  $k_x^2 + k_y^2 + k_z^2 = k^2 = \epsilon \frac{\omega^2}{c^2}$  We get the relations for the in and out-of-plane vectors:

$$\begin{aligned} k_x^2 &= \frac{\omega^2}{c^2} \frac{\epsilon_m \epsilon_d}{\epsilon_m + \epsilon_d} \\ k_z m^2 &= \frac{\omega^2}{c^2} \frac{\epsilon_m}{\epsilon_m + \epsilon_d} \\ k_z d^2 &= \frac{\omega^2}{c^2} \frac{\epsilon_d}{\epsilon_m + \epsilon_d} \end{aligned} \quad (1.19)$$

## Nonlinear plasmonics

Nonlinear effects are governed by photon-photon interactions in materials, and thus, are generally weak. The scattering and absorption cross-sections of plasmonic nanoparticles are

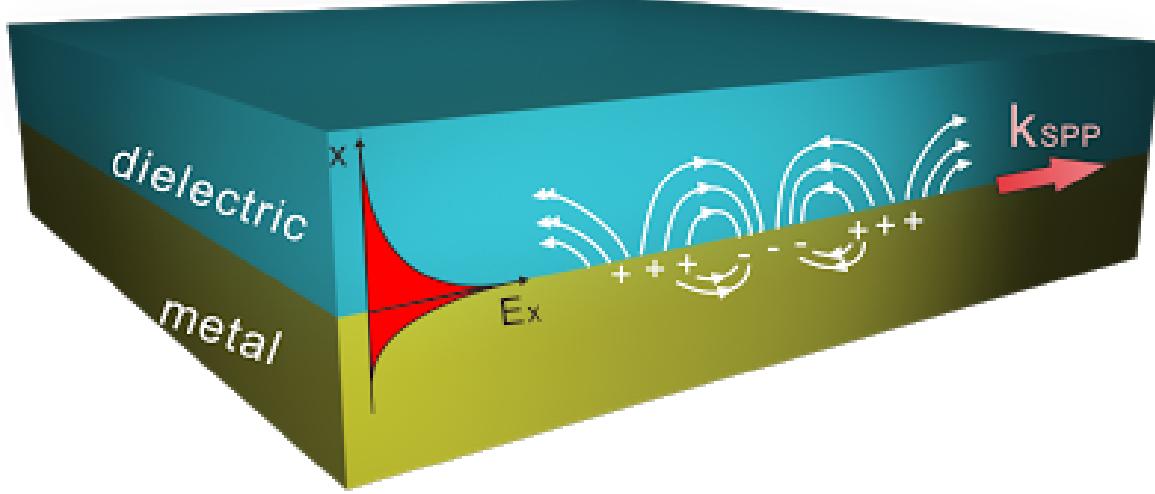


Figure 1.2: Surface plasmon polariton at a dielectric-metal interface.

much greater than their geometrical cross-sections which lead to large local field enhancements around the nanostructures to enable nonlinear effects to occur. In recent, nonlinear plasmonics has enabled surface-enhanced Raman scattering [Nie and Emery (1997)], second harmonic generation [Canfield et al. (2007)], and enhanced magneto-optical effects [Moocarme et al. (2014b); Belotelov et al. (2011)]. A material's response to an electric field,  $E$ , is governed by the material polarization  $P$  [Kaurranen and Zayats (2012)]:

$$P = \epsilon_0 [\chi^{(1)}E + \chi^{(2)}E^2 + \chi^{(3)}E^3 + \dots] \quad (1.20)$$

where  $\chi^{(n)}$  is the  $n$ -th order susceptibility of the material [Boyd (2008)]. In general the lower-order terms of Eq. 1.20 dominate, however, in the presence of high electric fields, such as around plasmonic materials at resonance, the higher-order terms become non-negligible. The linear effects consistent with the  $\chi^{(1)}$  term such as scattering and absorption are well understood [van de Hulst (1958)]. In the presence of strong fields, nonlinear effects need to be considered. Frequencies of radiation different from the incident will be produced due

to the  $E^n$  term when  $n \neq 1$ . Moreover, these new frequencies interact with the incident field that further influence the nonlinear fields produced. Sum- and difference-frequency generation are a result of the nonlinear response; an example of sum-frequency generation is two incident photons with the same frequency interact in the second order and produce one photon with double the frequency [Canfield et al. (2007)].

For a frequency  $\omega$ , first order responses vary as  $\Re[e^{-i\omega t}]$ ; second order responses vary as  $\Re[e^{-i\omega t}]^2 = \frac{1}{2}(1 + \Re[e^{-2i\omega t}])$ , where  $\Re$  denotes the real part. This is where the similarity between the second order responses that oscillate  $\propto 2\omega$  and the non-oscillating rectification responses are seen [Shen (1984)]. To this end DC responses can be measured by detecting the second harmonic,  $\cos(2\omega t)$ , term that has the same magnitude. It is such DC responses that are responsible for the Lorentz forces.

## Derivation of radiation and polarization forces

The force on an atom in the presence of electromagnetic fields can be determined by the Lorentz force,  $\mathbf{F}$  [Gordon (1973)]:

$$\mathbf{F} = (\mathbf{p} \cdot \nabla) \mathbf{E} + \frac{1}{c} \frac{d\mathbf{p}}{dt} \times \mathbf{B}, \quad (1.21)$$

where  $\mathbf{p}$  is the dipole moment of the atom,  $c$  is the speed of light,  $\mathbf{E}$  is the electric field and  $\mathbf{B}$  is the magnetic. The electric and magnetic field vary time-harmonically such that  $\mathbf{E} = \Re[\mathbf{E}_0 e^{-i\omega t}]$ ,  $\mathbf{B} = \Re[\mathbf{B}_0 e^{-i\omega t}]$ ,  $\mathbf{p} = \Re[\mathbf{p}_0 e^{-i\omega t}]$ . The time-average of the total force can be written as [Chaumet and Nieto-Vesperinas (2000)]:

$$\langle \mathbf{F} \rangle = \frac{1}{4T} \int_{-T/2}^{T/2} [(\mathbf{p} + \mathbf{p}^*) \cdot \nabla(\mathbf{E} + \mathbf{E}^*) + \frac{1}{c}(\dot{\mathbf{p}} + \dot{\mathbf{p}}^*) \times (\mathbf{B} + \mathbf{B}^*)] dt, \quad (1.22)$$

where  $\dot{\mathbf{p}} = \partial\mathbf{p}/\partial t$ . Performing the integral of Eq.1.22 for the  $i$ th Cartesian component the time averaged force becomes:

$$\langle F^i \rangle = \frac{1}{2} [p_{0j} \partial^j (E_0^i)^* + \frac{1}{c} \epsilon^{ijk} p_{0j} (\dot{B}_{0k})^*], \quad (1.23)$$

where  $\epsilon^{ijk}$  is the Levi-Cevita symbol. The dipole moment can be written as a reaction to the electric field  $p = \alpha E$ , and using the Maxwell equation:

$$\nabla \times \mathbf{E} = \frac{1}{c} \frac{\partial \mathbf{B}}{\partial t} = \frac{-i\omega}{c} \mathbf{B} \quad (1.24)$$

Equation 1.23 then becomes:

$$\langle F^i \rangle = \frac{1}{2} \Re [\alpha [E_{0j} \partial^j (E_0^i)^* + \epsilon^{ijk} \epsilon_{klm} E_{0j} \partial^l (E_0^m)^*]] \quad (1.25)$$

Using the relation between Levi-Cevita notation  $\epsilon^{ijk} \epsilon_{klm} = \delta_l^i \delta_m^j - \delta_m^i \delta_l^j$  the time-averaged DC force can be written as:

$$\langle F^i \rangle = \frac{1}{2} \Re [\alpha E_{0j} \partial^j (E_0^i)^*] \quad (1.26)$$

$$\langle \mathbf{F} \rangle = \frac{1}{2} \Re [\alpha \sum_i E_i \nabla E_i^*] \quad (1.27)$$

Resulting in a non-zero DC force in terms of an oscillating electromagnetic field.

# Chapter 2

## Ultra-low-intensity magneto-optical and mechanical effects in metal nanocolloids

### 2.1 Introduction

The plasmonic resonances of noble metal nanostructures manifest in the visible spectral range and have a fundamental role in shaping the optical properties of materials [Link and El-Sayed (1999); Cortie and Ford (2007)]. At such resonances the electromagnetic fields are concentrated around sub-wavelength structures producing high local field enhancements, which has been the study of many investigations [Barnes et al. (2003); Kelly et al. (2003); Ozbay (2006)]. Since the resonances are highly dependent on the refractive index of the material, as well as the surrounding medium, methods that modify a materials refractive index *i.e.*, electro-optically [Dicken et al. (2008); Chyou et al. (2005)] or thermally [Nikolajsen et al. (2004)], are realised by a shift in the plasmonic resonance. An external magnetic field can also modulate a material's optical properties if the material exhibits magneto-optical (MO)

behaviour [Temnov et al. (2010); Gonzalez-Diaz et al. (2009); Hai-Dong et al. (2008)]. The concurrent application of a magnetic field is associated with additional phenomena such as increased Faraday rotation [Du et al. (2011)], MO enhancement of localized and propagating surface plasmons [Sepulveda et al. (2010); Torrado et al. (2010)], or introduction of new magnetic modes [Pineider et al. (2013); Tang et al. (2011); Fan et al. (2010)]. Observations of these MO phenomena, however, are generally small unless the plasmonic material is mated with a ferromagnet. Another class of MO responses involves non-oscillating, DC, magnetic modes. Such modes are achieved in non-magnetic media via the polarization-dependent inverse Faraday effect [Hertel (2006)] though this DC or low frequency MO response is claimed to be too small to observe at room temperature and at low intensities due to thermal fluctuations [Gu and Kornev (2010)] (the effect is observed with high intensity lasers,  $>370$  MW/cm $^2$  [Raja et al. (1995)]). Recently, anomalously-large photo-induced magnetic responses are observed in non-ferromagnetic metal nanocolloids [Singh et al. (2012)], however the origin of the effect is unexplained. This chapter identifies and analyses the threshold transition between linear and nonlinear effects, which we attribute to a mechanical response of the nanocolloid.

This chapter demonstrates that nonzero time-averaged vortex currents on nanostructures enable the magnetization of non-magnetic materials and that such DC MO plasmonic responses are observable with broadband light illumination intensities less than 1 W/cm $^2$ . Moreover, there exists a nonlinear MO response that is explained by the theoretical model of Hertel (2006) when applied to nanostructures [Singh et al. (2012); Brandao and Cavalcanti (2013); Bliokh et al. (2011)]. This coupling between incident and scattered fields yields nonzero time-averaged azimuthal vortex power flows that differ distinctly in character from the polar-coordinate whirlpool flows investigated in other work [Boriskina and Reinhard (2012); Bashevoy et al. (2005)]. The vortex power flows associated with azimuthal currents that result in the formation of DC magnetic dipoles is quantified. More importantly, it

is demonstrated that such dipoles are non-negligible and external magnetic fields influence the nanocolloidal optical properties. Experimentally, the response is observed in the extinction spectra of aqueous 80-nm gold nanospheres when illuminated with circularly-polarized light and DC magnetic fields, in which changes occur on minute time-scales. The retarded response is attributed to magnetic-dipole interactions and the mechanical movement and settling of asymmetrical nanoparticles and nanoclusters. The formation of realizable DC magnetic dipoles and the associated mechanical effects are verified in numerical simulations.

Both linear and nonlinear plasmon phenomena lead to MO responses. Linear characteristics associated with volume charge densities are distinct from nonlinear characteristics associated with surface charges, which dominate the MO response above low-threshold magnetic fields. The linear dynamics are described by a conventional Hall-effect Drude model [Mullvaney (1996)], which provides a magnetic-field dependent refractive index via the Lorentz force. In contrast, the nonlinear dynamics are identified with the inverse Faraday effect, which yields a nonlinear current density proportional to the incident electric field intensity [Hertel (2006)]. It is fundamental to our analysis that while there is no net current i.e.,  $\langle \vec{j}_x \rangle = \langle \vec{j}_y \rangle = \langle \vec{j}_z \rangle = 0$ , non-zero time-averaged current loops exist such that  $\langle \vec{j}_\phi \rangle \neq 0$ . This existence of nonzero  $\langle \vec{j}_\phi \rangle$  forms the basis of the nonlinear DC MO response.

## 2.2 Linear dynamics

### 2.2.1 Addition of magnetic fields to equations of motion

The linear dynamics of the volume charge density, within the quasi-static limit [Maier (2007a)], are governed by the equations of motion with the Lorentz force:  $m^* \frac{d^2 \vec{r}}{dt^2} + m^* \gamma \frac{d\vec{r}}{dt} = q\vec{E} + q(\frac{d\vec{r}}{dt} \times \vec{B})_r - k\vec{r}$ , where  $\vec{r}$  denotes the spatial coordinate,  $m^*$  is the effective mass of the electron,  $\gamma$  is the decay rate,  $q$  is the charge of an electron, and  $k$  is the force

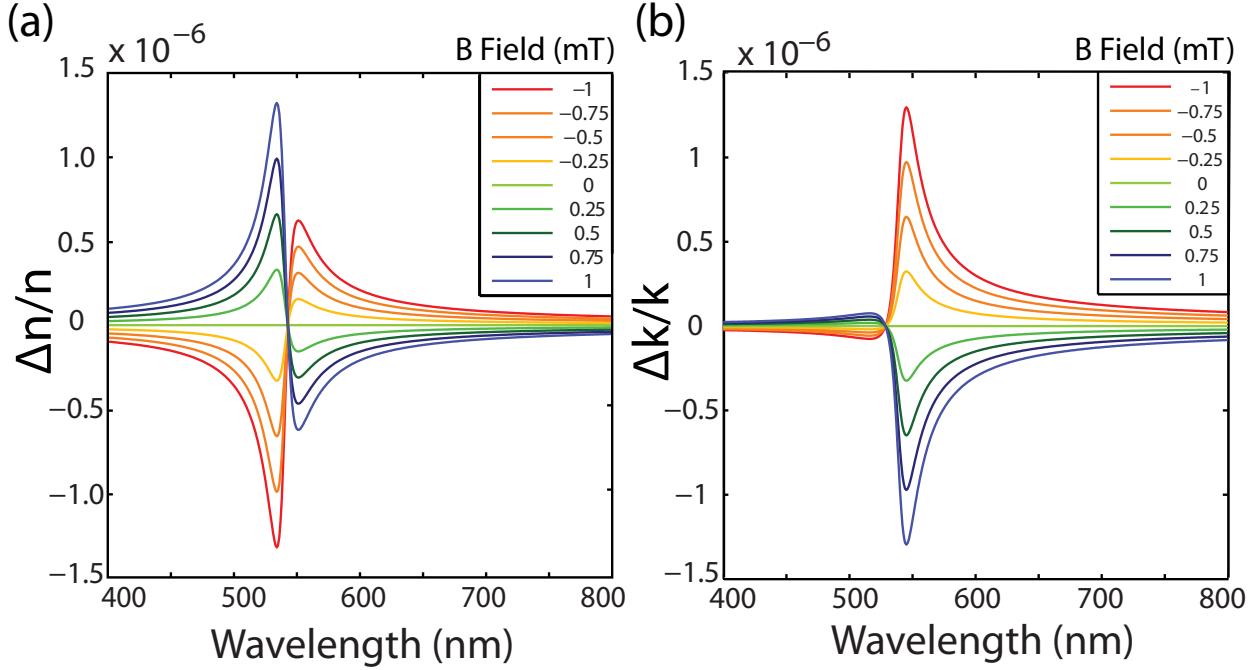


Figure 2.1: Relative MO shift of bulk gold when external fields are varied. (a) Real and (b) imaginary parts of the refractive index as a function of wavelength under illumination of  $1 \text{ W/cm}^2$  RHCP when magnetic fields are varied.

constant associated with the restoring force. The electric field propagates in the  $\hat{z}$  direction with time-harmonic circular-polarization of angular frequency  $\omega$  and amplitude  $E_0$ ,  $\vec{E}_\pm = E_0 e^{-i\omega t} (\hat{x} \pm i\hat{y})/\sqrt{2}$ , where  $+(-)i\hat{y}$  represents a right(left)-handed circular-polarized wave or RHCP(LHCP). When an externally-applied DC magnetic field is aligned with the direction of the electric-field propagation,  $\vec{B} = B_0 \hat{z}$ , the equations of motion yield a dielectric function in the form of a gyrotropic tensor:  $\epsilon = 1 + \omega_p^2 \begin{pmatrix} \alpha & -\beta & 0 \\ \beta & \alpha & 0 \\ 0 & 0 & \zeta \end{pmatrix}$ , in which  $\alpha = \frac{\omega_0^2 - \omega^2 - i\gamma\omega}{(\omega_0^2 - \omega^2 - i\gamma\omega)^2 + (\omega\omega_c)^2}$ ,  $\beta = \frac{i\omega\omega_c}{(\omega_0^2 - \omega^2 - i\gamma\omega)^2 + (\omega\omega_c)^2}$ , and  $\zeta = \frac{1}{\omega_0^2 - \omega^2 - i\gamma\omega}$ , where  $\omega_c = qB_0/m^*$  is the cyclotron frequency,  $\omega_p$  is the plasma frequency such that  $\omega_p^2 = \eta q^2/m^* \epsilon_0$ ,  $\omega_0$  is the frequency associated with a harmonic restorative force, and  $\eta$  is the electron density. The Lorentz force is largest when the DC magnetic field is parallel to the propagation of light [Sepulveda et al. (2010)].

As can be seen in Fig. 2.1, around the plasmon resonance (540 nm) there are significant shifts in the real and imaginary parts of the refractive index. This MO model explains the response from small magnetic-field perturbations, however is insufficient to explain the changes in optical properties at higher applied magnetic fields [Singh et al. (2012)]. The MO response of noble metals (calculated with linear dynamics) is significantly smaller compared to that which occurs with ferromagnets in part because the difference between the cyclotron and plasma frequencies is orders of magnitude apart [Schnatterly (1969)]. Moreover, the MO response depends on other factors such as the exchange interaction, specific band structure and spin-orbit coupling that allow ferromagnetic materials to have a greater MO response than noble metals [Armelles et al. (2013)].

## 2.3 Nonlinear dynamics

### 2.3.1 Nonlinear current density

In departure from prior investigations of MO effects on nanostructures, an analytical expression derived from the continuity equation [Hertel (2006)] describes a time-averaged solenoidal magnetization current density:

$$\langle \vec{j}_m \rangle = \frac{i}{4q\langle \eta \rangle \omega} \nabla \times (\sigma_0^* \vec{E}^* \times \sigma_0 \vec{E}), \quad (2.1)$$

where  $\langle \eta \rangle$  is the time-averaged electron density,  $\sigma_0$  is the specific conductivity of gold, and  $\vec{E}$  is the total electric field at the surface. As seen in Eq.(2.1)  $\langle \vec{j}_m \rangle$  is polarization-dependent in its direction and magnitude. For a circularly-polarized  $\vec{E}$  the term  $\vec{E}_\pm \times \vec{E}_\pm^*$  becomes  $\pm i|\vec{E}_0|^2 \hat{z}$  and for a linearly-polarized field this term is zero. Note that  $\langle \vec{j}_m \rangle$  scales inversely with  $\langle \eta \rangle$ , which may explain MO effects in non-metallic nanostructures [Kuznetsov et al. (2012)] and also scales with the intensity, in contrast to linear currents which scale with the

electric field ( $\vec{j} = \sigma_0 \vec{E}$ ).

### 2.3.2 Nonlinear magnetization

In our investigation of nanospheres, the time-averaged nonlinear current density is significant only in the azimuthal direction,  $\hat{\phi}$ ,  $\langle j_{m,r} \rangle = 0$ ,  $\langle j_{m,\theta} \rangle \ll \langle j_{m,\phi} \rangle$ . Although linear time-harmonic azimuthal currents exist, the current direction reverses every 1/2 cycle and time-average to zero. Since the nonlinear surface currents produce an anisotropic field-dependent perturbation to the specific conductivity, it is reasonable to employ a formalism similar to that used for the nonlinear polarization with the nonlinear current density as  $\vec{j}_p(\vec{E}) = \vec{j}_p^{(1)}(\vec{E}) + \vec{j}_p^{(2)}(\vec{E}, \vec{E}) + \dots = \sigma_{p,r}^{(1)} E_q + \sigma_{p,r,s}^{(2)} E_r E_s + \dots$ , where  $\sigma_{p,r}^{(1)}$  is the specific conductivity in isotropic media. Using Eq. (2.1) and Levi-Cevita notation  $\sigma_{p,r,s}^{(2)}$  can be written as a third-rank tensor in the form:

$$\sigma_{p,r,s}^{(2)} = \frac{i|\sigma_0|^2}{4q\langle\eta\rangle\omega} \frac{\epsilon_{p,r,s} \hat{\partial}_r \epsilon_{s,t,u} E_t^* E_u}{E_r E_s}. \quad (2.2)$$

A relation for the induced magnetization can also be obtained using  $\vec{j}_m = \nabla \times \vec{M}$ , such that:

$$\vec{M}_p = \frac{i|\sigma_0|^2}{4q\langle\eta\rangle\omega} \epsilon_{p,r,s} E_r^* E_s \quad (2.3)$$

## 2.4 Numerical predictions

### 2.4.1 Finite-element simulation results

Numerical, finite-element simulations illustrate the strong polarization dependence of the nonlinear current density that the theoretical analyses predict. As seen in Fig. 2.2(a) the

induced nonlinear current density,  $\langle \vec{j}_{m,\phi} \rangle$ , is calculated for an aqueous 80-nm gold nanosphere illuminated in the  $\hat{z}$  direction with different polarizations. To simplify the notation of the

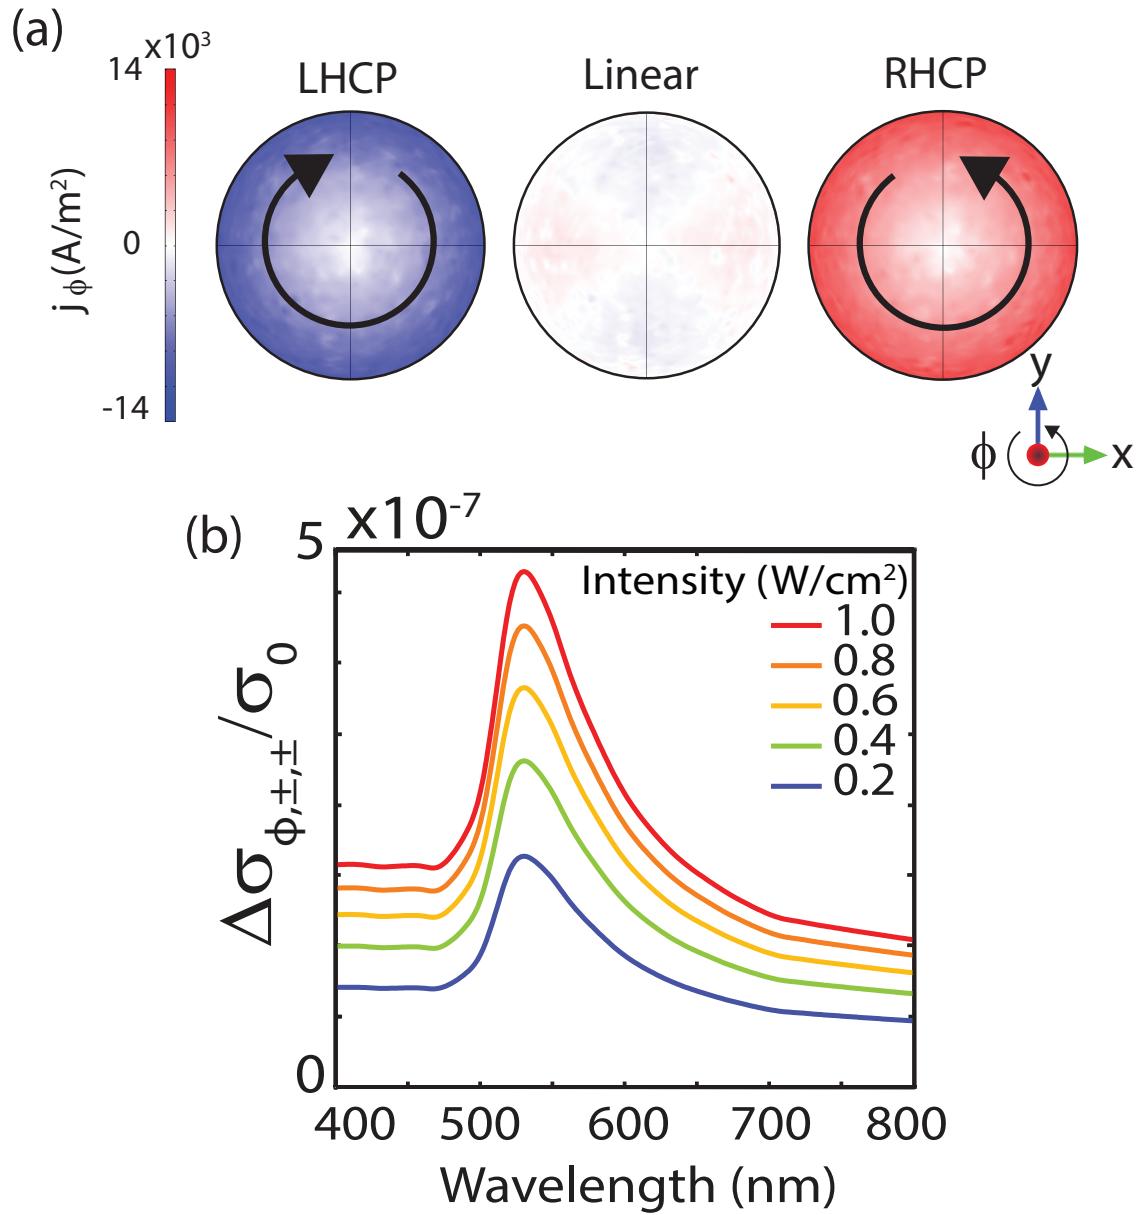


Figure 2.2: (a) Surface plots of the nonlinear current density of an aqueous 80-nm gold nanosphere when illuminated by LHCp, linearly-polarized and RHCp light in the  $\hat{z}$  direction at the plasmon resonance, 540 nm, at 1  $W/cm^2$ . (b) Volume-averaged relative change in azimuthal component of the conductivity as a function of wavelength when illumination intensity is varied for RHCp or LHCp.

nonlinear conductivity response only the first subscript of  $\sigma^{(2)}$  that denotes the direction of the anisotropic change. It can be shown that  $\sigma^{(2)}$  is nonzero only for curvilinear coordinates such as  $\phi$  or  $\theta$  in spherical coordinates. The numerical calculations illustrate that  $\sigma_{\phi}^{(2)}$  is negligible for incident linear polarization, and RHCP and LHCP yield the greatest  $\sigma_{\phi}^{(2)}$  with equal direction and magnitude; as illustrated in Fig. 2.2(b), as the light intensity increases, the conductivity of the nanoparticle also increases uniformly across wavelengths for both RHCP and LHCP. Since both the azimuthal currents ( $\propto \nabla \times \vec{E}^* \times \vec{E}$ ) and the electric-field components ( $\vec{E}_{\phi}$ ) reverse direction with polarization handedness, by symmetry, the relative changes in the conductivity tensor are identical for both RHCP and LHCP.

## 2.5 Experimental observation

### 2.5.1 Observation of transition from linear to nonlinear dynamics

Experimental data of relative MO changes in transmission spectra are illustrated in Fig. 2.3, alongside analytical results. The experiments were performed with samples of 0.05 mg/mL 80-nm poly-vinyl pyrrolidone(PVP)-capped gold nanoparticles dispersed in aqueous solution ( $2.5 \times 10^{-6}$  fill factor). A solar simulator, polymer thin-film linear polarizer, and 400-800 nm achromatic quarter-wave plate produce RHCP white light, and a Helmholtz coil generates a uniform magnetic field in the direction of light propagation around the sample. A CCD spectrometer that captures the extinction spectra is placed behind a 0.5-cm optical path length cuvette containing samples.

The dominant response is dependent on the illuminating light polarization at low magnetic fields and is polarization-independent in the presence of higher magnetic fields; a threshold behaviour exists. Experimentally, a magnetic field of 0.9 mT is associated as the bound between the linear (polarization-dependent) and nonlinear (polarization-independent) dy-

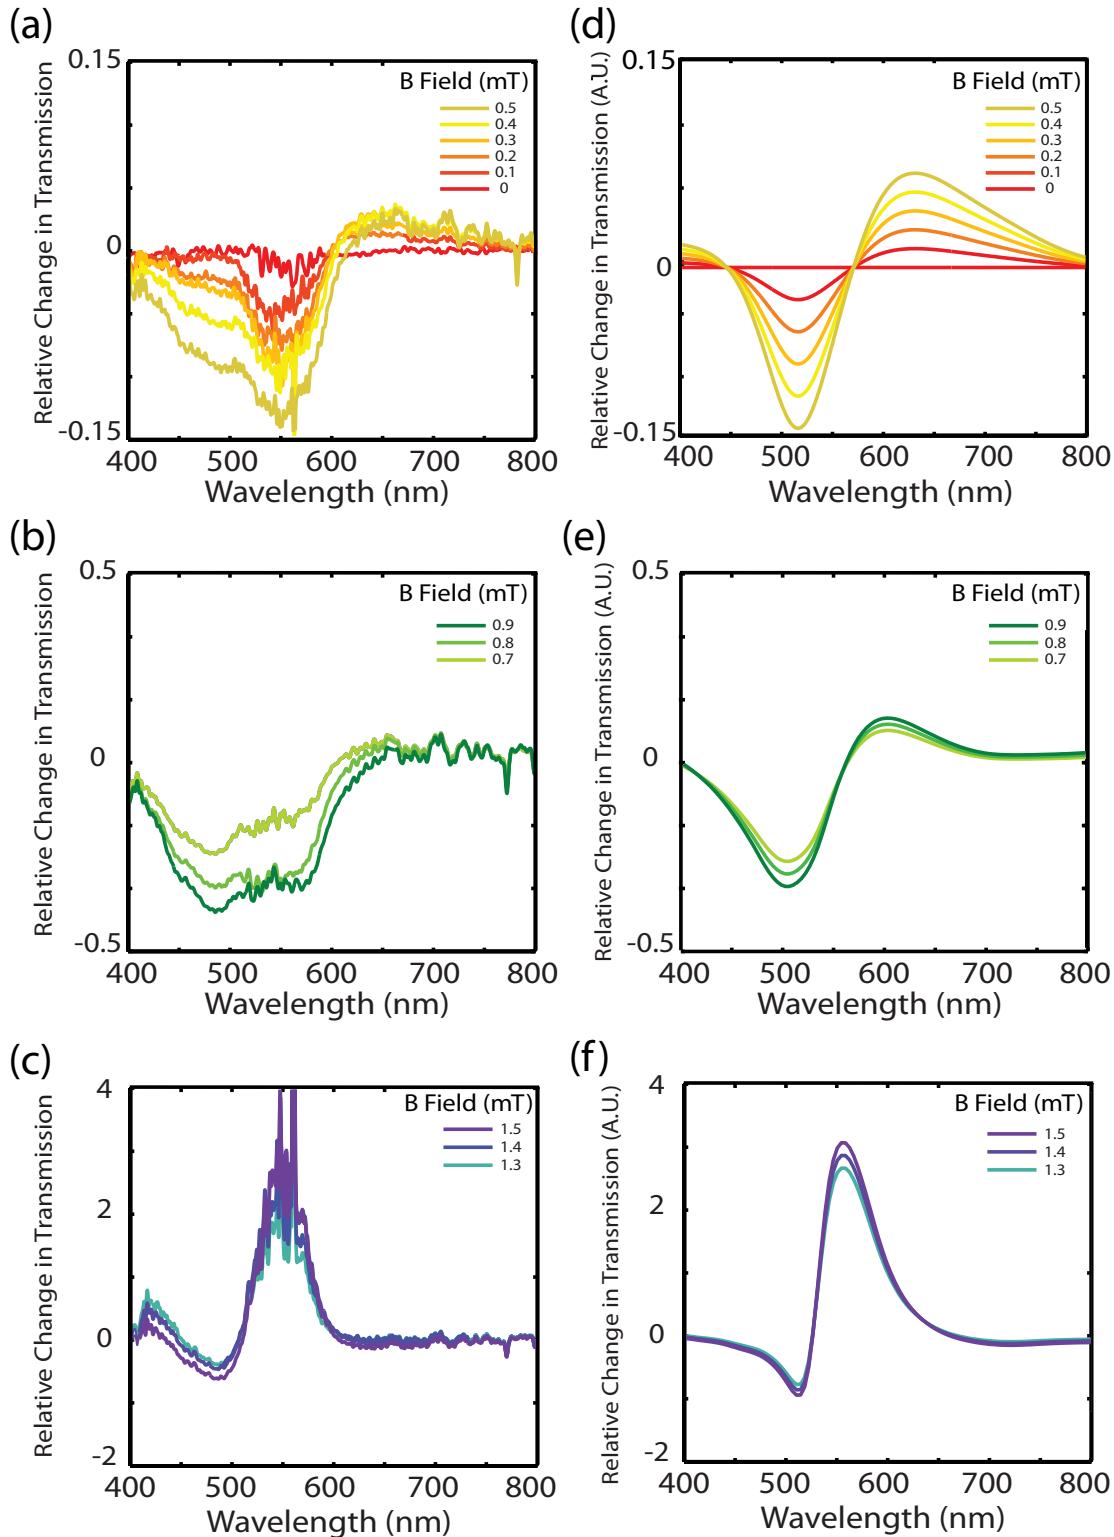


Figure 2.3: (Continued on the following page.)

Figure 2.3: (Previous page.) Normalized MO changes in transmission for aqueous gold nanocolloid at (a) low magnetic fields (b) intermediate magnetic fields and (c) higher magnetic fields. Theoretical MO change in transmission of aqueous 80-nm gold nanospheres in the (d) linear and (f) nonlinear analyses. Theoretical MO changes that combine the linear and nonlinear analyses are shown in (e) for intermediate magnetic fields. In all plots the illumination is  $1 \text{ W/cm}^2$  and RHCP.

namics. The experimental data [Fig. 2.3(a-c)] shows relative transmission data for RHCP and positive magnetic fields. Below the threshold, differences between the handedness of the polarizations are observed; the MO response is approximately equal and opposite in magnitude. Above, the transmission is similar for both RHCP and LHCP.

The experimental data agrees with analytical theory when the changes of the refractive index [Fig. 2.1] and conductivity [Fig. 2.2(b)] are incorporated to Mie theory [Mie (1908)] and the corresponding relative changes in extinction spectra are computed. These calculated linear and nonlinear MO responses are shown separately in Fig. 2.3(d) and Fig. 2.3(f) respectively, and both linear and nonlinear MO responses are incorporated to analyse the total response at intermediate fields near the threshold [Fig. 2.3(e)]. The relative change in the nonlinear MO response has been scaled to reflect the experimental behaviour. The nonlinear response is modelled as a function of the external magnetic field, which tunes the strength of the coupling that causes the MO response. The threshold behaviour observed experimentally is expected to occur when the theoretical linear and nonlinear effects are comparable. Moreover, our theoretical model provides excellent quantitative agreement; in our analysis of a single nanosphere the changes in the refractive index and conductivity via the linear and nonlinear responses are of similar magnitude with  $1\text{-W/cm}^2$  illumination intensities and  $1\text{-mT}$  magnetic fields. The transition between the polarization-dependent linear response and the polarization-independent nonlinear response occurs when either the magnetic field strength or the intensity of light is varied.

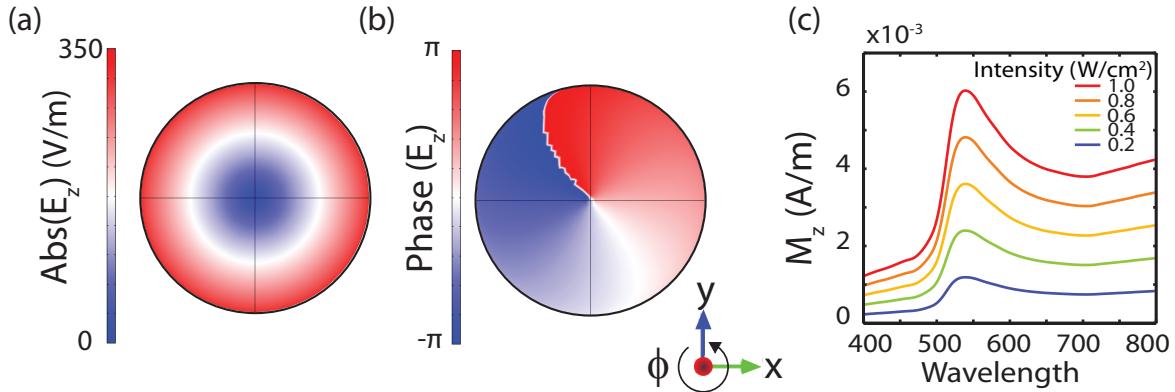


Figure 2.4: Numerically calculated (a) amplitude and (b) phase of the longitudinal component of the electric field,  $E_z$ , with 540-nm  $1 \text{ W/cm}^2$  RHCP illumination intensity. (c) Volume-averaged magnetization as a function of wavelength when illumination intensities are varied. All plots are for an aqueous 80-nm gold nanoparticle.

## 2.6 Discussion

### 2.6.1 Magnetization magnitudes

Our understanding of the light scattering at nanostructures is crucial for understanding both linear and nonlinear MO effects. In the limit of thin structures, the scattered component of the electric field is largest in the longitudinal direction,  $E_z$ , and carries phase singularities that change with circular polarization handedness [Vuong et al. (2010); Hasman et al. (2005)]. The locations of the phase singularities, as well as the topological charges themselves vary with nanostructure geometry and are associated with the loops in the *linear* current density. *Nonlinear* current loops are also produced by scattering events that induce surface charge densities, which couple with the incident fields [Eq. 2.1]. It is these nonlinear nonzero time-averaged current loops that lead to the material magnetization  $M_z$ . The amplitude and phase of  $E_z$  and corresponding  $M_z$  for an 80-nm gold nanosphere illuminated with RHCP are shown in Fig. 2.4. Although the non-magnetic nanoparticle magnetizations are small compared to that of a ferromagnet ( $10^5$  times smaller) due to masses on the order  $10^{-18} \text{ kg}$ , the subsequent mechanical motion becomes significant.

### 2.6.2 Time-dependent response

The delayed optical response to an applied magnetic field is likely the result of the settling motion of non-spherical nanoparticles and nanoclusters. Aggregates often form as a result of random Brownian motion and magnetic-dipole interactions, so they are considered in our analysis. Also acknowledged are irregularities in the nanoparticles employed in the experiments— they are not perfect spheres due to the fabrication process. Such variations from spherical geometry cause magnetization differences that depend on the nanoparticle orientation with respect to the electric field.

Changes in extinction spectra reflect the magnetization associated with the nanoparticle and nanoclusters reorientation. Structural anisotropy and orientation affect the magnetization of the nanoparticle, which is illustrated with dimer nanoclusters and ellipsoids of different aspect ratios. As can be seen in Fig. 2.5(a) there is a reduction in the magnetization by almost 50% as a dimer nanocluster rotates from minimal to maximal incident surface area with respect to electric field. The relative change in the magnetization is shown in Fig. 2.5(b) as a function of aspect ratio when ellipsoidal nanoparticles of equal volume are rotated from minimal to maximal incident surface area. Ellipsoids with aspect ratio 1 (spheres), exhibit no difference as they are rotated, and greater differences are observed when the aspect ratio increases. To guide the eye, a trendline that reflects the Biot-Savart law is provided in Fig. 2.5(b). Deviations from the trendline are attributed to changes in the plasmonic eigenfrequency. Regardless, anisotropy in the nanoparticle shape leads to MO magnetization that varies with the orientation, a concept in agreement with prior work Jain et al. (2006); Funston et al. (2009).

There exists a nanoparticle/nanocluster orientation with respect to the external magnetic field that maximises  $\langle \vec{j}_m \rangle$ . The system is expected to stabilize in an orientation that maximises the nanoparticle magnetization. The nanocolloid magnetization is largest at the

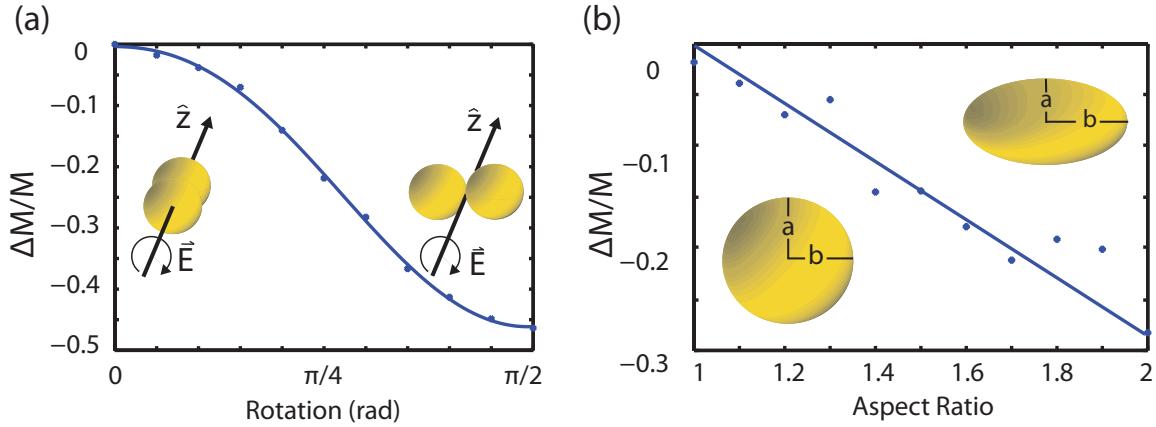


Figure 2.5: Numerically calculated relative change in magnetization (a) of a 80-nm gold dimer nanocluster as a function of angle of rotation, and (b) ellipsoidal gold nanoparticle rotated from minimal to maximal surface area as a function of aspect ratio, illuminated with 540-nm 1 W/cm<sup>2</sup> RHCP.

plasmon resonance when the local electric field and scattering is maximised.

Yet, scattering dynamics present a complex dynamical system that is not fully understood in the context of MO responses. Autocorrelation data reveals significant pulse broadening through gold nanocolloid solution that scales with the square of the sample thickness that suggests a strong scattering [Drake and Genack (1989)] despite low fill factors ( $2.5 \times 10^{-6}$ ). Another possibility for the larger-than-expected results is diffractive coupling between nanoparticles that can exhibit strong long-range interaction [Barnes and Ague (2009)] that lead to near-field enhancements, which are anticipated to increase in a 3-D matrix. The material properties of the matrix also influence the MO response. For instance, the presence of any ions or charged particles, common in solvents such as water, modifies the electrodynamics of the system, which subsequently influences the MO response of the system.

## 2.7 Conclusion

This chapter demonstrates the observation of MO responses in non-magnetic nanocolloids at ultra-low illumination intensities and magnetic fields. Metal nanocolloids are magnetized and the optical properties are shifted when excited by coincident elliptically-polarized electric fields and DC magnetic fields. Experimentally-observed extinction spectra are in good agreement with predictions of linear and nonlinear MO effects and new considerations are provided for novel mechanical effects that were previously considered unattainable. A theoretical model is demonstrated that successfully explains the transition between linear and nonlinear MO plasmon dynamics of metal nanoparticles. This chapter provides the theoretical framework to study MO responses in non-magnetic nanostructures. In particular, new methods to identify, optically self-assemble and magnetically torque large quantities of disperse, non-spherical nanoparticles with broadband light sources are realised.

## 2.8 Experimental difficulties and future work

The experimental procedure to study the transmission properties were quite difficult. One recurrent issue that occurred was a time dependence in the transmission properties before any magnetic field was applied. This issue was attributed to thermal stabilization of the system and was overcome by waiting for the transmission properties to thermally stabilize before turning on the magnetic field and taking any measurements.

Care was also taken in the amount of light intensity, as it was found that if the light intensity was too great, there would be aggregation and settling of the nanoparticles at the bottom of the substrate. Aggregation may affect the results by shifting the plasmonic resonance of the nanoparticles due to the increase in size, which may confound the results. Settling of the nanoparticles is also undesirable since there is a reduction of the nanoparticle density interacting with the electric and magnetic fields that way decrease the MO effect

and increase the transmission through the sample, confounding the results.

Future work on this subject may involve a deeper investigation of the threshold between the linear and nonlinear components that cause the respective transmission properties.

# **Chapter 3**

## **Plasmon-induced Lorentz forces of nanowire chiral hybrid modes**

### **3.1 Introduction**

While light is massless, it imparts momenta that are significant, which: confine ion beams [Petrich et al. (1993)]; propel solar sails [Janhunen and Sandroos (2007)]; rotate and twist objects [Beth (1936); Paterson et al. (2001); Tsai et al. (2014)]; levitate, trap, and move matter [Ashkin (1997); Nieminen et al. (2007); Novotny et al. (1997)]; cool atoms [Weiner et al. (1999)]; and alter the crystallization of solids [Chowdhury et al. (1985)]. Our knowledge of light's momentum transfer is intrinsic to the design of facilities for low-temperature and high-energy physics, cell and molecular biology, and advanced materials research [Ashkin (1997)], and is relevant to an expansive development of optomechanical devices for sensors and electronics technologies [Hugel et al. (2002); Kippenberg and Vahala (2007); Van Thourhout and Roels (2010)]. Currently, the laser trapping of uncharged dielectric matter is commonplace [Ashkin (1997)]; however, the optically-induced mechanics of conducting or plasmonic nanoparticles have been shown to be, at the very least, more complex [Dienerowitz et al.

(2008); Saija et al. (2009); Shvedov et al. (2010); Yan et al. (2012a,b, 2013a); Yan and Scherer (2013); Yan et al. (2013b)]. One challenge stems from the numerous channels through which energy is transferred: particles also move in the presence of electric fields, magnetic fields, and thermal gradients [Velev and Bhatt (2006); Keshoju et al. (2007); Edwards et al. (2006)], which are directly and indirectly produced by plasmons. Understanding these dynamic, momentum-conserving mechanisms involves, in part, understanding the interactions among these fields.

Theoretical considerations of the gradient-intensity trapping forces, radiation pressure forces, and induced-electric-dipole interactions [Ashkin (1997)] are insufficient for predicting the optomechanical behavior of plasmonic nanoparticles. It is increasingly apparent that the excitation of plasmons play a critical role in the optically-induced movement of nonspherical nanoparticles [Yan et al. (2013a)]. For example, a model of the induced electric dipole with an electric field only predicts that silver nanorods will align parallel to the direction of the illuminating linear polarization of light [Tong et al. (2010)], and that nanowires rotate continuously in the presence of circularly-polarized light or optical vortices via the transfer of spin or orbital angular momentum, respectively [Yan and Scherer (2013); Lehmuskero et al. (2013, 2014)]. However, this theoretical model that considers the nanoparticle polarizability alone cannot discriminate between the different mechanical behaviors associated with different nanorod-ends and particle aspect ratios [Tong et al. (2010)]. Nanoparticle geometry often dictates local surface plasmon modes [Knight et al. (2007)]; further insight into the physical phenomena that underlie the optomechanical behavior of non-spherical plasmonic particles is necessary.

This chapter investigates the Lorentz forces strictly attributed to surface plasmons on metal nanowires, which are of wide technological interest [Knight et al. (2007); Lal et al. (2007); Maier and Atwater (2005)], and potentially relevant to other plasmonic nanostructures such as carbon nanotubes, where similar chiral plasmonic behavior is tunable from the

UV to THz [Slepyan et al. (2006)]. The first successful trapping of a nanowire in a 3D optical trap identified an important role of plasmons. Yan, *et al.*, demonstrate that gold nanowires—but significantly, *not* silver nanowires—are confined by a Gaussian-beam optical trap [Yan et al. (2013a)]. Yan proposes that the macroscopic perspective of optical trapping is insufficient and should be replaced with a plasmonic model [Yan et al. (2012a)] and identifies asymmetric modes with trapping instabilities; nevertheless, to the best of our knowledge, a simple model that connects the dynamic instability of nanowires with its plasmonic behavior has not yet been advanced.

Plasmonically-induced Lorentz forces that are produced on gold nanowires by the illumination of linearly-polarized electromagnetic plane waves are investigated via numerical simulation. The plasmonically-induced forces are significant in chiral geometries and when chiral hybrid plasmonic modes [Zhang et al. (2011)] are present. This chapter identifies the electromagnetic torque and compression on the nanowires associated with the surface currents and asymmetric time-averaged fields. The results identify significant mechanical forces produced by surface plasmons in chiral hybrid modes that are currently neglected. Plasmonically-induced Lorentz forces are even expected to critically prevent the stable optical trapping of conducting nanowires, particularly when longer trapping-laser wavelengths *between* strong absorption resonances are employed. The approach highlights a critical dependence of nanoparticle shape [Knight et al. (2007); Tong et al. (2010)] and plasmon relaxation [Yan et al. (2013a)] on the optically-induced forces, and considerations are relevant to future microfluidic applications.

This chapter is organized as follows. In Sec. 3.2 the chiral geometry of our system is described, the numerical computations associated with Lorentz forces are outlined, and the asymmetric surface plasmon modes is illustrated. The electric dipole and plasmonic Lorentz forces of nanowires that are aligned in the transverse plane are evaluated, and agree with and clarify prior experimental results. In Sec. 3.3, the axial and translation forces associated

with surface plasmons are described, these forces are generally stronger than those associated with electric dipoles. In Sec. 3.4 an analysis of the torque forces that arise from the 3D scattering is provided. Analysis in this chapter ignores any nonlinear responses that may arise due to heat [Shvedov et al. (2010)], steam [Saija et al. (2009); Fang et al. (2013)], the electrochemical response of solvent [Arcenegui et al. (2013)], and nonlinear magneto-optical effects [Singh et al. (2012); Moocarme et al. (2014a)], although these effects are not negligible, particularly at high illumination intensities. Surface effects that may arise in the interaction between nanoparticles due to coatings or interfaces are also ignored, however this work is highly relevant to the understanding of such interactions with plasmonic materials [Bonin et al. (2002)]. The mechanical translation, compression, and torque forces associated with the plasmonic surface currents are significant and interfere with the optical trapping of elongated nanoparticles. The results in this chapter indicate that there exists a frequency cut-off at which the chiral plasmon excitation is minimized; avoiding chiral plasmon excitation will provide greater trapping stability.

## 3.2 Setup and simulations of 2D dynamics

### 3.2.1 Calculation of electromagnetic fields

In the numerical investigation (COMSOL v4.3a, RF module,  $\sim$ 2 million degrees of freedom), a linearly-polarized plane wave illuminates a gold nanowire immersed in deionized water, whose orientation is determined by  $\theta$  and  $\phi$ , as illustrated in Fig. 3.1(a). The nanowire dimensions are fixed with 75-nm diameter, and 950-nm length. The nanowire terminations are hemispherical, thus the nanowire measures 1025-nm end-to-end. The electromagnetic waves are polarized in the  $y$ -direction and propagate in the negative- $z$  direction.

In particular, this chapter focuses on the dynamics that occur when the wire is tilted

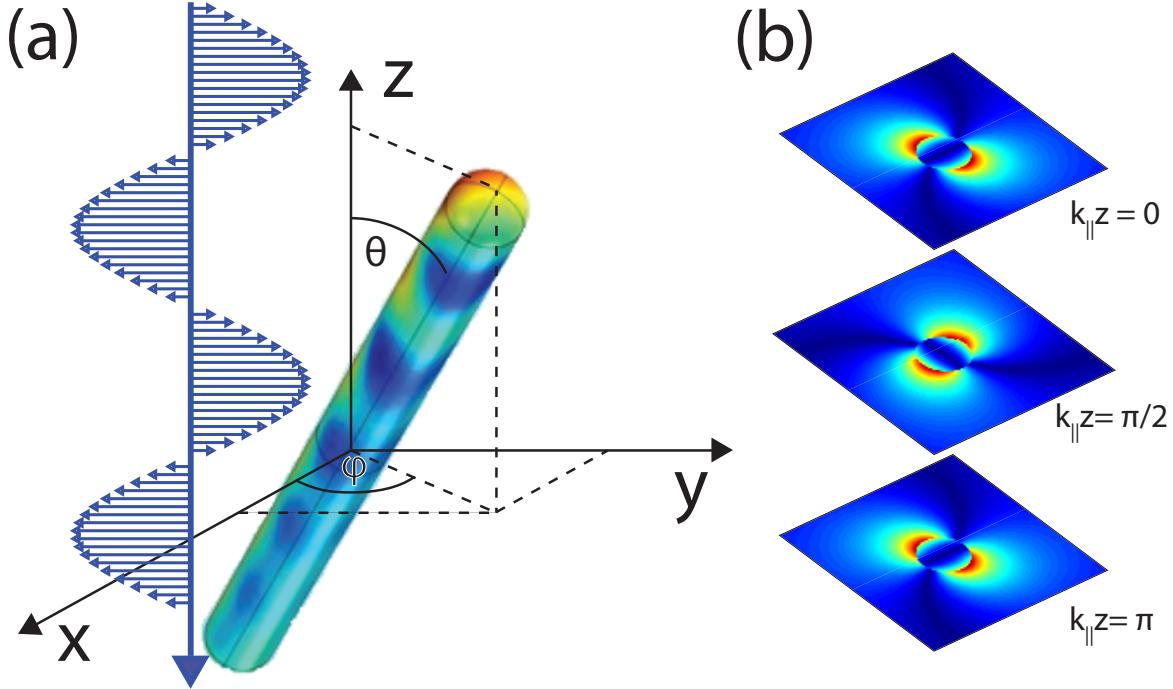


Figure 3.1: (a) System geometry: a gold nanowire (75-nm diameter, rounded-cap, 1025-nm length) is aligned about spherical coordinates  $\theta$  and  $\phi$ , and a  $y$ -polarized electromagnetic wave ( $1 \text{ W/cm}^2$ ) travels in the  $-z$  direction. (b) The electric field profile surrounding a nanowire resulting from superposed angular momentum modes  $m = 0, \pm 1$  with propagation lengths  $k_{\parallel}z = 0, \pi/2$ , and  $\pi$ .

towards the incoming plane wave, i.e.,  $\theta \neq 90^\circ$ . Such arrangements produce chiral plasmons, which are superpositions of the transverse and longitudinal modes. The signature for such modes is a time-averaged electric-field amplitude on the surface of the nanowire that varies azimuthally and over the length of the sample, a result of the superposition of two or more plasmon modes with varying azimuthal angular momentum number  $m$ , which are excited simultaneously by the incident fields. The phase difference associated with the different angular momentum numbers  $m$  determines the asymmetric nanowire intensity patterns [Zhang et al. (2011)]. In cylindrical coordinates the electromagnetic fields take the form [Chang et al. (2007)]:

$$\begin{aligned}
E_j(r) = \frac{1}{k_j} & \sum_m \left\{ \left[ \frac{m}{s} a_{j,m} F_{j,m} + \frac{k_m^{(\parallel)} k_{j,m}^{(\perp)}}{k_j} b_{j,m} F'_{j,m} \right] i \hat{s} \right. \\
& - \left[ k_{j,m}^{(\perp)} a_{j,m} F'_{j,m} + \frac{m k_m^{(\parallel)}}{k_j s} b_{j,m} F_{j,m} \right] \hat{\phi} \\
& \left. + \frac{[k_{j,m}^{(\perp)}]^2}{k_j} b_{j,m} F_{j,m} \hat{z} \right\} e^{ik_m^{(\parallel)} z + im\phi}
\end{aligned} \tag{3.1}$$

$$\begin{aligned}
H_j(r) = \frac{i}{\omega \mu_0} & \sum_m \left\{ \left[ \frac{k_m^{(\parallel)} k_{j,m}^{(\perp)}}{k_j} a_{j,m} F'_{j,m} + \frac{m}{s} b_{j,m} F_{j,m} \right] i \hat{s} \right. \\
& - \left[ \frac{m k_m^{(\parallel)}}{k_j s} a_{j,m} F_{j,m} + k_{j,m}^{(\perp)} F'_{j,m} \right] \hat{\phi} \\
& \left. + \frac{[k_{j,m}^{(\perp)}]^2}{k_j} a_{j,m} F_{j,m} \hat{z} \right\} e^{ik_m^{(\parallel)} z + im\phi}
\end{aligned} \tag{3.2}$$

where  $(s, \phi, z)$  are the cylindrical coordinates, the wave vectors are related by  $\epsilon_j k_0^2 = [k_{j,m}^{(\perp)}]^2 + [k_m^{(\parallel)}]^2$  where  $\epsilon_j$  is the dielectric constant in region  $j$  and  $k_0$  is the wave vector in vacuum.  $j = 1$  outside the cylinder where  $F_{1,m} = H_m(k_{1,m}^{(\perp)} s)$ , the Hankel function of  $m^{\text{th}}$  kind.  $j = 2$  inside the cylinder where  $F_{2,m} = J_m(k_{2,m}^{(\perp)} s)$ , the Bessel function of  $m^{\text{th}}$  kind, and primes denote derivatives with respect to the argument.  $a_{j,m}$  and  $b_{j,m}$  are constants determined by boundary conditions. The modes excited in this system are the  $m = 0$ ,  $\text{TM}_0$  mode and two degenerate first order  $m = \pm 1$  modes,  $\text{HE}_{\pm 1}$ . Specifically, chiral-hybrid modes occur when all three of the lower order modes are simultaneously excited *and* there is a phase difference between the  $\text{HE}_1$  and  $\text{HE}_{-1}$  modes. A superposition of the three lowest order modes,  $|m| \leq 1$  are shown in Fig. 3.1(b) at different cross-sections of the nanowire corresponding to  $k_1^{(\parallel)} z = 0, \pi/2$ , and  $\pi$ . In general, the patterns in the electromagnetic fields produced off-resonance correspond to a periodic, asymmetric pattern on the wire that neither

carries mirror symmetry along the length nor across the width of the wire. We anticipate that it is this asymmetry, which arises from the chiral illumination geometry, that produces a net translation and torques via Lorentz forces.

### 3.2.2 Calculation of Lorentz force

The well-known Lorentz law,  $\mathbf{f}_{Lorentz} = q(\mathbf{E} + [\mathbf{v} \times \mathbf{B}])$ , governs the force on a charge  $q$  with velocity  $\mathbf{v}$  in the presence of electric and magnetic fields,  $\mathbf{E}$  and  $\mathbf{B}$ . While it is true that displacement of a charged particle can be resolved to physical quantities such as dielectric function and plasma frequency the focus of our investigation is related the macroscopic movement of the nanowires. Investigated here, are the Lorentz forces that act on a free electron gas which is bound to the surface of the nanowire. Such forces arise from time-harmonic electric and magnetic fields and subsequently, the effects of time-harmonic charge densities and surface currents. We rewrite in time-averaged macroscopic force density:

$$\langle \mathbf{f}_{Lorentz} \rangle = \rho[\mathbf{E}^* + (\mathbf{v} \times \mathbf{B}^*)] + c.c. \quad (3.3)$$

$$= \epsilon_0(\nabla \cdot \mathbf{E})\mathbf{E}^* + \mathbf{J} \times \mathbf{B}^* + c.c. \quad (3.4)$$

$$= \mathbf{f}_E + \mathbf{f}_M \quad (3.5)$$

where  $\rho$  is the charge density,  $\epsilon_0$  is the permittivity constant, and *c.c.* refers to the complex conjugate.  $\mathbf{J}$  is the current density and can be determined from the electric field [Eq. 3.1] via the relation  $\mathbf{J} = \sigma\mathbf{E}$ . The volume-integrated terms of Eq. 3.4 yield separate effects. The induced electric-dipole force,  $\mathbf{f}_E$ , depends on the polarizability of the material, which is also shape-dependent [Liaw et al. (2014)] while the Lorentz force associated with surface currents,  $\mathbf{f}_M$ , is the focus of this investigation.

### 3.2.3 Calculation of torque forces

Also studied are the net torque forces associated with Eq. 3.4 with respect to the origin and geometric nanowire center. The torque associated with  $\mathbf{f}_M$  is numerically computed directly:

$$\mathbf{T}_M = \int_V \mathbf{r} \times \mathbf{f}_M dV, \quad (3.6)$$

whereas the time-averaged torque associated with the induced electric dipole is

$$\mathbf{T}_E = \int_V \mathbf{r} \times \mathbf{f}_E dV = \int_V \mathbf{P} \times \mathbf{E}^* dV + c.c., \quad (3.7)$$

where  $\mathbf{P}$  is the polarization and  $\mathbf{r}$  is the radial coordinate vector in spherical coordinates. Eqs 3.4, 3.6, 3.7, are calculated over the volume of the nanowire in the numerical simulations.

The study is introduced with a presentation of the well-studied plasmon-induced forces when the nanowire is normal to the incident electromagnetic wave, which represents the experiments performed when wires are pressed via radiation pressure along a normal surface such as a microscope slide in a 2-D trap [Tong et al. (2010)]. In this configuration, chiral plasmons are not produced; nevertheless, surface plasmons produce significant Lorentz forces. Figure 3.2(a) shows the absorption cross-section for a nanowire in this transverse configuration. When the nanowire is aligned with the polarization of incident radiation ( $\theta = 90^\circ, \phi = 90^\circ$ ), the longitudinal modes ( $\lambda = 625\text{nm}, 790\text{nm}$ ) are present; when it is aligned perpendicular ( $\theta = 90^\circ, \phi = 0^\circ$ ), only the transverse mode ( $\lambda = 510\text{nm}$ ) is present.

The longitudinal components of  $\mathbf{f}_M$  are significant (on the order of  $\text{pN}/(\text{MW}/\text{cm}^2)$ ) in the direction of light propagation ( $-z$ ) when the transverse and longitudinal plasmonic resonances are present [Fig. 3.2(c)]. Large longitudinal forces arise between wavelengths  $\lambda = 900\text{-}1100\text{nm}$  in where there is large scattering and low absorption [Fig. 3.2(a), (b)]. When the wire is perpendicular to the light polarization ( $\phi = 0^\circ$ ), the longitudinal force is positive and

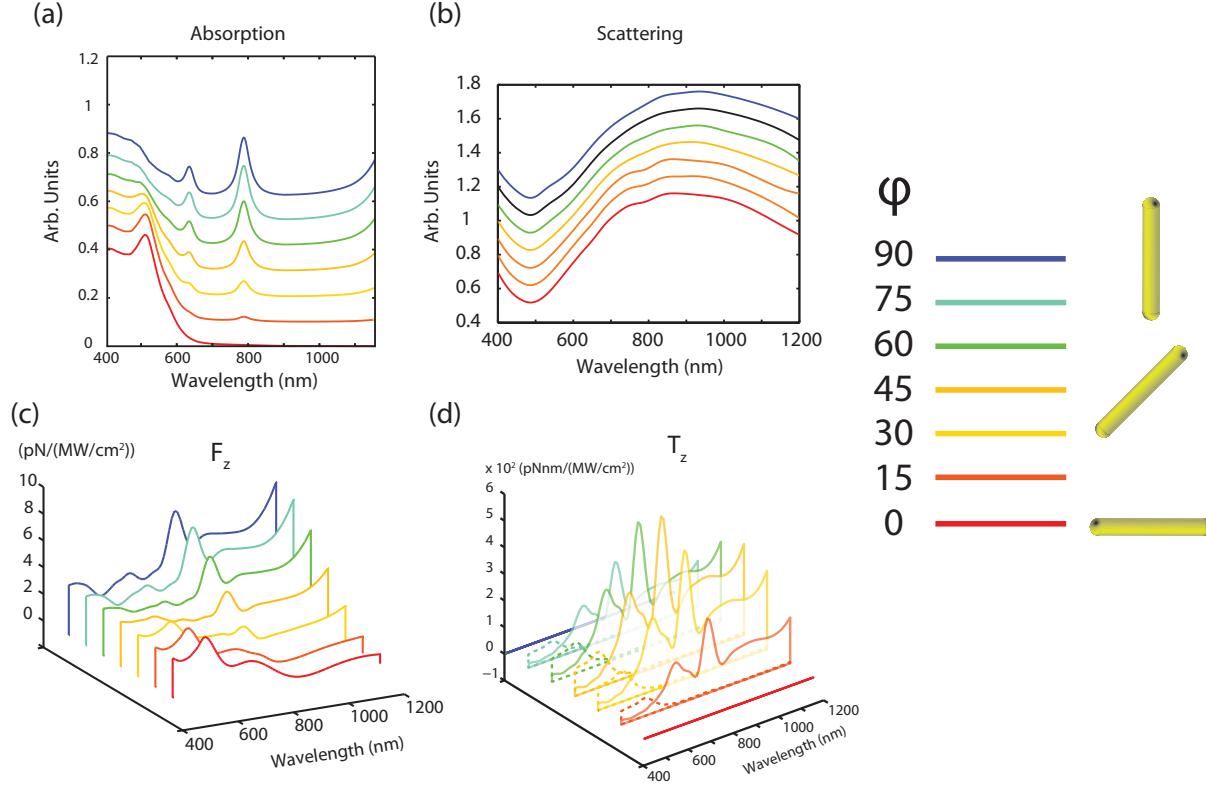


Figure 3.2: Characteristics of a nanowire in the  $x$ - $y$  plane for varying orientation angle  $\phi$  with  $\theta = 90^\circ$ . (a) Absorption cross-section. (b) Scattering cross-section, ((a), (b) spectra offset for clarity). (c) Net longitudinal force in the direction of light propagation,  $-F_z$ , associated with the plasmonic Lorentz force. (d) In-plane torque  $T_z$  produced by plasmons  $\mathbf{f}_M$  (solid lines) and the induced electric dipole  $\mathbf{f}_E$  (dashed lines).

pointed in a direction *opposite* to the light propagation, in a manner that is reminiscent of optical tractor beams [Ruffner and Grier (2012)]; when the wire is aligned parallel to the linear polarization of light ( $\phi = 90^\circ$ ), the longitudinal force increases significantly. It has generally been assumed that radiation pressure produces the strong longitudinal forces of nanowires; that longitudinal forces are *also* produced via surface currents implies additional considerations and the importance of understanding plasmonic Lorentz forces. Such plasmonic forces are strong even when there is minimal plasmonic absorption suggesting that the scattering off nanostructures plays a role.

Provided here is a comparison of the longitudinal components of  $\mathbf{T}_E$  and  $\mathbf{T}_M$  [Fig. 3.2(d)]

which further points to the importance of plasmonically-induced Lorentz forces although the contributions are qualitatively similar in 2D. Both torque terms are negligible when either  $\phi = 0^\circ$  or  $\phi = 90^\circ$  and both terms are largest at  $\phi = 45^\circ$ . The trends are in agreement with prior experimental results where a nanowire tends to aligns parallel or perpendicular to the illuminating polarization Tong et al. (2010); however, the effect of surface plasmons is significantly larger than that associated with the electric dipole. The underlying physical phenomena associated with nanowires is wavelength-dependent: at the transverse resonance, the in-plane rotation of nanowires is produced by the induced electric dipole force  $\mathbf{f}_E$ . At longer wavelengths, it is the rotation induced by surface plasmons via Lorentz forces  $\mathbf{f}_M$  that dominates. This is a central conclusion of this chapter: plasmonically-induced Lorentz forces are significant at longer wavelengths and are often stronger than electric-dipole induced forces, even when there is minimal absorption due to plasmon excitation.

### 3.3 Translation and compressive plasmonic forces

#### 3.3.1 Force visualized for various illumination wavelengths

A graphical representation of the forces produced by plasmons  $\mathbf{f}_M$  on three oblique geometries are illustrated with arrows in Fig. 3.3 for illuminating wavelength  $\lambda = 1071\text{nm}$ . The chiral-hybrid plasmons result from a superposition of the three lowest order modes ( $|m| \leq 1$ ) [Eq. 3.1]. The nanowire surface color denotes the relative strength of the time-averaged magnetic field. Chiral helices are also visible in the electric field. Both on and off resonance, the Lorentz forces yield compression forces on the nanowire. While the Lorentz forces are generally directed into and towards the axis of the nanowire, it varies in magnitude along the surface of the nanowire. In oblique illumination geometries ( $\theta \neq 0^\circ$  or  $90^\circ$ ), the magnetic-field and plasmonic Lorentz force patterns are not symmetric across the length or width of

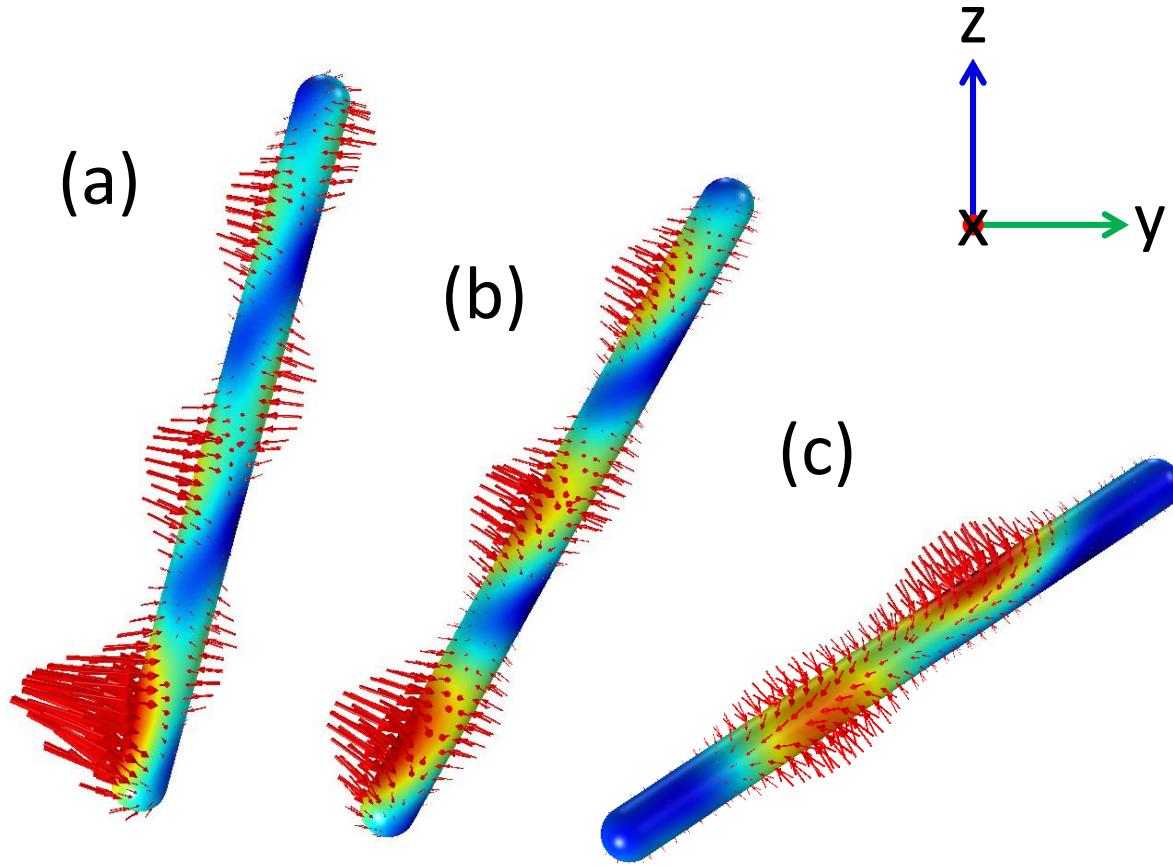


Figure 3.3: Forces on the nanowire surface produced by the surface currents (red arrows) and the norm of the surface magnetic field (surface colormap) for oblique geometries that excite the chiral hybrid plasmonic mode, where (a)  $\theta = 15^\circ, \phi = 90^\circ$  (b)  $\theta = 30^\circ, \phi = 75^\circ$  (c)  $\theta = 60^\circ, \phi = 60^\circ$  at  $\lambda = 1071\text{nm}$ .

the wire. This break in azimuthal and longitudinal symmetry subsequently yields net forces in the  $x, y, z$  direction that would result in translation and torque of the nanowire. The origin of the asymmetrical profile along the length of the nanowire stems from the lossy nature of the material, plasmons are coupled into the nanowire via the termination and propagate the length of the nanowire, which acts like a low-Q Fabry-Pérot resonator [Ditlbacher et al. (2005)]. The remaining part of this section describes the volume-integrated net translation forces; Sec. 3.4 will discuss the net torque of the nanowires.

Figure 3.4 illustrates  $\mathbf{f}_M$  for  $0 < \theta < 90^\circ$  and  $0 < \phi < 90^\circ$ . From this quarter-hemisphere, all nanowire positions are deduced. Five wavelengths are shown, which are uniformly spaced in the frequency domain. We illustrate a wavelength below the transverse resonance ( $\lambda = 441\text{nm}$ ), wavelengths associated with the transverse ( $\text{HE}_{\pm 1}$ ) and longitudinal ( $\text{TM}_0$ ) modes ( $\lambda = 517$ ,  $625$ , and  $790\text{nm}$ ), and a longer, off-resonance wavelength associated with the hybrid chiral plasmon ( $\lambda = 1071\text{nm}$ ). The orientations and wavelengths that correspond to Fig. 3.3 are marked. The color mappings are symmetrized; the components of  $\mathbf{f}_M$  are both positive and negative.

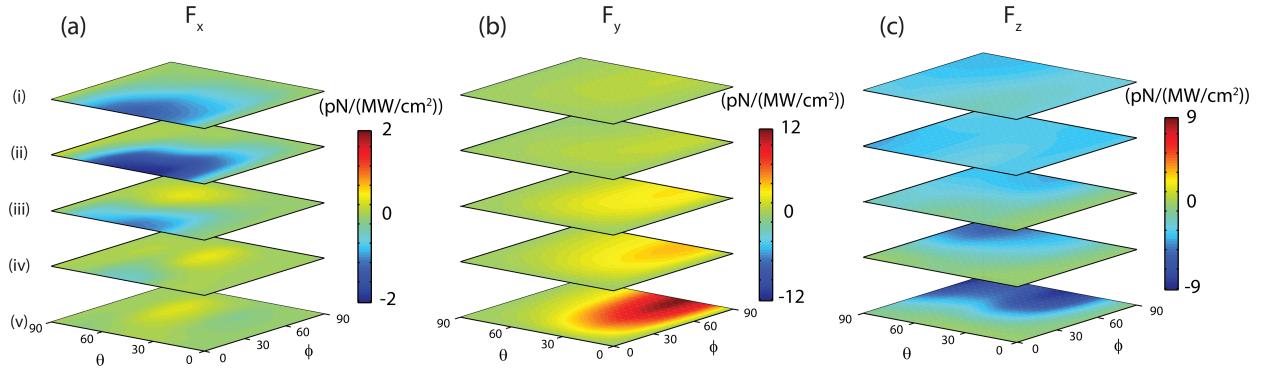


Figure 3.4: Net (volume-integrated) Lorentz forces associated with nanowire surface currents  $\mathbf{f}_M$  in (a)  $x$ -direction, (b)  $y$ -direction, and (c)  $z$ -directions for illuminating wavelengths  $\lambda =$  (i)  $441\text{nm}$  (ii)  $517\text{nm}$  (iii)  $625\text{nm}$  (iv)  $790\text{nm}$  (v)  $1071\text{nm}$ .

Plasmons on the nanowire not only yield longitudinal forces [Fig. 3.2(c)] but also appreciable forces *perpendicular* to the light Poynting at wavelengths where there is lower absorption and higher scattering. In general, the largest net translation forces are produced in the  $y$ -direction or direction of light polarization. The force perpendicular to the polarization, that is, in the  $x$ -direction, is negative at lower wavelengths, but either positive or negative at longer wavelengths, depending on the alignment of the wire. Moreover, the net translation forces are small on resonance compared to at longer wavelengths where chiral plasmons are present. For example, at the transverse and longitudinal resonances, that is,  $\lambda = 510\text{nm}$  and  $\lambda = 790\text{nm}$ , the net translation forces are at most  $2\text{pN}/(\text{MW}/\text{cm}^2)$ , whereas

at the wavelength of  $\lambda = 1071\text{nm}$ , the net translation force is as much as  $15\text{pN}/(\text{MW}/\text{cm}^2)$ . Therefore, the Lorentz forces that occur via scattering transfer momentum to the nanowire in a manner that does not require strong plasmonic absorption since there is large scattering [Fig. 3.2(b)] yet low absorption [Fig. 3.2(a)] where Lorentz forces are greatest.

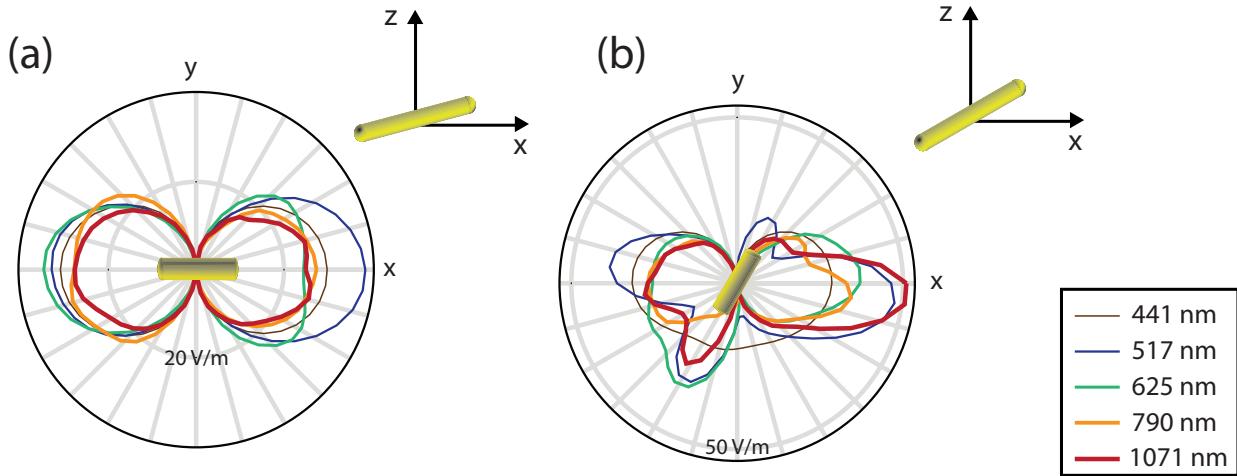


Figure 3.5: Far-field radiation patterns for a nanowire aligned (a) in the  $x$ - $z$  plane with  $\theta = 75^\circ$ ,  $\phi = 0^\circ$ , (b)  $\theta = 60^\circ$ ,  $\phi = 60^\circ$  for wavelengths  $\lambda = 441\text{nm}$ ,  $517\text{nm}$ ,  $625\text{nm}$ ,  $790\text{nm}$ , and  $1071\text{nm}$ .

### 3.3.2 Momentum transfer via scattering

It is expected that momentum transfer in the transverse  $x$ - $y$  plane associated with plasmons is observable in the scattered fields in order for linear momentum to be conserved and simulations indicate that momentum conservation is visible in the far-field power. Figure 3.5 shows the electric field norm in the far field for two geometries to illustrate transverse forces, from which the scattering dynamics can be extrapolated. The momentum transfer to the nanowire can be inferred by the symmetry of the dipole radiation patterns. In Fig. 3.5(a), the nanowire is aligned in the  $x$ - $z$  plane with  $\theta = 75^\circ$  and  $\phi = 0^\circ$ . At this orientation, the Lorentz force is calculated in the  $x$ -direction to be either negative ( $\lambda = 441$ ,  $517\text{nm}$ ) or positive ( $\lambda = 625$ ,  $790$ ,  $1071\text{nm}$ ) depending on the illuminating wavelength [Fig. 3.4(a)].

A positive value of  $F_x$ , at a wavelength of  $\lambda = 441\text{nm}$  is largely attributed to reflection since this wavelength is below the transverse-resonance cutoff. At higher wavelengths, the  $x$ -direction shifts in the far-field radiated power correspond with the sign of the plasmonic Lorentz forces in the  $x$ -direction. The shape of the far-field radiation corresponds to the characteristic dipole radiation from excitation of the longitudinal  $\text{TM}_0$  mode.

Similarly, in Fig. 3.5(b) shows a similar far-field normalized power for geometry  $\theta = 60^\circ$  and  $\phi = 60^\circ$ . Below the cutoff for plasmon excitation ( $\lambda = 441\text{nm}$ ), the radiation pattern indicates that momentum transfer in the  $y$ -direction is due to reflection. At higher wavelengths, an ‘antenna’ behavior of the wire is apparent, the radiation pattern exhibits directionality. The dipole radiation mode in the  $y$ -direction and transverse modes are uncoupled at  $\lambda = 517\text{nm}$ , and the far-field radiation pattern is an ‘ $x$ ’ shape that is aligned with the axis of the nanowire. The size of the arms of the ‘ $x$ ’ shape determine the relative strengths of the dipole modes present, the arm perpendicular to the nanowire axis corresponds to the fundamental,  $\text{TM}_0$  mode and the arm parallel to the  $\text{HE}_{\pm 1}$  modes.

At longer wavelengths the plasmonic Lorentz forces are significant [Fig. 3.4]. For wavelengths and orientations that produce significant Lorentz forces the far-field radiation patterns differ greatly in symmetry from dipole radiation patterns one might expect. For wavelengths of  $\lambda = 625, 790$ , and  $1071\text{nm}$ , the center of radiation pattern moves in the positive  $x$  and negative  $y$ -direction, corresponding with  $\mathbf{f}_M$  that is negative in the  $x$  and positive in the  $y$ -directions [Fig. 3.4]. Figure 3.5 indicates that the plasmonically-induced Lorentz forces result in 50-70% changes in far-field radiated power, which is experimentally measurable.

## 3.4 Torque in 3-dimensions

### 3.4.1 Torque visualized for various illumination wavelengths

The vector components of the dipole moment and plasmonically-induced Lorentz torque [ $\mathbf{T}_E + \mathbf{T}_M = (T_x, T_y, T_z)$ ] are shown in Fig. 3.6 for five wavelengths (441, 517, 625, 790, and 1071nm as chosen in the previous section). Large values of  $T_x$  and  $T_z$  represent large torques that rotate the nanowire in both the polar and azimuthal directions.  $T_x$  and  $T_z$  increase in magnitude as wavelength increases which correlates well to the existence of chiral hybrid modes at longer wavelengths. Subsequently, whether  $T_x$  and  $T_y$  are positive or negative depends on the polar orientation of the nanowire.

The orientations that produce large net translation forces [Fig. 3.4] do not necessarily coincide with large torques [Fig. 3.6]; the greater the asymmetry in  $\mathbf{f}_E$  and  $\mathbf{f}_M$ , the greater the torque. We find that the maximal torques produced by plasmons ( $\mathbf{T}_M$ ) are an order of magnitude larger than the maximal torques produced by dipole moments ( $\mathbf{T}_E$ ). Moreover, the magnitude of  $\mathbf{T}_E$  is negligible at wavelengths above 600nm; above 600nm,  $\mathbf{T}_M$  dominates. The magnitude of the  $\mathbf{T}_E$  is the same sign in our hemisphere quadrant of  $\theta$  and  $\phi$  since  $\mathbf{f}_E$  uniformly aligns the induced dipole with the axis of field polarization. In contrast,  $\mathbf{T}_M$

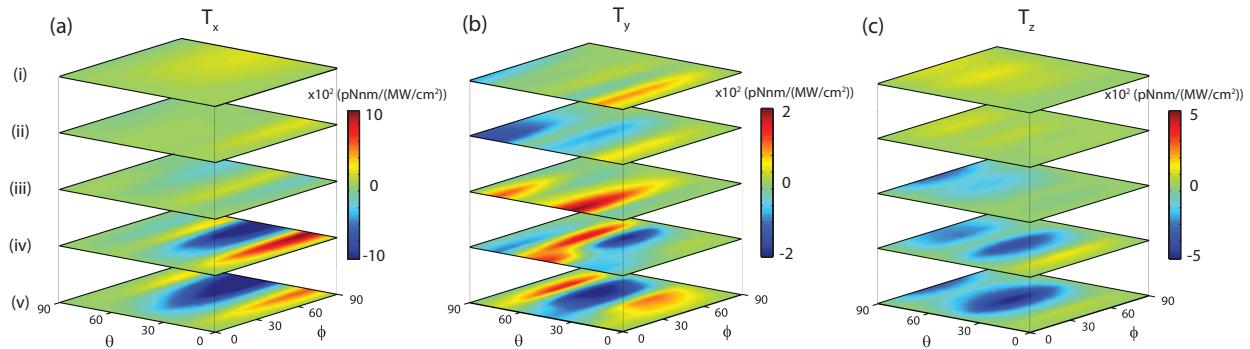


Figure 3.6: Torque around the (a)  $x$ -axis, (b)  $y$ -axis, and (c)  $z$ -axis at (i) 441nm, (ii) 535nm, (iii) 625nm, (iv) 790nm, and (v) 1071nm.

changes sign with nanowire orientation and illuminating wavelength [Fig. 3.6], which reflects the sensitive nature of the chiral hybrid plasmon.

### 3.4.2 Phase diagram illustrations

When the nanowire is free to rotate in three dimensions, the rotational behavior becomes complicated. The torque on the nanowire causes rotation which subsequently changes the torque on the nanowire. The results of this system that only accounts for Lorentz forces yields nonlinear dynamics that are beyond the scope of this chapter; nonetheless, the dynamics are illustrated with a phase portrait of the torques in spherical coordinates. The rotation in the  $\theta$  and  $\phi$  directions associated with  $\mathbf{T}_E + \mathbf{T}_M$  are:

$$A_\theta = -\sin \phi T_x + \cos \phi T_y \quad (3.8)$$

$$A_\phi = T_z. \quad (3.9)$$

The phase portrait, i.e. vectors  $[A_\phi, A_\theta]$  as a function of  $\theta, \phi$  of the nanowire are plot in Fig. 3.7.  $A_\theta$  and  $A_\phi$  are not equivalent to the angular acceleration since the rotational inertia, which changes as a function of angle, has not been taken into consideration. Moreover, the angular velocity will also influence the angular acceleration when the rotational inertia changes. Nonetheless, an understanding is gathered of the nanowire's stable orientations and dynamics from Fig. 3.7.

Points of stability occur when the angular motion is zero, which occurs when the torque is zero. Stable points occur when the vector field flows toward the point of zero torque; unstable points occur when the vector field flows away from the point of zero torque [Strogatz (1994)]. Saddle points occur when the vector field flows toward the point of zero torque in one direction, and away in another.

Similar to the observation of the 2D nanowire dynamics [Sec. 3.2], the nanowire aligns

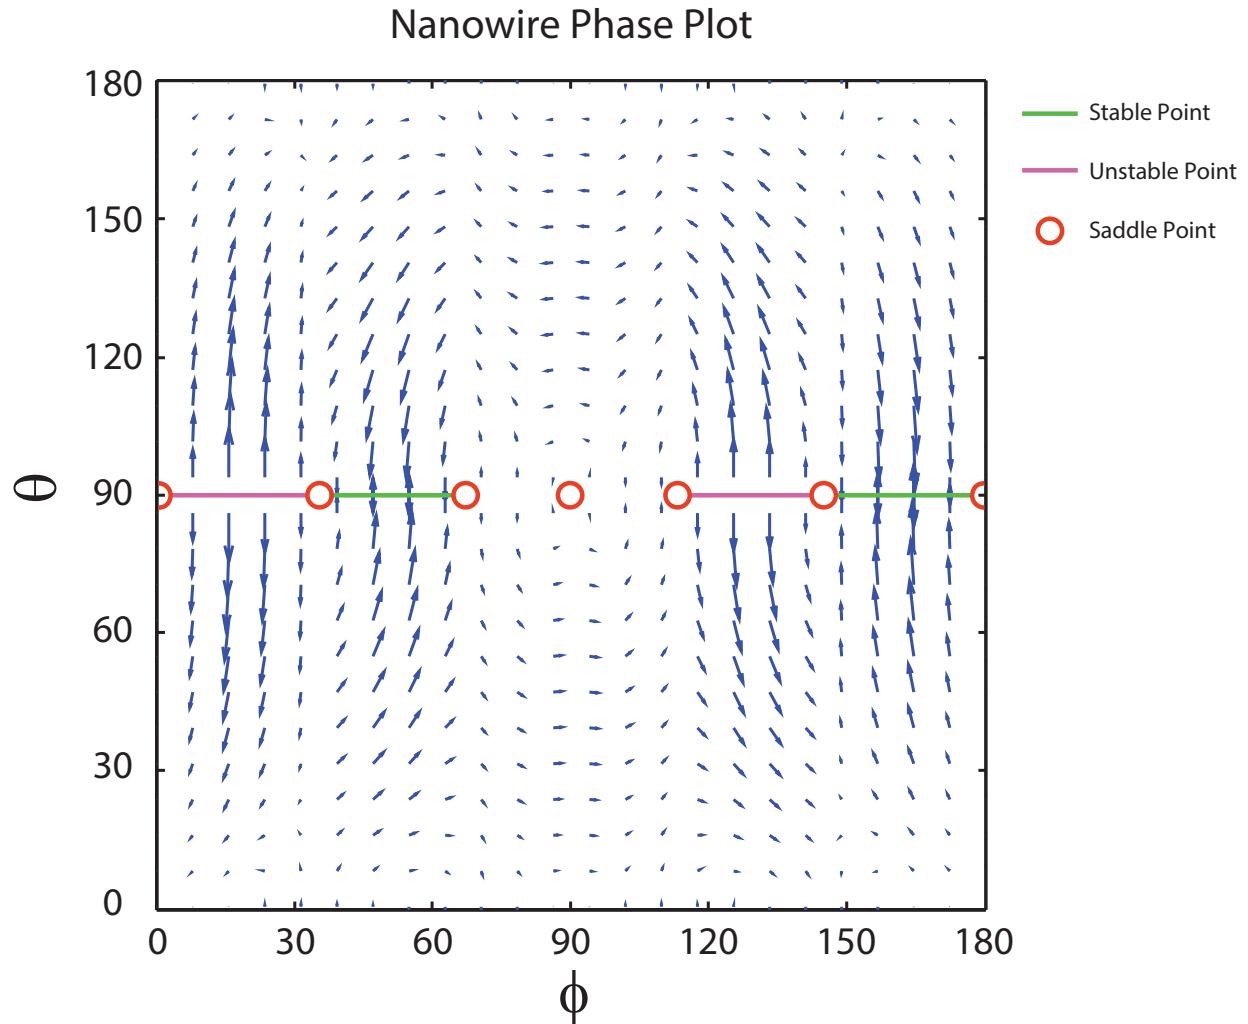


Figure 3.7: Phase portrait of the torque forces calculated at  $\lambda = 1071\text{nm}$ . Arrows in the  $x$  and  $y$  directions indicate torque that rotates the nanowire in the  $\phi$  and  $\theta$  directions respectively.

either parallel or perpendicular to the axis of polarization in a 3D system, settling at a stable point. Stable points occur when either  $\theta$  or  $\phi$  are equal to  $0^\circ$  or  $180^\circ$ , and  $\theta = 90^\circ$  consistent with the strong orientational trapping observed in previous research [Yan et al. (2012b); Tong et al. (2010)]. Interestingly, along the line of  $\theta = 90^\circ$  stable, unstable and saddle points exist and illustrate many rich and complicated dynamics already reported with the optical trapping of nanowires. Around stable fixed points oscillatory dynamics occur:

the nanowire will rotate, but more specifically, it will rock and spin in an oscillatory manner. Fig. 3.7 also explains the rotational accelerations and rapid reversals seen in light-driven experiments [Shelton et al. (2005)] that are associated with the saddle point behavior and sharp inflections, such as those dynamics indicated at  $\theta = 90^\circ$ .

This alludes to competing dynamics between the induced electric dipole and surface plasmons and explains the prior experimental observations that often contradict. It has been previously reported that nanowires align parallel or perpendicular to the linearly polarization of an optical trap. A theoretical model that limits consideration to  $\mathbf{T}_E$  only explains the stable alignment of the dipole parallel to the polarization. Yet moreover, prior experiments employ trapping wavelengths in the near-IR [Tong et al. (2010)], where the magnitude of  $\mathbf{T}_E$  is predicted to be negligible. This model predicts and explains the stable orientations of the nanowire, with longitudinal axis both parallel and perpendicular to the field polarization.

### 3.5 Conclusion

This chapter has shown that plasmonically-induced Lorentz forces are significant and greater than dipole-moment-induced forces, particularly at long-wavelength excitation between plasmon resonances. The nanowire forces produced by plasmons lead to axial compression, which changes spatially along the nanowire surface depending on the nanowire orientation. The existence of chiral plasmons coincides with spiral magnetic-field patterns that produce net transverse forces and torques, which is predicted to be experimentally observable in the far-field radiated power and polarization. The plasmonically-induced Lorentz forces are expected to interfere with the optical trapping of nanowires; selection of a laser-trap wavelength that prevents the excitation of the chiral plasmonic modes will enable greater control over the optical manipulation of nanowires.

The rotational dynamics present a highly nonlinear and complicated problem due to the

sensitive nature of the plasmonic resonance that conventional ray optics cannot explain. The plasmonically-induced Lorentz forces and torques produce rotational motion consistent with the spinning, rocking, and rapid reversals in rotation observed experimentally with elongated plasmonic nanoparticles. Plasmonically-induced torque may oppose the dipole-induced torque, although the Lorentz torque dominates almost completely above the transverse resonance of the nanowire. This theoretical investigation is the first to properly explain the stable positions of nanowires under illumination of linearly-polarized electromagnetic fields, and reveals a rich system of optomechanical plasmonically driven dynamics that has not yet been explored.

This work also points to novel methods that manipulate conducting nanoparticles that do not result in the extreme absorption and heating generally associated with the excitation of plasmons; strong plasmonically-induced Lorentz forces occur off-resonance where plasmonic absorption is minimal. This outcome is highly relevant to the development of new devices and mechanisms that efficiently leverage the nonlinear mechanical dynamics of conducting nanoparticles in fluids, not limited to elongated conducting particles but also chiral nanoparticles, polymer materials, and carbon metastructures.

## 3.6 Future work

Future work on this subject may involve experimental verification of the theoretical and numerical components of the work shown here. An experiment may consist of a microscope setup with two tightly focused beams at different wavelengths. One beam would act as the optical trapping beam that would stabilize the nanowire at the focal point of the microscope setup similar to the setups described in the references [Ashkin (2001); Lee and Padgett (2012); Kuo (2001); Lang and Block (2003)], and the other would act as the excitation beam that would generate the Lorentz forces described in this chapter.

# Chapter 4

## Robustness and spatial multiplexing via fractal architectures

### 4.1 Introduction

Many natural systems exhibit fractal properties [Mandlebrot (1982)]; in fact, scale invariance underlies many self-similar phenomena, from frost crystallization to animal colouration to stock-market pricing. In the realm of optics, the fractal anatomy of systems is widely associated with aggregated dielectric and metal colloids [Sorensen (2001)], crystals [Macke et al. (1996)], and tissues [Schmitt and Kumar (1998)]. Fractal systems are also observed in nonlinear optics [Soljacic et al. (2000); Segev et al. (2012)] and fractalized optical properties can even efficiently characterize or enhance the response of materials [Stockman et al. (1992); Tsai et al. (1994)]. Less well utilized are the features of fractals, or the diffraction patterns of fractal signals [Berry (1979); Horvath et al. (2010); Hou et al. (2004)]. Fractals feature in methods of encrypting data [Barrera et al. (2012)] as a versatile approach to double random-phase encoding [Unnikrishnan et al. (2000)]. However, to differentiate from previous work we exploit fractal architecture to improve transmission robustness.

This chapter explores diffractals for their application in signal processing [Verma et al. (2013, 2012)]. Free-space propagation of diffractal-signal architectures provides algorithmic value and spatial multiplexing properties; any arbitrary subsection of a diffractal contains sufficient information to recreate the original sparse signal that is transmitted with a specific fractal architecture. In a manner similar to compressive imaging [Duarte et al. (2007); Howland and Howell (2013)]—where sparse signals reveal greater information via the diffraction through structures—here the fractal structuring within the signal sparseness prevents the loss of information.

Like other applications of fractals in communications applications, the diffractal architecture exhibits trade-offs. Fractal antennas for the radio frequency and microwave regimes are known for being compact and versatile over wide spectral bands but are power intensive [Radonic et al. (2012); Puente-Baliarda et al. (1998)]; fractal encoding algorithms enable image compression with higher-resolution at the expense of greater algorithmic complexity [Jacquin (1993)]; this chapter identifies that diffractal architectures prevent the loss of information but require greater signal preprocessing. This investigation extends the understanding of fractal structures in signal communications and may increase robustness and transmission rates of satellite, wireless, and interplanetary communication systems, *i.e.*, networks that support a large number of roaming receivers.

The remainder of this chapter is organized as follows. First, the form of a transmitted fractal signal is formalized, it is shown that the far-field diffraction pattern or diffractal is also a fractal, and the reciprocal nature of fractals is illustrated with the Sierpinski carpet. Secondly, the robust retrieval of a signal from a diffractal is demonstrated; the original signal is reconstructed even when the majority of the diffractal signal is blocked. Finally, the future applications for diffractal spatial multiplexing in free-space communication systems is discussed.

## 4.2 Theoretical description

### 4.2.1 Spatial multiplexing of the diffractal

The fractal transmittance pattern is generated from any base matrix via recursive iterations where the matrix is resized and convolved with itself repeatedly [Allouche and Shallit (2003)].

The base matrix  $B(x, y)$  adopts a general form,

$$B_i(x, y) = \sum_j \delta(xr^{i-1} - x_j, yr^{i-1} - y_j), \quad (4.1)$$

where the subscript denotes the iteration  $i$ ,  $r > 1$  is the relative scaling between iterations, and  $\delta(x - x_j, y - y_j)$  is the Dirac delta function at  $x = x_j$  and  $y = y_j$ . The fractal transmittance function  $T(x, y)$  is calculated recursively,

$$T_n(x, y) = T_{n-1}(x, y) * B_{n-1}(x, y), \quad (4.2)$$

where the subscript denotes the order of the fractal or its expression at the  $n^{th}$  iteration,  $T_0$  is the initial profile of 1's, and  $*$  denotes the convolution operator.

Subsequently, the diffractal is the Fourier transform or the far-field of the transmittance function  $\tilde{T}$  [Horvath et al. (2010)],

$$\tilde{T}_n(k_x, k_y) = \tilde{T}_0(k_x, k_y) \prod_{i=1}^n \tilde{B}_i(k_x, k_y). \quad (4.3)$$

The Sierpinski carpet is one example of a fractal that is generated by this process and via

the iterated substitution of a  $3 \times 3$  base matrix of ones with removal of the center element:

$$\left\{ 0 \rightarrow \begin{bmatrix} 0 & 0 & 0 \\ 0 & 0 & 0 \\ 0 & 0 & 0 \end{bmatrix}, 1 \rightarrow \begin{bmatrix} 1 & 1 & 1 \\ 1 & 0 & 1 \\ 1 & 1 & 1 \end{bmatrix} \right\}. \quad (4.4)$$

The second substitution of Eq. 4.4 represents the mathematical expression for the base matrix  $B_0(x, y)$ . In the case of the Sierpinski-carpet base-matrix elements,  $r = 3$ , and  $x_j$  and  $y_j$  are the perimeter coordinates of a  $3 \times 3$  9-unit block centered at the origin, and  $(x_j, y_j) \in [(1, 1), (1, 0), (1, -1), (0, -1), (-1, -1), (-1, 0), (-1, 1), (0, 1)]$ . Since each of the Dirac delta functions in  $B_0(x, y)$  yields a phase shift in the Fourier domain, *i.e.*,  $\mathcal{F}\{\delta(\alpha x - x_i)\} = e^{2\pi i c k_x x_i} / |\alpha|$ , its scaled Fourier Transform at the  $i^{\text{th}}$  iteration of the Sierpinski carpet [Eq. 4.1] becomes:

$$\tilde{B}_i(k_x, k_y) = (2/r)^{i-1} [\cos(2\pi 3^{1-i} k_x) \cos(2\pi 3^{1-i} k_y) + \cos(2\pi 3^{1-i} k_x) + \cos(2\pi 3^{1-i} k_y)]. \quad (4.5)$$

With each iteration, the spatial frequency components  $k_x, k_y$  of the diffractal increase by a factor of 3 and spread the diffractal across a 3-times wider  $k_x, k_y$ -range, which is evident in Eq. 4.5; the cutoff of  $\tilde{T}_n$  scales in proportion with  $k_x, k_y \propto r^{n-1}$ .

The Sierpinski carpet,  $T$ , is calculated recursively [Eq. 4.2]: a second-order fractal is generated from the Kronecker tensor product of the base matrix  $\begin{bmatrix} 1 & 1 & 1 \\ 1 & 0 & 1 \\ 1 & 1 & 1 \end{bmatrix}$  with itself; a third-order fractal is generated from the Kronecker tensor product of a second-order fractal and the same base matrix [see Code File 1 Moocarme (2015a)]. Sierpinski carpets of  $n = 1, 3$ , and 5 are shown in Fig. 4.1a) with the corresponding diffractals  $\tilde{T}$  [Fig. 4.1b)].

```
function carpetHolo = Sierpinski(fracOrder);
    carpetBase = ones(3); % Initialize matrix
    carpetBase(2,2) = 0;
```

```

% Zero middle element

if fracOrder==0;

    % For zero order case
    carpetHolo = carpetBase;

else

    % For higher order cases
    carpetHolo= kron(carpetBase , carpetBase);

    % For loop iterates the Kronecker tensor product
    for i = 1:fracOrder-1

        carpetHolo = kron(carpetHolo , carpetBase);

    end

end

```

end

As the fractal order increases,  $\tilde{T}$  exhibits smaller self-similar features at higher  $k_x, k_y$ ; the diffractal also exhibits a fractal architecture, as observed in other literature [Berry (1979); Horvath et al. (2010)]. Moreover, when  $n$  is large, an arbitrary subsection of  $\tilde{T}$  closely resembles the whole, and the self-similarity is already apparent with  $n = 5$  [Fig. 4.1c-d)]. The iterated, self-similar, wide-spatial-frequency features contained in the diffractal  $\tilde{T}_n$  [Eq. 4.3] enable robust reconstruction of itself, which is described in the next subsection.

#### 4.2.2 Robust reconstruction of a blocked diffractal signal

The sparse matrix  $B_0$  and transmitted signal  $T$  are referred to as the original and fractalized signal, OS and FS, respectively; the diffractal signal DS is  $\tilde{T}$ , or, the Fourier transform of FS; BDS refers to an off-axis subsection of DS that is filtered; a reconstructed fractalized signal RFS refers to the inverse-Fourier transform of BDS; a regenerated version of the original

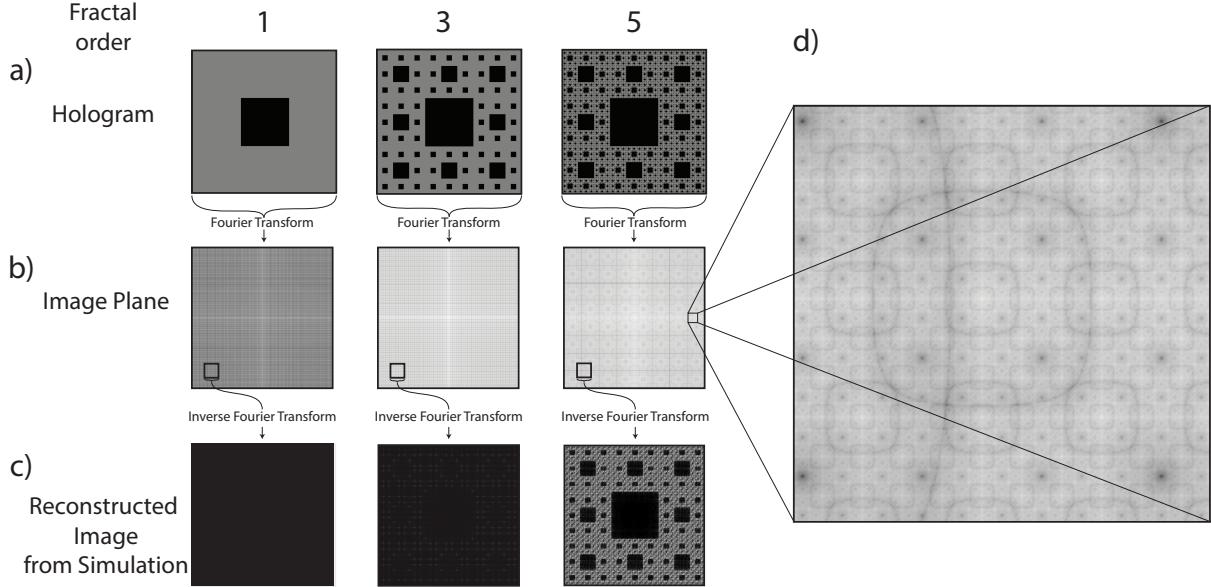


Figure 4.1: a) Signal patterns, or fractalized signals (FS) of orders  $n = 1, 3$ , and  $5$ . b) Corresponding Fourier transforms of signals on logarithm scale, or diffractal signals (DS). c) Reconstructed Fourier-transforms (RFS) from the 1% black-outlined subset, the blocked diffractal signal (BDS). d) Enlargement of a portion of the  $n = 5$  diffractal, which illustrates similar patterns at different length scales.

signal ROS interpolates RFS in order to obtain OS.

In Fig. 4.1(b), a subsection or BDS is outlined with a black square, which represents 1% of DS. The corresponding RFS from BDS are shown in Fig. 4.1(c). For  $n = 1, 3$ , RFS is ostensibly blank because BDS carries negligible power. In contrast, when  $n = 5$ , RFS carries features that resemble FS. We refer to the capacity to reproduce FS with 1% of the off-axis area from DS as *robust* reconstruction.

Robust reconstruction—where RFS resembles FS—is possible even when the size of BDS is significantly reduced [Verma et al. (2013)]. A corresponding increase in the FS fractal order  $n$  will yield RFS that resembles FS when BDS is arbitrarily small. With the example of the Sierpinski carpet, Fig. 4.1(a)–4.1(c), if the size of BDS is reduced to 1% of OS, then a comparable RFS is produced by increasing the fractal order of FS from  $n = 1$  to  $n = 5$ .

Robust reconstruction is defined as the capacity to regenerate OS from RFS from a

simple threshold function [see Code File 2 Moocarme (2015b)]. The threshold function of the Sierpinski carpet divides RFS into a  $3 \times 3$  array (identical size as OS) and measures the intensity in each of the 9 elements. Above a certain threshold value, the element is assigned a value of 1, and otherwise assigned a value of 0. The  $3 \times 3$  array that is processed with the threshold function, ROS, is theoretically identical to OS when OS is transmitted with the diffractal architecture.

```
function recon = reconFun( Threshold , carpetBaseLength , carpetHolo )
    % Ratio of length of hologram
    normLength = length( carpetHolo )/ carpetBaseLength ;

    % Convert to array of cells
    cellHolo = mat2cell( carpetHolo , repmat( normLength , 1 , ...
        carpetBaseLength ) , repmat( normLength , 1 , carpetBaseLength ) );

    % Calculate mean, determine if above threshold value, and plot
    pcolor( double( cell2mat( cellfun( @mean2 , cellHolo ))>Threshold ) );
end
```

The comparison between RFS and FS in peak signal-to-noise ratio (PSNR) for various fractal orders as a function of the fractional BDS size is shown in Fig. 4.2. The error bars represent the standard deviation from the mean value of 200 random locations of BDS. Since the size of RFS is reduced from FS, RFS is resized with nearest-neighbour interpolation. We provide 2 observations from Fig. 4.2: first, when BDS is greater than 0.01% of the fractional size of FS, larger fractal orders produce higher PSNR; second, as the fractional area of BDS increases the location of BDS becomes irrelevant since the standard deviation around the mean diminishes. For fractional BDS sizes smaller than 0.01% lower fractal orders yield a

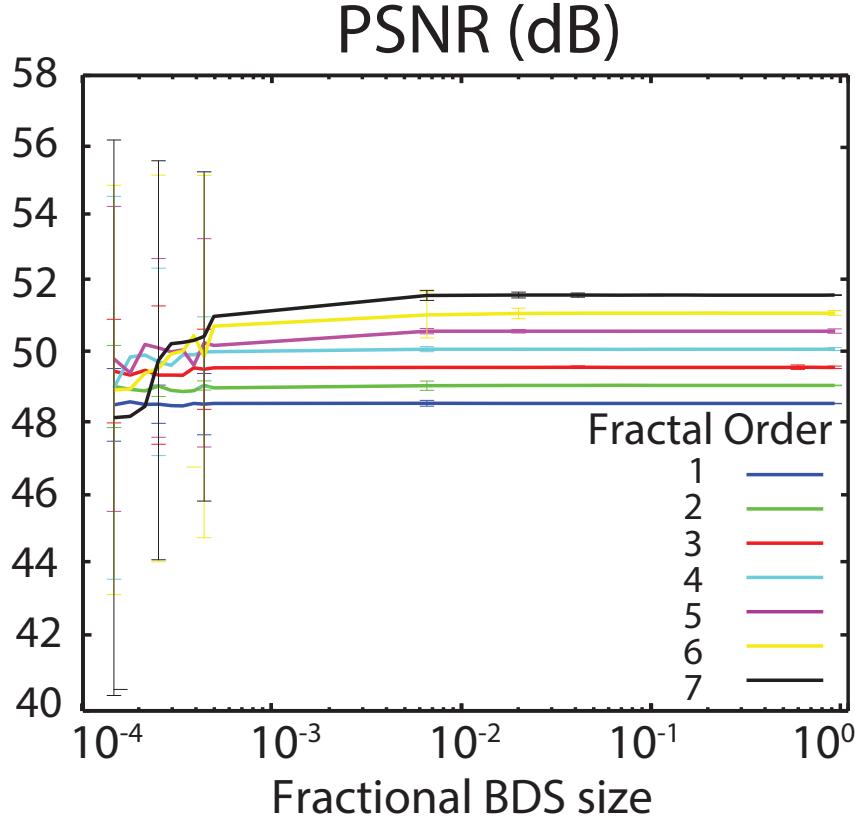


Figure 4.2: The peak signal-to-noise ratio (PSNR) of RFS to FS for various fractal orders as a function of the fractional BDS size.

higher PSNR since the minimum size matrix needed to completely recreate FS is larger for higher fractal orders. For example the minimum size matrix needed to recreate FS of order 1 is  $3 \times 3$ , for FS of order 2 it is  $9 \times 9$ , etc.

ROS is generally identical to OS when BDS is above 0.01% and the fractal order is greater than 3, regardless of BDS location. A partial explanation for the robust reconstruction is that increasing-order FS carry arbitrarily-high  $k_x, k_y$  and enable arbitrarily-small BDS to carry the information of FS or OS. If OS is strictly limited to binary or Dirac-delta functions, then FS has no  $k_x, k_y$  cut-off and as  $n$  approaches infinity, fractalized features appear in FS without a  $k_x, k_y$  cut-off. In fact, the amplitude of the additional  $k_x, k_y$  gained from each iteration

scales inversely with  $r^{n-1}$ , which provides a detection limit only in practice; in theory, each iteration generates high- $k_x, k_y$  copies of OS [Eq. (4.4)] that are spatially distributed from the origin.

Yet it is worth noting that the robust reconstruction is achieved because the diffractal architecture also couples  $k_x$  and  $k_y$  in iterated products [Eq. (4.3)]. As a result, RFS will resemble FS when either the BDS size *or location* changes. In a manner similar to spatial filtering, RFS will produce outlines of FS if  $n$  is not sufficiently large; however, unlike a high-pass spatial filter of a multi-scale random high- $k_x, k_y$  pattern [Duarte et al. (2007)], a change in the location or the size of BDS will not distort the outline of RFS. Subsequently, the diffractal architecture provides superior performance over other algorithms that regenerate sparse data, OS [Duarte et al. (2007); Howland and Howell (2013)].

### 4.3 Experimental results

The features of diffractals are experimentally demonstrated with a 4-*f* optical arrangement where the 2-dimensional Fourier transform of a collimated fractal image, DS, lies in the focal plane of an imaging lens Goodman (2005). The experimental setup that produces, filters and reconstructs FS is shown in Fig. 4.3a) and experimentally reconstructed images, RFS, are shown in Fig. 4.3b). An aperture of area approximately  $0.8\text{mm}^2$  blocks the majority of DS. The placement of the aperture is shifted roughly 4mm horizontally and 5mm vertically from the central point, in the focal plane of the lens. The SLM image has a resolution of  $800 \times 600$  pixels (16mm  $\times$  12mm).

When high order diffractal architectures are employed ( $n > 4$ ), a phenomenon is observed that is shown numerically: the placement of the aperture in DS is irrelevant in order to reconstruct the original image. When the aperture is moved laterally in the focal plane, RFS maintains strong resemblance to FS. In fact, only the intensity of RFS diminishes as

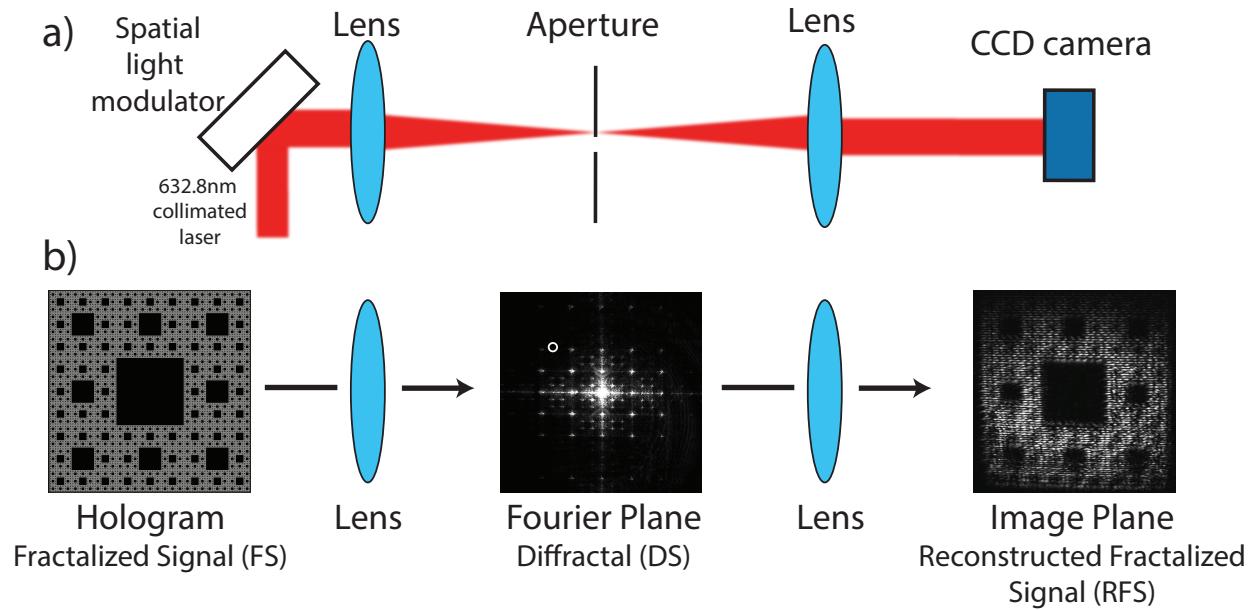


Figure 4.3: a) Light from a  $\lambda = 632.8\text{-nm}$  wavelength laser is spatially filtered, expanded, and collimated and illuminates the full area of a  $800 \times 600$  pixel spatial light modulator (SLM). The  $4-f$  system is composed of 2  $5\text{-cm}$  lenses placed after the SLM. The first lens Fourier transforms the fractal signal (FS) at the focal plane. An aperture is placed off-center at the focal plane and only transmits a portion of the diffractal (BDS). The second lens reconstructs the SLM image with the light that is transmitted through the aperture. b) The Sierpinski carpet hologram of order  $n=5$ , CCD image in the focal plane of the hologram after the lens, and the reconstructed image. A circle denotes the area utilized to reconstruct the image.

the aperture translates further from the DS center; the outline remains fixed as the aperture moves. For smaller fractal orders, RFS resembles FS only when the aperture is placed within  $0.8\text{mm}$  of the center, where the spatial frequency components are concentrated. The signal-to-noise of the experiment and CCD camera sensitivity limit effective reconstruction, while the highest order  $n$  is of FS is limited by the number of SLM pixels.

## 4.4 Discussion of applications

A distinction is made that diffractals are specific fractal structures. Not all fractals enable robust signal communications and the recursive transformation employed to generate FS and DS in Eqs. 4.1 and 4.5 differ fundamentally. For example, both of the Fourier Transform

pairs FS and DS are fractals and carry iterated, self-similar features, but if the roles were reversed in our transmission system, the reconstruction will instead depend severely on the size and location of BDS. In fact, if in the example of the Sierpinski carpet, the center subsection becomes BDS, then the ROS will not resemble the OS, regardless of fractal order. The diffractal is unique from general fractals and self-similar scale-invariance alone is an insufficient precondition for our system of robust reconstruction and spatial multiplexing.

It may seem contradictory that higher-order fractals lead to more robust signal transmission since the finer structure of a higher-order fractal is itself harder to reconstruct. There are two perspectives of diffractals that explain the robust reconstruction. Firstly, the self-similar structures of higher-order fractals have a greater spatial frequency range and finer detail, and subsequently smaller BDS carry sufficient information to reconstruct OS. Secondly, the higher-order diffractals carry higher spatial-frequency components where the  $k_x$  and  $k_y$  components are coupled, and subsequently the location of the subsection in DS is unimportant. In these experiments BDS of arbitrary size and location carry sufficient information to reconstruct OS but in practice, there exists clear limitations for the robust reconstruction even in the limit of infinite-order FS.

Note: it may also seem contradictory that an infinitesimally-sized BDS with infinitesimal power can carry information— this is not actually true: there is a minimal size for BDS fixed by the pixelation of the SLM. There exists a trade-off with the diffractal architecture between robust reconstruction and high bit rate; a greater bit-rate is achieved with a larger base matrix, which can limit the maximum fractal order that is transmitted. For example, with the  $3 \times 3$  or 9-element OS, there are 512 possible spatial bits, three of which are illustrated in Fig. 4.4a-c). A  $4 \times 4$  base matrix requires  $(\frac{4}{3})^{2n}$  more pixels than a  $3 \times 3$  to achieve the same fractal order,  $n$ . With a limited SLM pixel resolution, there is a choice between the generation of higher-order fractals and the utility of higher spatial bits.

If the trade-off between bit-rate and robust reconstruction are mitigated, then the diffrac-

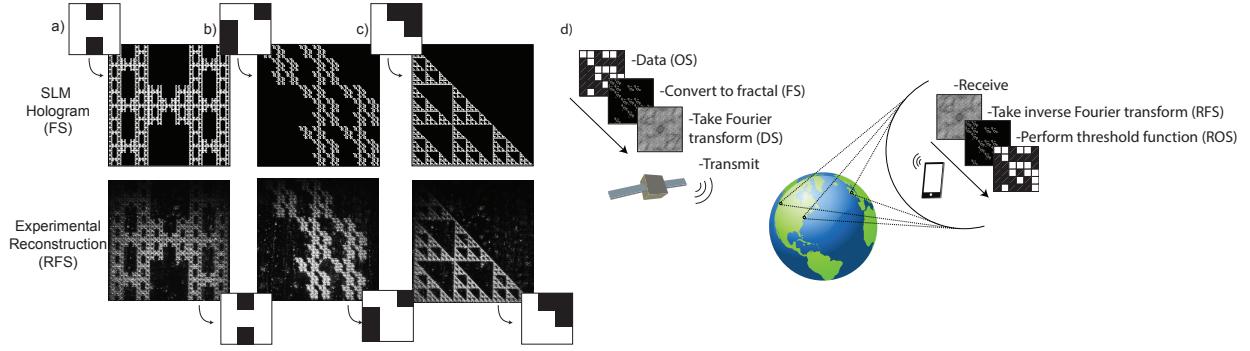


Figure 4.4: Three examples of 512 9-bit spatial patterns, associated with base matrices a)  $\begin{bmatrix} 1 & 0 & 1 \\ 1 & 1 & 1 \\ 1 & 1 & 1 \end{bmatrix}$ , b)  $\begin{bmatrix} 1 & 1 & 0 \\ 0 & 1 & 1 \\ 0 & 1 & 1 \end{bmatrix}$ , and c)  $\begin{bmatrix} 1 & 0 & 0 \\ 1 & 1 & 0 \\ 1 & 1 & 1 \end{bmatrix}$ . The fractal signals FS are shown with their corresponding experimentally-reconstructed fractal signals RFS from the experimental setup in Fig. 4.3a). The lower-right inset shows the reconstructed original signal ROS. d) Example application: transmitted fractal signal FS is received at a far-field distance as a diffractal signal DS, where a roaming set of receivers, with only a diffractal subsection BDS, reconstructs the original signal OS.

tal architecture could support a large number of roaming receivers with only one transmitter, such as wireless or satellite networks shown in Fig. 4.4d). The self-similar properties of the diffractal architecture and their corresponding far-field pattern provide a method to reach a large number of receivers, possibly moving, without signal degradation. The processing times required in the calculation of FS from OS are not trivial and scale with  $r^{2n}$ . Secondly, the refresh rates of a spatial light modulator or similar adaptive-optics device present constraints on the maximum achieved bit rate, which requires further consideration.

This can be applied to more complex shapes and structures, for example, an  $16 \times 16$  pixel smiley face. The Fourier transform of the smiley face is taken; part of the Fourier transform is blocked; and a reconstruction of the image is attempted via the inverse Fourier transform. The same experimental procedure as shown in Fig. 4.3 is utilized. As can be seen from Fig. 4.5 when just the image is sent through the experimental setup the image reconstructed is not recognizable at all. However when the image is fractalized even just one order the image becomes recognizable. Unfortunately due to the limitations of pixels on the SLM no higher orders can be achieved.

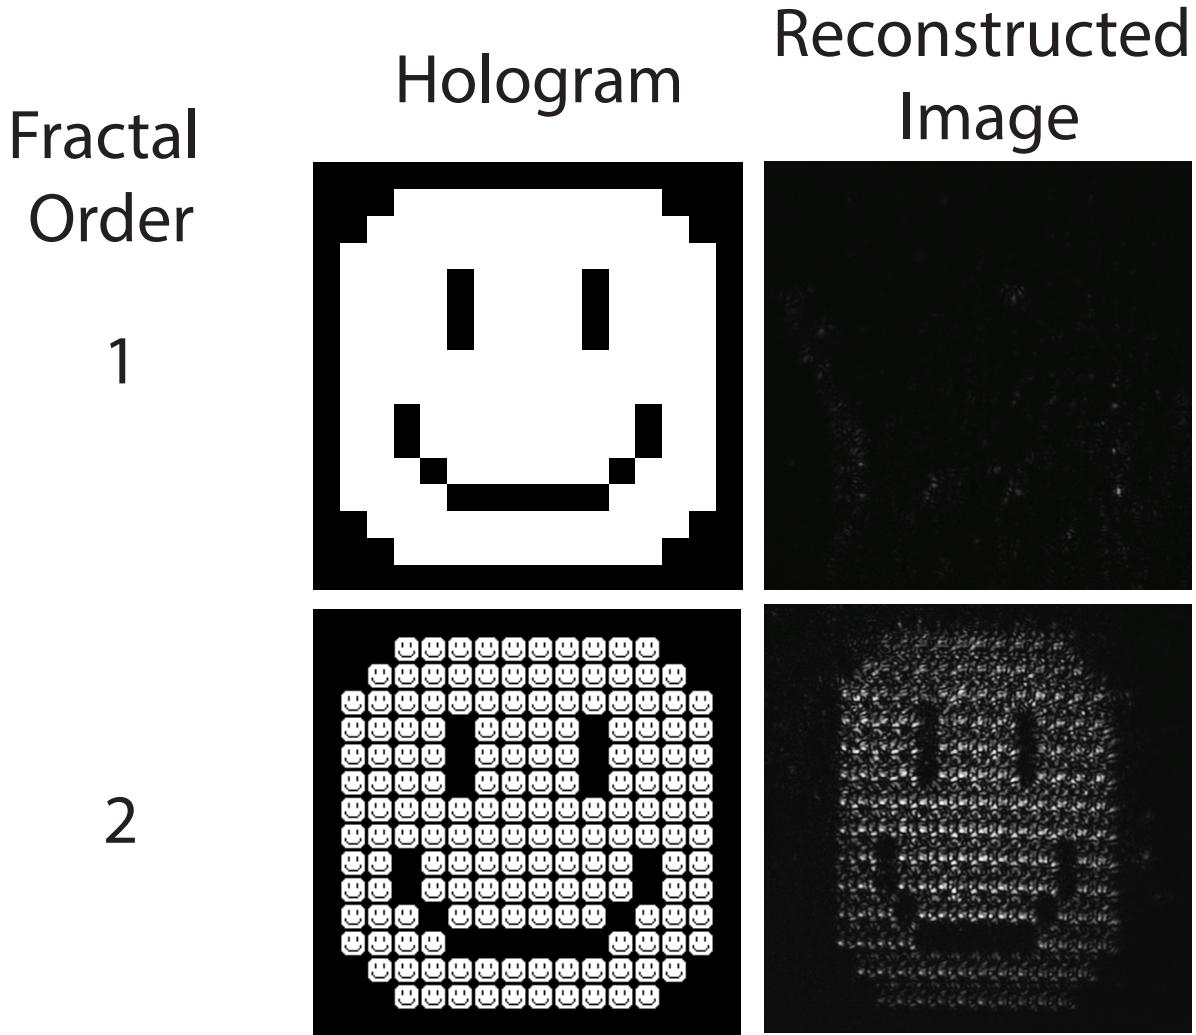


Figure 4.5: As an example of a more complicated image, a smiley face is fractalized, the Fourier transform is taken, 99% of the signal is blocked at the focal plane, and the image is reconstructed. This is compared to the original signal that is not fractalized.

Fractal structures have been utilized in signal communications and data compression for decades. Fractal antennas for the radio frequency and microwave regimes are known for being compact and versatile over wide spectral bands [Radonic et al. (2012); Puente-Baliarda et al. (1998)]. Fractal encoding algorithms enable image compressing with higher-

resolution compression at the expense of greater algorithmic complexity [Jacquin (1993)]. The trade-off for higher resolution fractal-compressed images is higher processing times, which presents a limitation of their presence in data communications. Recently, however, there has been a resurgence of interest in fractal architecture due to their robust properties in optical transmission.

## 4.5 Conclusion

This chapter has shown that the diffractal architecture provides the beneficial features of spatial multiplexing and robust reconstruction. Demonstrations have been shown with the Sierpinski carpet, a familiar fractal, although the results could have been demonstrated with 511 other patterns similarly imprinted with the diffractal architecture. Data that is transmitted with the diffractal architecture is highly robust to intermediate-obstacle signal blocks and diffractal subsections of arbitrary size and location carry sufficient information to regenerate the original signal without distorting outlines of its pattern. This research illuminates potential applications in data transmission systems when one transmitter sends data to a large number of moving receivers or through noisy media.

## 4.6 Experimental difficulties and future work

A SLM works well for experimentation because of its facile reconfigurability, however the resolution is limited to  $800 \times 600$  pixels, that limits the complexity of the data image sent in the process. Ways to overcome this could be to use photolithography to create transmission structures with a larger pattern on a glass film, however the structure would lose the reconfigurability that the SLM possesses. Transmission could even be created by printing the transmission structure pattern on transparency sheets, which would be a cheap alternative

method to achieve similar results with a lower resolution.

# Chapter 5

## Meta-optical chirality and emergent eigen-polarization modes via plasmon interactions

### 5.1 Introduction

Metamaterials are composed of sub-wavelength components, or meta-atoms that individually alter the intensity and phase of light. When placed on a 2D surface, metamaterials are known as metasurfaces [Zhao and Alu (2011)] and have enabled many applications from quarter [Yu et al. (2011)], half-wave plates[Ding et al. (2015)], and cross-polarizers [Qin et al. (2016)], to ultra-thin lenses [Aieta et al. (2012); Ni et al. (2013)]. Chiral metasurfaces can ultimately be defined as those that exhibit a response dependent on the incident circular-polarization handedness, though the specific mechanism behind the phenomena has been debated; it has been argued that planar structures such as metasurfaces cannot exhibit true optical activity (OA) or circular dichroism (CD) without the excitation of magnetic resonances since certain 3D symmetry properties are not satisfied [Hentschel et al. (2012); Eftekhari

and Davis (2012)]. The equivalent response from planar metasurfaces can be achieved by alternate methods such as the interaction of plasmon modes [Eftekhari and Davis (2012); Fan and Govorov (2010)], or by non-radiative dissipation [Khanikaev et al. (2016)], and is named optical chirality. The difference in transmission from different polarization states due to optical chirality produces an *equivalent* effect to OA and CD.

Optical chirality in metamaterials is produced in several ways. Not surprisingly, a chiral metamaterial can be composed of chiral meta-atoms, in which the mirror image of the structure cannot be superimposed on the original [Zhang et al. (2014); Tang et al. (2016)]. Intrinsically chiral materials are chiral due to the geometry of the meta-atoms themselves, and exhibit chiral behavior at normal illumination incidence. Helices [Kuzyk et al. (2012)], gam-madions [Cao et al. (2013); Kwon et al. (2008)], or nanoparticle assemblies [Fan et al. (2010); Guerrero-Martinez et al. (2011)] are common examples of intrinsically chiral meta-atoms that exhibit a strong chiral response. Another approach that achieves chiral asymmetry is the creation of a linear phase gradient, *i.e.*, illumination at oblique incidence [Yannopapas (2009); Cao and Cryan (2012); Cao et al. (2015b,a); Proscia et al. (2016)] or spatial variation of the unit cell [Aieta et al. (2012); Yu et al. (2011); Shaltout et al. (2014)]. The chiral response that arises from the linear phase gradient of either of these approaches is associated with extrinsic chirality.

This chapter instead focuses on the optical chirality that arises solely from the interactions between achiral meta-atoms. It is postulated that the nonlinear coupling between meta-atoms originates from an interaction force derived from the Liénard-Wiechert potential [Jackson (1999)], which accurately predicts measured changes in the experimental transmission spectra. Rectangular plasmonic resonators are studied whose arrangement leads to chiral phenomena at normal incidence, or identical tilted achiral nanostructures in a lattice that lead to a chiral response. The individual nanostructures are achiral, yet the periodic array is chiral [Plum et al. (2011); Prosvirnin and Zheludev (2005)], and thus any chiral

response distills the interaction between plasmonic structures. Optical chirality is expected when the lines of mirror symmetry of the nanostructures do not coincide with the lattice array—the mirror image cannot be superimposed with the original. “Meta-optical chirality” refers to the macroscopic optical chirality that is both observed in the far-field and attributed to the interactions between plasmonic resonators. While many have alluded to the coupling between meta-atoms, few have addressed the origin of the interaction force.

Experimentally, a simple Babinet-inverted rod (dimensions  $\approx \lambda/5$ ) is employed as the meta-atom of the metasurface and arranged in a square array. When rod-shaped nanoapertures are tilted at an angle of  $22.5^\circ$  and illuminated with low-intensity visible light ( $\ll 1W/cm^2$ ), CD is measured on the order of 0.6 degrees of ellipticity. In comparison, while optimized and twisted split ring resonators can reach CD up to 16 degrees in the near infrared [Decker et al. (2010)], such meta-atoms require small features ( $\approx \lambda/20$ ). The relatively-large dimensions of the rod nanoapertures support dipolar plasmon resonances and can be fabricated easily with robust large-area processes. An approach is demonstrated here that leverages the interactions between simpler meta-atoms in order to achieve an optical chirality. The general approach boasts facile design, circumvents the complex structures that intrinsically chiral materials generally require, and forgoes the oblique illumination angle-of-incidence that is the crux of extrinsically chiral materials.

The chiral response exhibited by our metasurface is both appreciable and unexpected since plasmonic interactions generally manifest as nonlinear optical responses, which require high illumination intensities [Metzger et al. (2012); Kauranen and Zayats (2012)]; optical chirality are observed at intensities far below those generally required to yield nonlinear optical responses. The metasurface is interrogated with a continuum of polarization states and find that the metasurface cannot be characterized simply from its response from orthogonal circular-polarization modes. In fact, a conventional transmission matrix description of the polarization properties is insufficient to accurately describe the optical behavior of the

metasurface. An alternative analytic representation is provided and supports a description of intensity-independent, weakly-nonlinear plasmonic limit cycles. The model also explains why the emergence of multiple eigen-polarization modes is observed, which is also measured experimentally. The work presented in this chapter furthers the understanding of metasurface design and breaks from the long-standing convention of transmission matrices.

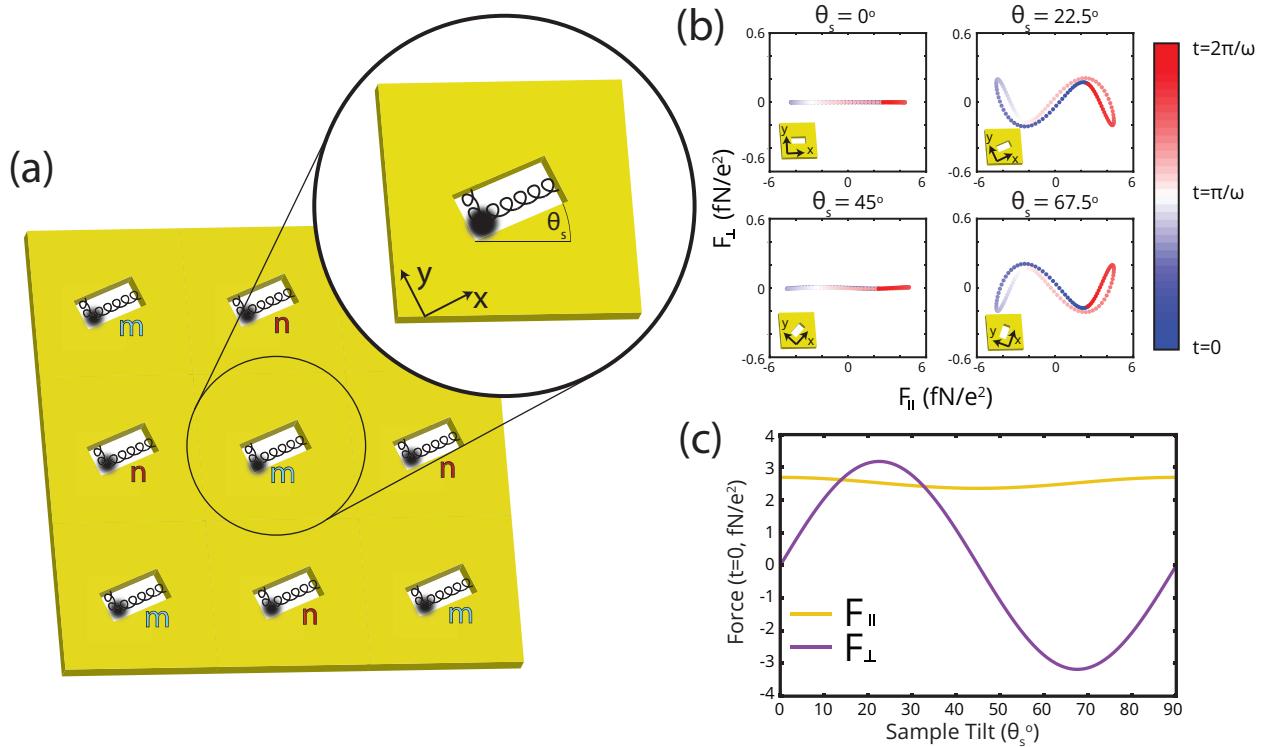


Figure 5.1: (a) Model representation: an array of plasmonic resonators (rod-shaped apertures) tilted at  $\theta_s$  relative to the base of the unit meta-atom where we separate the resonators into *m*- and *n*-type. The interaction force on *m*-type resonators results from the 4 nearest *n*-type resonators and vice-versa. (b) The interaction Lorentz force that arises from Larmor radiation [Eq. 5.1] for various  $\theta_s$  when resonators oscillate in the *x*-direction, as a function of time. (c) The interaction force in the parallel (*x*), and perpendicular (*y*) directions when the resonators oscillate in the *x*-direction, as a function of  $\theta_s$ .

## 5.2 The coupling force

In this model, the interaction between neighboring plasmonic resonators is defined as the Lorentz force produced from the oscillation of adjacent resonators. The interaction force is derived from the electromagnetic field of an accelerating charged particle given by the Liénard-Wiechert potential [Jackson (1999)]. The force from an  $m^{th}$  charge on the  $n^{th}$ ,  $\vec{F}_{mn}^{int}$ , is:

$$\vec{F}_{mn}^{int} = k_e q_n q_m \left( \frac{\hat{\boldsymbol{\nu}}_{mn} - \vec{\beta}_n}{(1 - \vec{\beta}_n \cdot \hat{\boldsymbol{\nu}}_{mn})^3 R_{mn}^2} \right) + \frac{k_e q_n q_m}{c} \left( \frac{\hat{\boldsymbol{\nu}}_{mn} \times [(\hat{\boldsymbol{\nu}}_{mn} - \vec{\beta}_n) \times \dot{\vec{\beta}}_n]}{(1 - \vec{\beta}_n \cdot \hat{\boldsymbol{\nu}}_{mn})^3 R_{mn}} \right) \quad (5.1)$$

where  $k_e$  is Coulomb's constant =  $1/4\pi\epsilon_0$ ,  $\epsilon_0$  is the permittivity of free space,  $\vec{\beta}_n = \dot{\vec{r}}_n/c$ ,  $c$  is the speed of light,  $\hat{\boldsymbol{\nu}}_{mn} = \frac{\vec{r}_m - \vec{r}_n}{|\vec{r}_m - \vec{r}_n|}$  is the unit direction from the  $m^{th}$  charge to the  $n^{th}$ ,  $R_{mn}$  is the lattice distance,  $q_n$  is the charge of the  $n^{th}$  particle, and  $\vec{r}_m, \vec{r}_n$  are the positions of the  $m^{th}$ , and  $n^{th}$  resonator, respectively, from the origin. When the charges are stationary, Eq. 5.1 collapses to the Coulomb force between two charged particles. The first term of Eq. 5.1 is referred to as the “velocity field” since it is independent of acceleration, and the second term is the “acceleration field”. With motion of the charges restricted to the 2-D plane of the metasurface, the interaction forces created by the surrounding resonators are produced in the plane of the metasurface. Though charges also oscillate in the  $z$ -direction, an investigation into the coupled behavior of the longitudinal fields is beyond the scope of this study. The associated Lorentz forces may explain the near-to-far-field coupling [Vuong et al. (2010)].

A representation of the model is shown in Fig. 5.1(a), in which all nanostructures are tilted by  $\theta_s$  relative to the base of the unit cell. The tilt effectively restricts the direction of motion of the resonator and we incorporate the interaction force into the equations of motion for a Lorentz-Drude plasmonic resonator [Rakic et al. (1998)]. The metasurface is modelled such that there is no spatial variation of the unit cell, *i.e.*, all nanoapertures are tilted at the

angle,  $\theta_s$ . For analytical reasons the  $x$  and  $y$ -axes also rotate by  $\theta_s$  such that the long (short)-axis of the plasmonic resonator is always parallel with the  $x$  ( $y$ )-axis. The  $\theta_s$  determines the directions of  $\vec{\beta}_m$ , and  $\vec{\nu}_{mn}$  in Eq. 5.1. The resonators are placed in a checkerboard-like pattern of  $m$ - and  $n$ -type oscillations, and calculate the motion of each set of resonators. The second-order terms cancel by symmetry, and subsequently the interaction force between resonators scales inversely with the distance cubed. The four closest resonators provide the interaction force that couple motion in the  $x$ - and  $y$ -directions, and between  $m$ - and  $n$ -type resonators. Interaction forces from diagonal dipoles are between like-type resonators ( $m$ - $m$ ,  $n$ - $n$ ) and are neglected, in part because the increased distance between resonators reduces the interaction force, and also because the focus is on the interactions between  $m$ - and  $n$ -type.

The total interaction force from the Larmor radiation of the four closest resonators is shown in Fig. 5.1(b-c), where  $\beta = -i\omega x_0/c\hat{i}$  and  $x_0$  is the maximum displacement of the charge oscillation, and  $x_0 = 20\text{nm}$ . Each resonator oscillates in the  $x$ -direction and produces a force in both parallel ( $x$ ) and perpendicular ( $y$ ) directions,  $F_{\parallel}$  and  $F_{\perp}$ .  $F_{\parallel}$  is calculated to be approximately 20 times larger than  $F_{\perp}$ . The  $F_{\parallel}$  —which is always co-aligned with the long axis of the nanostructures—is maximal when the nanostructures are oriented at  $0^\circ$  or  $90^\circ$  with the edge of the unit cell.  $F_{\parallel}$  couples the parallel motion between adjacent resonators in the formation of hybrid modes, which we document in the next section. When the angle of the nanostructure,  $\theta_s$ , is  $0^\circ$ ,  $45^\circ$ , or  $90^\circ$ ,  $F_{\perp}$  is zero, as shown in Fig. 5.1(b-c). These angles correspond to the lines of symmetry of the square lattice; the array is not intrinsically chiral. Alternatively, the magnitude of  $F_{\perp}$  is maximized at  $22.5^\circ$ , and  $67.5^\circ$  which would correspond to opposite-handed chiral structures.  $F_{\perp}$  couples to the orthogonal dipole moment of the adjacent resonators and is the source of optical chirality in the metasurface studied, which is further documented in the following section. Though this model incorporates the Liénard-Wiechert potential from rectangular nanostructures, the model can be generalized to model the interaction forces from arbitrary plasmonic shapes and arrays.

If the array was non-chiral there exists some combination of reflection, rotation, and translation of the nanoaperture array can be superimposed on the original. Figure 5.2 illustrates that when the nanoapertures are tilted at an angle  $\theta_s \neq m \times 45^\circ$  the modified array cannot be superimposed with the original.

### 5.3 Coupled equations of motion

The interaction force [Eq. 5.1] is summed from the four neighboring resonators to the Lorentz-Drude model and incorporate its interaction as a perturbation with the parameter,  $\delta$ :  $M\ddot{\vec{r}}_{m/n} = -M\omega_0^2\vec{r}_{m/n} - M\gamma\dot{\vec{r}}_{m/n} + q\vec{E}e^{-i\omega t} + \delta \sum_{n/m} \vec{F}_{mn}^{int}$ , where  $r$  is the displacement of the resonator from its equilibrium position,  $M$  is its mass,  $\omega_0$  is the natural harmonic frequency of the resonator,  $q$  is its charge,  $\gamma$  is the velocity-dependent damping rate,  $E_0$  is the strength of the incident driving electric field, with frequency  $\omega$ , subscript  $m/n$  refers to the motion of either  $m$ - or  $n$ -type resonators, and dot formalism corresponds to derivatives with respect to time,  $t$ . A separate solution is adopted for the displacement of the  $m$ - and  $n$ -type resonators shown below:

$$x/y(t) = \frac{E_{x/y}q/M}{\omega_{0x/y}^2 - i\gamma\omega - \omega^2} e^{-i\omega t} + \underbrace{x_h/y_h(t)}_{\text{homogeneous solution}} + \underbrace{\delta x_1/\delta y_1(t)}_{\text{perturbed solution}}, \quad (5.2)$$

which includes a homogeneous solution,  $x_h, y_h$ , often neglected [Metzger et al. (2016, 2012); Rakic et al. (1998)]. The homogeneous solution is the general solution to the equations of motion in the absence of an external electric field and its solution is determined from the initial conditions. Even though the homogeneous solution is neglected in Optics texts, it is generally present in studies of vibrations and when solving for the limit cycles of weakly nonlinear oscillators [Strogatz (1994)]. No exact analytical solution exists for the system in which the interaction force is included; our quantitative perturbative approach employs a

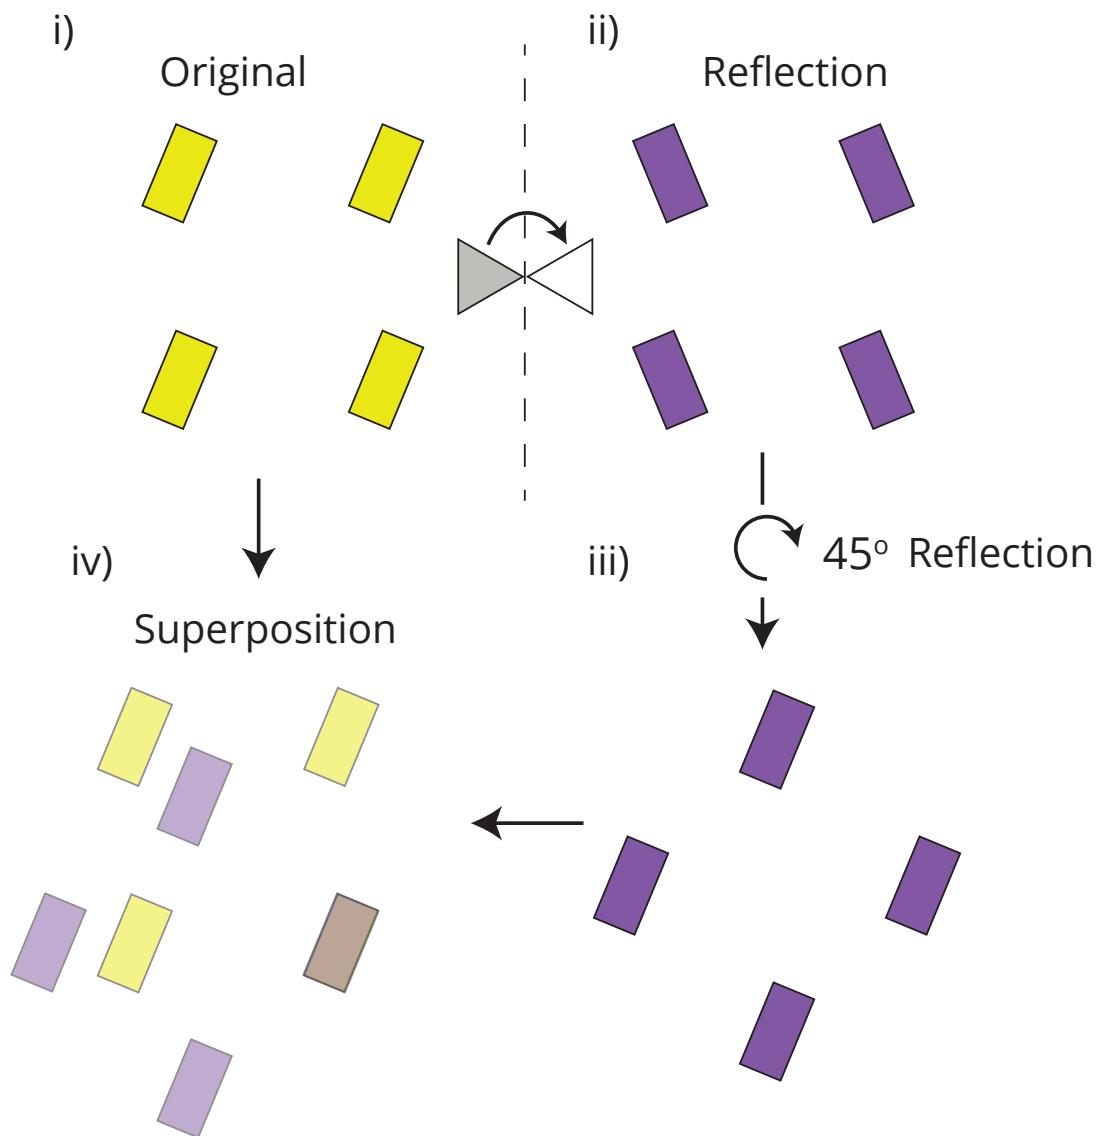


Figure 5.2: (i) The original array with tilt angle,  $\theta_s = 22.5^\circ$ . (ii) Reflection along the vertical axis. (iii) Rotation by  $45^\circ$ . (iv) Superposition of the original array with the modified array.

Taylor expansion of the interaction force,

$$\vec{F}_{mn}^{int} \approx \frac{k_e q_n q_m}{R_{mn}} \left[ \frac{(\hat{\boldsymbol{\nu}}_{mn} - \vec{\beta}_n)}{R_{mn}} + (\hat{\boldsymbol{\nu}}_{mn} \times [(\hat{\boldsymbol{\nu}}_{mn} - \vec{\beta}_n) \times \dot{\vec{\beta}}_n]) \frac{1}{c} \right] \\ \times \left( 1 + 3\vec{\beta}_n \cdot \hat{\boldsymbol{\nu}}_{mn} - 6(\vec{\beta}_n \cdot \hat{\boldsymbol{\nu}}_{mn})^2 - 10(\vec{\beta}_n \cdot \hat{\boldsymbol{\nu}}_{mn})^3 \right). \quad (5.3)$$

The low-power case is considered where the transmitted polarization is independent of illumination intensity and the interaction force is linear with respect to the electric field. The system remains nonlinear because the optical response cannot be described by a superposition of incident fields.

$$\begin{bmatrix} \ddot{x}_{1,m} \\ \ddot{y}_{1,m} \end{bmatrix} + \begin{bmatrix} \omega_{0x}^2 & 0 \\ 0 & \omega_{0y}^2 \end{bmatrix} \begin{bmatrix} x_{1,m} \\ y_{1,m} \end{bmatrix} + \gamma \begin{bmatrix} \dot{x}_{1,m} \\ \dot{y}_{1,m} \end{bmatrix} = \frac{1}{M} q_m \underbrace{\begin{bmatrix} \kappa_{1x,n} & \kappa_{3x,n} \\ \kappa_{3y,n} & \kappa_{1y,n} \end{bmatrix} \begin{bmatrix} E_x \\ E_y \end{bmatrix}}_{F^{int}}, \\ \begin{bmatrix} \ddot{x}_{1,n} \\ \ddot{y}_{1,n} \end{bmatrix} + \begin{bmatrix} \omega_{0x}^2 & 0 \\ 0 & \omega_{0y}^2 \end{bmatrix} \begin{bmatrix} x_{1,n} \\ y_{1,n} \end{bmatrix} + \gamma \begin{bmatrix} \dot{x}_{1,n} \\ \dot{y}_{1,n} \end{bmatrix} = \frac{1}{M} q_n \underbrace{\begin{bmatrix} \kappa_{1x,m} & \kappa_{3x,m} \\ \kappa_{3y,m} & \kappa_{1y,m} \end{bmatrix} \begin{bmatrix} E_x \\ E_y \end{bmatrix}}_{F^{int}}, \quad (5.4)$$

where

$$\kappa_{1x} = A_x \left[ 3ka + 2i + 6 + 3k^2 \left( -\langle x_h \rangle^2 (3ka \cos(4\theta_s) + A) \right. \right. \\ \left. \left. + \langle y_h \rangle^2 (9ka \cos(4\theta_s) + A) + \langle x_h y_h \rangle 9ka \sin(4\theta_s) \right) \right], \quad (5.5)$$

$$\kappa_{1y} = A_y \left[ 3ka + 2i + 6 + 3k^2 \left( \langle y_h \rangle^2 (3ka \cos(4\theta_s) + A) \right. \right. \\ \left. \left. + \langle x_h \rangle^2 (9ka \cos(4\theta_s) + A) - \langle x_h y_h \rangle 9ka \sin(4\theta_s) \right) \right], \quad (5.6)$$

$$\kappa_{3x} = 3A_x k^2 \left[ 3ka \sin(4\theta_s) (3\langle x_h \rangle^2 - \langle y_h \rangle^2) - 3\langle x_h y_h \rangle (9ka \cos(4\theta_s) + A) \right], \quad (5.7)$$

$$\kappa_{3y} = 3A_y k^2 \left[ -3ka \sin(4\theta_s) (3\langle y_h \rangle^2 - \langle x_h \rangle^2) - 3\langle x_h y_h \rangle (9ka \cos(4\theta_s) + A) \right], \quad (5.8)$$

and where  $A_x = \frac{2k_e q_m q_n k}{Ma^2} g_x$ ,  $A_y = \frac{2k_e q_m q_n k}{Ma^2} g_y$ ,  $A = 3ka + 4i$ ,  $a$  is the periodicity of the metasurface,  $k$  is the incident wavevector,  $\langle \rangle$  denotes the time-average, and  $g_{x/y} = \frac{1}{\omega_{0x/y}^2 - i\gamma\omega - \omega^2}$ .

While Eq. 5.4 may resemble a transmission-matrix formalism, the equations of motion of one type of resonator are coupled to the other by its homogeneous solution and subsequently, there are four coupled equations of motion instead of two. When the  $m$ -type resonators are excited, they generate Lorentz forces via the Liénard-Wiechert potential, which contribute to both parallel and perpendicular motions of the  $n$ -type resonators.

The perpendicular Lorentz force couples to the orthogonal modes of the different resonators, which leads to optical chirality in the metasurface. In order to understand the terms of Eq. 5.8, the plasmonic resonators are restricted to move only in either the  $x$ - or  $y$ -directions in the fundamental solution. The perturbative interaction becomes  $\kappa_{3x/y} = \pm \frac{9k_e q_m q_n 2k^4}{Ma} g_{x/y} \langle y_h/x_h \rangle^2 \sin(4\theta_s)$ , which is zero when  $\theta_s = 0^\circ, 45^\circ, 90^\circ$ , etc., in agreement with the exact evaluation of  $F^{int}$  [Fig. 5.1(b-c)]. Maximal optical chirality is achieved when the nanostructures are tilted at  $\theta_s = 22.5^\circ$  and  $67.5^\circ$ .

## 5.4 Mode hybridization and optical chirality

Experimentally, a metasurface is fabricated that maximizes  $F_\perp$  or  $\kappa_{3x/y}$  with  $\theta_s = 22.5^\circ$ , in which rod nanoapertures are arranged on a 30-nm gold film and measure 160nm by 80nm, as shown in Fig. 5.3(a). The periodicity,  $a$ , varies the relative strength of the interaction force. A periodicity of 375nm is employed in a square array, which is small enough to observe the coupling between nanoapertures, yet large enough so that the individual responses are still present.

The wavelength-dependent transmission properties are explored in Fig. 5.3(b), which shows the transmission for linearly-polarized light. The axis of the illuminating linear polarization is rotated counter-clockwise from  $0^\circ$  (vertical) through  $90^\circ$  (horizontal) to  $180^\circ$  (vertical). We observe two absorption dips in the transmission around 600nm and 730nm that correspond to the mode-splitting or mode hybridization of the plasmonic dipolar reso-

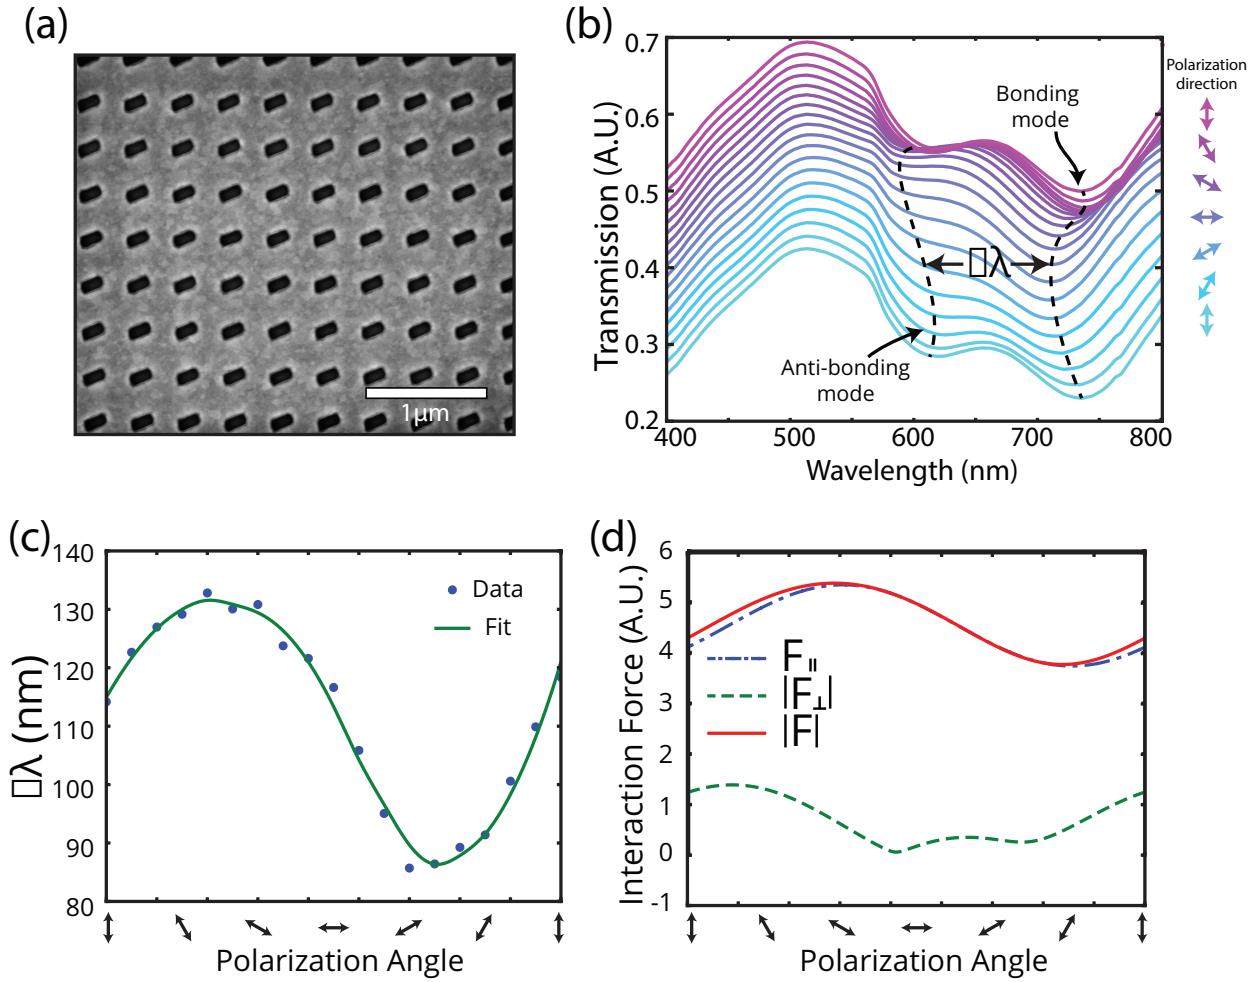


Figure 5.3: (a) A top-view scanning electron microscope image of the metasurface. (b) The transmission spectra associated with different linear polarization angles, where we observe the presence of bonding and anti-bonding modes. (c) Shift in the wavelengths of the bonding and anti-bonding modes as a function of polarization angle. (d) Interaction forces parallel and perpendicular to the polarization axis experienced by the resonators from Eq. 5.4 as a function of polarization angle.

nance [Prodan et al. (2003)]. The spectral locations of the bonding and anti-bonding modes correspond to the mode coupling or interaction force  $F^{int}$ . When the periodicity decreases,  $F^{int}$  increases and the resonances separate further; if the separation between meta-atoms increases, then the transmission resonances collapse to the transmission profile of a single resonator [Prodan et al. (2003)]. The trends associated with meta-atom spacing indicate that the transmission dips observed are not a Wood's anomaly grating effect, which is related to lattice absorption. Wood's anomaly resonances would scale in proportion with the metasurface spacing. Moreover, Wood's anomalies are characterized by ultrasharp resonances [Yang et al. (2016)] which are not observed.

The parallel component of the interaction force leads to the mode-splitting in the metasurface. The spectral difference between the bonding and anti-bonding modes is shown in Fig. 5.3(c) with a Savitzky-Golay filter [Savitzky and Golay (1964)] overlaid. The interaction force is evaluated in the approximation [Eq. 5.4] in order to relate the model to the mode

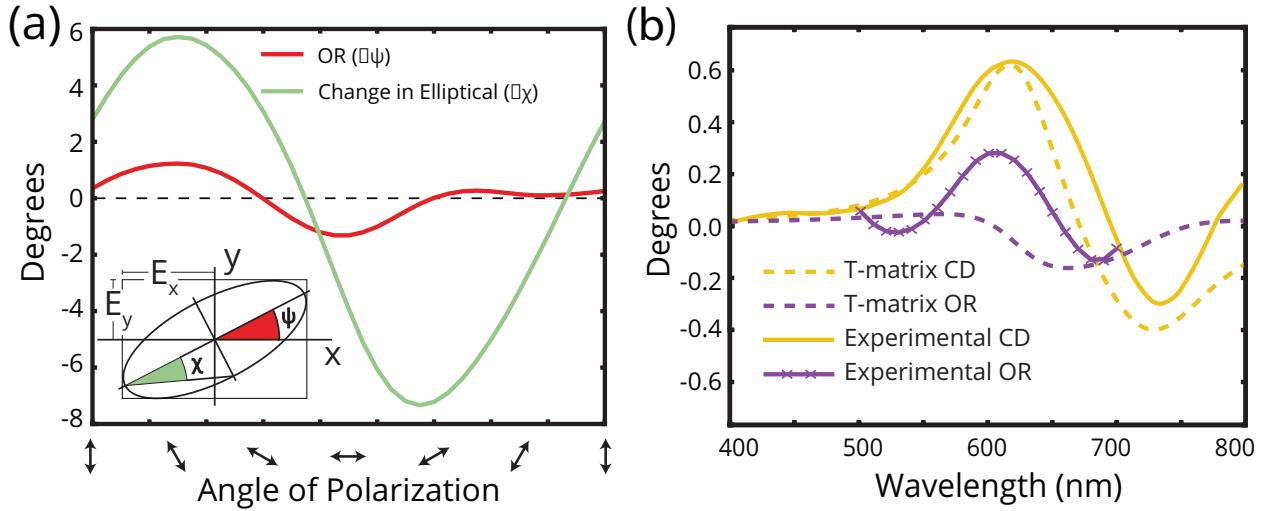


Figure 5.4: (a) The optical rotation (OR) and change in the elliptical component as a function of input polarization at 660nm. Inset: the relationship between  $E_x$  and  $E_y$ , OR and change in the elliptical on the polarization ellipse. (b) OR and circular dichroism (CD) calculated from a transmission (T-)matrix approach (dashed). Overlaid is the experimental measurements of OR (measured at  $\psi = +30^\circ$ ), and the CD (solid).

splitting. The components of the interaction force,  $F_{\perp}$ ,  $F_{\parallel}$ , and  $|F| = \sqrt{F_{\perp}^2 + F_{\parallel}^2}$  are shown in Fig. 5.3(d), where the input polarization is rotated from  $0^\circ$  to  $180^\circ$ . The  $F_{\parallel}$  and the trendline of the spectral shift both exhibit maximal values between  $45^\circ$  and  $55^\circ$ , where the illuminating linear polarization connects opposite ends of vertically-adjacent resonators. The minimal values of the spectral splitting occur between  $135^\circ$  and  $145^\circ$  and correspond with an angle where the illuminating linear polarization connects opposite ends of horizontally-adjacent resonators. Differences between the model and experiment result from the fact that in the model, only 20nm resonator displacement is considered whereas in experiment, the effective resonator dipole is the length of the nanorod, or 180nm. Moreover, the approximation of  $F^{int}$  only accounts for the four nearest resonators and incorporates only time-harmonic terms. Nevertheless, the strength of the parallel force  $F_{\parallel}$  scales approximately with the experimentally-measured spectral splitting of transmission resonances.

The interaction force leads to other experimentally-measured polarization-dependent metasurface responses. We illuminate the metasurface with linearly-polarized light (ellipticity  $\chi < 1^\circ$ ) at a wavelength  $\lambda = 660\text{nm}$  and observe that the transmitted changes in the azimuthal and elliptical components of the fields,  $\Delta\psi$  and  $\Delta\chi$ , depend on the angle of linear polarization [Fig. 5.4(a)]. The change in azimuth  $\Delta\psi$  denotes optical rotation (OR) and the change in the elliptical component  $\Delta\chi$  denotes the phase accumulation between the  $E_x$  and  $E_y$ -components. When the illuminating polarization angle rotates a full revolution, the trendline for the OR exhibits 4 inflection points. The OR and the perpendicular interaction force  $F_{\perp}$  follow a similar trend [Fig. 5.3(d)], which is expected since  $F_{\perp}$  is the source of the optical chirality in our metasurface.

Optical chirality is conventionally determined by the off-diagonal elements of transmission matrix of the metasurface [Wu et al. (2016); Plum et al. (2016, 2011)] but there are limits to this transmission matrix formalism. The polarization density of the material is calculated with the relation  $\vec{P} = N_0 q \vec{r}$ , where  $N_0$  is the free charge carrier concentration of the material,

$q$  is the charge of the particles, and  $\vec{r}$  is the direction and subsequently:  $\vec{P} = N_0 q \begin{bmatrix} x_0 + x_1 \\ y_0 + y_1 \end{bmatrix} = \epsilon_0(\epsilon - 1)\vec{E}(\omega, r) + \Gamma(\nabla \times \vec{E}(\omega, r))$ , and the non-locality parameter,  $\Gamma_{x/y} = \frac{iN_0 q_m q_n \kappa_{3x/y}}{k(\omega_{0x/y}^2 - i\gamma\omega - \omega^2)}$ , and  $\Gamma$  is the mean of  $\Gamma_x$  and  $\Gamma_y$ . The relations for OR =  $\frac{\omega}{2c}\Re(\Gamma)$ , and CD =  $\frac{2\omega}{c}\Im(\Gamma)$ , are shown as a function of the incident wavelength for tilt angle of  $\theta_s = 22.5^\circ$  in Fig 5.4(b) and the experimental observation is overlaid. The CD is defined as the differential circular-polarization absorption as  $CD(^o) = (T_{RCP} - T_{LCP}) \times 32.982^\circ$  in degrees of ellipticity [Barron (2009)]. The experimental results for CD qualitatively agree well with the analytical theory for the CD, where peaks in CD are present at both dipolar modes. In a transmission-matrix calculation, there is less agreement between the real component of  $\Gamma$  and the experimentally-measured OR. It is expected that CD may be more accurately modeled with transmission matrices because the rotating circular polarization averages all linear-polarization responses, and reduces the polarization-dependence illustrated in Fig. 5.3. The discrepancies between theoretical and experimental OR indicate the limit of the transmission matrix formalism that assumes that all resonators oscillate in-phase, which may not be true when an interaction force is present between meta-atoms.

## 5.5 Emergent polarization eigenmodes

The metasurface is interrogated with a continuum of polarization states and observe polarization-dependent responses other than OR that cannot be recreated by transmission matrices. The properties of the metasurface eigen-polarization modes are characterized at a wavelength of 660nm on the Poincaré sphere [Fig. 5.5(a)]. Figure 5.5(b) shows the eigen-polarization modes mapped onto the  $x - y$  plane, where the wave travels in the  $z$ -direction. The eigen-polarization modes of the system are interpreted as eigenmodes of the coupled equations of motion of the system.

Six eigen-polarization modes of the metasurface are measured, where a standard transmission matrix approach asserts the existence of only two [Gevorgyan and Rafayelyan (2013)]. Two of the six eigen-polarization modes are approximately linearly-polarized, and the remaining four are elliptically-polarized. The presence of the multiple eigen-polarization modes cannot be characterized by the conventional, single transmission matrix formulation —which assumes that adjacent resonators are excited in phase —and supports an alternative model of coupled resonators.

There is potentially a misconception that transmission matrices should describe any metasurface optical response that is independent of the illumination intensity. The optical response from our metasurface is linear because the transmitted polarization does not change with illumination intensity and would not produce the prototypical nonlinear optical response, for example, higher-harmonic generation, particularly at low illumination intensities. At the same time, the transmitted polarization from our metasurface is nonlinear in a manner that the optical response cannot be described by a superposition of incident fields. It appears insufficient to characterize the polarization properties of the metasurface

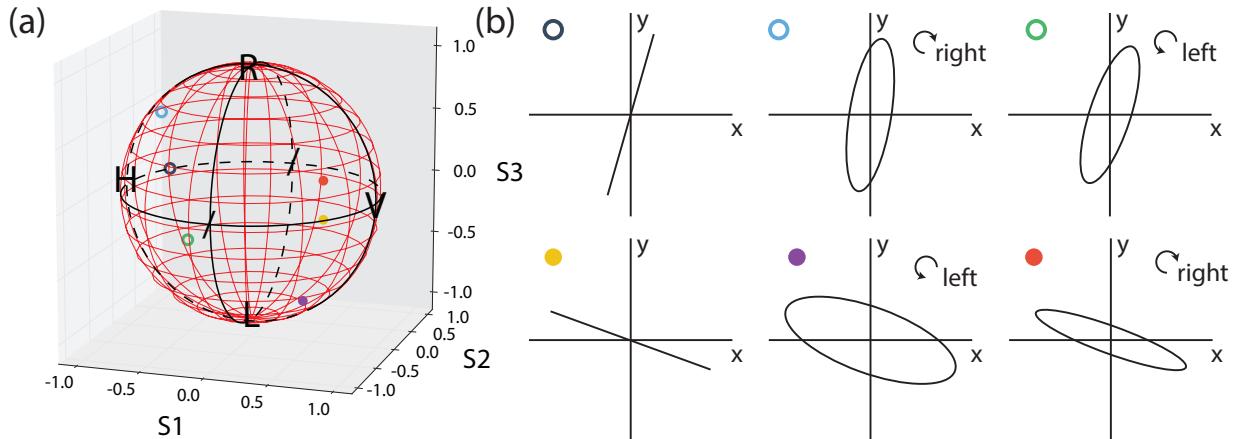


Figure 5.5: Eigen-polarization modes of the system at 660nm are shown on (a), the Poincaré sphere, where solid circles represent eigen-polarization states on the near surface of the sphere and hollow circles represent states on the far surface. (b) illustrates the eigen-polarization states measured in the  $x - y$  plane.

by deriving a transmission matrix from the optical response of select linear or orthogonal circular polarizations. The corresponding system of equations in the model predicts multiple polarization eigenmodes that are observed at visible wavelengths and at low illumination power, independent of illumination intensity.

## 5.6 Discussion

The inclusion of an interaction force leads to responses that are not predicted via transmission matrices, such as polarization-dependent OR or multiple eigen-polarization modes, which are measured in this investigation. Discrepancies from a transmission matrix formalism may be minimal when the interaction force is small and when meta-atoms are separated significantly far apart [Haus (2014)]. However, initial calculations suggest that the Larmor radiation from adjacent meta-atoms achieves intensities comparable to that of the incident electric field, even at low illumination intensities, due to the strong acceleration of charges on sub-wavelength nanostructures at visible wavelengths. Moreover, the constructive interference of Larmor fields in periodic lattice structures such as metasurfaces is measurable. The Larmor radiation field may be engineered to produce a desired electromagnetic response. One method to increase the Larmor radiation, and thus the optical chirality, is to reduce the periodicity of the nanostructures since the interaction force [Eq. 5.1] scales with the inverse distance between resonators. However, as Lee and Park (2016) showed, the dependence on periodicity does not continue to increase the interactions forces indefinitely since at the limit of zero periodicity we expect the scattering cross section of the array of coupled plasmonic resonators to reduce to that of a single resonator. In order to satisfy this condition, a screening factor of  $S = 1 - e^{-\sqrt{2/3}ka}$  is employed so that the interaction forces converge to zero at zero periodicity.

## 5.7 Conclusion

In conclusion this chapter proposes a facile design approach to achieve optical chirality at normal incidence in planar arrays of achiral nanoapertures that leverages the interaction force between coupled resonators. Optical chirality results from perpendicular Lorentz forces associated with the Liénard-Wiechert potentials when plasmonic resonators are sufficiently close. Bonding/anti-bonding modes observed in the transmission spectra result from the parallel components of the interaction forces. The polarization properties are studied and it is demonstrated that this metasurface exhibits both OR and CD equivalent responses at normal incidence in the visible regime, a property found only in chiral materials. The OR depends on the incident angle of polarization and cannot be fully described by transmission matrices. This principle is further demonstrated through the measurements of several eigen-polarization modes. The presence of appreciable optical chirality in our metasurface indicate Larmor radiation plays a significant role in the polarization properties of metasurfaces.

## 5.8 Fabrication methods and measurement

The device can be fabricated by depositing a nanopatterned gold layer onto an ohmic conductor. The gold layer can be deposited onto the ohmic contact via thermal deposition which can give accurate layer thicknesses. Layer thicknesses are determined using a Filmetrics spectral reflectance analyzer. A calibration layer is first deposited on a substrate to correctly determine the rate of deposition for particular equipment settings. Once the rate of the metal are determined, the layer can be deposited, and the layer thicknesses determined using the spectral reflectance analyzer. Following, a layer of high resolution positive electron beam resist, ZEP-520A, is spin-coated on the gold layer. ZEP-520A is required to show the sharp definitions and high resolution that the nanostructure design demands. The nanostructure is patterned into the ZEP-520A resist using electron beam lithography,

using ion beam milling the patterned resist is removed and gold where the the resist was etched away. This process can be done to leave either gold nanostructures or a gold film with nanoapertures.

The patterns are created in Adobe Illustrator since the dimensions of the objects are accurately input. Adobe Illustrator also has the feature of exporting to DXF and DWG files. These files are compatible with the BEAMER software that is provided at Brookhaven National Lab to create the patterns compatible with the electron beam lithography machine.




Figure 5.6: Electron beam lithography pattern, nanoapertures measure 80nm by 160nm in a square lattice with periodicity between the structures measuring 375nm.

### 5.8.1 Development

#### Electron beam resist

The electron beam resist used was ZEP-520A, the resist thicknesses as a function of spin speed and dilution has been studied elsewhere [Bojko (2013)], the thickness data is given as follows in Fig. 5.7. ZEP-520A has the properties of showing very high resolution, a rectangle pattern profile, and high sensitivity. This is important for this work since the structures that will be fabricated are on the order of  $10^{-8}m(10nm)$ , and thus the electron beam resist needs to show the greatest contrast for the nanostuctures to be well defined and have the desired optical properties.

Another common electron beam resist that was considered is PMMA. PMMA is the most common electron beam resist used since it offers high resolution, is easy to handle and film characteristics have been well-studied. Though, like ZEP-520A, PMMA also provides high resolution it exhibits low contrast, which could lead to undesired optical properties.

Characteristics of ZEP-520A, are that it has a positive tone, resolution of at least 20nm, has a dry etch resistance similar to many photo resists. The film life, however is relatively short compared to other electron-beam resists such as PMMA.

#### Fracturing

The shot pitch of the electron beam lithography machine is set to 0.125nm. Since at some points of the structure the shot pitch is not exactly divisible by the shape size, the dimensions of the shape produced may be slightly off (by a maximum of one shot pitch) To solve this problem shot pitch fracturing is enabled, such that some extra pixels are overlapped and the correct dimensions specified are achieved [BEA (2010)]. This is important in fabricating the structures since they have very small feature sizes. Plasmonic effects are highly sensitive to structure dimensions, thus, shot pitch fracture is necessary to retain the specific dimensions

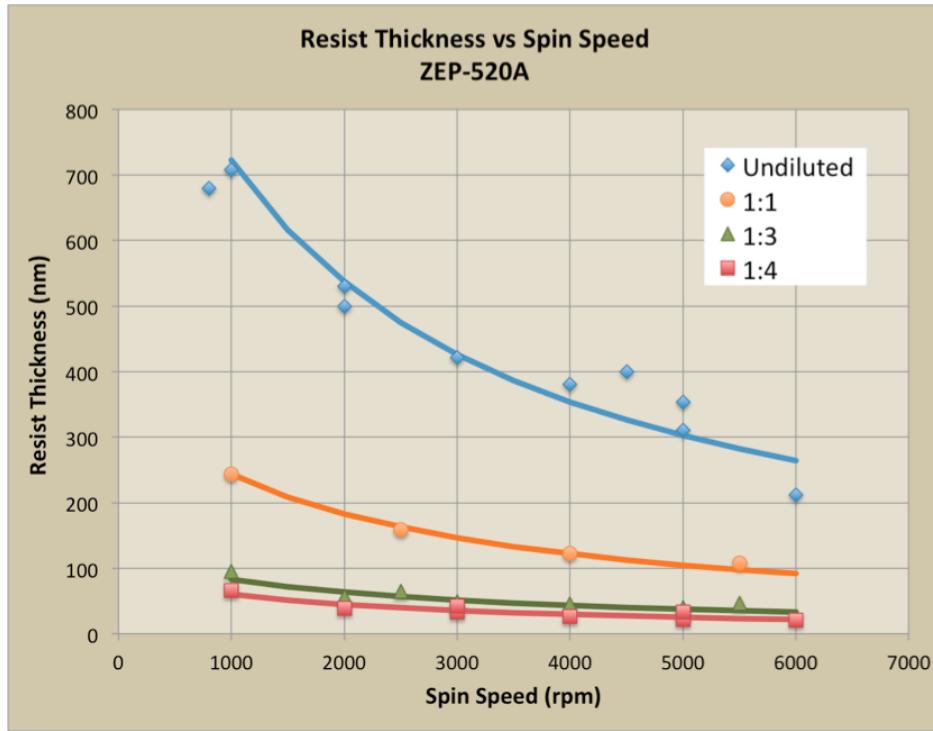


Figure 5.7: Spin curve for ZEP-520A.

Image: <https://ebeam.mff.uw.edu/ebeamweb/process/process/zep520a.html>

of the nanostructures, and by relation the plasmonic response is preserved.

### Proximity effect correction

From looking at SEM images of the 2D nanostructures it is clear that the shapes do not have as sharp corners as originally intended. The reason for this is due to scattering of the electron beam in the resist and substrate leading to undesired resist etching in the proximity of the beam, known as the proximity effect [Owen and Rissman (1983)]. Though the individual shapes are the same size the edges of nanostructures are likely to experience the proximity effect.

One way to use proximity effect correction is via dose modulation, in which each individual shape in a pattern is given a dose such that the shape prints the correct size. Generally, the proximity effect can be thought of as larger-patterned areas receive larger doses due to

the electron scattering. To compensate the larger areas receive slightly lower dosages, or alternatively, the smaller areas receive slightly higher dosages.

Another method to resolve the proximity effect is via pattern biasing. In this method the larger dose that greater area patterns receive from the proximity effect is compensated by making the area either smaller or less dense.

Practically it is easier to implement the second method on the electron beam lithography machine, as it keeps the dosage the same throughout the writing of the pattern, only varying the pattern itself.

## Developers

There are a number of different developers available for use. Xylenes is a common developer since the dosage needed is low, so patterns can be written faster, however the contrast is generally low. Amyl-acetate has a higher contrast, and hexyl-acetate has the highest contrast, though the higher the contrast, the higher dosage generally needed to write the pattern and develop effectively. Better yet is to use hexyl-acetate at low temperature.

### 5.8.2 Recipe

The recipe of rod-shaped nanoapertures is as follows: First on a glass substrate a 3-nm wetting layer of chromium was deposited, followed by a 30-nm layer of gold with an electron beam evaporator. The thicknesses of the layers were accurately measured via a Filmetrics F20-UV thin film analyzer that is available both at Brookhaven national lab and at the Vuong lab. From an initial test sample the rates of the electron beam evaporator were accurately determined to produce reliable film thicknesses. The rates of chromium and gold were deposited at a rate of  $0.4\text{\AA}$  per second to produce film with high uniformity and low

surface roughness(<2nm).

Next a layer of ZEP 520a is spin-coated onto the sample. The thickness of which is determined by the thickness of gold and the ion-milling rates of both gold and ZEP 520a. Since the desired result is a gold film with rod-shaped apertures that propagate the entire thickness of the film, once the pattern is written on the resist, and developed, there will be rod-shaped apertures in the resist. At the ion-milling stage, where the pattern is written gold is exposed to the ion miller and will be milled away, everywhere else only the resist is exposed to the ion miller and will be milled. Ideally, as the resist is milled away, and the gold is milled away where the pattern is written, once the entire layer of resist is completely milled away, so is the gold, where the pattern is written. Therefore the layer of resist that needs to be spin-coated is equal to:

$$L_{ZEP} = \frac{MR_{Au}}{MR_{ZEP}} \times L_{Au}, \quad (5.9)$$

where  $MR_{Au}$  is the milling rate of gold,  $MR_{ZEP}$  is the milling rate of the resist, ZEP 520a,  $L_{Au}$  is the layer thickness of gold, and  $L_{ZEP}$  is the layer thickness of ZEP 520a.

Using a two test samples of substrates with gold and spin-coated ZEP 520a, by measuring the thicknesses of the respective layers both before and after a specified time of ion-milling, the milling rates for both gold and ZEP 520a were determined to be around  $0.1\text{\AA/s}$  and  $1\text{\AA/s}$  respectively. With a gold layer thickness of 30nm, the layer of ZEP 520a that was spin-coated necessarily had to be over 300nm. In this way, in the ion milling process the layer of resist will be completely milled away at the same time that the gold will be milled away where the pattern is written.

Once the layer of resist needed is known the spin speed can be determined via the spin curve given in Fig 5.7. From here we can see that a 1:1 dilution of ZEP 520a with a spin speed around 500rpm.

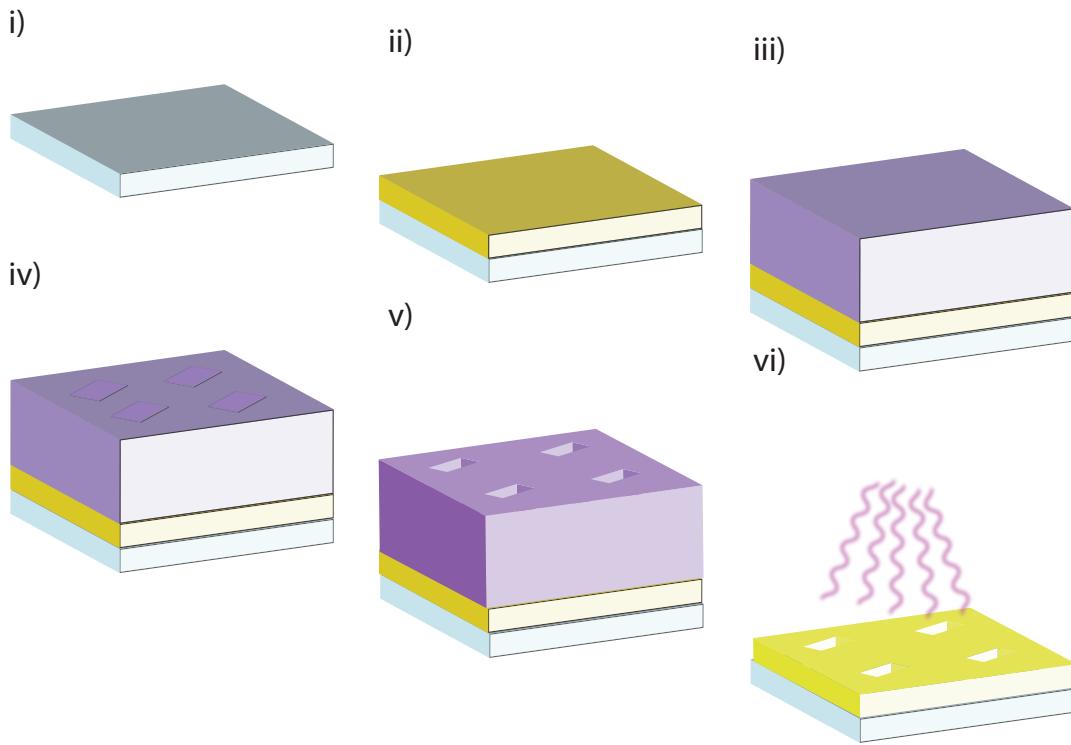


Figure 5.8: Recipe to fabricate nanoapertures. i) Glass substrate, ii) gold layer is deposited, iii) ZEP 520a electron beam resist is deposited, iv) pattern is written via electron beam lithography, v) pattern is developed, vi) resist and gold is milled away

Next, a  $1.5\text{mm} \times 1.5\text{mm}$  area pattern is written on the resist with the electron beam lithography machine. A via trial-and-error a dosage of  $500\mu\text{C}/\text{cm}^2$  was used. Trial-and-error was performed by setting a variety of dosages, running the pattern, developing, and inspecting under a scanning electron microscope to determine which particular dosages were under/over-exposed, and which worked best. In the same way the current of the electron beam was determined to be  $250\text{pA}$ .

Once the pattern is written the sample was developed, hexyl-acetate was determined to be the best developer due to its high contrast especially at low temperature conditions. The sample was developed in hexyl-acetate at  $-25^\circ\text{C}$  in a propylene glycol bath for 90 seconds followed by a rinse in iso-propyl alcohol.

Finally the sample was ion-milled such that the remainder of the resist is removed. The

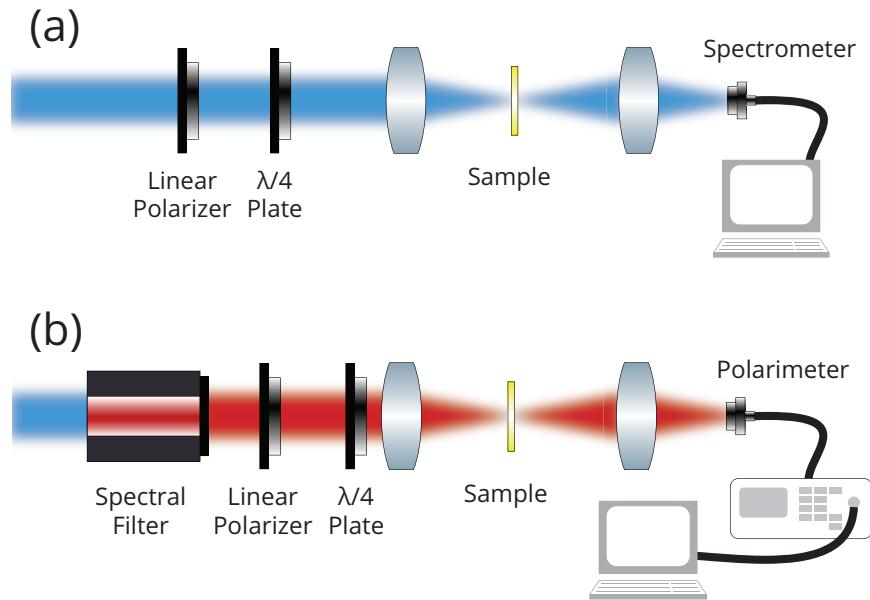


Figure 5.9: The schematic diagram for (a) transmission measurements and (b) polarization measurements.

sample was visually inspected for any resist.

Figure 5.3(a) shows a scanning electron microscope image of the metasurface from the top.

### 5.8.3 Transmission measurement setup

To measure the optical chirality from the metasurface we use a xenon solar simulator that provides stable broadband illumination between 400nm and 1000nm. The polarization state of light is controlled with a wire grid polarizer a 400-nm to 800-nm achromatic quarter-wave plate. The spectrum from the sample is captured via a CCD-coupled spectrometer [Fig. 5.9(a)].

### 5.8.4 Polarization measurement setup

The eigen-polarization states are determined in a similar setup described above, however a spectral filter is used and the CCD-coupled spectrometer is replaced with a polarimeter to

determine the polarization of transmitted light [Fig. 5.9(b)].

## 5.9 Experimental difficulties and future work

It has been demonstrated that chiral phenomena exists in regular arrays of rod-shaped nanoapertures tilted at  $22.5^\circ$ . To further establish this phenomena, arrays of nanoapertures may be fabricated with varying tilt angles and periodicities. Variation of the periodicity would affect the coupling between nanostructures, and variation of the tilt angle would vary the strength of the perpendicular force generated that leads to the chiral phenomena observed.

The same effect may also be achieved with nanostructures, i.e., the non Babinet-inverted structure. The recipe for this type of metasurface was attempted however, due to the lift-off step, which can be quite difficult to perform, this type of metasurface was not pursued. The type of metasurface is fabricated in much the same manner as the one investigated, however the gold film is deposited after the electron beam lithography process. This makes the fabrication challenging as the non-conductive property of the glass substrate creates a difficult environment to perform the electron beam lithography.

Future work may also involve exploration into the optical forces that arise with the chiral phenomena, named optical rectification. Transverse Lorentz forces arise when light is illuminated on the metasurface [Proscia et al. (2016)] that are realised as a transverse voltage which are theoretically measurable on this metasurface. Moreover due to the non-centrosymmetric pattern that the rod-shaped nanoapertures exhibit when tilted at angles such as that studied here,  $\theta_s = 22.5^\circ$ , the transverse voltages should exist even at normal incidence. These measurements typically require intense pulsed laser fields ( $>1\text{MW/cm}^2$ ) and sensitive voltage measurement instruments.

Preliminary work was performed in the area of chiral responses and transverse voltages

from other shapes, namely semi-circles or D-shapes. These shapes differ from the rectangular, rod-shapes studied here in that the fundamental shape is non-centrosymmetrical, the shape can only be superimposed in rotation of  $n \times 2\pi$  radians, where  $n$  is an integer. The rod-shapes however are identical when rotated by  $n \times \pi$  radians. Arrays of both shapes, when placed in an array cannot be titled at an angle  $m \times \pi/4$  radians, where  $m$  is integers including 0, otherwise symmetry is not broken. If the shapes are tilted prescribed by the condition above chiral phenomena occurs at normal incidence. The phenomena is much weaker in magnitude at normal incidence than structures optimized for oblique incidence but serves a much more general method to achieve chiral phenomena in metasurfaces.

# Chapter 6

## Summary and Outlook

### 6.1 What has been done

The work carried out as part of this thesis has discussed many aspects on the optical properties and manipulation of metallic nanoparticles. The light-matter interactions studied here range from the magneto optical effects that can be exhibited in non ferromagnetic nanoparticles to the spatial encoding of information via fractal architectures, and ultimately contribute to the next generation of metamaterials and metasurfaces. To reveal the full potential of optical manipulation devices such as metasurfaces they will have to manufactured at large scale using bottom-up techniques. While top-down techniques, such as electron-beam lithography, offer excellent nanometer precision of the arrangement of individual features, typically only small areas can be patterned at a time ( $<1\text{cm}^2$ ), and suffer from limitations such as the need for expensive machines and fabrication time is long. The work in this thesis looks at the optically generated forces that make bottom-up self-assembly of metasurfaces and metamaterials possible in the future. Also studied in this thesis are applications to metasurfaces that include increased and robust data transmission rates, as well as a demonstration of their versatility via the fabrication of a chiral metasurface by the arrangement of nonchiral sub

structures.

The light-matter interactions studied here are derived from plasmonic excitations that occur when light is incident on metallic nanoparticles. Plasmonic interactions are popular for a variety of factors including high local field confinement, and therefore enhancement [Novotny and van Hulst (2011); Kaurranen and Zayats (2012)]. Popularity of plasmonic materials also stems from their sensitivity to the optical properties the metal and dielectric materials that compose the interface of which plasmons are created [Homola (2008)]. Further exploration into exploiting these features of plasmonic have been studied here.

In chapter 2 magneto-optical effects are observed in gold nanoparticles. Specifically gold nanoparticles are illuminated by circularly-polarized light that generates plasmon-assisted solenoidal currents to flow on the surface of the nanoparticles. According to Faraday's law it is these solenoidal currents that form the basis of magnetization of the nanoparticles, whose effects are observed experimentally via extinction spectra.

In chapter 3 the Lorentz force is investigated when nanowires are illuminated with plane waves at oblique incidences. The plasmonic modes that are excited on the nanowire induce forces and torques that explain the rocking and spinning motion that other experimental scientists have observed.

Chapter 4 shows that information is encoded robustly when designed and transmitted with fractal architecture. Self-similar transmission profiles are less sensitive to intermediate-obstacle signal blocks and are regenerated easily without distortion of the original image. Applications of this work may be relevant to any large-scale data transmission platforms.

In chapter 5 chirality is shown in a metasurface composed of non-chiral sub structures, namely rod-shaped apertures. The chirality is present due to interactions between neighboring substructures that is derived from the Liénard-Wiechert potential, and is observed experimentally in the polarization through the metasurface. The polarization exhibits optical rotation and circular dichroism at normal incidence—the signature of chiral phenomena.

Developing chiral media is important for applications where either accurate control over the polarization is desired or for the development of a new generation of polarization detectors [Mueller et al. (2016)].

## 6.2 What is left to do

One of the limitations listed of nanofabrication is the necessity for extremely expensive machines that make research inaccessible to many. One of the future goals of the research studied in this thesis is to develop new methods to self-assemble structures at the nanoscale. Understanding how Lorentz forces are generated at the nanoscale is unintuitive, yet fundamental to fabricating consistent, uniform nanostructures at scale. Further explorations into this topic may look into further methods to validate the magnitudes, directions, and locations of Lorentz forces when light is applied to nanostructures.

Challenges in the experimental verification occur in a number of ways, from the optical trapping of nanostructures, to confinement of light at the orders similar to the wavelength. Regardless the highly diverse nature of plasmonics presents an exciting future, where, for example, the development of ultrafast computing, active plasmonic devices or biochemical applications.

Control over the polarization has been explored here through the use of a chiral meta-surface. It is a goal of scientists to probe the nature of materials via various optical characterization methods. This work began by simply observing the scattering and absorption properties [Mie (1908)], this method later gave rise to spectrophotometry. Optical characterization techniques since grown to include methods such as Fourier transform infra-red spectroscopy [Andrew Chan and Kazarian (2016)], ellipsometry [Theeten et al. (1981)] and surface enhanced raman spectroscopy [Wang and Kong (2015)]. To this end it is the goal of scientists to develop materials that are able to efficiently modify the polarization fields of

light to probe a materials properties such as the structure or composition. Metasurfaces are one way of achieving efficient polarization control, they modify the polarization over length scales that are less than the wavelength. For comparison, traditional polarization optics need length scales around 3 orders of magnitude greater than the wavelength, such as polarizers, and quarter wave-plates, making metasurfaces very attractive in this regard.

One area of improvement that can be made in the development of future metasurfaces is reconfigurability. Similar to how a spatial light modulator is able to manipulate the phase, the same can be achieved with metasurfaces. The work presented as part of this thesis lays out methods to optically manipulate either metallic nanoparticles (chapters 2,3) or to manipulate the polarization (chapter 5), from metallic nanostructures reminiscent of nanoparticles easily available (gold nanorods). It is conceivable that future applications of the work studied here may combine the two, optically arranging metallic nanoparticles on a large scale using Lorentz forces derived from the plasmonic interaction, into some configuration, for example exhibiting a linear phase gradient [Aieta et al. (2012)], or even the fractal geometries explored in chapter 3. The metasurface could demonstrate its function, manipulating the polarization of light. Following, the metasurface may be reconfigured for another purpose or function. Challenges in this area will involve uniform fabrication—any irregularities may give rise to structural correlations that lead to unwanted effects, or nonlocal effects at the nanoscale. Challenges may also be faced in having to overcome any optical losses associated with metallic nanoparticles, where dielectric materials may be more desirable. Work in this area may fall under the category of aperiodic metamaterial research.

The ability to self-assemble metasurfaces is highly attractive and has the potential to usher an era of large-scale manufacturing of materials to probe the fundamentals properties of materials. Metallic nanoparticles can act as the building blocks of metasurfaces, not only can their size, shape, composition can be modified to produce the desired optical properties, but their spatial arrangement can lead to more complicated and precise control over light,

from intensity to polarization, as has been touched upon in this thesis.

# Previously Published Materials

The content of this dissertation is based substantially on material previously published by Matthew Moocarme and colleagues. This includes in particular the list of journal articles below.

Moocarme, M., Dominguez-Juarez, J. L., and Vuong, L. T. (2014b). Ultralow-Intensity Magneto-Optical and Mechanical Effects in Metal Nanocolloids. *Nano Letters*, 14(3):1178–1183

Moocarme, M., Kusin, B., and Vuong, L. T. (2014c). Plasmon-induced lorentz forces of nanowire chiral hybrid modes. *Optical Materials Express*, 4(11):2355–2367

Moocarme, M. and Vuong, L. T. (2015). Robustness and spatial multiplexing via diffractal architectures. *Optics Express*, 23(22):28471–28478

Moocarme, M., Proscia, N., and Vuong, L. T. (2016). Meta-optical chirality and emergent eigen-polarization modes via plasmon interactions. *Scientific Reports*, Accepted

# Bibliography

- (2010). Layout BEAMER Advanced Features. [https://www.nanolithography.gatech.edu/training/Layout\\_BEAMER\\_Advanced\\_Features.pdf](https://www.nanolithography.gatech.edu/training/Layout_BEAMER_Advanced_Features.pdf).
- Aieta, F., Genevet, P., Yu, N., Kats, M. A., Gaburro, Z., and Capasso, F. (2012). Out-of-Plane Reflection and Refraction of Light by Anisotropic Optical Antenna Metasurfaces with Phase Discontinuities. *Nano Letters*, 12(3):1702–1706.
- Allouche, J. and Shallit (2003). *Automatic Sequence: Theory, Applications, Generalizations*. Cambridge University Press.
- Alù, A., Silveirinha, M. G., Salandrino, A., and Engheta, N. (2007). Epsilon-near-zero metamaterials and electromagnetic sources: Tailoring the radiation phase pattern. *Phys. Rev. B*, 75:155410.
- Andrew Chan, K. L. and Kazarian, S. G. (2016). Attenuated total reflection fourier-transform infrared (atr-ftir) imaging of tissues and live cells. *Chem. Soc. Rev.*, 45:1850–1864.
- Arcenegui, J. J., Garcia-Sanchez, P., Morgan, H., and Ramos, A. (2013). Electro-orientation and electrorotation of metal nanowires. *Physical Review E*, 88:063018.
- Armelles, G., Cebollada, A., Garcia-martin, A., and Gonzalez, M. (2013). Magnetoplasmonics: combining magnetic and plasmonic functionalities. *Advanced Optical Materials*, 1:10–35.
- Ashkin, A. (1997). Optical trapping and manipulation of neutral particles using lasers. *Proceedings of the National Academy of Sciences*, 94(10):4853–4860.
- Ashkin, A. (2001). *History of Optical Trapping and Manipulation of Small Neutral Particles, Atoms, and Molecules*, pages 1–31. Springer Berlin Heidelberg, Berlin, Heidelberg.
- Atwater, H. (2007). The promise of plasmonics. *Scientific American*, 296(4):56.
- Barnes, W. and Aguie, B. (2009). Diffractive coupling in gold nanoparticle arrays and the effect of disorder. *Optics Letters*, 34:401–403.
- Barnes, W., Dereux, A., and Ebbesen, T. (2003). Surface plasmon subwavelength optics. *Nature*, 424:824–830.

- Barrera, J. F., Tebaldi, M., Amaya, D., Furlan, W. D., Monsoriu, J. A., Bolognini, N., and Torroba, R. (2012). Multiplexing of encrypted data using fractal masks. *Optics Letters*, 37(14):2895–2897.
- Barron, L. D. (2009). *Molecular Light Scattering and Optical Activity*. Cambridge University Press, New York, NY, USA, 2nd edition.
- Bashevoy, M., Fedotov, V., and Zheludev, N. (2005). Optical whirlpool on an absorbing metallic nanoparticle. *Optics Express*, 13(21):8372–8379.
- Belotelov, V. I., Akimov, I. A., Pohl, M., Kotov, V. A., Kasture, S., Vengurlekar, A. S., Gopal, A. V., Yakovlev, D. R., Zvezdin, A. K., and Bayer, M. (2011). Enhanced magneto-optical effects in magnetoplasmonic crystals. *Nature Nanotechnology*, 6(6):370–376.
- Berry, M. (1979). Diffractals. *Journal of Phys A - Mathematical and General*, 12(6):781–797.
- Beth, R. A. (1936). Mechanical detection and measurement of the angular momentum of light. *Physical Review*, 50:115–125.
- Bliokh, K. Y., Ostrovskaya, E. A., Alonso, M. A., Rodríguez-Herrera, O. G., Lara, D., and Dainty, C. (2011). Spin-to-orbital angular momentum conversion in focusing, scattering, and imaging systems. *Optics Express*, 19(27):26132–26149.
- Bojko, R. (2013). ZEP-520A Process Information. <https://ebeam.mff.uw.edu/ebeamweb/process/process/zep520a.html>.
- Bonin, K., Kourmanov, B., and Walker, T. (2002). Light torque nanocontrol, nanomotors and nanorockers. *Optics Express*, 10(19):984–989.
- Boriskina, S. V. and Reinhard, B. M. (2012). Molding the flow of light on the nanoscale: from vortex nanogears to phase-operated plasmonic machinery. *Nanoscale*, 4:76–90.
- Boyd, R. W. (2008). *Nonlinear Optics*. Academic Press, Burlington, third edition.
- Brandao, P. A. and Cavalcanti, S. B. (2013). Optical spin-to-orbital plasmonic angular momentum conversion in subwavelength apertures. *Optics Letters*, 38(6):920–922.
- Canfield, B. K., Husu, H., Laukkanen, J., Bai, B., Kuittinen, M., Turunen, J., and Kauranen, M. (2007). Local field asymmetry drives second-harmonic generation in noncentrosymmetric nanodimers. *Nano Letters*, 7(5):1251–1255.
- Cao, T. and Cryan, M. J. (2012). Enhancement of circular dichroism by a planar non-chiral magnetic metamaterial. *Journal of Optics*, 14(8).
- Cao, T., Wei, C., and Mao, L. (2015a). Numerical study of achiral phase-change meta-materials for ultrafast tuning of giant circular conversion dichroism. *Scientific Reports*, 5.

- Cao, T., Wei, C.-W., Mao, L.-B., and Wang, S. (2015b). Tuning of giant 2D-chiroptical response using achiral metasurface integrated with graphene. *Optics Express*, 23(14):18620–18629.
- Cao, T., Zhang, L., Simpson, R. E., Wei, C., and Cryan, M. J. (2013). Strongly tunable circular dichroism in gammadion chiral phase-change metamaterials. *Optics Express*, 21(23):27841–27851.
- Chang, D. E., Sørensen, A. S., Hemmer, P. R., and Lukin, M. D. (2007). Strong coupling of single emitters to surface plasmons. *Physical Review B*, 76:035420.
- Chaumet, P. and Nieto-Vesperinas, M. (2000). Time-averaged total force on a dipolar sphere in an electromagnetic field. *Optics Letters*, 25(15):1065–1067.
- Chowdhury, A., Ackerson, B., and Clark, N. (1985). Laser-induced freezing. *Physical Review Letters*, 55(8):833–836.
- Chyou, J., Chu, C., Shih, Z., Lin, C., Chen, S., and Shu, F. (2005). Fabrication and metrology of an electro-optic polymer light modulator based on waveguide-coupled surface plasmon resonance. *Optical Engineering*, 44(3):034001–034001–7.
- Cortie, M. and Ford, M. (2007). A plasmon-induced current loop in gold semi-shells. *Nanotechnology*, 18(23):235704.
- Decker, M., Zhao, R., Soukoulis, C. M., Linden, S., and Wegener, M. (2010). Twisted split-ring-resonator photonic metamaterial with huge optical activity. *Optics Letters*, 35(10):1593–1595.
- Deshko, Y., Krusin-Elbaum, L., Menon, V., Khanikaev, A., and Trevino, J. (2016). Surface plasmon polaritons in topological insulator nano-films and superlattices. *Optics Express*, 24(7):7398–7410.
- Dicken, M. J., Sweatlock, L. A., Pacifici, D., Lezec, H. J., Bhattacharya, K., and Atwater, H. A. (2008). Electrooptic modulation in thin film barium titanate plasmonic interferometers. *Nano Letters*, 8(11):4048–4052.
- Dienerowitz, M., Mazilu, M., and Dholakia, K. (2008). Optical manipulation of nanoparticles: a review. *Journal of Nanophotonics*, 2(1):021875–021908.
- Ding, F., Wang, Z., He, S., Shalaev, V. M., and Kildishev, A. V. (2015). Broadband high-efficiency half-wave plate: A supercell-based plasmonic metasurface approach. *ACS Nano*, 9(4):4111–4119. PMID: 25790895.
- Ditlbacher, H., Hohenau, A., Wagner, D., Kreibig, U., Rogers, M., Hofer, F., Ausseneegg, F. R., and Krenn, J. R. (2005). Silver nanowires as surface plasmon resonators. *Physical Review Letters*, 95:257403.

- Dolling, G., Wegener, M., Soukoulis, C. M., and Linden, S. (2007). Negative-index metamaterial at 780 nm wavelength. *Optics Letters*, 32(1):53–55.
- Drake, J. and Genack, A. (1989). Observation of Nonclassical Optical Diffusion. *Physical Review Letters*, 63(3):259–262.
- Du, G.-X., Saito, S., and Takahashi, M. (2011). Magnetic field effect on the localized plasmon resonance in patterned noble metal nanostructures. *IEEE Transactions on Magnetics*, 47(10):3167–3169.
- Duarte, M. F., Davenport, M. A., Wakin, M. B., Laska, J. N., Takhar, D., Kelly, K. F., and Baraniuk, R. G. (2007). Multiscale random projections for compressive classification. In *Image Processing, 2007. ICIP 2007. IEEE International Conference on*, volume 6, pages VI – 161–VI – 164.
- Edwards, B., Mayer, T. S., and Bhiladvala, R. B. (2006). Synchronous electrorotation of nanowires in fluid. *Nano letters*, 6(4):626–632.
- Eftekhari, F. and Davis, T. J. (2012). Strong chiral optical response from planar arrays of subwavelength metallic structures supporting surface plasmon resonances. *Physical Review B*, 86(7).
- Fan, J. A., Wu, C., Bao, K., Bao, J., Bardhan, R., Halas, N. J., Manoharan, V. N., Nordlander, P., Shvets, G., and Capasso, F. (2010). Self-assembled plasmonic nanoparticle clusters. *Science*, 328(5982):1135–1138.
- Fan, Z. and Govorov, A. O. (2010). Plasmonic circular dichroism of chiral metal nanoparticle assemblies. *Nano Letters*, 10(7):2580–2587. PMID: 20536209.
- Fang, Z., Zhen, Y.-R., Neumann, O., Polman, A., Garca de Abajo, F. J., Nordlander, P., and Halas, N. J. (2013). Evolution of light-induced vapor generation at a liquid-immersed metallic nanoparticle. *Nano Letters*, 13(4):1736–1742. PMID: 23517407.
- Funston, A. M., Novo, C., Davis, T. J., and Mulvaney, P. (2009). Plasmon coupling of gold nanorods at short distances and in different geometries. *Nano Letters*, 9(4):1651–1658.
- Gevorgyan, A. H. and Rafayelyan, M. S. (2013). Optics of anisotropic metamaterial based structurally chiral photonic crystals. *Journal of Optics*, 15(12):125103.
- Gonzalez-Diaz, J. B., Garcia-Martin, J. M., Garcia-Martin, A., Navas, D., Asenjo, A., Vazquez, M., Hernandez-Velez, M., and Armelles, G. (2009). Plasmon-enhanced magneto-optical activity in ferromagnetic membranes. *Applied Physics Letters*, 94(26).
- Goodman, J. W. (2005). *Introduction to Fourier optics*. Roberts and Co.
- Gordon, J. (1973). Radiation forces and momenta in dielectric media. *Physical Review A*, 8:14–21.

- Gu, Y. and Kornev, K. G. (2010). Plasmon enhanced direct and inverse faraday effects in non-magnetic nanocomposites. *Journal of the Optical Society of America B*, 27(11):2165–2173.
- Guerrero-Martinez, A., Lorenzo Alonso-Gomez, J., Auguie, B., Magdalena Cid, M., and Liz-Marzan, L. M. (2011). From individual to collective chirality in metal nanoparticles. *Nano Today*, 6(4):381–400.
- Hai-Dong, D., Jin, L., Wei-Ren, Z., Wei, Z., Xu-Sheng, L., Ting, S., Qiao-Feng, D., Li-Jun, W., Sheng, L., and Gopal, A. V. (2008). Enhancement of switching speed by laser-induced clustering of nanoparticles in magnetic fluids. *Applied Physics Letters*, 92(23):233103.
- Hasman, E., Biener, G., Niv, A., and V., K. (2005). Space-variant polarization manipulation. *Progress in Optics*, 47:215–289.
- Haus, H. (2014). *Waves and Fields in Optoelectronics*. Prentice Hall.
- Hecht, B., Bielefeldt, H., Novotny, L., Inouye, Y., and Pohl, D. (1996). Local excitation, scattering, and interference of surface plasmons. *Physical Review Letters*, 77:1889–1892.
- Hentschel, M., Schaeferling, M., Weiss, T., Liu, N., and Giessen, H. (2012). Three-Dimensional Chiral Plasmonic Oligomers. *Nano Letters*, 12(5):2542–2547.
- Hertel, R. (2006). Theory of the inverse faraday effect in metals. *Journal of Magnetism and Magnetic Materials*, 303(1):L1–L4.
- Homola, J. (2008). Surface plasmon resonance sensors for detection of chemical and biological species. *Chemical Reviews*, 108(2):462–493. PMID: 18229953.
- Horvath, P., Smid, P., Vaskova, I., and Hrabovsky, M. (2010). Koch fractals in physical optics and their Fraunhofer diffraction patterns. *Optik*, 121(2):206–213.
- Hou, B., Xu, G., Wen, W., and Wong, G. (2004). Diffraction by an optical fractal grating. *Applied Physics Letters*, 85(25):6125–6127.
- Howland, G. A. and Howell, J. C. (2013). Efficient High-Dimensional Entanglement Imaging with a Compressive-Sensing Double-Pixel Camera. *Physical Review X*, 3(1).
- Hugel, T., Holland, N., Cattani, A., Moroder, L., Seitz, M., and Gaub, H. (2002). Single-molecule optomechanical cycle. *Science*, 296(5570):1103–1106.
- Jackson, J. D. (1999). *Classical electrodynamics*. Wiley, New York, NY, 3rd ed. edition.
- Jacquin, A. (1993). Fractal Image-Coding - A Review. *Proceedings of the IEEE*, 81(10):1451–1465.

- Jain, P. K., Eustis, S., and El-Sayed, M. A. (2006). Plasmon coupling in nanorod assemblies: optical absorption, discrete dipole approximation simulation, and exciton-coupling model. *Journal of Physical Chemistry B*, 110(37):18243–18253.
- Janhunen, P. and Sandroos, A. (2007). Simulation study of solar wind push on a charged wire: basis of solar wind electric sail propulsion. *Annales Geophysicae*, 25(3):755–767.
- Kauranen, M. and Zayats, A. V. (2012). Nonlinear plasmonics. *Nature Photonics*, 6(11):737–748.
- Kauranen, M. and Zayats, A. V. (2012). Nonlinear Plasmonics. *Nature Photonics*, 6:737–748.
- Kelly, K., Coronado, E., Zhao, L., and Schatz, G. (2003). The optical properties of metal nanoparticles: The influence of size, shape, and dielectric environment. *Journal of Physical Chemistry B*, 107(3):68–677.
- Keshoju, K., Xing, H., and Sun, L. (2007). Magnetic field driven nanowire rotation in suspension. *Applied Physics Letters*, 91(12):123114.
- Khanikaev, A. B., Arju, N., Fan, Z., Purtseladze, D., Lu, F., Lee, J., Sarriugarte, P., Schnell, M., Hillenbrand, R., Belkin, M. A., and Shvets, G. (2016). Experimental demonstration of the microscopic origin of circular dichroism in two-dimensional metamaterials. *Nature Communications*, 7.
- Khorasaninejad, M., Chen, W. T., Devlin, R. C., Oh, J., Zhu, A. Y., and Capasso, F. (2016a). Metalenses at visible wavelengths: Diffraction-limited focusing and subwavelength resolution imaging. *Science*, 352(6290):1190–1194.
- Khorasaninejad, M., Chen, W. T., Zhu, A. Y., Oh, J., Devlin, R. C., Rousso, D., and Capasso, F. (2016b). Multispectral chiral imaging with a metalens. *Nano Letters*, 16(7):4595–4600. PMID: 27267137.
- Kippenberg, T. J. and Vahala, K. J. (2007). Cavity opto-mechanics. *Optics Express*, 15(25):17172–17205.
- Knight, M. W., Grady, N. K., Bardhan, R., Hao, F., Nordlander, P., and Halas, N. J. (2007). Nanoparticle-mediated coupling of light into a nanowire. *Nano Letters*, 7(8):2346–2350. PMID: 17629348.
- Kretschmann, E. and Raether, H. (1968). Radiative decay of nonradiative surface plasmons excited by light. *Z. Naturforsch. A*, 23:2135.
- Kumar, A., Boruah, B. M., and Liang, X.-J. (2011). Gold nanoparticles: Promising nano-materials for the diagnosis of cancer and hiv/aids. *Journal of Nanomaterials*, 2011:22:22–22:22.

- Kuo, S. C. (2001). Using optics to measure biological forces and mechanics. *Traffic*, 11(2):757–763.
- Kuznetsov, A. I., Miroshnichenko, A. E., Fu, Y. H., Zhang, J., and Luk'yanchuk, B. (2012). Magnetic light. *Scientific Reports*, 2.
- Kuzyk, A., Schreiber, R., Fan, Z., Pardatscher, G., Roller, E.-M., Hoegele, A., Simmel, F. C., Govorov, A. O., and Liedl, T. (2012). DNA-based self-assembly of chiral plasmonic nanostructures with tailored optical response. *Nature*, 483(7389):311–314.
- Kwon, D.-H., Werner, P. L., and Werner, D. H. (2008). Optical planar chiral metamaterial designs for strong circular dichroism and polarization rotation. *Optics Express*, 16(16):11802–11807.
- Lal, S., Link, S., and Halas, N. J. (2007). Nano-optics from sensing to waveguiding. *Nature Photonics*, 1(11):641–648.
- Landau, L. and Lifshitz, E. (1960). *Electrodynamics of Continuous Media*. Pergamon Press.
- Lang, M. J. and Block, S. M. (2003). Resource letter: Lbot-1: Laser-based optical tweezers. *American Journal of Physics*, 71(3):201–215.
- Lee, M. P. and Padgett, M. J. (2012). Optical tweezers: a light touch. *Journal of Microscopy*, 248(3):219–222.
- Lee, S. and Park, Q.-H. (2016). Dynamic coupling of plasmonic resonators. *Scientific Reports*, 6.
- Lehmuskero, A., Li, Y., Johansson, P., and Käll, M. (2014). Plasmonic particles set into fast orbital motion by an optical vortex beam. *Optics Express*, 22(4):4349–4356.
- Lehmuskero, A., Ogier, R., Gschneidtner, T., Johansson, P., and Kll, M. (2013). Ultrafast spinning of gold nanoparticles in water using circularly polarized light. *Nano Letters*, 13(7):3129–3134.
- Liaw, J.-W., Lo, W.-J., and Kuo, M.-K. (2014). Wavelength-dependent longitudinal polarizability of gold nanorod on optical torques. *Optics Express*, 22(9):10858–10867.
- Link, S. and El-Sayed, M. (1999). Spectral properties and relaxation dynamics of surface plasmon electronic oscillations in gold and silver nanodots and nanorods. *Journal of Physical Chemistry B*, 103(40):8410–8426.
- Link, S. and El-Sayed, M. (2000). Shape and size dependence of radiative, non-radiative and photothermal properties of gold nanocrystals. *International Review of Physical Chemistry*, 19(3):409–453.

- Macke, A., Mueller, J., and Raschke, E. (1996). Single scattering properties of atmospheric ice crystals. *Journal of the Atmospheric Sciences*, 53(19):2813–2825.
- Maier, S. (2007a). *Plasmonics: Fundamentals and Applications*. Springer.
- Maier, S. A. (2007b). *Plasmonics: Fundamentals and Applications*. Springer, first edition.
- Maier, S. A. and Atwater, H. A. (2005). Plasmonics: Localization and guiding of electromagnetic energy in metal/dielectric structures. *Journal of Applied Physics*, 98(1):9.
- Mandlebrot, B. (1982). *The Fractal Geometry of Nature*. Freeman, New York.
- Metzger, B., Hentschel, M., Lippitz, M., and Giessen, H. (2012). Third-harmonic spectroscopy and modeling of the nonlinear response of plasmonic nanoantennas. *Optics Letters*, 37(22):4741–4743.
- Metzger, B., Hentschel, M., Nesterov, M., Schumacher, T., Lippitz, M., and Giessen, H. (2016). Nonlinear optics of complex plasmonic structures: linear and third-order optical response of orthogonally coupled metallic nanoantennas. *Applied Physics B- Lasers and Optics*, 122(4).
- Mie, G. (1908). Beitrge zur optik trber medien, speziell kolloidaler metallsungen. *Annalen der Physik*, 25:377.
- Moocarme, M. (2015a). Sierpinski carpet generator. <https://github.com/moocarme/Diffractions/blob/master/Sierpinski.m>.
- Moocarme, M. (2015b). Sierpinski carpet reconstruction algorithm. <https://github.com/moocarme/Diffractions/blob/master/reconFun.m>.
- Moocarme, M., Dominguez-Juarez, J. L., and Vuong, L. T. (2014a). Ultralow-intensity magneto-optical and mechanical effects in metal nanocolloids. *Nano Letters*, 14(3):1178–1183.
- Moocarme, M., Dominguez-Juarez, J. L., and Vuong, L. T. (2014b). Ultralow-Intensity Magneto-Optical and Mechanical Effects in Metal Nanocolloids. *Nano Letters*, 14(3):1178–1183.
- Moocarme, M., Kusin, B., and Vuong, L. T. (2014c). Plasmon-induced lorentz forces of nanowire chiral hybrid modes. *Optical Materials Express*, 4(11):2355–2367.
- Moocarme, M., Proscia, N., and Vuong, L. T. (2016). Meta-optical chirality and emergent eigen-polarization modes via plasmon interactions. *Scientific Reports*, Accepted.
- Moocarme, M. and Vuong, L. T. (2015). Robustness and spatial multiplexing via diffractal architectures. *Optics Express*, 23(22):28471–28478.

- Mueller, J. P. B., Leosson, K., and Capasso, F. (2016). Ultracompact metasurface in-line polarimeter. *Optica*, 3(1):42–47.
- Mulvaney, P. (1996). Surface plasmon spectroscopy of nanosized metal particles. *Langmuir*, 12(3):788–800.
- Ni, X., Ishii, S., Kildishev, A. V., and Shalaev, V. M. (2013). Ultra-thin, planar, Babinet-inverted plasmonic metalenses. *Light: Science & Applications*, 2.
- Nie, S. and Emery, S. (1997). Probing single molecules and single nanoparticles by surface-enhanced Raman scattering. *Science*, 275(5303):1102–1106.
- Nieminen, T. A., Knorer, G., Heckenberg, N. R., and Rubinsztein-Dunlop, H. (2007). Physics of optical tweezers. In Berns, MW and Greulich, KO, editor, *Laser Manipulation of Cells and Tissues*, volume 82 of *Methods in Cell Biology*, pages 207–236. Elsevier Academic Press Inc.
- Nikolajsen, T., Leosson, K., and Bozhevolnyi, S. (2004). Surface plasmon polariton based modulators and switches operating at telecom wavelengths. *Applied Physics Letters*, 85(24):5833–5835.
- Novotny, L., Bian, R. X., and Xie, X. S. (1997). Theory of nanometric optical tweezers. *Physical Review Letters*, 79:645–648.
- Novotny, L. and van Hulst, N. (2011). Antennas for light. *Nature Photonics*, 5:83–90. PMID: 18229953.
- Owen, G. and Rissman, P. (1983). Proximity Effect Correction for Electron-Beam Lithography by Equalization of Background Dose. *Journal of Applied Physics*, 54(6):3573–3581.
- Ozbay, E. (2006). Plasmonics: Merging photonics and electronics at nanoscale dimensions. *Science*, 311(5758):189–193.
- Padilla, W. J., Basov, D. N., and Smith, D. R. (2006). Negative refractive index metamaterials. *Materials Today*, 9(78):28 – 35.
- Park, J., Kang, J.-H., Liu, X., and Brongersma, M. L. (2015). Electrically tunable epsilon-near-zero (en<sub>z</sub>) metafilm absorbers. *Sci. Rep.*, 5:15754.
- Paterson, L., MacDonald, M., Arlt, J., Sibbett, W., Bryant, P., and Dholakia, K. (2001). Controlled rotation of optically trapped microscopic particles. *Science*, 292(5518):912–914.
- Petrich, W., Grieser, M., Grimm, R., Gruber, A., Habs, D., Miesner, H., Schwalm, D., Wanner, B., Wernoe, H., Wolf, A., Grieser, R., Huner, G., Klein, R., Kuhl, T., Neumann, R., and Schroder, S. (1993). Laser cooling of stored high-velocity ions by means of the spontaneous force. *Physical Review A*, 48(3):2127–2144.

- Pineider, F., Campo, G., Bonanni, V., Fernandez, C. d. J., Mattei, G., Caneschi, A., Gatteschi, D., and Sangregorio, C. (2013). Circular magnetoplasmonic modes in gold nanoparticles. *Nano Letters*, 13(10):4785–4789.
- Plum, E., Fedotov, V. A., and Zheludev, N. I. (2011). Asymmetric transmission: a generic property of two-dimensional periodic patterns. *Journal of Optics*, 13(2):024006.
- Plum, E., Fedotov, V. A., and Zheludev, N. I. (2016). Specular optical activity of achiral metasurfaces. *Applied Physics Letters*, 108(14).
- Prodan, E., Radloff, C., Halas, N., and Nordlander, P. (2003). A hybridization model for the plasmon response of complex nanostructures. *Science*, 302(5644):419–422.
- Proscia, N. V., Moocarme, M., Chang, R., Kretzschmar, I., Menon, V. M., and Vuong, L. T. (2016). Control of photo-induced voltages in plasmonic crystals via spin-orbit interactions. *Optics Express*, 24(10).
- Prosvirnin, S. L. and Zheludev, N. I. (2005). Polarization effects in the diffraction of light by a planar chiral structure. *Physical Review E*, 71:037603.
- Puente-Baliarda, C., Romeu, J., Pous, R., and Cardama, A. (1998). On the behavior of the Sierpinski multiband fractal antenna. *IEEE Transactions on Antennas and Propagation*, 46(4):517–524.
- Qin, F., Ding, L., Zhang, L., Monticone, F., Chum, C. C., Deng, J., Mei, S., Li, Y., Teng, J., Hong, M., Zhang, S., Alù, A., and Qiu, C.-W. (2016). Hybrid bilayer plasmonic metasurface efficiently manipulates visible light. *Science Advances*, 2(1).
- Radonic, V., Palmer, K., Stojanovic, G., and Crnojevic-Bengin, V. (2012). Flexible Sierpinski Carpet Fractal Antenna on a Hilbert Slot Patterned Ground. *International Journal of Antennas and Propagation*.
- Raja, M., Allen, D., and Sisk, W. (1995). Room-temperature inverse faraday effect in terbium gallium garnet. *Applied Physics Letters*, 67(15):2123–2125.
- Rakic, A., Djurisic, A., Elazar, J., and Majewski, M. (1998). Optical properties of metallic films for vertical-cavity optoelectronic devices. *Applied Optics*, 37(22):5271–5283.
- Ritchie, R., Arakawa, E., Cowan, J., and Hamm, R. (1968). Surface-plasmon resonance effect in grating diffraction. *Physical Review Letters*, 21:1530–1533.
- Ruffner, D. B. and Grier, D. G. (2012). Optical conveyors: A class of active tractor beams. *Physical Review Letters*, 109:163903.
- Saija, R., Denti, P., Borghese, F., Maragò, O. M., and Iatì, M. A. (2009). Optical trapping calculations for metal nanoparticles. Comparison with experimental data for Au and Ag spheres. *Optics Express*, 17(12):10231–10241.

- Sambles, J. R., Bradbery, G. W., and Yang, F. (1991). Optical excitation of surface plasmons: An introduction. *Contemporary Physics*, 32(3):173–183.
- Savitzky, A. and Golay, M. J. E. (1964). Smoothing and differentiation of data by simplified least squares procedures. *Analytical Chemistry*, 36(8):1627–1639.
- Schmitt, J. M. and Kumar, G. (1998). Optical scattering properties of soft tissue: a discrete particle model. *Applied Optics*, 37(13):2788–2797.
- Schnatterly, S. E. (1969). Magnetoreflection measurements on the noble metals. *Physical Review*, 183:664–667.
- Segev, M., Soljacic, M., and Dudley, J. M. (2012). Fractal optics and beyond. *Nature Photonics*, 6(4):209–210.
- Sepulveda, B., Gonzalez-Diaz, J. B., Garcia-Martin, A., Lechuga, L. M., and Armelles, G. (2010). Plasmon-induced magneto-optical activity in nanosized gold disks. *Physical Review Letters*, 104(14):147401.
- Shaltout, A., Liu, J., Shalaev, V. M., and Kildishev, A. V. (2014). Optically Active Metasurface with Non-Chiral Plasmonic Nanoantennas. *Nano Letters*, 14(8):4426–4431.
- Shelby, R. A., Smith, D. R., Nemat-Nasser, S. C., and Schultz, S. (2001). Microwave transmission through a two-dimensional, isotropic, left-handed metamaterial. *Applied Physics Letters*, 78(4):489–491.
- Shelton, W., Bonin, K., and Walker, T. (2005). Nonlinear motion of optically torqued nanorods. *Physical Review E*, 71(3):036204.
- Shen, Y. R. (1984). *The Principles of Nonlinear Optics*. Wiley.
- Shvedov, V. G., Rode, A. V., Izdebskaya, Y. V., Desyatnikov, A. S., Krolikowski, W., and Kivshar, Y. S. (2010). Giant optical manipulation. *Physical Review Letters*, 105:118103–118107.
- Singh, N. D., Moocarme, M., Edelstein, B., Punnoose, N., and Vuong, L. T. (2012). Anomalously-large photo-induced magnetic response of metallic nanocolloids in aqueous solution using a solar simulator. *Optics Express*, 20(17):19214–19225.
- Slepyan, G. Y., Shuba, M. V., Maksimenko, S. A., and Lakhtakia, A. (2006). Theory of optical scattering by achiral carbon nanotubes and their potential as optical nanoantennas. *Physical Review B*, 73:195416.
- Soljacic, M., Segev, M., and Menyuk, C. (2000). Self-similarity and fractals in soliton-supporting systems. *Physical Review E*, 61(2):R1048–R1051.

- Sorensen, C. M. (2001). Light scattering by fractal aggregates: A review. *Aerosol Science and Technology*, 35(2):648–687.
- Stockman, M. I., Shalaev, V. M., Moskovits, M., Botet, R., and George, T. F. (1992). Enhanced raman scattering by fractal clusters: Scale-invariant theory. *Physical Review B*, 46:2821–2830.
- Strogatz, S. H. (1994). *Nonlinear dynamics and chaos : with applications to physics, biology, chemistry, and engineering*. Studies in nonlinearity. Westview Press, Cambridge (Mass.). Autre(s) tirage(s) : 2000.
- Tang, C. J., Zhan, P., Cao, Z. S., Pan, J., Chen, Z., and Wang, Z. L. (2011). Magnetic field enhancement at optical frequencies through diffraction coupling of magnetic plasmon resonances in metamaterials. *Physical Review B*, 83(4):041402.
- Tang, J., Xiao, Z., Xu, K., Ma, X., Liu, D., and Wang, Z. (2016). Cross polarization conversion based on a new chiral spiral slot structure in thz region. *Optical and Quantum Electronics*, 48(2):1–11.
- Temnov, V. V., Armelles, G., Woggon, U., Guzatov, D., Cebollada, A., Garcia-Martin, A., Garcia-Martin, J.-M., Thomay, T., Leitenstorfer, A., and Bratschitsch, R. (2010). Active magneto-plasmonics in hybrid metal-ferromagnet structures. *Nature Photonics*, 4(2):107–111.
- Theeten, J. B., , and Aspnes, D. E. (1981). Ellipsometry in thin film analysis. *Annual Review of Materials Science*, 11(1):97–122.
- Todorov, Y., Andrews, A. M., Sagnes, I., Colombelli, R., Klang, P., Strasser, G., and Sirtori, C. (2009). Strong Light-Matter Coupling in Subwavelength Metal-Dielectric Microcavities at Terahertz Frequencies. *Physical Review Letters*, 102(18).
- Tong, L., Miljkovic, V. D., and Kall, M. (2010). Alignment, rotation, and spinning of single plasmonic nanoparticles and nanowires using polarization dependent optical forces. *Nano Letters*, 10(1):268–273. PMID: 20030391.
- Torrado, J. F., Gonzalez-Diaz, J. B., Gonzalez, M. U., Garcia-Martin, A., and Armelles, G. (2010). Magneto-optical effects in interacting localized and propagating surface plasmon modes. *Optics Express*, 18(15):15635–15642.
- Tsai, D. P., Kovacs, J., Wang, Z., Moskovits, M., Shalaev, V. M., Suh, J. S., and Botet, R. (1994). Photon scanning tunneling microscopy images of optical excitations of fractal metal colloid clusters. *Physical Review Letters*, 72:4149–4152.
- Tsai, W.-Y., Huang, J.-S., and Huang, C.-B. (2014). Selective trapping or rotation of isotropic dielectric microparticles by optical near field in a plasmonic archimedes spiral. *Nano Letters*, 14(2):547–552.

- Unnikrishnan, G., Joseph, J., and Singh, K. (2000). Optical encryption by double-random phase encoding in the fractional Fourier domain. *Optics Letters*, 25(12):887–889.
- Urbas, A. M., Jacob, Z., Negro, L. D., Engheta, N., Boardman, A. D., Egan, P., Khanikaev, A. B., Menon, V., Ferrera, M., Kinsey, N., DeVault, C., Kim, J., Shalaev, V., Boltasseva, A., Valentine, J., Pfeiffer, C., Grbic, A., Narimanov, E., Zhu, L., Fan, S., Al, A., Poutrina, E., Litchinitser, N. M., Noginov, M. A., MacDonald, K. F., Plum, E., Liu, X., Nealey, P. F., Kagan, C. R., Murray, C. B., Pawlak, D. A., Smolyaninov, I. I., Smolyaninova, V. N., and Chanda, D. (2016). Roadmap on optical metamaterials. *Journal of Optics*, 18(9):093005.
- van de Hulst, H. C. (1958). *Light scattering by small particles*. John Wiley & Sons, Ltd, first edition.
- Van Thourhout, D. and Roels, J. (2010). Optomechanical device actuation through the optical gradient force. *Nature Photonics*, 4(4):211–217.
- Velev, O. D. and Bhatt, K. H. (2006). On-chip micromanipulation and assembly of colloidal particles by electric fields. *Soft Matter*, 2:738–750.
- Verma, R., Banerjee, V., and Senthilkumaran, P. (2012). Redundancy in Cantor Diffractals. *Optics Express*, 20(8):8250–8255.
- Verma, R., Sharma, M. K., Banerjee, V., and Senthilkumaran, P. (2013). Robustness of Cantor Diffractals. *Optics Express*, 21(7):7951–7956.
- Vial, A., Grimault, A., Macias, D., Barchiesi, D., and de la Chapelle, M. (2005). Improved analytical fit of gold dispersion: Application to the modeling of extinction spectra with a finite-difference time-domain method. *Physical Review B*, 71(8).
- Vuong, L. T., Adam, A. J. L., Brok, J. M., Planken, P. C. M., and Urbach, H. P. (2010). Electromagnetic spin-orbit interactions via scattering of subwavelength apertures. *Physical Review Letters*, 104(8):083903.
- Wang, A. X. and Kong, X. (2015). Review of recent progress of plasmonic materials and nano-structures for surface-enhanced raman scattering. *Materials*, 8(6):3024.
- Weiner, J., Bagnato, V., Zilio, S., and Julienne, P. (1999). Experiments and theory in cold and ultracold collisions. *Reviews of Modern Physics*, 71(1):1–85.
- Wu, X., Meng, Y., Wang, L., Tian, J., Dai, S., and Wen, W. (2016). Anisotropic metasurface with near-unity circular polarization conversion. *Applied Physics Letters*, 108(18).
- Yan, Z., Jureller, J. E., Sweet, J., Guffey, M. J., Pelton, M., and Scherer, N. F. (2012a). Three-dimensional optical trapping and manipulation of single silver nanowires. *Nano Letters*, 12(10):5155–5161.

- Yan, Z., Pelton, M., Vigderman, L., Zubarev, E. R., and Scherer, N. F. (2013a). Why single-beam optical tweezers trap gold nanowires in three dimensions. *ACS Nano*, 7(10):8794–8800.
- Yan, Z. and Scherer, N. F. (2013). Optical vortex induced rotation of silver nanowires. *Journal of Physical Chemistry Letters*, 4(17):2937–2942.
- Yan, Z., Shah, R. a., Chado, G., Gray, S. K., Pelton, M., and Scherer, N. F. (2013b). Guiding spatial arrangements of silver nanoparticles by optical binding interactions in shaped light fields. *ACS Nano*, 7(2):1790–1802.
- Yan, Z., Sweet, J., Jureller, J. E., Guffey, M. J., Pelton, M., and Scherer, N. F. (2012b). Controlling the position and orientation of single silver nanowires on a surface using structured optical fields. *ACS Nano*, 6(9):8144–8155.
- Yang, Q., Gu, J., Wang, D., Zhang, X., Tian, Z., Ouyang, C., Singh, R., Han, J., and Zhang, W. (2014). Efficient flat metasurface lens for terahertz imaging. *Optics Express*, 22(21):25931–25939.
- Yang, S., Liu, Z., Xia, X., E, Y., Tang, C., Wang, Y., Li, J., Wang, L., and Gu, C. (2016). Excitation of ultrasharp trapped-mode resonances in mirror-symmetric metamaterials. *Physical Review B*, 93(23).
- Yannopapas, V. (2009). Circular dichroism in planar nonchiral plasmonic metamaterials. *Optics Letters*, 34(5):632–634.
- Yu, N., Genevet, P., Kats, M. A., Aieta, F., Tetienne, J.-P., Capasso, F., and Gaburro, Z. (2011). Light Propagation with Phase Discontinuities: Generalized Laws of Reflection and Refraction. *Science*, 334(6054):333–337.
- Zhang, S., Wei, H., Bao, K., Håkanson, U., Halas, N. J., Nordlander, P., and Xu, H. (2011). Chiral surface plasmon polaritons on metallic nanowires. *Physical Review Letters*, 107:096801.
- Zhang, W., Zhu, W. M., Chia, E. E. M., Shen, Z. X., Cai, H., Gu, Y. D., Ser, W., and Liu, A. Q. (2014). A pseudo-planar metasurface for a polarization rotator. *Optics Express*, 22(9):10446–10454.
- Zhao, Y. and Alu, A. (2011). Manipulating light polarization with ultrathin plasmonic metasurfaces. *Physical Review B*, 84(20).