Henry Commercial Roof Restoration and Repair Solutions – Gold Seal Training

Building Confidence™

© 2022 Henry Company. All rights reserved.

Henry Roof Restoration Services

Agenda:

- Who is Henry Company?
- Roofing Overview and Lifecycle
- Qualifying Your Roof: Is It A Candidate For Restoration?
- The Restoration Process
- Henry® Roof Restoration Systems Solutions
- Henry® Warranty, Product & Technical Support



WATER MANAGEMENT



AIR MANAGEMENT



ENERGY SAVINGS



SUSTAINABILITY

2

Who is Henry Company?

We Have Been Serving Building Owners For More Than 90 Years By Extending The Life Of Commercial Roofs With An Advanced Portfolio Of Liquid Coating Systems. Our Goal Is Simple: **Enabling The Gift Of Time** For Our Customers. Our Dedicated Team Of Experts Is **Invested In Your Success** From Start To Finish And Beyond, Providing The Option For Ongoing Maintenance For The Life Of Your Commercial Roof.

- ✓ World-Class Solutions That Extend The Life Of Commercial Roofs
- ✓ Better Performing, More Energy-efficient Structures That Save Money
- ✓ Tailored Maintenance Plans To Monitor And Correct Issues Before They Become Major Problems
- ✓ Reduces Landfill Waste And Associated Costs



Henry
A CARLISLE COMPANY

Who is Henry Company?


We Have Been Serving Roofing Contractors For More Than 90 Years By Offering An Advanced Portfolio Of Liquid Roof Coating Systems. Our Goal Is Simple: **Enabling The Gift Of Time** For Our Customers. Our Dedicated Team Of Experts Is **Invested In Your Success** On Every Project, Providing The Unsurpassed Service, Support, And Training.

- ✓ A Complete Systems Solution Simplifies Installation And Reduces Time On The Roof
- ✓ Quality Products From A Trusted Brand Offers Your Customers The Assurance Of A Better Performing, More Energy-efficient Structure
- ✓ More Time Working, Less Time Finding Work – We Share Qualified Leads And Promote You As A Valued Member Of Our Vetted Network
- ✓ Industry-leading Continuing Education And Training To Sharpen Skills And Improve Efficiency For Faster Job Turns



Leader in Building Envelope Systems®

1. Air Barriers
2. Flashings & Sealants
3. Below Grade Waterproofing
4. Roof Restoration Coatings
5. Roof Underlayments
6. Roof Flashings
7. Modified Bitumen Roofing
8. Plaza Deck and Vegetative Roofing
9. Paving Preservation
10. OEM Solutions
    - Gypsum Additives
    - Marine Sealants
    - Concrete Joint Sealants

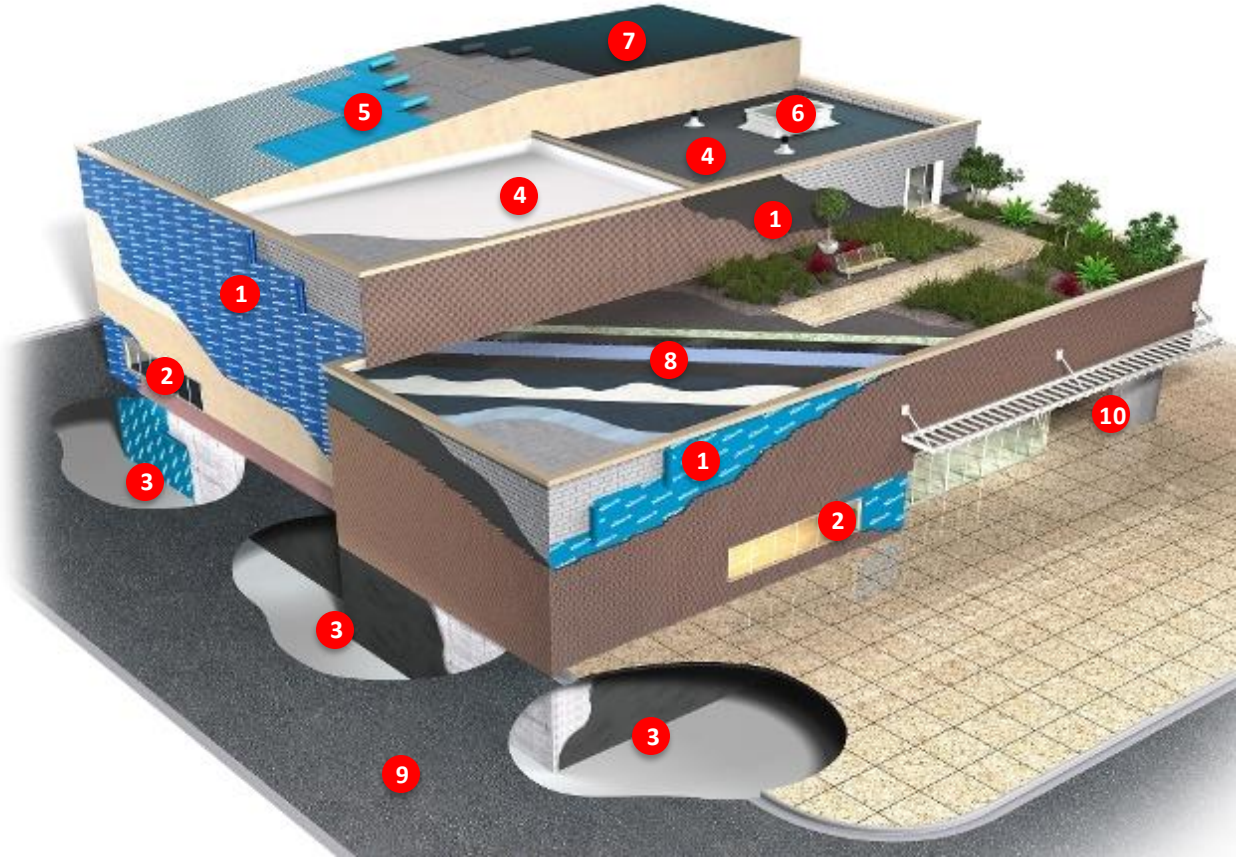

Henry
A CARLISLE COMPANY

5

Timeline – How Did We Get Here



1933
Henry Company Founded

1981
Henry Company Incorporated

2020
Henry Company Acquired National Coatings In October of 2020. Known For Their Robust High Performance Acrylic Systems

2021
Carlisle Companies, Inc. Acquired Henry Company Expanding Their Portfolio And Providing The Most Complete Building Envelope Solution From Below Grade To Roof. CCM Was Split To Form CWT (Carlisle Weatherproofing Technologies)

2023
Consolidation of Henry, Carlise Roof Foam and Coatings and National Coatings Portfolios to Form Henry A Carlilse Company

6

Henry A Carlisle Company





Henry®

A CARLISLE COMPANY

Henry vs. Competitors

	SILICONE	ACRYLIC	ALUM.	EMULSION	POLYURETHANE	SPF	MASTICS	MOD-BIT
Henry	✓	✓	✓	✓	✓	✓	✓	✓
Gaco	✓	✓	✗	✗	✓	✓	✓	✗
TRP Roofing Products	✓	✓	✗	✓	✗	✓	✓	✓
Karnak	✓	✓	✓	✓	✗	✗	✓	✗
GAF	✓	✓	✗	✗	✗	✗	✓	✓
APOC	✓	✓	✓	✓	✗	✗	✓	✗
Uniflex	✓	✓	✓	✓	✗	✓	✗	✗
Progressive Materials	✓	✓	✗	✗	✗	✓	✗	✗

Roofing Overview and Lifecycle

NEW INSTALLATION


New Construction Roofs:
Henry® MB, BUR, SPF & Vegetative Roof Systems

REPLACE

If A Roof Is At The End Of Its Life, And Conditions Prevent A Recover, Then Tear-off & Replacement Is The Only Option.
Henry® Roof Systems Featuring Henry® MB, BUR And SPF Systems

RECOVER

Recovering The Existing Roof Near The End Of Its Lifecycle With A New Roof May Be A Practical Option Under The Right Conditions.
Henry® Recover Systems Using SPF With Henry® Or Pro-Grade® Coatings Or Henry® MB And BUR Systems

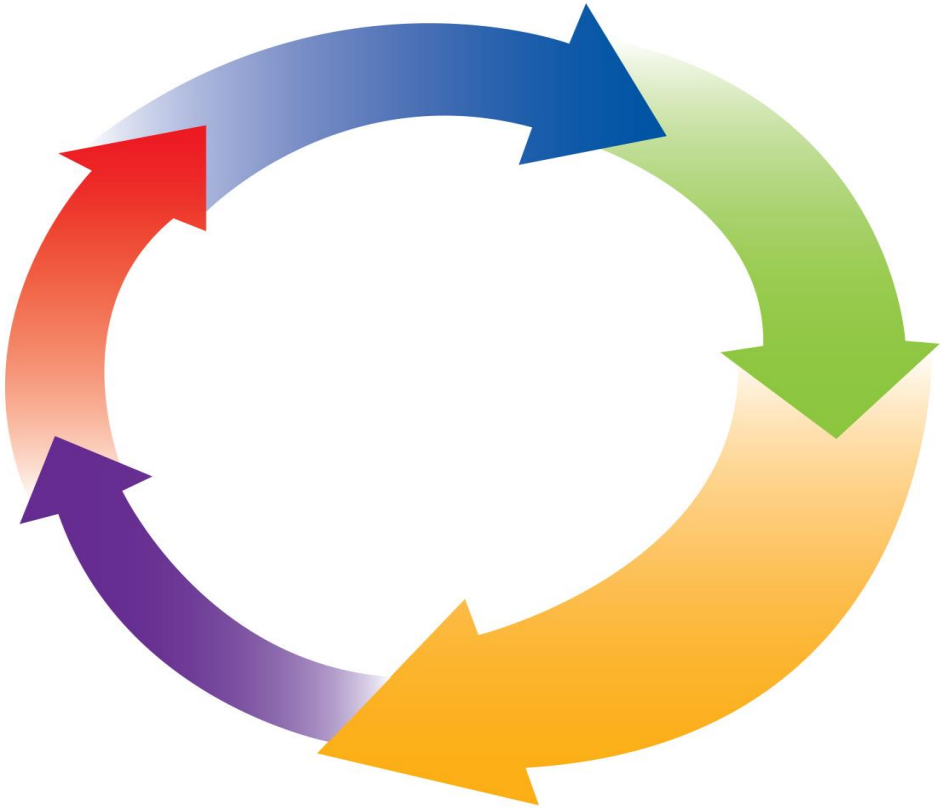

REPAIR

Ongoing Maintenance And Repair Are Imperative To Prolong The Life Span Of A Roofing System.
Henry® Coatings, Mastics, Sealants & Reinforcements Make For Easy Repairs

RESTORE

Extending The Life Of An Existing Roof Asset With A Restoration System Provides Less Disruption, Lower Cost & Equivalent Warranties To Recover & Replacement Options.
Henry® Restoration Systems Featuring Pro-Grade® Silicone, Acrylic, Aluminum & Other Advanced Products

All Roofs Weather with Time

- The Sun's Heat And UV Rays Cause A Roof To Deteriorate Over The Years
- As A Roof Ages It Begins To Wear And Eventually Leak – Leading Some People To Think The Roof Needs To Be Replaced
- Perhaps Just 5-10% Of The Roof Needs Repair And The Rest Can Be Restored



Restore Or Replace?

Replacement:

- Building Owners And Facility Managers Know That Eventually They'll Have To Face The Prospect Of Replacing Their Roof.

- This Typically Requires:
  - A Large Capital Investment
  - Significant Disruption In Daily Activities

Restoration:

- A Money-Saving Alterative To Re-Roofing:
  - **Henry Commercial Roof Restoration Systems**

- **Henry's Advanced Roof Coating Technologies**
  - Silicone, Acrylic, Aluminum, Emulsion or Spray Polyurethane Foam
  - Roof Membrane Restored At A Fraction Of The Cost Of Roof Replacement
  - Ultimately Extending The Roof Membrane Life Cycle

- A Window Of Opportunity For Roof Restoration Before It's Too Late.
  - Less Than 25% Needs To Be Replaced

Restoration – Good For The Building Owner

- Lowest Initial Installed Cost
- Minimal Waste Disposal Fees
- Tax Rebates And Incentives
- Energy Savings
- Lower Maintenance/Repair Costs
- Protective Barrier For Existing Roof System
- UV, Hail, Foot Traffic, Chemical And Thermal Shock Resistance
- Slows Heat Aging
- May Be Recoated Multiple Times



Restoration – Good For The Contractor

- Lower Labor Costs – Easily Applied (Sprayed Or Rolled)
- Save Time And Money
- Low Equipment Cost
- Safer Than Hot Asphalt Or Torches
  - Easy To Train New Workforce
- Easier Mobilization
- Maintenance Program Revenue For The Life Of The Building
- Long-Term Relationship And Revenue Stream
- Henry Support Materials, Training And Tools To Help You Sell Building Owners



Make The Old New Again

- Roof Restoration Is The Process Of Restoring A Roof To A Water-Tight And Energy Efficient Condition
- Just Like This Classic Car, We Can Repair Your Roof And Make It Function And Look Great Again



Henry
A CARLISLE COMPANY

When Is A Roof A Good Candidate?

Three Simple Rules:

- Clean
- Dry
- Sound

15

Are They A Candidate?









Henry
A CARLISLE COMPANY

Are They A Candidate?









Henry
A CARLISLE COMPANY


Henry Pro-Grade® 988 Silicone Restoration System

Building Confidence™

© 2022 Henry Company. All rights reserved.

Facts About High-Solids Silicone Coatings

- Excellent Flexibility
  - -15°F To + 180°F
- Excellent Elongation Properties
- Tenacious Adhesion Properties
- Very High Non-Porous Qualities
- Moisture Cured
  - Cannot Re-Emulsify Under Ponded Water Conditions
- Low VOC
- High UV Stability
  - Loss of ~.1 Mils/Year
- Application Temperature of 35 Deg F And Rising
- High Solids
  - 90%+
- Non-Carbon Based – Will Not Chalk
- Silicon Is The 2nd Most Abundant Element On The Planet
  - Makes Up ~27% Of The Earth's Crust

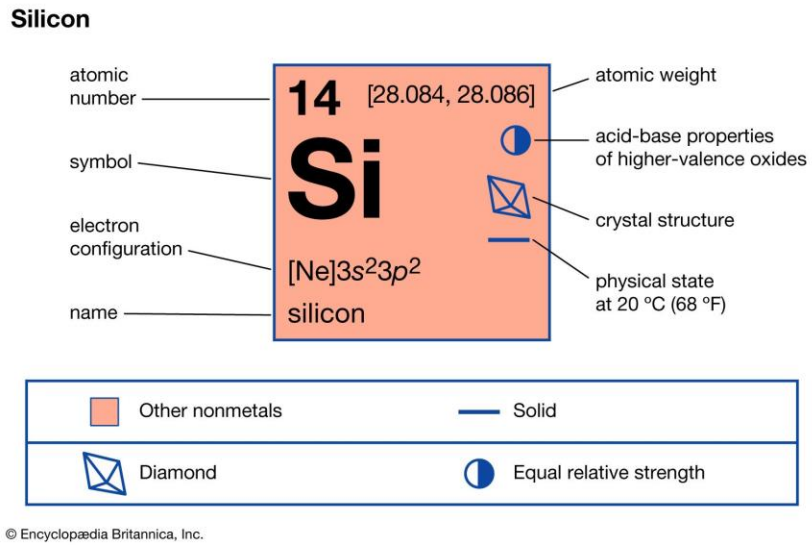



Henry
A CARLISLE COMPANY

High-Solids Silicone Roof Coating Cons

- Poor Dirt Pick-Up Resistance
- Can Only Be Recoated And Repaired With Silicone Products
- Asphalt Bleed-Through
- Clean-up Tools / Spray Equipment
- Specialized Commercial Spray Equipment
- Lack Of Contractor Familiarity
- High-Solids Silicone Is Relatively New Technology
  - ~20+ Years








Henry
A CARLISLE COMPANY

When Is Silicone A Good Fit?

- Flat Roofs
- Low-Steep Roofs (3:12 or Less)
- Harsh Climates
  - Extreme Temps
- Maximum UV Protection
- Ponding Water Areas*

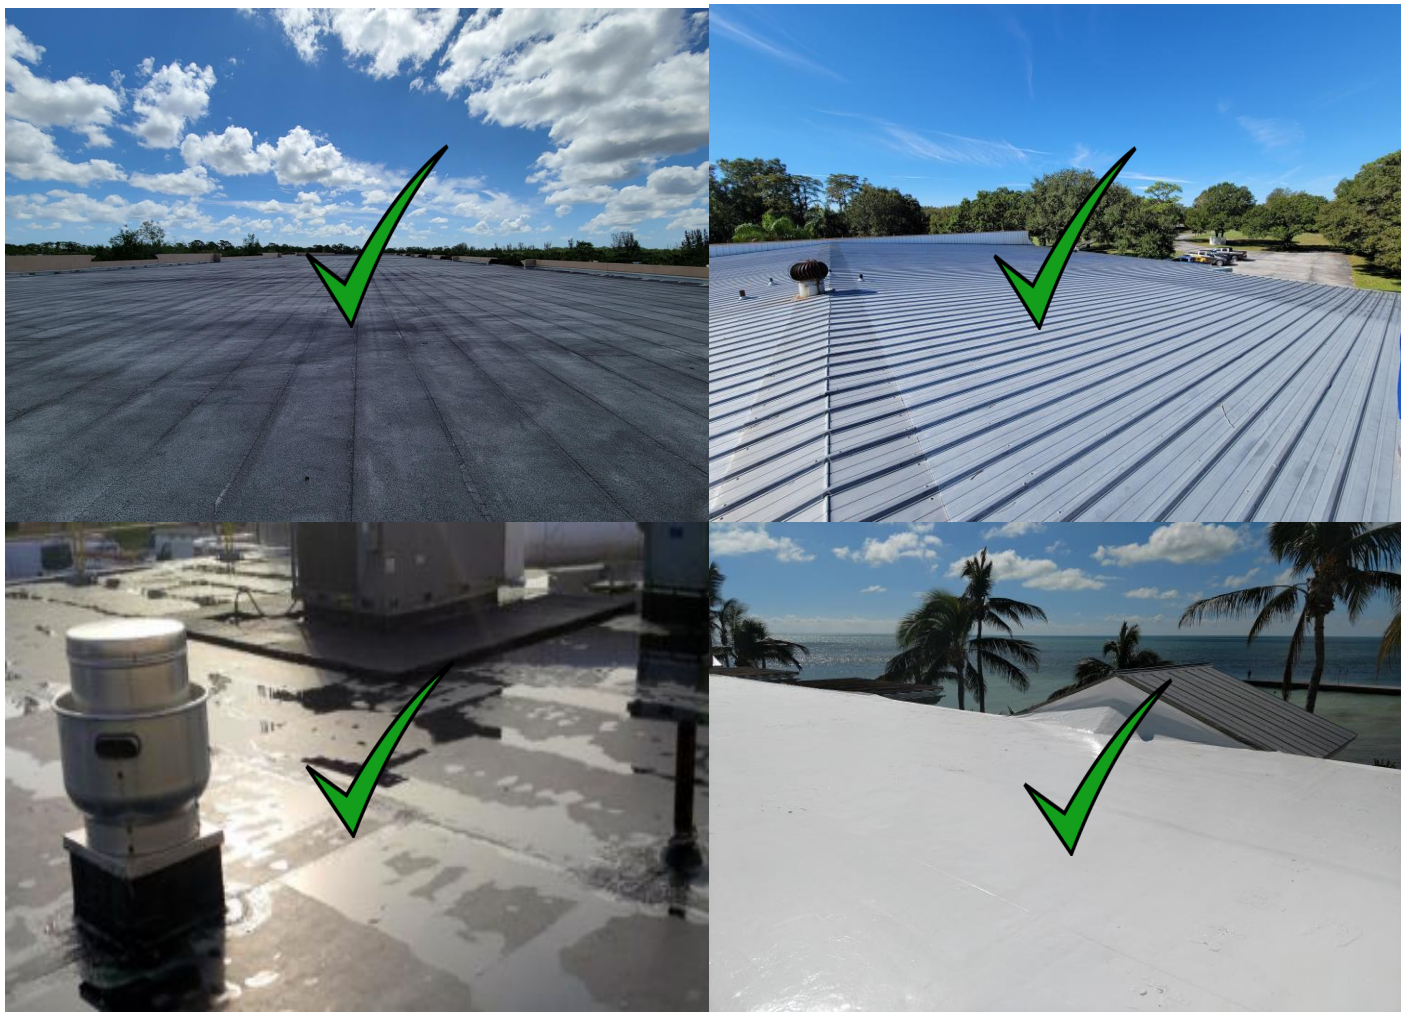

*Not Swimming Pools or Lakes. Positive Drainage Must Be Created

21

When Is Silicone Not A Good Fit?

- Ponding Water Areas*
- Steep Roofs (Greater Than 3:12)
- Barrel Style Roofs
- High-Foot Traffic Areas



*No Swimming Pools or Lakes

22

What Types Of Roofs Can We Restore?

What Types of Roofs Can We Restore?

Asphaltic

Granulated/Smooth Modified Bitumen



BUR



24

What Types of Roofs Can We Restore?

Single-Ply

TPO/PVC



EPDM




25

What Types of Roofs Can We Restore?

Metal



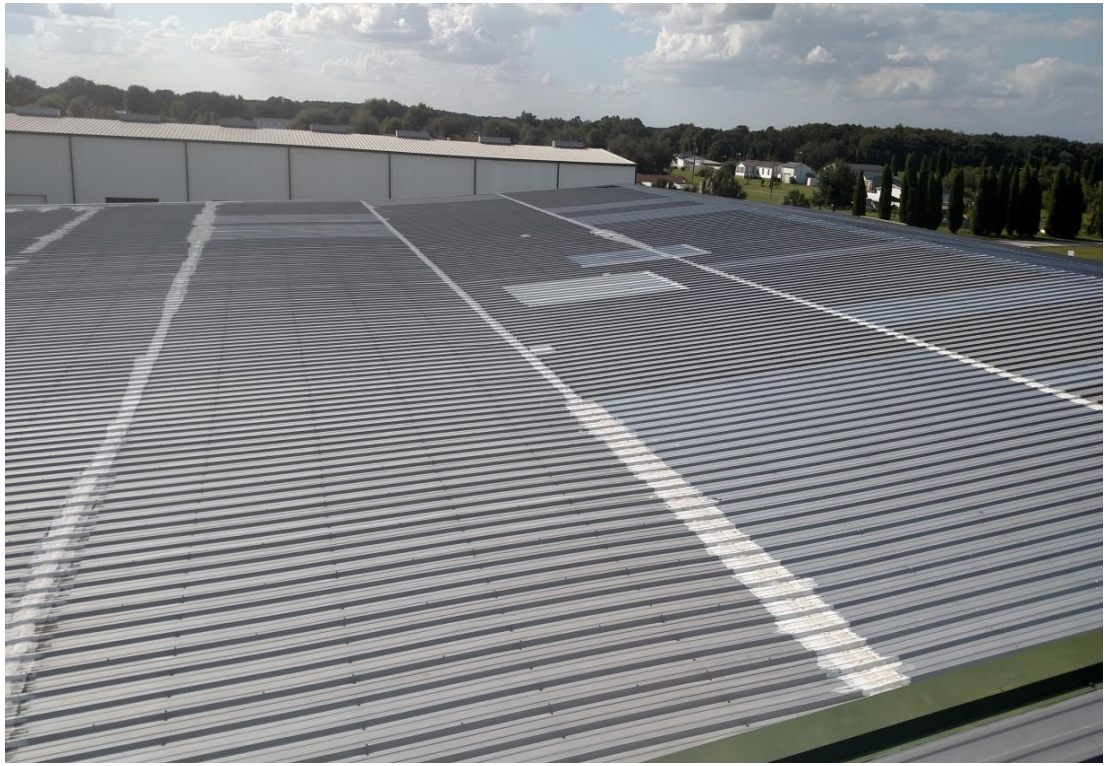

26


What Types of Roofs Can We Restore?

Previously Coated Substrates







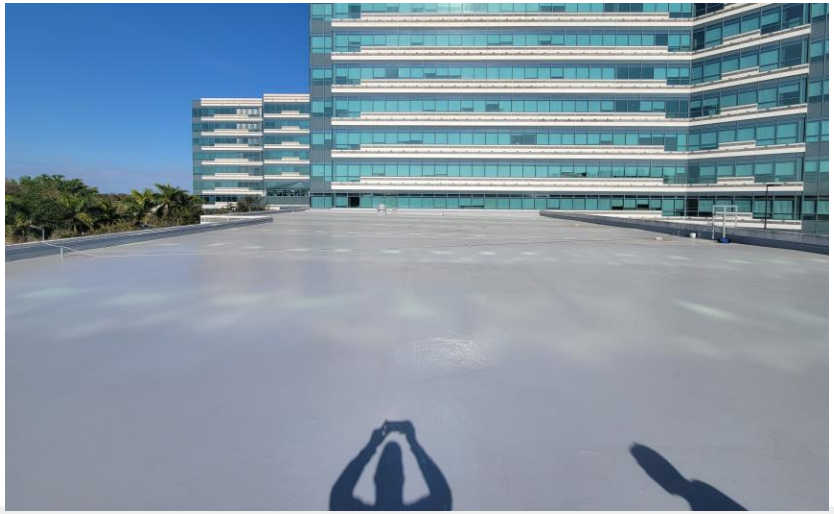

27

What Types of Roofs Can We Restore?

Spray Polyurethane Foam





28

What Types of Roofs Can We Restore?

Tar & Gravel







29

What Types of Roofs Can We Restore?

Tar & Gravel
Spray Polyurethane Foam





30

Pro-Grade® Silicone Restoration Process

The Restoration Process- Warranted Systems

- Visual Roof Inspection
  - If Required
- Adhesion Testing
  - If Required
- Moisture Survey
  - If Required
- Roof Repairs
- Restore
- Final Inspection
  - If Required

Visual Roof Inspection

- **Preferably By Henry Representative For Gold Seal Warranted Systems**
  - **No Charge**
  - **Need Roof Access**











Henry
A CARLISLE COMPANY


Adhesion Testing

- Ensures Adequate Adhesion Of Elastomeric Coating Candidate To Existing Roof System
  - Required:
    - Single-Ply
    - Metal
    - Smooth Asphalt
    - Previously Coated






Ideal Result: Cohesive Failure

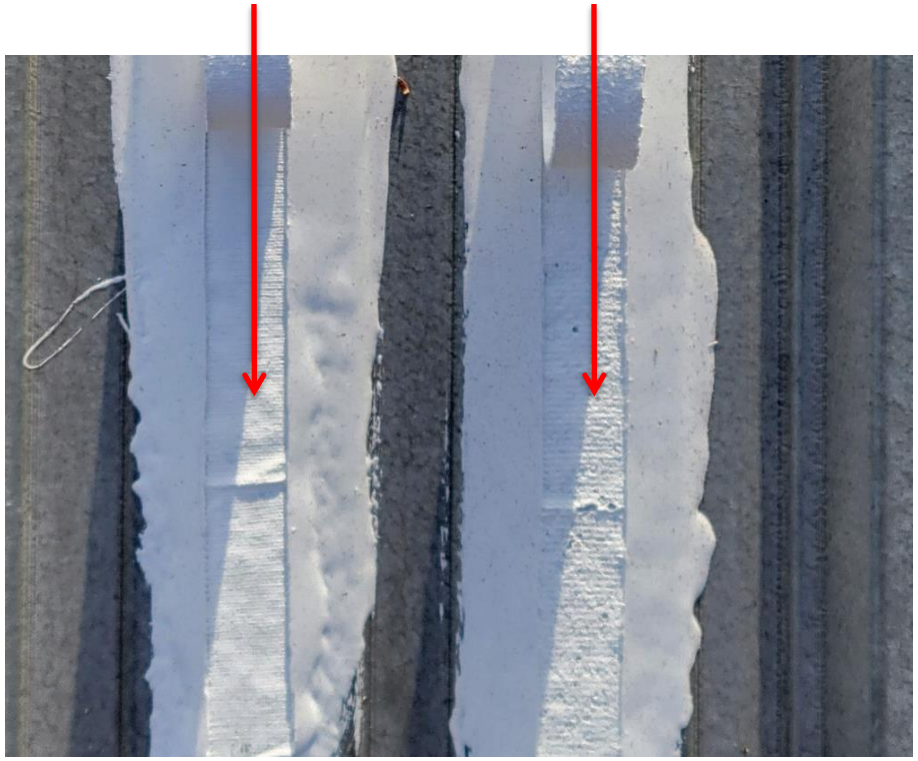

Henry
A CARLISLE COMPANY


Adhesion Testing



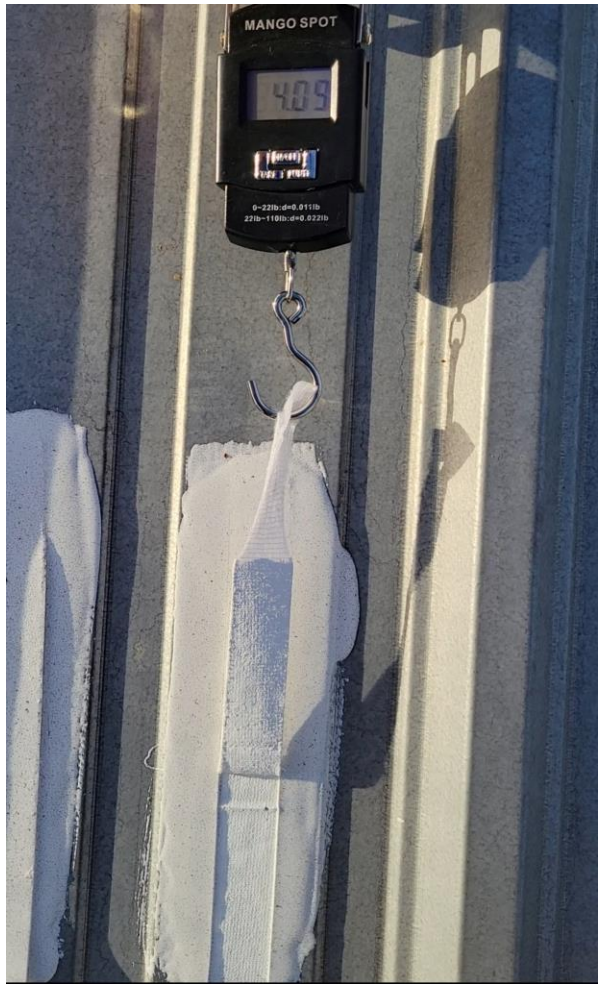

Result:
Adhesive Failure

Ideal Result: Cohesive Failure

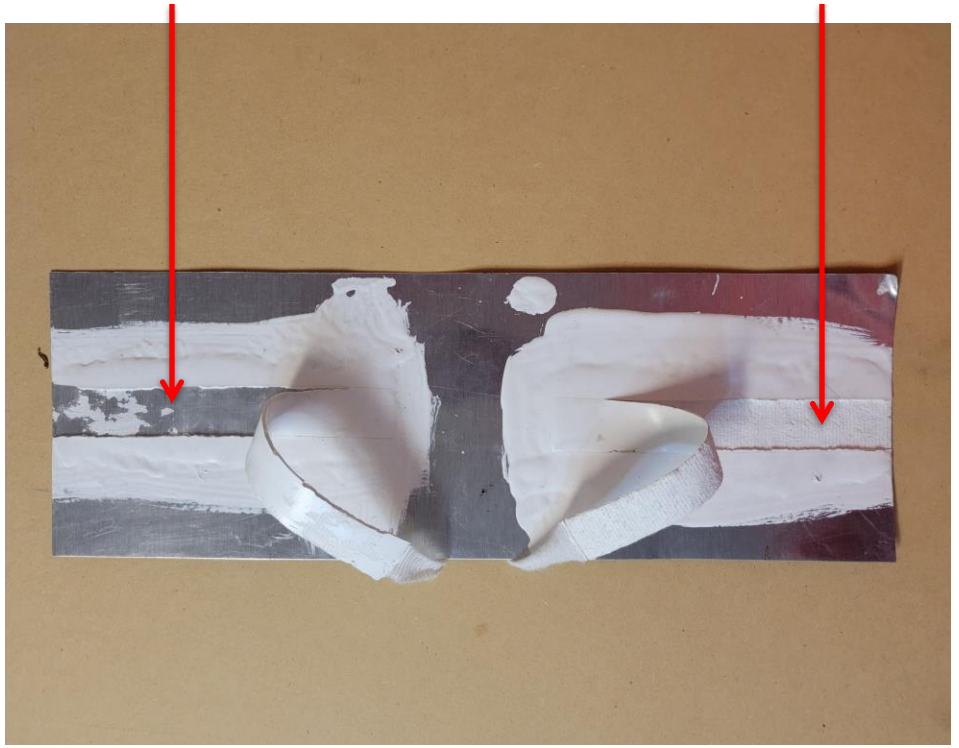

Samples Are Scored On Each Side Of The Strip And Pulled Up And Back (90-135 Degrees To The Roof) And Need To Obtain 2.0 lbs./Linear Inch Minimum Result With Cohesive Failure

Henry
A CARLISLE COMPANY

Moisture Surveys

Moisture Survey

- Infrared Scanning & Core Cut Evaluation Of Existing Roof Assembly Helps Determine Roof's Qualification For Restoration
  - If >25% Is Wet And Needs Replacement, The Roof Is Not A Candidate
  - If <25% Is Wet, Then Damaged Roof Section(s) Can Be Removed And Replaced With Like Materials


Accepted Testing Methods

- Nuclear
- Infrared
- Impedance/Capacitance
- Cores
  - Roof Map and NRCA Guidelines Required

***Not Required On Metal Roofs**





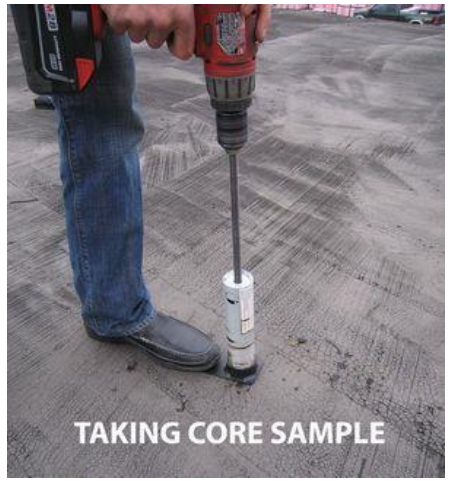






Moisture Surveys

Drone Thermal Moisture Survey



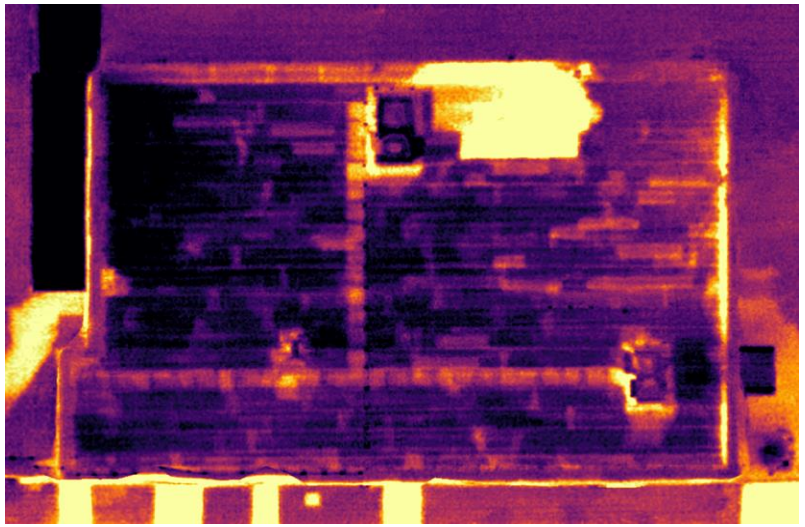

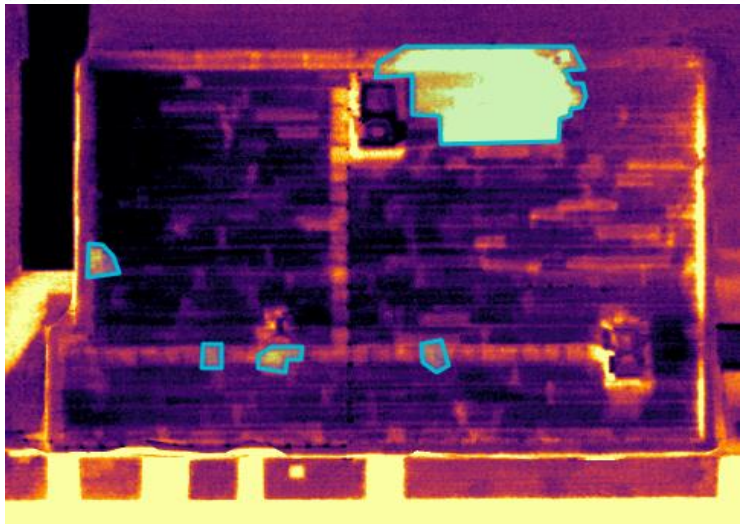

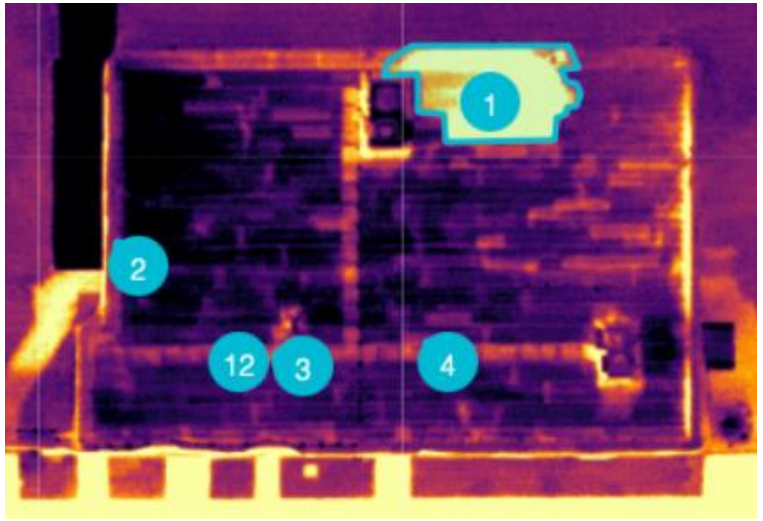

Henry
A CARLISLE COMPANY

Repairs

Repair First, Then Restore

- Remove & Replace Wet Insulation
- Remove & Replace Damaged Decking
- Infill Damaged Area With Like Roofing Materials

Prior To Restoration, The Existing Roof Must Be Brought Back To A Sound, Watertight Serviceable Condition.







Complete Line of Products
Saving Contactors Time and Money

Pro-Grade® Silicone Roof Coatings

Silicone System Offering
Pro-Grade® 988 Silicone
Pro-Grade® 957 Silicone Fibered Roof Sealer
Pro-Grade® 923 Butter Grade Silicone Roof Sealer
Pro-Grade® 928 Pitch Pocket & Self Leveling Roof Sealer
Pro-Grade® 920 Silicone White Roof Sealants
Seal-Tek Micro Fibers
Pro-Grade® 294 Base Coat & Sealer
Prime-Tek TPO Primer
Prime-Tek GP Primer
Pro-Grade® 941 Adhesion Promoting Primer



The Pro-Grade® 988 Silicone Difference

Pro-Grade® 988 Silicone Roof Coating

A Solvent-Free, One-Component, Moisture-Curing Silicone Rubber Roof Coating System For Use On Existing Smooth Asphaltic BUR, Smooth Or Granulated Cap Sheet, Single Ply Roof Membrane, Well-Adhered Acrylic Coating, Metal, Sprayed-in-Place Polyurethane Foam And Various Aged Membrane Roofing.



- 1 Coat Coverage
  - Up To 50 Mils In 1 Coat
- Primerless Application*
- Rain Safe In 15 Minutes
- No Fabric
- New Patented Dirt Pick-Up Resistant Formula
  - Stays Whiter & Brighter Longer
- Passes ASTM D7281
  - Standard Test Method for Determining Water Migration Resistance Through Roof Membranes

- *Pending Adhesion Testing. PG294 Basecoat & Sealer Required Over Asphalt Surfaces To Minimize Staining

Pro-Grade® 988 Silicone Roof Coating

- Does Not Contain Chalk
  - Some Competitors Contain Up To 50%
- NSF P151 Rainwater Catchment Safe
  - Potable Water Safe
- Solvent Free
- Low VOC
  - Less Than 10g/l
- 2 Year Shelf-Life**
- Colors: White, Gray, Tan
  - Premium Colors and Custom Colors Available
- Sizes:
  - 5-gallon Pail
  - 55-gallon Drum



- **Unopened, stored in a cool, dry and shaded location

Pro-Grade® 988 Silicone Dirt Pick-Up Resistant Formula

Henry Pro-Grade 988 Silicone Dirt Pick-Up Resistant Formula







Competitor








44

Pro-Grade® 988 Silicone Early Rain Resistance

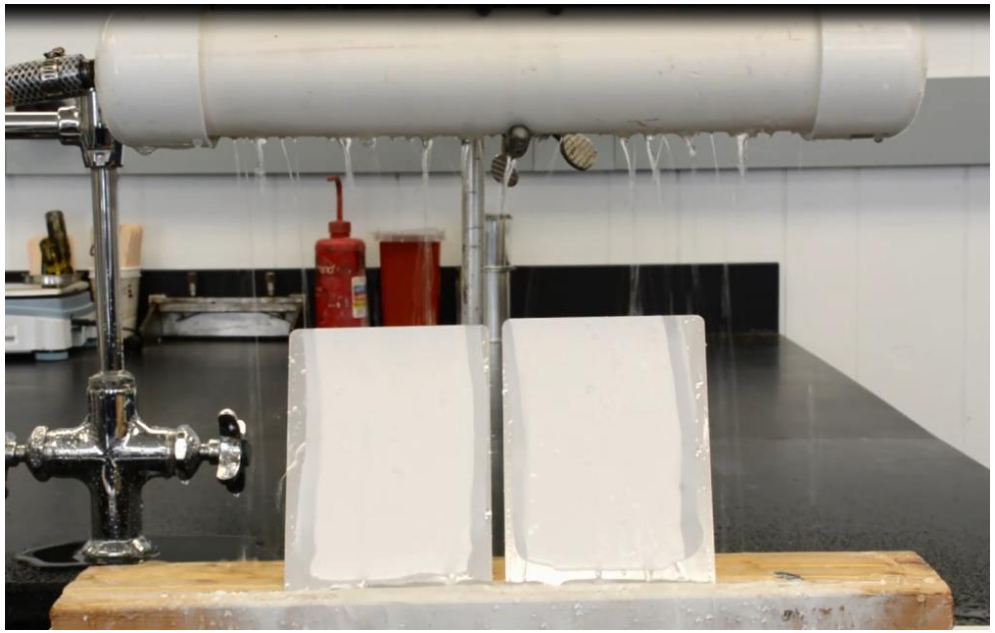

15-minute dry time of the silicone roof coating, followed by 30 minutes of Heavy Rain

Pro-Grade 988




Competitor




45

Why ASTM D7281 Matters? - True Waterproofing

- **Watertight Performance**
  - Seals Roof Terminations, Penetrations And Other Details Of The Roof That Are Typical Leak Sources
  - Seamless
    - True Waterproofing Performance
    - Impervious To Ponding Water

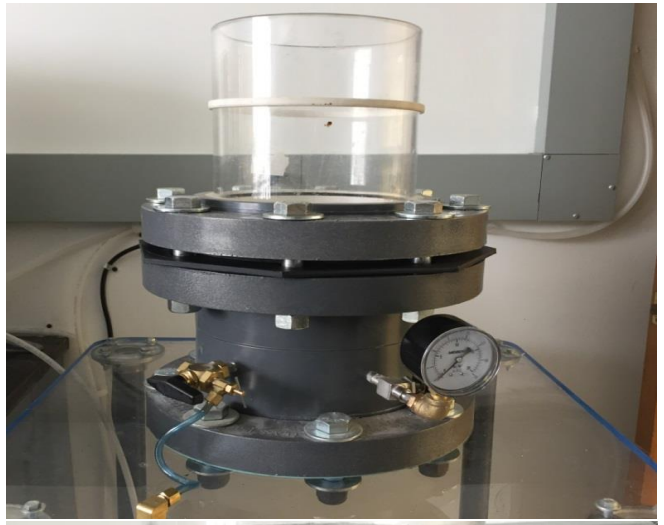

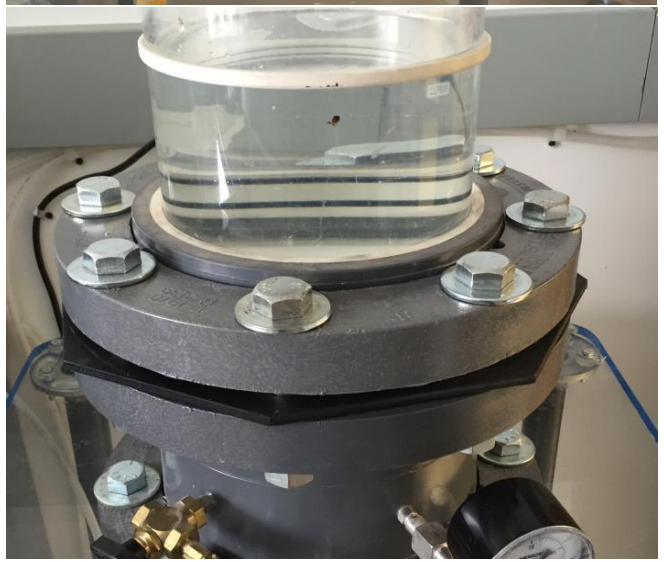



Henry
A CARLISLE COMPANY

Pro-Grade® Silicone Accessories & Primers

Pro-Grade® 923 Butter Grade Silicone Roof Sealer

Silicone Roof Sealer

- No Mixing- Ready To Use
- Tough
- Flexible
- Can Be Easily Applied
  - Brush, Trowel Or Spreader
  - Up To ¼” Thick (250 Mils)
- Vertical And Horizontal Application

- Uses Include
  - Penetrations
  - Flashings
  - Seams
  - Fasteners
  - Repairs

Color: White

Sizes:

- 2-gallon Pail









48

Pro-Grade® 957 Fibered Silicone Roof Sealer

A Silicone Fibered Roof Sealer

- No Mixing- Ready To Use
- Tough
- Flexible
- Can Be Easily Applied
  - Trowel
  - Up To ½” Thick (500 Mils)
- Vertical And Horizontal Application

- Uses Include
  - Penetrations
  - Flashings
  - Drains
  - Seams
  - Fasteners
  - Repairs

Color: White

Sizes:

- 2-gallon Pail









49

Pro-Grade® 928 Pitch Pocket & Self-Leveling Sealer

A Self-Leveling Silicone Sealant That Forms A Watertight Seal For Pipe Penetrations Through Roof Decks In Metal Pitch Pocket Flashings, With No Shrinkage.

- **Seals Fasteners On Low And Semi-steep Sloped Metal Roofs**
  - **100 Fasteners At ½" Diameter Per 10.1 Oz Cartridge**
  - **No Tooling Required –Saves Time!**


Color: Black

Sizes:

- **10.1 Oz Tube**





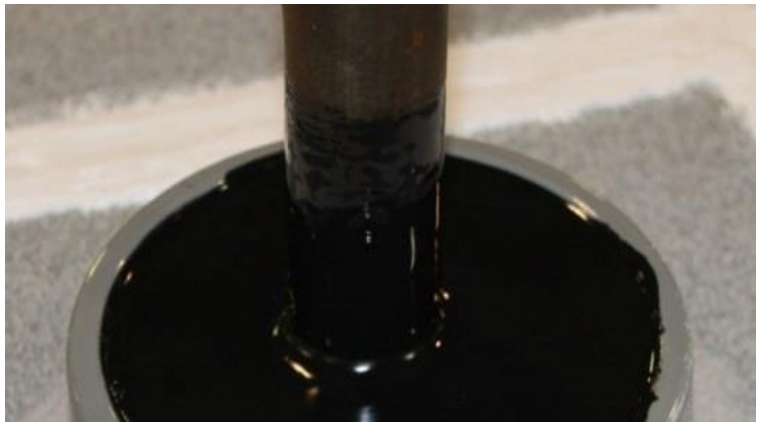





Pro-Grade® 920 Silicone Roof Sealer

One-Component, Moisture-Curing Silicone Sealant

- **Seals Roof Membrane Seams, Concrete Cracks, Flashings, Drains And Damaged Areas On Most Roof Substrates**
  - **100 Punctures At ½" Diameter Per 10.1 Oz Cartridge**
  - **No Hardening, Chalking, Cracking Or Reverting**

Color: White

Sizes:

- **10.1 Oz Tube**







51

Pro-Grade® 294 Basecoat & Sealer

One Part, Stain Blocking Acrylic Coating For Asphaltic Surfaces

- **Spray, Roller Or Brush Apply**
- **Always Should Be First Step On Asphaltic Roofs!**





Color: Gray

Sizes

- **5-gallon Pail**
- **55-gallon Drum**
- **275-gallon Tote**



53

Prime-Tek TPO Primer

A Low VOC Solvent-Based Primer Designed To Promote Optimal Adhesion for AcryShield Acrylics and Pro-Grade 988 Silicone to New Or Existing TPO

For Use Over:

- **TPO Only**
- **Dries Quickly**

Color: Red

Sizes:

- **5-gallon Pail**



Pro-Grade® 941 Adhesion Primer


A One-Component, Film Forming *Adhesion Promoter* For Single Ply Membrane Roofs, Metal Roofs And Previously Coated Roofs

- **Dries Quickly**
- **Spray, Roller Or Brush Applied (Recommended Sprayed)**
- **400 To 600 Sq. Ft./Gal Coverage**

Color: Clear/Yellow

Sizes:

- **1-gallon Can**

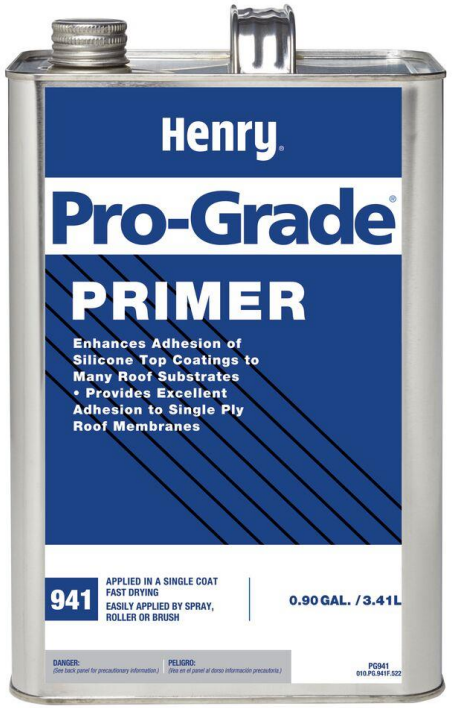



56

Project Startup

Preparation- Cleaning

Granulated Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)

Smooth Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)



Single-Ply Roofs

- Clean With 1500-2,000 PSI Pressure Washer
  - Wash With Water Only!



Metal Roofs

- Clean With 3,000 Psi Or Greater Pressure Washer
  - Wash With Water Only!
- Air Lance (195 CFM)
- Wire Brush/Brush Blast (Metal Surfaces)



ENSURE ALL RESIDUE IS REMOVED AND ROOF IS DRY PRIOR TO SEALER OR COATING APPLICATION

58


Preparation- Basecoat & Sealer


Asphaltic Roofs/Roofs Previously Coated with Aluminum Coating

Pro-Grade 294 Basecoat & Sealer

- **Roll**
- **Squeegee and Back Roll**
- **Spray and Back Roll**
- **Tank Spreader**



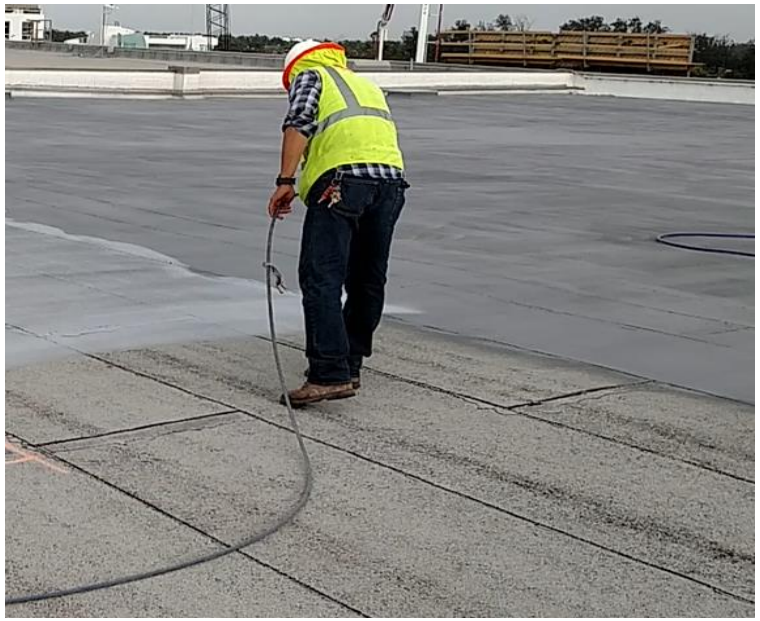


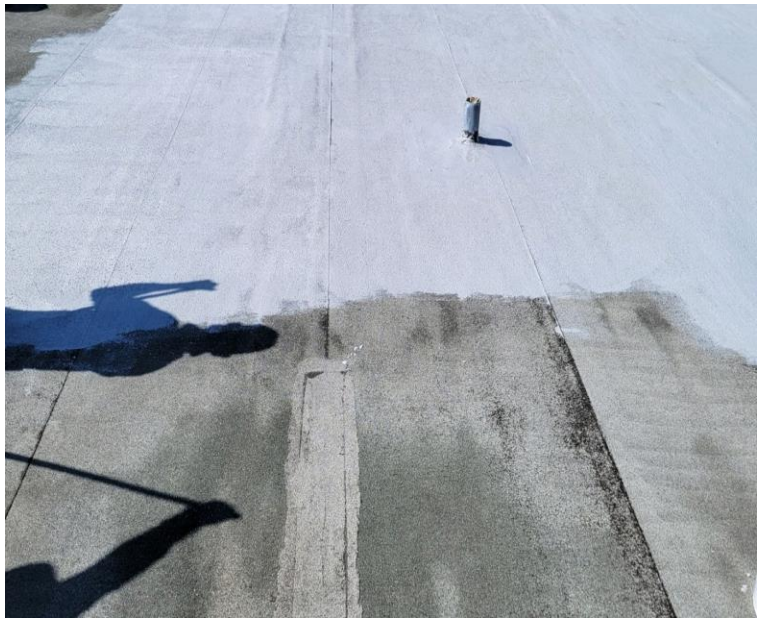

59

Preparation- Adhesion Primer

Single-Ply, Metal, Previously Coated Roofs

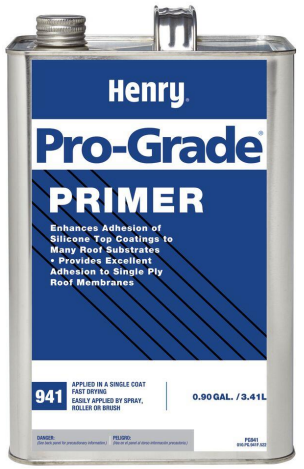

Pro-Grade 941 Adhesion Primer (If Needed)

- Spray
  - Chapin Extreme Pump Sprayer (Recommended)







60

Preparation- The Details

- Seams
- Penetrations
- Curbs
- Terminations
- Transitions
- Parapet

90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!









61

Preparation- The Details

Asphalt/Single-Ply Roofs

- **Seam Options**
  - **Pro-Grade 988**
    - **Brush**
    - **Roll**
    - **Spray**
  - **Pro-Grade 923 Butter Grade**
    - **Brush**
    - **Trowel**
  - **Pro-Grade 957 Fibered Roof Sealer**
    - **Trowel**
- **Penetration/Drain Options**
  - **Pro-Grade 923 Butter Grade**
    - **Brush**
    - **Trowel**
  - **Pro-Grade 957 Fibered Roof Sealer**
    - **Trowel**


Metal Roofs


Seam/Penetration/Fastener Options

- **Pro-Grade 923 Butter Grade**
  - **Brush**
  - **Trowel**
- **Pro-Grade 957 Fibered Roof Sealer**
  - **Trowel**
- **Pro-Grade 928 Self-Leveling Sealer**
  - **Caulk Gun**





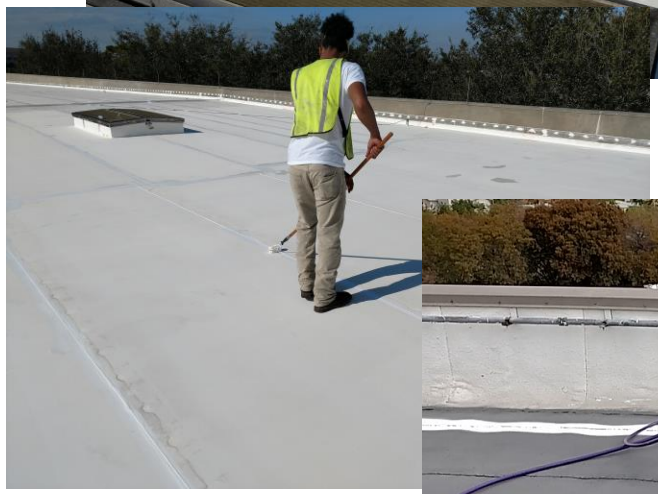

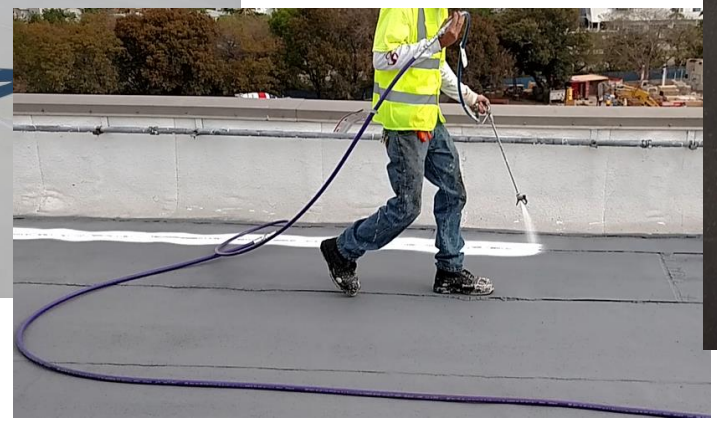



90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!

Pro-Grade® Silicone Application

Installation – Roof Grid Process

- **Measure And Mark 10’x10’ Squares On The Roof, Each Representing One Square (100 Sq.Ft.)**

Example:

If The Spec Calls For 2 Gallons/Square Of Coating, Then One 5-gallon Pail Of Pro-Grade 988 Will Cover 2.38 Squares. (Smooth Surfaces)

- **Granulated Mod-bit & Rough Surfaces Will Require More Coating To Meet DFT**








65

Installation – Easy Application

Roll

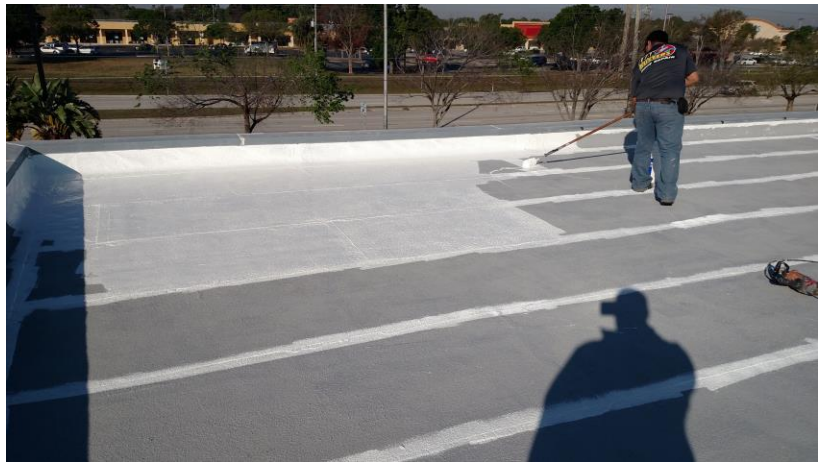





66

Installation – Easy Application

Squeegee and Back Roll







Installation – Easy Application

Spray and Back Roll





68

Installation – Easy Application

Tank Spreader





69

Warranty Information

Henry Warranty Program

Industry-Leading Warranty Program

Warranty Options Provide Up To 20 Years Labor, Workmanship And Materials Coverage

- Transferable And Renewable Options

Silicone Restoration Systems Warranties

- No Exclusions To Ponding Water*
- Lifetime Limited Material Warranty



*Not Swimming Pools or Lakes. Positive Drainage Must Be Created

71

Henry Pro-Grade® Silicone Warranty Options

Warranty program

Henry® Pro-Grade® Silicone Roof Coating System

A roof restoration system from Henry®, Pro-Grade® Silicone high performance roof coating system extends the life cycle of your roof, resulting in a cost-effective alternative to a full replacement.

Warranty Options from Henry®
– Choose your desired level of warranty protection to meet your needs: Material Plus or Gold Seal.
– Both options can be available when installation is in compliance with the information below.

Material Plus Warranty
This warranty option provides material and labor coverage at no charge during the applicable warranty term to repair the affected roof area when product manufacturing defects have been determined. Product(s) must be installed by a Material Plus or Gold Seal Authorized Contractor.

Gold Seal Warranty
This warranty option provides material and labor to repair the affected area when product defects or workmanship installation deficiencies have been determined. Product(s) must be installed by a Gold Seal Authorized Contractor.

Warranty installation options

10-year Pro-Grade® Silicone roof coating system[1]

	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Aged or 1" new PremiR+ Evo SPF[3]	Single ply membrane (TPO/PVC/EPDM/Hypalon®)	Metal*	Warranty cost	
								Material Plus	Gold Seal
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.06/SF $900 minimum
	BC	Pro-Grade® 988	1.00 gal./sq. 15 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT		
	TC	Pro-Grade® 988	1.00 gal./sq. 15 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT		
Option #2	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.06/SF $900 minimum
	TC	Pro-Grade® 988	2.00 gal./sq. 30 mil DFT	1.50 gal./sq. 22 mil DFT	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mil DFT		

15-year Pro-Grade® Silicone roof coating system[2]

	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Aged or 1.5" new PremiR+ Evo SPF[3]	Single ply membrane (TPO/PVC/EPDM/Hypalon®)	Metal*	Warranty cost	
								Material Plus	Gold Seal
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.08/SF $1,200 minimum
	BC	Pro-Grade® 988	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT		
	TC	Pro-Grade® 988	1.50 gal./sq. 22 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT		
Option #2	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.08/SF $1,200 minimum
	TC	Pro-Grade® 988	2.50 gal./sq. 37 mils DFT	2.00 gal./sq. 30 mil DFT	2.00 gal./sq. 30 mil DFT	2.00 gal./sq. 30 mil DFT	2.00 gal./sq. 30 mil DFT		

Warranty installation options

10-year Pro-Grade® Silicone roof coating system[1]

	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Aged or 1" new PremiR+ Evo SPF[3]	Single ply membrane (TPO/PVC/EPDM/Hypalon®)	Metal*	Warranty cost	
								Material Plus	Gold Seal
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.06/SF $900 minimum
	BC	Pro-Grade® 988	1.00 gal./sq. 15 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT		
	TC	Pro-Grade® 988	1.00 gal./sq. 15 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT	0.75 gal./sq. 11 mil DFT		
Option #2	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.06/SF $900 minimum
	TC	Pro-Grade® 988	2.00 gal./sq. 30 mil DFT	1.50 gal./sq. 22 mil DFT	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mil DFT		

15-year Pro-Grade® Silicone roof coating system[2]

	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Aged or 1.5" new PremiR+ Evo SPF[3]	Single ply membrane (TPO/PVC/EPDM/Hypalon®)	Metal*	Warranty cost	
								Material Plus	Gold Seal
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.08/SF $1,200 minimum
	BC	Pro-Grade® 988	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT		
	TC	Pro-Grade® 988	1.50 gal./sq. 22 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT	1.00 gal./sq. 15 mil DFT		
Option #2	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost	$.08/SF $1,200 minimum
	TC	Pro-Grade® 988	2.50 gal./sq. 37 mils DFT	2.00 gal./sq. 30 mil DFT	2.00 gal./sq. 30 mil DFT	2.00 gal./sq. 30 mil DFT	2.00 gal./sq. 30 mil DFT		

Henry Pro-Grade® Silicone Warranty Options

20-year Pro-Grade® Silicone roof coating system²								
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Aged or 1.5" new PremiR+ Evo SPF³	Single ply membrane (TPO/ PVC/EPDM/ Hypalon®)	Metal*	Warranty cost
								Material Plus / Gold Seal
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost / $.10/SF $1,500 minimum
	BC	Pro-Grade® 988	1.50 gal./sq. 22 mils DFT	1.00 gal./sq. 15 mils DFT	1.00 gal./sq. 15 mils DFT	1.00 gal./sq. 15 mils DFT	1.00 gal./sq. 15 mils DFT	
	TC	Pro-Grade® 988	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mil DFT	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mils DFT	1.50 gal./sq. 22 mil DFT	
Option #2	PC	Pro-Grade® 294	1.25 gal./sq. 11 mil DFT	1.00 gal./sq. 9 mil DFT	n/a	n/a	n/a	No cost / $.10/SF $1,500 minimum
	TC	Pro-Grade® 988	3.00 gal./sq. 44 mils DFT	2.50 gal. /sq. 37 mils DFT	2.50 gal./sq. 37 mils DFT	2.50 gal./sq. 37 mils DFT	2.50 gal./sq. 37 mils DFT	

Ancillary components for all warranted assemblies				
Application		Product name	Product description	Coverage rate
Option #1	S Penetrations, flashings and seams	Pro-Grade® 923	Butter grade sealant	80 linear feet per 2 gallon pail applied at 1/8" thick and 4" wide
		Pro-Grade® 957	Fiber grade silicone sealant	80 linear feet per 2 gallon pail applied at 1/8" thick and 4" wide
Option #2	RC Penetrations, flashings and seams	Pro-Grade® 988	Silicone roof coating	350 linear feet per 5 gallon pail
		195 Polyester Fabric	Repair and Reinforcement Fabric	300 linear feet per 6" x 300'-0" roll 300 linear feet per 4" x 300'-0" roll
**Optional primer		Pro-Grade® 941	For metal, single-ply and previously coated roofs	500 square feet per gallon unit
Fastener head encapsulation		Pro-Grade® 928	Fastener sealer for metal roofs/pitch pocket sealer	100 fasteners per 10.1 fl. oz. cartridge
Punctures		Pro-Grade® 920	Standard grade silicone sealant	100 punctures per 10.1 fl. oz. cartridge

PC Primer coat BC Base coat TC Top coat

NOTES:
* For slopes greater than 3:12, contact Henry® Technical Support or the local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area.
DFT = Dry Film Thickness (minimum requirement).
Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc.
For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.
¹Pro-Grade 957 Silicone Fibered Sealer can be used to treat seams.
²Pro-Grade 923 is required at seams and parapets, 1/8" (125 mils) extending a minimum of 2" past area
³Use Pro-Grade® 941 Primer as required. For new SPF, 1" is required for 10-year warranty and 1.5" is required for 15- and 20-year warranties.

Material Plus Warranty Process
Step 1: Complete Authorized Contractor Application for a Henry® Material Plus Warranty and submit to warranty@henry.com.
Step 2: Complete Henry® Extended Warranty Application by clicking on the following link: http://us.henry.com/warranty.
Step 3: Complete the project following the appropriate Pro-Grade® 988 Guide Specification.
Step 4: Warranty typically issued within 10 business days upon completion of warranty application and project.

Gold Seal Warranty Process
Step 1: Complete Authorized Contractor Application for a Henry® Gold Seal Warranty and submit to warranty@henry.com.
Step 2: Complete Henry® Extended Warranty Application by clicking on the following link: http://us.henry.com/warranty.
Step 3: Complete the project following the appropriate Pro-Grade® 988 Guide Specification.
Step 4: Final inspection is completed by an authorized Henry® Representative and submitted to warranty@henry.com.
Step 5: Warranty typically issued within 10 business days upon completion of warranty application, project and final inspection.

Call 1-800-486-1278 or email warranty@henry.com for more warranty information.

73

Henry Pro-Grade® Silicone Application Guide

Application guide

Henry® Pro-Grade® Silicone Roof Coating System

This application guide provides instructions for successfully applying a Henry® Pro-Grade® Silicone roof coating system on metal, aged single-ply (TPO, PVC, EPDM and Hypalon®), asphalt roofs (roll roofing, modified bitumen and built-up roofing) and previously coated roofs. A Pro-Grade® Silicone roof coating system is a roof restoration system providing a cost-effective alternative to a full replacement. When installed according to these instructions, it is designed to provide a waterproof, fluid applied roofing system, supported by a variety of warranty offerings. This application guide is not intended to be used for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

PC Primer coat BC Base coat TC Top coat S Sealant RC Reinforced coating

Coverage rates

Coating assembly configuration			Granulated cap sheet	Smooth cap sheet/ BUR (non-aggregate)	Aged or new PremiR+ EVO SPF[3]	Single ply (TPO/PVC/ EPDM/Hypalon®)	Metal*
10-year Pro-Grade® Silicone roof coating system options[1]							
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. (11 mil DFT)	1.00 gal./sq. (9 mil DFT)	n/a	n/a	n/a
	BC	Pro-Grade® 988	1.00 gal./sq. (15 mil DFT)	0.75 gal./sq. (11 mil DFT)	0.75 gal./sq. (11 mil DFT)	0.75 gal./sq. (11 mil DFT)	0.75 gal./sq. (11 mil DFT)
	TC	Pro-Grade® 988	1.00 gal./sq. (15 mil DFT)	0.75 gal./sq. (11 mil DFT)	0.75 gal./sq. (11 mil DFT)	0.75 gal./sq. (11 mil DFT)	0.75 gal./sq. (11 mil DFT)
Option #2	BC	Pro-Grade® 294	1.25 gal./sq. (11 mil DFT)	1.00 gal./sq. (9 mil DFT)	n/a	n/a	n/a
	TC	Pro-Grade® 988	2.00 gal./sq. (30 mil DFT)	1.50 gal./sq. (22 mil DFT)	1.50 gal./sq. (22 mils DFT)	1.50 gal./sq. (22 mil DFT)	1.50 gal./sq. (22 mil DFT)
15-year Pro-Grade® Silicone roof coating system options[2]							
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. (11 mil DFT)	1.00 gal./sq. (9 mil DFT)	n/a	n/a	n/a
	BC	Pro-Grade® 988	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)
	TC	Pro-Grade® 988	1.50 gal./sq. (22 mil DFT)	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mil DFT)
Option #2	BC	Pro-Grade® 294	1.25 gal./sq. (11 mil DFT)	1.00 gal./sq. (9 mil DFT)	n/a	n/a	n/a
	TC	Pro-Grade® 988	2.50 gal./sq. (37 mil DFT)	2.00 gal./sq. (30 mil DFT)	2.00 gal./sq. (30 mil DFT)	2.00 gal./sq. (30 mil DFT)	2.00 gal./sq. (30 mil DFT)
20-year Pro-Grade® Silicone roof coating system options[2]							
Option #1	PC	Pro-Grade® 294	1.25 gal./sq. (11 mil DFT)	1.00 gal./sq. (9 mil DFT)	n/a	n/a	n/a
	BC	Pro-Grade® 988	1.50 gal./sq. (22 mil DFT)	1.50 gal./sq. (15 mil DFT)	1.00 gal./sq. (15 mils DFT)	1.50 gal./sq. (15 mil DFT)	1.50 gal./sq. (15 mil DFT)
	TC	Pro-Grade® 988	1.50 gal./sq. (22 mil DFT)	1.50 gal./sq. (22 mil DFT)	1.50 gal./sq. (22 mils DFT)	1.50 gal./sq. (22 mil DFT)	1.50 gal./sq. (22 mil DFT)
Option #2	BC	Pro-Grade® 294	1.25 gal./sq. (11 mil DFT)	1.00 gal./sq. (9 mil DFT)	n/a	n/a	n/a
	TC	Pro-Grade® 988	3.00 gal./sq. (44 mil DFT)	2.50 gal./sq. (37 mil DFT)	2.50 gal./sq. (37 mils DFT)	2.50 gal./sq. (37 mil DFT)	2.50 gal./sq. (37 mil DFT)

Ancillary components for all warranted assemblies

Application			Product name	Product description	Coverage rate
Option #1	S	Penetrations, flashings and seams	Pro-Grade® 923	Butter grade sealant	80 linear foot per 2 gallon pail applied at 1/8" thick and 4" wide
			Pro-Grade® 957	Fiber grade silicone sealant	80 linear foot per 2 gallon pail applied at 1/8" thick and 4" wide
Option #2	RC	Penetrations, flashings and seams	Pro-Grade® 988	Silicone roof coating	350 linear foot per 5 gallon pail
			196 Polyester Fabric	Repair and Reinforcement Fabric	300 linear feet per 6" x 300'-0" roll 300 linear feet per 4" x 300'-0" roll
**Optional primer			Pro-Grade® 941	for metal, single-ply and previously coated roofs	500 square feet per gallon unit
Fastener head encapsulation			Pro-Grade® 928	Fastener sealer for metal roofs/pitch pocket sealer	100 fasteners per 10.1 fl. oz. cartridge
Punctures			Pro-Grade® 920	Standard grade silicone sealant	100 punctures per 10.1 fl. oz. cartridge

NOTES: * For slopes greater than 3:12, contact Henry® Technical Support or the local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area. DFT = Dry Film Thickness (minimum requirement). Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable. [2]Pro-Grade 957 Silicone Fibered Sealer can be used to treat seams. [3]Pro-Grade 923 is required at seams and parapets, 1/8" (125 mils) extending a minimum of 2" past area. [4]Use Pro-Grade® 941 Primer as required. For new SPF, 1" is required for 10-year warranty and 1.5" is required for 15- and 20-year warranties.

Warranty: Henry® Pro-Grade® Silicone roof coating system warranty durations are based on overall coating thicknesses. See coverage rate chart for requirements. Coverage rates do not take into account material loss due to spraying, surface texture, waste, etc. Coverage rates are applicable for previously coated and non-coated roofs.

Safety statements: Use caution when applying and walking on coated surfaces. Coated surfaces can be extremely slippery and can create a fall hazard resulting in injury or death. All air intake ventilation equipment should be turned off to prevent fumes from entering building.

STEP 1: Substrate examination

I. Suitability of substrate:

A. Substrate, insulation and all surfaces must be sound, dry, clean and free of oil, grease, rust, dirt, excess mortar, frost, laitance, loose and flaking particles or contaminants.

B. Ensure skylights, scuppers, gutters, penetrations and structures are firmly secured, watertight and in good working condition.

C. Ensure fasteners are secure and tight; replace loose fasteners with larger diameter fastener.

D. Repair or replace defective existing roofing:

1. Metal:
   a. Replace damaged, weakened or corroded metal panels, fascia, gutters, vents, ridge caps or flashings compromising structural integrity.
   b. Remove rust with wire brush, sandblast or mechanical abrasion until substrate is smooth and free of loose rust.
   c. Remove old and damaged mastic repairs at laps, seams and metal fasteners.
2. Modified Bitumen/Smooth BUR:
   a. Remove and replace wet insulation and/or defective materials with like-materials and tie into existing roofing in accordance with NRCA standard roofing practices.
   b. Coat seams with Pro-Grade® 923 or Pro-Grade® 957 at 1/8" thick (125 wet mils) extending 2" on each side of seam.
3. Single ply:
   a. To remove wet insulation and/or defective materials, cut membrane on three sides; fold back and replace with like-materials.
   b. Fold single ply roofing back into place and patch using like materials or PG923 Butter Grade.

E. All areas must promote positive drainage. Contact Henry® Product Support or your sales representative for ponding area repair procedures.

II. Adhesion tests: (For instructions see link): www.us.henry.com/silicone-adhesion-instructions

A. Granulated modified bitumen: not required

B. Adhesion test requirements:

1. Conduct a roof mem area of we surfaces.
2. Any chan
3. Existing r
4. Shaded a
5. Areas indi

C. Verify minin test for war

D. Adhesion te
1. Apply Pro Contact H represent

III. Moisture su

A. The installin roofing ass installation

B. Evaluate ex including s component replace in a

C. Do not insta or substrat

D. Moisture su or more of
1. Infrared th
2. Nuclear s
3. Electric ca
4. Roof core

IV. Weather con

A. Substrate t and rising, dry 15 minu

STEP 2: Substrate preparation

I. Clean:

A. Confirm local water run-off ordinances and restrictions prior to cleaning roof.

B. Surface cleaning:

1. Carefully pressure wash all roof surfaces with greater than 2,000 psi pressure to remove loose granules, debris, rust, scale, dirt, dust, chalking, peeling or flaking coatings, etc. Do not force water into the roof system or damage roof surfaces.
2. Remove grease, oils or contaminates which may interfere with adhesion using warm water and mild detergent.
3. Treat areas of algae, mildew or fungus with a solution of household bleach and water.
4. Rinse roof to ensure removal of all detergent or anything else that could affect adhesion.

II. Primers:

A. Single-ply membrane or metal roof:

1. Apply Pro-Grade® 941 where adhesion test results were less than 2.0 pli.
2. Rust primer: Install a commercial grade rust-inhibitive primer per primer manufacturer recommendations.

B. Asphaltic membranes, asphaltic coatings and/or asphaltic mastics:

1. Apply Pro-Grade® 294 as a bleed-blocker prior to installing Pro-Grade® 988 and silicone accessories.

Pre-treatment of secure and intact seams*

Flashing options	Modified Bitumen (MB) and Single Ply		Metal	
	10- and 15-year warranties	20-year warranty	Crimped standing vertical seams	Hor seal
Option #1	Apply Pro-Grade® 923 or Pro-Grade® 957 using a stiff brush or sealant knife at 1/8" thick (125 wet mils) extending 2" minimum each side of seam.		No seam pre-treatment required	App bru ext
Option #2	Install one layer of coating at 1.5 gallons per square (24 wet mils) extending 2" on each side of seam.	1. Install one layer of roof coating at 2 gallons per square (32 wet mils) extending 4" minimum on each side of seam. 2. Center 6" wide 196 Polyester Fabric over seam and fully embed into roof coating, ensuring 3" of fabric on each side of seam. Brush or roll fabric for proper adhesion and remove all voids. 3. Allow roof coating to dry to touch prior to subsequent layer. 4. Apply a second layer of roof coating at 1 gallon per square (16 wet mils), extending 4" minimum on each side of seam; ensure fabric is fully coated.	No seam pre-treatment required	1. In (3 se 2. C fu o a 3. A la 4. A s s

*Built-up roof (BUR) assemblies do not require pre-treatment of secure and intact seams.

III. Flashing and details:

A. Complete detailing and flashings prior to roof coating installation.

B. Mix Pro-Grade® 988 with drill and mixer blade prior to use until consistent viscosity is achieved.

C. Refer to chart I intact seams.

D. Metal seams:

1. Completely r and sealants.
2. Horizontal lag ridge cap sea
   a. Apply foot p to horizonta gaps openi panel lap to eliminate ga

E. MB/BUR and s

1. Defective, loc
   a. Apply Pro-G generously cracks, blis stiff brush c
   b. Firmly pres
   c. Apply seala top, extend coated.

Roof curbs, parapets and pipe penetrations for MB/BUR, single ply and metal roofs	
Option #1	Apply Pro-Grade® 923 or Pro-Grade® 957 using a stiff brush or sealant knife at 1/8" thick (125 wet mils) extending 4" minimum onto horizontal and vertical surfaces.
Option #2	1. Install roof coating at 2 gallons per square (32 wet mils), extending 4" minimum onto horizontal and vertical surfaces. 2. Center 6" wide 196 Polyester Fabric at upturn and fully embed into roof coating ensuring 3" of fabric on both horizontal and vertical surfaces. Brush or roll fabric for proper adhesion and remove all voids. 3. Allow roof coating to dry to touch prior to subsequent layer. 4. Apply roof coating at 1 gallon per square (16 wet mils), extending 4" minimum onto horizontal and vertical surfaces; ensuring fabric is fully coated.
Fastener heads for MB/BUR, single ply and metal roofs	
Completely encapsulate fastener heads with Pro-Grade® 928	
Drains for MB/BUR, single ply and metal roofs	
1. Remove strainer, ring and other drain components. 2. Apply Pro-Grade® 923 or Pro-Grade® 957 using a stiff brush or sealant knife at 1/8" thick (125 wet mils) from the drain hole opening, extending 12" minimum continuously around the drain perimeter ensuring a smooth and continuous finish.	

STEP 3: Roof coating application

I. Application of roof coating: Refer to the Coverage Rate Chart for warranted minimum requirements.

A. Mix roof coating with drill and mixer blade prior to use until consistent viscosity is achieved.

B. Clean and prepare substrate in accordance with **Step 2: Substrate preparation** of this application guide.

C. Install Pro-Grade® 988 in accordance with this application guide.

1. Modified Bitumen/BUR, steep-slopes and rough or aged surfaces may require additional coats to obtain a uniform and consistent thickness.

D. Multiple coat systems:

1. Pro-Grade® 988 may be utilized as a base and top coat; is intended as a base coat only.
2. Ensure base coat and/or primer coat is fully cured prior to subsequent installation.
3. Ensure cured coating is clean prior to subsequent coating application.
4. Apply subsequent coats perpendicular in fashion to the previous coat.

II. Walkways (optional):

A. Ensure substrate is clean in accordance with **Step 2: Substrate preparation** of this application guide prior to coating application.

B. Apply additional Pro-Grade® 988 at traffic areas at a minimum 1 gallon per square (16 wet mils).

C. Apply Henry Roofing Granules uniformly into wet roof coating at a rate of 20-30 pounds per square.

D. Allow roof coating to dry.

E. Remove loose particles from roof to avoid clogging drains.

Henry. Building Envelope Systems® Roofing | Air Barrier | Waterproofing
Ask us today about other Henry® solutions that help manage the flow of water, air, vapor and energy.
productsupport@henry.com | 1-800-486-1278
www.henry.com
© 2023 Henry Company. All rights reserved.
Printed in U.S.A. 142.SUS.E059 (10/23)

74

Henry AcryShield® Acrylic Restoration Systems

Building Confidence™

© 2022 Henry Company. All rights reserved.

Facts About Acrylics

- Excellent Flexibility
- Great Elongation Properties
- Excellent Adhesion Properties
- Easy To Apply
  - Spray, Brush, Roll
- Breathable
  - High Permeability
- Can Be Coated Over With Other Types Of Coatings
- Good Cost Effective/Performance
- Low VOC





Acrylic Roof Coating Cons

- Ponding Water
  - Will Re-Emulsify
- Multiple Coat Application Required
- Application Window Affected More By Weather
  - Must Be Applied at 50 Deg F and Rising
  - No Rain for 24 Hours+
    - Potential Wash-Off
- Longer Cure Time
- Organic-Based
  - Food Source For Mold And Mildew
- UV Loss
  - ~1-2 Mils/Year
- Lower Solids
  - Typical ~50%
- Over 380 Acrylics
  - Many Made With Lower Quality Chemistries (Styrene And Vinyl)







Henry
A CARLISLE COMPANY

When Is Acrylic A Good Fit?

- Steep Roofs (3:12 or Higher)
- Metal Roofs
- Flat Roofs*
- Barrel Style Roofs
- Hot, Dry Climates
- Minimal Disruption
- Cost-Effective Solution



*Areas That Have Little Rainfall and Great Positive Drainage (No Ponding Water)

78

When Is Acrylic Not A Good Fit?

- Ponding Water Areas
- Flat Roofs*
- High-Foot Traffic Areas
- Needing Maximum UV Protection
- Roofs With Frequent Freezing & Thawing Cycles









*Little To No Positive Drainage

79

What Types Of Roofs Can We Restore?

What Types of Roofs Can We Restore?

Asphaltic

Granulated/Smooth Modified Bitumen



BUR



81

What Types of Roofs Can We Restore?

Single-Ply

PVC/TPO



EPDM




82

What Types of Roofs Can We Restore?

Metal



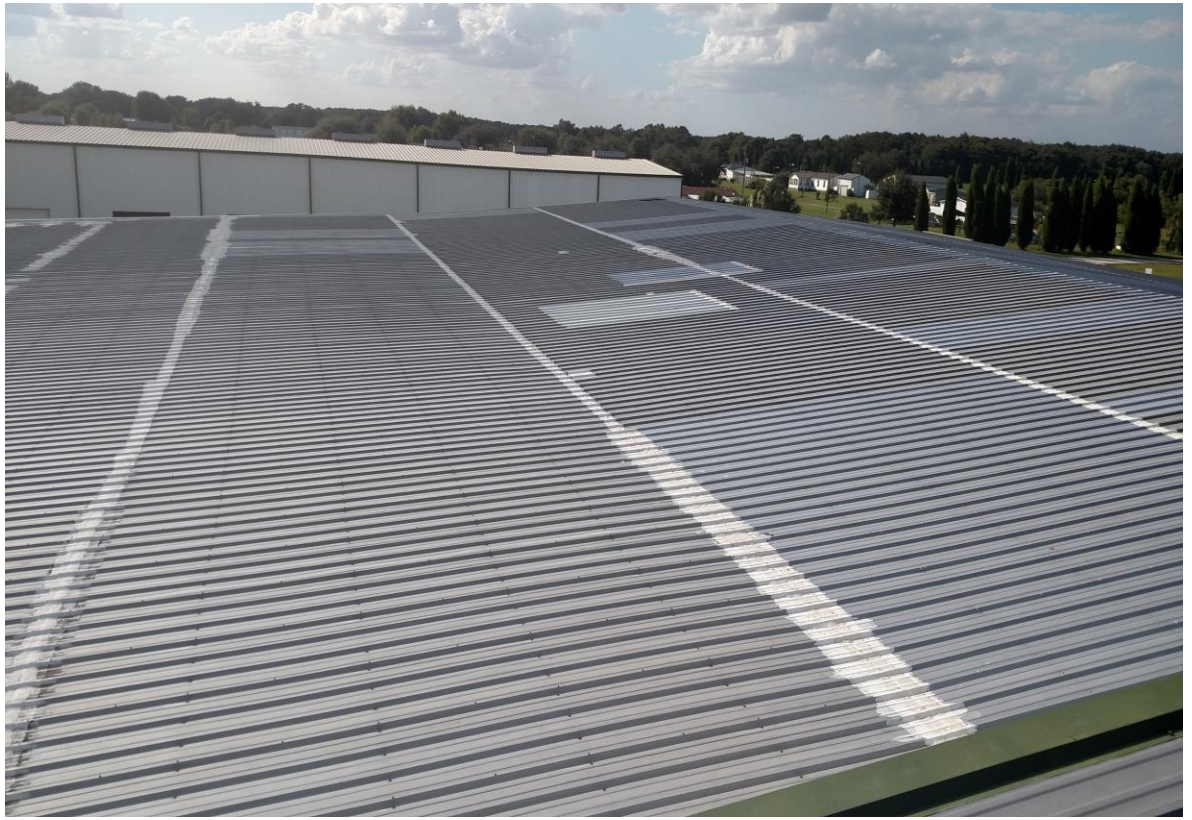

83

What Types of Roofs Can We Restore?

Spray Polyurethane Foam






84

What Types of Roofs Can We Restore?

Previously Coated Roofs*





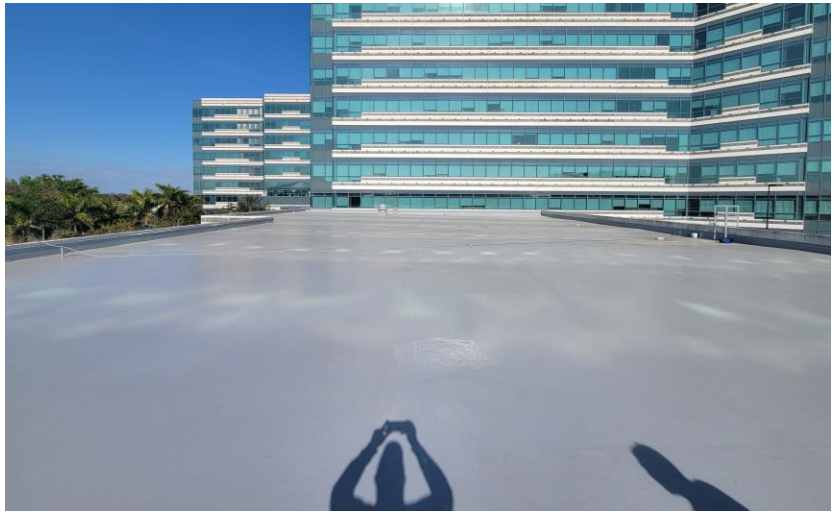

*Exception: Silicone Coated Roofs

85

What Types of Roofs Can We Restore?

Tar & Gravel







What Types of Roofs Can We Restore?

Tar & Gravel
Spray Polyurethane Foam





87

AcryShield® Acrylic Restoration Process

The Restoration Process- Warranted Systems

- Visual Roof Inspection
  - If Required
- Adhesion Testing
  - If Required
- Moisture Survey
  - If Required
- Roof Repairs
- Restore
- Final Inspection
  - If Required

Visual Roof Inspection

- **Preferably by Henry Representative**
  - **No Charge**
  - **Need Roof Access**











Henry
A CARLISLE COMPANY


Adhesion Testing

- Ensures Adequate Adhesion Of Elastomeric Coating Candidate To Existing Roof System
  - Required:
    - Single-ply
    - Metal
    - Smooth Asphalt
    - Previously Coated






Ideal Result: Cohesive Failure

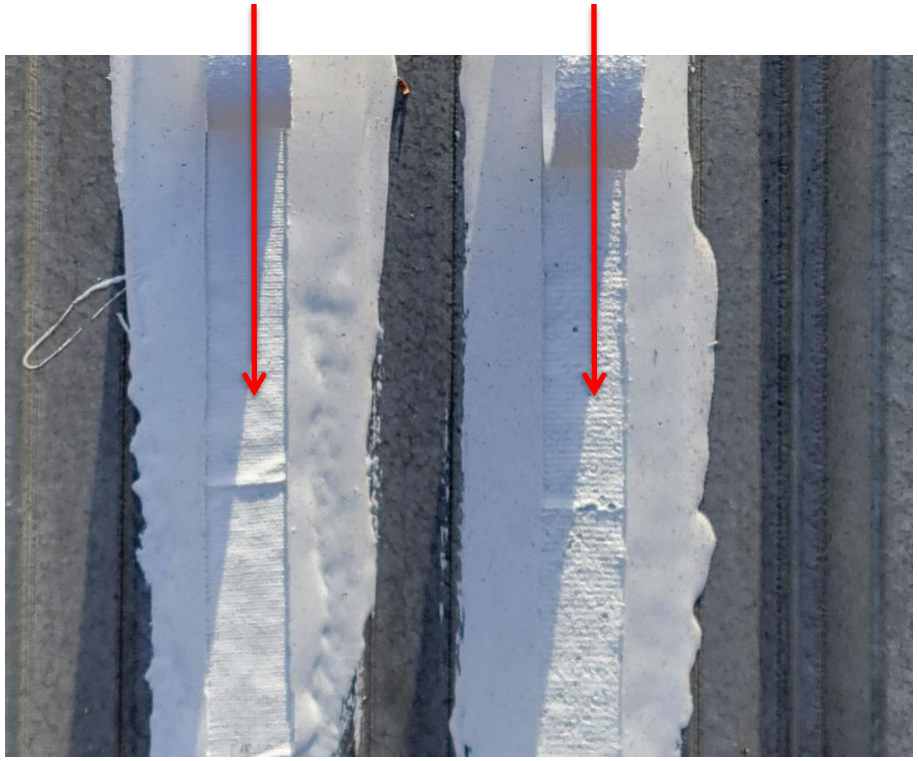

Henry
A CARLISLE COMPANY


Adhesion Testing



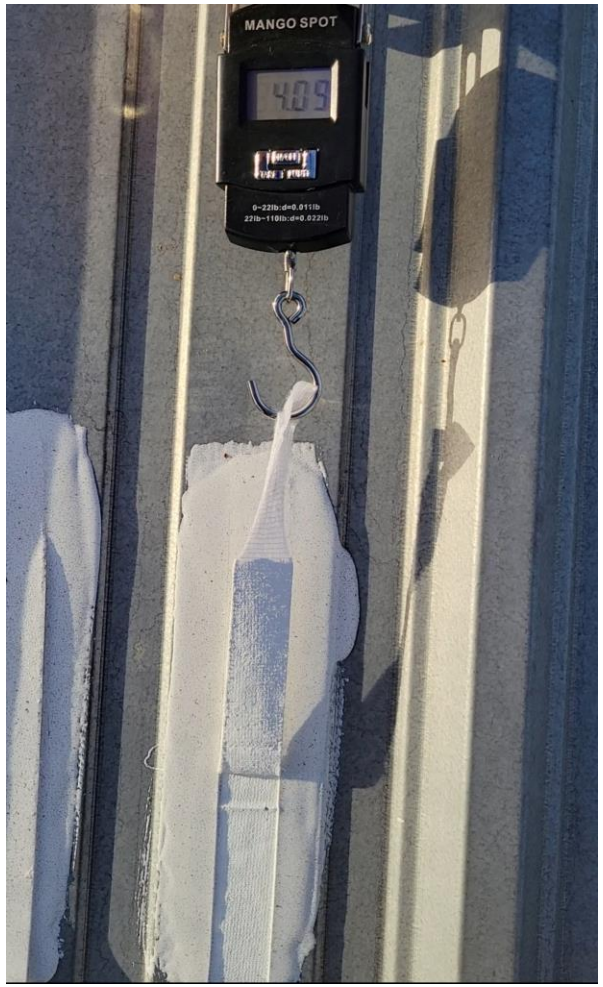

Result:
Adhesive Failure

Ideal Result: Cohesive Failure

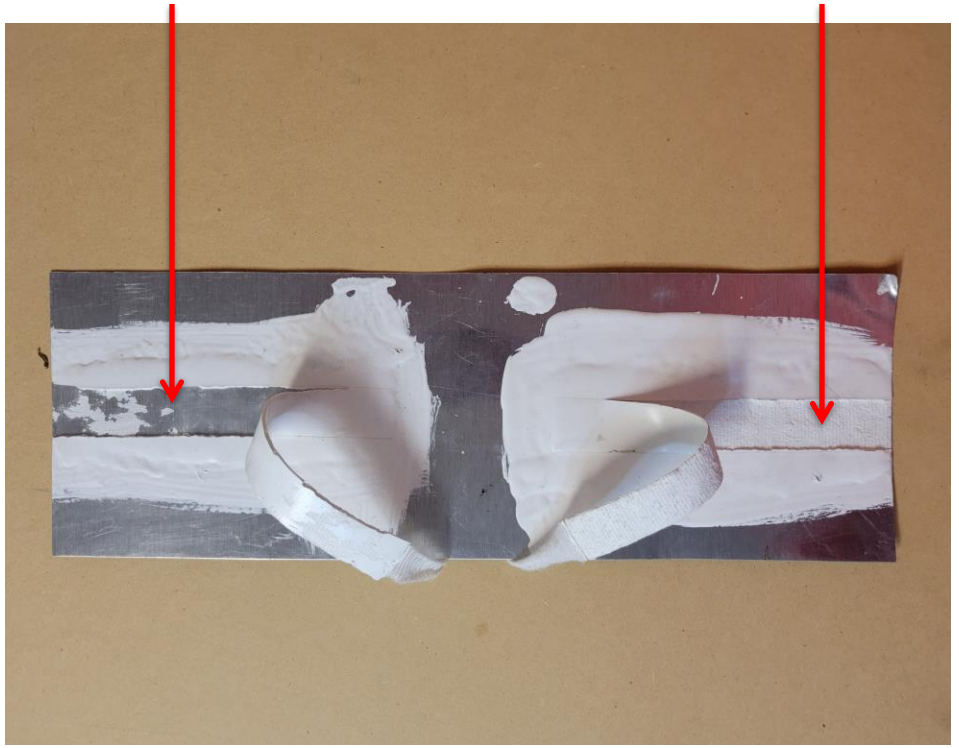

Samples Are Scored On Each Side Of The Strip And Pulled Up And Back (90-135 Degrees To The Roof) And Need To Obtain 2.0 lbs./Linear Inch Minimum Result With Cohesive Failure

Henry
A CARLISLE COMPANY

Moisture Surveys

Moisture Survey

- Infrared Scanning & Core Cut Evaluation Of Existing Roof Assembly Helps Determine Roof's Qualification For Restoration
  - If >25% Is Wet And Needs Replacement, The Roof Is Not A Candidate
  - If <25% Is Wet, Then Damaged Roof Section(s) Can Be Removed And Replaced With Like Materials


Accepted Testing Methods

- Nuclear
- Infrared
- Impedance/Capacitance
- Cores
  - Roof Map and NRCA Guidelines Required

***Not Required On Metal Roofs**





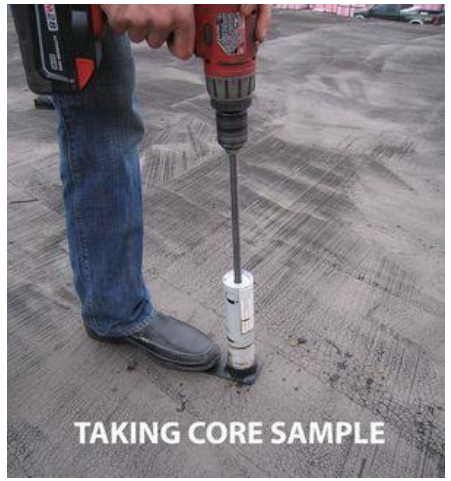





Henry
A CARLISLE COMPANY


Moisture Surveys

Drone Thermal Moisture Survey



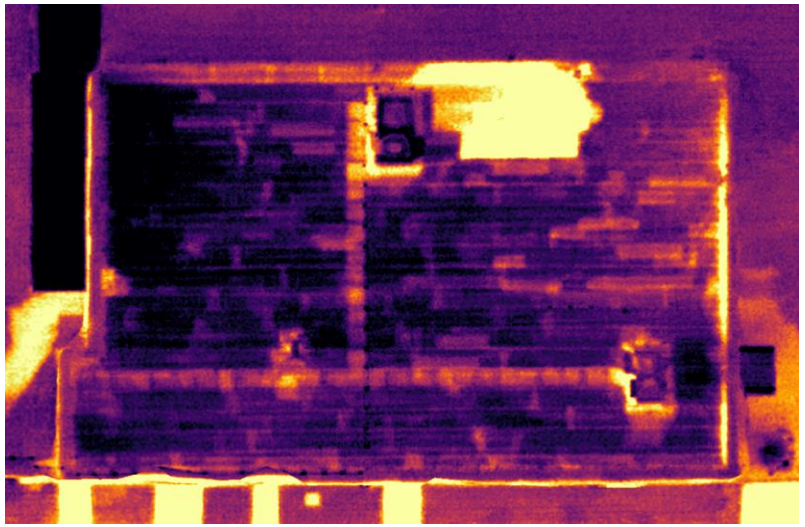

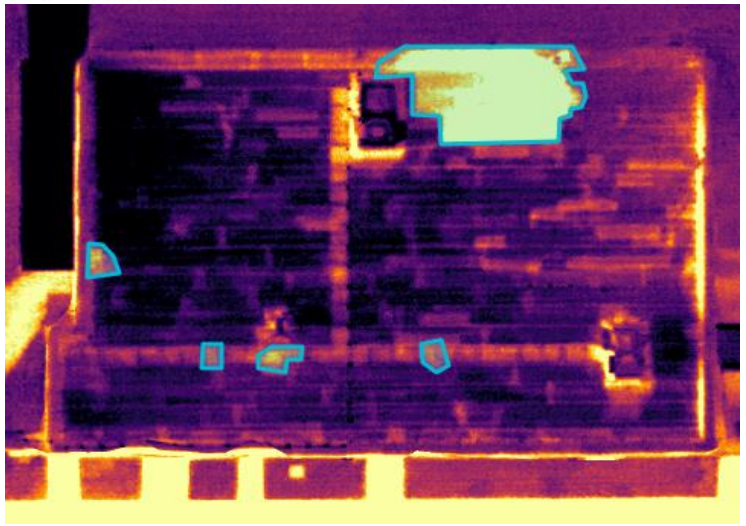

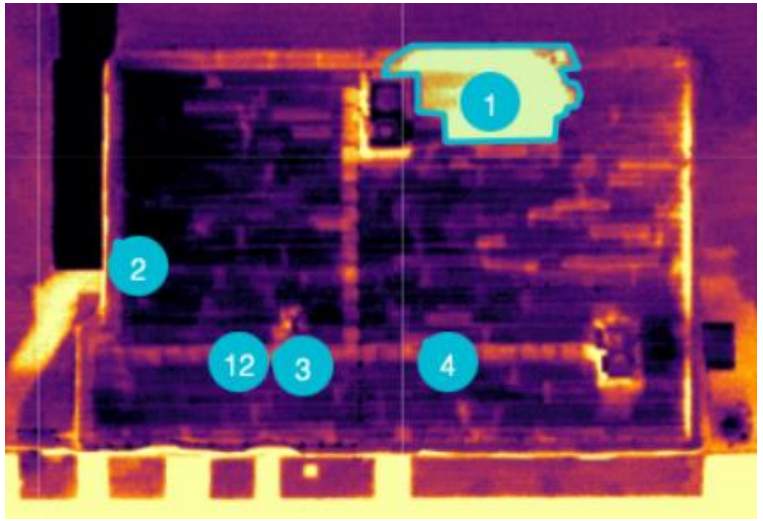

Henry
A CARLISLE COMPANY

Repairs

Repair First, Then Restore

- Remove & Replace Wet Insulation
- Remove & Replace Damaged Decking
- Infill Damaged Area With Like Roofing Materials





Prior To Restoration, The Existing Roof Must Be Brought Back To A Sound, Watertight Serviceable Condition.



Complete Line of Products
Saving Contactors Time and Money

AcryShield® Roof Coatings

Acrylic System Offering
AcryShield® 510 Topcoat
AcryShield® 505 Basecoat
AcryShield® 610 Fast-Set Topcoat
AcryShield® 605 Fast-Set Basecoat
AcryShield® 550 High Tensile Topcoat
AcryShield® 400 Elastomeric Roof Coating
AcryShield® 501 SPF Basecoat
Pro-Grade® 197 Asphalt Emulsion
Prime-Tek TPO Primer
Henry® 289 White Roof Sealant
Henry® 295 Metal Seam Sealer
Seal-Tek Micro Fibers
Henry® 195/196 Polyester Fabric



*Pro-Grade® 280 Elastomeric White Roof Coating & Pro-Grade® 294 Basecoat & Sealer available for existing specifications

Henry® A CARLISLE COMPANY

AcryShield® Topcoats

AcryShield Topcoat Options – Standard Specifications



AcryShield® 510 TC
Standard "Go-To" Premium Topcoat
Meets Codes/Approvals
5-Gal & 55-gal Drum
White, Sand, Light & Dark Gray



AcryShield® 610 FST
Premium Topcoat
Fast-Setting For Heavy Dew & Light Rain
Meets Codes/Approvals
5-Gal & 55-Gal Drum
White, Sand, Light & Dark Gray



AcryShield® 550 HT
Premium Topcoat
Highest Tensile & Elongation
Meets Codes/Approvals
Highest Reflectivity, Emissivity & SRI
5-Gal & 55-Gal Drum
White, Sand, Light & Dark Gray



AcryShield® 400 Roof Coating
Multi-Purpose Topcoat
Meets Codes/Approvals
5-Gal & 55-Gal Drum
White, Sand, Light & Dark Gray

AcryShield 250 Elastomeric Roof Coating – NEW PRODUCT



AcryShield® 250 Elastomeric Roof Coating
Economical Topcoat/Basecoat
CRRC Rated/Title 24
5-Gal, 55-gal Drum
White
No Materials Plus or Gold Seal Warranties
MATERIAL WARRANTY ONLY

AcryShield® Basecoats, Accessories and Primers

AcryShield Basecoat Options – Standard Specifications



AcryShield® 505 BC
Standard "Go-To" Basecoat
Bleed Blocker & Superior Adhesion
5-Gal & 55-gal Drum
Buff



AcryShield® 605 FSB
Fast-Setting For Heavy Dew & Light Rain
Bleed Blocker & Superior Adhesion
5-Gal & 55-Gal Drum
Buff



AcryShield® 400 Roof Coating
Bleed Blocker
5-Gal & 55-Gal Drum
White, Sand, Light & Dark Gray



Pro-Grade® 294 Basecoat & Sealer
Spec Driven With Pro-Grade 280
Bleed Blocker
5-Gal, 55-gal Drum, 275-Gal Tote
Med Gray

Henry
A CARLISLE COMPANY

Prime-Tek TPO Primer

A Low VOC Solvent-Based Primer Designed To Promote Optimal Adhesion for AcryShield Acrylics and Pro-Grade 988 Silicone to New Or Existing TPO

For Use Over:

- **TPO Only**
- **Dries Quickly**



Color: Red

Sizes:

- **5-gallon Pail**

Pro-Grade® 197 Asphalt Emulsion

A Premium, Cold-applied Protective Coating That Resists Moisture Intrusion And Levels Irregularities In Asphaltic Roof Surfaces

- Helps Extend The Existing Roof Membrane Life Cycle
- Low Odor And VOC Compliant In All Jurisdictions
- Must Be Top Coated
  - Acrylic
  - Aluminum



Color: Black

Sizes:

- 5 Gal Pail
- 55 Gal Drum
- 275 Gal Tote
- Bulk

Henry
A CARLISLE COMPANY

Henry® 295 Metal Seam Sealer

A White, SEBS Rubber-Based, Mastic-Grade, Elastomeric Sealant

- High Tensile Strength And Elongation
- Seam Movement Less Than 1/8”
  - No Fabric Required
- Can Be Coated With
  - Water Or Solvent-based Reflective Coatings
  - Aluminum Roof Coatings
- Can Be Easily Applied
  - Brush, Spray (Pumped) Or Bulk Gun Loader
- **Uses Include:**
  - **Seams**
  - **Fasteners**
  - **Penetrations**
  - **Flashings**



Color: Off White

Sizes:

- **5 Gallon Pail**

Henry® 289 White Roof Sealant

A White, Elastomeric Acrylic Patching Compound

- Applies To Dry Or Damp (Not Wet) Surfaces
- No Mixing – Ready To Use
- Skins Over Quickly
- Doesn't Bleed Trough Reflective Coatings
- Can Be Coated With
  - White Or Tinted Acrylic Coatings
- Can Be Easily Applied
  - Trowel Or Brush
  - Up To ¼" Thick Application
- **Uses Include:**
  - **Penetrations**
  - **Flashings**
  - **Drains**
  - **Seams**
  - **Fasteners**
  - **Repairs**

Color: White

Sizes:

- **3.5 Gallon Pail**
- **1 Gallon Pail**
- **10.1 Oz Cartridge**









Henry® A CARLISLE COMPANY

Henry® 195/196 Polyester Fabric

Henry 195 Polyester Fabric

- Stich bonded, High-Performance Fabric
- Soft Finish
- Conforms to Irregular Surfaces

Henry 196 Polyester Fabric

- Stich bonded, High-Performance Fabric
- Firm Finish

- Uses include:
  - Drains
  - Seams
  - Repairs

Color: Off White - White

Sizes:

- Henry 195
  - 40” x 324’ Roll
  - 12” x 300’ Roll
  - 6” x 300’ Roll
- Henry 196
  - 40” x 324’ Roll
  - 4” x 300’ Roll



Project Startup

Preparation- Cleaning

Granulated Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)

Smooth Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)



Single-Ply Roofs

- Clean With 1500-2,000 PSI Pressure Washer
  - Wash With Water Only!



Metal Roofs

- Clean With 3,000 Psi Or Greater Pressure Washer
  - Wash With Water Only!
- Air Lance (195 CFM)
- Wire Brush/Brush Blast (Metal Surfaces)



ENSURE ALL RESIDUE IS REMOVED AND ROOF IS DRY PRIOR TO SEALER OR COATING APPLICATION

Preparation- Basecoat

Asphaltic Roofs/Roofs Previously Coated with Aluminum Coating

- **AcryShield A505 Or A605 Basecoat**
  - **Roll**
  - **Squeegee and Back Roll**
  - **Spray and Back Roll**
  - **Better Spreader**



Metal Roofs

- **AcryShield A400 TC Or A605**
  - **Roll**
  - **Spray and Back Roll**
  - **Tank Spreader**



118

Preparation- The Details

- Seams
- Penetrations
- Curbs
- Terminations
- Transitions
- Parapet







90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!

119

Preparation- The Details

Asphalt/Single-Ply Roofs

- **Seam/Penetration/Drain Options**
  - **Henry 289 Roofing Sealant (Not Required for Full Fabric System)**
    - **Brush**
    - **Trowel**

Metal Roofs

- **Seam/Penetration/Fasteners**
  - **Henry 295 Metal Seam Sealer**
    - **Brush**
    - **Bulk Loader Gun**
  - **Henry 289 Roof Sealant**
    - **Brush**

90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!









120

AcryShield® Acrylic Application

Installation – Roof Grid Process

- **Measure And Mark 10’x10’ Squares On The Roof, Each Representing One Square (100 Sq.Ft.)**

Example:

If The Spec Calls For 3 Gallons/Square Of Coating, Then One 5-gallon AcryShield Will Cover 1.6 Squares. (Smooth Surfaces)

- **Granulated Mod-bit & Rough Surfaces Will Require More To Meet DFT**









122

Installation – Easy Application

Roll

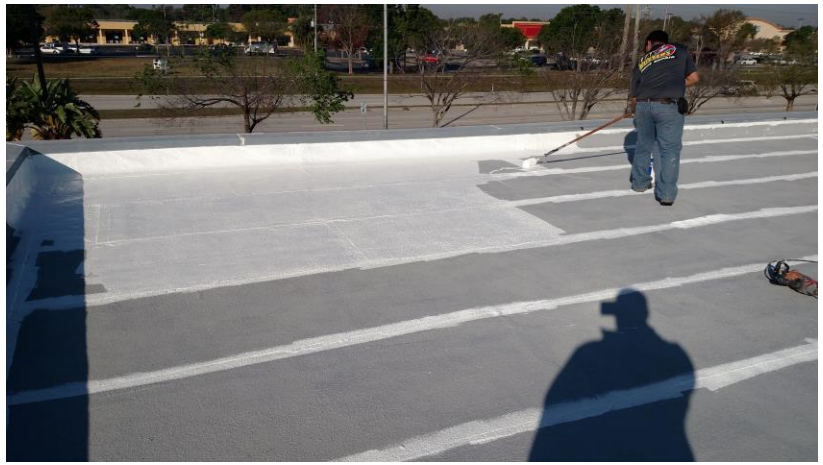



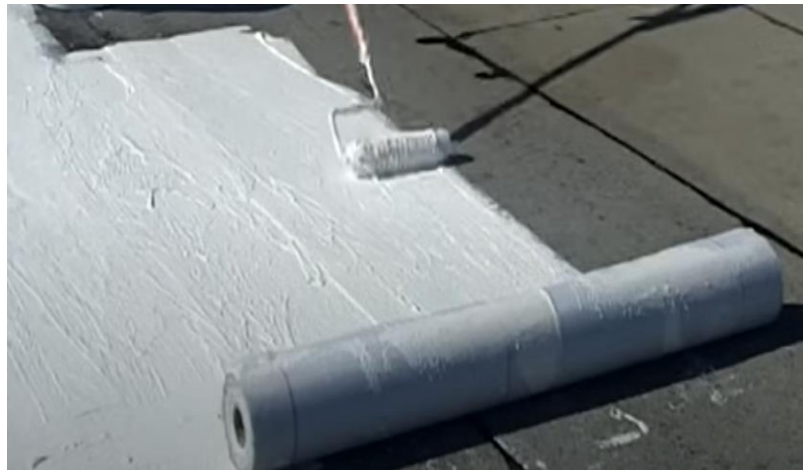

Installation – Easy Application

Squeegee and Back Roll







Installation – Easy Application

Spray and Back Roll





125

Installation – Easy Application

Tank Spreader





126

Warranty Information

Henry Warranty Program

Industry-Leading Warranty Program

Warranty Options Provide Up To 20 Years Labor, Workmanship And Materials Coverage

- Transferable And Renewable Options



AcryShield® Acrylic Warranty Options

Application guide

Henry® Acrylic Restoration & Fluid Applied Membrane Systems

This application guide provides instructions for successfully applying a Henry® acrylic roof coating system on metal, aged single ply, asphalt roofs (roll roofing, modified bitumen, built-up roofing, and spray polyurethane foam) and previously coated roofs. An acrylic roof coating system is a fluid-applied roof restoration system, supported by a variety of warranty offerings, that provides a cost-effective alternative to a full roof replacement. This application guide is not intended for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

Acrylic Restoration System Warranty installation options

10-year Acrylic Restoration Warranty								
		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Metal	Aged or 1" new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.06/sq. ft $900 min.
BC	AcryShield® Base Coat 400 505, or 605 501 for SPF applications; or Pro-Grade 280 Acrylic**	15 mils DFT min. 1.75 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	32 mils DFT min. 3.75 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq		

PC Primer coat BC Base coat TC Top coat

Acrylic Restoration System Warranty installation options

10-year Acrylic Restoration Warranty								
		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Metal	Aged or 1" new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.06/sq. ft $900 min.
BC	AcryShield® Base Coat 400 505, or 605 501 for SPF applications; or Pro-Grade 280 Acrylic**	15 mils DFT min. 1.75 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	32 mils DFT min. 3.75 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq		

PC Primer coat BC Base coat TC Top coat

15-year Acrylic Restoration Warranty								
		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO,PVC, EPDM)	Metal	Aged or 1.5" new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.08/sq. ft $1200 min.
BC	AcryShield Base Coat 400, 505, or 605; 501 for SPF applications; or Pro-Grade 280 Acrylic**	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
	Total (min. thickness)	34 mils DFT min 4 gal/sq	30 mils DFT min. 3.5 gal/sq	30 mils DFT min. 3.5 gal/sq	30 mils DFT min. 3.5 gal/sq	30 mils DFT min. 3.5 gal/sq		

AcryShield® Acrylic Warranty Options

Application guide

Henry® Acrylic Restoration & Fluid Applied Membrane Systems

This application guide provides instructions for successfully applying a Henry® acrylic roof coating system on metal, aged single ply, asphalt roofs (roll roofing, modified bitumen, built-up roofing, and spray polyurethane foam) and previously coated roofs. An acrylic roof coating system is a fluid-applied roof restoration system, supported by a variety of warranty offerings, that provides a cost-effective alternative to a full roof replacement. This application guide is not intended for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

Acrylic Restoration System Warranty installation options

10-year Acrylic Restoration Warranty

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Metal	Aged or 1" new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.06/sq. ft $900 min.
BC	AcryShield® Base Coat 400 505, or 605 501 for SPF applications; or Pro-Grade 280 Acrylic**	15 mils DFT min. 1.75 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	32 mils DFT min. 3.75 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq		

PC Primer coat BC Base coat TC Top coat

20-year Acrylic Restoration Warranty*

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO,PVC, EPDM)	Metal	Aged or 1.5" new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.10/sq. ft $1500 min.
BC	AcryShield Base Coat 400, 505, or 605; 501 for SPF applications; or Pro-Grade 280 Acrylic**	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC1	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC2	AcryShield Top Coat 400, 510, 550 HT, 610; or Pro-Grade 280 Acrylic	13 mils DFT min. 1.5 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
	Total (min. thickness)	47 mils DFT min. 5.5 gal/sq	43 mils DFT min. 5 gal/sq	43 mils DFT min. 5 gal/sq	43 mils DFT min. 5 gal/sq	43 mils DFT min. 5 gal/sq		

NOTES:
* Most likely will require 3 coats
** When using Pro-Grade 280, Pro-Grade 294 can be used as a base coat; excluding SPF and single ply applications. Follow the appropriate Pro-Grade 280 Guide Specification.
For cold storage or cryogenic structures, please contact your Henry Technical Representative.

DFT = Dry Film Thickness (minimum requirement).
Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc.
For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.

130

AcryShield® Acrylic Warranty Options

Application guide

Henry® Acrylic Restoration & Fluid Applied Membrane Systems

This application guide provides instructions for successfully applying a Henry® acrylic roof coating system on metal, aged single ply, asphalt roofs (roll roofing, modified bitumen, built-up roofing, and spray polyurethane foam) and previously coated roofs. An acrylic roof coating system is a fluid-applied roof restoration system, supported by a variety of warranty offerings, that provides a cost-effective alternative to a full roof replacement. This application guide is not intended for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

Acrylic Restoration System Warranty installation options

10-year Acrylic Restoration Warranty

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Metal	Aged or 1* new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.06/sq. ft $900 min.
BC	AcryShield® Base Coat 400 505, or 605 501 for SPF applications; or Pro-Grade 280 Acrylic**	15 mils DFT min. 1.75 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	32 mils DFT min. 3.75 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq		

PC Primer coat BC Base coat TC Top coat

Acrylic Fluid Applied Membrane System Warranty installation options

10-year Acrylic Fluid Applied Membrane System Warranty

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Warranty Cost	
					Material Plus	Gold Seal
PC		As Required	As Required	As Required	No cost	0.06/sq. ft $900 min.
BC	AcryShield Base Coat 400*, 505, or 605 Applications	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
RL	Henry 195 or 196 Polyester Fabric	Reinforcement Layer	Reinforcement Layer	Reinforcement Layer		
MC	AcryShield Top Coat 510, 550 HT and 610	17 mils DFT min. 2 gal/sq	8 mils DFT min. 1 gal/sq	8 mils DFT min. 1 gal/sq		
TC	AcryShield Top Coat 510, 550 HT and 610	15 mils DFT min. 1.75 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	49 mils DFT min. 5.75 gal/sq	38 mils DFT min 4.5 gal/sq	38 mils DFT min 4.5 gal/sq		

15-year Acrylic Fluid Applied Membrane System Warranty

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Warranty Cost	
					Material Plus	Gold Seal
PC		As Required	As Required	As Required	No cost	0.08/sq. ft $1200 min.
BC	AcryShield Base Coat 400*, 505, or 605 Applications	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
RL	Henry 195 or 196 Polyester Fabric	Reinforcement Layer	Reinforcement Layer	Reinforcement Layer		
MC	AcryShield Top Coat 510, 550 HT and 610	17 mils DFT min. 2 gal/sq	8 mils DFT min. 1 gal/sq	8 mils DFT min. 1 gal/sq		
T1C	AcryShield Top Coat 510, 550 HT and 610	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC2	AcryShield Top Coat 510, 550 HT and 610	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	60 mils DFT min. 7.0 gal/sq	51 mils DFT min 6.0 gal/sq	51 mils DFT min 6.0 gal/sq		

PC Primer coat BC Base coat TC Top coat RL Reinforcement Layer MC Mid coat S Sealant

131

AcryShield® Acrylic Warranty Options

Application guide

Henry® Acrylic Restoration & Fluid Applied Membrane Systems

This application guide provides instructions for successfully applying a Henry® acrylic roof coating system on metal, aged single ply, asphalt roofs (roll roofing, modified bitumen, built-up roofing, and spray polyurethane foam) and previously coated roofs. An acrylic roof coating system is a fluid-applied roof restoration system, supported by a variety of warranty offerings, that provides a cost-effective alternative to a full roof replacement. This application guide is not intended for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

Acrylic Restoration System Warranty installation options

10-year Acrylic Restoration Warranty

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Metal	Aged or 1ª new PremiR+ EVO SPF	Warranty Cost	
							Material Plus	Gold Seal
PC		As Required	As Required	As Required	As Required	As Required	No cost	0.06/sq. ft $900 min.
BC	AcryShield® Base Coat 400 505, or 605 501 for SPF applications; or Pro-Grade 280 Acrylic**	15 mils DFT min. 1.75 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield Top Coat 400, 510, 550 HT and 610; or Pro-Grade 280 Acrylic	17 mils DFT min. 2 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	32 mils DFT min. 3.75 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq	26 mils DFT min 3 gal/sq		

PC Primer coat BC Base coat TC Top coat

20-year Acrylic Fluid Applied Membrane System Warranty**

		Granulated Cap Sheet	Smooth Cap/BUR (non-aggregate)	Single Ply (TPO, PVC, EPDM)	Warranty Cost	
					Material Plus	Gold Seal
PC		As Required	As Required	As Required	No cost	0.10/sq. ft $1500 min.
BC	AcryShield Base Coat 400*, 505, or 605 Applications	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
RL	Henry 195 or 196 Polyester Fabric	Reinforcement Layer	Reinforcement Layer	Reinforcement Layer		
MC	AcryShield Top Coat 510, 550 HT and 610	17 mils DFT min. 2 gal/sq	8 mils DFT min. 1 gal/sq	8 mils DFT min. 1 gal/sq		
T1C	AcryShield Top Coat 510, 550 HT and 610	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
TC2	AcryShield Top Coat 510, 550 HT and 610	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq	17 mils DFT min. 2 gal/sq		
	Total (min. thickness)	68 mils DFT min. 8 gal/sq	59 mils DFT min 7 gal/sq	59 mils DFT min 7 gal/sq		

Ancillary components for all warranted assemblies

Application			Product name	Product description	Coverage rate
Metal seams, fasteners and defects		S	Henry® 295 Metal Seam Sealer or Henry 289	Metal seam sealer	Varies by application
MB/BUR fasteners/ defects	Option #1	S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application
	Option #2		HE 195 Polyester Fabric	Reinforcement fabric	300 linear feet per 6" x 300' roll
Single Ply fasteners/defects		S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application
MB/BUR cap sheet and Single Ply seams	Option #1	S	Henry® 289 White Roofing Sealant	Roofing sealant	37.5 linear feet per gallon applied at ⅛" thick and 4" wide 25 linear feet per gallon applied at ⅛" thick and 6" wide
	Option #2	S	Seal-Tek Micro Fibers	Fibered roofing sealant	****see mixing guide on TDS
	Option #3	S	Fully Reinforced System Not Required	n/a	n/a

PC Primer coat BC Base coat TC Top coat RL Reinforcement Layer MC Mid coat S Sealant

NOTES:
* AcryShield 400 can be used as a top coat on material only warranty applications
** Most likely will require 3 coats
*** Total thickness to be must be achieved but you must give consideration to temperature and humidity levels during the time of application for curing and application coats.
**** Seal-Tek Micro-Fibers can be utilized for fasteners/defects in lieu of 289; consult Henry Technical Representatives for more information.

DFT = Dry Film Thickness (minimum requirement).
Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc.
For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.
Reinforcement layer will add approximately 8-13 mils to the total DFT listed in each application.

Henry Pro-Grade® Aluminum Restoration System

Building Confidence™

© 2022 Henry Company. All rights reserved.

Facts About Aluminums

- Primerless Application
- Can Be Applied To Tight Rust
- Reflective
- Easy To Apply
  - Brush, Roll, Spray
- Cost Efficient
- 40 Deg F And Rising Application Temperature
- Easy To Recoat





Aluminum Roof Coating Cons

- Ponding Water Resistance
  - Acts Like An Acrylic
- Less Reflective Than a “White Coating”
- Hard To Mix
  - Aluminum Brick At Bottom Of Bucket
- Not For Use On
  - Single-Ply
  - SPF
- High VOCs
  - Typically, Solvent-Based



When Is Aluminum A Good Fit?

- Metal Roofs
- Tightly Adhered Rusted Metal Roofs
- Flat Roofs*
- Minimal Disruption
- Most Cost-Effective Solution





*Areas That Have Positive Drainage (Minimal Ponding Water)

136

When Is Aluminum Not A Good Fit?

- Ponding Water Areas
- Flat Roofs*
- Single-Ply & SPF Roofs
- Needing Maximum UV Protection
- High-Foot Traffic Areas






*Little To No Positive Drainage

137

What Types Of Roofs Can We Restore?

What Types of Roofs Can We Restore?

Asphaltic

Granulated/Smooth Modified Bitumen



BUR



139

What Types of Roofs Can We Restore?

Metal



140


What Types of Roofs Can We Restore?

Previously Coated Acrylic and Aluminum Substrates







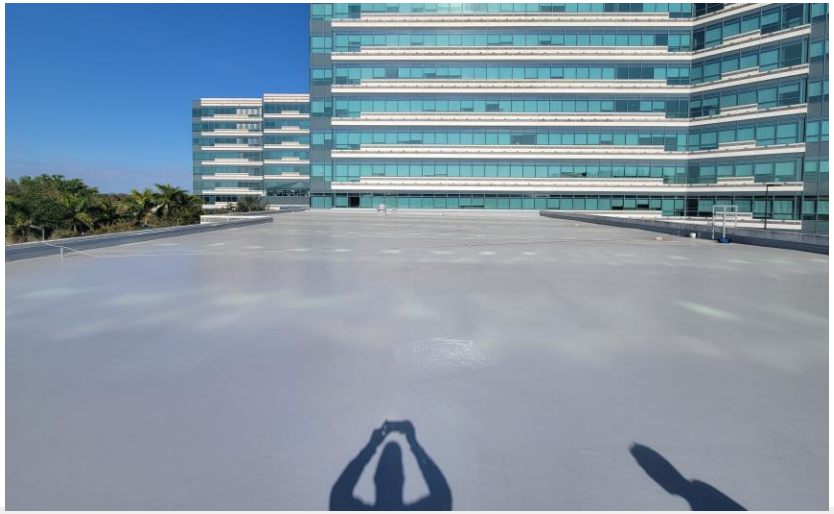

141

What Types of Roofs Can We Restore?

Tar & Gravel



142

Pro-Grade® Aluminum Restoration Process

The Restoration Process- Warranted Systems

- Visual Roof Inspection
  - If Required
- Adhesion Testing
  - If Required
- Moisture Survey
  - If Required
- Roof Repairs
- Restore
- Final Inspection
  - If Required

Visual Roof Inspection

- **Preferably By Henry Representative**
  - **No Charge**
  - **Need Roof Access**












Henry
A CARLISLE COMPANY


Adhesion Testing – Aluminum Coatings


Conduct ASTM D3359 Tape Test

- Metal
- Smooth Asphalt MB/BUR
- Previously Coated Surfaces

- Slice Existing Coating In An X-cut
- Fully Adhere Semitransparent Pressure Sensitive Tape Over X-cut Intersection
- Remove Tape By Pulling Rapidly Back Over Itself At A 180º Angle
- Adhesion Results Indicating Removal Of Coating Are Not Acceptable

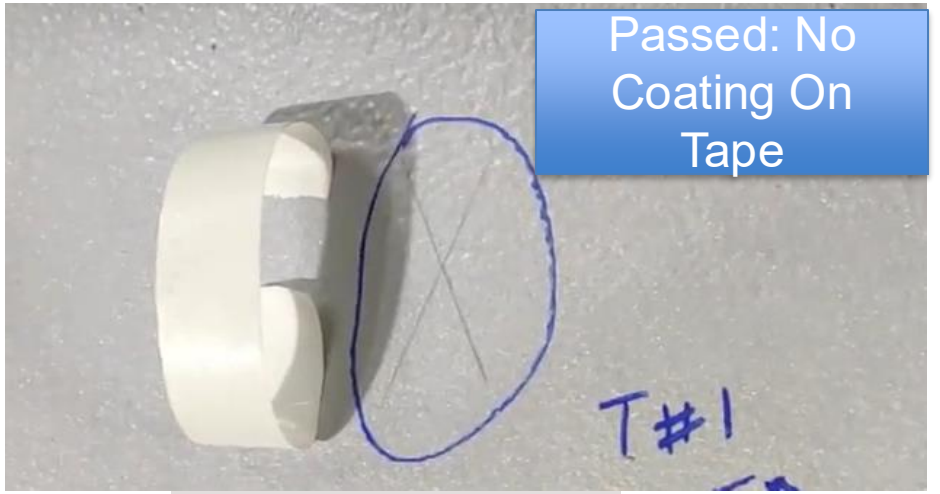

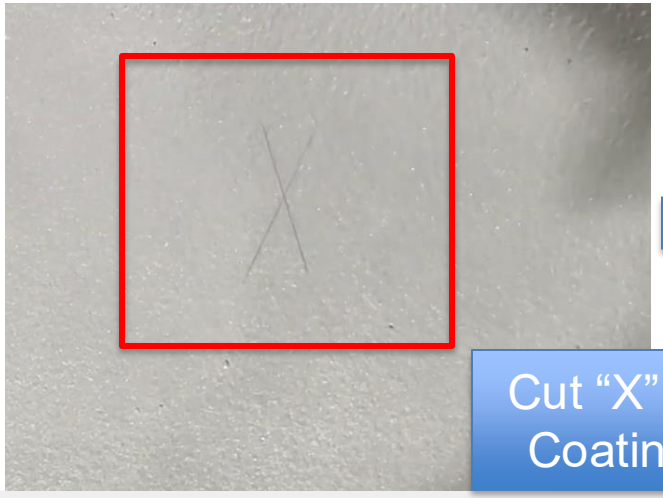

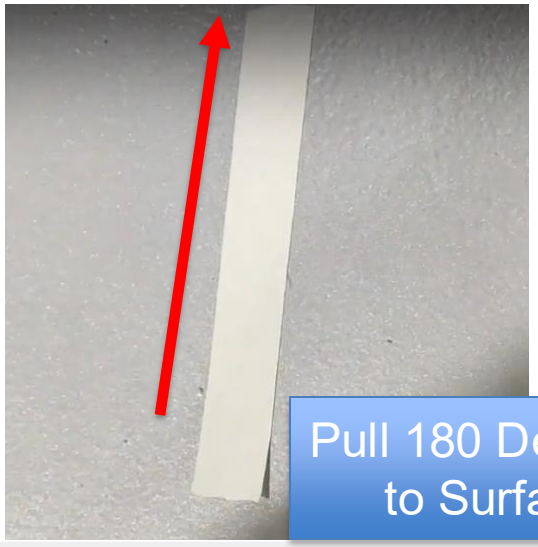




Moisture Surveys

Moisture Survey

- Infrared Scanning & Core Cut Evaluation Of Existing Roof Assembly Helps Determine Roof's Qualification For Restoration
  - If >25% Is Wet And Needs Replacement, The Roof Is Not A Candidate
  - If <25% Is Wet, Then Damaged Roof Section(s) Can Be Removed And Replaced With Like Materials





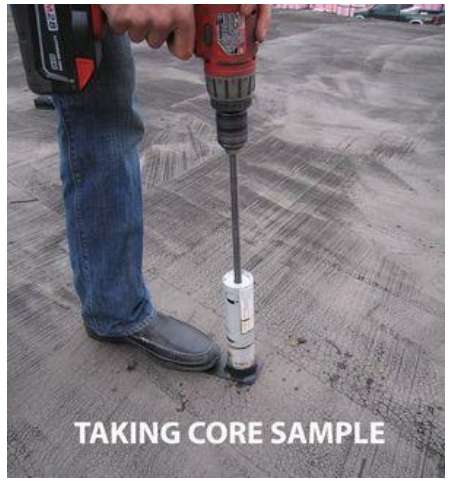



Accepted Testing Methods


- Nuclear
- Infrared
- Impedance/Capacitance
- Cores
  - Roof Map and NRCA Guidelines Required


***Not Required On Metal Roofs**


Henry
A CARLISLE COMPANY


Moisture Surveys

Drone Thermal Moisture Survey

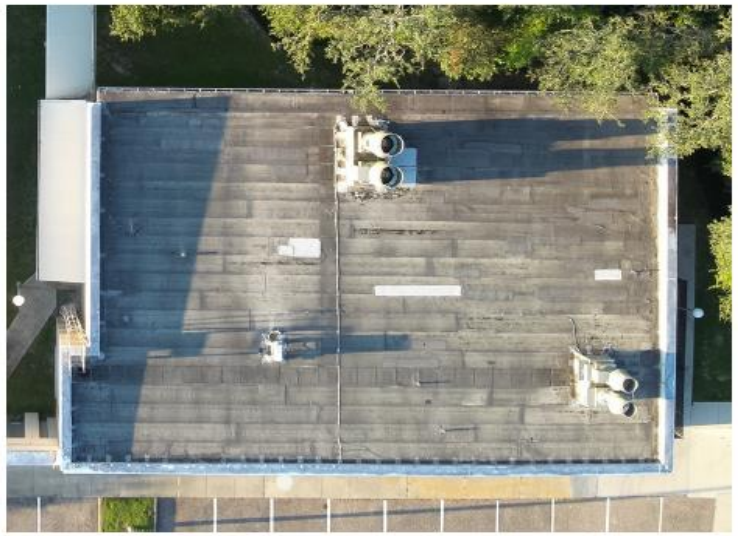

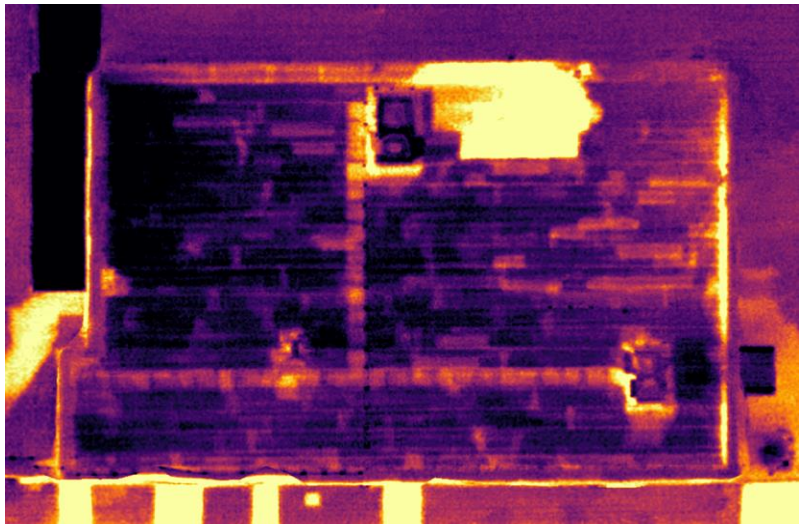

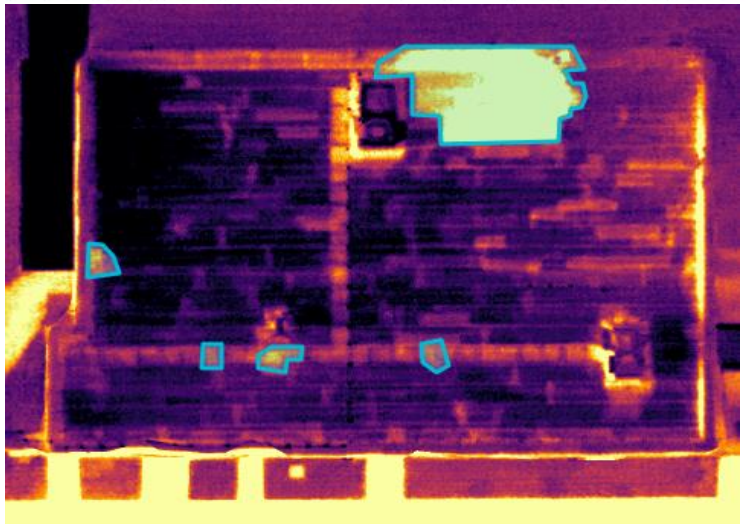

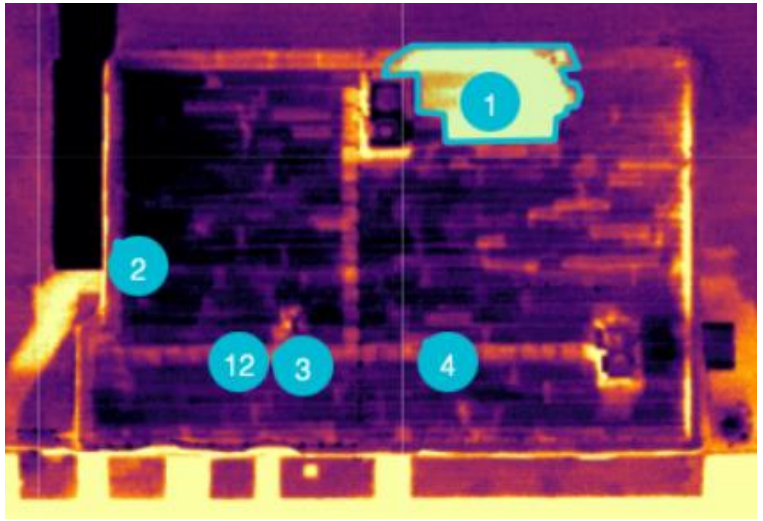

Henry
A CARLISLE COMPANY

Repairs

Repair First, Then Restore

- Remove & Replace Wet Insulation
- Remove & Replace Damaged Decking
- Infill Damaged Area With Like Roofing Materials

Prior To Restoration, The Existing Roof Must Be Brought Back To A Sound, Watertight Serviceable Condition.







Complete Line of Products
Saving Contactors Time and Money

Henry Pro-Grade® Aluminum Roof Coatings

Aluminum System Offering
Pro-Grade® 599 Rubberized Aluminum Roof Coating
Pro-Grade® 586 Aluminum Roof Coating
Pro-Grade® 588 WB Aluminum Roof Coating
Pro-Grade® 197 Asphalt Emulsion
Henry® 295 Metal Seam Sealer
Pro-Grade® 167 Extreme Rubberized Flashing Cement
Henry® 289 White Roof Sealant
Henry® 195/196 Polyester Fabric
Henry® 183 Yellow Fiberglass Repair Fabric



Henry®
A CARLISLE COMPANY

Pro-Grade® Aluminum Roof Coatings

BEST BETTER GOOD

Henry Pro-Grade 599 Rubberized Aluminum Roof Coating - Solvent-based



- One-coat application – no primer required
- Excellent flexibility
- Helps extend the existing roof membrane life cycle
- Helps lower interior temperatures as well as energy costs
- Restoration System installation qualifies for up to 12-Year Material, Labor & Workmanship Henry Gold Seal Warranty

Coverage: 1.5 - 2.5 gallons/square
Sizes available: 5 gallon pail and 50 gallon drum

Pro-Grade® 586 Fibered Aluminum Roof Coating



- Resists moisture intrusion and levels irregularities in asphaltic roof surfaces
- Helps extend the existing roof membrane life cycle
- Low odor and VOC compliant in all jurisdictions
- Restoration System installation qualifies for up to a 12-Year Material, Labor & Workmanship Henry Gold Seal Warranty

Coverage: 1.5 - 2.5 gallons/square
Sizes available: 5 gallon pail and 50 gallon drum

Pro-Grade® 588 Aluminum WB Roof Coating



- Resists moisture intrusion and levels irregularities in asphaltic roof surfaces
- Helps extend the existing roof membrane life cycle
- Low odor and VOC compliant in all jurisdictions
- Restoration System installation qualifies for up to a 12-Year Material, Labor & Workmanship Henry Gold Seal Warranty

Coverage: 1.5 gallons/square
Sizes available: 5 gallon pail, 50 gallon drum and 250 gallon tote

152

Pro-Grade® 588 Aluminum Roof Coating

Combination Of Premium Aluminum Flakes Suspended In Emulsified Asphalt Provides Outstanding Weathering Resistance And Reflectance.



- Professional Grade Water-Based, Fibered Aluminum Roof Coating
- Low VOC
- For Use in Southern California
- UL, CRRC and Energy Star Rated

Color: Silver

Sizes:

- **5-gallon Pail**
- **50-gallon Drum**

153

Pro-Grade® 586 Aluminum Roof Coating

Premium Fibered Aluminum Coating For New Or Aged Smooth Surface BUR, Modified Bitumen Membranes, Aged Galvanized Metal Roofs And New Asphalt Emulsion That Forms A Tough, Brilliant Reflective Surfacing.



- Professional Grade Fire-Rated, Fibered Aluminum Roof Coating
- Solvent-Based
- 1-Coat Application
- UL, FM, CRRC, Miami-Dade and Energy Star Rated

Color: Silver

Sizes:

- **5-gallon Pail**
- **50-gallon Drum**

154

Pro-Grade® 599 Aluminum Roof Coating

A Premium, Highly Reflective Coating Made With SBS Rubber Polymers, Which Provides Outstanding Strength And Elastic Properties. It Is An Excellent Weathering Surfacing For New Or Aged Asphalt Roof Surfaces Including Smooth BUR, Modified Bitumen Membranes And Metal Roofs.



- Professional Grade SBS Rubberized, Aluminum Roof Coating
- Good Ponding Water Resistance
- Solvent-Based
- 1-Coat Application
- CRRC, Miami-Dade and Energy Star Rated (Low and Steep Slope)

Color: Silver

Sizes:

- **5-gallon Pail**
- **50-gallon Drum**

155

Why Pro-Grade® Aluminum Roof Coatings?

- Soft-pack Technology For Reduced Mixing Time
- Primerless Applications
- Paint-Quality Aluminum Paste
- Can Be Applied Over Tight Rust
- Fills In “Alligatoring”
- Also, An Ideal Fit In Northern Climates – Holds In Winter Heat
- One-Coat Economical Application
- Stops Pinhole-Sized Leaks







156

Pro-Grade® Aluminum Accessories

Pro-Grade® 197 Asphalt Emulsion

A Premium, Cold-applied Protective Coating That Resists Moisture Intrusion And Levels Irregularities In Asphaltic Roof Surfaces

- Helps Extend The Existing Roof Membrane Life Cycle
- Low Odor And VOC Compliant In All Jurisdictions
- Must Be Top Coated
  - Acrylic
  - Aluminum



Color: Black

Sizes:

- 5 Gal Pail
- 55 Gal Drum
- 275 Gal Tote
- Bulk

Henry
A CARLISLE COMPANY

Pro-Grade® 167 Extreme Rubberized Flashing Cement

A Superior, Rubberized Roof Cement For All Applications And Permanent Repairs.

- Apply In Wet Or Dry Weather Conditions
- Contains UV Inhibitors And SEBS Rubber For Enhanced Durability
- Installation Temperature Range (Ambient): -20º F To 140º F

Compliance:

- Meets Or Exceeds ASTM D4586
- 100% Underwater Adhesion Per ASTM D3409
- Miami-Dade County Approved

Color: Black

Sizes:

- **1-gallon Can**
- **3-gallon Pail**







Henry® 295 Metal Seam Sealer

A White, SEBS Rubber-Based, Mastic-Grade, Elastomeric Sealant

- High Tensile Strength And Elongation
- Seam Movement Less Than 1/8”
  - No Fabric Required
- Can Be Coated With
  - Water Or Solvent-based Reflective Coatings
  - Aluminum Roof Coatings
- Can Be Easily Applied
  - Brush, Spray (Pumped) Or Bulk Gun Loader
- **Uses Include:**
  - **Seams**
  - **Fasteners**
  - **Penetrations**
  - **Flashings**



Color: Off White

Sizes:

- **5 Gallon Pail**

Henry® 289 White Roof Sealant

A White, Elastomeric Acrylic Patching Compound

- Applies To Dry Or Damp (Not Wet) Surfaces
- No Mixing – Ready To Use
- Skins Over Quickly
- Doesn't Bleed Trough Reflective Coatings
- Can Be Coated With
  - White Or Tinted Acrylic Coatings
- Can Be Easily Applied
  - Trowel Or Brush
  - Up To ¼" Thick Application
- **Uses Include:**
  - **Penetrations**
  - **Flashings**
  - **Drains**
  - **Seams**
  - **Fasteners**
  - **Repairs**
- **Color: White**
- **Sizes:**
  - **3.5 Gallon Pail**
  - **1 Gallon Pail**
  - **10.1 Oz Cartridge**









Henry® A CARLISLE COMPANY

Henry® 195/196 Polyester Fabric

Henry 195 Polyester Fabric

- Stich bonded, High-Performance Fabric
- Soft Finish
- Conforms to Irregular Surfaces

Henry 196 Polyester Fabric

- Stich bonded, High-Performance Fabric
- Firm Finish

- Uses include:
  - Drains
  - Seams
  - Repairs

Color: Off White - White

Sizes:

- Henry 195
  - 40” x 324’ Roll
  - 12” x 300’ Roll
  - 6” x 300’ Roll
- Henry 196
  - 40” x 324’ Roll
  - 4” x 300’ Roll



Henry® 183 Yellow Fiberglass Repair Fabric

A Yellow Resin Coated Glass Fabric Woven Fabric Made Of Yarns Of Inert, Flexible Filaments Of Pure Glass

- Acid & Heat Resistant
- Won't Rot Or Decay
- Compatible
  - Asphalt
  - Emulsions
  - Coatings
- Uses Include:
  - Penetrations
  - Flashings
  - Seams
  - Repairs

- Sizes:
  - 4" X 150' Roll
  - 6" X 25' Roll
  - 36" X 150' Roll



Henry® A CARLISLE COMPANY

Project Startup

Preparation- Cleaning

Granulated Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)

Smooth Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)



Metal Roofs

- Clean With 3,000 Psi Or Greater Pressure Washer
  - Wash With Water Only!
- Air Lance (195 CFM)
- Wire Brush/Brush Blast (Metal Surfaces)





ENSURE ALL RESIDUE IS REMOVED AND ROOF IS DRY PRIOR TO SEALER OR COATING APPLICATION

165

Preparation- The Details

- Seams
- Penetrations
- Curbs
- Terminations
- Transitions
- Parapet





90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!



Preparation- The Details

Asphalt Roofs

- **Seam/Penetration/Drain Options**
  - **Pro-Grade 197 With HE 195 Fabric (Not Required for Full Fabric or Emulsion System)**
    - **Brush**
    - **Roll**
    - **Spray**
  - **Pro-Grade 167 with HE 183 Yellow Fabric**
    - **Brush**
    - **Trowel**





Metal Roofs

- **Seam/Penetration/Fastener Options**
  - **Henry 295 Metal Seam Sealer**
    - **Brush**
    - **Bulk Loader Gun**
  - **Henry 289 Roof Sealant***
    - **Brush**



90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!

* **Where HE295 doesn't meet VOC Requirements**

167

Pro-Grade® Aluminum Application

Installation – Roof Grid Process

- **Measure And Mark 10’x10’ Squares On The Roof, Each Representing One Square (100 Sq.Ft.)**

Example:

If The Spec Calls For 2.5 Gallons/Square Of Coating, Then One 5-gallon Pail Of Pro-Grade Aluminum Will Cover 2 Squares. (Smooth Surfaces)

- **Granulated Mod-Bit & Rough Surfaces Will Cover Less And Require More To Meet DFT**







169

Installation – Easy Application

Roll/Brush







Installation – Easy Application

Spray and Back Roll





171

Installation – Easy Application

Tank Spreader





172

Warranty Information

Henry Warranty Program

Industry-Leading Warranty Program

Warranty Options Provide Up To 12 Years Labor, Workmanship And Materials Coverage

- Transferable And Renewable Options



174

Henry Pro-Grade® Aluminum Warranty Options

Henry.

Warranty program

Henry® Pro-Grade® Aluminum Roof Coating System

A roof restoration system from Henry®, Pro-Grade® Aluminum high performance roof coating system extends the life cycle of your roof, resulting in a cost-effective alternative to a full replacement.

Warranty Options from Henry®
-Choose your desired level of warranty protection to meet your needs: Material Plus or Gold Seal.
-Both options can be available when installation is in compliance with the information below.

Material Plus Warranty
This warranty option provides material and labor coverage at no charge during the applicable warranty term to repair the affected roof area when product manufacturing defects have been determined. Product(s) must be installed by a Material Plus or Gold Seal Authorized Contractor.

Gold Seal Warranty
This warranty option provides material and labor to repair the affected area when product defects or workmanship installation deficiencies have been determined. Product(s) must be installed by a Gold Seal Authorized Contractor.

Warranty installation options

10-year Pro-Grade® Aluminum roof coating system							
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal*	Warranty cost	
						Material Plus	Gold Seal
Option #1	TC	Pro-Grade® 586	2.50 gal./sq. 20 mil DFT	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT	No cost	$.10/SF $1,000 minimum
Option #2	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.10/SF $1,000 minimum
	TC	Pro-Grade® 586	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT			
California only	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.10/SF $1,000 minimum
	TC	Pro-Grade® 588	2.00 gal./sq. 7 mil DFT	2.00 gal./sq. 7 mil DFT			

12-year Pro-Grade® Aluminum roof coating system							
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal*	Warranty cost	
						Material Plus	Gold Seal
Option #1	FC	Pro-Grade® 197**	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	R	195 Polyester Fabric	Reinforcement	Reinforcement			
	FC	Pro-Grade® 197	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT			
	TC	Pro-Grade® 586	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT			
Option #2	TC	Pro-Grade® 599	2.50 gal./sq. 17 mil DFT	2.00 gal./sq. 14 mil DFT	2.00 gal./sq. 14 mil DFT	No cost	$.12/SF $1,200 minimum
Option #3	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	TC	Pro-Grade® 599	2.00 gal./sq. 14 mil DFT	2.00 gal./sq. 14 mil DFT			
California only	FC	Pro-Grade® 197**	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	R	195 Polyester Fabric	Reinforcement	Reinforcement			
	FC	Pro-Grade® 197	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT			
	TC	Pro-Grade® 588	2.50 gal./sq. 9 mil DFT	2.50 gal./sq. 9 mil DFT			

FC Foundation coat TC Top coat R Reinforced coating

NOTES:
* For slopes greater than 3:12, contact Henry® Technical Support or the local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area.
** Recommended when existing roof surface is "alligatored" or heavily textured. Refer to Pro-Grade® 197 TDS and appropriate HRS Guide Specification for application information.

DFT = Dry Film Thickness (minimum requirement).
Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.

Warranty installation options

10-year Pro-Grade® Aluminum roof coating system							
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal*	Warranty cost	
						Material Plus	Gold Seal
Option #1	TC	Pro-Grade® 586	2.50 gal./sq. 20 mil DFT	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT	No cost	$.10/SF $1,000 minimum
Option #2	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.10/SF $1,000 minimum
	TC	Pro-Grade® 586	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT			
California only	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.10/SF $1,000 minimum
	TC	Pro-Grade® 588	2.00 gal./sq. 7 mil DFT	2.00 gal./sq. 7 mil DFT			

12-year Pro-Grade® Aluminum roof coating system							
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal*	Warranty cost	
						Material Plus	Gold Seal
Option #1	FC	Pro-Grade® 197**	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	R	195 Polyester Fabric	Reinforcement	Reinforcement			
	FC	Pro-Grade® 197	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT			
	TC	Pro-Grade® 586	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT			
Option #2	TC	Pro-Grade® 599	2.50 gal./sq. 17 mil DFT	2.00 gal./sq. 14 mil DFT	2.00 gal./sq. 14 mil DFT	No cost	$.12/SF $1,200 minimum
Option #3	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	TC	Pro-Grade® 599	2.00 gal./sq. 14 mil DFT	2.00 gal./sq. 14 mil DFT			
California only	FC	Pro-Grade® 197**	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	R	195 Polyester Fabric	Reinforcement	Reinforcement			
	FC	Pro-Grade® 197	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT			
	TC	Pro-Grade® 588	2.50 gal./sq. 9 mil DFT	2.50 gal./sq. 9 mil DFT			

FC Foundation coat TC Top coat R Reinforced coating

NOTES:
* For slopes greater than 3:12, contact Henry® Technical Support or the local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area.
** Recommended when existing roof surface is "alligatored" or heavily textured. Refer to Pro-Grade® 197 TDS and appropriate HRS Guide Specification for application information.

DFT = Dry Film Thickness (minimum requirement).
Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.

Henry Pro-Grade® Aluminum Application Guide

Application guide

Henry® Pro-Grade® Aluminum Roof Coating System

This application guide provides instructions for successfully applying a Henry® Pro-Grade® Aluminum roof coating system* on metal, asphalt roofs (roll roofing, modified bitumen and built-up roofing) and previously coated roofs. A Pro-Grade® Aluminum roof coating system* is a roof restoration system providing a cost-effective alternative to a full replacement. When installed according to these instructions, it is designed to provide a fluid applied roofing system supported by a variety of warranty offerings. This application guide is not intended for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

FC Foundation Coat TC Top coat S Sealant RC Reinforced coating RM Reinforced mastic

Coverage rates

Coating assembly configuration			Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal****
10-year Pro-Grade® Aluminum roof coating system options					
Option #1	TC	Pro-Grade® 586	2.50 gal./sq. (20 mil DFT)	2.00 gal./sq. (16 mil DFT)	2.00 gal./sq. (16 mil DFT)
Option #2	FC	Pro-Grade® 197***	5.00 gal./sq. (32 mil DFT)	4.00 gal./sq. (25 mil DFT)	n/a
	TC	Pro-Grade® 586	2.00 gal./sq. (16 mil DFT)	2.00 gal./sq. (16 mil DFT)	n/a
California only	FC	Pro-Grade® 197***	5.00 gal./sq. (32 mil DFT)	4.00 gal./sq. (25 mil DFT)	n/a
	TC	Pro-Grade® 588	2.00 gal./sq. (17 mil DFT)	2.00 gal./sq. (7 mil DFT)	n/a
12-year Pro-Grade® Aluminum roof coating system* options					
Option #1	FC	Pro-Grade® 197***	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	RC	Henry® 195 Polyester Fabric	Reinforcement	Reinforcement	n/a
	FC	Pro-Grade® 197	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	TC	Pro-Grade® 586	2.00 gal./sq. (16 mil DFT)	2.00 gal./sq. (16 mil DFT)	n/a
Option #2	TC	Pro-Grade® 599	2.50 gal./sq. (17 mil DFT)	2.00 gal./sq. (14 mil DFT)	2.00 gal./sq. (14 mil DFT)
Option #3	FC	Pro-Grade® 197***	5.00 gal./sq. (32 mil DFT)	4.00 gal./sq. (25 mil DFT)	n/a
	TC	Pro-Grade® 599	2.00 gal./sq. (14 mil DFT)	2.00 gal./sq. (14 mil DFT)	n/a
California only	FC	Pro-Grade® 197***	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	RC	Henry®195 Polyester Fabric	Reinforcement	Reinforcement	n/a
	FC	Pro-Grade® 197	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	TC	Pro-Grade® 588	2.50 gal./sq. (9 mil DFT)	2.50 gal./sq. (9 mil DFT)	n/a

Ancillary components for all warranted assemblies

Application			Product name	Product description	Coverage rate
Metal seams		S	Henry® 295 Metal Seam Sealer**	Metal seam sealer	190 linear foot per 5 gal. pail (1/8" thick at 4" wide)
Metal fasteners/defects		S	Henry® 295 Metal Seam Sealer**	Metal seam sealer	Varies by application
MB cap sheet seams	Option #1	RC	Pro-Grade® 197	Asphalt emulsion	210 linear foot per 5 gal. pail (56 mils thick at 6" wide; 3-course)
		RC	Henry® 195 Polyester Fabric	Reinforcement fabric	300 linear foot per 6" x 300' roll
	Option #2	RM	Pro-Grade® 167	Asphalt roof cement	40 linear foot per 3 gal. pail (1/4" thick at 6" wide; two coats 3-course)
			Henry® 183 Roof Repair Fabric	Yellow fiberglass repair fabric	150 linear foot per 4" x 150' or 36" X 150' roll
MB/BUR fasteners/ defects	Option #1	S	Pro-Grade® 167	Asphalt roof cement	Varies by application
	Option #2	S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application

*Authorized Henry® Pro-Grade® Aluminum roof coatings include: Pro-Grade® 586, Pro-Grade® 588 or Pro-Grade® 589. Contact Henry® Company for project specific recommendations.
**Use Henry® 289 White Roofing Sealant in areas where Henry® 295 Metal Seam Sealer does not meet local VOC requirements.
***Recommended when existing roof surface is "alligatored" or heavily textured. Built-Up Roof (BUR) and reinforced foundation coat assemblies do not require pre-treatment of secure and intact seams.
****For slopes greater than 3:12 contact Henry® Technical Support or your local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area
DFT = Dry Film Thickness (minimum requirement)

Warranty: Henry® Pro-Grade® Aluminum roof coating system* warranty durations are based on overall coating thicknesses. See coverage rate chart for requirements. Coverage rates do not account for material loss due to spraying, surface texture, waste, etc. Coverage rates are applicable for previously coated and non-coated roofs. Actual product quantity requirements may vary and are the responsibility of the contractor.

Safety statements: Use caution when applying and walking on coated surfaces. Coated surfaces can be extremely slippery and can create a fall hazard resulting in injury or death. All air intake ventilation equipment should be turned off to prevent fumes from entering building.

STEP 1: Substrate examination

I. Suitability of substrate:
A. Conduct a visual inspection to ensure substrate suitability.
1. Roofs must have positive drainage.
2. Substrate, insulation and all surfaces must be sound, dry, clean and free of oil, grease, rust, dirt, excess mortar, frost, laitance, loose and flaking particles or contaminants.

II. Adhesion tests:
A. Granulated modified bitumen: not required
B. Metal:
1. Non-previously coated: not required
2. Previously coated: required
a. Conduct ASTM D3359 tape test.
1. Slice existing coating in an x-cut.
2. Fully adhere semitransparent pressure sensitive tape over x-cut intersection.
3. Remove tape by pulling rapidly back over itself at a 180° angle.
4. Adhesion results indicating removal of coating are not acceptable.
C. Adhesion test requirements:
1. Conduct at least two tests in the field of existing roof membrane, one every 10,000 sq. ft., plus any area of worn roofing, such as cracked or abraded surfaces.
2. Any change in roof substrate
3. Existing roof areas installed in phases
4. Shaded areas
5. Areas indicating ponding water
D. Contact Henry® Product Support or your sales representative where adhesion test results indicate jagged coating removal along incision.

III. Moisture survey:
A. The installing contractor must verify the existing roofing assembly is dry and leak free prior to installation.
B. Evaluate existing roof assembly for moisture, including saturated insulation, roof deck, roof components and defective roofing. Repair and replace in accordance with National Roofing Contractors Association (NRCA).
C. Do not install Pro-Grade® Aluminum roof coating* over saturated insulation or substrates.
D. Moisture survey includes a visual inspection and one or more of the following:
1. Infrared thermography
2. Nuclear
3. Electric
4. Roof cor

IV. Repair or re
A. Ensure sk structures working co
B. Ensure fas fasteners
C. Metal:
1. Replace panels, f flashings
2. Remove mechani free of lo
3. Remove coating
D. Modified E
1. Remove defective existing

V. Weather cor
A. Substrate
B. Refer to m

Product name
Pro-Grade® 586
Pro-Grade® 58
Pro-Grade® 59
Pro-Grade® 19
Henry® 295 Me
Pro-Grade® 16

STEP 2: Substrate preparation

I. Clean:
A. Confirm local water run-off ordinances and restrictions prior to cleaning roof.
B. Surface cleaning:
1. MB/smooth BUR and metal:
a. Carefully pressure wash roof surfaces with greater than 2,000 psi pressure to remove loose granules, debris, rust, scale, dirt, dust, chalking, peeling or flaking coatings, etc. Do not force water into the roof system or damage roof surfaces.
b. Remove grease, oils or contaminates which may interfere with adhesion using warm water and mild detergent.
c. Treat areas of algae, mildew or fungus with a solution of household bleach and water.
d. Rinse roof to ensure removal of all detergent or anything else that could affect adhesion.

II. Primers:
A. Metal roof and metal components:
1. Optional rust primer: Install a commercial grade rust-inhibitive primer per primer manufacturer recommendation.

III. Flashing and details:
A. Complete flashings and details prior to Pro-Grade® Aluminum roof coating* installation.
B. Mix Pro-Grade® Aluminum roof coating* with drill and mixer blade prior to, and during use as needed, to main of alu
C. Refe
D. Meta
1. Ho rid
a. A to ga la ga

Fastener heads for metal roofs and metal components on MB/BUR roofs	
MB/BUR	Metal
Completely encapsulate fastener heads with Pro-Grade® 167.	Completely encapsulate fastener heads with Henry® 295 Metal Seam Sealer**.

Drains for MB/BUR roofs	
Flashing Options	MB/BUR
Option #1	1. Remove and clean strainer, ring and other drain components. 2. Install one layer of Pro-Grade® 197 at 3 gallons per square (48 wet mils) from the drain hole opening, extend 14" minimum beyond drain. 3. Fully embed Henry® 195 Polyester Fabric into foundation coat, extend 12" beyond drain hole. Brush or roll fabric for proper adhesion and remove all voids. 4. Apply second layer of Pro-Grade® 197 at 3 gallons per square (48 wet mils) from the drain hole opening; ensure fabric is fully coated.
Option #2	1. Remove and clean strainer, ring and other drain components. 2. Apply Pro-Grade® 167 using a trowel at 1/8" thick (125 wet mils) into the drain hole and completely encapsulating the drain bowl. 3. Fully embed Henry® 183 Roof Repair Fabric into Pro-Grade® 167, extend 12" beyond drain hole. Brush or roll fabric for proper adhesion and remove all voids. 4. Apply second layer of Pro-Grade® 167 over fabric at 1/8" thick (125 wet mils); ensure fabric is fully coated and extend roof coating 14" minimum beyond drain.

STEP 3: Roof coating application

I. Application of roof coating: Refer to the Coverage Rate Chart for warranted minimum requirements.
A. Mix Pro-Grade® Aluminum roof coating* with drill and mixer blade, prior to and during use as needed, to maintain consistent viscosity and uniform distribution of aluminum content throughout application.
B. Clean/prepare substrate in accordance with **Step 2: Substrate preparation** of this application guide.
C. Refer to **coverage rate chart** for coating assembly configuration and coverage rates.
1. No foundation coat: proceed to **Step D.**
2. Unreinforced foundation coat assemblies:
a. Apply Pro-Grade® 197, starting installation at low point of roof; extend 8" up vertical surfaces.
b. Allow Pro-Grade® 197 to dry prior to subsequent layer.
c. Proceed to **Step D.**
3. Reinforced foundation coat assemblies:
a. Apply one layer of Pro-Grade® 197, starting installation at low point of roof; extend 8" up vertical surfaces.
b. Install Henry® 195 Polyester Fabric perpendicular to roof slope and fully embed into Pro-Grade® 197; ensure 4" overlap at seams. Brush or roll fabric for proper adhesion and remove all voids. Dry fabric overlap is not acceptable.
c. Immediately apply Pro-Grade® 197 onto Henry® 195 Polyester Fabric; ensure fabric is fully coated. Do not walk on wet Pro-Grade® 197. Allow to dry prior to coating application. Proceed to **Step D.**
D. Install Pro-Grade® Aluminum roof coating* in accordance with this application guide.
1. Installation tips:
a. Application to damp surface will cause Pro-Grade® Aluminum roof coating* discoloration.
b. Install coating to optimize "leaf action"; aluminum flakes floating to surface after initial application:
1. Do not over brush/roll Pro-Grade® aluminum roof coating*. Over brushing will cause aluminum flake disorientation and decrease reflectivity.
2. Utilize high quality soft bristled brush, heavy nap roller, or commercial grade spray equipment.
3. Apply at a consistent/liberal rate.
4. Brush in one direction.
2. Install Pro-Grade® Aluminum roof coating*, extend 8" minimum up vertical surfaces.

Henry and Pro-Grade are registered trademarks of Henry Company
Kynar is a registered trademark of Arkema
Hylar is a registered trademark of Solvay

Henry | Building Envelope Systems® Roofing | Air Barrier | Waterproofing
Ask us today about other Henry® solutions that help manage the flow of water, air, vapor and energy.
productsupport@henry.com | 1-800-486-1278
www.henry.com
© 2016 Henry Company All rights reserved.
Printed in U.S.A 141.20JUL0403 (04/16)

Henry® A CARLISLE COMPANY 176

Henry Pro-Grade® Asphalt Repair Mastics/Emulsion Restoration Systems

Building Confidence™

© 2022 Henry Company. All rights reserved.

Facts About Asphalt Emulsion

- Resists Moisture Intrusion
- Monolithic When Applied With Re-Enforcement
- Easy To Apply
  - Spray, Brush, Roll
- Good Cost Effective/Performance
- 0 VOC





Henry
A CARLISLE COMPANY

Asphalt Emulsion Cons

- Must Be Top Coated With A Reflective Coating
  - Not UV Stable
- Multiple Coat Application Required
- Longer Cure Time
- Application Window Affected More By Weather
  - Must Be Applied at 50 Deg F and Rising
  - No Rain for 6-12 Hours+
    - Potential Wash-Off
- Not For Use On
  - Single-Ply Membranes
  - Metal
- Organic-Based
  - Food Source For Mold And Mildew
- Lower Solids
  - Typical ~50%





When Is Emulsion A Good Fit?

- Flat Asphaltic Roofs*
- Alligatored Asphaltic Roofs
- Previously Coated Aluminum and Acrylic Roofs



*Areas That Have Positive Drainage (No Ponding Water)

180

When Is Emulsion Not A Good Fit?

- Ponding Water Areas
- Flat Roofs*
- Single-Ply & SPF Roofs
- Needing Maximum UV Protection
- High-Foot Traffic Areas






*Little To No Positive Drainage

181

Pro-Grade® Emulsion Restoration

What Types Of Roofs Can We Restore?

What Types of Roofs Can We Restore?

Asphaltic

Granulated/Smooth Modified Bitumen



BUR




What Types of Roofs Can We Restore?

Previously Coated Acrylic and Aluminum Asphalt Substrates





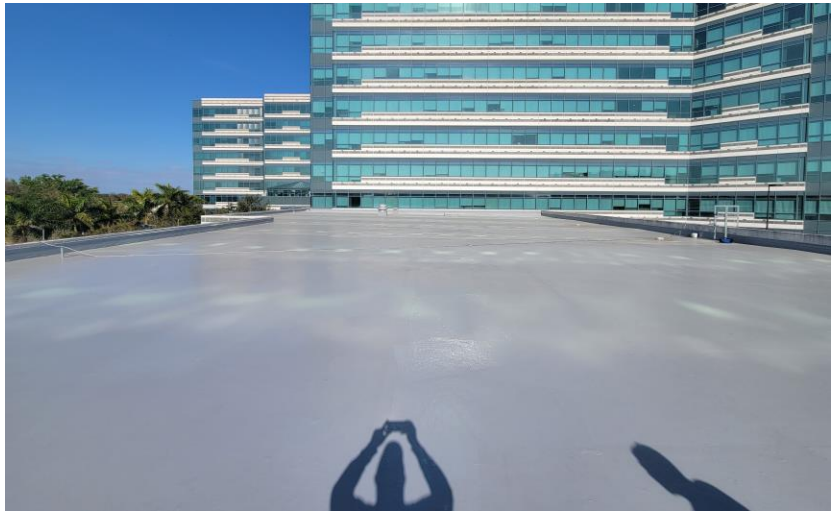

185

What Types of Roofs Can We Restore?

Tar & Gravel*



*System In Review

186

Pro-Grade® Emulsion Restoration Process

The Restoration Process- Warranted Systems

- Visual Roof Inspection
  - If Required
- Adhesion Testing
  - If Required
- Moisture Survey
  - If Required
- Roof Repairs
- Restore
- Final Inspection
  - If Required

Moisture Surveys

Moisture Survey

- Infrared Scanning & Core Cut Evaluation Of Existing Roof Assembly Helps Determine Roof's Qualification For Restoration
  - If >25% Is Wet And Needs Replacement, The Roof Is Not A Candidate
  - If <25% Is Wet, Then Damaged Roof Section(s) Can Be Removed And Replaced With Like Materials


Accepted Testing Methods

- Nuclear
- Infrared
- Impedance/Capacitance
- Cores
  - Roof Map and NRCA Guidelines Required

***Not Required On Metal Roofs**





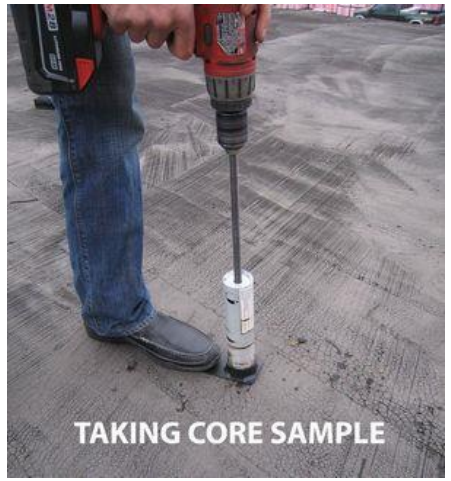





Henry
A CARLISLE COMPANY


Moisture Surveys

Drone Thermal Moisture Survey



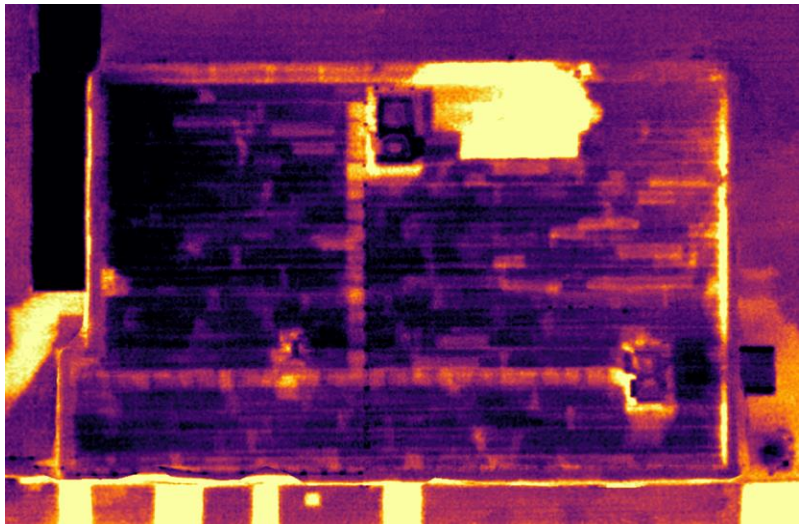

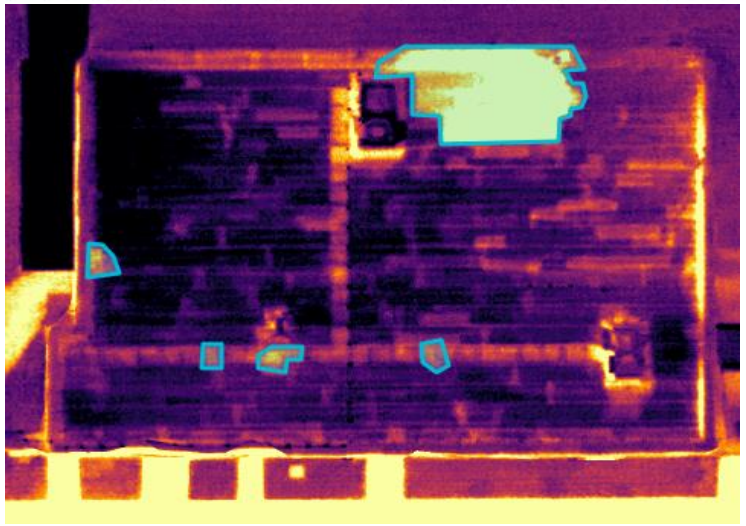

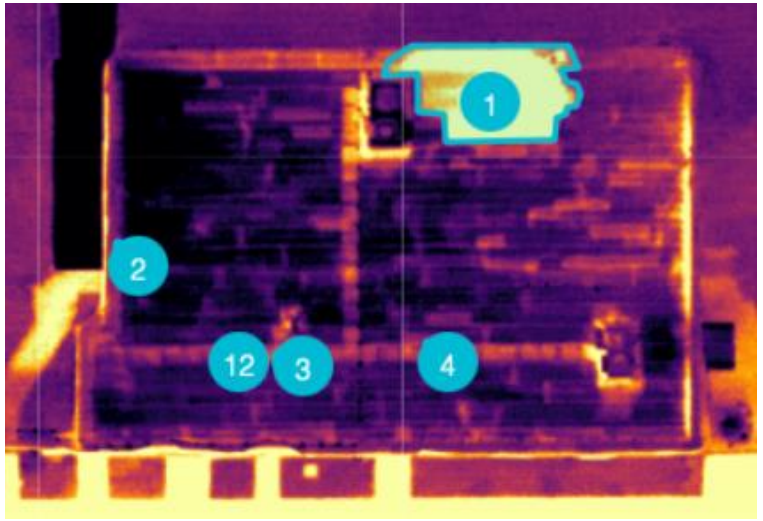

Henry
A CARLISLE COMPANY

Repairs

Repair First, Then Restore

- Remove & Replace Wet Insulation
- Remove & Replace Damaged Decking
- Infill Damaged Area With Like Roofing Materials





Prior To Restoration, The Existing Roof Must Be Brought Back To A Sound, Watertight Serviceable Condition.



Henry
A CARLISLE COMPANY

Complete Line of Products
Saving Contactors Time and Money


Henry Pro-Grade® Emulsion Roof Coatings

Emulsion System Offering
Pro-Grade® 197 Asphalt Emulsion
AcryShield® 510 Topcoat/505 Basecoat
AcryShield® 610 Topcoat/605 Basecoat
AcryShield® 550 High Tensile Topcoat
AcryShield® 400 Topcoat
Pro-Grade® 599 Rubberized Aluminum Roof Coating
Pro-Grade® 586 Aluminum Roof Coating
Pro-Grade® 588 WB Aluminum Roof Coating
Henry® 195/196 Polyester Fabric







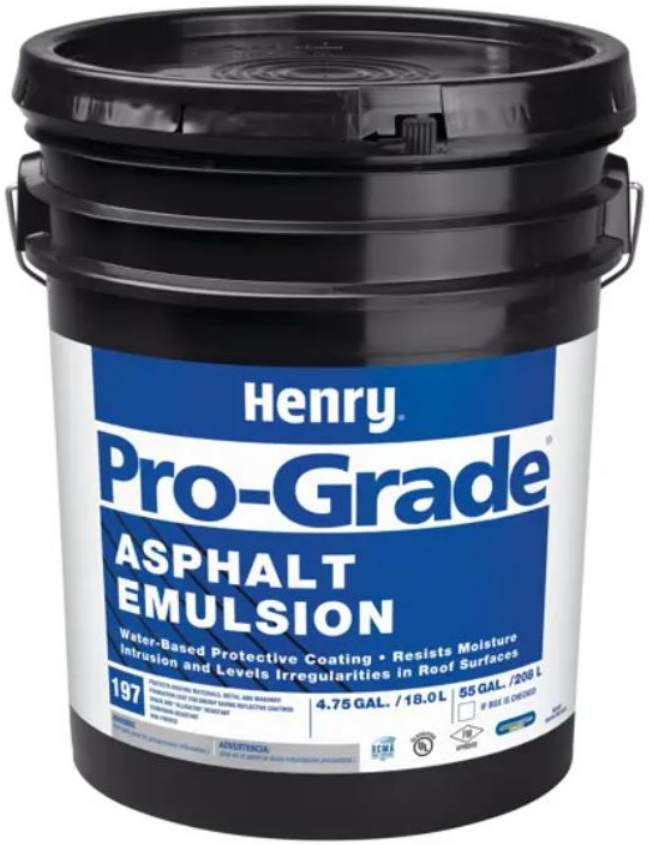









*Pro-Grade® 280 Elastomeric White Roof Coating & Pro-Grade® 294 Basecoat & Sealer available for existing specifications

Henry® A CARLISLE COMPANY

Pro-Grade® 197 Asphalt Emulsion

A Premium, Cold-applied Protective Coating That Resists Moisture Intrusion And Levels Irregularities In Asphaltic Roof Surfaces

- Helps Extend The Existing Roof Membrane Life Cycle
- Low Odor And VOC Compliant In All Jurisdictions
- Must Be Top Coated
  - Acrylic
  - Aluminum

- Color: Black
- Sizes:
  - 5 Gal Pail
  - 55 Gal Drum
  - 275 Gal Tote
  - Bulk



Henry
A CARLISLE COMPANY

Pro-Grade® Emulsion Basecoat/Topcoat Options

AcryShield® 505 Basecoat

A One Component, Low VOC, Water-based Coating Designed For Basecoat Application To Roofing Membranes:

- BUR
- Mod-Bit
- Metal
- Single-Ply
- Asphalt Emulsion

- **AcryShield 505 BC**
  - Bleed Blocking Properties
  - Excellent Ponding Water Resistance
  - Low VOC
  - Excellent Adhesion To Prepared Surfaces
- **Color: Beige**
- **Sizes:**
  - 5-gallon Pail
  - 55-gallon Drum



Henry
A CARLISLE COMPANY

AcryShield® 510 Topcoat

High Quality 100% Acrylic Elastomeric Coating For Topcoat Use Over A Variety Of Substrates:

- SPF
- Single-Ply
- Metal Roofing
- Asphalt Roofing

AcryShield 510 TC

- "Go-To" Acrylic
- Is not a Bleed Blocker
- Can be used in Colder Climates Where Extra Levels Of Low Temperature Flexibility Are Required.
- AcryShield 510 Exceeds ASTM D6083 Requirements

Colors: White, Sand, Light and Dark Gray, Custom

Sizes:

- 5-gallon Pail
- 55-gallon Drum



Henry
A CARLISLE COMPANY

AcryShield® 605 Fast-Set Basecoat

Unique Fast Setting One Component, Low VOC, Water-based Coating Designed For Basecoat Application Use Over A Variety Of Substrates:

- BUR
- Mod-Bit
- Metal
- Single-Ply
- Asphalt Emulsion

- AcryShield 605 FSB
  - Early Wash-Off Resistance
    - Heavy Dew
    - Light Rain
- Color: Beige
- Sizes:
  - 5-gallon Pail
  - 55-gallon Drum



Henry
A CARLISLE COMPANY

AcryShield® 610 Fast-Set

Unique Fast-Setting 100% Acrylic Elastomeric Coating For Topcoat Use Over A Variety Of Substrates:

- SPF
- Single-Ply
- Metal Roofing
- Asphalt

AcryShield A610 FST

- Early Wash-Off Resistance
- Heavy Dew
- Light Rain

Colors: White, Sand, Light and Dark Gray, Custom

Sizes:

- 5-gallon Pail
- 55-gallon Drum



Henry
A CARLISLE COMPANY

AcryShield® 550 High Tensile

100% Acrylic Elastomeric High Tensile Coating Topcoat Use Over A Variety Of Substrates:

- SPF
- Single-Ply
- Metal Roofing
- Asphalt Roofing

AcryShield 550 HT

- Urethane-Like Qualities
- Superior protection against
  - Foot Traffic
  - Physical Abuse
- AcryShield 550 Exceeds ASTM D6083 Requirements

Colors: White, Sand, Light and Dark Gray

Sizes:

- 5-gallon Pail
- 55-gallon Drum



Henry
A CARLISLE COMPANY

AcryShield® 400

Multi-Purpose 100% Acrylic Elastomeric Coating For Topcoat Use Over A Variety Of Substrates:

- **Asphalt**
- **Single-Ply**
- **Metal Roofing**

ACRYSHIELD 400

- **Unique "Bleed Blocking" Properties For Coating Over Asphalt Surfaces**
- **Exceeds Several ASTM D6083 Requirements Such As Tensile Strength, Elongation, Wet Adhesion And Weatherability**

Colors: White, Sand, Light and Dark Gray

Sizes:

- **5-gallon Pail**
- **55-gallon Drum**



Henry
A CARLISLE COMPANY

Pro-Grade® 588 Aluminum Roof Coating

Combination Of Premium Aluminum Flakes Suspended In Emulsified Asphalt Provides Outstanding Weathering Resistance And Reflectance.



- Professional Grade Water-Based, Fibered Aluminum Roof Coating
- Low VOC
- For Use in Southern California
- UL, CRRC and Energy Star Rated

Color: Silver

Sizes:

- **5-gallon Pail**
- **50-gallon Drum**

Pro-Grade® 586 Aluminum Roof Coating

Premium Fibered Aluminum Coating For New Or Aged Smooth Surface BUR, Modified Bitumen Membranes, Aged Galvanized Metal Roofs And New Asphalt Emulsion That Forms A Tough, Brilliant Reflective Surfacing.



- Professional Grade Fire-Rated, Fibered Aluminum Roof Coating
- Solvent-Based
- 1-Coat Application
- UL, FM, CRRC, Miami-Dade and Energy Star Rated

Color: Silver

Sizes:

- **5-gallon Pail**
- **50-gallon Drum**

Pro-Grade® 599 Aluminum Roof Coating

A Premium, Highly Reflective Coating Made With SBS Rubber Polymers, Which Provides Outstanding Strength And Elastic Properties. It Is An Excellent Weathering Surfacing For New Or Aged Asphalt Roof Surfaces Including Smooth BUR, Modified Bitumen Membranes And Metal Roofs.



- Professional Grade SBS Rubberized, Aluminum Roof Coating
- Good Ponding Water Resistance
- Solvent-Based
- 1-Coat Application
- CRRC, Miami-Dade and Energy Star Rated (Low and Steep Slope)

Color: Silver

Sizes:

- **5-gallon Pail**
- **50-gallon Drum**

Pro-Grade® Emulsion Accessories

Henry® 195/196 Polyester Fabric

Henry 195 Polyester Fabric

- Stich bonded, High-Performance Fabric
- Soft Finish
- Conforms to Irregular Surfaces

Henry 196 Polyester Fabric

- Stich bonded, High-Performance Fabric
- Firm Finish

- Uses include:
  - Drains
  - Seams
  - Repairs

Color: Off White - White

Sizes:

- Henry 195
  - 40” x 324’ Roll
  - 12” x 300’ Roll
  - 6” x 300’ Roll
- Henry 196
  - 40” x 324’ Roll
  - 4” x 300’ Roll



Project Startup

Preparation- Cleaning

Granulated Modified Bitumen/BUR

- Power Broom
- Dry Vac
- Air Lance (195 CFM)



Smooth Modified Bitumen

- Power Broom
- Dry Vac
- Air Lance (195 CFM)



ENSURE ALL RESIDUE IS REMOVED AND ROOF IS DRY PRIOR TO SEALER OR COATING APPLICATION

Preparation- The Details

- Seams
- Penetrations
- Curbs
- Terminations
- Transitions
- Parapet









90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!

Preparation- The Details

Seam Options

- Pro-Grade® 197 With HE 195 Fabric (Not Required for Full Fabric System)
  - Brush
  - Roll
  - Spray

Penetrations

- Pro-Grade® 197 With HE 195 Fabric
  - Brush
- Henry® 289 Roof Sealant
  - Brush



Fasteners

- Henry® 295 Metal Seam Sealer
  - Brush
  - Bulk Loader Gun

- Henry® 289 Roof Sealant
  - Brush

90% Of Roof Leaks Occur At These Places
We Must Sweat The Details!

Pro-Grade® Emulsion Application

Installation – Roof Grid Process

- **Measure And Mark 10’x10’ Squares On The Roof, Each Representing One Square (100 Sq.Ft.)**

Example:

If The Spec Calls For 5 Gallons/Square Of Coating, Then One 5-gallon Pail Of Pro-Grade 197 Will Cover 1.0 Squares. (Smooth Surfaces)

- **Granulated Mod-Bit & Rough Surfaces Will Require More To Meet DFT**









Installation – Easy Application

Broom, Squeegee, Roll

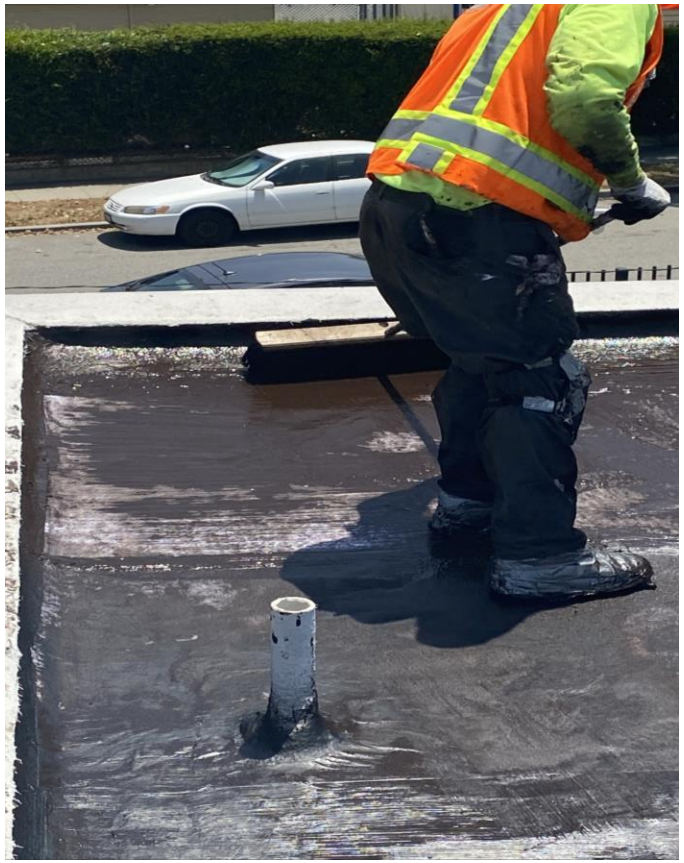

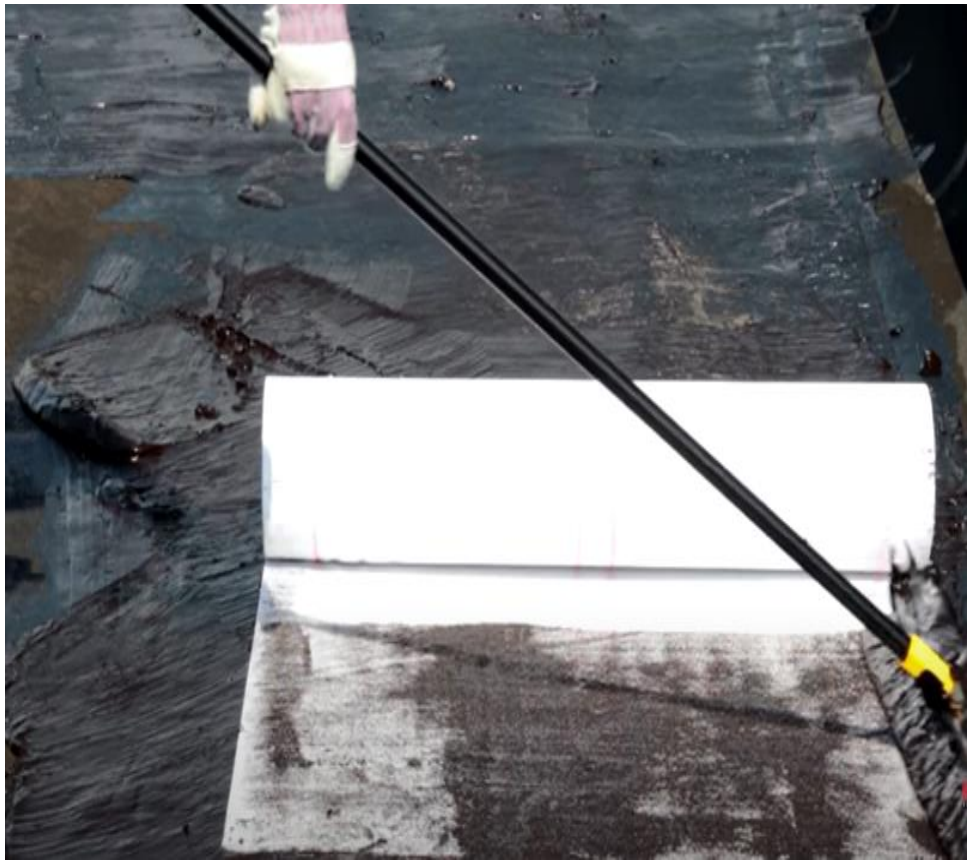



Installation – Easy Application

Spray and Broom In







Installation – Easy Application

Topcoat

Roll



Squeegee And Back Roll



Spray And Back Roll



Warranty Information

Henry Warranty Program

Industry-Leading Warranty Program

Warranty Options Provide Up To 15 Years Labor, Workmanship And Materials Coverage

Acrylic-Emulsion Restoration Systems Warranties

- Up to 15 Years
- Transferable And Renewable Options

Aluminum-Emulsion Restoration Systems Warranties

- Up to 12 Years
- Transferable And Renewable Options



217

Henry AcryShield® Acrylic Warranty Options

Application guide

Henry® Asphalt Roof Emulsion Restoration System

This application guide provides instructions for successfully applying a Henry® Acrylic roof coating system on asphalt roofs (roll roofing, modified bitumen and built-up roofing). An asphalt roof emulsion coating system is a fluid-applied roof restoration system, supported by a variety of warranty offerings, that provides a cost-effective alternative to a full replacement.

Warranty installation options

10-year Asphalt Emulsion roof coating system					
		Granulated Cap Sheet	Smooth Cap sheet/BUR (non-aggregate)	Warranty Cost	
				Materials Plus	Gold Seal
FC	Pro-Grade® 197	40 mils DFT min. 5 gal/sq	32 mils DFT min. 4 gal/sq	No cost	$0.06/sq.ft. $900 min
BC	AcryShield® Base Coat 400*, 505	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield® Top Coat 510, 550 HT or 610	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	66 mils DFT min. 8 gal/sq	58 mils DFT min. 7 gal/sq		

15-year Asphalt Emulsion roof coating system**					
		Granulated Cap Sheet	Smooth Cap sheet/BUR (non-aggregate)	Warranty Cost	
				Materials Plus	Gold Seal
FC	Pro-Grade® 197	32 mils DFT min. 4 gal/sq	24 mils DFT min. 3 gal/sq	No cost	$0.08/sq.ft. $1200 min
R	Henry® 195 Polyester Fabric	Reinforcing layer	Reinforcing layer		
FC	Pro-Grade® 197	32 mils DFT min. 4 gal/sq	24 mils DFT min. 3 gal/sq		
BC	AcryShield® Base Coat 400*	17 mils DFT min. 2.0 gal/sq	17 mils DFT min. 2.0 gal/sq		
TC	AcryShield® Top Coat 510, 550 HT or 610	17 mils DFT min. 2.0 gal/sq	17 mils DFT min. 2.0 gal/sq		
	Total (min. thickness)	98 mils DFT min. 12 gal/sq	82 mils DFT min. 10 gal/sq		

Ancillary components for all warranted assemblies				
Application		Product name	Product description	Coverage rate
MB/BUR fasteners/defects	S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application
	S	Seal-Tek Micro Fibers	Fibered roofing sealant	See application guidelines for mixing instructions
MB/BUR cap sheet	S	Fully Reinforced System Not Required	n/a	n/a

FC Foundation coat BC Base coat TC Top coat R Reinforcing layer S Sealant

NOTES:
* AcryShield 400 can be used as a top coat in certain assemblies/applications
** Total thickness to be must be achieved but you must give consideration to temperature and humidity levels during the time of application for curing and application coats. Will require multiple coats
DFT = Dry Film Thickness (minimum requirement).

Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.

Warranty installation options

10-year Asphalt Emulsion roof coating system					
		Granulated Cap Sheet	Smooth Cap sheet/BUR (non-aggregate)	Warranty Cost	
				Materials Plus	Gold Seal
FC	Pro-Grade® 197	40 mils DFT min. 5 gal/sq	32 mils DFT min. 4 gal/sq	No cost	$0.06/sq.ft. $900 min
BC	AcryShield® Base Coat 400*, 505	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield® Top Coat 510, 550 HT or 610	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	66 mils DFT min. 8 gal/sq	58 mils DFT min. 7 gal/sq		

15-year Asphalt Emulsion roof coating system**					
		Granulated Cap Sheet	Smooth Cap sheet/BUR (non-aggregate)	Warranty Cost	
				Materials Plus	Gold Seal
FC	Pro-Grade® 197	32 mils DFT min. 4 gal/sq	24 mils DFT min. 3 gal/sq	No cost	$0.08/sq.ft. $1200 min
R	Henry® 195 Polyester Fabric	Reinforcing layer	Reinforcing layer		
FC	Pro-Grade® 197	32 mils DFT min. 4 gal/sq	24 mils DFT min. 3 gal/sq		
BC	AcryShield® Base Coat 400*	17 mils DFT min. 2.0 gal/sq	17 mils DFT min. 2.0 gal/sq		
TC	AcryShield® Top Coat 510, 550 HT or 610	17 mils DFT min. 2.0 gal/sq	17 mils DFT min. 2.0 gal/sq		
	Total (min. thickness)	98 mils DFT min. 12 gal/sq	82 mils DFT min. 10 gal/sq		

Ancillary components for all warranted assemblies				
Application		Product name	Product description	Coverage rate
MB/BUR fasteners/defects	S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application
	S	Seal-Tek Micro Fibers	Fibered roofing sealant	See application guidelines for mixing instructions
MB/BUR cap sheet	S	Fully Reinforced System Not Required	n/a	n/a

FC Foundation coat BC Base coat TC Top coat R Reinforcing layer S Sealant

NOTES:
* AcryShield 400 can be used as a top coat in certain assemblies/applications
** Total thickness to be must be achieved but you must give consideration to temperature and humidity levels during the time of application for curing and application coats. Will require multiple coats
DFT = Dry Film Thickness (minimum requirement).

Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.

218

Henry AcryShield® Acrylic-Emulsion Application Guide

Application guide

Henry® Asphalt Roof Emulsion Restoration System

This application guide provides instructions for successfully applying a Henry® Acrylic roof coating system on asphalt roofs (roll roofing, modified bitumen and built-up roofing). An asphalt roof emulsion coating system is a fluid-applied roof restoration system, supported by a variety of warranty offerings, that provides a cost-effective alternative to a full replacement.

Warranty installation options

10-year Asphalt Emulsion roof coating system					
		Granulated Cap Sheet	Smooth Cap sheet/BUR (non-aggregate)	Warranty Cost	
				Materials Plus	Gold Seal
FC	Pro-Grade® 197	40 mils DFT min. 5 gal/sq	32 mils DFT min. 4 gal/sq	No cost	$0.06/sq.ft. $900 min
BC	AcryShield® Base Coat 400*, 505	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
TC	AcryShield® Top Coat 510, 550 HT or 610	13 mils DFT min. 1.5 gal/sq	13 mils DFT min. 1.5 gal/sq		
	Total (min. thickness)	66 mils DFT min. 8 gal/sq	58 mils DFT min. 7 gal/sq		

15-year Asphalt Emulsion roof coating system**					
		Granulated Cap Sheet	Smooth Cap sheet/BUR (non-aggregate)	Warranty Cost	
				Materials Plus	Gold Seal
FC	Pro-Grade® 197	32 mils DFT min. 4 gal/sq	24 mils DFT min. 3 gal/sq	No cost	$0.08/sq.ft. $1200 min
R	Henry® 195 Polyester Fabric	Reinforcing layer	Reinforcing layer		
FC	Pro-Grade® 197	32 mils DFT min. 4 gal/sq	24 mils DFT min. 3 gal/sq		
BC	AcryShield® Base Coat 400*	17 mils DFT min. 2.0 gal/sq	17 mils DFT min. 2.0 gal/sq		
TC	AcryShield® Top Coat 510, 550 HT or 610	17 mils DFT min. 2.0 gal/sq	17 mils DFT min. 2.0 gal/sq		
	Total (min. thickness)	98 mils DFT min. 12 gal/sq	82 mils DFT min. 10 gal/sq		

Ancillary components for all warranted assemblies				
Application		Product name	Product description	Coverage rate
MB/BUR fasteners/defects	S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application
	S	Seal-Tek Micro Fibers	Fibered roofing sealant	See application guidelines for mixing instructions
MB/BUR cap sheet	S	Fully Reinforced System Not Required	n/a	n/a

FC Foundation coat BC Base coat TC Top coat R Reinforcing layer S Sealant

NOTES:
* AcryShield 400 can be used as a top coat in certain assemblies/applications
** Total thickness to be must be achieved but you must give consideration to temperature and humidity levels during the time of application for curing and application coats. Will require

Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above

Warranty: Henry® asphalt emulsion roof coating system warranty durations are based on overall coating thicknesses. See coverage rate chart for requirements. Coverage rates do not account for material loss due to spraying, surface texture, waste, etc. Coverage rates are applicable for previously coated and non-coated roofs.

Safety statements: Use caution when applying and walking on coated surfaces. Coated surfaces can be extremely slippery and can create a fall hazard resulting in injury or death. All air intake ventilation equipment should be turned off to prevent fumes from entering building.

STEP 1: Substrate examination

I. Suitability of substrate:

A. Conduct a visual inspection to ensure subst suitability.
1. Roofs must have positive drainage.
2. Substrate, insulation and all surfaces mus sound, dry, clean and free of oil, grease, r excess mortar, frost, laitance, loose and fl particles or contaminants.

II. Moisture survey:

A. The installing contractor must verify the existir assembly is dry and leak free prior to installati
B. Evaluate existing roof assembly for moisture including saturated insulation, roof deck, roc components and defective roofing. Repair a replace in accordance with National Roofing Contractors Association (NRCA).
C. Do not install asphalt emulsion over saturat insulation or substrates.
D. Moisture survey includes a visual inspection and one or more of the following:
1. Infrared thermography
2. Nuclear scan
3. Electric capacitance/impedance testing
4. Roof core cut samples

III. Repair or replace defective existing roofing:

STEP 2: Substrate preparation

I. Clean:

A. Confirm local water run-off ordinances and restrictions prior to cleaning roof.
B. Surface cleaning:
1. MB/smooth BUR and metal:
a. Carefully pressure wash roof surfaces with greater than 2,000 psi pressure to remove loose granules, debris, rust, scale, dirt, dust, chalking, peeling or flaking coatings, etc. Do not force water into the roof system or damage roof surfaces.
b. Remove grease, oils or contaminates which may interfere with adhesion using warm water and mild detergent.
c. Treat areas of algae, mildew or fungus.
d. Rinse roof to ensure removal of all detergent or anything else that could affect adhesion.

Pre-treatment of MB/BUR de	
Flashing	MB/BUR
Option #1	1. Generously apply Henry® 289 White Roofing Sealant unde using a brush or trowel and firmly press loose roof membr 2. Apply Henry® 289 White Roofing Sealant at ⅛" thick (125 3. Center 6" wide Henry® 195 Polyester Fabric over seam an Brush or roll fabric for proper adhesion and remove all voi 4. Apply second layer of Henry® 289 White Roofing Sealant ensure fabric is fully coated.
Roof curbs, parapets and pi	
Flashing Options	MB/BUR
Option #1	Apply Henry® 289 White Roofing Sealant using a brush or tro vertical surfaces.
Option #2	Apply Seal-Tek Micro-Fibers using a brush or trowel at 1/8"
Drains fo	
1. Remove and clean strainer, ring and other drain components. 2. Apply Henry® 289 White Roofing Sealant using a stiff bristled brush or s encapsulating the drain bowl. 3. Install one layer of acrylic roof coating at 2 gallons per square (32 wet m 4. Fully embed Henry® 195 Polyester Fabric into roof coating, extend 12" b all voids. 5. Apply second layer of acrylic roof coating over fabric at 2 gallons per sq 14" minimum beyond drain.	

II. Flashing and details:

A. Complete flashings and details prior to roof coating installation.
B. Mix acrylic roof coating with drill and mixer blade

STEP 3: Asphalt emulsion application

I. Application of roof coating: Refer to the Coverage Rate Chart for warranted minimum requirements.

A. Clean/prepare substrate in accordance with **Step 2: Substrate preparation** of this application guide.
B. Refer to **coverage rate chart** for roof coating assembly configuration and coverage rates.
1. No foundation coat: proceed to Step D.
2. Unreinforced foundation coat assemblies:
a. Apply Pro-Grade® 197, starting installation at low point of roof; extend 8" up vertical surfaces.
b. Allow Pro-Grade® 197 to dry prior to subsequent layer. Proceed to Step D.
3. Reinforced foundation coat assemblies:
a. Apply one layer of Pro-Grade® 197, starting installation at low point of roof; extend 8" up vertical surfaces.
b. Install Henry® 195 Polyester Fabric perpendicular to roof slope and fully embed into Pro-Grade® 197; ensure 4" overlap at seams. Brush or roll fabric for proper adhesion and remove all voids. Dry fabric overlap is not acceptable.
c. Immediately apply Pro-Grade® 197 onto Henry® 195 Polyester Fabric; ensure fabric is fully coated. Do not walk on wet Pro-Grade® 197. Allow to dry prior to coating application. Proceed to Step D.
C. Mix acrylic roof coating with drill and mixer blade prior to use until consistent viscosity is achieved.
D. Install acrylic roof coating base coat, extend 8" minimum up vertical surfaces; ensure coating is clean and dry prior to subsequent layer.
E. Install acrylic roof coating top coat, extend 8" minimum up vertical surfaces; install perpendicular to cured base coat.

II. Walkways (optional):

A. Ensure substrate is clean in accordance with **Step 2: Substrate preparation** of this application guide prior to coating application.
B. Apply additional acrylic roof coating at traffic areas at a minimum 1 gallon per square (16 wet mils).
C. Apply granules uniformly into wet roof coating at a rate of 20-30 pounds per square.
D. Allow roof coating to dry.
E. Remove loose particles from roof to avoid clogging drain.

Henry. Building Envelope Systems® Roofing | Air Barrier | Waterproofing
Ask us today about other Henry® solutions that help manage the flow of water, air, vapor and energy.

Henry Pro-Grade® Aluminum Warranty Options

Henry.

Warranty program

Henry® Pro-Grade® Aluminum Roof Coating System

A roof restoration system from Henry®, Pro-Grade® Aluminum high performance roof coating system extends the life cycle of your roof, resulting in a cost-effective alternative to a full replacement.

Warranty Options from Henry®
-Choose your desired level of warranty protection to meet your needs: Material Plus or Gold Seal.
-Both options can be available when installation is in compliance with the information below.

Material Plus Warranty
This warranty option provides material and labor coverage at no charge during the applicable warranty term to repair the affected roof area when product manufacturing defects have been determined. Product(s) must be installed by a Material Plus or Gold Seal Authorized Contractor.

Gold Seal Warranty
This warranty option provides material and labor to repair the affected area when product defects or workmanship installation deficiencies have been determined. Product(s) must be installed by a Gold Seal Authorized Contractor.

Warranty installation options

10-year Pro-Grade® Aluminum roof coating system							
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal*	Warranty cost	
						Material Plus	Gold Seal
Option #1	TC	Pro-Grade® 586	2.50 gal./sq. 20 mil DFT	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT	No cost	$.10/SF $1,000 minimum
Option #2	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.10/SF $1,000 minimum
	TC	Pro-Grade® 586	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT			
California only	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.10/SF $1,000 minimum
	TC	Pro-Grade® 588	2.00 gal./sq. 7 mil DFT	2.00 gal./sq. 7 mil DFT			

12-year Pro-Grade® Aluminum roof coating system							
	Assembly configuration		Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal*	Warranty cost	
						Material Plus	Gold Seal
Option #1	FC	Pro-Grade® 197**	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	R	195 Polyester Fabric	Reinforcement	Reinforcement			
	FC	Pro-Grade® 197	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT			
	TC	Pro-Grade® 586	2.00 gal./sq. 16 mil DFT	2.00 gal./sq. 16 mil DFT			
Option #2	TC	Pro-Grade® 599	2.50 gal./sq. 17 mil DFT	2.00 gal./sq. 14 mil DFT	2.00 gal./sq. 14 mil DFT	No cost	$.12/SF $1,200 minimum
Option #3	FC	Pro-Grade® 197**	5.00 gal./sq. 32 mil DFT	4.00 gal./sq. 25 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	TC	Pro-Grade® 599	2.00 gal./sq. 14 mil DFT	2.00 gal./sq. 14 mil DFT			
California only	FC	Pro-Grade® 197**	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT	n/a	No cost	$.12/SF $1,200 minimum
	R	195 Polyester Fabric	Reinforcement	Reinforcement			
	FC	Pro-Grade® 197	4.00 gal./sq. 25 mil DFT	3.00 gal./sq. 19 mil DFT			
	TC	Pro-Grade® 588	2.50 gal./sq. 9 mil DFT	2.50 gal./sq. 9 mil DFT			

FC Foundation coat TC Top coat R Reinforced coating

NOTES:
* For slopes greater than 3:12, contact Henry® Technical Support or the local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area.
** Recommended when existing roof surface is "alligatored" or heavily textured. Refer to Pro-Grade® 197 TDS and appropriate HRS Guide Specification for application information.

DFT = Dry Film Thickness (minimum requirement).
Product coverage rates represent minimum application requirement. Coverage rates are theoretical and do not take into account material loss due to spraying, surface texture, waste, etc. For previously coated roof membranes, the product coverage rates indicated in the charts above are applicable.

Henry® A CARLISLE COMPANY 220

Henry Pro-Grade® Aluminum Application Guide

Application guide

Henry® Pro-Grade® Aluminum Roof Coating System

This application guide provides instructions for successfully applying a Henry® Pro-Grade® Aluminum roof coating system* on metal, asphalt roofs (roll roofing, modified bitumen and built-up roofing) and previously coated roofs. A Pro-Grade® Aluminum roof coating system* is a roof restoration system providing a cost-effective alternative to a full replacement. When installed according to these instructions, it is designed to provide a fluid applied roofing system supported by a variety of warranty offerings. This application guide is not intended for applications on shingles, coal tar substrates, gravel covered roofs, cold storage or cryogenic structures, and Kynar® or Hylar® coated metal roofs. Metal roofs must be greater than 28 gauge (0.015").

FC Foundation Coat TC Top coat S Sealant RC Reinforced coating RM Reinforced mastic

Coverage rates

Coating assembly configuration			Granulated cap sheet	Smooth cap sheet/BUR (non-aggregate)	Metal****
10-year Pro-Grade® Aluminum roof coating system options					
Option #1	TC	Pro-Grade® 586	2.50 gal./sq. (20 mil DFT)	2.00 gal./sq. (16 mil DFT)	2.00 gal./sq. (16 mil DFT)
Option #2	FC	Pro-Grade® 197***	5.00 gal./sq. (32 mil DFT)	4.00 gal./sq. (25 mil DFT)	n/a
	TC	Pro-Grade® 586	2.00 gal./sq. (16 mil DFT)	2.00 gal./sq. (16 mil DFT)	n/a
California only	FC	Pro-Grade® 197***	5.00 gal./sq. (32 mil DFT)	4.00 gal./sq. (25 mil DFT)	n/a
	TC	Pro-Grade® 588	2.00 gal./sq. (17 mil DFT)	2.00 gal./sq. (7 mil DFT)	n/a
12-year Pro-Grade® Aluminum roof coating system* options					
Option #1	FC	Pro-Grade® 197***	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	RC	Henry® 195 Polyester Fabric	Reinforcement	Reinforcement	n/a
	FC	Pro-Grade® 197	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	TC	Pro-Grade® 586	2.00 gal./sq. (16 mil DFT)	2.00 gal./sq. (16 mil DFT)	n/a
Option #2	TC	Pro-Grade® 599	2.50 gal./sq. (17 mil DFT)	2.00 gal./sq. (14 mil DFT)	2.00 gal./sq. (14 mil DFT)
Option #3	FC	Pro-Grade® 197***	5.00 gal./sq. (32 mil DFT)	4.00 gal./sq. (25 mil DFT)	n/a
	TC	Pro-Grade® 599	2.00 gal./sq. (14 mil DFT)	2.00 gal./sq. (14 mil DFT)	n/a
California only	FC	Pro-Grade® 197***	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	RC	Henry®195 Polyester Fabric	Reinforcement	Reinforcement	n/a
	FC	Pro-Grade® 197	4.00 gal./sq. (25 mil DFT)	3.00 gal./sq. (19 mil DFT)	n/a
	TC	Pro-Grade® 588	2.50 gal./sq. (9 mil DFT)	2.50 gal./sq. (9 mil DFT)	n/a

Ancillary components for all warranted assemblies

Application			Product name	Product description	Coverage rate
Metal seams		S	Henry® 295 Metal Seam Sealer**	Metal seam sealer	190 linear foot per 5 gal. pail (1/8" thick at 4" wide)
Metal fasteners/defects		S	Henry® 295 Metal Seam Sealer**	Metal seam sealer	Varies by application
MB cap sheet seams	Option #1	RC	Pro-Grade® 197	Asphalt emulsion	210 linear foot per 5 gal. pail (56 mils thick at 6" wide; 3-course)
			Henry® 195 Polyester Fabric	Reinforcement fabric	300 linear foot per 6" x 300' roll
	Option #2	RM	Pro-Grade® 187	Asphalt roof cement	40 linear foot per 3 gal. pail (1/4" thick at 6" wide; two coats 3-course)
			Henry® 183 Roof Repair Fabric	Yellow fiberglass repair fabric	150 linear foot per 4" x 150' or 36" X 150' roll
MB/BUR fasteners/ defects	Option #1	S	Pro-Grade® 187	Asphalt roof cement	Varies by application
	Option #2	S	Henry® 289 White Roofing Sealant	Roofing sealant	Varies by application

*Authorized Henry® Pro-Grade® Aluminum roof coatings include: Pro-Grade® 586, Pro-Grade® 588 or Pro-Grade® 589. Contact Henry® Company for project specific recommendations.
**Use Henry® 289 White Roofing Sealant in areas where Henry® 295 Metal Seam Sealer does not meet local VOC requirements.
***Recommended when existing roof surface is "alligatored" or heavily textured. Built-Up Roof (BUR) and reinforced foundation coat assemblies do not require pre-treatment of secure and intact seams.
****For slopes greater than 3:12 contact Henry® Technical Support or your local Henry® sales representative. Include a stretch factor increase of 15 to 30% when calculating metal roof surface area
DFT = Dry Film Thickness (minimum requirement)

Warranty: Henry® Pro-Grade® Aluminum roof coating system* warranty durations are based on overall coating thicknesses. See coverage rate chart for requirements. Coverage rates do not account for material loss due to spraying, surface texture, waste, etc. Coverage rates are applicable for previously coated and non-coated roofs. Actual product quantity requirements may vary and are the responsibility of the contractor.

Safety statements: Use caution when applying and walking on coated surfaces. Coated surfaces can be extremely slippery and can create a fall hazard resulting in injury or death. All air intake ventilation equipment should be turned off to prevent fumes from entering building.

STEP 1: Substrate examination

I. Suitability of substrate:

A. Conduct a visual inspection to ensure substrate suitability.
1. Roofs must have positive drainage.
2. Substrate, insulation and all surfaces must be sound, dry, clean and free of oil, grease, rust, dirt, excess mortar, frost, laitance, loose and flaking particles or contaminants.

II. Adhesion tests:

A. Granulated modified bitumen: not required
B. Metal:
1. Non-previously coated: not required
2. Previously coated: required
a. Conduct ASTM D3359 tape test.
1. Slice existing coating in an x-cut.
2. Fully adhere semitransparent pressure sensitive tape over x-cut intersection.
3. Remove tape by pulling rapidly back over itself at a 180° angle.
4. Adhesion results indicating removal of coating are not acceptable.
C. Adhesion test requirements:
1. Conduct at least two tests in the field of existing roof membrane, one every 10,000 sq. ft., plus any area of worn roofing, such as cracked or abraded surfaces.
2. Any change in roof substrate
3. Existing roof areas installed in phases
4. Shaded areas
5. Areas indicating ponding water
D. Contact Henry® Product Support or your sales representative where adhesion test results indicate jagged coating removal along incision.

III. Moisture survey:

A. The installing contractor must verify the existing roofing assembly is dry and leak free prior to installation.
B. Evaluate existing roof assembly for moisture, including saturated insulation, roof deck, roof components and defective roofing. Repair and replace in accordance with National Roofing Contractors Association (NRCA).
C. Do not install Pro-Grade® Aluminum roof coating* over saturated insulation or substrates.
D. Moisture survey includes a visual inspection and one or more of the following:
1. Infrared thermography
2. Nuclear
3. Electric
4. Roof cor

IV. Repair or re

A. Ensure sk structures working co
B. Ensure fas fasteners
C. Metal:
1. Replace panels, f flashings
2. Remove mechani free of lo
3. Remove coating
D. Modified E
1. Remove defective existing

V. Weather cor

A. Substrate
B. Refer to m

Product name
Pro-Grade® 586
Pro-Grade® 58
Pro-Grade® 59
Pro-Grade® 19
Henry® 295 Me
Pro-Grade® 16

STEP 2: Substrate preparation

I. Clean:

A. Confirm local water run-off ordinances and restrictions prior to cleaning roof.
B. Surface cleaning:
1. MB/smooth BUR and metal:
a. Carefully pressure wash roof surfaces with greater than 2,000 psi pressure to remove loose granules, debris, rust, scale, dirt, dust, chalking, peeling or flaking coatings, etc. Do not force water into the roof system or damage roof surfaces.
b. Remove grease, oils or contaminates which may interfere with adhesion using warm water and mild detergent.
c. Treat areas of algae, mildew or fungus with a solution of household bleach and water.
d. Rinse roof to ensure removal of all detergent or anything else that could affect adhesion.

II. Primers:

A. Metal roof and metal components:
1. Optional rust primer: Install a commercial grade rust-inhibitive primer per primer manufacturer recommendation.

III. Flashing and details:

A. Complete flashings and details prior to Pro-Grade® Aluminum roof coating* installation.
B. Mix Pro-Grade® Aluminum roof coating* with drill and mixer blade prior to, and during use as needed, to main of alu
C. Refe
D. Meta
1. Ho rid a. A to ga la ga

Fastener heads for metal roofs and metal components on MB/BUR roofs	
MB/BUR	Metal
Completely encapsulate fastener heads with Pro-Grade® 187.	Completely encapsulate fastener heads with Henry® 295 Metal Seam Sealer**.

Drains for MB/BUR roofs	
Flashing Options	MB/BUR
Option #1	1. Remove and clean strainer, ring and other drain components. 2. Install one layer of Pro-Grade® 197 at 3 gallons per square (48 wet mils) from the drain hole opening, extend 14" minimum beyond drain. 3. Fully embed Henry® 195 Polyester Fabric into foundation coat, extend 12" beyond drain hole. Brush or roll fabric for proper adhesion and remove all voids. 4. Apply second layer of Pro-Grade® 197 at 3 gallons per square (48 wet mils) from the drain hole opening; ensure fabric is fully coated.
Option #2	1. Remove and clean strainer, ring and other drain components. 2. Apply Pro-Grade® 187 using a trowel at 1/8" thick (125 wet mils) into the drain hole and completely encapsulating the drain bowl. 3. Fully embed Henry® 183 Roof Repair Fabric into Pro-Grade® 187, extend 12" beyond drain hole. Brush or roll fabric for proper adhesion and remove all voids. 4. Apply second layer of Pro-Grade® 187 over fabric at 1/8" thick (125 wet mils); ensure fabric is fully coated and extend roof coating 14" minimum beyond drain.

STEP 3: Roof coating application

I. Application of roof coating: Refer to the Coverage Rate Chart for warranted minimum requirements.

A. Mix Pro-Grade® Aluminum roof coating* with drill and mixer blade, prior to and during use as needed, to maintain consistent viscosity and uniform distribution of aluminum content throughout application.
B. Clean/prepare substrate in accordance with **Step 2: Substrate preparation** of this application guide.
C. Refer to **coverage rate chart** for coating assembly configuration and coverage rates.
1. No foundation coat: proceed to **Step D.**
2. Unreinforced foundation coat assemblies:
a. Apply Pro-Grade® 197, starting installation at low point of roof; extend 8" up vertical surfaces.
b. Allow Pro-Grade® 197 to dry prior to subsequent layer.
c. Proceed to **Step D.**
3. Reinforced foundation coat assemblies:
a. Apply one layer of Pro-Grade® 197, starting installation at low point of roof; extend 8" up vertical surfaces.
b. Install Henry® 195 Polyester Fabric perpendicular to roof slope and fully embed into Pro-Grade® 197; ensure 4" overlap at seams. Brush or roll fabric for proper adhesion and remove all voids. Dry fabric overlap is not acceptable.
c. Immediately apply Pro-Grade® 197 onto Henry® 195 Polyester Fabric; ensure fabric is fully coated. Do not walk on wet Pro-Grade® 197. Allow to dry prior to coating application. Proceed to **Step D.**
D. Install Pro-Grade® Aluminum roof coating* in accordance with this application guide.
1. Installation tips:
a. Application to damp surface will cause Pro-Grade® Aluminum roof coating* discoloration.
b. Install coating to optimize "leaf action"; aluminum flakes floating to surface after initial application:
1. Do not over brush/roll Pro-Grade® aluminum roof coating*. Over brushing will cause aluminum flake disorientation and decrease reflectivity.
2. Utilize high quality soft bristled brush, heavy nap roller, or commercial grade spray equipment.
3. Apply at a consistent/liberal rate.
4. Brush in one direction.
2. Install Pro-Grade® Aluminum roof coating*, extend 8" minimum up vertical surfaces.

Pre-treatment of MB/BUR defects and loose	
MB/BUR	
1. Install Pro-Grade® 187 at 1/8" thick (125 mils), extend 3" minimum on each side of seam. 2. Center 4" wide Henry® 183 Roof Repair Fabric over seam and fully embed into roof mastic, ensuri adhesion and remove all voids. 3. Apply Pro-Grade® 187 at 1/8" thick (125 mils) minimum, extend 3" on each side of seam; ensure f	

Pre-treatment of secure and intact se	
Modified Bitumen (MB)	Metal
Unreinforced foundation coat assemblies	Crimped standing vertical seams
1. Install Pro-Grade® 197 at 3 gallons per square (48 wet mils), extend 4" minimum on each side of seam. 2. Center 6" wide Henry® 195 Polyester Fabric over seam and fully embed into foundation coat, ensuring 3" of fabric on each side of seam. Brush or roll fabric for proper adhesion and remove all voids. 3. Apply Pro-Grade® 197 at 3 gallons per square (48 wet mils), extend 4" minimum on each side of seam; ensure fabric is fully coated.	No seam pre-treatment required.

Roof curbs, parapets and pipe penetrations for MB/		
Flashing Options	MB/BUR	Metal
Option #1	Apply Pro-Grade® 187 using a trowel at 1/8" thick (125 wet mils), extend 4" minimum onto horizontal/vertical surfaces.	Apply Henry® 295 Metal Seam Sealer** horizontal/vertical surfaces.
Option #2	1. Install one layer of Pro-Grade® 197 at 2 gallons per square (32 wet mils), extend 4" 2. Center 6" wide Henry® 195 Polyester Fabric at upturn and fully embed into foundati fabric for proper adhesion and remove all voids. 3. Apply second layer of Pro-Grade® 197 at 2 gallons per square (32 wet mils), extend coated.	

Henry and Pro-Grade are registered trademarks of Henry Company
Kynar is a registered trademark of Arkema
Hylar is a registered trademark of Solvay

Henry® Building Envelope Systems® Roofing | Air Barrier | Waterproofing
Ask us today about other Henry® solutions that help manage the flow of water, air, vapor and energy.
productsupport@henry.com | 1-800-486-1278
www.henry.com
© 2016 Henry Company All rights reserved.
Printed in U.S.A. 141.20JUL8403 (04/16)

What Types Of Roofs Can We Repair?

What Types of Roofs Can We Repair?

Asphaltic

Granulated/Smooth Modified Bitumen



BUR



223

Complete Line of Products
Saving Contactors Time and Money

Pro-Grade® Asphalt Mastics

Henry Pro-Grade® Roof Mastics and Cements



Pro-Grade® Roof Mastics and Cements

Comprehensive portfolio. Simplified selection.

Our streamlined portfolio of roof cements and mastics covers all your application needs in any weather – all while delivering superior workability, durability and water-tight solutions.

Features and Benefits

- 100% underwater adhesion ensures you stop the leak immediately
- Wider application temperature ranges offer greater versatility
- Maintains workable consistency at low temperatures
- For use in any repair application – emergency, permanent, wet/dry or vertical/horizontal



3 1 U.S. GAL

Pro-Grade® 167 Extreme Rubberized Flashing Cement

A superior, rubberized roof cement for all applications and permanent repairs.

- Apply in wet or dry weather conditions
- Contains UV inhibitors and SEBS rubber for enhanced durability
- Installation temperature range (ambient): -20° F to 140° F

Compliance:
- Meets or exceeds ASTM D4586
- 100% underwater adhesion per ASTM D3409
- Miami-Dade County Approved



3 1 U.S. GAL

Pro-Grade® 163 Emergency Leak Repair Sealant

A premium-grade, rubberized roof sealant for immediate roof leak repairs.

- Apply in wet or dry weather conditions
- Tenacious adhesion even when applied underwater
- Installation temperature range (ambient): 0° F to 120° F

Compliance:
- Meets or exceeds ASTM D4586
- 100% underwater adhesion per ASTM D3409
- Miami-Dade County Approved



5 U.S. GAL

Pro-Grade® 161 All Weather Flashing Cement

A premium-grade, rubberized roof cement for all applications.

- Apply in wet or dry weather conditions
- Appropriate for setting and repairing SBS Modified Bitumen flashings
- Low-temperature and summer-grade formulations allow for an installation temperature range (ambient) of 20° F to 120° F

Compliance:
- Meets or exceeds ASTM D4586
- 100% underwater adhesion per ASTM D3409
- Miami-Dade County Approved



5 U.S. GAL

Pro-Grade® 155 Flashing Cement

A contractor-grade, rubberized roof cement for applications where the roof cement is a redundant part of good flashing details.

- Dry applications only
- For vertical and horizontal applications
- Will not sag/slip even at high roof temperatures
- Low-temperature and summer-grade formulations allow for an installation temperature range (ambient) of 20° F to 120° F

Compliance:
- Meets or exceeds ASTM D4586
- Miami-Dade County Approved



5 U.S. GAL

Pro-Grade® 151 Plastic Cement

A contractor-grade roof cement.

- Dry applications only
- For horizontal applications
- Low-temperature and summer-grade formulations allow for an installation temperature range (ambient) of 20° F to 120° F

Compliance:
- Meets or exceeds ASTM D4586
- Miami-Dade County Approved

Henry® A CARLISLE COMPANY

Pro-Grade® 151 Plastic Cement

A Roof Cement For Standard Horizontal Applications Where The Roof Cement Is A Redundant Part Of Good Flashing Details.

- Easier To Apply At Low Temperatures; Low Temp & Summer Grades (20 – 120F)

Compliance:

- Meets Or Exceeds ASTM D4586
- Miami-Dade County Approved

- Color: Black

Sizes:

- **5-gallon Pail**



Henry
A CARLISLE COMPANY

Pro-Grade® 155 Flashing Cement

A Rubberized Roof Cement For Vertical And Horizontal Applications Where The Roof Cement Is A Redundant Part Of Good Flashing Details.

- Won't Sag/Slip Even At High Roof Temperatures (140 F)
- Easier To Apply At Low Temperatures; Low Temp & Summer Grades (20 – 120F)



Compliance:

- Meets Or Exceeds ASTM D4586
- Miami-Dade County Approved

Color: Black

- **Sizes:**
  - **5-gallon Pail**

Henry
A CARLISLE COMPANY

Pro-Grade® 161 All Weather Flashing Cement

A Premium-Grade, Rubberized Roof Cement For All Applications.

- Apply In Wet Or Dry Weather Conditions
- Appropriate For Setting And Repairing SBS Modified Bitumen Flashings
- Low-temperature And Summer-grade Formulations Allow For An Installation Temperature Range (Ambient) Of 20º F To 120º F

Compliance:

- Meets Or Exceeds ASTM D4586
- 100% Underwater Adhesion Per ASTM D3409
- Miami-Dade County Approved

Color: Black

Sizes:

- **5-gallon Pail**





Henry
A CARLISLE COMPANY

Pro-Grade® 163 Emergency Leak Repair Sealant

A Premium-Grade, Rubberized Roof Sealant For Immediate Roof Leak Repairs.

- Apply In Wet Or Dry Weather Conditions
- Tenacious Adhesion Even When Applied Underwater
- Installation Temperature Range (Ambient): 0º F To 120º F

Compliance:

- Meets Or Exceeds ASTM D4586
- 100% Underwater Adhesion Per ASTM D3409
- Miami-Dade County Approved

Color: Black

Sizes:

- **10.1 Fl. Oz. Tube**
- **1-gallon Can**
- **3-gallon Pail**







Henry
A CARLISLE COMPANY

Pro-Grade® 167 Extreme Rubberized Flashing Cement

A Superior, Rubberized Roof Cement For All Applications And Permanent Repairs.

- Apply In Wet Or Dry Weather Conditions
- Contains UV Inhibitors And SEBS Rubber For Enhanced Durability
- Installation Temperature Range (Ambient): -20º F To 140º F

Compliance:

- Meets Or Exceeds ASTM D4586
- 100% Underwater Adhesion Per ASTM D3409
- Miami-Dade County Approved

Color: Black

Sizes:

- **1-gallon Can**
- **3-gallon Pail**







Henry® 183 Yellow Fiberglass Repair Fabric

A Yellow Resin Coated Glass Fabric Woven Fabric Made Of Yarns Of Inert, Flexible Filaments Of Pure Glass

- Acid & Heat Resistant
- Won't Rot or Decay
- Compatible
  - Asphalt
  - Emulsions
  - Coatings
- Uses Include:
  - Penetrations
  - Flashings
  - Seams
  - Repairs



Color: Yellow
Sizes:

- 4" x 150' Roll
- 6" x 25' Roll
- 36" x 150' Roll

Pro-Grade® Roof Mastics and Cements

Our Mastics Work In The Greatest Temperature Extremes

- Products Maintain Workable Consistency Even At Low Temperatures
- Less Inventory To Stock
- Fewer Buckets To Carry Around

All Of Our **Wet/Dry** Mastics Are Formulated To Achieve **100% Underwater Adhesion** Per **ASTM D3409**

- When You're Stopping Leaks, You Want **100%**!



Henry® A CARLISLE COMPANY

Why Pro-Grade® Roof Mastics and Cements

Understanding ASTM D3409

Why having **100% underwater adhesion** matters:
(both of these products claim ASTM D3409)



Competitor

Product is following trowel; notice minimum adhesion underwater



Competitor




Henry

Henry
(Link to Video)


Henry
A CARLISLE COMPANY


Pro-Grade® Roof Mastics and Cements Application

Pro-Grade® Roof Mastics and Cements

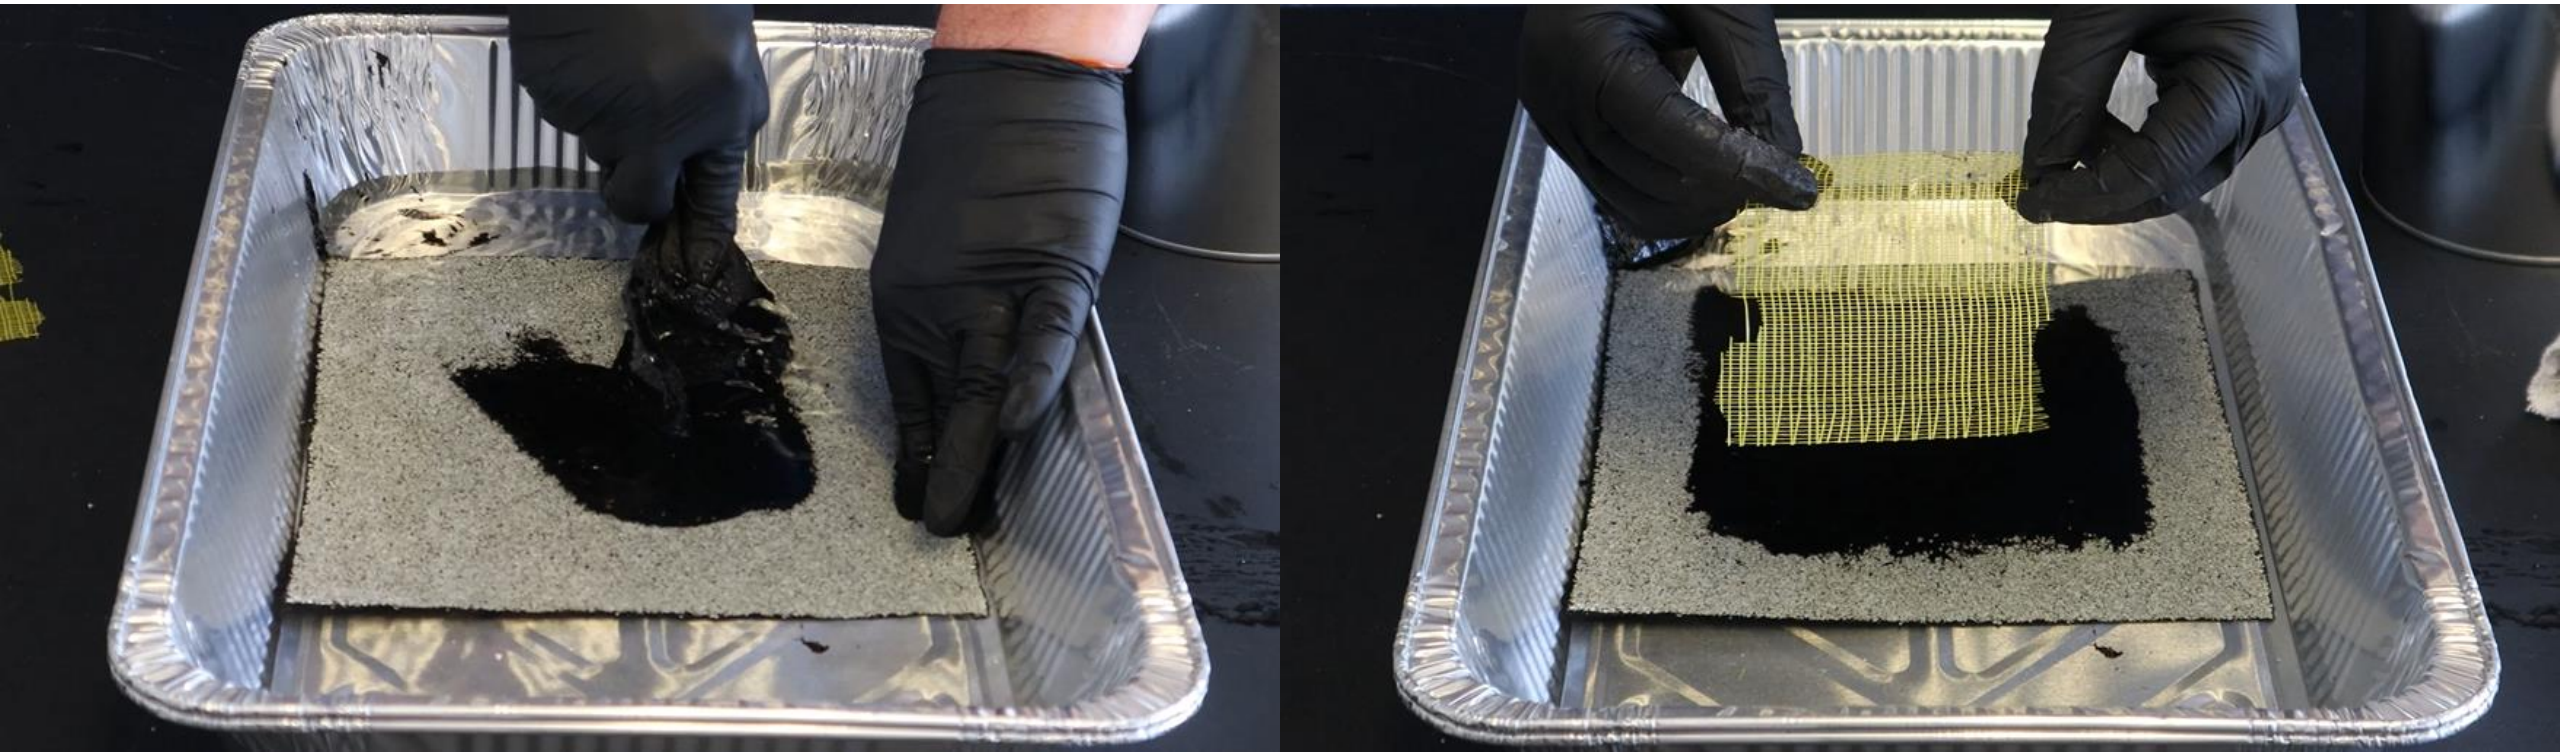

Pro-Grade® Roof Mastics and Cements

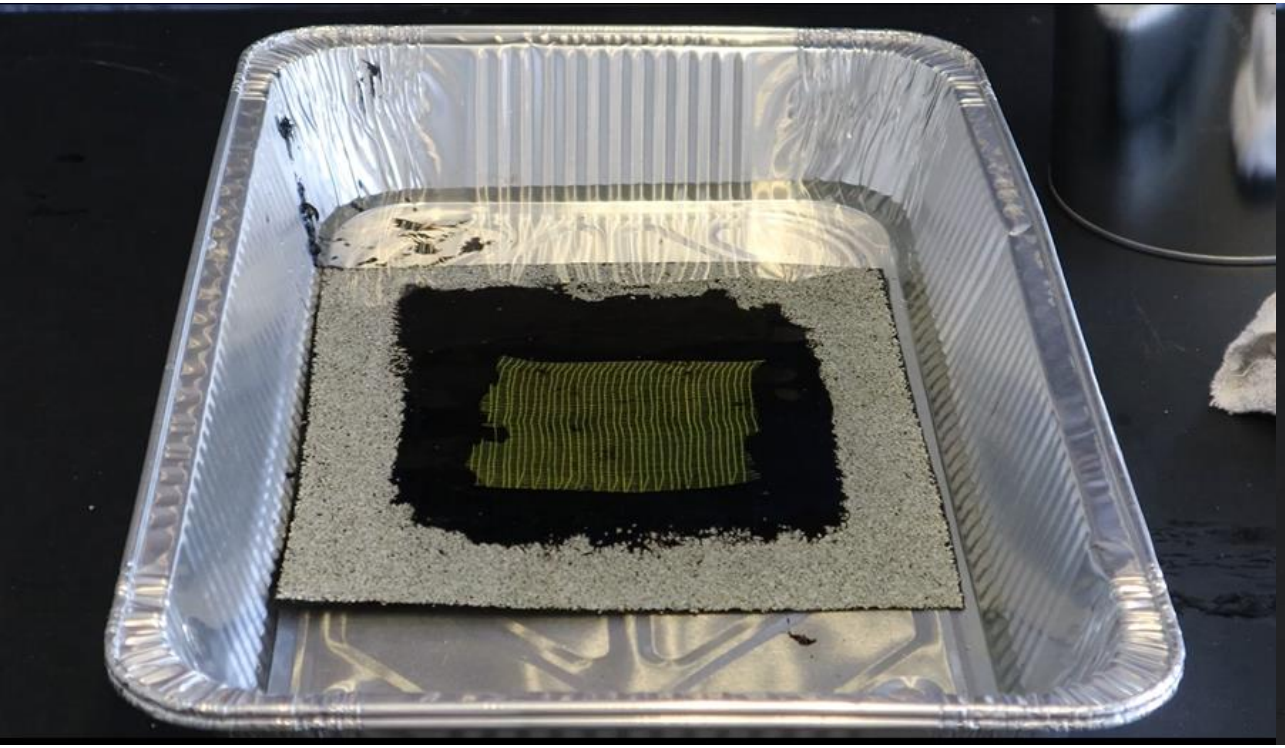

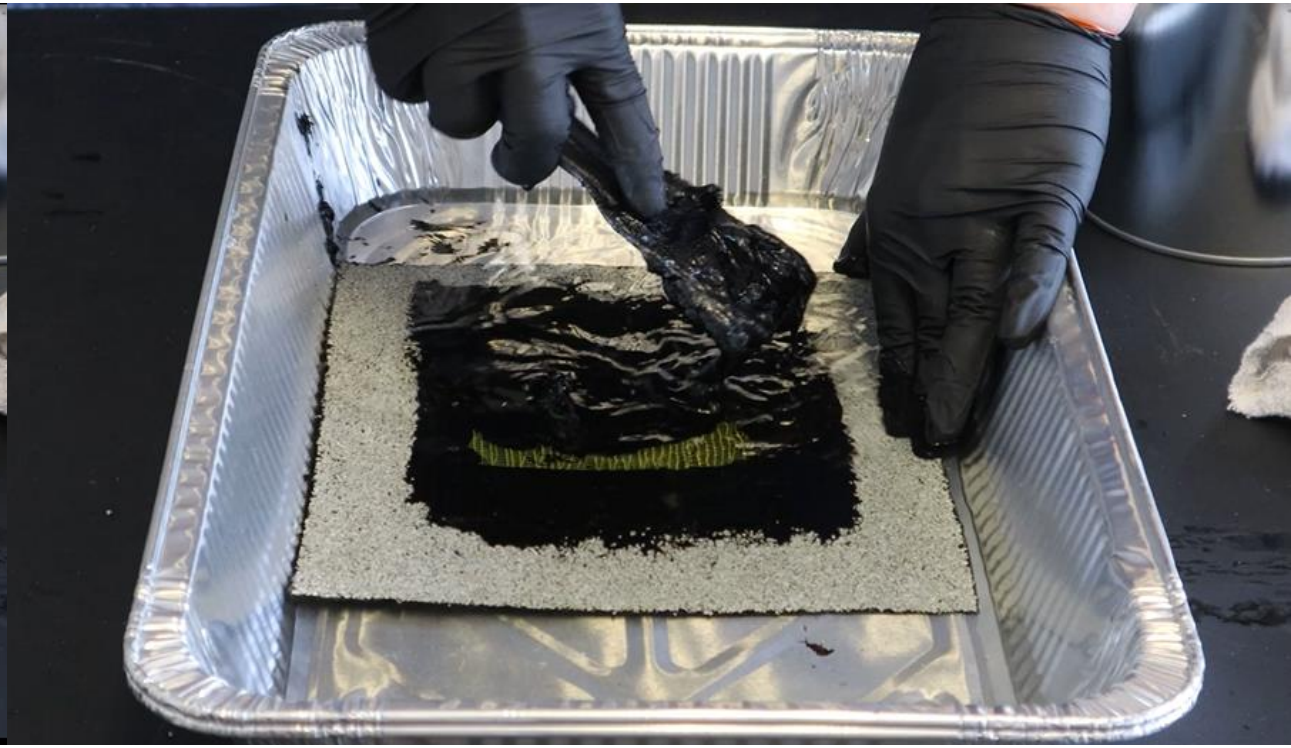

Pro-Grade® Roof Mastics and Cements



Henry
A CARLISLE COMPANY

Warranty Information
Becoming an Authorized Applicator

Building Confidence™

© 2022 Henry Company. All rights reserved.

Warranty Options

Warranty	Coverage	Details
Manufacturer Defect Free Implied Warranty	1 Year or a duration up to product expiration. Product will perform as stated on the data sheet. As per statutory legal requirements.	Requires Proof Of Purchase Material must be handled, stored and installed per manufacturer guidelines.
Limited Lifetime Warranty – Pro-Grade 988 Silicone Only	Warrants Pro-Grade Silicone Products To Be Free Of Defects For The Life Of The Existing Roof.	If there is a defect with the material, then like material will be provided for the life of the roof. Replacement product is free of charge and available thru the Henry website. **Requires Proof of Purchase and must use two products.**
Material Plus Warranty	Provides Material And Labor needed to install the material at No Charge if the product is found to be defective.	1. The contractor must sign a material plus contractor authorization agreement prior to obtaining a material plus warranty. 2. Material plus warranties must be applied for through the henry.com/warranty website by selecting the material plus option.
Gold Seal Warranty	Provides Material And Labor To Repair Affected Area Due To Product(s) Manufacturing Defect Or Workmanship Deficiencies In Installation	1. The contractor must sign a Gold Seal contractor authorization agreement prior to obtaining a material plus warranty. 2. Gold Seal warranties must be applied for through the henry.com/warranty website by selecting the Gold Seal option. 3. Please refer to system warranty guidelines for pricing and application rates.

- **Product(s) must be installed by a Henry Authorized Contractor per Technical Data Sheets and appropriate Guide Specification or Application Guide.**

How to Become a Henry Authorized Contractor?

- Contractor Must Complete The Authorized Contractor Application
  - Submit All Required Documentation To Henry Warranty Department warranty@henry.com and Ray Leake rleake@henry.com
  - Schedule A Training Event With Your Technical Team
  - Once Approved and Contractor Will Receive Authorized Contactor Agreement From Henry Warranty


Henry. A LEADER IN BUILDING ENVELOPE SYSTEMS®

Authorized Contractor Application

Type of Henry Authorization You Are Applying

☐Gold Seal® HRS only – Pro-Grade Acrylic, Aluminum and Silicone *entitles Contractor to apply for Henry Gold Seal Warranties*


☐Material PLUS HRS only – Pro-Grade Acrylic, Aluminum and Silicone® *entitles Contractor to apply for Henry Material PLUS Warranties*

Directions for Application

1. Fill out complete application.
2. Attach valid proof of Liability Insurance; Worker's Compensation Insurance (Canada -WSIB Clearance Letter/Certificate); and if applicable, business license(s) to work in the State(s)/Province(s) listed on application.
3. Email to:

warranty@henry.com
ph: (866) 787-6947
cc: rleake@henry.com


Authorized Contractor Application Available Today For Completion By Authorized Signor

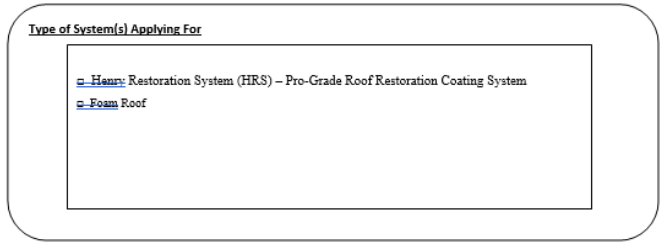
Type of System(s) Applying For

☐ Henry Restoration System (HRS) – Pro-Grade Roof Restoration Coating System

☐ Foam Roof

Training Requirements For Authorization Level:
MUST BE COMPLETED BEFORE THE START OF THE WARRANTED PROJECT

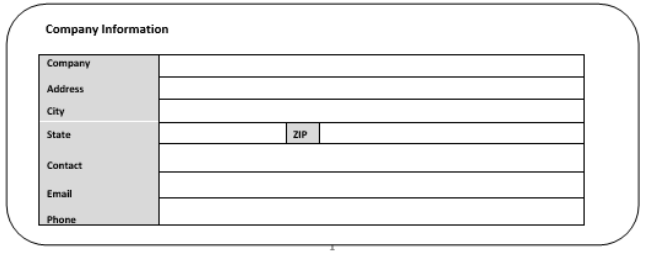
Company Information

Company	
Address	
City	
State	ZIP
Contact	
Email	
Phone	

Materials Plus
- Classroom Training To Cover Installation Guidelines, Application Guidelines And Correct Detailing

Gold Seal
- Review Of Full Product Knowledge Presentation
- Cover Installation Guidelines, Application Guidelines And Correct Detailing with Hands On Training
- Will Include
  - First Job – Start Up Assistance With Technical

OR
  - Start Up Optional With Substantial, Verified Work History In Roof Coatings In The System To Be Applied

Henry® A CARLISLE COMPANY

Types of Contractor Authorization

Material Plus Authorized Contractor	Gold Seal Authorized Contractor
Authorized By Henry Types Of Systems: Silicone Coating Roof Restoration Acrylic Coating Roof Restoration Aluminum Coating Roof Restoration Emulsion Restoration Roofing License (If Required By State) Liability Insurance Worker's Compensation Insurance Business License	Authorized By Henry Types Of Systems: Silicone Coating Roof Restoration Acrylic Coating Roof Restoration Aluminum Coating Roof Restoration Emulsion Restoration Roofing License (If Required By State) Liability Insurance Worker's Compensation Insurance Business License
Warranty Requirements	**Warranty Requirements**
Submit Job Warranty Application Existing Roof Prequalification • Per Applicable HRS Guide Specification Preform Adhesion Test Preform Moisture Survey Install Per Applicable Guide Specification	**Pre-Job Roof Inspection** Submit Job Warranty Application Existing Roof Prequalification • Per Applicable HRS Guide Specification Submit Proof of Adhesion Testing Submit Proof of Moisture Survey Install Per Applicable Guide Specification

Henry Warranty Options

Material Plus Warranty

- Provides Warranty For Henry Products Determined To Be Defective
- Warrants All Henry Products For Same Duration As Restoration Coating
- Contractor Must Be A Henry Material Plus Or Gold Seal Authorized Contractor
- **No Warranty Fee**
- Transferable
- Requires Confirmation That An Adhesion Test And Moisture Survey Was Conducted Where Appropriate
- **No Ponding Water Exclusions (Silicone Only)**

Lifetime Warranty (Pro-Grade 988 Only)

- **Requires Pro-Grade 988 and One Additional Pro-Grade Silicone Product**
- **Requires Stripping of All Seams with Pro-Grade 988 Silicone**
- **Does Not Require To Be An Approved Applicator**
- Transferrable

Gold Seal Warranty

- Provides Warranty For Henry Products Determined To Be Defective
- Warrants All Henry Products For Same Duration As Restoration Coating
- **Covers Workmanship Installation Deficiencies**
- **Contractor Must Be A Henry Gold Seal Authorized Contractor**
- **Contractor Is Only Liable For Two Years Of Workmanship**
  - Other Manufacturers Require Contractor Liability For About Half The Warranty Term
- **Warranty Fee**
- Transferable
- **No Ponding Water Exclusions (Silicone Only)**
- **Requires Pre-Job Inspection, Submittal Of Adhesion Tests And Moisture Survey Conducted Where Appropriate**
- **Final Inspection By Henry Authorized Representative Required**

Final Inspections

© 2022 Henry Company. All rights reserved.

Final Inspections

Process

- Final Inspections Required for **ALL Gold Seal Warranties**
- Contractor Completes The Warranty Application (Project Complete)
  - Submit All Required Documentation to Henry Warranty Department Including:
    - Adhesion Testing Documentation
    - Moisture Survey Documentation
- Henry Warranty Department Informs Area Tech Representative And Contractor to Schedule
- Area Tech Rep Completes Inspection
  - Inspection Report and Punch List Items Sent to Henry Warranty and Contractor
- Contractor Completes Punch List Items
  - Submits Before and After Photos
  - Signs Punch List Completion Form
- If Complete, Henry Issues Warranty to Contractor Via Email And Separate Invoice Sent For Warranty Fee(s)



245

Common Punch List Items

Open Seams







Open Seams







Penetrations Not Sealed







Open Flashings







Thin Coating








Fasteners



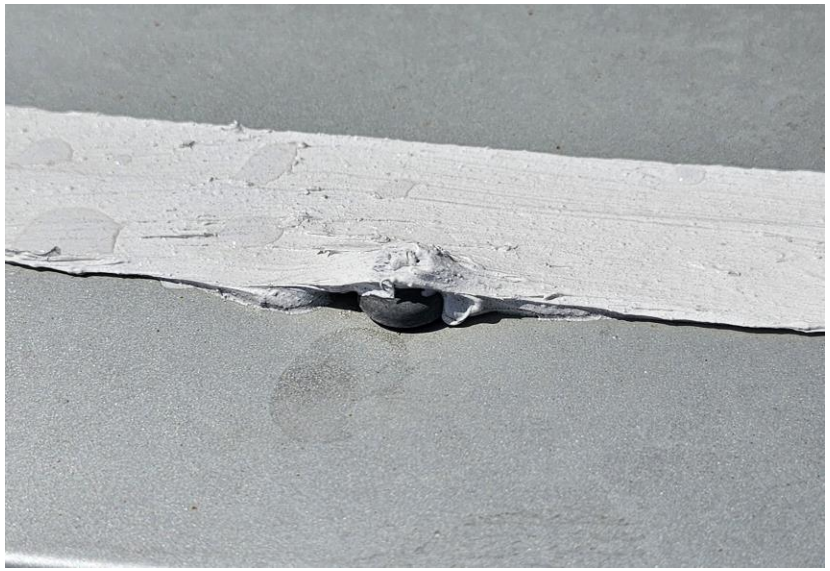



Fasteners/Skylights/Drains







The End Result

© 2022 Henry Company. All rights reserved.

The End Result

BEFORE



AFTER



The End Result

BEFORE



AFTER



The End Result

BEFORE



AFTER



257

The End Result

BEFORE



AFTER



258

The End Result

BEFORE




AFTER



Technical Support

© 2022 Henry Company. All rights reserved.

Technical Field Support

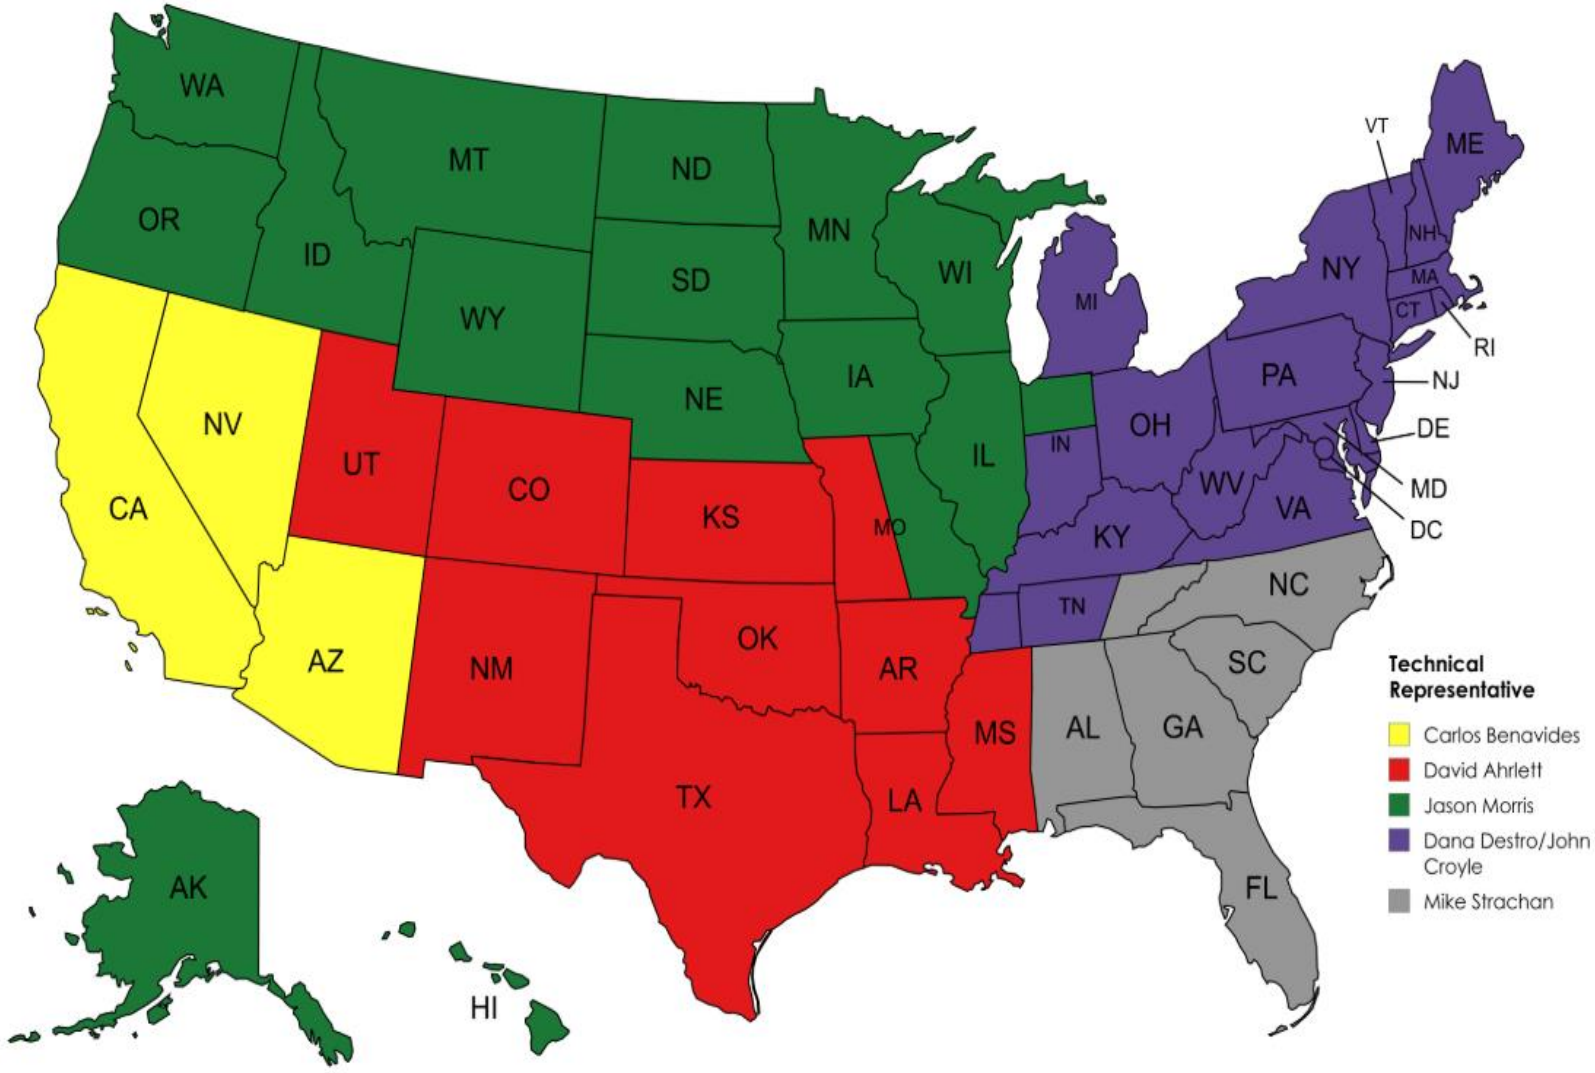

Name	Phone #	Email	Area	Title
Carlos Benavides	951.617.0783	cbenavides@henry.com	CA, AZ, NV	Technical Services Rep
David Ahrlett	817.771.4026	dahrlett@henry.com	TX, OK, AR, Memphis, Western MO, LA, MS, NM, CO, KS, UT	Technical Services Rep
Jason Morris	773.412.9022	jmorris@henry.com	NW. IN, IL, Eastern MO, IA, MN, ND, SD, NE, WA, OR, ID, MT, WY, AK, HI	Technical Services Rep
Dana Destro John Croyle	215.817.6386 440.547.5344	ddestro@henry.com jcroyle@henry.com	ME, VT, VA, NH, MA, CT, RI, NY, NJ, MD, DE, DC, PA, OH, WV, IN, MI, KY, Central and Western TN	Technical Services Rep
Michael Strachan	727.589.6493	mstrachan@henry.com	FL, GA, AL, SC, NC, Eastern TN	Technical Services Rep

Questions?

© 2022 Henry Company. All rights reserved.