

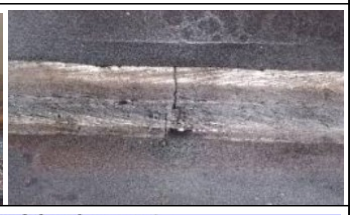
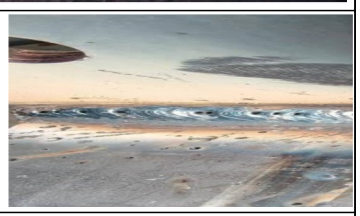
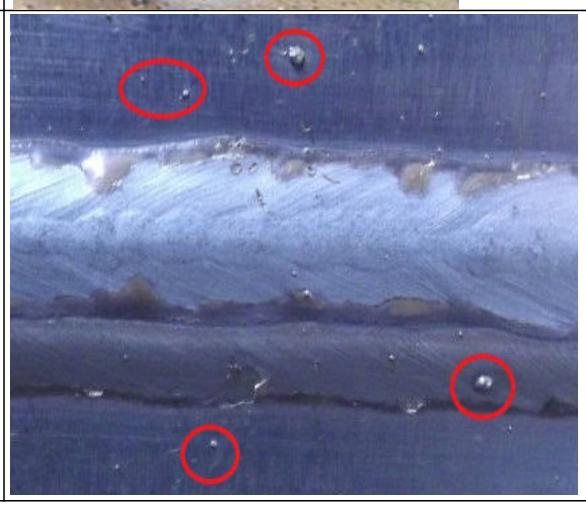
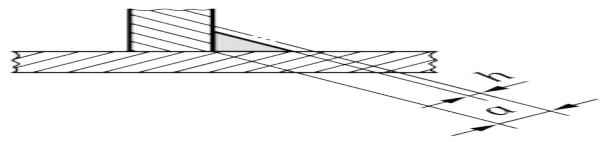
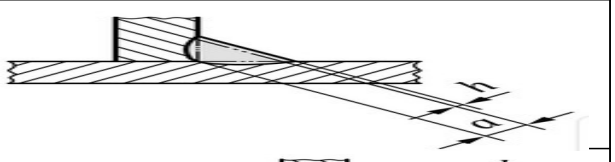
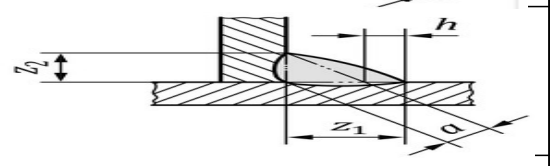
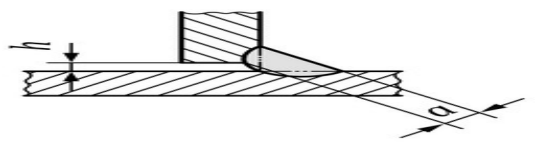
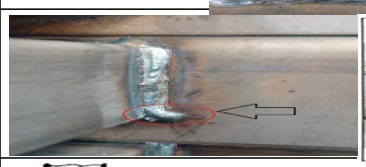
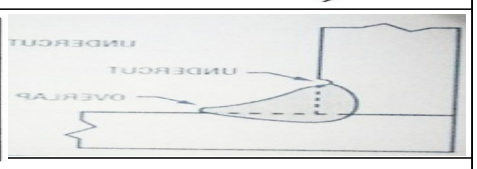
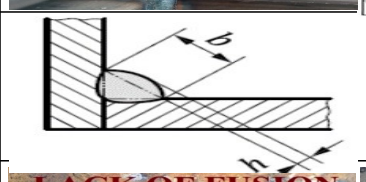
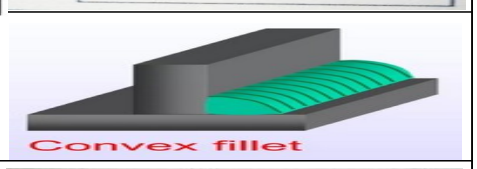
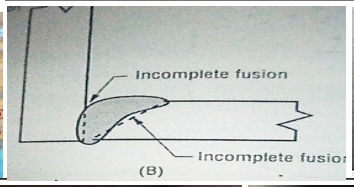
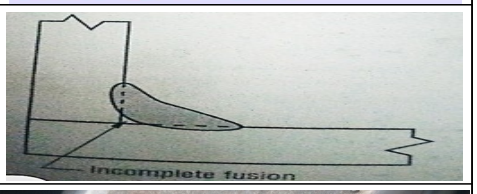
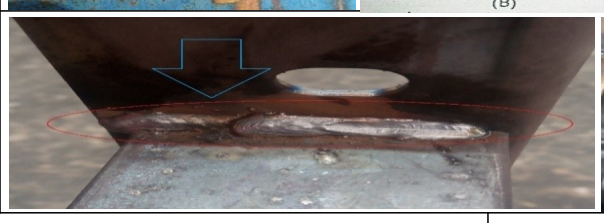
Link Misr International Quality department	Acceptance limits for common welding imperfections according to ISO 5817 - level B & CSA W59 سماحيات القبول لعيوب اللحام طبقا للمواصفات	LINKMISR ADVANCED STORAGE SOLUTIONS

Imperfection	Acceptance criteria		Samples for defects
	For material thickness less than or equal to 3 mm للخامات اقل من او يساوى 3 مم	For material thickness greater than 3 mm للخامات اكبر من 3 مم	
Crack شروخ	All types of cracks arent permitted كل انواع الشروخ مرفوضة		 Root (underbead) crack  Toe crack  
Undercut جروف يمين اوشمال اللحام	Continuous under cut (Not Permitted) Intermittent , Max Depth 0.5 mm المتصل مرفوض اقصي عمق 0.5 مم للمتقطع	Continuous undercut (Not Permitted) Intermittent , Max Depth 0.5 mm اقصي عمق 0.5 مم	 
Surface pore / Surface porosity بخبخة سطحية	Not permitted مرفوض	Not permitted مرفوض	 
Spatter غلو	Excessive clustered spatters arent permitted , regardless size or place تجمع الحبيبات مرفوض بغض النظر عن حجمها او مكانها Separated spatters with distance greater than or equal to 50 mm , and size of each one less than 2 mm (Accepted) الحبيبات المنفصلة بمسافة اكبر من او تساوى 50 مم وحجم الواحدة منها اقل من 2 مم (مقبولة) spatters with size 2 mm or greater (for one spatter , clustered and separated) (Not permitted) الحبيبات بحجم 2 مم او اكبر (سواء اكانت مفردة او مجتمعة او منفصلة (مرفوضة)		 

Link Misr International Quality department		LINKMISR ADVANCED STORAGE SOLUTIONS

Insufficient throat thickness	Not permitted مرفوض	Not permitted مرفوض	a:measured throat thickness after welding. h:shortage in throat thickness after measuring.	
Excessive throat thickness	Less than or equal to 1.3 mm . اقل من او يساوى 1.3 مم		h:excessive length in throat a: throat thickess	
Excessive unequal leg length	Less than or equal to 1.8 mm اقل من او يساوى 1.8 مم		z2=z1-h h:excessive length in leg size	
Incorrect gap / clearance خلوص خطا	Less than or equal to 0.4 mm اقل من او يساوى 0.4 مم	Less than or equal to 0.7 mm اقل من او يساوى 0.7 مم	h=gap/clearance	 
Overlap	Not permitted مرفوض			  
Max.Convexity	Less than or equal to 1.4 mm اقل من او يساوى 1.4			  
Lack of fusion عدم اندماج/انصهار	Not permitted مرفوض			  
Irregularities & sharp edges عدم انتظام /حواف حادة	Not permitted مرفوض			 

Form Code:	WI-PD-03-01	Issue No.: 02	Issue Date:	2/1/2025