A new strategy for fatigue analysis in presence of general multiaxial time varying loadings

Keywords : Fatigue ; Energy ; High cycle ; Plasticity ; Mean stress

Ma Zepeng

Solid Mechanics Laboratory
Ecole Polytechnique

24 September 2016

Outline

1   Weakening scales and yield function

2   Construction of an energy based fatigue approach

3   Damage accumulation

4   Loop on time and scales

5   Application

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   Application

The concept of weakening scales

Outline

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales Application
○○●○○○○○○ 00000000 0000000000
The concept of weakening scales

Physical consideration

1. We follow the Dang Van paradigm. The structure is elastic at the macroscopic scale.

2. At each material points, there is a stochastic distribution of weak points which will undergo strong plastic yielding, which contribute to energy dissipation without affecting the overall macroscopic stress.

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales Application
00●00000 00000000 0000000000

The concept of weakening scales

Statistics method

From a microscopic point of view, there is a distribution of weakening scales, namely $s \in [1, \infty)$. S_{max} is the macroscopic stress intensity. σ_y is the yield limit before weakening.

- $1 \leqslant s \leqslant \sigma_y/S_{max} \longrightarrow S_{max} \leqslant \sigma_y/s \longrightarrow$ elastic regime $\longrightarrow$ no energy dissipation.

- $\sigma_y/S_{max} \leqslant s \leqslant \infty \longrightarrow S_{max} \geqslant \sigma_y/s \longrightarrow$ plastic regime $\longrightarrow$ energy dissipation.

Which is to say at each scale s there is a weakened yield limit σ_y/s, zero initial plastic strain $\underline{\underline{\varepsilon}}_p$ and zero initial backstress $\underline{\underline{b}}$ at initial time t_0.

We assume the weakening scales have a probability distribution of power law :

$$P(s) = Cs^{-\beta},$$

$$\int_1^\infty P(s)ds = \left[\frac{Cs^{1-\beta}}{1-\beta} \right]_1^\infty = 0 - \frac{C}{1-\beta} = 1$$

we get $C = \beta - 1$, so

$$P(s) = Cs^{-\beta} = (\beta - 1)s^{-\beta}$$

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   Application

The concept of weakening scales

Statistics method

Weakening scales distribution

Probability distribution P(S)
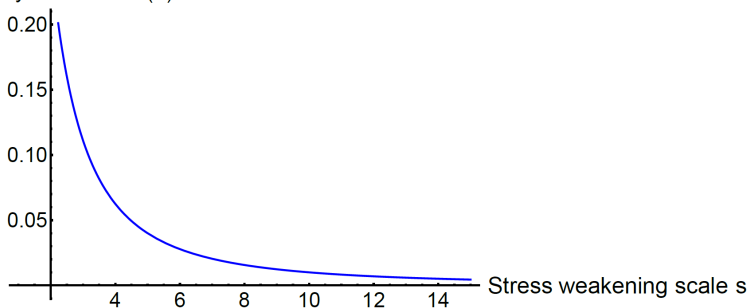
FIGURE : Weakening scales *s* probability distribution curve

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales Application

Yield function with mean stress effect

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   Application
○○○○○●○○   ○○○○○○○○   ○○○○○○○○○○○
Yield function with mean stress effect

Mean stress effect

The idea is to consider as in the work of Maitournam and Krebs that the yield limit σ_y can be reduced in presence of positive mean stress. The mesoscopic yield function can therefore be written as :

$$f(s) = ||\underline{\underline{S}}(s) - \underline{\underline{b}}(s)|| + (\lambda \Sigma_H - \sigma_y)/s \leqslant 0 \tag{1}$$

with $\underline{\underline{S}}$ denoting the deviatoric part of the stress tensor at microscale, and $\underline{\underline{b}}(s)$ the corresponding backstress at the same scale.

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales Application
○○○○○○●○   ○○○○○○○○   ○○○○○○○○○○
Local plastic model

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   Application
○○○○○○○●   ○○○○○○○○   ○○○○○○○○○○
Local plastic model

Description of the mesoscopic stress state

- $\dot{\underline{\underline{S}}}(s, M, t) = dev\dot{\underline{\underline{\Sigma}}}(M, t) - \dfrac{E}{1+\nu}\dot{\underline{\underline{\varepsilon}}}^p(s, M, t)$, Taylor-Lin scale transition model.

- $\dot{\underline{\underline{b}}}(s, M, t) = \dfrac{kE}{E-k}\dot{\underline{\underline{\varepsilon}}}^p(s, M, t)$, kinematic hardening model.

- $\dot{\underline{\underline{\varepsilon}}}^p(s, M, t) = \gamma\dfrac{\partial f(s, M, t)}{\partial \underline{\underline{S}}}$, the associated plastic flow rule assuming $\gamma = 0$ when $f < 0$(elastic) and $\gamma \geqslant 0$ when $f = 0$(plastic).

The local dissipated energy rate per volume at weakening scales s is given by the local entropy dissipation :
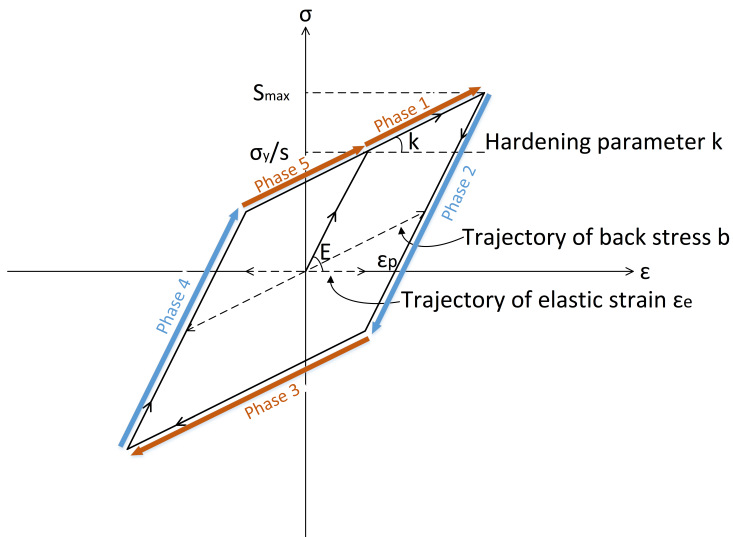
$$\dot{w}(s, M, t) = (\underline{\underline{S}} - \underline{\underline{b}})(s, M, t) : \dot{\underline{\underline{\varepsilon}}}^p(s, M, t).$$

Outline

Uniaxial load with plastic dissipation

Description of the mesoscopic stress state

In uniaxial cyclic loading, there will be 3 kinds of loading patterns :

1. Elastic regime, in phase 2 and 4,where $\dot{\underline{\underline{\varepsilon}}}^p(s, M, t) = 0$, and
   $|\underline{\underline{S}} - \underline{\underline{b}}| < (\sigma_y - \lambda\Sigma_H)/s$.

2. Plastic regime according to plastic flow rule, with increasing plastic deformation, in
   phase 5 and 1, where $\dot{\underline{\underline{\varepsilon}}}^p(s, M, t) = \gamma \dfrac{\underline{\underline{S}}(s) - \underline{\underline{b}}(s)}{||\underline{\underline{S}}(s) - \underline{\underline{b}}(s)||} > 0$ with
   $\gamma = \left(dev\dot{\Sigma}\right)\left(\dfrac{kE}{E - k} + \dfrac{E}{1 + \nu}\right)^{-1}$, with $\underline{\underline{S}} - \underline{\underline{b}} = (\sigma_y - \lambda\Sigma_H)/s$ and $\dot{\underline{\underline{S}}} - \dot{\underline{\underline{b}}} = 0$.

3. Plastic regime in the other direction, in phase 3, there is $\dot{\underline{\underline{\varepsilon}}}^p(s, M, t) < 0$, then
   $\underline{\underline{S}} - \underline{\underline{b}} = -(\sigma_y - \lambda\Sigma_H)/s$ and $\dot{\underline{\underline{S}}} - \dot{\underline{\underline{b}}} = 0$

Cyclic load calculation

Energy dissipation in different phases

- $dW = (S - b)d\varepsilon^p = \dfrac{(E - k)(1 + \nu)}{E(E + k\nu)} \dfrac{\sigma_y - \lambda\Sigma_H}{s} \left(S_{max} - \dfrac{\sigma_y - \lambda\Sigma_H}{s} \right)$ (phase 1)

- $dW(phase1) = dW(phase5) = \dfrac{1}{2}dW(phase3)$.

The local dissipated energy W at point M during one cycle

$$
\begin{aligned}
W_{cyc} &= 4 \int_{(\sigma_y - \lambda\Sigma_H)/S_{max}}^{\infty} dW(s, M, t)P(s)ds \\
&= \frac{4(E - k)(1 + \nu)(\beta - 1)}{E(E + k\nu)\beta(\beta + 1)} \frac{S_{max}^{\beta+1}}{(\sigma_y - \lambda\Sigma_H)^{\beta-1}}.
\end{aligned}
\tag{2}
$$

Where k is the hardening modulus.

Outline

Generalized damage accumulation

We combine a damage incremental law with relative increment of dissipated energy per unit time :

Damage incremental law

$$\delta[1 - (1 - D)^{\gamma+1}]^{1-\alpha} = \frac{\dot{W}}{W_F}\delta t. \tag{3}$$

W_F is the total energy stored in the material.

Generalized damage accumulation

$$\dot{W}(M, t) = \int_{s=1}^{\infty} \dot{w}(s, M, t)P(s)ds = \int_{s=1}^{\infty} \left(\underline{\underline{S}} - \underline{b}\right)(s, M, t) : \underline{\dot{\underline{\varepsilon}}^p}(s, M, t)P(s)ds. \tag{4}$$

Outline

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation **Loop on time and scales** Application

Integration rules for $\dot{W}$ and δD

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   **Loop on time and scales**   Application

Integration rules for $\dot{W}$ and δD

Integration rules

- There are certain limitations of cycle counting method. Firstly we need a load history decomposition in cycles. Secondly in real life the perfect close loop cycle is hardly applicable.

- We propose in a more general method which can be integrated by a step by step strategy.

- Instead of doing the scale integration directly which can be difficult for complex loading, the Gaussian Quadrature rule with Legendre points is used to give the value of local dissipated energy rate.

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation **Loop on time and scales** Application

Integration rules for $\dot{W}$ and δD

Integration rules

The dissipated energy summed on all scales is :

$$
\begin{aligned}
\dot{W} &= \int_1^\infty \dot{w}(s)(\beta - 1)(s)^{-\beta} ds \\
&= \frac{1}{2} \int_{-1}^1 \dot{w} \left[\left(\frac{x+1}{2} \right)^{\frac{1}{1-\beta}} \right] dx \\
&\approx \frac{1}{2} \sum_i \omega_i d\dot{w} \left[\left(\frac{x_i + 1}{2} \right)^{\frac{1}{1-\beta}} \right],
\end{aligned}
\tag{5}
$$

where ω_i and x_i are respectively the weights and nodes of the Gauss Legerndre integration rule used for the numerical integration. In this work, we used 25 points.

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation **Loop on time and scales** Application

Regime determination under multiple scales

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   **Loop on time and scales**   Application

Regime determination under multiple scales

Regime determination

The material could be both in elastic and plastic regime under different scales.

Elastic regime :

There we have $\dot{\underline{\underline{\varepsilon}}}^p = 0$, $\dot{\underline{b}} = 0$ and $\dot{\underline{\underline{S}}} = dev\dot{\underline{\underline{\Sigma}}}$, so

$$\dot{\underline{\underline{S}}} - \dot{\underline{b}} = dev\dot{\underline{\underline{\Sigma}}},$$

yielding

$$\left(\underline{\underline{S}} - \underline{b}\right)(t + dt) = \left(\underline{\underline{S}} - \underline{b}\right)(t) + dev\dot{\underline{\underline{\Sigma}}}dt := \left(\underline{\underline{S}} - \underline{b}\right)_{trial}(s, t + dt). \qquad (6)$$

We are in elastic regime at scale s as long as we satisfy

$$\left(\underline{\underline{S}} - \underline{b}\right)(t + dt) \leqslant (\sigma_y - \lambda\Sigma_H)/s.$$

Regime determination

Plastic regime :

$$
\begin{cases}
\underline{\dot{\underline{\varepsilon}}}^p = \gamma \frac{\underline{\underline{S}} - \underline{b}}{\left\| \underline{\underline{S}} - \underline{b} \right\|}, \gamma > 0, & \text{plastic flow,} & (7) \\[2ex]
\left\| \underline{\underline{S}} - \underline{b} \right\| = \left(\sigma_y - \lambda \Sigma_H \right) / s, & \text{yield limit,} & (8) \\[2ex]
\left(\underline{\underline{S}} - \underline{b} \right) : \left(\underline{\dot{\underline{S}}} - \underline{\dot{b}} \right) = 0, & \text{yield limit time invariance,} & (9) \\[2ex]
\underline{\dot{b}} = \frac{kE}{E - k} \underline{\dot{\underline{\varepsilon}}}^p, & \text{kinematic hardening rule,} & (10) \\[2ex]
\underline{\dot{\underline{S}}} = dev \underline{\dot{\underline{\Sigma}}} - \frac{E}{1 + \nu} \underline{\dot{\underline{\varepsilon}}}^p, & \text{localisation rule.} & (11)
\end{cases}
$$

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation **Loop on time and scales** Application

Regime determination under multiple scales

Regime determination

In all cases, we get in plastic regime :

$$\left(\underline{\underline{S}} - \underline{\underline{b}}\right)(s, t + dt) = \frac{\left(\underline{\underline{S}} - \underline{\underline{b}}\right)_{trial}(s, t + dt)}{1 + \eta}, \tag{12}$$

$$\eta = max \left\{ \underbrace{0}_{elastic\ regime}, \quad \underbrace{\frac{\left\|\underline{\underline{S}} - \underline{\underline{b}}\right\|_{trial} - 1}{(\sigma_y - \lambda\Sigma_H)/s}}_{plastic\ regime\ when\ this\ number\ is\ positive} \right\}.$$

That is to say, when the structure is in elastic regime at time t and scale s, we have $\left(\underline{\underline{S}} - \underline{\underline{b}}\right)(s, t) = \left(\underline{\underline{S}} - \underline{\underline{b}}\right)_{trial}(s, t)$. Otherwise, if the norm of $\left(\underline{\underline{S}} - \underline{\underline{b}}\right)_{trial}(s, t)$ is greater than the local yield limit $(\sigma_y - \lambda\Sigma_H)/s$, $\left(\underline{\underline{S}} - \underline{\underline{b}}\right)(s, t)$ will be projected on the yield limit.

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   **Loop on time and scales**   Application
○○○○○○○○   ○○○○○○○○○○○○○○○○○○○○○○○   ○○○○○○○○○   ○○○○○○○●   ○○○○○○○○○○○○○
Regime determination under multiple scales

Regime determination

Final expression of energy dissipation during time step dt

$$W = \dot{W}dt$$

$$= \frac{1}{2} \sum_i \omega_i \dot{w} \left[\left(\frac{x+1}{2} \right)^{\frac{1}{1-\beta}} \right] dt \tag{13}$$

$$= \frac{(E-k)(1+\nu)}{2E(E+k\nu)} \sum_i \omega_i \left\langle \left\| \underline{\underline{S}} - \underline{\underline{b}} \right\|_{trial} - \frac{\sigma_y - \lambda\Sigma_H}{\left(\frac{x_i+1}{2} \right)^{\frac{1}{1-\beta}}} \right\rangle \frac{\sigma_y - \lambda\Sigma_H}{\left(\frac{x_i+1}{2} \right)^{\frac{1}{1-\beta}}}.$$

$$g_{n+1} = g_n + \frac{\dot{W}dt}{W_F} = g_n + \frac{W}{W_F},$$

$$\text{with } D_n = \left[1 - \left(1 - g_n^{\frac{1}{1-\alpha}} \right)^{\frac{1}{\gamma+1}} \right].$$

Outline

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**
00000000   00000000   00000000   •000000000

One dimensional application to simple cyclic data

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**

One dimensional application to simple cyclic data

Material parameters

The test is performed on a sinusoidal axial load $\Sigma = C sin(t)$, giving the deviatoric

amplitude $S_{max} = \sqrt{\dfrac{2}{3}} C$.

Parameters	Value
Load	$\Sigma = 5e8 sin(t)$ Pa
Young's modulus	$E = 2e11$ Pa
Hardening parameter	$k = 6e8$ Pa
Weakening scales distribution exponent	$\beta = 3$
Hydrostatic pressure sensitivity	$\lambda = 0.5$
Macroscopic yield stress	$\sigma_y = 6.38e8$ Pa
Mean stress	$\Sigma_H = 0$ Pa
Material parameter from Chaboche law(Wohler curve exponent)	$\gamma = 0.5$
Non-linearity of damage accumulation	$\alpha = 0.8$
Initial damage	$D = 0$
Initial time	$t = 0$ s
Dissipated energy to failure per unit volume	$W_F = 3e6$ J
Looping step	1 s

TABLE : Material parameters in a simple cyclic load

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**

One dimensional application to simple cyclic data
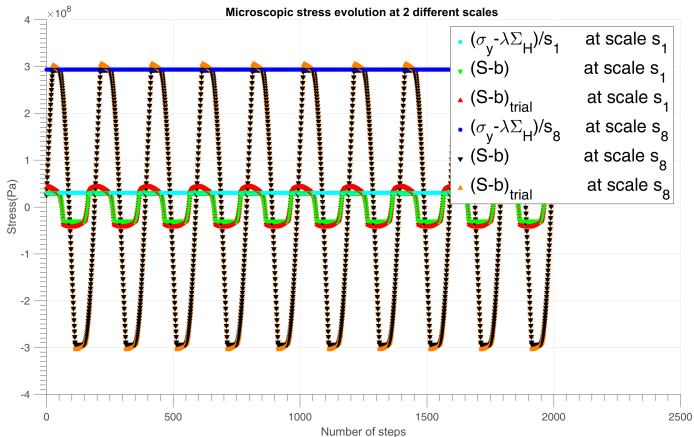
Sinusoidal test

FIGURE : Microscopic $\left(\underline{\underline{S}} - \underline{b}\right)_{trial}$ and $\left(\underline{\underline{S}} - \underline{b}\right)$ evolution with time under different weakening scales in sinusoidal load($s_1 = 21.21657929229650$ and $s_8 = 2.176132808422946$)

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**

One dimensional application to simple cyclic data
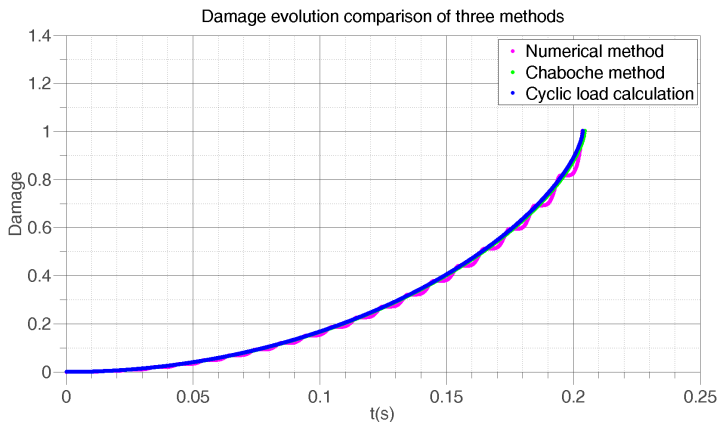
Sinusoidal test

FIGURE : Damage evolution with time under sinusoidal load with two different methods

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**
○○○○○○○○○ ○○○○○○○○ ○○○○○●○○○○○
One dimensional application to simple cyclic data

Convergence test

Because the step by step damage accumulation grows in a power law, so the amplitude of difference grows with time. However, the difference between the two methods swing around 0 so we could consider the numerical method converges in cyclic load calculation method.
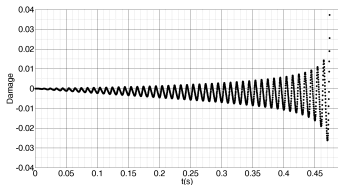
FIGURE : Difference between cyclic load calculation and numerical method as function of time(time step=1/5000s)
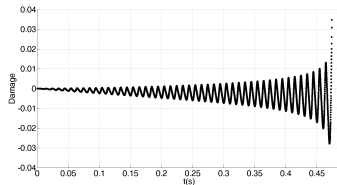
FIGURE : Difference between cyclic load calculation and numerical method as function of time(time step=1/15000s)

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**
00000000   00000000   00000000   000000000   000000●0000

One dimensional application to PSA data

Outline

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**

One dimensional application to PSA data

One dimensional application
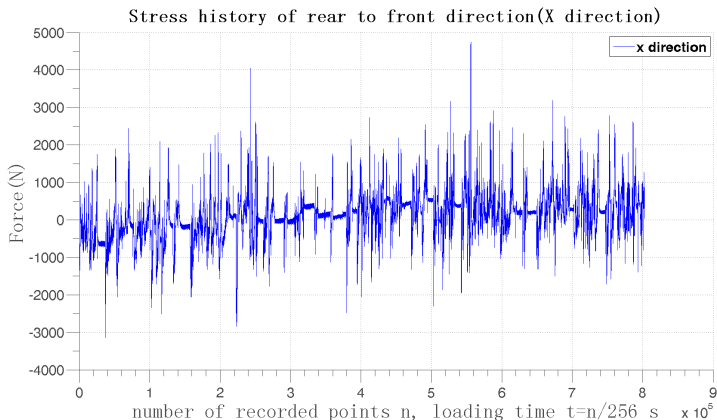
FIGURE : Loading history of X direction, force vs the record index n, with 256 sample recorded per second

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**
00000000   00000000   00000000   0000000   0000000●00●0

One dimensional application to PSA data

One dimensional application

Numerical methods :

- The sample recording rate is 256 per second. In order to accumulate damage using very small steps, we have created 10 additional points between every 2 recorded points by linear interpolation. So the sample rate is $256 * 10$ per second.

- The force on wheel is firstly considered as under uniaxial loading F_x. Here we temporally set $\Sigma_x = F_x/A$ where $A = \dfrac{1}{6e5} \, m^2$ is the area of force, and $W_F = 3e6J$.
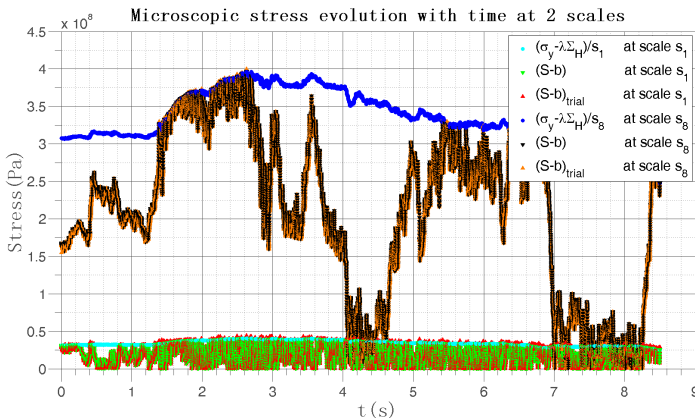
Weakening scales and yield function　　Construction of an energy based fatigue approach　　Damage accumulation　　Loop on time and scales　　**Application**

One dimensional application to PSA data

One dimensional application

FIGURE : $\left(\underline{\underline{S}} - \underline{b}\right)_{trial}$ and $\left(\underline{\underline{S}} - \underline{b}\right)$ evolution with time under different weakening scales in PSA load history

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**

One dimensional application to PSA data

One dimensional application
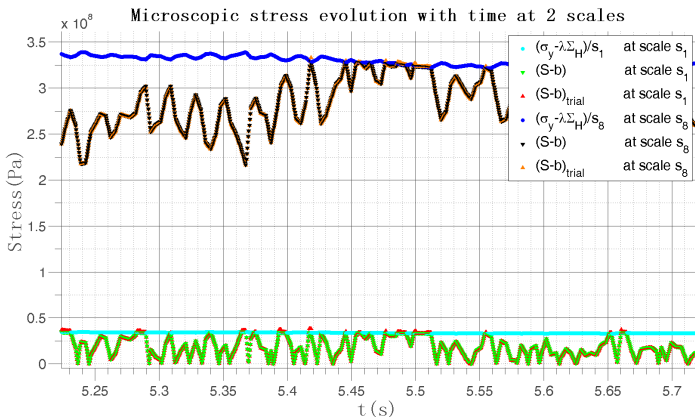
FIGURE : Circled area magnification where there is more $\left(\underline{\underline{S}} - \underline{\underline{b}} \right)_{trial} > \sigma_y$ (plasticity) at scale s_1 than at s_8

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**
○○○○○○○○   ○○○○○○○○   ○○○○○○○○   ○○○○○○○○○○○○

One dimensional application to PSA data

One dimensional application
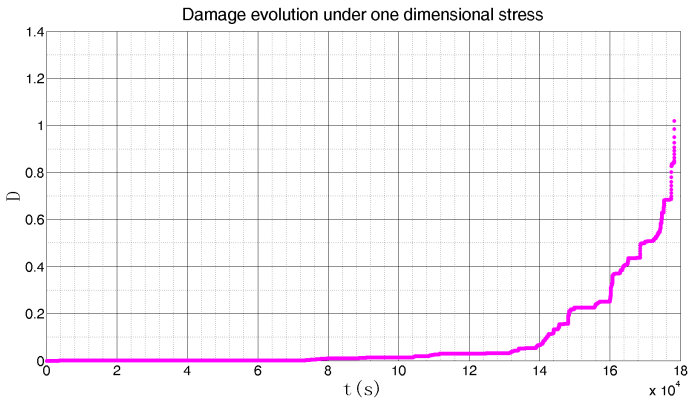
FIGURE : Damage evolution with time at one dimension PSA load history

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**
○○○○○○○○   ○○○○○○○○   ○○○○○○○○   ○○○○○○○○○○○

Multi-dimensional application to PSA data

Outline

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**
○○○○○○○○   ○○○○○○○○○   ○○○○○○○○○○○

Multi-dimensional application to PSA data

Multi-dimensional application

We now consider a situation where we have force recorded measured in 3 different directions as shown in FIGURE 10.
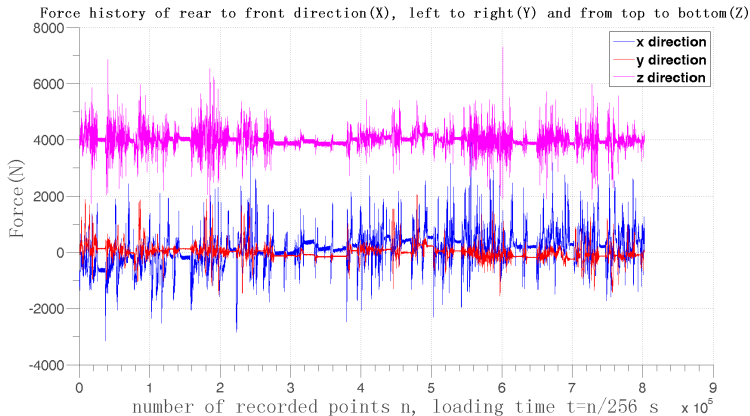

FIGURE : Loading history of 3 different directions

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**
   0000000   00000000   0000000000

Multi-dimensional application to PSA data

Multi-dimensional application

In real case, the vertical force F_z is much larger than the axial and horizontal forces F_x and F_y. However, in order to investigate large domains of interest, we first scale the axial and horizontal forces to reach comparable impact and transform them in principal stresses $c_x \dfrac{F_x}{A}$ applied along the stress principle vector $\underline{e}_\alpha$ (respectively $\underline{e}_\beta$) that we choose randomly. We therefore consider the following macroscopic stress tensor :

$$\underline{\underline{\Sigma}} = \frac{F_z(t)}{A} \underline{e}_1 \otimes \underline{e}_1 + c_x \frac{F_x(t)}{A} \underline{e}_\alpha \otimes \underline{e}_\alpha + c_y \frac{F_y(t)}{A} \underline{e}_\beta \otimes \underline{e}_\beta \qquad (14)$$

where $\underline{e}_\alpha$ and $\underline{e}_\beta$ are principal vectors whose spherical coordinate are θ_x, φ_x, θ_y and φ_y respectively :

$$\underline{e}_\alpha = cos\theta_x \underline{e}_1 + sin\theta_x cos\varphi_x \underline{e}_2 + sin\theta_x sin\varphi_x \underline{e}_3,$$

$$\underline{e}_\beta = cos\theta_y \underline{e}_1 + sin\theta_y cos\varphi_y \underline{e}_2 + sin\theta_y sin\varphi_y \underline{e}_3.$$

Parameter	A(m^2)	c_x	c_y	θ_x	φ_x	θ_y	φ_y
Value	1/6e4	10	60	0.5	0.3	0.6	0.4

TABLE : The structural data in 3D analysis

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**
00000000   00000000   0000000000

Multi-dimensional application to PSA data

Multi-dimensional application

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   Application

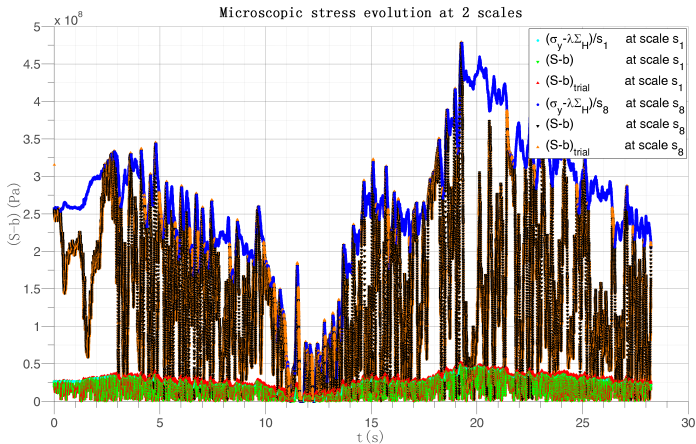Multi-dimensional application to PSA data

Multi-dimensional application

FIGURE : $\left(\underline{\underline{S}} - \underline{b}\right)_{trial}$ and $\left(\underline{\underline{S}} - \underline{b}\right)$ evolution with time under different weakening scales in PSA load history

Weakening scales and yield function   Construction of an energy based fatigue approach   Damage accumulation   Loop on time and scales   **Application**
○○○○○○○○   ○○○○○○○○   ○○○○○○○○○○○○

Multi-dimensional application to PSA data

Multi-dimensional application

FIGURE : Damage evolution under multidimensional stress

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**
○○○○○○○○   ○○○○○○○○   ○○○○○○○○○○
Multi-dimensional application to PSA data

Discussion

Discussion

1 We work on the stress tensor directly in 3D analysis in stead of using the multidimensional equivalent stress.

2 The energy based fatigue approach takes into account impurities and hardness in the material and is applicable to any type of micro plasticity law and multiaxial load geometry.

3 The small step-by-step strategy does not ignore small fluctuations in load history and the big stress effect is magnified which reflects the real situation.

Weakening scales and yield function Construction of an energy based fatigue approach Damage accumulation Loop on time and scales **Application**
00000000   00000000   00000000   00000000   0000000000

Multi-dimensional application to PSA data

Thanks for your attention!