

## Lecture 4 - Eshelby

Dr. Nicholas Smith

Wichita State University, Department of Aerospace Engineering

27 January 2022

1

### schedule

- 27 Jan - 1D Micromechanics (HW1 Due)
- 1 Feb - Mean-field
- 3 Feb - Orientation Averaging (HW2 Due)
- 8 Feb - Variational Calculus

2

- eshelby
- aspect ratio

## eshelby's equivalent inclusion

---

- Eshelby formulated the exact elastic solution for an elliptical inclusion in an infinite matrix
- While this is not often useful, it serves as an exact analytical model to compare numerical results with
- It is also the base for more useful mean-field theories


4

## eshelby's thought experiment

- Eshelby solution starts with a thought experiment
- Suppose we have a homogeneous, elastic body in equilibrium
- We now cut an ellipsoidal piece out of that body and allow it to undergo a stress-free transformation, such as thermal expansion
- This stress-free transformation is referred to as the transformation strain,  $\epsilon^T$

5

## eshelby's thought experiment

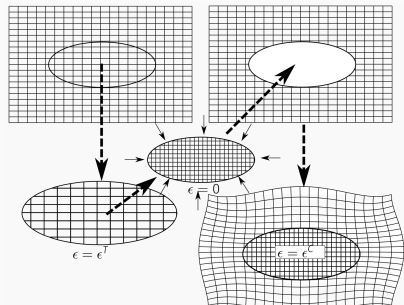

6

## eshelby's thought experiment

- Now, we weld that expanded ellipsoid back into the original body
- Tractions need to be applied to force it to fit
- Once the stresses equilibrate, the ellipsoid has a constrained strain,  $\epsilon^C$

7

- After equilibrium is reached the inclusion is still under a state of uniform strain
- The inclusion stress,  $\sigma_I$  can be found as:

$$\sigma_I = C_m(\epsilon^C - \epsilon^T)$$

Where  $C_m$  is the stiffness of the material.

- One of Eshelby's critical findings is that

$$\epsilon^C = S\epsilon^T$$

- $S$  is known as the Eshelby Tensor, and is a fourth-order tensor
- Function of shape and poisson's ratio
- It has been calculated exactly for ellipsoids, and numerically for other shapes

- $\nu$  represents the matrix Poisson's ratio
- $s$  is the aspect ratio of the fibers
- $l_1 = \frac{2s}{(s^2-1)^{\frac{3}{2}}} (s(s^2-1)^{\frac{1}{2}} - \cosh^{-1} s)$
- $Q = \frac{3}{8(1-\nu)}$
- $R = \frac{1-2\nu}{8(1-\nu)}$
- $T = \frac{Q(4-3l_1)}{3(s^2-1)}$
- $l_3 = 4 - 2l_1$

10

## eshelby tensor

$S_{ijkl}$	Long Fibers	Short Fibers (Ellipsoids)
$S_{1111} = S_{2222}$	$\frac{5-\nu}{8(1-\nu)}$	$Q + Rl_1 + \frac{3T}{4}$
$S_{3333}$	0	$\frac{4Q}{3} + Rl_3 + 2s^2 T$
$S_{1122} = S_{2211}$	$\frac{-1+4\nu}{8(1-\nu)}$	$\frac{Q}{3} - Rl_1 + \frac{4T}{3}$
$S_{1133} = S_{2233}$	$\frac{\nu}{2(1-\nu)}$	$-Rl_1 - s^2 T$
$S_{3311} = S_{3322}$	0	$-Rl_3 - T$
$S_{1212} = S_{1221}$	$\frac{3-4\nu}{8(1-\nu)}$	$\frac{Q}{3} + Rl_1 + \frac{T}{4}$
$= S_{2112} = S_{2121}$		
$S_{1313} = S_{1331}$		
$= S_{3113} = S_{3131}$	$\frac{1}{4}$	$2R - \frac{l_1 R}{2} - \frac{1+s^2}{2} T$
$= S_{3232} = S_{3223}$		
$= S_{2332} = S_{2323}$		
all other $S_{ijkl}$	0	0

11

- Eshelby's initial thought experiment was for a homogeneous material
- To consider a different type of inclusion, we need to relate the transformation strain between some fictitious ellipsoid of matrix material which would be equivalent to our inclusion.
- We will refer to the inclusion stiffness as  $C_f$ , the transformation strain in the matrix as  $\epsilon^T$ , and the transformation strain in the inclusion  $\epsilon^{T*}$ .

12

- We are trying to find a transformation equivalent to our inclusion, so we set

$$\sigma_I = C_m(\epsilon^C - \epsilon^T) = C_f(\epsilon^C - \epsilon^{T*})$$

- Now we substitute the relation  $\epsilon^C = S\epsilon^T$

$$C_m(S - I)\epsilon^T = C_f(S\epsilon^T - \epsilon^{T*})$$

13

- We can solve this to find the transformation strain

$$\epsilon^T = [(C_f - C_m)S + C_m]^{-1} C_f \epsilon^{T*}$$

- Since the transformation strain is arbitrary, we can choose  $\epsilon^T$  such that  $\epsilon^{T*}$  is 0
- Now suppose we impose some strain,  $\epsilon^0$  on the composite

14

## stiffness

- The stress in the inclusion will be

$$\sigma_I = C_m(\epsilon^0 + \epsilon^C - \epsilon^T) = C_f(\epsilon^0 + \epsilon^C)$$

- Simplifying terms gives

$$(C_f - C_m)(\epsilon^0 + \epsilon^C) = -C_m \epsilon^T$$

15



- We now assume  $\epsilon^0 + \epsilon^C = \bar{\epsilon}^f$  and multiply both sides by  $S C_m^{-1}$

$$S (C_m)^{-1} (C_f - C_m) \bar{\epsilon}^f = -\epsilon^C$$

- Recall  $S \epsilon^T = \epsilon^C$
- We can also write  $\epsilon^C$  in terms of  $\bar{\epsilon}^f$

$$S (C_m)^{-1} (C_f - C_m) \bar{\epsilon}^f = \epsilon^0 - \bar{\epsilon}^f$$

16

## strain concentration

- Finally, we can add  $I \bar{\epsilon}^f$  to both sides to find

$$[I + S (C_m)^{-1} (C_f - C_m)] \bar{\epsilon}^f = \epsilon^0$$

- We define the inverse of the left-hand side the Eshelby strain-concentration tensor

$$A^E = [I + S (C_m)^{-1} (C_f - C_m)]^{-1}$$

- The stiffness can be calculated as

$$C = C_m + v_i (C_f - C_m) A^E$$

17

- This stiffness calculation is valid for any number of inclusions
- However, it is only appropriate for very dilute concentrations ( $<1\%$  volume fraction)
- This ensures that the assumption  $\epsilon^0 + \epsilon^C = \bar{\epsilon}^f$


## aspect ratio

---

- Some studies have been done to evaluate Eshelby tensors for short fibers
- Long fibers are approximated by an ellipsoid with infinitely long major axis
- This is not appropriate for short fibers
- We could logically consider three different ellipsoids to represent a short fiber

19

## aspect ratio

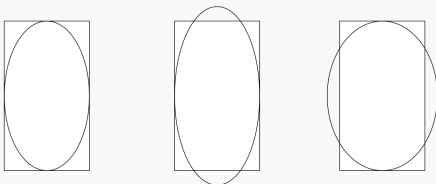

(a) The first ellipsoid considered, with aspect ratio equal to fiber aspect ratio

(b) The second ellipsoid considered, with minor axis equal to fiber diameter and volume equal to fiber volume

(c) The third ellipsoid considered, with major axis equal to fiber length and volume equal to fiber volume

**Figure 1:** aspect ratio comparisons

20

## aspect ratio

- Steif and Hoysan investigated the effect of aspect ratio numerically
- Found that (a) and (c) were good for short fibers
- As fibers get longer, and as stiffness ratio of fiber to matrix increases, (a) gives best results
- (a) is also the easiest to use (same aspect ratio), so that is what is done in Eshelby-based models

21

## fiber orientation

- With Eshelby (and derivative models), fibers at different orientations are modeled as a different inclusion
- Since the Eshelby tensor,  $S$  is a fourth-order tensor, we can treat it the same way as  $C$
- Write it as 6x6 matrix, transform using  $R^\sigma$

22

## example

- As an example, let us consider a “laminate” of short fiber composites
- This is a good approximate for many 3D printed composites
- We have a  $\pm 45^\circ$  laminate, with very short carbon fibers,  $s = 15$

23

## example

- First we find the Eshelby tensor for  $s = 15$
- We also need the matrix Poisson's ratio,  $\nu = 0.4$
- We find the parameters here
- Then we use this slide to find  $S_{ijkl}$
- Notice that this assumes fibers are pointed in the 3-direction

24

## example

- Next, we rotate  $S_{ijkl}$  to find  $S^{45}$  and  $S^{-45}$
- Notice: the eshelby tensor,  $S$  accounts for rotation, we do not rotate  $C_f$
- So we find  $A^{45}$  and  $A^{-45}$

$$A^{45} = \left[ I + S^{45}(C_m)^{-1}(C_f - C_m) \right]^{-1}$$

$$A^{-45} = \left[ I + S^{-45}(C_m)^{-1}(C_f - C_m) \right]^{-1}$$

25

## example

- This gives our total stiffness calculation as

$$C = C_m + v^{45}(C_f - C_m)A^{45} + v^{-45}(C_f - C_m)A^{-45}$$

- If we assume the volume fraction of fibers in our part is 20%
- And that there are equally many fibers in 45 and -45 directions
- Then  $v^{45} = v^{-45} = 0.1$
- Note: Since this is not a dilute concentration, we would not expect this to be very accurate

26

- Python code for this example (with some typical values for  $C_m$  and  $C_f$ ) is posted here<sup>1</sup>

---

<sup>1</sup>[https://colab.research.google.com/drive/1aUs\\_BfeWugyUfwQiKoPx5g-hxvrsQqNs?usp=sharing](https://colab.research.google.com/drive/1aUs_BfeWugyUfwQiKoPx5g-hxvrsQqNs?usp=sharing)


## fiber orientation

---

- While a laminate analogy works well for some cases, in general short fibers are not aligned in laminates
- It is not practical to model each possible fiber orientation as a separate inclusion
- Advani-Tucker introduced a tensorial representation of fiber orientation

28

## fiber in spherical coordinates

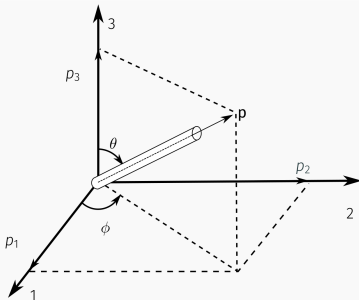

29



Component	Definition
$p_1$	$\sin \theta \cos \phi$
$p_2$	$\sin \theta \sin \phi$
$p_3$	$\cos \theta$

## orientation tensor

- Within a given volume, a distribution of fibers can be defined by some orientation distribution function,  $\psi(\theta, \phi)$ .
- Advani and Tucker introduced tensor representations of fiber orientation distribution functions

$$a_{ij} = \oint p_i p_j \psi(p) dp$$

- And

$$a_{ijkl} = \oint p_i p_j p_k p_l \psi(p) dp$$

- Note: any order tensor may be defined in this manner, the orientation distribution function must be even, due to fiber symmetry, and thus any odd-ordered tensor will be zero.

32

## orientation tensor

- It can be noted that some symmetries must exist due to the way the tensors are defined.
- In the second order tensor we have

$$a_{ij} = a_{ji}$$

- and in the fourth order tensor

$$a_{ijkl} = a_{jikl} = a_{kijl}$$

and so on for any permutation of i, j, k and l.

33

- The orientation tensor is also normalized such that:


$$a_{ii} = 1$$

- And any lower-order tensor can be expressed in terms of the next higher-order tensor, for example

$$a_{ijkk} = a_{ij}$$

34

### example - 2D random

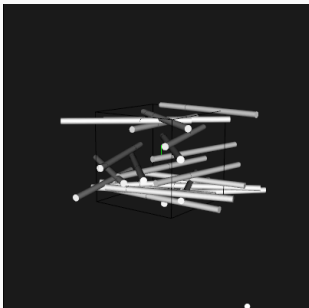

A visualization of a 2D random orientation distribution. This is expressed with the second-order tensor  $a_{11} = a_{22} = 0.5$  with all other  $a_{ij} = 0$ .

35


## example - 3D random



A visualization of a 3D random orientation distribution. This is expressed with the second-order tensor  $a_{11} = a_{22} = a_{33} = 1/3$  with all other  $a_{ij} = 0$ .

36

## example - aligned 45

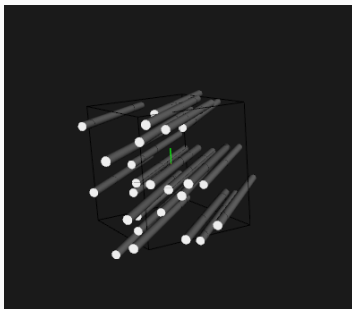

A visualization of a perfectly aligned, off-axis orientation distribution. This is expressed by rotating the tensor with  $a_{11} = 1$  and all other  $a_{ij} = 0$ .

37

- Orientation averaging
- Self-consistent and Mori-Tanaka methods