Numerical analysis of superconducting phases in the extended Hubbard model with non-local pairing

University of Pisa, a.y. 2025-2026

Alessandro Gori*

Thesis for the Master's degree in Physics

Abstract

[To be continued...]

Contents

1 Mean-field theory discussion of the EHM **1**
1.1 Extended Hubbard model symmetries and Wick's theorem . . . 1
1.1.1 Spatial and topological symmetries . . . 1
1.1.2 Spin and charge symmetries . . . 2
1.1.3 Particle-hole symmetry at half-filling . . . 3
1.2 MFT on Hubbard lattices . . . 5
1.2.1 MFT general procedure, self-consistency and Wick's theorem . . . 5
1.2.2 MFT treatment of the pure Hubbard model . . . 6
1.3 The non-local attraction $\hat{H}_V$ as a source of symmetry-breaking interactions . . . 7
1.3.1 Real space description . . . 7
1.3.2 Fourier transform of the model . . . 8
1.4 General approach MFT through iterative Hartree-Fock algorithms . . . 11
1.4.1 Sketch of the Hartree-Fock iterative algorithm . . . 11
1.4.2 Self-consistency and RMPs . . . 12
1.4.3 Fixed density simulations and the role of μ . . . 12
1.5 Square lattice spatial symmetry channels . . . 13

2 The normal phase **17**
2.1 The "normal" phase and its symmetries . . . 17
2.2 Hartree effects: chemical potential renormalization . . . 17
2.2.1 Hartree channel in the normal phase: analytic derivation . . . 18
2.2.2 Hartree contraction energy . . . 19
2.3 Fock effects: bare bands renormalization . . . 19
2.3.1 Fock channel in the normal phase: analytic derivation . . . 20
2.3.2 Fock contraction energy . . . 22
2.3.3 Extending hopping to d-wave bands . . . 22
2.4 Normal free energy density . . . 23
2.5 Numerical simulations . . . 24
2.5.1 HF iterative algorithm sketch . . . 24

*a.gori23@studenti.unipi.it / nepero27178@github.com

3 Antiferromagnetic instability **27**
3.1 The AF phase and its symmetries . . . 27
3.1.1 Antiferromagnetism in the HM . . . 27
3.1.2 Extension to the EHM . . . 29
3.2 Non-local Hartree effects: chemical potential renormalization . . . 30
3.2.1 Hartree channel in the AF phase: analytic derivation . . . 31
3.2.2 Hartree contraction energy . . . 31
3.3 Fock effects: gap and bands renormalization . . . 32
3.3.1 Fock channel in the AF phase: analytic derivation . . . 33
3.3.2 Fock contraction energy . . . 36
3.4 Full MFT hamiltonian and gap complexification . . . 37
3.4.1 The relative phase in the zero temperature half-filled ground state . . . 38
3.4.2 AF phase flavours and spin degeneracy . . . 38
3.5 Stability of the AF phase . . . 39
3.6 AF free energy density . . . 40
3.7 Numerical simulations . . . 41
3.7.1 HF iterative algorithm sketch . . . 41

4 Superconducting instability **43**
4.1 The SC phase and its symmetries . . . 43
4.1.1 Superconductivity in the HM . . . 44
4.1.2 Extension to the EHM . . . 45
4.2 Non-local Hartree effects: chemical potential renormalization . . . 46
4.2.1 Hartree channel in the SC phase: analytic derivation . . . 46
4.2.2 Hartree contraction energy . . . 46
4.3 Fock effects: bare bands renormalization . . . 47
4.3.1 Fock channel in the SC phase: analytic derivation . . . 47
4.3.2 Fock contraction energy . . . 48
4.4 Cooper effects: anisotropic pairing . . . 49
4.4.1 Cooper o.s. channel in the SC phase: analytic derivation . . . 49
4.4.2 Cooper o.s. contraction energy . . . 50
4.4.3 Cooper s.s. channel in the SC phase: analytical considerations . . . 51
4.5 Full MFT hamiltonian and anisotropic pairing . . . 51
4.5.1 The relative phase in the zero temperature half-filled ground state . . . 52
4.6 SC free energy density . . . 52
4.7 Numerical simulations . . . 55
4.7.1 HF iterative algorithm sketch . . . 55

A Superexchange and virtual hopping in Hubbard lattices **57**
A.1 Virtual hopping in the 2-sites Hubbard lattice . . . 57
A.1.1 Exact solution of the half-filled model . . . 58
A.1.2 Virtual hopping . . . 58

B Mean-Field Theory in Hubbard lattices **59**
B.1 Antiferromagnetic phase . . . 59
B.1.1 MFT treatment of the Hartree channel . . . 59
B.1.2 Nambu representation of the AF phase and diagonalization . . . 60
B.1.3 Explicit zero-temperature AF ground state at half-filling . . . 63
B.1.4 Spin degeneracy removal . . . 64
B.1.5 Chemical potential and system density . . . 64
B.1.6 Self-consistency gap equation and magnetization . . . 65
B.1.7 Instability of the commensurate AF solution and atypical metallic bands . . . 66
B.1.8 Hartree-Fock algorithm results in reciprocal space . . . 67
B.2 (Impossibility of a stable) superconducting phase . . . 68
B.2.1 MFT treatment of the Hartree channel . . . 69
B.2.2 MFT treatment of the Cooper channel . . . 69

B.2.3 Nambu representation of the SC phase and diagonalization 70
B.2.4 Explicit zero-temperature SC ground state at half-filling 71
B.2.5 Superconducting fluctuations suppression in the conventional HM 72

List of symbols and abbreviations

AF	Antiferromagnetic
BCS	Bardeen-Cooper-Schrieffer (theory)
β	Inverse temperature
$\Delta^{(\gamma)}$	γ-wave component of the gap function
DoF	Degree(s) of freedom
EHM	Extended Hubbard model
EV(s)	Expectation value(s)
FS	Fermi surface
HF	Hartree-Fock
HFP(s)	Hartree-Fock parameter(s)
HM	Hubbard model
L_ℓ	Number of lattice sites in direction ℓ
LRT	Linear Response Theory
MFT	Mean-Field Theory
NN(s)	Nearest neighbor(s)
RWC(s)	Relevant Wick's contraction(s)
RMP(s)	Renormalized model parameter(s)
SC	Superconductor
SDW	Spin-density wave
SSB	Spontaneous symmetry breaking
T_c	Critical temperature

Chapter 1

Mean-field theory discussion of the EHM

This chapter is devoted to develop a Mean Field Theory (MFT) framework of the Extended Hubbard model (EHM) of Eq. (**??**),

$$\hat{H} = \underbrace{-t \sum_{\langle ij \rangle} \sum_{\sigma} \hat{c}^{\dagger}_{i\sigma} \hat{c}_{j\sigma}}_{\hat{H}_t} \underbrace{+U \sum_{i} \hat{n}_{i\uparrow} \hat{n}_{i\downarrow}}_{\hat{H}_U} \underbrace{-V \sum_{\langle ij \rangle} \sum_{\sigma\sigma'} \hat{n}_{i\sigma} \hat{n}_{j\sigma'}}_{\hat{H}_V}$$

Mean Field Theory (MFT) is a widely used and simple theoretical tool, often sufficient to describe the leading orders in phase transition phenomena of Many-Body Physics. Here MFT is employed generically, in order to later discuss both the effects of the non-local term $\hat{H}_V$ onto the AF phase (Chap. 3), as well as the insurgence of anisotropic superconductivity (Chap. 4). The latter, following the path of Bardeen-Cooper-Schrieffer (BCS) theory in describing conventional s-wave superconductivity. As will be thoroughly described, the lattice spatial structure directly influences the topology of the gap function, giving rise to anisotropic pairing.

1.1 Extended Hubbard model symmetries and Wick's theorem

The general aim of this project is to study the phase diagram of the EHM by comparing ground-state energies of different phases. The phases we consider in next chapters for the EHM are the normal state (N), the antiferromagnetic ordering (AF), given by a non-uniform distribution of charge in each spin sector, and the anisotropic superconducting (SC) phase, described by a uniformly distributed charge allowing for Cooper pairing instabilities.

At the end of this section, in Tab. 1.2 we summarize all symmetries with the relative operations. Throughout the entire thesis we will refer to specific SSB for given groups to establish a specific phase.

1.1.1 Spatial and topological symmetries

Let us start from the trivial topology of the lattice we are working on. The EHM of Eq. (**??**) is evidently translational invariant on both the x and y directions. We refer to these groups as $\mathrm{T}_1^{(x)}$, $\mathrm{T}_1^{(x)}$. The "1" subscript indicates the one-site translations under which the model is symmetric.

Evidently, the following statement holds:

$$\mathrm{T}_n^{(\ell)} \supset \mathrm{T}_{kn}^{(\ell)} \qquad k \in \mathbb{R}$$

A model which is invariant for n-sites translations in the ℓ direction, also is for kn-sites translations. Then we can break translation symmetry in a given direction reducing it to a smaller group. For example, the commensurate AF phase we analyze halves translational invariance,

$$\mathrm{T}_1^{(\ell)} \quad \overset{\text{SSB}}{\rightarrow} \quad \mathrm{T}_2^{(\ell)}$$

since it deals with two-site periodic spin-density waves (SDWs); insted the SC phase preserves translational invariance.

Another natural symmetry of the EHM is the four-fold point group C_4 of $\pi/2$ rotations, expressing the square lattice property being mapped onto itself under said rotations. A similar property as for the translations hold for point groups,

$$\mathrm{C}_n \supset \mathrm{C}_{n/k} \qquad k, n/k \in \mathbb{R}$$

which expresses the fact that, if a system is topologically invariant under n-fold rotations and $k \in \mathbb{R}$ exists such that $n/k \in \mathbb{R}$, then the smaller point group is automatically included. As for translations, we can break the point group reducing it to a smaller subgroup, say

$$\mathrm{C}_4 \quad \overset{\text{SSB}}{\rightarrow} \quad \mathrm{C}_2$$

This is what happens in general with the effective arising of anisotropic corrections to the kinetic hamiltonian due to non-local interactions, as will be discussed in Sec. 2.3. For our purposes, we will leave C_4 unbroken both in the AF and SC phases.

Finally, the system also is inversion-symmetric: let I_2 be the inversion group on the two-dimensional square lattice, containing trivially just the inversion operator and the identity. In general, rotations and mirroring are different operations from a group-theoretical point of view. However, when it comes to the square lattice, operatively it holds

$$\mathrm{I}_2 \equiv \mathrm{C}_2$$

To rotate by π is the same as to mirror the lattice. The inversion symmetry is then already included in C_4, and we leave it unspecified.

1.1.2 Spin and charge symmetries

When it comes to Fermi algebra and operators, an evident symmetry of the EHM is a global U(2) symmetry [**arovas2022hubbard**] given by the transformation

$$\hat{c}_{i\sigma} \rightarrow \sum_{\sigma'} \mathcal{U}_{\sigma\sigma'} \hat{c}_{i\sigma'} \quad \text{with} \quad \mathcal{U}_{\sigma\sigma'} \in \mathrm{U}(2) \tag{1.1}$$

The proof is trivial and follows from the fact that $\mathcal{U}^\dagger \mathcal{U} = \mathcal{U}\mathcal{U}^\dagger = \mathbb{I}$. Note that the the following decomposition holds,

$$\mathrm{U}(2) = \mathrm{SU}(2) \otimes \mathrm{U}^{\mathrm{c}}(1) \tag{1.2}$$

which expresses the separate charge conservation and spin rotational symmetries. In detail:

- $\mathrm{U}^{\mathrm{c}}(1)$ charge conservation, coming from Eq. (1.2) decomposition. By breaking this symmetry, we allow for the total charge to fluctuate in the ground state. This fluctuation is only allowed in the SC phase in the present text;

- SU(2) spin rotation symmetry, also , coming from Eq. (1.2) decomposition. Note that:

  $$\mathrm{SU}(2) \supset \mathrm{U}^z(1)$$

  The z subscript we included to distinguish from the charge group. Hence SU(2) symmetry can be broken, selecting a particular vectorial direction for the order parameter (we call z), and reduced to a smaller $\mathrm{U}^z(1)$ symmetry which is essentially expressed by the conservation of the magnitude of the order parameter.

The last point is important: for the AF phase, for example, there is no need for the magnetization vector to be directed along the physical z-axis, which is the one perpendicular to the lattice plane. SU(2) symmetry breaks when (staggered) magnetization is established along a particular direction, but spin rotations around said direction still are ground state symmetries. This is shown schematically in Fig. 1.1.

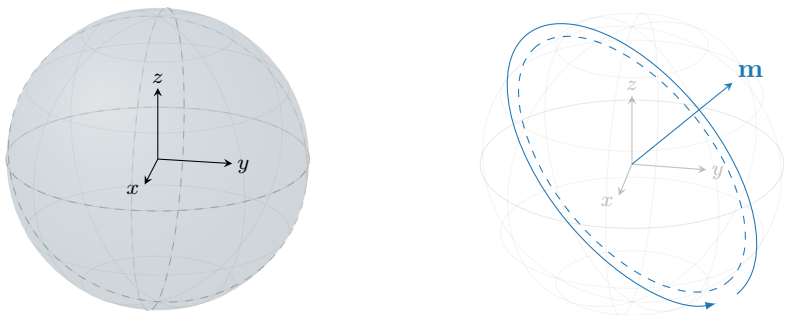

a | SU(2) rotations domain before SSB.

b | U(1) rotations domain after SSB.

Figure 1.1 | Graphic representation of the concept of $\mathrm{SU}(2) \to \mathrm{U}^z(1)$ SSB. The blue color identifies, in both cases, the rotations domain for the current symmetry. When SSB takes place in a magnetic phase, the magnetization order parameter acquires a precise direction which was previously invariant over the full spherical domain. After SSB, the hamiltonian is rotationally invariant only for rotations *around* the selected magnetization vector.

Phase	**SSBs**
AF	$\mathrm{T}_1^{(\ell)} \to \mathrm{T}_2^{(\ell)}$
	$\mathrm{SU}(2) \to \mathrm{U}^z(1)$
SC	$\mathrm{U}^c(1) \to 0$

Table 1.1 | SSB interpretation of the AF and SC phases. In the last line, the 0 on the SSB right-hand side indicates a completely disrupted symmetry.

1.1.3 Particle-hole symmetry at half-filling

The half-filled EHM is of particular interest due to its particle-hole symmetry (PHS), which is immediately distrupted at infinitesimal doping. Let us prove that. Consider the generic unitary operation

$$\mathrm{P} \quad : \quad \hat{c}_{i\sigma} \quad \to \quad e^{i\eta_{i\sigma}} \hat{h}^\dagger_{i\sigma}$$

being in general η_i a phase dependent on the fermionic quantum state $(i\sigma)$. Inserting the above transformation in the EHM, we get

$$\mathrm{P}\{\hat{H}\} = -t \sum_{\langle ij \rangle} \sum_{\sigma} e^{i(\eta_{i\sigma}+\eta_{j\sigma})} \hat{h}_{i\sigma} \hat{h}^\dagger_{j\sigma} + U \sum_i \hat{h}_{i\uparrow} \hat{h}_{i\downarrow} \hat{h}^\dagger_{i\downarrow} \hat{h}^\dagger_{i\uparrow} - V \sum_{\langle ij \rangle} \sum_{\sigma\sigma'} \hat{h}_{i\sigma} \hat{h}_{j\sigma'} \hat{h}^\dagger_{j\sigma'} \hat{h}^\dagger_{i\sigma}$$

For the two interactions $\hat{H}_U$, $\hat{H}_V$ the phase factors cancelled out. We aim to find the conditions under which the above hamiltonian is mapped onto the EHM of (**??**),

$$\mathrm{P}\{\hat{H}\} \stackrel{?}{=} -t \sum_{\langle ij \rangle} \sum_{\sigma} \hat{h}^\dagger_{i\sigma} \hat{h}_{j\sigma} + U \sum_i \hat{h}^\dagger_{i\uparrow} \hat{h}^\dagger_{i\downarrow} \hat{h}_{i\downarrow} \hat{h}_{i\uparrow} - V \sum_{\langle ij \rangle} \sum_{\sigma\sigma'} \hat{h}^\dagger_{i\sigma} \hat{h}_{j\sigma'} \hat{h}_{j\sigma'} \hat{h}_{i\sigma}$$

Before starting the derivation, an extension of the argument of **arovas2022hubbard** [**arovas2022hubbard**] about the conventional HM, let us discuss some properties of the hole operators. Due to the presence of the phase factors in the PHS operative definition, the Fermi anticommutation rules hold regardless of the phase factor:

$$\begin{aligned} \{\hat{h}_{i\sigma}, \hat{h}^\dagger_{j\sigma'}\} &= e^{i(\eta_{i\sigma}-\eta_{j\sigma'})} \{\hat{c}^\dagger_{i\sigma}, \hat{c}_{j\sigma'}\} \\ &= e^{i(\eta_{i\sigma}-\eta_{j\sigma'})} \delta_{ij} \delta_{\sigma\sigma'} \\ &= \delta_{ij} \delta_{\sigma\sigma'} \end{aligned}$$

and evidently:

$$\hat{h}_{i\sigma}\hat{h}^\dagger_{i\sigma} = \hat{n}_{i\sigma}$$

being $\hat{n}_{i\sigma}$ the fermionic number operator on site i with spin σ. It follows, for quartic interactions

$$\begin{aligned}
\hat{h}_{i\sigma}\hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'}\hat{h}^\dagger_{i\sigma} &= -\hat{h}_{i\sigma}\hat{h}_{j\sigma'}\hat{h}^\dagger_{i\sigma}\hat{h}^\dagger_{j\sigma'} \\
&= \hat{h}_{i\sigma}\hat{h}^\dagger_{i\sigma}\hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'} - \hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma'}\delta_{ij}\delta_{\sigma\sigma'} \\
&= -\hat{h}^\dagger_{i\sigma}\hat{h}_{i\sigma}\hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'} + \hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'} - \hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma'}\delta_{ij}\delta_{\sigma\sigma'} \\
&= \hat{h}^\dagger_{i\sigma}\hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma'}\hat{h}_{j\sigma'} - \hat{h}^\dagger_{i\sigma}\hat{h}_{i\sigma} + \hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'} - \hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma'}\delta_{ij}\delta_{\sigma\sigma'} \\
&= -\hat{h}^\dagger_{i\sigma}\hat{h}^\dagger_{j\sigma'}\hat{h}_{i\sigma}\hat{h}_{j\sigma'} - \hat{h}^\dagger_{i\sigma}\hat{h}_{i\sigma} + \hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'} - \left(\hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma'} - \hat{h}^\dagger_{i\sigma}\hat{h}_{j\sigma'}\right)\delta_{ij}\delta_{\sigma\sigma'} \\
&= \hat{h}^\dagger_{i\sigma}\hat{h}^\dagger_{j\sigma'}\hat{h}_{j\sigma'}\hat{h}_{i\sigma} + (\hat{n}_{i\sigma} + \hat{n}_{j\sigma'}) - 1 - \left(\hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma'} - \hat{h}^\dagger_{i\sigma}\hat{h}_{j\sigma'}\right)\delta_{ij}\delta_{\sigma\sigma'}
\end{aligned}$$

The first term of the last passage is mirrored with respect to the starting term. Now, let us deal with the kinetic, local and non-local interactions separately.

Kinetic term. Consider the kinetic term,

$$\mathrm{P}\{\hat{H}_t\} = -t\sum_{\langle ij\rangle}\sum_{\sigma} e^{i(\eta_{i\sigma}+\eta_{j\sigma})}\hat{h}_{i\sigma}\hat{h}^\dagger_{j\sigma}$$

It suffices to anticommute the two fermionic operators, and exchange site labels $i \leftrightarrow j$, to get

$$\mathrm{P}\{\hat{H}_t\} = -t\sum_{\langle ij\rangle}\sum_{\sigma} e^{i(\eta_{i\sigma}+\eta_{j\sigma}+\pi)}\hat{h}^\dagger_{i\sigma}\hat{h}_{j\sigma}$$

A necessary condition on the unitary operation P is the following,

$$\eta_{i\sigma} + \eta_{j\sigma} = (2k-1)\pi \quad \text{with} \quad k \in \mathbb{Z}$$

valid for NN sites.

Local repulsion. Substitute in $\hat{H}_U$ the above derivation,

$$\begin{aligned}
\mathrm{P}\{\hat{H}_U\} &= U\sum_i \hat{h}_{i\uparrow}\hat{h}_{i\downarrow}\hat{h}^\dagger_{i\downarrow}\hat{h}^\dagger_{i\uparrow} \\
&= U\sum_i \hat{h}^\dagger_{i\uparrow}\hat{h}^\dagger_{i\downarrow}\hat{h}_{i\downarrow}\hat{h}_{i\uparrow} + U\sum_i(\hat{n}_{i\uparrow} + \hat{n}_{i\downarrow}) - U\sum_i(1) \\
&= U\sum_i \hat{h}^\dagger_{i\uparrow}\hat{h}^\dagger_{i\downarrow}\hat{h}_{i\downarrow}\hat{h}_{i\uparrow} + U(\hat{N} - L_xL_y)
\end{aligned}$$

Thus, a state realizing

$$\langle\hat{N}\rangle = L_xL_y$$

preserves PHS in the local sector.

Non-local attraction. Proceed identicall for $\hat{H}_V$,

$$\begin{aligned}
\mathrm{P}\{\hat{H}_V\} &= -V\sum_{\langle ij\rangle}\sum_{\sigma\sigma'}\hat{h}_{i\sigma}\hat{h}_{j\sigma'}\hat{h}^\dagger_{j\sigma'}\hat{h}^\dagger_{i\sigma} \\
&= -V\sum_{\langle ij\rangle}\sum_{\sigma\sigma'}\hat{h}^\dagger_{i\sigma}\hat{h}^\dagger_{j\sigma'}\hat{h}_{j\sigma'}\hat{h}_{i\sigma} - V\sum_{\langle ij\rangle}\sum_{\sigma\sigma'}(\hat{n}_{i\sigma} + \hat{n}_{j\sigma'}) + V\sum_{\langle ij\rangle}\sum_{\sigma\sigma'}(1) \\
&= -V\sum_{\langle ij\rangle}\sum_{\sigma\sigma'}\hat{h}^\dagger_{i\sigma}\hat{h}^\dagger_{j\sigma'}\hat{h}_{j\sigma'}\hat{h}_{i\sigma} - 2zV(\hat{N} - L_xL_y)
\end{aligned}$$

Symmetry	Operations
$\mathrm{T}_1^{(x)} \otimes \mathrm{T}_1^{(y)}$	One-site discrete translations separately in both directions
C_4	Four-fold point group (real $\pi/2$ angle rotations)
$\mathrm{U}^{\mathrm{c}}(1)$	Charge-conserving global phase shifts
SU(2)	Three-dimensional rotations in spin space
PHS	Particle-hole exchange (only at half filling)
$\mathrm{U}^{z}(1)$	Reduced two-dimensional rotations in spin space

Table 1.2 Model symmetries and relative group operations. Note that $\mathrm{U}^{\mathrm{c}}(1)$ represents the charge conserving group, while $\mathrm{U}^{z}(1)$ represents the subgroup obtained by breaking the SU(2) symmetry with a vector order parameter and preserving its amplitude. Since the latter is "derived" from SU(2), we write it separated from the four main symmetries of the model.

with $z = 4$ the lattice coordination number. In the last passage, we used that on the square lattice

$$\begin{aligned}\sum_{\langle ij\rangle}(1) &= \sum_{i\in\mathcal{S}/2}\sum_{j\in\mathrm{NN}(i)}(1)\\ &= \frac{L_x L_y}{2}\times z\end{aligned} \tag{1.3}$$

which will turn out quite often. As before, an half-filled phase preserves PHS in the non-local sector. In last passage we used the fact that summing over NNs means overcounting each site $z/2$ times, and spin degeneracy.

No other condition on phases is derived, thus we conclude the half-filled EHM preserves PHS if the two sublattices $\mathcal{S}_a$, $\mathcal{S}_b$ the square lattice can be divided into, being a (trivial) bipartite lattice, differ by a π phase difference under PHS transform. In other words, if P is defined by the unitary operation

$$\mathrm{P} \quad : \quad \begin{cases}\hat{c}_{i\sigma} \to \hat{h}^{\dagger}_{i\sigma} & \text{for} \quad i\in\mathcal{S}_a\\ \hat{c}_{i\sigma} \to -\hat{h}^{\dagger}_{i\sigma} & \text{for} \quad i\in\mathcal{S}_b\end{cases}$$

and the system is half-filled, PHS is respected. Any other phase choice, as long as it alternates by π on the two sublattices, is good enough. To summarize, we report in Tab. 1.2 all identified symmetries.

1.2 MFT on Hubbard lattices

This section serves as groundwork for everything that follows. We here define the MFT scheme as well as the iterative HF computational scheme we use to estimate parametrically the relevant physical quantities of the various phases. We start by recalling the general features of MFT and then move to the specificity of the EHM, apply Wick's theorem and finally move to algorithic aspects.

1.2.1 MFT general procedure, self-consistency and Wick's theorem

The Mean Field Theory approach to any fermionic quartic operator is given by the following procedure: given the hamiltonian made of the quadratic operators $\hat{A}$ and $\hat{B}$

$$\hat{H} \equiv \hat{A}\hat{B}$$

we define the fluctuations

$$\delta\hat{A} \equiv \hat{A} - \langle\hat{A}\rangle \qquad \delta\hat{B} \equiv \hat{B} - \langle\hat{B}\rangle$$

thus the following chain holds:

$$\begin{aligned}\hat{A}\hat{B} &= \langle\hat{A}\rangle\langle\hat{B}\rangle + \delta\hat{A}\langle\hat{B}\rangle + \langle\hat{A}\rangle\delta\hat{B} + \delta\hat{A}\delta\hat{B}\\ &= -\langle\hat{A}\rangle\langle\hat{B}\rangle + \hat{A}\langle\hat{B}\rangle + \langle\hat{A}\rangle\hat{B} + \underbrace{\delta\hat{A}\delta\hat{B}}_{\mathcal{O}(\delta)^2}\end{aligned}$$

which implies

$$\langle \hat{H} \rangle = \langle \hat{A} \rangle \langle \hat{B} \rangle + \langle \delta \hat{A} \delta \hat{B} \rangle$$

Thus, if $|\langle \hat{A} \rangle \langle \hat{B} \rangle| \gg |\langle \delta \hat{A} \delta \hat{B} \rangle|$, in a statistical sense we can neglect the $\mathcal{O}(\delta)^2$ part of the hamiltonian and approximate

$$\hat{H} \simeq \hat{A} \langle \hat{B} \rangle + \langle \hat{A} \rangle \hat{B} - \langle \hat{A} \rangle \langle \hat{B} \rangle \quad \Longrightarrow \quad \langle \hat{H} \rangle \simeq \langle \hat{A} \rangle \langle \hat{B} \rangle \tag{1.4}$$

Self consistency of MFT procedure is thus embodied by the condition

$$\left| \frac{\langle \delta \hat{A} \delta \hat{B} \rangle}{\langle \hat{A} \rangle \langle \hat{B} \rangle} \right| \ll 1 \quad \Longrightarrow \quad \left| \frac{\langle \hat{A} \hat{B} \rangle}{\langle \hat{A} \rangle \langle \hat{B} \rangle} - 1 \right| \ll 1 \tag{1.5}$$

which essentially states that the least the fluctuations, the better the approximation. This rule of thumb is necessary in order to interpret the physical relevance of numerical MFT results. We will come back to this in the end, for now assuming the validity of MFT approximation and deriving the mathematical results.
[To be continued...]

1.2.2 MFT treatment of the pure Hubbard model

The pure Hubbard model, $\hat{H}_t + \hat{H}_U$, offers a simple framework for MFT analysis of the AF phase: this is described in detail in App. **??**. The key passage is there given by the MFT approximation

$$\hat{n}_{i\uparrow} \hat{n}_{i\downarrow} \simeq \hat{n}_{i\uparrow} \langle \hat{n}_{i\downarrow} \rangle + \langle \hat{n}_{i\uparrow} \rangle \hat{n}_{i\downarrow} + (\text{constants}) \tag{1.6}$$

from which the AF structure is simply recovered. In terms of the discussion of the above paragraph, we have $\hat{A} \equiv \hat{n}_{i\uparrow}$ and $\hat{B} \equiv \hat{n}_{i\downarrow}$. However the "full" operator is given by

$$\hat{n}_{i\uparrow} \hat{n}_{i\downarrow} = \hat{c}^\dagger_{i\uparrow} \hat{c}^\dagger_{j\downarrow} \hat{c}_{j\downarrow} \hat{c}_{i\uparrow}$$

which contracts in three different ways following Wick's Theorem:

$$\langle \hat{c}^\dagger_{i\uparrow} \hat{c}^\dagger_{i\downarrow} \hat{c}_{i\downarrow} \hat{c}_{i\uparrow} \rangle \simeq \underbrace{\langle \hat{c}^\dagger_{i\uparrow} \hat{c}^\dagger_{i\downarrow} \rangle \langle \hat{c}_{i\downarrow} \hat{c}_{i\uparrow} \rangle}_{\text{Cooper}} - \underbrace{\langle \hat{c}^\dagger_{i\uparrow} \hat{c}_{i\downarrow} \rangle \langle \hat{c}^\dagger_{i\downarrow} \hat{c}_{i\uparrow} \rangle}_{\text{Fock}} + \underbrace{\langle \hat{c}^\dagger_{i\uparrow} \hat{c}_{i\uparrow} \rangle \langle \hat{c}^\dagger_{i\downarrow} \hat{c}_{i\downarrow} \rangle}_{\text{Hartree}} \tag{1.7}$$

where the $-$ sign in the Fock term comes from fermionic anticommutation rules.

As a first approximation, the theorem is assumed to hold (which, in a BCS-like fashion, is equivalent to assuming for the ground-state to be a coherent state). The AF ground state reduces translational invariance and rotational symmetry, as explained in Tab. 1.1. Thus, of the three terms above, when considering the pure Hubbard model in AF phase:

- Cooper fluctuations are suppressed, because they break charge conservation;
- Similarly the Fock term is null as well because if $i = j$ and $\sigma' = \overline{\sigma}$ (as is for the local interaction, which contains the operator $\hat{n}_{i\uparrow} \hat{n}_{i\downarrow}$) the expectation values involved are describing a process breaking the survivor $\mathrm{U}^z(1)$ spin symmetry.

Thus, correctly, the Wick's decomposition of pure HM only involves Hartree-terms of Eq. (1.7), getting us back to (1.6). The distinction between the normal phase and the AF phase is given by whether the Hartree fluctuations break or not translational symmetry: AF is indeed a specific SDW ordering which weakens the latter. In general the three parts of the decomposition (Hartree, Fock, Cooper) need to be considered altogether: this is what is done in the next chapters. What said here extends naturally to the EHM: the relevant contributions for each phase given by the local repulsion $\hat{U}$ in the EHM are listed in Tab. 1.3.

Term	Normal phase	Antiferromagnet	Superconductor
Hartree			
Fock	Prohibited	Prohibited	Prohibited
Cooper	Prohibited	Prohibited	

Table 1.3 | Summary of Wick's terms selection rules and relevant contributions to the effective hamiltonian for each phase limitedly to $\hat{H}_U$.

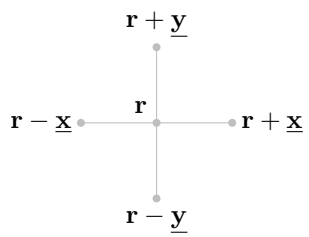

Figure 1.2 | Schematic representation of the four NNs of a given site i for a planar square lattice.

1.3 The non-local attraction $\hat{H}_V$ as a source of symmetry-breaking interactions

Let us now extend the discussion to the EHM and consider the NN non-local attraction,

$$\hat{H}_V \equiv -V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma\sigma'} \hat{n}_{\mathbf{r}\sigma} \hat{n}_{\mathbf{r}'\sigma'} \tag{1.8}$$

where we changed notation, and replaced the site index i with its 2D position on the lattice

$$i \quad \rightarrow \quad \mathbf{r} = (x, y)$$

Let also the lattice versors,

$$\underline{\mathbf{x}} \equiv (1, 0) \qquad \underline{\mathbf{y}} \equiv (0, 1)$$

as in Fig. 1.2.

Evidently the hamiltonian can be decomposed in various spin terms,

$$\begin{aligned} \hat{H}_V &= \sum_{\sigma\sigma'} \hat{H}_V^{\sigma\sigma'} \\ &= \underbrace{\hat{H}_V^{\uparrow\uparrow} + \hat{H}_V^{\downarrow\downarrow}}_{\text{Same-spin}} + \underbrace{\hat{H}_V^{\uparrow\downarrow} + \hat{H}_V^{\downarrow\uparrow}}_{\text{Opposite-spin}} \end{aligned} \tag{1.9}$$

The role of said terms is crucial in establishing the pairing channel of the dominant physical phase. As an example, the s.s. terms can be seen as a possible source of triplet pairing superconductivity. Next section are devoted to analyze said terms and derive a simple analytical result in reciprocal space.

1.3.1 Real space description

Let us start from the real space form of Eq. (1.9). To carry out a summation over nearest neighbors $\langle \mathbf{r}\mathbf{r}' \rangle$ of a square lattice means precisely to sum over all links of the lattice. Then we can identify the generic opposite-spin (o.s.) term $\hat{H}_V^{\sigma\overline{\sigma}}$ as the one collecting the σ operators of sublattice $\mathcal{S}_a$ and $\overline{\sigma}$ operators of sublattice $\mathcal{S}_b$. The o.s. non-local interactions can be written as a sum of terms over just one of the two sublattices $\mathcal{S}_a$ and $\mathcal{S}_b$. Define the site hamiltonian

$$\hat{h}_V^{(\mathbf{r})} \equiv -V \sum_{\boldsymbol{\delta}} (\hat{n}_{\mathbf{r}\uparrow} \hat{n}_{\mathbf{r}+\boldsymbol{\delta}\downarrow} + \hat{n}_{\mathbf{r}\uparrow} \hat{n}_{\mathbf{r}-\boldsymbol{\delta}\downarrow}) \quad \text{with} \quad \boldsymbol{\delta} \in \{\underline{\mathbf{x}}, \underline{\mathbf{y}}\} \tag{1.10}$$

Then, it follows,

$$\begin{aligned}\hat{H}_V^{(\text{o.s.})} &= \overbrace{\sum_{\mathbf{r}\in\mathcal{S}_a} \hat{h}_V^{(\mathbf{r})}}^{\hat{H}_V^{\uparrow\downarrow}} + \overbrace{\sum_{\mathbf{r}\in\mathcal{S}_b} \hat{h}_V^{(\mathbf{r})}}^{\hat{H}_V^{\downarrow\uparrow}} \\ &= \sum_{\mathbf{r}\in\mathcal{S}} \hat{h}_V^{(\mathbf{r})} \end{aligned} \tag{1.11}$$

Here the notation of Fig. **??** is used. For each site $\mathbf{r}$ in a given sublattice, the nearest neighbors sites are four – all in the other sublattice. Similarly, the same-spin (s.s.) hamiltonian decomposes as

$$\hat{H}_V^{(\text{s.s.})} = -V \sum_{\mathbf{r}\in\mathcal{S}_a} \sum_{\boldsymbol{\delta},\sigma} (\hat{n}_{\mathbf{r}\sigma}\hat{n}_{\mathbf{r}+\boldsymbol{\delta}\sigma} + \hat{n}_{\mathbf{r}\sigma}\hat{n}_{\mathbf{r}-\boldsymbol{\delta}\sigma}) \quad \text{with} \quad \boldsymbol{\delta} \in \{\underline{\mathbf{x}}, \underline{\mathbf{y}}\}$$

Opposite-spin terms. Consider first the o.s. terms of Eq. (**??**): take e.g. the NNs term $\hat{n}_{i\uparrow}\hat{n}_{\mathbf{r}+\boldsymbol{\delta}\downarrow}$. As in Eq. (1.7), taking Wick's contractions,

$$\begin{aligned}\langle \hat{n}_{\mathbf{r}\uparrow}\hat{n}_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\rangle &= \langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\hat{c}_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\hat{c}_{\mathbf{r}\uparrow}\rangle \\ &\simeq \underbrace{\langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\rangle\langle \hat{c}_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\hat{c}_{\mathbf{r}\uparrow}\rangle}_{\text{Cooper}} - \underbrace{\langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\rangle\langle \hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\hat{c}_{\mathbf{r}\uparrow}\rangle}_{\text{Fock}} + \underbrace{\langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}_{\mathbf{r}\uparrow}\rangle\langle \hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\hat{c}_{\mathbf{r}+\boldsymbol{\delta}\downarrow}\rangle}_{\text{Hartree}}\end{aligned}$$

Identical decompositions are given for all others NNs. Of the three terms above:

- The Coooper term breaks $\mathrm{U}^{\mathrm{c}}(1)$ charge symmetry, allowing for supeconducting instabilities;
- The Fock term breaks the $\mathrm{U}^z(1)$ symmetry, because it accounts for a site hop *plus* spin flip process;
- The Hartree term can reduce both translational invariance and spin rotational symmetry.

As a general rule of thumb, throughout this text we will discard the o.s. Fock term eveywhere, preserving a robust $\mathrm{U}^z(1)$ symmetry. For the normal state as well as for the AF instability only the Hartree term is to be accounted; in superconducting instability also the Cooper term contributes. Note that for superconducting instabilities, due to superexchange mechanism (as explained in App. B) the o.s. term account for singlet pairing as well as zero-projection triplet pairing. Which channel is preferred, is a matter of thermodynamic advantage.

Same-spin terms. Consider then the same-spin terms: take e.g. the term $\hat{n}_{\mathbf{r}\uparrow}\hat{n}_{\mathbf{r}+\boldsymbol{\delta}\uparrow}$. As above,

$$\begin{aligned}\langle \hat{n}_{\mathbf{r}\uparrow}\hat{n}_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\rangle &= \langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\hat{c}_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\hat{c}_{\mathbf{r}\uparrow}\rangle \\ &= \underbrace{\langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\rangle\langle \hat{c}_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\hat{c}_{\mathbf{r}\uparrow}\rangle}_{\text{Cooper}} - \underbrace{\langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\rangle\langle \hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\hat{c}_{\mathbf{r}\uparrow}\rangle}_{\text{Fock}} + \underbrace{\langle \hat{c}^\dagger_{\mathbf{r}\uparrow}\hat{c}_{\mathbf{r}\uparrow}\rangle\langle \hat{c}^\dagger_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\hat{c}_{\mathbf{r}+\boldsymbol{\delta}\uparrow}\rangle}_{\text{Hartree}}\end{aligned}$$

Identical consideration as in the above paragraph hold for each term. The only difference with the o.s. terms is given by the Fock term: since the spin-flip process is absent, now the Fock fluctuations actually contribute as an effective NN hopping term. In other words, this term does not break $\mathrm{U}^z(1)$ symmetry and thus is perfectly legitimate in each phase. Tab. 1.4 summarizes the selection rules hereby presented.

1.3.2 Fourier transform of the model

It is useful to derive analytically the reciprocal-space form of the three parts of the hamiltonian. By the sign $\overset{\mathcal{F}}{=}$, we indicate a passage where a Fourier-transform is performed. $\mathcal{F}$-transform is obtained according to the convention Fourier transform it according to the convention

$$\hat{c}_{\mathbf{r}\sigma} \overset{\mathcal{F}}{=} \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k}\in\mathrm{BZ}} e^{-i\mathbf{k}\cdot\mathbf{r}} \hat{c}_{\mathbf{k}\sigma} \tag{1.12}$$

Sector	Term	Normal phase	Antiferromagnet	Superconductor
o.s.	Hartree			
	Fock	Prohibited	Prohibited	Prohibited
	Cooper	Prohibited	Prohibited	
s.s.	Hartree			
	Fock			
	Cooper	Prohibited	Prohibited	

Table 1.4 Summary of Wick's terms selection rules and relevant contributions to the effective hamiltonian for each phase limitedly to $\hat{H}_V$.

Kinetic part. The kinetic part is the easiest to transform. Apply the definition,

$$\begin{aligned}
-t\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}\left[\hat{c}^\dagger_{\mathbf{r}\sigma}\hat{c}_{\mathbf{r}'\sigma}+\text{h.c.}\right] &\overset{\mathcal{F}}{=} -t\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}\frac{1}{\sqrt{L_xL_y}}\sum_{\mathbf{k}\in\text{BZ}}e^{i\mathbf{k}\cdot\mathbf{r}}\hat{c}^\dagger_{\mathbf{k}\sigma}\frac{1}{\sqrt{L_xL_y}}\sum_{\mathbf{k}'\in\text{BZ}}e^{-i\mathbf{k}'\cdot\mathbf{r}'}\hat{c}_{\mathbf{k}'\sigma}+\text{h.c.}\\
&= -2t\sum_{\mathbf{k},\mathbf{k}'}\sum_{\sigma}\hat{c}^\dagger_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}'\sigma}\frac{1}{L_xL_y}\sum_{\mathbf{r}\in\mathcal{S}/2}e^{i(\mathbf{k}-\mathbf{k}')\cdot\mathbf{r}}\left[e^{ik'_x}+e^{-ik'_x}+e^{ik'_y}+e^{-ik'_y}\right]\\
&= \sum_{\mathbf{k}\in\text{BZ}}\sum_{\sigma}\epsilon_{\mathbf{k}}\hat{c}^\dagger_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma} \qquad (1.13)
\end{aligned}$$

where the bare bands were defined,

$$\epsilon_{\mathbf{k}} \equiv -2t\left(\cos k_x+\cos k_y\right) \qquad (1.14)$$

Non-local attraction. Consider a generic bond, say, the one connecting NNs $\mathbf{r}$ and $\mathbf{r}\pm\boldsymbol{\delta}$. Then:

$$\begin{aligned}
\hat{n}_{\mathbf{r}\sigma}\hat{n}_{\mathbf{r}\pm\boldsymbol{\delta}\sigma'} &= \hat{c}^\dagger_{\mathbf{r}\sigma}\hat{c}^\dagger_{\mathbf{r}\pm\boldsymbol{\delta}\sigma'}\hat{c}_{\mathbf{r}\pm\boldsymbol{\delta}\sigma'}\hat{c}_{\mathbf{r}\sigma}\\
&\overset{\mathcal{F}}{=} \frac{1}{(L_xL_y)^2}\sum_{\mathbf{k}_1,\cdots,\mathbf{k}_4}e^{i[(\mathbf{k}_1+\mathbf{k}_2)-(\mathbf{k}_3+\mathbf{k}_4)]\cdot\mathbf{r}}e^{\pm i(\mathbf{k}_2-\mathbf{k}_3)\cdot\boldsymbol{\delta}}\hat{c}^\dagger_{\mathbf{k}_1\sigma}\hat{c}^\dagger_{\mathbf{k}_2\sigma'}\hat{c}_{\mathbf{k}_3\sigma'}\hat{c}_{\mathbf{k}_4\sigma}
\end{aligned}$$

Then, the interaction at site $\mathbf{r}$, spin σ with its NNs at spin σ' – indicated as $(\mathbf{r}\sigma\sigma')$ – is given by

$$\begin{aligned}
(\mathbf{r}\sigma\sigma') &= -V\sum_{\boldsymbol{\delta}}\hat{n}_{\mathbf{r}\sigma}\hat{n}_{\mathbf{r}\pm\boldsymbol{\delta}\sigma'}\\
&\overset{\mathcal{F}}{=} -\frac{V}{(L_xL_y)^2}\sum_{\boldsymbol{\delta}}\sum_{\mathbf{k}_1,\cdots,\mathbf{k}_4}e^{i[(\mathbf{k}_1+\mathbf{k}_2)-(\mathbf{k}_3+\mathbf{k}_4)]\cdot\mathbf{r}}\\
&\qquad\times\left(e^{i(\mathbf{k}_2-\mathbf{k}_3)\cdot\boldsymbol{\delta}}+e^{-i(\mathbf{k}_2-\mathbf{k}_3)\cdot\boldsymbol{\delta}}\right)\hat{c}^\dagger_{\mathbf{k}_1\sigma}\hat{c}^\dagger_{\mathbf{k}_2\sigma'}\hat{c}_{\mathbf{k}_3\sigma'}\hat{c}_{\mathbf{k}_4\sigma}\\
&= -\frac{2V}{(L_xL_y)^2}\sum_{\boldsymbol{\delta}}\sum_{\mathbf{k}_1,\cdots,\mathbf{k}_4}e^{i[(\mathbf{k}_1+\mathbf{k}_2)-(\mathbf{k}_3+\mathbf{k}_4)]\cdot\mathbf{r}}\cos\left[(\mathbf{k}_2-\mathbf{k}_3)\cdot\boldsymbol{\delta}\right]\hat{c}^\dagger_{\mathbf{k}_1\sigma}\hat{c}^\dagger_{\mathbf{k}_2\sigma'}\hat{c}_{\mathbf{k}_3\sigma'}\hat{c}_{\mathbf{k}_4\sigma}
\end{aligned}$$

The full non-local interaction is given by summing over all sites of $\mathcal{S}_a$ (which is, half the sites of $\mathcal{S}$). This gives back momentum conservation,

$$\frac{1}{L_xL_y}\sum_{\mathbf{r}\in\mathcal{S}_a}e^{i[(\mathbf{k}_1+\mathbf{k}_2)-(\mathbf{k}_3+\mathbf{k}_4)]\cdot\mathbf{r}} = \frac{1}{2}\delta_{\mathbf{k}_1+\mathbf{k}_2=\mathbf{k}_3+\mathbf{k}_4}$$

Let $\mathbf{k}_1+\mathbf{k}_2=\mathbf{k}_3+\mathbf{k}_4=\mathbf{K}$, and define $\mathbf{k}$, $\mathbf{k}'$ such that

$$\mathbf{k}_1\equiv\mathbf{K}+\mathbf{k} \qquad \mathbf{k}_2\equiv\mathbf{K}-\mathbf{k} \qquad \mathbf{k}_3\equiv\mathbf{K}-\mathbf{k}' \qquad \mathbf{k}_4\equiv\mathbf{K}+\mathbf{k}' \qquad \delta\mathbf{k}\equiv\mathbf{k}-\mathbf{k}'$$

Sums over these variables must be intended as over the Brillouin Zone (BZ). Hence:

$$\begin{aligned}\hat{H}_V &= \sum_{\mathbf{r}\in\mathcal{S}_a}\sum_{\sigma\sigma'}(\mathbf{r}\sigma\sigma') \\ &\overset{\mathcal{F}}{=} -\frac{V}{L_xL_y}\sum_{\sigma\sigma'}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\cos(\delta\mathbf{k}\cdot\boldsymbol{\delta})\,\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma'}\hat{c}_{\mathbf{K}-\mathbf{k}'\sigma'}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} \\ &= -\frac{V}{L_xL_y}\sum_{\sigma\sigma'}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\left[\cos(\delta k_x)+\cos(\delta k_y)\right]\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma'}\hat{c}_{\mathbf{K}-\mathbf{k}'\sigma'}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}\end{aligned} \tag{1.15}$$

which decomposes in s.s. and o.s. channels as:

$$\hat{H}_V \overset{\mathcal{F}}{=} \overbrace{-\frac{V}{L_xL_y}\sum_{\sigma}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\left[\cos(\delta k_x)+\cos(\delta k_y)\right]\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}'\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}}^{\text{s.s.}}$$
$$\underbrace{-\frac{V}{L_xL_y}\sum_{\sigma}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\left[\cos(\delta k_x)+\cos(\delta k_y)\right]\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\overline{\sigma}}\hat{c}_{\mathbf{K}-\mathbf{k}'\overline{\sigma}}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}}_{\text{o.s.}}$$

The o.s. part can be simplified: since

$$\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\overline{\sigma}}\hat{c}_{\mathbf{K}-\mathbf{k}'\overline{\sigma}}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} = \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\overline{\sigma}}\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}'\overline{\sigma}}$$

due to fermionic anti-commutation rules, and since the composite transform

$$\mathbf{k}\to-\mathbf{k} \qquad \mathbf{k}'\to-\mathbf{k}'$$

leaves the form factor $\cos(\delta k_x)+\cos(\delta k_y)$ invariant, we reduce the spin sum to two times the $\sigma=\uparrow$ part,

$$\hat{H}_V^{(\text{o.s.})} = -\frac{2V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\left[\cos(\delta k_x)+\cos(\delta k_y)\right]\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\uparrow}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\downarrow}\hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow}\hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow} \tag{1.16}$$

whil the explicit s.s. sector is given immediately by:

$$\begin{aligned}\hat{H}_V^{(\text{s.s.})} = -\frac{V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}&\left[\cos(\delta k_x)+\cos(\delta k_y)\right] \\ &\times\left[\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\uparrow}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\uparrow}\hat{c}_{\mathbf{K}-\mathbf{k}'\uparrow}\hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow}+\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\downarrow}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\downarrow}\hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow}\hat{c}_{\mathbf{K}+\mathbf{k}'\downarrow}\right]\end{aligned} \tag{1.17}$$

The result here obtained will be used various times in next chapters. Note that different Wick contraction schemes lead to different results:

$$\overbracket{c^\dagger_{\mathbf{K}+\mathbf{k}\sigma}c^\dagger_{\mathbf{K}-\mathbf{k}\sigma'}}c_{\mathbf{K}-\mathbf{k}'\sigma'}c_{\mathbf{K}+\mathbf{k}'\sigma} \qquad \text{Cooper contraction} \tag{1.18}$$

$$\overbracket{c^\dagger_{\mathbf{K}+\mathbf{k}\sigma}c^\dagger_{\mathbf{K}-\mathbf{k}\sigma'}c_{\mathbf{K}-\mathbf{k}'\sigma'}}c_{\mathbf{K}+\mathbf{k}'\sigma} \qquad \text{Fock contraction} \tag{1.19}$$

$$\overbracket{c^\dagger_{\mathbf{K}+\mathbf{k}\sigma}c^\dagger_{\mathbf{K}-\mathbf{k}\sigma'}c_{\mathbf{K}-\mathbf{k}'\sigma'}c_{\mathbf{K}+\mathbf{k}'\sigma}} \qquad \text{Hartree contraction} \tag{1.20}$$

which will be used explicitly later on.

Local repulsion. A somewhat identical argument can be carried out for the local interaction,

$$\hat{H}_U = U\sum_{\mathbf{r}\in\mathcal{S}}\hat{n}_{\mathbf{r}\uparrow}\hat{n}_{\mathbf{r}\downarrow}$$

The only difference here is made by the fact that the interaction is repulsive on-site, thus the final structure factor in the Fourier transform disappears as well as the minus sign,

$$\hat{H}_U \overset{\mathcal{F}}{=} \frac{U}{L_xL_y}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\uparrow}\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\downarrow}\hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow}\hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow} \tag{1.21}$$

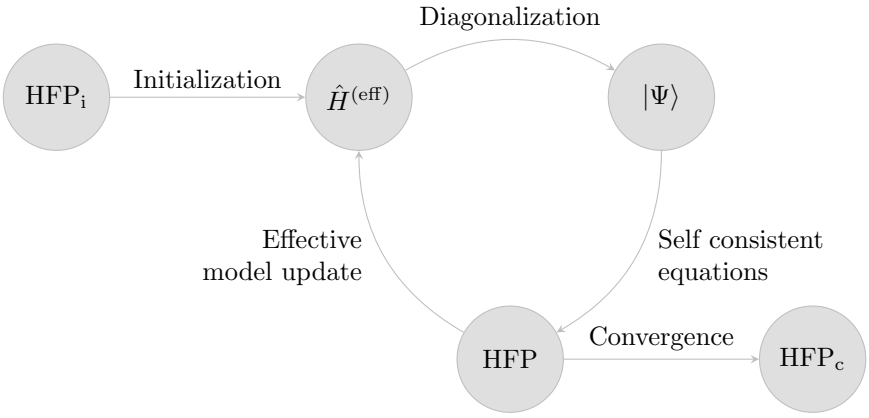

Figure 1.3 Schematization of the self-consistent Hartree Fock method described in Sec. 1.4. The effective model is solved, the solution is used to estimate self-consistently the Hartree Fock vector, which is then used to update iteratively the model itself. HFP$_\mathrm{i}$ indicates the initialzer HFPs vector, HFP$_\mathrm{c}$ the converged HFPs vector.

When contracting these fermionic operators, identical considerations as for the non-local counterpart (1.15) hold. Note the similarity of this Fourier transform with the o.s. sector of the non-local attraction, given in Eq. (1.15). With this, we conclude the general introduction to the model and pass to the setup of the Hartree-Fock (HF) algorithm.

1.4 General approach MFT through iterative Hartree-Fock algorithms

This section is devoted to the explanation of the general iterative strategy we use to simulate the EHM within MFT. The simplicity of the algorithm is only possible thanks to the violent reduction of complexity MFT is able to reach. We use an iterative self-consistent scheme, thus solving a finite set of equation searching for a fixed point in parameters space for each phase.

1.4.1 Sketch of the Hartree-Fock iterative algorithm

The general sketch of a self-consistent Hartree-Fock algorithm in our context is simple enough. Start from a fermionic quartic hamiltonian,

$$\hat{H} = \sum_{\alpha\beta} A_{\alpha\beta}\hat{c}^\dagger_\alpha\hat{c}_\beta + \sum_{\alpha\beta\gamma\delta} B_{\alpha\beta\gamma\delta}\hat{c}^\dagger_\alpha\hat{c}^\dagger_\beta\hat{c}_\gamma\hat{c}_\delta + \text{h.c.} \tag{1.22}$$

where $A_{\alpha\beta}$, $B_{\alpha\beta\gamma\delta}$ are model parameters. We limit ourselves to quartic hamiltonians, but the idea can be extended. As discussed before, in this kind of context MFT is employed by applying Wick's theorem. This way, the quartic hamiltonian is effectively reduced to a quadratic hamiltonian,

$$\hat{H} \simeq \hat{H}^{(\mathrm{eff})} = \sum_{\alpha\beta} C_{\alpha\beta}\hat{c}^\dagger_\alpha\hat{c}_\beta + \sum_{\alpha\beta} D_{\alpha\beta}\hat{c}^\dagger_\alpha\hat{c}^\dagger_\beta + \text{h.c.} \tag{1.23}$$

where now the new parameters, which we will refer to as Hartree-Fock parameters (HFP), depend on the model itself via the equations

$$C_{\alpha\beta} = A_{\alpha\beta} + \sum_{\gamma\delta} \left[B_{\alpha\gamma\delta\beta} - B_{\alpha\gamma\beta\delta}\right] \left\langle \hat{c}^\dagger_\gamma\hat{c}_\delta \right\rangle$$

$$D_{\alpha\beta} = \sum_{\gamma\delta} B_{\alpha\beta\gamma\delta} \left\langle \hat{c}_\gamma\hat{c}_\delta \right\rangle$$

These equations are determined by many-body expectation values, which in general are computed by the means of thermal averages over the lowest energy density matrix. A self consistent Hartree-Fock scheme goes as follows:

1. Apply MFT to the quartic hamiltonian, recovering its general theoretic effective form;
2. Impose selection rules on the parameters $C_{\alpha\beta}$, $D_{\alpha\beta}$, eventually eliminating those not respecting the symmetry sector we are working in[1];
3. Choose a starting value and a coherent symmetry structure for the remaining parameters;
4. Enter iterative scheme of Fig. 1.3:
   a) Based on the current HFPs, determine $\mu[C, D]$ that gives the correct density;
   b) Diagonalize the effective hamiltonian $\hat{H}^{(\text{eff})}[C, D] - \mu[C, D]\hat{N}$ and recover the ground-state $|\Psi[C, D]\rangle$;
   c) Compute the new HFPs $C'_{\alpha\beta}$, $D'_{\alpha\beta}$ via the self consistent equations;
   d) Initialize the new effective hamiltonian $\hat{H}^{(\text{eff})}[C', D']$ and repeat the cycle until the HFPs have converged to stable values.

The stable values we are referring to in the last point are our solutions. The resulting vector is a fixed point in the parametric recursive map defined by the set of MFT self-consistent equations.

Of course, to work any of these algorithms we need to know how to diagonalize the hamiltonian. In the context of the Extended Hubbad Model at thermal equilibrium, due to the phases we are simulating, we know analytically the diagonalized hamiltonian, and making use of this knowledge we are able to reduce the self consistent scheme to a simple iterative algorithm. An explicit example of HF algorithm used in present text, somewhat simplified due to the presence of a single HFP, is given in App. B.1.8.

1.4.2 Self-consistency and RMPs

As will be thoroughly discussed in the following derivations for each physical phase we treat, treating the EHM via MFT keeping under strict control the effects of Wick's theorem produces ground states whose parametric properties (band structures, gap functions, chemical potential) are controlled parametrically and self-consistently by the model two-body interactions $\hat{H}_U$ and $\hat{H}_V$. Let us define the concept of Renormalized model parameter (RMP), meaning one model that is effectively renormalized via interactions.

Let us invent a relevant example to explain the concept of RMP. Suppose that under MFT, for a given phase the decomposition $\hat{H}_V$ has a net effect of defining the RMP $\tilde{t}$,

$$t \xrightarrow{V} \tilde{t}$$

In other words, the decomposition of $\hat{H}_V$ produces a free Fermionic hamiltonian whose diffusive parameter is $\tilde{t}$. We define $\tilde{t}$ as an RMP, being the result of the original model parameter t plus the effect of interactions.

1.4.3 Fixed density simulations and the role of μ

In the context of the present text, all simulations are performed at fixed density, determining self-consistently the value of the chemical potential. This means that, for a given step i and the relative HFPs vector $\mathbf{v}_i$, and for a fixed density $n \in [0, 1]$, μ_i (the chemical potential at the current step) is determined as

$$\mu_i \quad : \quad \min_{\mu} \left\{ \frac{1}{2L_x L_y} \sum_{\mathbf{k}} \sum_{\sigma} \langle \hat{n}_{\mathbf{k}\sigma} \rangle \Big|_{\mathbf{v}=\mathbf{v}_i} - n \right\} \tag{1.24}$$

being $\mathbf{v} = \mathbf{v}_i$ and indication that the averaging operation is performed over the ground state determined parametrically by the current value of the HFPs.

[1] As an example: if we choose not to break charge conservation, set $\forall \alpha, \beta : \; D_{\alpha\beta} = 0$.

Hence, if we are able to perform averages and know both $\mathbf{v}_i$ and n, at step i we infer the correct chemical potential. Now, as we will discuss $\tilde{\mu}$ will turn out to be an RMP itself, meaning that theoretically

$$\mu \to \mu + F[\mathbf{v}] \equiv \tilde{\mu}[\mathbf{v}]$$

being F some functional of the HFPs. In other words, a common effect of interactions under MFT will be precisely to shift the chemical potential. At step i, keeping the density fixed, the chemical potential we are determining numerically and using in our equations is then $\tilde{\mu}_i$. In simpler words, the designed algorithm "does not know" about chemical potential renormalization and thus just determines the number that solves Eq. (1.24). But we know that this number is made of two contributions: the "physical" μ_i and the effective shift produced by the model itself, $F[\mathbf{v}_i]$. So, when it comes to μ_i, this consideration becomes important.

It is the case of the ground state energy estimation. Let us abstract from the EHM and MFT, and consider a generic hamiltonian $\hat{H}$. To find the ground state $|\Psi\rangle$ means precisely to solve

$$\frac{\delta}{\delta \langle\Psi|} \langle\Psi|\hat{H}|\Psi\rangle = 0$$

Now, working with a fixed particles number N means we are performing a constrained minimization (which is, taking the functional derivative) on the composite operator

$$\hat{H} - \mu(\hat{N} - N) \equiv \hat{K} + \mu N$$

being μ the Lagrange multiplier, $\hat{N}$ the number operator and $\hat{K} \equiv \hat{H} - \mu\hat{N}$. Finding the constrained ground state parametrized by a vector $\mathbf{v}$ now means to solve

$$\mathbf{v} \implies |\Psi[\mathbf{v}]\rangle \quad : \quad \begin{cases} \dfrac{\delta}{\delta \langle\Psi|} \langle\Psi|\hat{K} + \mu N|\Psi\rangle \Big|_{|\Psi\rangle = |\Psi[\mathbf{v}]\rangle} = 0 \\ \langle\Psi[\mathbf{v}]|\hat{N}|\Psi[\mathbf{v}]\rangle = N \end{cases}$$

Of course, in the first line μN is derived to zero. The constraint is imposed in the second line. This means that, when it comes to determining the parametric ground state, $\hat{K}$ is functionally minimized. If in this context μ (the Lagrange multiplier) sums with other effective terms arisen from algebraic manipulations of $\hat{H}$ giving a grand total of $\tilde{\mu}$, the number operator $\hat{N}$ average is performed over the many-body ground state $|\Psi[\mathbf{v}]\rangle$ with the total effective chemical potential $\tilde{\mu}$, not μ. However, when it comes to computing energy,

$$\begin{aligned} \langle\hat{H}\rangle &= \langle\Psi[\mathbf{v}]|\hat{K}|\Psi[\mathbf{v}]\rangle + \mu N \\ &= \Omega[\mathbf{v}] + (\tilde{\mu}[\mathbf{v}] - F[\mathbf{v}])N \end{aligned}$$

being Ω the expectation value (EV) of $\hat{K}$. In the last passage we wrote everything in terms of functionals of the HFPs vector $\mathbf{v}$. Using this relation, when the algorithm has converged, we can estimate the physical energy.

1.5 Square lattice spatial symmetry channels

In next sections we introduce spatial symmetry structures and discuss their relation with point groups. We will aways refer to various spatial structures as "symmetry channels", throughout the system is able to establish a given order parameter defined in space.

Looking at $\hat{H}$, the main difference between its two-body interactions $\hat{H}_U$ and $\hat{H}_V$ of course relies in locality (first) and non-locality (second). Both operators in principle are able to break C_4 symmetry, as will later be discussed extensively.

For the 2D square lattice, various spatial symmetries are possible. Let i be a specific site, and consider a generic complex function g_{ij} whose domain is given by the site itself and its four NNs (the domain concides with the points of Fig. 1.2). Then it is immediate to see that the function can be written in the following basis

$$g_{ij} = \sum_{\gamma} g^{(\gamma)} \varphi_{ij}^{(\gamma)}$$

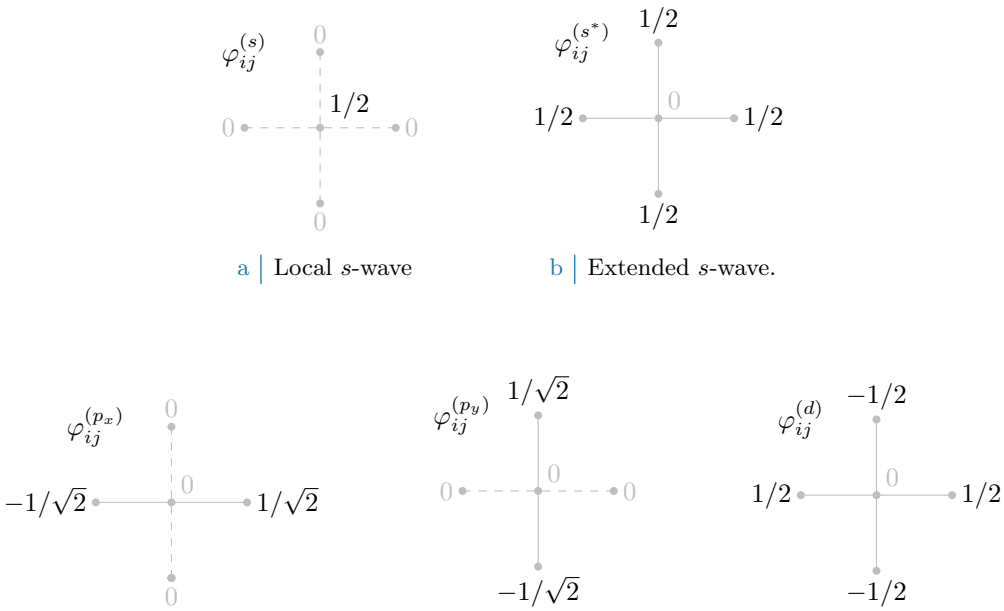

a | Local s-wave b | Extended s-wave.

c | p_x-wave. d | p_y-wave. e | $d_{x^2-y^2}$-wave.

Figure 1.4 | Form factors at different topologies, as listed in Tab. 1.5. In figures five sites are represented: the hub site i and its four NN. Solid lines represent non-zero values for $\varphi_{\boldsymbol{\delta}}$, while dashed lines represent vanishing factors.

Structure	Form factor	Graph
s-wave	$\varphi_{\mathbf{r}\mathbf{r}'}^{(s)} = \delta_{\mathbf{r}\mathbf{r}'}$	Fig. 1.4a
Extended s-wave	$\varphi_{\mathbf{r}\mathbf{r}'}^{(s^*)} = \frac{1}{2}\left[\delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{x}}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{x}}} + \delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{y}}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{y}}}\right]$	Fig. 1.4b
p_x-wave	$\varphi_{\mathbf{r}\mathbf{r}'}^{(p_x)} = \frac{1}{\sqrt{2}}\left[\delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{x}}} - \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{x}}}\right]$	Fig. 1.4c
p_y-wave	$\varphi_{\mathbf{r}\mathbf{r}'}^{(p_y)} = \frac{1}{\sqrt{2}}\left[\delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{y}}} - \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{y}}}\right]$	Fig. 1.4d
$d_{x^2-y^2}$-wave	$\varphi_{\mathbf{r}\mathbf{r}'}^{(d)} = \frac{1}{2}\left[\delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{x}}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{x}}} - \delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{y}}} - \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{y}}}\right]$	Fig. 1.4e

Table 1.5 | Form factors for a function defined on a square lattice, with a prefactor included for normalization. We use lattice vector notation here. The last column indicates the graph representation of each contribution given in Fig. 1.4. Subscript $x^2 - y^2$ is omitted for notational clarity.

where $g^{(\gamma)} \in \mathbb{C}$ are the g_{ij} symmetry channels coefficients while $\varphi_{ij}^{(\gamma)}$ are the form factors listed in Tab. 1.5 and plotted in Fig. 1.5, a simple orthonormal rearrangement of the harmonics basis.

When dealing with phases which respect translational symmetry, or at most reduce it to a weaker symmetry by shrinking the Brillouin Zone, it' useful to work in reciprocal space, as discussed in Sec. 1.3. As said, a particular phase can show specific spatial symmetries, and so will the Hartree Fock parameters. The key point to notice is that self-consistent equations involve sums (or integrals) to be computed over fermionic states, which can be heavily simplified by employing said symmetries. Consider the form factors of Tab. 1.5, and their Fourier transforms of Tab. 1.6.

Structure	Structure factor	Graph
s-wave	$\varphi_{\mathbf{k}}^{(s)} = 1$	Fig. 1.4a
Extended s-wave	$\varphi_{\mathbf{k}}^{(s^*)} = \cos k_x + \cos k_y$	Fig. 1.4b
p_x-wave	$\varphi_{\mathbf{k}}^{(p_x)} = i\sqrt{2}\sin k_x$	Fig. 1.4c
p_y-wave	$\varphi_{\mathbf{k}}^{(p_y)} = i\sqrt{2}\sin k_y$	Fig. 1.4d
$d_{x^2-y^2}$-wave	$\varphi_{\mathbf{k}}^{(d)} = \cos k_x - \cos k_y$	Fig. 1.4e

Table 1.6 Structure factors derived from the correlation structures of Tab. 1.5. The functions hereby defined are orthonormal, and are plotted in Fig- 1.5.

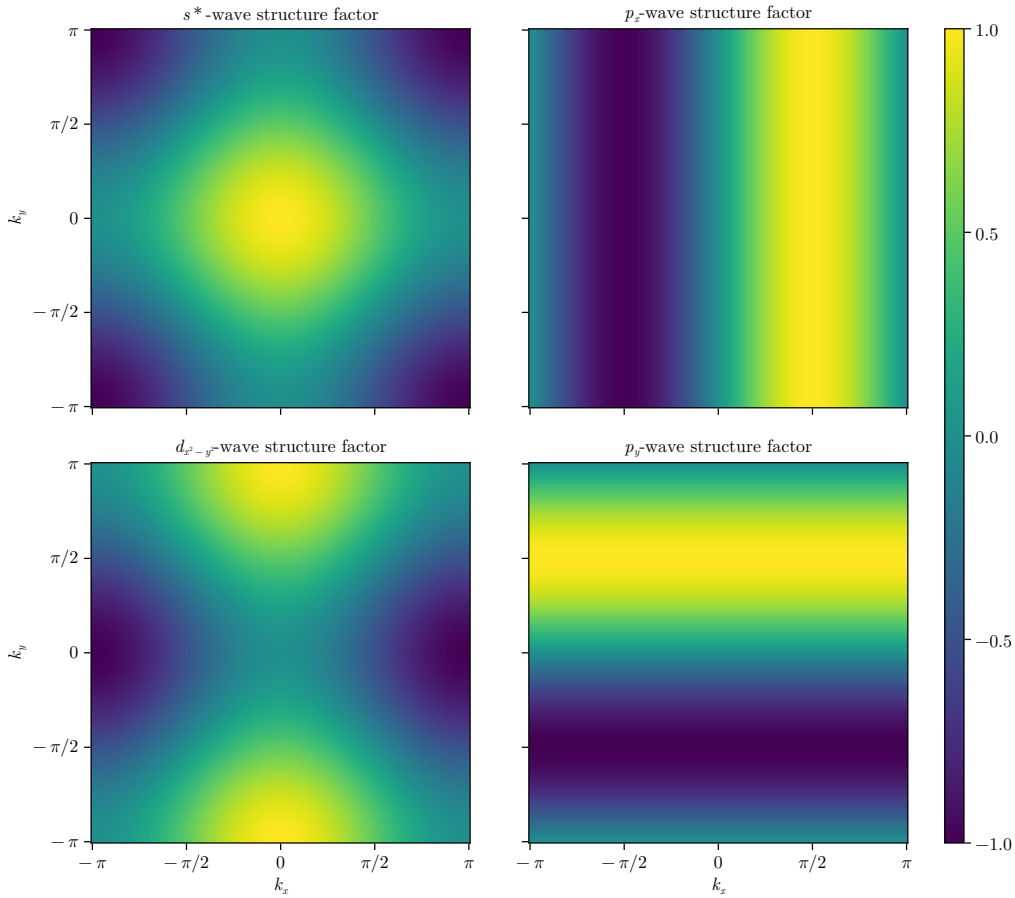

Figure 1.5 Representation of the various structure factors listed in Tab. 1.6 on the BZ. For the s^* and $d_{x^2-y^2}$-wave factors, the real part is plotted; for the p_ℓ factors, the imaginary part is plotted.

They satisfy the relations:

$$\frac{1}{L_x L_y}\sum_{ij}\varphi_{ij}^{(\gamma)}\varphi_{ij}^{(\gamma)*} = \delta_{\gamma\gamma'} \qquad \frac{1}{L_x L_y}\sum_{\mathbf{k}}\varphi_{\mathbf{k}}^{(\gamma)}\varphi_{\mathbf{k}}^{(\gamma)*} = \delta_{\gamma\gamma'}$$

If these symmetries are developed by the HFPs, it's of no use to integrate over the entire BZ, since different regions linked by periodicity of the form factors will lead to redundant calculations.

Finally, a very useful detail is given by the following argument. Consider the equation

$$\cos(\delta k_x) + \cos(\delta k_y) = \cos k_x \cos k_x' + \sin k_x \sin k_x' + \cos k_y \cos k_y' + \sin k_y \sin k_y'$$

For the sake of readability, the notations

$$c_\ell \equiv \cos k_\ell \qquad s_\ell \equiv \sin k_\ell \qquad c'_\ell \equiv \cos k'_\ell \qquad s'_\ell \equiv \sin k'_\ell$$

are used. Group the four terms above,

$$\underbrace{\left(c_x c'_x + c_y c'_y\right)}_{\text{Symmetric}} + \underbrace{\left(s_x s'_x + s_y s'_y\right)}_{\text{Anti-symmetric}} \tag{1.25}$$

The first two exhibit inversion symmetry for both arguments $\mathbf{k}$, $\mathbf{k}'$; the second two exhibit anti-symmetry. Decoupling the symmetric part, we obtain

$$c_x c'_x + c_y c'_y = \frac{1}{2}(c_x + c_y)(c'_x + c'_y) + \frac{1}{2}(c_x - c_y)(c'_x - c'_y)$$

which finally gives:

$$\begin{aligned}
\cos(\delta k_x) + \cos(\delta k_y) = \frac{1}{2}(c_x + c_y)(c'_x + c'_y) & \qquad (s^*\text{-wave}) \\
+ s_x s'_x & \qquad (p_x\text{-wave}) \\
+ s_y s'_y & \qquad (p_y\text{-wave}) \\
+ \frac{1}{2}(c_x - c_y)(c'_x - c'_y) & \qquad (d_{x^2-y^2}\text{-wave})
\end{aligned}$$

or, in a more compact form

$$\cos(\delta k_x) + \cos(\delta k_y) = \frac{1}{2}\sum_\gamma \varphi^{(\gamma)}_{\mathbf{k}} \varphi^{(\gamma)*}_{\mathbf{k}'} \quad \text{for } \gamma \in \{s^*, p_x, p_y, d_{x^2-y^2}\} \tag{1.26}$$

$$= \frac{1}{2}\sum_\gamma \varphi^{(\gamma)*}_{\mathbf{k}} \varphi^{(\gamma)}_{\mathbf{k}'} \tag{1.27}$$

This decomposition will become particularly handy in later calculations.

Chapter 2

The normal phase

This chapter is devoted to the MFT analysis of the "normal phase", which is, the one where interacting electrons do not develop an antiferromagnetic or superconducting gap, although undergoing an effective non-trivial transformation. What will be derived here, in particular the hopping renormalization effect, constitutes a peculiarity of effective MFT treatment of the EHM and will be the groundwork of following analyses. Note that this chapter is structured in such a way that what is derived here mathematically is recovered and expanded to more complex phases in next chapters.

2.1 The "normal" phase and its symmetries

The normal phase is simply the one where no symmetry is broken, and the many-body ground state preserves the entire U(2) structure of Eq. (1.2) as well as full translational symmetry $\mathrm{T}_1^{(x)} \otimes \mathrm{T}_1^{(y)}$. In terms of spatial symmetries, we here theoretically allow for

$$\mathrm{C}_4 \overset{\mathrm{SSB}}{\to} \mathrm{C}_2$$

symmetry reduction and extract the mathematical interesting consequences. While this implies immediately inversion symmetry preservation, full C_4 symmetry will be imposed later.

The normal phase is essentially given by the null gap limit of both the AF and SC phases. By discussing it separately now, we highlight a MFT feature of the EHM of particular interest, namely, the insurgence of a new, self-consistent hopping parameter. From Tabs. 1.3 and 1.4, we know that the relevant Wick's contractions (RWCs) for this phase are

$\hat{H}_U$	Hartree contraction
$\hat{H}_V$ (o.s. sector)	Hartree contraction
$\hat{H}_V$ (s.s. sector)	Hartree and Fock contractions

We anticipate the final effects of all RWCs. As we will see in detail and is reported in Tab. 2.1, the Hartree contractions account essentially for chemical potential shifts, while the only Fock contraction for a renormalization effects on the bare bands.

In the normal phase, spin is a pure physical degeneracy, being the $\uparrow$ and $\downarrow$ sectors separated; moreover, $\hat{H}$ is $\mathbb{Z}_2$ invariant with respect to spin inversion, $\sigma \leftrightarrow \overline{\sigma}$. This implies that all physical quantities, as is for the normal phase, should not depend on the spin index. We will perform all computations leaving σ explicit and using this consideration at the end.

2.2 Hartree effects: chemical potential renormalization

The first RMP we discuss is μ, whose numerical value is renormalized by Hartree channel interactions within MFT. As is discussed in Sec. 1.4.3, in the context of numerical simulations at fixed density, the chemical potential is determined self-consistently; thus any net effect that shifts μ is effectively ignored within (and limitedly to) the iterative algorithm. Renormalization effects become relevant when computing free energy.

Operator	Sector	RWCs	Net effect
$\hat{H}_U$		Hartree	μ shift by $-nU$
$\hat{H}_V$	o.s.	Hartree	μ shift by nzV
$\hat{H}_V$	s.s.	Hartree Fock	μ shift by nzV Bands renormalization and resymmetrization

Table 2.1 | Relevant Wick's contractions and net effect in the normal phase.

2.2.1 Hartree channel in the normal phase: analytic derivation

Within this section we discuss analytically the effects of MFT on the Hartree channel, separating the local and non-local interactions and obtaining a set of HFPs needed to setup an interative HF algorithm.

Local repulsion. In the normal phase, the local repulsion $\hat{H}_U$ decomposes in Hartree channel as

$$\hat{H}_U \simeq U \sum_i \left[\langle \hat{n}_{i\uparrow}\rangle \hat{n}_{i\downarrow} + \hat{n}_{i\uparrow}\langle \hat{n}_{i\downarrow}\rangle - \langle \hat{n}_{i\downarrow}\rangle\langle \hat{n}_{i\uparrow}\rangle\right]$$

For a translationally invariant phase such as the normal phase, it holds

$$\langle \hat{n}_{i\sigma}\rangle = n \tag{2.1}$$

which gives immediately

$$\begin{aligned}\hat{H}_U &\simeq nU \sum_i \left[\hat{n}_{i\uparrow} + \hat{n}_{i\downarrow}\right] - U \sum_i n^2 \\ &= nU \times \hat{N} - E^{(\mathrm{N})}_{\mathrm{H}/U}\end{aligned}$$

being $\hat{N}$ the total number operator and $E^{(\mathrm{N})}_{\mathrm{H}/U}$ the "contraction energy" (also known as double counting term) due to the Hartree (H) contraction of the U repulsion, discussed in Sec. 2.2.2. The chemical potential is corrected by

$$\mu \to \mu - nU \tag{2.2}$$

The non-local attraction further corrects μ.

Non-local attraction. Let us break down $\hat{H}_V$ isolating its Hartree RWCs in both o.s. and s.s. sectors:

$$\begin{aligned}\hat{H}_V \simeq &\overbrace{-V \sum_{\langle ij\rangle} \sum_\sigma \left[\langle \hat{n}_{i\sigma}\rangle \hat{n}_{j\sigma} + \hat{n}_{i\sigma}\langle \hat{n}_{j\sigma}\rangle - \langle \hat{n}_{i\sigma}\rangle\langle \hat{n}_{j\sigma}\rangle\right]}^{\text{s.s.}} \\ &\underbrace{-V \sum_{\langle ij\rangle} \sum_\sigma \left[\langle \hat{n}_{i\sigma}\rangle \hat{n}_{j\bar{\sigma}} + \hat{n}_{i\sigma}\langle \hat{n}_{j\bar{\sigma}}\rangle - \langle \hat{n}_{i\sigma}\rangle\langle \hat{n}_{j\bar{\sigma}}\rangle\right]}_{\text{o.s.}} + (\text{all the rest})\end{aligned} \tag{2.3}$$

where "all the rest" collects all non-Hartree RWCs. Recalling the Ansatz of Eq. (2.1), we get

$$\hat{H}_V \simeq \underbrace{-nV \sum_{\langle ij\rangle} \sum_\sigma \left[\hat{n}_{j\sigma} + \hat{n}_{i\sigma}\right]}_{\text{s.s.}} \underbrace{-nV \sum_{\langle ij\rangle} \sum_\sigma \left[\hat{n}_{j\bar{\sigma}} + \hat{n}_{i\sigma}\right]}_{\text{o.s.}} - E^{(\mathrm{N})}_{\mathrm{H}/V} + (\text{all the rest})$$

with $E^{(\mathrm{N})}_{\mathrm{H}/V}$ the normal state shift to energy brought by $\hat{H}_V$. Now, evidently both sums above are just a number operator, thus including the degeneracies introduced by the summations

$$\hat{H}_V \simeq -2nzV \times \hat{N} - E^{(\mathrm{N})}_{\mathrm{H}/V} + (\text{all the rest})$$

This accounts for the final Hartree shift of μ,

$$\mu \to \mu + 2znV \tag{2.4}$$

Considering the net shift to μ due to both interactions by combining Eqns. (2.2), (2.4), we get the final RMP anticipated in Tab. 2.1,

$$\tilde{\mu} \equiv \mu + n(2zV - U) \tag{2.5}$$

This result remains valid throughout all phases discussed in this text: for the AF phase, the SDW character leaves this shift untouched, while the SC phase we will discuss is inherently translational invariant.

2.2.2 Hartree contraction energy

The double counting terms accounting for energy shifts in the Hartree channel are, as anticipated:

$$\begin{aligned} E^{(\mathrm{N})}_{\mathrm{H}/U} &= \sum_i \langle \hat{n}_{i\downarrow}\rangle\langle \hat{n}_{i\uparrow}\rangle \\ &= L_x L_y \times n^2 U \end{aligned} \tag{2.6}$$

for the local repulsion and

$$\begin{aligned} E^{(\mathrm{N})}_{\mathrm{H}/V} &= -V \sum_{\langle ij\rangle}\sum_{\sigma} \left[\langle \hat{n}_{i\sigma}\rangle\langle \hat{n}_{j\sigma}\rangle + \langle \hat{n}_{i\sigma}\rangle\langle \hat{n}_{j\overline{\sigma}}\rangle\right] \\ &= -2V \sum_{\langle ij\rangle}\sum_{\sigma} n^2 \\ &= -L_x L_y \times 2zn^2 V \end{aligned} \tag{2.7}$$

for the non-local attraction. In the last passage, we used Eq. (1.3), as well as spin degeneracy. Note that, correctly, the contraction energy is an extensive quantity. This implies that we can define a contraction energy per site – something we will do later when computing total free energy density.

2.3 Fock effects: bare bands renormalization

Up to now, no relevant changes have been made to the starting situation of the conventional degenerate Fermi gas. The scenario changes now, with the analysis of the Fock RWCs. Even if no gap opens, in the normal phase the particles interact by the means of a non-local attraction, a feature that effectively redefines the bare fermionic bands.

From Wick's decomposition of $\hat{H}_V$, the only allowed Fock term comes from the same-spin part due to SU(2) symmetry selection rules. Let us focus only on this term when decomposing $\hat{H}$:

$$\hat{H}_V \simeq (\text{Hartree channel}) + V \sum_{\langle ij\rangle}\sum_{\sigma} \left[\langle \hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma} + \hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\langle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle - \langle \hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\langle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle\right] \tag{2.8}$$

(note the + sign in front of the displayed term). A bond-wise hopping amplitude can be defined,

$$\tilde{t}_{ij\sigma} \equiv t - V\langle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle$$

The effective kinetic hamiltonian is given by

$$\begin{aligned} \hat{H}_{\tilde{t}} &= \hat{H}_t + V \sum_{\langle ij\rangle}\sum_{\sigma} \left[\langle \hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma} + \text{h.c.}\right] \\ &= -\sum_{\langle ij\rangle}\sum_{\sigma} \left[\tilde{t}_{ij\sigma}\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma} + \text{h.c.}\right] \end{aligned}$$

To proceed, it is useful to move to reciprocal space.

2.3.1 Fock channel in the normal phase: analytic derivation

In reciprocal space, the effective hopping must be transformed as well. Consider the Fourier Transform $\mathcal{F}$ given in Eq. (1.15), applied to the displayed part of Eq. (2.8),

$$V\sum_{\langle ij\rangle}\sum_{\sigma}\left[\langle\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}+\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\langle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle-\langle\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\langle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle\right]$$
$$\overset{\mathcal{F}}{=}\frac{2V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\sum_{\sigma}\left[\cos(\delta k_x)+\cos(\delta k_y)\right]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}'\sigma}\rangle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}-E^{(\mathrm{N})}_{\mathrm{F}/V} \tag{2.9}$$

Here, the 2 prefactor comes from recognizing that the first two operators in square brackets in the first line generate identical contributions to the full sum; the double counting energy shift is given by

$$E^{(\mathrm{N})}_{\mathrm{F}/V}\equiv\frac{V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\sum_{\sigma}\left[\cos(\delta k_x)+\cos(\delta k_y)\right]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}'\sigma}\rangle\langle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}\rangle \tag{2.10}$$

Up to this point, this derivation is general and will be re-used in next chapters. Here the specificity of the physical phase settles in: if we assume the normal state to be a free degenerate Fermi gas with renormalized bands, we get

$$\langle\hat{c}^\dagger_{\mathbf{k}_1\sigma_1}\hat{c}_{\mathbf{k}_2\sigma_2}\rangle=\delta_{\mathbf{k}_1=\mathbf{k}_2}\delta_{\sigma_1=\sigma_2}f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu}) \tag{2.11}$$

being f the Fermi-Dirac distribution,

$$f(\epsilon;\beta,\mu)\equiv\frac{1}{e^{\beta(\epsilon-\mu)}+1}$$

In other words, we are assuming a solution to exist, we call "normal", such that the net effect of the interactions is to generate an effective correction to bands such that the final hamiltonian is just $\hat{H}\simeq\hat{H}_{\tilde{t}}+(\text{shifts})$. It follows that Eq. (2.9) becomes

$$V\sum_{\langle ij\rangle}\sum_{\sigma}\left[\langle\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}+\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\langle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle-\langle\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\langle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle\right]$$
$$\overset{\mathcal{F}}{=}\frac{2V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k}}\sum_{\sigma}\left[\cos(2k_x)+\cos(2k_y)\right]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}\sigma}-E^{(\mathrm{N})}_{\mathrm{F}/V} \tag{2.12}$$

since the only contribution comes from $\mathbf{k}'=-\mathbf{k}$. Let now $\mathbf{q}\equiv\mathbf{K}+\mathbf{k}$, $\mathbf{q}'\equiv\mathbf{K}-\mathbf{k}$. Being for $\ell=x,y$

$$\begin{aligned}\delta q_\ell&\equiv q_\ell-q'_\ell\\&=(K_\ell+k_\ell)-(K_\ell-k_\ell)\\&=2k_\ell\end{aligned}$$

we reduce Eq. (2.9) to

$$V\sum_{\langle ij\rangle}\sum_{\sigma}\left[\langle\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}+\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\langle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle-\langle\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\langle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle\right]$$
$$\overset{\mathcal{F}}{=}\frac{2V}{L_xL_y}\sum_{\mathbf{q},\mathbf{q}'}\sum_{\sigma}\left[\cos(\delta q_x)+\cos(\delta q_y)\right]\langle\hat{c}^\dagger_{\mathbf{q}\sigma}\hat{c}_{\mathbf{q}\sigma}\rangle\hat{c}^\dagger_{\mathbf{q}'\sigma}\hat{c}_{\mathbf{q}'\sigma}-E^{(\mathrm{N})}_{\mathrm{F}/V} \tag{2.13}$$

Recall now the result of the symmetry channels decomposition of Eq. (1.26),

$$\cos(\delta q_x)+\cos(\delta q_y)=\frac{1}{2}\sum_{\gamma}\varphi^{(\gamma)}_{\mathbf{q}}\varphi^{(\gamma)*}_{\mathbf{q}'}\quad\text{for }\gamma\in\{s^*,p_x,p_y,d_{x^2-y^2}\}$$

Symmetry	Self-consistency equation	Graph
s^*-wave	$u^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\cos k_x + \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$	Fig. 1.4b
$d_{x^2-y^2}$-wave	$u^{(d)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\cos k_x - \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$	Fig. 1.4e

Table 2.2 | Symmetry resolved self-consistency equations for the harmonics of $u_{\mathbf{k}}$.

Thanks to this handy property, we reduce Eq. (2.13) to

$$V \sum_{\langle ij\rangle} \sum_{\sigma} \left[\langle \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma}\rangle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma} + \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma} \langle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma}\rangle - \langle \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma}\rangle \langle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma}\rangle \right]$$
$$\stackrel{\mathcal{F}}{=} \sum_{\gamma,\sigma} \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{BZ}} \varphi^{(\gamma)}_{\mathbf{q}} u_{\mathbf{q}\sigma} \right] \times V \sum_{\mathbf{q}'\in\mathrm{BZ}} \varphi^{(\gamma)*}_{\mathbf{q}'} \hat{c}^\dagger_{\mathbf{q}'\sigma} \hat{c}_{\mathbf{q}'\sigma} - E^{(\mathrm{N})}_{\mathrm{F}/V} \tag{2.14}$$

where we defined the EV:

$$u_{\mathbf{q}\sigma} \equiv \langle \hat{c}^\dagger_{\mathbf{q}\sigma} \hat{c}_{\mathbf{q}\sigma}\rangle \qquad u_{\mathbf{q}\sigma} = u^*_{\mathbf{q}\sigma} \tag{2.15}$$

Of course, the numerical value of $u_{\mathbf{q}\sigma}$ is given by the Fermi-Dirac distribution; however, for the sake of reproducibility of this derivation in next chapters, we omit that for a moment. Let $u^{(\gamma)}_\sigma$ be its γ-wave component,

$$u^{(\gamma)}_\sigma = \frac{1}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{BZ}} \varphi^{(\gamma)}_{\mathbf{q}} \langle \hat{c}^\dagger_{\mathbf{q}\sigma} \hat{c}_{\mathbf{q}\sigma}\rangle$$

Now, the bare bands $\epsilon_{\mathbf{k}}$ are s^*-wave symmetric, but in general $\tilde{\epsilon}_{\mathbf{k}}$ can exhibit a more complex symmetry. We assume respected spatial inversion invariance, so it must be

$$u_{\mathbf{q}\sigma} = u_{-\mathbf{q}\sigma}$$

thus

$$u^{(p_\ell)}_\sigma = 0 \quad \text{for} \quad \ell \in \{x, y\}$$

recalling the antisymmetric form factors of Tab 1.6. The remaining s^* and d symmetries are legitimate HFPs with relative self-consistency equations, reported in Tab. 2.2 using spin degeneracy.

However, $u^{(s^*)}_\sigma$ and $u^{(d)}_\sigma$ are in general non-zero, since we are allowing theoretically the possibility for $\mathrm{C}_4 \to \mathrm{C}_2$ SSB. Hence Eq. (2.14) becomes

$$V \sum_{\langle ij\rangle} \sum_{\sigma} \left[\langle \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma}\rangle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma} + \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma} \langle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma}\rangle - \langle \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma}\rangle \langle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma}\rangle \right]$$
$$\stackrel{\mathcal{F}}{=} V \sum_{\mathbf{q}\in\mathrm{BZ}} \sum_{\sigma} \left[u^{(s^*)}_\sigma \varphi^{(s^*)*}_{\mathbf{q}} + u^{(d)}_\sigma \varphi^{(d)*}_{\mathbf{q}} \right] \hat{c}^\dagger_{\mathbf{q}\sigma} \hat{c}_{\mathbf{q}\sigma} - E^{(\mathrm{N})}_{\mathrm{F}/V} \tag{2.16}$$

Let

$$\tilde{\epsilon}_{\mathbf{k}\sigma} \equiv \epsilon_{\mathbf{k}\sigma} + u^{(s^*)}_\sigma V(\cos q_x + \cos q_y) + u^{(d)}_\sigma V(\cos q_x - \cos q_y) \tag{2.17}$$

This equation defines the bands renormalization and resymmetrization anticipated in Tab. 2.1, and is actually spin-independent. The fact that both a s^* and a d-wave component appear introduces an interesting anisotropy that is discusses in next section.

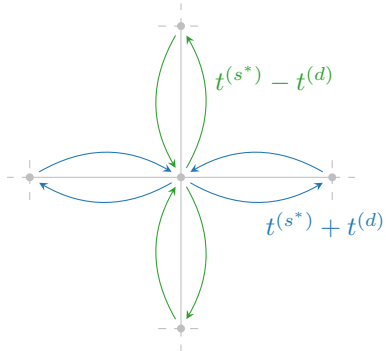

Figure 2.1 | Graphic rendition of anisotropic hopping, with a s^*-wave component (symmetric by $\pi/$ rotations) and a d-wave component (antisymmetric).

2.3.2 Fock contraction energy

Finally, let us derive the Fock contraction energy by expanding Eq. (2.10):

$$\begin{aligned} E^{(\mathrm{N})}_{\mathrm{F}/V} &= \frac{V}{L_x L_y} \sum_{\mathbf{q},\mathbf{q}'} \sum_{\sigma} \left[\cos(\delta q_x) + \cos(\delta q_y)\right] \langle \hat{c}^\dagger_{\mathbf{q}\sigma} \hat{c}_{\mathbf{q}'\sigma} \rangle \langle \hat{c}^\dagger_{\mathbf{q}\sigma} \hat{c}_{\mathbf{q}'\sigma} \rangle \\ &= L_x L_y \times \frac{V}{2} \sum_{\gamma,\sigma} \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}\in \mathrm{BZ}} \varphi^{(\gamma)}_{\mathbf{q}} u_{\mathbf{q}\sigma} \right] \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}'\in \mathrm{BZ}} \varphi'^{(\gamma)*}_{\mathbf{q}} u^*_{\mathbf{q}'\sigma} \right] \\ &= L_x L_y \times \frac{V}{2} \sum_{\sigma} \left[\left| u^{(s^*)}_\sigma \right|^2 + \left| u^{(d)}_\sigma \right|^2 \right] \end{aligned} \tag{2.18}$$

This expression gives the Fock contraction energy coming from the $\hat{H}_V$ operator. The particularly relevant result, here, is the fact that the full spectral amplitude of $u_{\mathbf{k}\sigma}$ here is weighted and contributes to contraction energy with a V linear prefactor. This suggests that a mixed-symmetry band could be energetically preferred.

2.3.3 Extending hopping to d-wave bands

From Tabs. 1.5 and 1.6 we can inverse Fourier transform the form factors to get the full effective hopping,

$$\tilde{t}_{ij\sigma} = \sum_{\gamma\in\{s^*,s\}} t^{(\gamma)}_\sigma \varphi^{(\gamma)}_{ij}$$

with

$$t^{(s^*)}_\sigma = t - \frac{u^{(s^*)}_\sigma V}{2} \qquad t^{(d)}_\sigma = -\frac{u^{(d)}_\sigma V}{2}$$

Interestingly enough, in principle an anisotropy in the normal diffusion between x and y direction emerges. A schematics of anisotropic mixed symmetry hopping is depicted in Fig. 2.1: as is evident, for each bond linking two sites the hopping parameter can be a positive or negative combination of the two components whether the link direction is vertical or horizontal. Naturally, the solution needs to be invariant under exchange $x \leftrightarrow y$, making the actual SSB of the class $\mathrm{C}_4 \to \mathrm{C}_4/\mathbb{Z}_2$.

The fact that hopping is here anisotropic does not break full translational invariance $\mathrm{T}^{(x)}_1 \otimes \mathrm{T}^{(x)}_2$. In fact, the fact itself that we are imposing a free degenerate Fermi gas ground state in Eq. (2.11) necessarily gives a uniform density, whatever the shape of the band. In fact, Fourier-transforming the site number operator,

$$\hat{c}^\dagger_{\mathbf{r}\sigma} \hat{c}_{\mathbf{r}\sigma} \overset{\mathcal{F}}{=} \frac{1}{L_x L_y} \sum_{\mathbf{k},\mathbf{k}'} e^{i(\mathbf{k}-\mathbf{k}')\cdot\mathbf{r}} \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}'\sigma}$$

which obviously implies

$$\langle \hat{n}_{i\sigma} \rangle = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

Whatever the shape of the bands, a perfectly degenerate Fermi gas is always translational invariant and thus exhibits uniform symmetry. The fact that hopping is allowed to be anisotropic does not interfere with that: C_4 breaking is not manifested this way.

Note that for null HFPs,

$$u_\sigma^{(s^*)} = 0 \qquad u_\sigma^{(d)} = 0$$

we have, in vector notation and recalling Tab. 1.5:

$$\tilde{t}_{\mathbf{r}\mathbf{r}'\sigma} = \frac{t}{2}\left[\delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{x}}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{x}}} + \delta_{\mathbf{r}'=\mathbf{r}+\underline{\mathbf{y}}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{\mathbf{y}}}\right]$$

The fact that $t/2$ appears here instead of t is not inconsistent, it's just a consequence of the equivalence:

$$-t\sum_{\langle ij\rangle}\sum_\sigma\left[\hat{c}_{i\sigma}^\dagger\hat{c}_{j\sigma} + \text{h.c.}\right] = -\frac{t}{2}\sum_{i,j\in\mathcal{S}}\sum_\sigma\left[\hat{c}_{i\sigma}^\dagger\hat{c}_{j\sigma} + \text{h.c.}\right]$$

The diffusion RMP $\tilde{t}_{ij\sigma}$ is to be interpreted like the right-hand side of the above equation, with the kinetic operator becoming:

$$\hat{H}_{\tilde{t}} \equiv -\frac{1}{2}\sum_{i,j\in\mathcal{S}}\sum_\sigma\left[\tilde{t}_{ij\sigma}\hat{c}_{i\sigma}^\dagger\hat{c}_{j\sigma} + \text{h.c.}\right]$$

To limit the sum to NNs is a matter of the symmetry structure of the function $\tilde{t}_{ij\sigma}$.

2.4 Normal free energy density

An important quantity to derive in order to compare different phases is free energy density, defined as

$$f_{\text{MFT}}^{(\text{N})} \equiv \frac{F_{\text{MFT}}^{(\text{N})}}{L_x L_y}$$

being F_{MFT} the total free energy. Consider the complete hamiltonian

$$\hat{H} \simeq \sum_{\mathbf{k},\sigma}\tilde{\epsilon}_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma}^\dagger\hat{c}_{\mathbf{k}\sigma} + E_{\text{c}}^{(\text{N})} - \tilde{\mu}\hat{N}$$

where $E_{\text{c}}^{(\text{N})}$ is the (negative) total contraction energy for the normal phase,

$$E_{\text{c}}^{(\text{N})} \equiv -\left[E_{\text{H}/U}^{(\text{N})} + E_{\text{H}/V}^{(\text{N})} + E_{\text{F}/V}^{(\text{N})}\right]$$

having included the various contraction energies from Eqns. (2.6), (2.7) and (2.18).

Let us now take together all terms. From now on, we will omit spin index σ, making use of the always present $\mathbb{Z}_2$ spin inversion symmetry discussed in Sec. 2.1. For a free Fermi gas, the free energy density is simply obtained by summing four contributions:

1. The free particles thermal ground state energy density,

$$e_{\text{g}}^{(\text{N})} = \frac{2}{L_x L_y}\sum_{\mathbf{k}\in\text{BZ}}(\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu})f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})$$

2. The contraction energy density,

$$\begin{aligned} e_{\text{c}}^{(\text{N})} &\equiv \frac{E_{\text{c}}^{(\text{N})}}{L_x L_y} \\ &= -n^2 U + V\left[2zn^2 - \left|u^{(s^*)}\right|^2 - \left|u^{(d)}\right|^2\right] \end{aligned}$$

3. The entropic contribution to free energy

$$e_s^{(\mathrm{N})} \equiv -Ts$$

with $T = 1/k_B\beta$ and s the free Fermi gas entropy density for a single spin sector [**grosso2014solid**],

$$s = -\frac{k_B}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \left[(1 - f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})) \ln (1 - f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})) + f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu}) \ln f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})\right] \tag{2.19}$$

We use the identity:

$$\ln\left(1 - \frac{1}{e^x+1}\right) = x + \ln\left(\frac{1}{e^x+1}\right)$$

and reduce the above expression to:

$$s = -\frac{k_B}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \Big[\ln (1 - f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})) + f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu}) \ln f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu}) \\ - \beta(\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu}) - f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu}) \ln f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})\Big]$$

Second and fourth terms cancel out, and multiplying by $-2T$ (taking care of spin degeneracy) we have

$$e_s^{(\mathrm{N})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \ln (1 - f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})) - \frac{2}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})$$

4. The chemical potential correction

$$e_n^{(\mathrm{N})} = \mu n$$

Note here that we are using the "physical" value of μ, not its RMP counterpart $\tilde{\mu}$. The reason for this is discussed in Sec. 1.4.3.

Thus, composing everything

$$\begin{aligned} f_{\mathrm{MFT}}^{(\mathrm{N})} &\equiv e_{\mathrm{g}}^{(\mathrm{N})} + e_{\mathrm{c}}^{(\mathrm{N})} + e_s^{(\mathrm{N})} + e_n^{(\mathrm{N})} \\ &= \frac{2}{\beta L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \ln (1 - f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})) - n^2 U + V\left[2zn^2 - \left|u^{(s^*)}\right|^2 - \left|u^{(d)}\right|^2\right] + \mu n \end{aligned} \tag{2.20}$$

When it comes to algorithmic computation of this quantity, it is important to express μ in terms of its RMP counterpart $\tilde{\mu}$, as discussed in Sec. 1.4.3. By doing this we are considering all the effects of MFT decomposition of $\hat{H}$.

2.5 Numerical simulations

[To be continued...]

2.5.1 HF iterative algorithm sketch

We are finally able to move to the computational part of this chapter. The aim is to write down an algorithm of the kind of Sec. 1.4.1. For the normal phase, the HFPs vector has two components:

$$\mathbf{v} = \begin{bmatrix} u^{(s^*)} \\ u^{(d)} \end{bmatrix}$$

As before, we treat spin as a pure degeneracy. The HFPs are characterized by the self-consistency equations of Tab. 2.2. The resulting model has two RMPs:

$$\tilde{t}_{ij} \equiv \left(t - \frac{u^{(s^*)}V}{2}\right)\varphi_{ij}^{(s^*)} - \frac{u^{(d)}V}{2}\varphi_{ij}^{(d)} \tag{2.21}$$

$$\tilde{\mu} \equiv \mu + n(2zV - U) \tag{2.22}$$

the second one being only dependent on the model parameters and not on HFPs. We can define the direction-dependent hopping as

$$\tilde{t}^{(x)} \equiv t - \frac{u^{(s^*)} - u^{(d)}}{2} V \tag{2.23}$$

$$\tilde{t}^{(y)} \equiv t - \frac{u^{(s^*)} + u^{(d)}}{2} V \tag{2.24}$$

Both components are controlled by V. Evidently $u^{(s^*)}$ is a measure of the direction-averaged hopping shift with respect to V,

$$u^{(s^*)} = \frac{\left(t - \tilde{t}^{(x)}\right) + \left(t - \tilde{t}^{(y)}\right)}{V}$$

while $u^{(d)}$ measures the hopping anisotropy with respect to V,

$$u^{(d)} = \frac{\tilde{t}^{(y)} - \tilde{t}^{(x)}}{V}$$

Finally, the phase free energy is given by Eq. (2.20). [To be continued...]

Chapter 3

Antiferromagnetic instability

This chapter is devoted to an in-depth discussion of the antiferromagnetic (AF) long-range ordering in the EHM by the means of MFT. In the context of the 2D HM, discussed in App. B, AF ordering establishes as an unconventional metallic phase which is only stable at half-filling (as is discussed in Sec. B.1.7). The situation for the EHM is similar: the present analysis is carried out based on the argument that, given the symmetry structure of the non-local NN interaction, the fundamental features of the commensurate AF phase of the HM are effectively preserved, while the parameters are redefined by the interaction itself. The two most relevant effects we discuss in this chapter are the gap "complexification" and the bands renormalization and resymmetrization (both in Sec. 3.3), the latter being a general feature of the EHM common to all phases preserving (or, at most, weakening without destroying) translational invariance, discussed previously in Sec. 2.3.

3.1 The AF phase and its symmetries

The AF phase is not uniquely defined; actually, there exists a variety of ways to establish a SDW phase in a spin-balanced square lattice, which means a system where both spin sectors are equally populated, but differently displaced. [ToDo: graphics of various SDW structures]

The AF phase hereby presented is a symmetry reduction of the normal phase, and is described by simultaneous spin rotational symmetry reduction and translational symmetry halving:

$$\mathrm{SU}(2) \overset{\mathrm{SSB}}{\to} \mathrm{U}^z(1)$$
$$\mathrm{T}_1^{(x)} \otimes \mathrm{T}_1^{(y)} \overset{\mathrm{SSB}}{\to} \mathrm{T}_2^{(x)} \otimes \mathrm{T}_2^{(y)}$$

We describe a SDW whose period is of two sites. As done for the normal phase, we allow theoretically

$$\mathrm{C}_4 \overset{\mathrm{SSB}}{\to} \mathrm{C}_2$$

in order to capture the same anisotropy effects seen in Sec. 2.3.1.

Recall Tabs. 1.3 and 1.4, collecting the RWCs for the AF phase,

$\hat{H}_U$	Hartree contraction
$\hat{H}_V$ (o.s. sector)	Hartree contraction
$\hat{H}_V$ (s.s. sector)	Hartree and Fock contractions

We anticipate the role of all RWCs in Tab. 3.1.

3.1.1 Antiferromagnetism in the HM

In this short section we recall the principal features of the AF phase established in the conventional HM, discussed in Sec. B.1. Before starting, let us define as in Eqns. (B.3) and (B.2) the AF and density fluctuations operators,

$$\hat{n}_{\mathbf{k}\sigma} \equiv \hat{c}^\dagger_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma} \tag{3.1}$$
$$\hat{\psi}_{\mathbf{k}\sigma} \equiv \hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma}\hat{c}_{\mathbf{k}\sigma} \tag{3.2}$$

Operator	Sector	RWCs	Net effect
$\hat{H}_U$		Hartree	μ shift by $-nU$
$\hat{H}_V$	o.s.	Hartree	μ shift by nzV
$\hat{H}_V$	s.s.	Hartree	μ shift by nzV
		Fock	Bands renormalization and resymmetrization, gap complexification

Table 3.1 Relevant Wick's contractions and net effect in the AF phase. Note the similarity with Tab. 2.1.

which represent the two essential fermionic quadratic operators of the analytic MFT derivation. Within the pure HM, the AF phase is specified by the Ansatz (B.4) which is explicitly breaking translational invariance in each spin sector, while preserving $\mathrm{U}^z(1)$ and $\mathrm{U}^c(1)$ symmetries. As reported in Tab. 1.3, the only RWC comes in Hartree channel, since the local two-body interaction couples operators at opposite spin index. The hamiltonian $\hat{H}$ is reduced thereby to the form of Eq. (B.5)

$$\hat{H}_t + \hat{H}_U \overset{\text{MFT}}{\simeq} -t \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \left[\hat{c}^\dagger_{\mathbf{r}\sigma} \hat{c}_{\mathbf{r}'\sigma} + \text{h.c.} \right] + nU \sum_{\mathbf{r}} \left[\hat{n}_{\mathbf{r}\uparrow} + \hat{n}_{\mathbf{r}\downarrow} \right] - mU \sum_{\mathbf{r}} (-1)^{x+y} \left[\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow} \right] - E^{(\text{AF})}_{\text{H}/U}$$

with $E^{(\text{AF})}_{\text{H}/U}$ the contraction energy resulting from double counting terms, given explicitly in Eq. (B.6). In reciprocal space, the hamiltonian decomposes as in Eq. (B.8),

$$\hat{H}_t + \hat{H}_U \overset{\text{MFT}}{\simeq} \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Psi}^\dagger_{\mathbf{k}\sigma} h_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} - E^{(\text{AF})}_{\text{H}/U} \quad \text{being} \quad h_{\mathbf{k}\sigma} \equiv \begin{bmatrix} \epsilon_{\mathbf{k}\sigma} & -\Delta^*_{\mathbf{k}\sigma} \\ -\Delta_{\mathbf{k}\sigma} & -\epsilon_{\mathbf{k}\sigma} \end{bmatrix}$$

and $\Delta_{\mathbf{k}\sigma} = (-1)^{\delta_{\sigma=\downarrow}} mU$. Nambu spinorial formulation is used,

$$\hat{\Psi}_{\mathbf{k}\sigma} \equiv \begin{bmatrix} \hat{c}_{\mathbf{k}\sigma} \\ \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \end{bmatrix}$$

and the free electrons energy is simply the tight binding energy of Eq. (1.14) written with an explicit spin index,

$$\epsilon_{\mathbf{k}\sigma} = -2t \left(\cos k_x + \cos k_y \right)$$

which is spin-invariant. The MFT description of the model reduces to a gas of free "γ-fermions", described by the Nambu spinor of Eq. (**??**),

$$\hat{\Gamma}_{\mathbf{k}\sigma} = W_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} = \begin{bmatrix} \hat{\gamma}^{(+)}_{\mathbf{k}\sigma} \\ \hat{\gamma}^{(-)}_{\mathbf{k}\sigma} \end{bmatrix}$$

where

$$W_{\mathbf{k}\sigma} = \begin{bmatrix} \cos\theta_{\mathbf{k}\sigma} & -\sin\theta_{\mathbf{k}\sigma} \\ \sin\theta_{\mathbf{k}\sigma} & \cos\theta_{\mathbf{k}\sigma} \end{bmatrix} \quad \text{and} \quad \sin 2\theta_{\mathbf{k}\sigma} \equiv \frac{\Delta_{\mathbf{k}\sigma}}{E_{\mathbf{k}\sigma}}$$

These fermions populate the two bands $\pm E_{\mathbf{k}\sigma} = \sqrt{\epsilon^2_{\mathbf{k}\sigma} + |\Delta_{\mathbf{k}\sigma}|^2}$. The entire system is mapped onto an ensemble of pseudo-spins, each subject to a pseudo-field, as in Fig. 3.1. To diagonalize the system essentially means to anti-align each pseudo-spin with the z axis. Each pseudospin component expectation value (EV) is described by a simple equation and has a precise meaning, listed in Tab. 3.2.

EV	Meaning	Equation
$\langle \hat{s}^x_{\mathbf{k}\sigma} \rangle$	$\left\langle \hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}^\dagger_{\mathbf{k}\sigma} \right\rangle$	(B.17)
$\langle \hat{s}^y_{\mathbf{k}\sigma} \rangle$	$i \left\langle \hat{\psi}_{\mathbf{k}\sigma} - \hat{\psi}^\dagger_{\mathbf{k}\sigma} \right\rangle$	(B.18)
$\langle \hat{s}^z_{\mathbf{k}\sigma} \rangle$	$\langle \hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \rangle$	(B.19)

Table 3.2 | List of the various expectation values (EVs) of each pseudospin component, their meaning in terms of fermionic operators and the reference equations from the pure HM.

3.1.2 Extension to the EHM

Consider now the non-local interaction $\hat{H}_V$. Being the RWCs the same as for the normal phase, the discussion is essentially the same of Chap. 2, with the only relevant difference being the Ansatz we use in Eq. (2.1), substituted by the commensurate oscillatory Ansatz of Eq. (B.4),

$$\langle \hat{n}_{\mathbf{r}\sigma} \rangle = n - (-1)^{x+y+\delta_{\sigma=\uparrow}} m \tag{3.3}$$

As for the normal phase, by design the MFT solution to the model for the given phase is described by a redefinition of the various physical quantities and mathematical objects,

$$\epsilon_{\mathbf{k}\sigma} \to \tilde{\epsilon}_{\mathbf{k}\sigma} \qquad E_{\mathbf{k}\sigma} \to \tilde{E}_{\mathbf{k}\sigma} \qquad \Delta_{\mathbf{k}\sigma} \to \tilde{\Delta}_{\mathbf{k}\sigma} \qquad \mu \to \tilde{\mu}$$

The band energies renormalization is simply

$$\tilde{E}_{\mathbf{k}\sigma} \equiv \sqrt{\tilde{\epsilon}^2_{\mathbf{k}\sigma} + |\tilde{\Delta}_{\mathbf{k}\sigma}|^2}$$

and the following relations hold (the *tilde* sign indicates the renormalized quantity):

$$\langle \hat{\Psi}^\dagger_{\mathbf{k}\sigma} \tau^x \hat{\Psi}_{\mathbf{k}\sigma} \rangle = -\sin 2\tilde{\theta}_{\mathbf{k}\sigma} \cos 2\tilde{\zeta}_{\mathbf{k}\sigma} \langle \hat{\Gamma}^\dagger_{\mathbf{k}\sigma} \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \tag{3.4}$$

$$\langle \hat{\Psi}^\dagger_{\mathbf{k}\sigma} \tau^y \hat{\Psi}_{\mathbf{k}\sigma} \rangle = -\sin 2\tilde{\theta}_{\mathbf{k}\sigma} \sin 2\tilde{\zeta}_{\mathbf{k}\sigma} \langle \hat{\Gamma}^\dagger_{\mathbf{k}\sigma} \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \tag{3.5}$$

$$\langle \hat{\Psi}^\dagger_{\mathbf{k}\sigma} \tau^z \hat{\Psi}_{\mathbf{k}\sigma} \rangle = \cos 2\tilde{\theta}_{\mathbf{k}\sigma} \langle \hat{\Gamma}^\dagger_{\mathbf{k}\sigma} \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \tag{3.6}$$

equivalent to the ones for the pure HM, Eqns. (B.17), (B.18) and (B.19). Moving to the the tilted frame, the z component of the pseudospin is just a thermal superposition of the "up" and "down" states

$$\langle \hat{\Gamma}^\dagger_{\mathbf{k}\sigma} \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle = \frac{1}{2} \left[f\left(\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}\right) - f\left(-\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}\right) \right] \tag{3.7}$$

Let us define the (renormalized) thermal factors as in Eq. (B.16),

$$\tilde{\mathrm{Th}}^{(\pm)}_{\mathbf{k}\sigma}[\beta, \tilde{\mu}] \equiv f\left(\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}\right) \pm f\left(-\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}\right) \tag{3.8}$$

The angles satisfy:

$$\sin(2\tilde{\xi}_{\mathbf{k}\sigma}) = \frac{\mathrm{Re}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}{|\tilde{\Delta}_{\mathbf{k}\sigma}|} \qquad \cos(2\tilde{\xi}_{\mathbf{k}\sigma}) = \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}{|\tilde{\Delta}_{\mathbf{k}\sigma}|} \qquad \sin(2\tilde{\theta}_{\mathbf{k}\sigma}) = \frac{|\tilde{\Delta}_{\mathbf{k}\sigma}|}{\tilde{E}_{\mathbf{k}\sigma}} \qquad \cos(2\tilde{\theta}_{\mathbf{k}\sigma}) = \frac{\tilde{\epsilon}_{\mathbf{k}\sigma}}{\tilde{E}_{\mathbf{k}\sigma}} \tag{3.9}$$

The physical behaviour is the same as for the pure HM. In terms of MFT discussion, the AF phase is similar enough to the normal phase of Chap. 2: the RWCs are the same of Sec. 2.1, listed in Tabs. 1.3 and 1.4. All three Hartree contractions, responsible in the normal phase of the chemical potential shift, and the s.s. Fock contraction, that originated the hopping renormalization. Let us start by the Hartree terms: due to the "staggered" nature of the commensurate AF phase, their role is here more complex. Then we will move to the Fock term, discussing the MFT approximations effect on bands. Next sections are basically an extension of the calculations of Chap. 2.

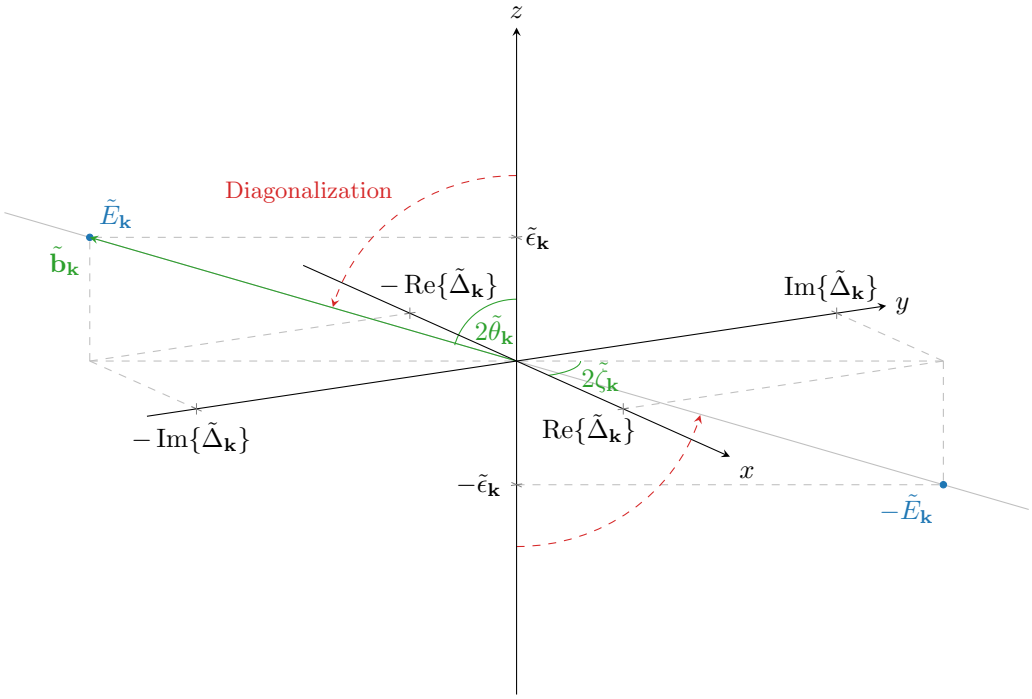

Figure 3.1 Sketch of the diagonalization of the pseudo-spin problem. The dashed line represents the diagonalization given by the z-axis alignment with the field direction. In the top-right side of the picture are listed the expectation values of the original Nambu spinor. For simplicity everywhere the index $\sigma = \uparrow$ has been omitted.

3.2 Non-local Hartree effects: chemical potential renormalization

As in Eq. (2.3), the same-spin and opposite-spin non-local Hartree terms are

$$\hat{H}_V \simeq \overbrace{-V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \hat{n}_{j\sigma} + \hat{n}_{i\sigma} \langle \hat{n}_{j\sigma} \rangle - \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\sigma} \rangle]}^{\text{s.s.}}$$
$$\underbrace{-V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \hat{n}_{j\bar{\sigma}} + \hat{n}_{i\sigma} \langle \hat{n}_{j\bar{\sigma}} \rangle - \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\bar{\sigma}} \rangle]}_{\text{o.s.}} + (\text{all the rest})$$

Let $i \to \mathbf{r} = (x, y)$ and $j \to \mathbf{r}' = (x', y')$. The key difference in the present derivation, with respect to the normal phase, is the single-site density Ansatz: instead of Eq. (2.1), we use Eq. (3.3), which describes an oscillatory density for each spin sector,

$$\langle \hat{n}_{\mathbf{r}\sigma} \rangle = n - (-1)^{x+y+\delta_{\sigma=\uparrow}} m$$

This Ansatz is composed of two parts: the offset n, and the oscillatory part m. The algebraic derivation relative to the n part is, of course, the same as for the normal phase. We now treat separately the "operatorial" part of the braced terms of Eq. (2.3),

$$-V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\langle \hat{n}_{\mathbf{r}\sigma} \rangle \hat{n}_{\mathbf{r}'\sigma} + \hat{n}_{\mathbf{r}\sigma} \langle \hat{n}_{\mathbf{r}'\sigma} \rangle] - V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\langle \hat{n}_{\mathbf{r}\sigma} \rangle \hat{n}_{\mathbf{r}'\bar{\sigma}} + \hat{n}_{\mathbf{r}\sigma} \langle \hat{n}_{\mathbf{r}'\bar{\sigma}} \rangle] \tag{3.10}$$

as well as the its scalar counterpart

$$V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \langle \hat{n}_{\mathbf{r}'\sigma} \rangle + V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \langle \hat{n}_{\mathbf{r}'\bar{\sigma}} \rangle \tag{3.11}$$

which accounts for the energy shift to be accounted when performing Wick's contractions.

3.2.1 Hartree channel in the AF phase: analytic derivation

Let us start from the operator of Expr. (3.10). By inserting the Ansatz of Eq. (B.4), we get

$$\overbrace{-nV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}[\hat{n}_{\mathbf{r}'\sigma}+\hat{n}_{\mathbf{r}\sigma}]+mV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}(-1)^{\delta_{\sigma=\uparrow}}\left[(-1)^{x+y}\hat{n}_{\mathbf{r}'\sigma}+(-1)^{x'+y'}\hat{n}_{\mathbf{r}\sigma}\right]}^{\text{s.s.}}$$
$$\underbrace{-nV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}[\hat{n}_{\mathbf{r}'\overline{\sigma}}+\hat{n}_{\mathbf{r}\sigma}]+mV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}\left[(-1)^{x+y+\delta_{\sigma=\uparrow}}\hat{n}_{\mathbf{r}'\overline{\sigma}}+(-1)^{x'+y'+\delta_{\overline{\sigma}=\uparrow}}\hat{n}_{\mathbf{r}\sigma}\right]}_{\text{o.s.}}$$

For a square lattice, if $\mathbf{r}=(x,y)$ and $\mathbf{r}'=(x',y')$ are NNs, evidently

$$(-1)^{x'+y'}=(-1)^{x+y+1}$$

Moreover,

$$(-1)^{\delta_{\overline{\sigma}=\uparrow}}=(-1)^{\delta_{\sigma=\uparrow}+1}$$

We obtain

$$\overbrace{-nV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}[\hat{n}_{\mathbf{r}\sigma}+\hat{n}_{\mathbf{r}'\sigma}]}^{\text{s.s. (density)}}-\overbrace{mV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}(-1)^{x+y+\delta_{\sigma=\uparrow}}[\hat{n}_{\mathbf{r}\sigma}-\hat{n}_{\mathbf{r}'\sigma}]}^{\text{s.s. (magnetization)}}$$
$$\underbrace{-nV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}[\hat{n}_{\mathbf{r}\sigma}+\hat{n}_{\mathbf{r}'\overline{\sigma}}]}_{\text{o.s. (density)}}+\underbrace{mV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}(-1)^{x+y+\delta_{\sigma=\uparrow}}[\hat{n}_{\mathbf{r}\sigma}+\hat{n}_{\mathbf{r}'\overline{\sigma}}]}_{\text{o.s. (magnetization)}} \tag{3.12}$$

In the above expressions the various contribution have been separated in "density" contributions and "magnetization" contributions. Let us deal with these separately.

Density terms. Consider the s.s. and o.s. (density) terms of Expr. (3.12),

$$-nV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}[\hat{n}_{\mathbf{r}\sigma}+\hat{n}_{\mathbf{r}'\sigma}]-nV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}[\hat{n}_{\mathbf{r}\sigma}+\hat{n}_{\mathbf{r}'\overline{\sigma}}] \tag{3.13}$$

The discussion is identical to the one of Sec. 2.2.1 for the normal phase, with the renormalization of μ being the same of Eq. (2.5).

$$\tilde{\mu}\equiv\mu+n(2zV-U) \tag{3.14}$$

Within this equation we are also already implicitly considering the μ shift effect due to $\hat{H}_U$.

Magnetization terms. The s.s. and o.s. (magnetization) terms of Expr. (3.12) perfectly cancel out:

$$mV\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}(-1)^{x+y+\delta_{\sigma=\uparrow}}[(\hat{n}_{\mathbf{r}\sigma}-\hat{n}_{\mathbf{r}'\sigma})-(\hat{n}_{\mathbf{r}\sigma}+\hat{n}_{\mathbf{r}'\overline{\sigma}})]=0$$

thus the only net effect of the Hartree RWCs affects μ. This is somewhat to be expected: in the context of the HM, the gap function emerges in its purely s-wave structure from this precise computation on Hartree terms. However, the $\hat{H}_V$ non-local interaction cannot provide a pure s-wave potential component. Effects on the gap function are to be observed somewhere else.

Let us now move to the last part of the Hartree effects on the AF phase originated by $\hat{H}_V$, which is, the energy shift due to double counting terms originated by MFT decomposition of the quartic interactions $\hat{H}_U$ and $\hat{H}_V$.

3.2.2 Hartree contraction energy

Consider the scalar Expr. (3.11): it's the sum of two parts, the first coming from s.s. sector, the second from o.s. sector.

s.s. sector double counting energy. For the s.s. part, explicitating the two spin sectors, we get

$$V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}\langle \hat{n}_{\mathbf{r}\sigma}\rangle\langle \hat{n}_{\mathbf{r}'\sigma}\rangle = \overbrace{V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\Big[(n+(-1)^{x+y}m)(n+(-1)^{x'+y'}m)\Big]}^{\sigma=\uparrow} + \underbrace{V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\Big[(n-(-1)^{x+y}m)(n-(-1)^{x'+y'}m)\Big]}_{\sigma=\downarrow}$$

Evidently the mixed terms (those of order $\mathcal{O}(n)\times\mathcal{O}(m)$) cancel out, and considering that the sign factor is necessarily alternating on neighboiring site, the remainder is just

$$V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}\langle \hat{n}_{i\sigma}\rangle\langle \hat{n}_{j\sigma}\rangle = V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}2(n^2-m^2)$$

o.s. sector double counting energy. Proceeding identically on the o.s. sector, we get

$$V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\sum_{\sigma}\langle \hat{n}_{\mathbf{r}\sigma}\rangle\langle \hat{n}_{\mathbf{r}'\overline{\sigma}}\rangle = \overbrace{V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\Big[(n+(-1)^{x+y}m)(n-(-1)^{x'+y'}m)\Big]}^{\sigma=\uparrow} + \underbrace{V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}\Big[(n-(-1)^{x+y}m)(n+(-1)^{x'+y'}m)\Big]}_{\sigma=\downarrow}$$

which gives immediately

$$V\sum_{\langle ij\rangle}\sum_{\sigma}\langle \hat{n}_{i\sigma}\rangle\langle \hat{n}_{j\overline{\sigma}}\rangle = V\sum_{\langle \mathbf{r}\mathbf{r}'\rangle}2(n^2+m^2)$$

Hence, the total "contraction energy", given by the sum of both contributions, is identical to the normal one of Eq. (2.7) indeed:

$$E^{(\mathrm{AF})}_{\mathrm{H}/V} = -2V\sum_{\langle ij\rangle}\sum_{\sigma}n^2 = 4n^2V\times\frac{z}{2}L_xL_y \tag{3.15}$$

the minus sign coming from the fact that we are subtracting this energy shift. This implies that, when comparing normal and AF phase, we can rule out this energy contribution, being equal for both free energy densities.

3.3 Fock effects: gap and bands renormalization

We explored thoroughly the Hartree contractions effects on the MFT hamiltonian. Let us now move to the effects originated by Fock contractions. We can use the derivation of Sec. 2.3 up to Eq. (2.12),

$$\begin{aligned} &V\sum_{\langle ij\rangle}\sum_{\sigma}\Big[\langle \hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}+\hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\langle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle-\langle \hat{c}^\dagger_{i\sigma}\hat{c}_{j\sigma}\rangle\langle \hat{c}^\dagger_{j\sigma}\hat{c}_{i\sigma}\rangle\Big] \\ &\qquad\overset{\mathcal{F}}{=}\frac{2V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k}}\sum_{\sigma}\left[\cos(2k_x)+\cos(2k_y)\right]\langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}\sigma}-E^{(\mathrm{AF})}_{\mathrm{F}/V} \end{aligned} \tag{3.16}$$

where $E^{(\mathrm{AF})}_{\mathrm{F}/V}$ is defined as in Eq. (2.10), with the expectation value being computed on the AF (thermal) ground-state. As before, we discuss the operatorial part and the scalar part separately.

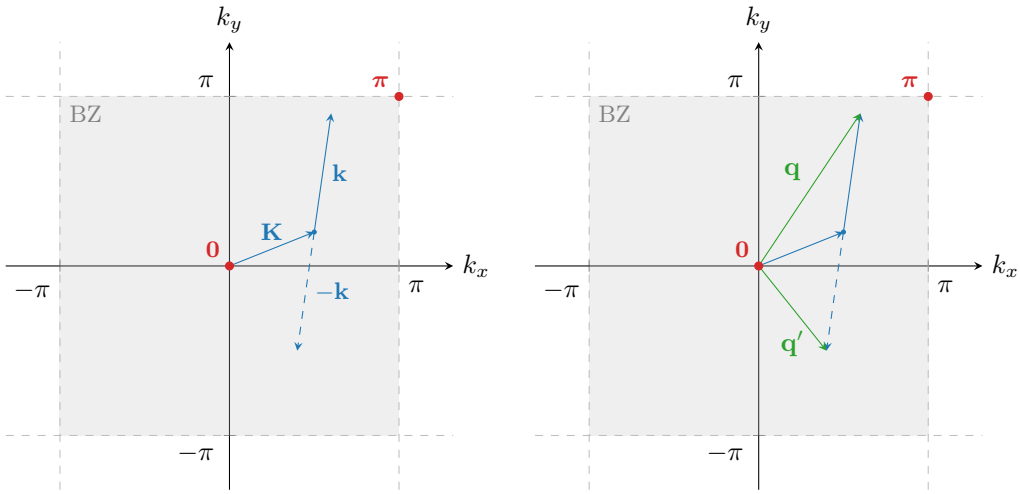

a | Generic vectors. b | Change of variables.

Figure 3.2 | Representation of the vectors involved in the diagonal terms of Eq. (**??**). In Fig. 3.2a generic vectors are considered, cycling over all values of $\mathbf{K}, \mathbf{k} \in \text{BZ}$. In Fig. 3.2b is depicted the variables change to the new vectors $\mathbf{q}, \mathbf{q}'$.

3.3.1 Fock channel in the AF phase: analytic derivation

The commensurate AF phase is essentially described by two EVs being in principle non-zero,

$$\left|\langle \hat{n}_{\mathbf{k}\sigma}\rangle\right| \geq 0 \qquad \left|\langle \hat{\psi}_{\mathbf{k}\sigma}\rangle\right| \geq 0$$

The AF ground state is a degenerate Fermi gas of $\gamma^{(\pm)}$ quasiparticles, and for null temperature acquires the simple form of Eq. (B.27). Going back to Eq. (3.16), this implies only two contributions are non-zero:

$$\mathbf{k} = -\mathbf{k}' \quad \text{or} \quad \mathbf{k} + \boldsymbol{\pi} = -\mathbf{k}'$$

The first case gives us the normal fermionic EV, $\langle \hat{n}_{\mathbf{k}\sigma}\rangle$, the second the staggered AF order parameter, $\langle \hat{\psi}_{\mathbf{k}\sigma}\rangle$. Then Eq. (3.16) is reduced to:

$$(\cdots) \overset{\mathcal{F}}{=} \frac{2V}{L_x L_y} \sum_{\mathbf{K},\mathbf{k}} \sum_{\sigma} \left[\cos(2k_x) + \cos(2k_y)\right] \left[\underbrace{\langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}}_{\text{Diagonal terms}} - \underbrace{\langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma}\rangle \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma}}_{\text{Off-diagonal terms}}\right] \tag{3.17}$$

Now, the above equation presents *diagonal* and *off-diagonal* terms.

Diagonal terms. The diagonal terms of Eq. (3.17) are simple density interactions with the mean density field. Consider Fig. 3.2a: density at vector $\mathbf{q} \equiv \mathbf{K} + \mathbf{k}$ interacts with the mean density at vector $\mathbf{q}' \equiv \mathbf{K} - \mathbf{k}$. These variables are depicted in Fig. 3.2b. Apply in the diagonal part of Eq. (3.17) this variables change (which is the same of Eq. (2.13))

$$\begin{aligned}
&\frac{2V}{L_x L_y} \sum_{\mathbf{q},\mathbf{q}'} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \hat{c}_{\mathbf{K}-\mathbf{k}\sigma} \\
&\qquad = \frac{2V}{L_x L_y} \sum_{\mathbf{q},\mathbf{q}'} \sum_{\sigma} \left[\cos(\delta q_x) + \cos(\delta q_y)\right] \langle \hat{c}^\dagger_{\mathbf{q}\sigma} \hat{c}_{\mathbf{q}\sigma}\rangle \hat{c}^\dagger_{\mathbf{q}'\sigma} \hat{c}_{\mathbf{q}'\sigma} \\
&\qquad \overset{*}{=} \sum_{\gamma,\sigma} \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}} \varphi^{(\gamma)}_{\mathbf{q}} \langle \hat{n}_{\mathbf{q}\sigma}\rangle\right] \times V \sum_{\mathbf{q}'} \varphi^{(\gamma)*}_{\mathbf{q}'} \hat{c}^\dagger_{\mathbf{q}'\sigma} \hat{c}_{\mathbf{q}'\sigma}
\end{aligned} \tag{3.18}$$

Symmetry	Self-consistency equation	Graph
s^*-wave	$u^{(s^*)} = \frac{1}{2L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}(\cos q_x + \cos q_y)\frac{\tilde{\epsilon}_{\mathbf{q}\sigma}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}]$	Fig. 1.4b
$d_{x^2-y^2}$-wave	$u^{(d)} = \frac{1}{2L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}(\cos q_x - \cos q_y)\frac{\tilde{\epsilon}_{\mathbf{q}\sigma}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}]$	Fig. 1.4e

Table 3.3 | Symmetry resolved self-consistency equations for the harmonics of $u_{\mathbf{k}}$.

where the sign $\overset{*}{=}$ indicates that we have substituted the decomposition of Eq. (1.26). Define as in Eq. (2.15) the EV

$$u_{\mathbf{q}\sigma} \equiv \langle \hat{n}_{\mathbf{q}\sigma}\rangle \tag{3.19}$$

The expression in square brackets of Eq. (3.18) is just its γ component, and is expanded in

$$\begin{aligned}
u^{(\gamma)}_{\sigma} &= \frac{1}{L_xL_y}\sum_{\mathbf{q}\in\mathrm{BZ}}\varphi^{(\gamma)}_{\mathbf{q}}\langle\hat{n}_{\mathbf{q}\sigma}\rangle \\
&= \frac{1}{L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}\left[\varphi^{(\gamma)}_{\mathbf{q}}\langle\hat{n}_{\mathbf{q}\sigma}\rangle + \varphi^{(\gamma)}_{\mathbf{q}+\boldsymbol{\pi}}\langle\hat{n}_{\mathbf{q}+\boldsymbol{\pi}\sigma}\rangle\right] \\
&= \frac{1}{L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}\varphi^{(\gamma)}_{\mathbf{q}}\left[\langle\hat{n}_{\mathbf{q}\sigma}\rangle - \langle\hat{n}_{\mathbf{q}+\boldsymbol{\pi}\sigma}\rangle\right] \\
&= \frac{1}{L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}\varphi^{(\gamma)}_{\mathbf{q}}\langle\hat{\Psi}^{\dagger}_{\mathbf{q}\sigma}\tau^z\hat{\Psi}_{\mathbf{q}\sigma}\rangle \\
&= \frac{1}{2L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}\varphi^{(\gamma)}_{\mathbf{q}}\frac{\tilde{\epsilon}_{\mathbf{q}\sigma}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}]
\end{aligned} \tag{3.20}$$

where, in the last passage, Eqns. (3.6), (3.7) and (3.8) have been used. Now, the AF phase does not break inversion symmetry: this implies that, whatever the shape of the renormalized bands, it must be

$$\tilde{\epsilon}_{\mathbf{q}\sigma} = \tilde{\epsilon}_{-\mathbf{q}\sigma} \quad\Longrightarrow\quad u^{(p_\ell)}_{\sigma} = 0 \quad \text{with} \quad \ell\in\{x,y\}$$

The renormalized bands need to be symmetric functions of the moment. Hence for $\gamma\in\{p_x,p_y\}$ the above sum vanishes. The remaining s^* and d symmetries are legitimate HFPs with relative self-consistency equations, reported in Tab. 3.3 using spin degeneracy.

Eq. (**??**) becomes

$$\begin{aligned}
\frac{2V}{L_xL_y}\sum_{\mathbf{q},\mathbf{q}'}\sum_{\sigma}&\left[\cos(2k_x)+\cos(2k_y)\right]\langle\hat{c}^{\dagger}_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle\hat{c}^{\dagger}_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}\sigma} \\
&= V\sum_{\mathbf{q},\sigma}\left[u^{(s^*)}_{\sigma}(\cos q_x+\cos q_y) + u^{(d)}_{\sigma}(\cos q_x - \cos q_y)\right]\hat{c}^{\dagger}_{\mathbf{q}\sigma}\hat{c}_{\mathbf{q}\sigma}
\end{aligned}$$

These two factors, together, define the full bands renormalization

$$\tilde{\epsilon}_{\mathbf{k}\sigma} \equiv \epsilon_{\mathbf{k}\sigma} + u^{(s^*)}_{\sigma}V(\cos q_x+\cos q_y) + u^{(d)}_{\sigma}V(\cos q_x - \cos q_y) \tag{3.21}$$

as was for the normal phase in Eq. (2.17). In Sec. 2.3.3 we discussed the appearance of anisotropic hopping with d-wave extension of the bands: here the theory predicts something identical. These RMPs are, as before, controlled linearly by V and in principle can lead to relevant changes in the kinetic sector of the hamiltonian.

Symmetry	Self-consistency equation	Graph
s-wave	$w^{(s)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$	Fig. 1.4a
s^*-wave	$w^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\cos k_x + \cos k_y) \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta, \tilde{\mu}]$	Fig. 1.4b
p_x-wave	$w^{(p_x)} = \frac{i\sqrt{2}}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \sin k_x \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta, \tilde{\mu}]$	Fig. 1.4c
p_y-wave	$w^{(p_y)} = \frac{i\sqrt{2}}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \sin k_y \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta, \tilde{\mu}]$	Fig. 1.4d
$d_{x^2-y^2}$-wave	$w^{(d)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\cos k_x - \cos k_y) \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta, \tilde{\mu}]$	Fig. 1.4e

Table 3.4 | Symmetry resolved self-consistency equations for the harmonics of $v_{\mathbf{k}}$.

Off-diagonal terms. Consider the off-diagonal terms of Eq. (3.17). These contribute instead to the full gap, being out of diagonal in the 2×2 hamiltonian matrix. In terms of the pseudospin picture, they account for a transverse field. Define $\mathbf{q}$, $\mathbf{q}'$ as in Fig. 3.2b, and rewrite as for Eq. (3.18)

$$
\begin{aligned}
-\frac{2V}{L_x L_y} \sum_{\mathbf{q},\mathbf{q}'} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma} \rangle \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} \\
= -\sum_{\gamma,\sigma} \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}} \varphi^{(\gamma)}_{\mathbf{q}} \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \right] \times V \sum_{\mathbf{q}'} \varphi^{(\gamma)*}_{\mathbf{q}'} \hat{c}^\dagger_{\mathbf{q}'\sigma} \hat{c}_{\mathbf{q}'+\boldsymbol{\pi}\sigma}
\end{aligned}
\tag{3.22}
$$

Proceed as done previously: define the expectation value

$$
v_{\mathbf{q}\sigma} \equiv i \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \tag{3.23}
$$

(which is just the AF order parameter with a complex factor) and its γ-wave component, with $\gamma \in \{s^*, d, p_x, p_y\}$:

$$
\begin{aligned}
v^{(\gamma)}_{\sigma} &= \frac{i}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{BZ}} \varphi^{(\gamma)}_{\mathbf{q}} \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \\
&= \frac{i}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{MBZ}} \left[\varphi^{(\gamma)}_{\mathbf{q}} \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle + \varphi^{(\gamma)}_{\mathbf{q}+\boldsymbol{\pi}} \langle \hat{\psi}_{\mathbf{q}+\boldsymbol{\pi}\sigma} \rangle \right] \\
&= \frac{i}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{MBZ}} \varphi^{(\gamma)}_{\mathbf{q}} \left[\langle \hat{\psi}_{\mathbf{q}\sigma} \rangle - \langle \hat{\psi}^\dagger_{\mathbf{q}\sigma} \rangle \right] \\
&= -\frac{1}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{MBZ}} \varphi^{(\gamma)}_{\mathbf{q}} \langle \hat{\Psi}^\dagger_{\mathbf{q}\sigma} \tau^y \hat{\Psi}_{\mathbf{q}\sigma} \rangle \\
&= \frac{1}{2 L_x L_y} \sum_{\mathbf{q}\in\mathrm{MBZ}} \varphi^{(\gamma)}_{\mathbf{q}} \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta, \tilde{\mu}]
\end{aligned}
\tag{3.24}
$$

where we made use of the relations of Tab. 3.2 as well as Eq. (3.5). We also used the obvious facts that $\langle \hat{\psi}_{\mathbf{q}+\boldsymbol{\pi}\sigma} \rangle = \langle \hat{\psi}^\dagger_{\mathbf{k}\sigma} \rangle$ and $\varphi^{(\gamma)}_{\mathbf{q}+\boldsymbol{\pi}} = -\varphi^{(\gamma)}_{\mathbf{q}}$. There is no particular reason to exclude one component or another. Tab. 3.4

From the definitions of the structure factors of Tab. 1.6, it's immediate to see that:

$$
v^{(s^*)}_{\sigma}, v^{(d)}_{\sigma} \in \mathbb{R} \qquad v^{(p_x)}_{\sigma}, v^{(p_y)}_{\sigma} \in i\mathbb{R}
$$

Getting back to Eq. (3.22) and inserting these components, we get

$$-\frac{2V}{L_xL_y}\sum_{\mathbf{q},\mathbf{q}'}\sum_{\sigma}[\cos(2k_x)+\cos(2k_y)]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} = iV\sum_{\gamma,\sigma}v^{(\gamma)}_\sigma\sum_{\mathbf{q}\in\mathrm{BZ}}\varphi^{(\gamma)*}_{\mathbf{q}}\hat{\psi}_{\mathbf{q}\sigma} \quad (3.25)$$

We can expand on the MBZ as

$$-\frac{2V}{L_xL_y}\sum_{\mathbf{q},\mathbf{q}'}\sum_{\sigma}[\cos(2k_x)+\cos(2k_y)]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} = iV\sum_{\gamma,\sigma}\sum_{\mathbf{q}\in\mathrm{MBZ}}\left[v^{(\gamma)}_\sigma\varphi^{(\gamma)*}_{\mathbf{q}}\hat{\psi}_{\mathbf{q}\sigma}+v^{(\gamma)}_\sigma\varphi^{(\gamma)*}_{\mathbf{q}+\boldsymbol{\pi}}\hat{\psi}^\dagger_{\mathbf{q}\sigma}\right] \quad (3.26)$$

Recalling Tab. 1.6, for the symmetries we are considering

$$iv^{(\gamma)}_\sigma\varphi^{(\gamma)*}_{\mathbf{q}}\in i\mathbb{R}$$

Moreover, since $\varphi^{(\gamma)}_{\mathbf{q}}=-\varphi^{(\gamma)}_{\mathbf{q}+\boldsymbol{\pi}}$, we have

$$iv^{(\gamma)}_\sigma\varphi^{(\gamma)*}_{\mathbf{q}+\boldsymbol{\pi}}=\left(iv^{(\gamma)}_\sigma\varphi^{(\gamma)*}_{\mathbf{q}}\right)^*$$

Therefore

$$-\frac{2V}{L_xL_y}\sum_{\mathbf{q},\mathbf{q}'}\sum_{\sigma}[\cos(2k_x)+\cos(2k_y)]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}\sigma}\rangle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} = V\sum_{\gamma,\sigma}\sum_{\mathbf{q}\in\mathrm{MBZ}}\left[iv^{(\gamma)}_\sigma\varphi^{(\gamma)*}_{\mathbf{q}}\hat{\psi}_{\mathbf{q}\sigma}+\mathrm{h.c.}\right] \quad (3.27)$$

Four more real HFPs are then identified, with their self-consistency equations,

$$v^{(s^*)}_\sigma=\frac{1}{2L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}(\cos q_x+\cos q_y)\frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}] \quad (3.28)$$

$$v^{(d)}_\sigma=\frac{1}{2L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}(\cos q_x-\cos q_y)\frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}] \quad (3.29)$$

$$-iv^{(p_x)}_\sigma=\frac{1}{\sqrt{2}L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}\sin q_x\frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}] \quad (3.30)$$

$$-iv^{(p_y)}_\sigma=\frac{1}{\sqrt{2}L_xL_y}\sum_{\mathbf{q}\in\mathrm{MBZ}}\sin q_y\frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{q}\sigma}[\beta,\tilde{\mu}] \quad (3.31)$$

As we will discuss later in Sec. 3.4.2, not all these HFPs can coexist simultaneously. For now, let us move to the free energy density computation.

3.3.2 Fock contraction energy

Let us now get back to $E^{(\mathrm{AF})}_{\mathrm{F}/V}$, the double counting energy of Eq. (3.16). As said before, its definition is the same as for the normal phase, Eq. (2.10), with the averaging operation being performed on the AF ground state:

$$E^{(\mathrm{AF})}_{\mathrm{F}/V}\equiv\frac{V}{L_xL_y}\sum_{\mathbf{K},\mathbf{k},\mathbf{k}'}\sum_{\sigma}[\cos(\delta k_x)+\cos(\delta k_y)]\langle\hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma}\hat{c}_{\mathbf{K}-\mathbf{k}'\sigma}\rangle\langle\hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma}\hat{c}_{\mathbf{K}+\mathbf{k}'\sigma}\rangle \quad (3.32)$$

Proceeding exactly as in Eq. (3.17) and making the change of variables of Fig. 3.2, we get

$$E_{\mathrm{F}/V}^{(\mathrm{AF})} = \frac{V}{L_x L_y} \sum_{\mathbf{q},\mathbf{q}'} \sum_{\sigma} \left[\cos\left(\delta q_x\right) + \cos\left(\delta q_y\right)\right] \Big[\underbrace{\langle \hat{n}_{\mathbf{q}\sigma}\rangle\langle \hat{n}_{\mathbf{q}'\sigma}\rangle}_{\text{Diagonal terms}} - \underbrace{\langle \hat{\psi}_{\mathbf{q}\sigma}\rangle\langle \hat{\psi}_{\mathbf{q}'\sigma}\rangle}_{\text{Off-diagonal terms}} \Big]$$

Apply the decomposition of Eq. (1.26) and use Eqns. (3.19), (3.23),

$$E_{\mathrm{F}/V}^{(\mathrm{AF})} = \frac{V}{2L_x L_y} \sum_{\gamma,\sigma} \sum_{\mathbf{q},\mathbf{q}'} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} \left[u_{\mathbf{q}\sigma} u_{\mathbf{q}'\sigma} + v_{\mathbf{q}\sigma} v_{\mathbf{q}'\sigma}\right] \tag{3.33}$$

Now: it holds

$$u_{\mathbf{q}\sigma} = \langle \hat{n}_{\mathbf{q}\sigma}\rangle \quad \Longrightarrow \quad u_{\mathbf{q}\sigma} = u_{\mathbf{q}\sigma}^*$$

and then

$$\begin{aligned}\frac{1}{(L_x L_y)^2} \sum_{\mathbf{q},\mathbf{q}'} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} u_{\mathbf{q}\sigma} u_{\mathbf{q}'\sigma} &= \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} u_{\mathbf{q}\sigma}\right] \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}'\in\mathrm{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} u_{\mathbf{q}'\sigma}^*\right] \\ &= \left|u_{\sigma}^{(\gamma)}\right|^2\end{aligned}$$

At the same time,

$$v_{\mathbf{q}\sigma} = i\langle \hat{\psi}_{\mathbf{q}\sigma}\rangle \quad \Longrightarrow \quad v_{\mathbf{q}+\boldsymbol{\pi}\sigma} = -v_{\mathbf{q}\sigma}^*$$

Since the form factors satisfy $\varphi_{\mathbf{q}+\boldsymbol{\pi}}^{(\gamma)} = -\varphi_{\mathbf{q}}^{(\gamma)}$, we get:

$$\begin{aligned}\frac{1}{(L_x L_y)^2} \sum_{\mathbf{q},\mathbf{q}'} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} v_{\mathbf{q}\sigma} v_{\mathbf{q}'\sigma} &= \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}\in\mathrm{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} v_{\mathbf{q}\sigma}\right] \left[\frac{1}{L_x L_y} \sum_{\mathbf{q}'\in\mathrm{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} v_{\mathbf{q}'\sigma}\right] \\ &= v_{\sigma}^{(\gamma)} \left[\frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \varphi_{\mathbf{k}+\boldsymbol{\pi}}^{(\gamma)*} v_{\mathbf{k}+\boldsymbol{\pi}\sigma}\right] \\ &= v_{\sigma}^{(\gamma)} \left[\frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \varphi_{\mathbf{k}}^{(\gamma)*} v_{\mathbf{k}\sigma}^*\right] \\ &= v_{\sigma}^{(\gamma)} \times v_{\sigma}^{(\gamma)*}\end{aligned}$$

where in the second passage we employed the change of variables $\mathbf{q}' = \mathbf{k}+\boldsymbol{\pi}$ and used BZ periodicity to map the original sum onto a new sum for $\mathbf{k} \in \mathrm{BZ}$. Inserting the above results in Eq. (3.33), this last becomes:

$$E_{\mathrm{F}/V}^{(\mathrm{AF})} = L_x L_y \times \frac{V}{2} \sum_{\gamma,\sigma} \left[\left|u_{\sigma}^{(\gamma)}\right|^2 + \left|v_{\sigma}^{(\gamma)}\right|^2\right] \tag{3.34}$$

Interestingly enough, the new HFPs amplitudes contribute to lowering the contraction energy.

3.4 Full MFT hamiltonian and gap complexification

Finally, it is time to collect everything in a single hamiltonian operator. The MFT model is approximated by:

$$\begin{aligned}\hat{H} \simeq \sum_{\sigma} \sum_{\mathbf{k}\in\mathrm{MBZ}} \tilde{\epsilon}_{\mathbf{k}\sigma} \left[\hat{n}_{\mathbf{k}\sigma} - \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma}\right] \\ - \sum_{\sigma} \sum_{\mathbf{k}\in\mathrm{MBZ}} \left[\tilde{\Delta}_{\mathbf{k}\sigma} \hat{\psi}_{\mathbf{k}\sigma} + \tilde{\Delta}_{\mathbf{k}\sigma}^* \hat{\psi}_{\mathbf{k}\sigma}^\dagger\right] - \left[E_{\mathrm{H}/U}^{(\mathrm{AF})} + E_{\mathrm{H}/V}^{(\mathrm{AF})} + E_{\mathrm{F}/V}^{(\mathrm{AF})}\right]\end{aligned}$$

where the renormalized bands are given by:

$$\tilde{\epsilon}_{\mathbf{k}\sigma} = \epsilon_{\mathbf{k}\sigma} + V \sum_{\gamma\in\{s^*,d\}} u_{\sigma}^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*}$$

and the full gap function by

$$\tilde{\Delta}_{\mathbf{k}\sigma} = \Delta_{\mathbf{k}\sigma} + iV \sum_{\gamma,\sigma} v_\sigma^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*}$$

The gap correction is purely imaginary, compared to the HM gap $\Delta_{\mathbf{k}\sigma} = (-1)^{\delta_{\sigma=\downarrow}} mU$. This has two obvious consequences: being no other contribution to the x pseudospin projections other than the pure HM ones, spin antisymmetry is preserved within such direction

$$\langle \hat{s}^x_{\mathbf{k}\sigma} \rangle = - \langle \hat{s}^x_{\mathbf{k}\bar{\sigma}} \rangle$$

which is relevant in the computation of the physical magnetization,

$$\begin{aligned} m &= \frac{1}{2L_x L_y} \sum_{\mathbf{r}} (-1)^{x+y} \langle \hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow} \rangle \\ &= \frac{1}{2L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \left\langle \hat{s}^x_{\mathbf{k}\uparrow} - \hat{s}^x_{\mathbf{k}\downarrow} \right\rangle \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \left\langle \hat{s}^x_{\mathbf{k}\uparrow} \right\rangle \end{aligned}$$

A proof of the above derivation is given in Sec. B.1.6. Moreover, the net effect $\hat{H}_V$ is a "gap complexification". In other words,

$$\left| \mathrm{Im}\{\Delta_{\mathbf{k}\sigma}\} \right| \geq 0 \quad \Longrightarrow \quad \left| \langle s^y_{\mathbf{k}\sigma} \rangle \right| \geq 0$$

while for the HM the y pseudospin component was identically null.

3.4.1 The relative phase in the zero temperature half-filled ground state

In Sec. B.1.3, we derive analytically the AF ground state on the conventional HM at zero temperature, as a simple Bloch's transform of a polarized (tilted) pseudospins collective pure state. Eq. (B.26) reports the final form of said ground-state. Said quantum state is in general pretty similar to the conventional BCS state.

At half-filling and zero temperature, it is rather easy to extended that state to the new complexified gap. By performing an identical calculation as in Sec. B.1.3 we here omit, it's easy to show that the new ground state for the EHM in the AF phase is identical, with RMPs in the various amplitudes and a relative phase taking care of the gap function complex phase,

$$|\Psi\rangle = \bigotimes_{\sigma} \bigotimes_{\mathbf{k}\in\mathrm{MBZ}} \left[\sin\tilde{\theta}_{\mathbf{k}\sigma} \hat{c}^\dagger_{\mathbf{k}\sigma} + e^{2i\tilde{\zeta}_{\mathbf{k}\sigma}} \cos\tilde{\theta}_{\mathbf{k}\sigma} \hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma} \right] |\Omega_{\mathbf{k}\sigma}\rangle \tag{3.35}$$

which is identical to Eq. (B.26). The angles appearing in the above Eq. (3.9), which acquire a physical meaning: [To be continued...]

3.4.2 AF phase flavours and spin degeneracy

The AF phase we are studying cannot break inversion symmetry, a core property of the system which is respected from all our approximations. This translates in the simple requirement that:

$$\tilde{E}_{\mathbf{k}\sigma} \overset{!}{=} \tilde{E}_{-\mathbf{k}\sigma}$$

We know that:

$$\tilde{E}_{\mathbf{k}\sigma} = \sqrt{\tilde{\epsilon}^2_{\mathbf{k}\sigma} + \mathrm{Re}^2\{\tilde{\Delta}_{\mathbf{k}\sigma}\} + \mathrm{Im}^2\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}$$

The renormalized bare bands as well as the real part of the gap satisfy the inversion symmetry requirement,

$$\tilde{\epsilon}_{\mathbf{k}\sigma} = \tilde{\epsilon}_{-\mathbf{k}\sigma} \qquad \mathrm{Re}\{\tilde{\Delta}_{\mathbf{k}\sigma}\} = \mathrm{Re}\{\tilde{\Delta}_{-\mathbf{k}\sigma}\}$$

hence inversion symmetry is respected only if

$$\mathrm{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\} = \pm\, \mathrm{Im}\{\tilde{\Delta}_{-\mathbf{k}\sigma}\}$$

Phase	HFPs
sAF	$\{m, u^{(s^*)}, u^{(d)}, v^{(s^*)}, v^{(d)}\}$
aAF	$\{m, u^{(s^*)}, u^{(d)}, -iv^{(p_x)}, -iv^{(p_y)}\}$

Table 3.5 Set of HFP for the two possible realization of the AF phase, respectively a symmetric and an antisymmetric imaginary part of the gap.

which is: either the imaginary part of the gap is inversion symmetric, or is antisymmetric. Based on this trivial consideration, we are able two discard two of the four self-consistency equations for the v-related HFPs: s^* and d-wave symmetries HFPs – Eqns. (3.28) and (3.29), respectively – are nonzero if $\mathrm{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}$ is momentum-even; p_x and p_y-wave symmetries HFPs – Eqns. (3.30) and (3.31), respectively – are nonzero if $\mathrm{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}$ is momentum-odd. The two option cannot coexist, and separate simulations can be implemented in the two symmetry sectors. We name the two possible symmetries "sAF" (symmetric antiferromagnet) and "aAF" (antisymmetric antiferromagnet). The set of HFPs then restricts in these AF structures, and is reported for both cases in Tab. 3.5.

Moreover, from now on we will omit the σ index, working just in the $\uparrow$ sector. As said in Sec. **??**, the AF phase does not break $\mathbb{Z}_2$ spin inversion symmetry, being the SDW ordering generated by a staggered but symmetric spin density distribution among sites. The MFT hamiltonian is invariant by a $\sigma \leftrightarrow \overline{\sigma}$ exchange, thus all measurable physical quantities must be. What is unmeasurable and has no effect on Physics is free to be σ-dependent, as for the sign of $\mathrm{Re}\{\Delta_{\mathbf{k}\sigma}\}$. Since all it's relevant of both the complex components of the gap function is their magnitude, we can safely treat σ as a pure degeneracy. This gives a simple equation for the last HFP,

$$\begin{aligned} m &= \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \langle \hat{s}^x_{\mathbf{k}\uparrow} \rangle \\ &= -\frac{1}{2L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \frac{\mathrm{Re}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{k}}[\beta, \tilde{\mu}] \end{aligned} \tag{3.36}$$

[To be continued...]

3.5 Stability of the AF phase

The discussion above is formally correct and self-consistent, thus a HF algorithm can be sketched to extract the HFPs. However we cannot proceed without considering the instability effects of Sec. B.1.7. As is known (and we would have liked to notice earlier) the AF-SSB at wavevector $\boldsymbol{\pi}$ we are studying here, responsible of halving the BZ down to the MBZ, can produce a stable phase on pure Hubbard lattices only at half filling [**singh1990collective**]. For the EHM the situation is even worse than that: repeating the simple Linear Reponse Theory (LRT) computations of Sec. B.1.7 and mimicking Eq. (B.31), we get a proper response function

$$\tilde{\chi}_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\mathbf{k}, \omega) = \frac{\chi_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\mathbf{k}, \omega)}{1 - [U - 2V(\cos k_x + \cos k_y)]\, \chi_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\mathbf{k}, \omega)} \tag{3.37}$$

[Double check the red part and conclude this paragraph...].

As is well documented in literature [**wietek2021stripes**], AF can establish in a wide range of spatial structures with particular shapes, for example stripes. In order to extract the precise AF phase, we should

1. Choose an initializer wavevector, say $\mathbf{k} = \boldsymbol{\pi}$;
2. Solve self-consistently for the HFPs at $\mathbf{k}$;
3. Compute the free energy F as a functional of the wavevector around $\mathbf{k}$;
4. Look for gradient descent of the free energy, $\boldsymbol{\nabla} F < 0$;

5. If the gradient descent is found, update $\mathbf{k} \to \mathbf{k} + \delta\mathbf{k}$ and repeat from step 2, otherwise halt.

Of course the sketched procedure can lead to a lot of complications, first the fact that at incommensurate wavevector $\mathbf{k} \neq \boldsymbol{\pi}$ the unit cell is not as simple as a pair of sites, but can become much larger requiring more refined computational solutions.

In this text we will show the self consistent result for AF-SSB at wavevector $\boldsymbol{\pi}$ even at finite doping as a first step in the above sketched procedure. The presented results are self-consistent, but unfortunately deeply unstable and unphysical at finite doping, a situation where an incommensurate and insulating AF phase is preferred to this commensurate metallic counterpart. Nevertheless we present them anyway.

3.6 AF free energy density

In order to derive the expression of the free energy density for the AF phase, we proceed precisely as in Sec. 2.4. The only notable difference is in entropy: Eq. (2.19) is written for two opposite bands on MBZ

$$s = s^{(+)} + s^{(-)}$$

with

$$s^{(\pm)} \equiv -\frac{k_B}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \Big[\Big(1 - f(\pm\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})\Big) \ln \Big(1 - f(\pm\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})\Big) + f(\pm\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu}) \ln f(\pm\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu}) \Big] \tag{3.38}$$

Consider also that we are computing free energy on the gran-canonical hamiltonian

$$\hat{H} - \mu\hat{N} \simeq \sum_{\sigma} \sum_{\mathbf{k}\in\mathrm{MBZ}} \Big[(\tilde{E}_{\mathbf{k}} - \tilde{\mu}) \hat{\gamma}^{(+)\dagger}_{\mathbf{k}\sigma} \hat{\gamma}^{(+)}_{\mathbf{k}\sigma} - (\tilde{E}_{\mathbf{k}} + \tilde{\mu}) \hat{\gamma}^{(-)\dagger}_{\mathbf{k}\sigma} \hat{\gamma}^{(-)}_{\mathbf{k}\sigma} \Big] + E_{\mathrm{c}}^{(\mathrm{AF})}$$

being $E_{\mathrm{c}}^{(\mathrm{AF})}$ the total AF contraction energy. Note that on the left-hand side we have μ and on the right-hand side its RMP counterpart $\tilde{\mu}$.

With identical meaning of the notation with respect to Sec. 2.4, the free energy contributions are:

1. Quasiparticles energy, taking care of spin degeneracy:

$$e_{\mathrm{g}}^{(\mathrm{AF})} = \frac{2}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} (\tilde{E}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu}) - \frac{2}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} (\tilde{E}_{\mathbf{k}} + \tilde{\mu}) f(-\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})$$

2. Contraction energy:

$$e_{\mathrm{c}}^{(\mathrm{AF})} = U(m^2 - n^2) + V \left[2zn^2 - \sum_{\gamma} \Big(\big|u^{(\gamma)}\big|^2 + \big|v^{(\gamma)}\big|^2 \Big) \right]$$

3. Entropic energy

$$e_{s}^{(\mathrm{AF})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \ln \Big(1 - f(\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})\Big) - \frac{2}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} (\tilde{E}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})$$
$$\frac{2}{\beta L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \ln \Big(1 - f(-\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})\Big) + \frac{2}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} (\tilde{E}_{\mathbf{k}} + \tilde{\mu}) f(-\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})$$

4. Chemical potential correction

$$e_{n}^{(\mathrm{AF})} = \mu n$$

Compose everything

$$f_{\mathrm{MFT}}^{(\mathrm{AF})} \equiv e_{\mathrm{g}}^{(\mathrm{AF})} + e_{\mathrm{c}}^{(\mathrm{AF})} + e_{s}^{(\mathrm{AF})} + e_{n}^{(\mathrm{AF})}$$

and we get

$$f_{\mathrm{MFT}}^{(\mathrm{AF})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \left[\ln\left(1 - f(\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})\right) + \ln\left(1 - f(-\tilde{E}_{\mathbf{k}};\beta,\tilde{\mu})\right)\right] + U(m^2 - n^2) + V\left[2zn^2 - \sum_{\gamma}\left(\left|u^{(\gamma)}\right|^2 + \left|v^{(\gamma)}\right|^2\right)\right] + \mu n \quad (3.39)$$

It's of particular interest the half-filling condition, with $\tilde{\mu} = 0$. [To be continued...]

3.7 Numerical simulations

[To be continued...]

3.7.1 HF iterative algorithm sketch

[To be continued...]

Chapter 4

Superconducting instability

This chapter is devoted to studying the superconducting phase of the system. The only symmetry we assume to break is the $\mathrm{U}^{\mathrm{c}}(1)$ charge symmetry, thus allowing for superconducting fluctuations. As is described thoroughly in Sec. 4.3.1, the hopping amplitude is renormalized because of the non-local attraction. The symmetry structure of the pairing mechanism determines the contributing Cooper fluctuations: for s-wave and d-wave superconductivity, only the o.s. Cooper term contributes; for p_ℓ-wave superconductivity, the s.s. term contributes as well. In the following sections, a derivation containing both Cooper terms is proposed.

4.1 The SC phase and its symmetries

The starting point is, as done for the other phases, the discussion of the symmetries of the SC phase. We said in introduction we are studying the

$$\mathrm{SU}(2) \times \mathrm{U}^{\mathrm{c}}(1) \times (\text{Point group}) \quad \overset{\text{SSB}}{\to} \quad \mathrm{SU}(2) \times (\text{Point group})$$

symmetry breaking. Therefore the system density we assume to be uniform across all sites, similarly to the normal phase discussed in Chap. 2. [To be continued...]

Let us highlight now an important point regarding the Cooper class Wick's contractions performed on the general EHM of Eq. (**??**),

$$\hat{H} = \underbrace{-t \sum_{\langle ij \rangle} \sum_{\sigma} \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma}}_{\hat{H}_t} \underbrace{+U \sum_{i} \hat{c}^\dagger_{i\uparrow} \hat{c}^\dagger_{i\downarrow} \hat{c}_{i\downarrow} \hat{c}_{i\uparrow}}_{\hat{H}_U} \underbrace{-V \sum_{\langle ij \rangle} \sum_{\sigma\sigma'} \hat{c}^\dagger_{i\sigma} \hat{c}^\dagger_{j\sigma'} \hat{c}_{j\sigma'} \hat{c}_{i\sigma}}_{\hat{H}_V}$$

As is discussed in Sec. 1.3, when applying Wick's theorem the resulting terms break the natural symmetries of the model. The superconducting symmetry we study breaks just the $\mathrm{U}^{\mathrm{c}}(1)$ charge conservation. Now, when dealing with superconducting Cooper pairing we need to account also for the spatial structure of the Cooper pair itself. Consider the generic Cooper fluctuation

$$\langle \hat{c}^\dagger_{i\sigma} \hat{c}^\dagger_{j\sigma'} \rangle \quad \text{with } i, j \text{ NN}$$

From basic Quantum Mechanics we know the summation rules of the spin algebra $\mathfrak{su}(2)$,

$$\frac{1}{2} \otimes \frac{1}{2} = 0 \oplus 1$$

The two pairing channels are, at this level, the singlet channel associated to total spin 0 and the triplet channel associated to total spin 1. If we impose a specific spatial symmetry on the hamiltonian the ground state wavefunction will follow naturally, and the pairing channel will be the one providing a total anti-symmetry to the full wavefunction. This gives a selection rule over the relevant pairings: if we work with space symmetric structures – say, s^*-wave or d-wave – the pairing will take place in singlet channel, allowing us to eliminate the triplet pairing. Working with antisymmetric structures, inversely, we can eliminate the singlet channel. This concept is summarized in Tab. 4.1.

Spatial structure	Pairing channel	RWCs in Cooper channel
Symmetric wave function	Singlet pairing	Just $\langle \hat{c}^\dagger_{i\sigma}\hat{c}^\dagger_{j\bar{\sigma}}\rangle$
Anti-symmetric wave function	Triplet pairing	Both $\langle \hat{c}^\dagger_{i\sigma}\hat{c}^\dagger_{j\bar{\sigma}}\rangle$ and $\langle \hat{c}^\dagger_{i\sigma}\hat{c}^\dagger_{j\sigma}\rangle$

Table 4.1 Relation of the Cooper pairing channel with the wavefunction spatial symmetry (intended as the inversion $(x, y) \to (-x, -y)$).

4.1.1 Superconductivity in the HM

In Sec. B.2, we discuss in detail the (impossibility of a stable) s-wave SC phase in the conventional HM. This is an obvious result, since the two-body interaction thereby present $\hat{H}_U$ is local and repulsive. We nevertheless treat the model within the MFT framework, and here recall the main widely known results, and later use them as groundwork for the EHM extension. Similarly to Sec. 3.1.1, let us define the operators

$$\hat{n}_{\mathbf{k}\sigma} \equiv \hat{c}^\dagger_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma} \tag{4.1}$$

$$\hat{\phi}_{\mathbf{k}} \equiv \hat{c}_{-\mathbf{k}\downarrow}\hat{c}_{\mathbf{k}\uparrow} \tag{4.2}$$

whose EVs are relevant for the SC phase. Let:

$$u_{\mathbf{k}\sigma} \equiv \langle \hat{n}_{\mathbf{q}\sigma}\rangle \tag{4.3}$$

$$w_{\mathbf{k}} \equiv \langle \hat{\phi}^\dagger_{\mathbf{k}}\rangle \tag{4.4}$$

The MFT hamiltonian is given explicitly for the HM in Eq. (B.42),

$$\hat{H}_t + \hat{H}_U \overset{\text{MFT}}{\simeq} \sum_{\mathbf{k}\in\text{BZ}} \epsilon_{\mathbf{k}} \left[\hat{c}^\dagger_{\mathbf{k}\uparrow}\hat{c}_{\mathbf{k}\uparrow} - \hat{c}_{\mathbf{k}\downarrow}\hat{c}^\dagger_{\mathbf{k}\downarrow}\right] + E^{(\text{SC})}_{\text{a}} - \sum_{\mathbf{q}\in\text{BZ}} \left[\Delta^{(s)}\hat{\phi}_{\mathbf{q}} + \Delta^{(s)*}\hat{\phi}^\dagger_{\mathbf{q}}\right] + nU \times \hat{N} - \left[E^{(\text{SC})}_{\text{H}/U} + E^{(\text{SC})}_{\text{C}/U}\right]$$

with $E^{(\text{SC})}_{\text{H}/U}$, $E^{(\text{SC})}_{\text{C}/U}$ the contraction energies arising from Hartree and Cooper channels, and $E^{(\text{SC})}_{\text{a}}$ the energy shift resulting from anticommutation rules, given respectively in Eq. (B.35), (B.40), and (B.44).

In deriving this result we decomposed the interaction of the intermediate passage of Eq. (B.36) and assumed the Cooper pair to have null total momentum. Moreover, we recognized in the passage of Eq. (B.39) the presence of a s-wave harmonic transform of the function $w_{\mathbf{q}}$, and thus defined in Eq. (B.38),

$$w^{(s)} \equiv \frac{1}{L_x L_y} \sum_{\mathbf{q}\in\text{BZ}} w_{\mathbf{q}} \quad \text{and} \quad \Delta^{(s)} \equiv -U w^{(s)}$$

Nambu-Bogoliubov representation of the MFT hamiltonian is given in Eq. (B.45) and equivalently in Eq. (B.47),

$$\hat{H}_t + \hat{H}_U - \mu\hat{N} \simeq \sum_{\mathbf{k}\in\text{BZ}} \sum_{\sigma} \hat{\Phi}^\dagger_{\mathbf{k}} h_{\mathbf{k}} \hat{\Phi}_{\mathbf{k}} + E^{(\text{SC})}_{\text{a}} - \left[E^{(\text{SC})}_{\text{H}/U} + E^{(\text{SC})}_{\text{C}/U}\right]$$

being

$$h_{\mathbf{k}} \equiv \begin{bmatrix} \xi_{\mathbf{k}} & -\Delta^*_{\mathbf{k}} \\ -\Delta_{\mathbf{k}} & -\xi_{\mathbf{k}} \end{bmatrix} \quad \text{with} \quad \xi_{\mathbf{k}} \equiv \epsilon_{\mathbf{k}} - \tilde{\mu}$$

and $\Delta_{\mathbf{k}} = \Delta^{(s)}$. The hamiltonian can be written equivalently as

$$h_{\mathbf{k}} = \xi_{\mathbf{k}}\tau^z - \text{Re}\{\Delta_{\mathbf{k}}\}\tau^x - \text{Im}\{\Delta_{\mathbf{k}}\}\tau^y$$

Nambu spinors are, in this case,

$$\hat{\Phi}_{\mathbf{k}} \equiv \begin{bmatrix} \hat{c}_{\mathbf{k}\uparrow} \\ \hat{c}^\dagger_{-\mathbf{k}\downarrow} \end{bmatrix}$$

EV	Meaning	Equation
$\langle \hat{s}^x_{\mathbf{k}} \rangle$	$\left\langle \hat{\phi}_{\mathbf{k}} + \hat{\phi}^\dagger_{\mathbf{k}} \right\rangle$	(B.55)
$\langle \hat{s}^y_{\mathbf{k}} \rangle$	$i \left\langle \hat{\phi}_{\mathbf{k}} - \hat{\phi}^\dagger_{\mathbf{k}} \right\rangle$	(B.56)
$\langle \hat{s}^z_{\mathbf{k}} \rangle$	$\langle \hat{n}_{\mathbf{k}\uparrow} + \hat{n}_{\mathbf{k}\downarrow} \rangle - 1$	(B.57)

Table 4.2 List of the various expectation values (EVs) of each pseudospin component, their meaning in terms of fermionic operators and the reference equations from the pure HM. The z component refers also to Eq. (B.43).

For the SC phase in the HM model, in general, we can admit for a complex gap function – although being the gap a constant it can always be reduced to a purely real gap. Diagonalization by the angles defined in Eq. (B.46) is performed via the composed rotation of Eq. (B.48),

$$W_{\mathbf{k}} = \begin{bmatrix} \cos\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} & -\sin\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \\ \sin\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} & \cos\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \end{bmatrix}$$

The Bogoliubov bands are $\pm E_{\mathbf{k}} = \sqrt{\xi^2_{\mathbf{k}} + |\Delta_{\mathbf{k}}|^2}$. The only crucial difference with the AF Bogoliubov bands it that here, apart from the absence of the spin index – a degeneracy that is solved now by enlarging the computation to the entire BZ –, also the bare bands $\epsilon_{\mathbf{k}}$ are substituted by their shifted version $\xi_{\mathbf{k}}$. This difference is essential: it is this feature that makes the superconducting phase gapped in an insulating sense, which means, opening the gap at the position of $\tilde{\mu}$. Instead for the AF phase the gap was always opened at "midband", the MBZ contour where $\epsilon_{\mathbf{k}} = 0$. As a final remark, as is proven trivially at the end of Sec. B.2.5, s-wave SC is impossible at MFT level on the pure HM. This was obvious, due to the necessity of an even small attractive interaction to form Cooper pairs. To conclude, in Tab. 4.2 we report the operator-pseudospin map for each direction.

4.1.2 Extension to the EHM

Add now the non-local interaction $\hat{H}_V$: translational invariance is preserved while charge conservation is broken, thus all three channels (Hartree, Fock and Cooper) contribute via RWCs to the MFT hamiltonian. As for the AF phase, we aim to derive a MFT solution for the SC phase which is an extension of the HM solution of Sec. B.2, with an effective redefinition of the various physical quantities and mathematical objects,

$$\xi_{\mathbf{k}} \to \tilde{\xi}_{\mathbf{k}} \qquad E_{\mathbf{k}} \to \tilde{E}_{\mathbf{k}} \qquad \Delta_{\mathbf{k}} \to \tilde{\Delta}_{\mathbf{k}} \qquad \mu \to \tilde{\mu}$$

To be completely correct, the chemical potential was already renormalized in the HM derivation in Sec. B.2.1. It here acquires yet another renormalization. The band energies renormalization is simply

$$\tilde{E}_{\mathbf{k}} \equiv \sqrt{\tilde{\xi}^2_{\mathbf{k}} + |\tilde{\Delta}_{\mathbf{k}}|^2}$$

and as for the AF phase:

$$\langle \hat{\Phi}^\dagger_{\mathbf{k}} \tau^x \hat{\Phi}_{\mathbf{k}} \rangle = -\sin 2\tilde{\theta}_{\mathbf{k}} \sin 2\tilde{\zeta}_{\mathbf{k}} \langle \hat{\Gamma}^\dagger_{\mathbf{k}} \tau^z \hat{\Gamma}_{\mathbf{k}} \rangle \tag{4.5}$$

$$\langle \hat{\Phi}^\dagger_{\mathbf{k}} \tau^y \hat{\Phi}_{\mathbf{k}} \rangle = -\sin 2\tilde{\theta}_{\mathbf{k}} \cos 2\tilde{\zeta}_{\mathbf{k}} \langle \hat{\Gamma}^\dagger_{\mathbf{k}} \tau^z \hat{\Gamma}_{\mathbf{k}} \rangle \tag{4.6}$$

$$\langle \hat{\Phi}^\dagger_{\mathbf{k}} \tau^z \hat{\Phi}_{\mathbf{k}} \rangle = \cos 2\tilde{\theta}_{\mathbf{k}} \langle \hat{\Gamma}^\dagger_{\mathbf{k}} \tau^z \hat{\Gamma}_{\mathbf{k}} \rangle \tag{4.7}$$

These equations are identical to the ones for the pure HM, Eqns. (B.55), (B.56) and (B.57). In the tilted frame, we have the analogous of Eq. (3.7) with the important exception that the chemical potential in the Fermi-Dirac factors is zero,

$$\langle \hat{\Gamma}^\dagger_{\mathbf{k}} \tau^z \hat{\Gamma}_{\mathbf{k}} \rangle = \frac{1}{2} \left[f\left(\tilde{E}_{\mathbf{k}}; \beta, 0\right) - f\left(-\tilde{E}_{\mathbf{k}}; \beta, 0\right) \right] \tag{4.8}$$

This is because all the chemical potential operatorial contributions were absorbed in the bare bands $\tilde{\xi}_{\mathbf{k}}$, thus the pseudospin state is thermally described by an effective null chemical potential.

The (renormalized) thermal factors as in Eq. (B.54) are

$$\tilde{\mathrm{Th}}_{\mathbf{k}}^{(\pm)}[\beta, \tilde{\mu}] \equiv f\left(\tilde{E}_{\mathbf{k}}; \beta, 0\right) \pm f\left(-\tilde{E}_{\mathbf{k}}; \beta, 0\right) \tag{4.9}$$

which simply reduce to

$$\tilde{\mathrm{Th}}_{\mathbf{k}}^{(+)} = 1$$
$$\tilde{\mathrm{Th}}_{\mathbf{k}}^{(-)} = -\tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$$

For the angles it holds

$$\sin(2\tilde{\xi}_{\mathbf{k}}) = \frac{\mathrm{Re}\{\tilde{\Delta}_{\mathbf{k}}\}}{|\tilde{\Delta}_{\mathbf{k}}|} \quad \cos(2\tilde{\xi}_{\mathbf{k}}) = \frac{\mathrm{Im}\{\tilde{\Delta}_{\mathbf{k}}\}}{|\tilde{\Delta}_{\mathbf{k}}|} \quad \sin(2\tilde{\theta}_{\mathbf{k}}) = \frac{|\tilde{\Delta}_{\mathbf{k}}|}{\tilde{E}_{\mathbf{k}}} \quad \cos(2\tilde{\theta}_{\mathbf{k}}) = \frac{\tilde{\xi}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tag{4.10}$$

From Tabs. 1.3 and 1.4, we know all channel contribute. It is already known the effect of the Fock contractions, responsible as for the normal phase (Chap. 2) of the bare bands renormalization. Cooper terms are to be handled more carefully, since can contribute to superconductivity both in the s.s. and in the o.s. spin sectors.

4.2 Non-local Hartree effects: chemical potential renormalization

As always, let us start with a very brief section about the Hartree effects on the MFT decomposition of the hamiltonian. We will not delve in the detailed calculations of the Hartree channel MFT effects, already described in previous chapter as well as in Sec. B.2. The only effect here is the chemical potential renormalization.

4.2.1 Hartree channel in the SC phase: analytic derivation

The Hartree fluctuations are density-density couplings in the MFT hamiltonian. Knowing the deal with a uniform-density phase, we can re-use as it is the derivation of Sec. 2.2.1. Without repeating the calculations, the $\hat{H}_V$ is reduced in the Hartree channel to

$$\hat{H}_V \simeq -2nzV \times \hat{N} - E_{\mathrm{H}/V}^{(\mathrm{SC})} + (\text{all the rest})$$

This, together with the $\hat{H}_U$ Hartree channel decomposition

$$\hat{H}_U \simeq nU \times \hat{N} - E_{\mathrm{H}/U}^{(\mathrm{SC})}$$

gives the chemical potential full renormalization, identical to Eq. (2.5),

$$\tilde{\mu} \equiv \mu + n(2zV - U) \tag{4.11}$$

4.2.2 Hartree contraction energy

The contraction energy for the non-local sector was derived in Eq. (2.7),

$$E_{\mathrm{H}/V}^{(\mathrm{SC})} = -L_x L_y \times 2zn^2 V$$

and together with the local counterpart of Eq. (2.6)

$$E_{\mathrm{H}/U}^{(\mathrm{SC})} = L_x L_y \times n^2 U$$

Now we move to the more interesting Fock sector.

4.3 Fock effects: bare bands renormalization

[To be continued...]

4.3.1 Fock channel in the SC phase: analytic derivation

When it comes to the Fock RWCs, being the SC phase density-uniform we can re-use almost the entirety of the derivation of Sec. 2.3. Setting as in Eq. (2.15)

$$u_{\mathbf{k}\sigma} \equiv \langle \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma} \rangle \tag{4.12}$$

Eq. (2.16) stands perfectly valid, translated to the SC phase

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} \Big[\langle \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma} \rangle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma} + \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma} \langle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma} \rangle - \langle \hat{c}^\dagger_{i\sigma} \hat{c}_{j\sigma} \rangle \langle \hat{c}^\dagger_{j\sigma} \hat{c}_{i\sigma} \rangle \Big] \\ \stackrel{\mathcal{F}}{=} \sum_{\gamma,\sigma} \left[\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \mathrm{BZ}} \varphi^{(\gamma)}_{\mathbf{k}} u_{\mathbf{k}\sigma} \right] \times V \sum_{\mathbf{k}' \in \mathrm{BZ}} \varphi^{(\gamma)*}_{\mathbf{k}'} \hat{c}^\dagger_{\mathbf{k}'\sigma} \hat{c}_{\mathbf{k}'\sigma} - E^{(\mathrm{SC})}_{\mathrm{F}/V} \end{aligned} \tag{4.13}$$

being

$$E^{(\mathrm{SC})}_{\mathrm{F}/V} \equiv \frac{V}{L_x L_y} \sum_{\mathbf{k},\mathbf{k}'} \sum_{\sigma} \left[\cos(\delta k_x) + \cos(\delta k_y) \right] \langle \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma} \rangle \langle \hat{c}^\dagger_{\mathbf{k}'\sigma} \hat{c}_{\mathbf{k}'\sigma} \rangle \tag{4.14}$$

To get to this point, we employed the assumption

$$\langle \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}'\sigma'} \rangle = \delta_{\mathbf{k}=\mathbf{k}'} \delta_{\sigma=\sigma'} \langle \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma} \rangle$$

which essentially states translational invariance and spin degeneracy. This assumption is obviously well-verified by the BCS ground state of Eq. [Missing]. Recognising the symmetry decomposition

$$u^{(\gamma)}_{\sigma} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \mathrm{BZ}} \varphi^{(\gamma)}_{\mathbf{k}} \langle \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma} \rangle$$

due to inversion symmetry the conclusion is identical to Eqns. (2.16) and (2.17) (considering spin degeneracy),

$$\tilde{\epsilon}_{\mathbf{k}} \equiv \epsilon_{\mathbf{k}} + u^{(s^*)} V (\cos k_x + \cos k_y) + u^{(d)} V (\cos k_x - \cos k_y)$$

In order to estimate the γ-wave components renormalizing the bare bands, we need to compute separately in spin sectors the EVs of $u_{\mathbf{k}\sigma}$

$$\begin{aligned} u_{\mathbf{k}\uparrow} &= \langle \hat{c}^\dagger_{\mathbf{k}\uparrow} \hat{c}_{\mathbf{k}\uparrow} \rangle \\ &= \left\langle \hat{\Phi}^\dagger_{\mathbf{k}} \frac{\mathbb{I} + \tau^z}{2} \hat{\Phi}_{\mathbf{k}} \right\rangle \\ &= \frac{1}{2} \left[\left\langle \hat{\Gamma}^\dagger_{\mathbf{k}} \hat{\Gamma}_{\mathbf{k}} \right\rangle + \langle \hat{s}^z_{\mathbf{k}} \rangle \right] \\ &= \frac{1}{2} \left[\tilde{\mathrm{Th}}^{(+)}_{\mathbf{k}}[\beta] + \cos 2\tilde{\theta}_{\mathbf{k}} \tilde{\mathrm{Th}}^{(-)}_{\mathbf{k}}[\beta] \right] \\ &= \frac{1}{2} \left[1 - \cos(2\tilde{\theta}_{\mathbf{k}}) \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2} \right) \right] \end{aligned} \tag{4.15}$$

Symmetry	Self-consistency equation	Graph
s^*-wave	$u^{(s^*)} = \frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{BZ}}(\cos k_x + \cos k_y)\left[1 - \frac{\tilde{\xi}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}}\tanh\left(\frac{\beta\tilde{E}_{\mathbf{k}}}{2}\right)\right]$	Fig. 1.4b
$d_{x^2-y^2}$-wave	$u^{(d)} = \frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{BZ}}(\cos k_x - \cos k_y)\left[1 - \frac{\tilde{\xi}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}}\tanh\left(\frac{\beta\tilde{E}_{\mathbf{k}}}{2}\right)\right]$	Fig. 1.4e

Table 4.3 | Symmetry resolved self-consistency equations for the harmonics of $u_{\mathbf{k}}$.

having we used Eq. (4.9) and following. For the spin $\downarrow$ EV,

$$\begin{aligned}
u_{-\mathbf{k}\downarrow} &= \langle \hat{c}^\dagger_{-\mathbf{k}\downarrow}\hat{c}_{-\mathbf{k}\downarrow}\rangle \\
&= 1 - \langle \hat{c}_{-\mathbf{k}\downarrow}\hat{c}^\dagger_{-\mathbf{k}\downarrow}\rangle \\
&= 1 - \left\langle \hat{\Phi}^\dagger_{\mathbf{k}}\frac{\mathbb{I}-\tau^z}{2}\hat{\Phi}_{\mathbf{k}}\right\rangle \\
&= 1 - \frac{1}{2}\left[\left\langle \hat{\Gamma}^\dagger_{\mathbf{k}}\hat{\Gamma}_{\mathbf{k}}\right\rangle - \langle \hat{s}^z_{\mathbf{k}}\rangle\right] \\
&= 1 - \frac{1}{2}\left[\tilde{\mathrm{Th}}^{(+)}_{\mathbf{k}}[\beta] - \cos 2\tilde{\theta}_{\mathbf{k}}\tilde{\mathrm{Th}}^{(-)}_{\mathbf{k}}[\beta]\right] \\
&= 1 - \frac{1}{2}\left[1 + \cos(2\tilde{\theta}_{\mathbf{k}})\tanh\left(\frac{\beta\tilde{E}_{\mathbf{k}}}{2}\right)\right]
\end{aligned} \tag{4.16}$$

From the above results, note first that

$$u_{\mathbf{k}\uparrow} = u_{-\mathbf{k}\downarrow}$$

which is coherent with our requirement of a uniform-density, spin uniform and inversion symmetric phase. Moreover,

$$\begin{aligned}
\lim_{\tilde{\theta}_{\mathbf{k}}\to 0} u_{\mathbf{k}\sigma} &= \frac{1}{2}\left[1 + \tanh\left(\frac{\beta\tilde{\xi}_{\mathbf{k}}}{2}\right)\right] \\
&= \frac{1}{2}\left[\frac{e^{\beta\tilde{\xi}_{\mathbf{k}}/2} + e^{-\beta\tilde{\xi}_{\mathbf{k}}/2}}{e^{\beta\tilde{\xi}_{\mathbf{k}}/2} + e^{-\beta\tilde{\xi}_{\mathbf{k}}/2}} - \frac{e^{\beta\tilde{\xi}_{\mathbf{k}}/2} - e^{-\beta\tilde{\xi}_{\mathbf{k}}/2}}{e^{\beta\tilde{\xi}_{\mathbf{k}}/2} + e^{-\beta\tilde{\xi}_{\mathbf{k}}/2}}\right] \\
&= f(\tilde{\epsilon}_{\mathbf{k}};\beta,\tilde{\mu})
\end{aligned}$$

Correctly, the null-gap limit (for which the angle reduces to zero) gives back a perfectly degenerate Fermi gas.

We can then derive the $u_{\mathbf{k}}$-related HFPs self-consistency equations. In next passages, we use $\sigma = \uparrow$ but could have used the opposite due to spin degeneracy discussed above. Then:

$$\begin{aligned}
u^{(\gamma)} &\equiv \frac{1}{L_xL_y}\sum_{\mathbf{k}\in\mathrm{BZ}}\varphi^{(\gamma)}_{\mathbf{k}}\langle \hat{n}_{\mathbf{k}\uparrow}\rangle \\
&= \frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{BZ}}\varphi^{(\gamma)}_{\mathbf{k}}\left[1 - \cos(2\tilde{\theta}_{\mathbf{k}})\tanh\left(\frac{\beta\tilde{E}_{\mathbf{k}}}{2}\right)\right]
\end{aligned} \tag{4.17}$$

reported explicitly for the only two inversion symmetric structures in Tab. 4.3.

4.3.2 Fock contraction energy

In terms of the energy shift due to Wick's contraction, Eq. (2.18) holds identically

$$E^{(\mathrm{SC})}_{\mathrm{F}/V} = L_xL_y \times V\left[\left|u^{(s^*)}\right|^2 + \left|u^{(d)}\right|^2\right]$$

with the only obvious difference that the $u^{(\gamma)}$ are computed on the SC ground state by the means of Eqns. (4.15), (4.16).

4.4 Cooper effects: anisotropic pairing

Anisotropic pairing in superconducting fluctuations is induced by the Cooper RWCs. The two sectors of $\hat{H}_V$ (o.s., s.s.) are Fourier-transformed respectively in Eqns. (1.16), (1.17). In Tab. 4.1 we identified the correct RWCs for singlet and triplet pairing channels, noting that the o.s. sector contributes to both while the s.s. to just the triplet channel.

4.4.1 Cooper o.s. channel in the SC phase: analytic derivation

This section deals with Cooper fluctuations induced by the o.s. part of the non-local hamiltonian –referring to the notation of Eq. (1.9)– somewhat the simplest form of Cooper pairing. This sector contributes both to singlet pairing and triplet pairing. Considering Cooper fluctuations in the singlet channel, we need to break $\mathrm{U}^{\mathrm{c}}(1)$ symmetry imposing space inversion symmetry, while for the triplet anti-symmetry is required. Set as in Eq. (4.4) the EV

$$w_{\mathbf{k}} = \langle \hat{\phi}^{\dagger}_{\mathbf{k}} \rangle$$

Let us now break down the MFT discussion for the local and non-local interactions.

Local repulsion. The detailed treatment of $\hat{H}_U$ is discussed in Sec. B.2.2, in the context of conventional HM. We here just sketch the most important results. By contracting in the Cooper channel the Fourier transform of $\hat{H}_U$ of Eq. (**??**),

$$\hat{H}_U \overset{\mathcal{F}}{=} \frac{U}{L_x L_y} \sum_{\mathbf{K},\mathbf{k},\mathbf{k}'} \hat{c}^{\dagger}_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^{\dagger}_{\mathbf{K}-\mathbf{k}\downarrow} \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow}$$

in the hypothesis that preserving space translations invariance the net momentum of the Cooper pair is null, as in Eq. (B.39) the local part of the hamiltonian is reduced to

$$\hat{H}_U \simeq (\text{Hartree channel}) + \frac{U}{L_x L_y} \sum_{\mathbf{k},\mathbf{k}'} \left[w_{\mathbf{k}} \hat{\phi}_{\mathbf{k}'} + w^{*}_{\mathbf{k}'} \hat{\phi}^{\dagger}_{\mathbf{k}} \right] - E^{(\mathrm{SC})}_{\mathrm{C}/U} \tag{4.18}$$

being $E^{(\mathrm{SC})}_{\mathrm{C}/U}$ the Cooper contraction given in Eq. (B.40). The Hartree channel is discussed in Sec. B.2.1. Let now:

$$w^{(s)} \equiv \frac{1}{L_x L_y} \sum_{\mathbf{k}\in \mathrm{BZ}} w_{\mathbf{k}}$$

which reduces Eq. (4.18) to

$$\hat{H}_U \simeq (\text{Hartree channel}) + U \sum_{\mathbf{k}\in \mathrm{BZ}} \left[w^{(s)} \hat{\phi}_{\mathbf{k}} + w^{(s)*} \hat{\phi}^{\dagger}_{\mathbf{k}} \right] - E^{(\mathrm{SC})}_{\mathrm{C}/U} \tag{4.19}$$

As in Eq. (B.41), this will produce the s-wave part of the gap function.

Non-local attraction. Consider Eq. (1.16), and perform Wick contractions in the Cooper channel, giving

$$\begin{aligned}
\hat{H}^{(\mathrm{o.s.})}_V \simeq\ & (\text{Hartree channel}) \\
& - \frac{2V}{L_x L_y} \sum_{\mathbf{K},\mathbf{k},\mathbf{k}'} \left[\cos(\delta k_x) + \cos(\delta k_y) \right] \times \Big[\langle \hat{c}^{\dagger}_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^{\dagger}_{\mathbf{K}-\mathbf{k}\downarrow} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow} \\
& \qquad + \hat{c}^{\dagger}_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^{\dagger}_{\mathbf{K}-\mathbf{k}\downarrow} \langle \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow} \rangle - \langle \hat{c}^{\dagger}_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^{\dagger}_{\mathbf{K}-\mathbf{k}\downarrow} \rangle \langle \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow} \rangle \Big]
\end{aligned}$$

Identical considerations as above hold, and just the $\mathbf{K} = \mathbf{0}$ term contributes.:

$$\begin{aligned}
\hat{H}^{(\mathrm{o.s.})}_V \simeq\ & (\text{Hartree channel}) \\
& - \frac{2V}{L_x L_y} \sum_{\mathbf{k},\mathbf{k}'} \left[\cos(\delta k_x) + \cos(\delta k_y) \right] \times \Big[\langle \hat{c}^{\dagger}_{\mathbf{k}\uparrow} \hat{c}^{\dagger}_{-\mathbf{k}\downarrow} \rangle \hat{c}_{-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{k}'\uparrow} \\
& \qquad + \hat{c}^{\dagger}_{\mathbf{k}\uparrow} \hat{c}^{\dagger}_{-\mathbf{k}\downarrow} \langle \hat{c}_{-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{k}'\uparrow} \rangle - \langle \hat{c}^{\dagger}_{\mathbf{k}\uparrow} \hat{c}^{\dagger}_{-\mathbf{k}\downarrow} \rangle \langle \hat{c}_{-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{k}'\uparrow} \rangle \Big]
\end{aligned}$$

Recognizing our superconducting order parameter in the various EVs, we get

$$\hat{H}_V^{(\text{o.s.})} \simeq (\text{Hartree channel}) - \frac{V}{L_x L_y} \sum_\gamma \sum_{\mathbf{k},\mathbf{k}'} \varphi_{\mathbf{k}}^{(\gamma)} \varphi_{\mathbf{k}'}^{(\gamma)*} \left[w_{\mathbf{k}} \hat{\phi}_{\mathbf{k}'} + w_{\mathbf{k}}^* \hat{\phi}_{\mathbf{k}'}^\dagger \right] - E_{\text{C}/V/\text{o.s.}}^{(\text{SC})} \tag{4.20}$$

We also made use of the harmonics decomposition of Eq. (1.26). In the above equation, the contraction energy is given by

$$E_{\text{C}/V/\text{o.s.}}^{(\text{SC})} \equiv -\frac{V}{L_x L_y} \sum_\gamma \sum_{\mathbf{k},\mathbf{k}'} \varphi_{\mathbf{k}}^{(\gamma)} \varphi_{\mathbf{k}'}^{(\gamma)*} w_{\mathbf{k}} w_{\mathbf{k}'}^* \tag{4.21}$$

Let then the harmonics $w^{(\gamma)}$ be

$$w^{(\gamma)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)} w_{\mathbf{k}}$$

Eq. (4.20) becomes

$$\hat{H}_V^{(\text{o.s.})} \simeq (\text{Hartree channel}) - V \sum_\gamma \sum_{\mathbf{k}\in\text{BZ}} \left[w^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*} \hat{\phi}_{\mathbf{k}} + \text{h.c.} \right] - E_{\text{C}/V/\text{o.s.}}^{(\text{SC})}$$

extending the symmetry sum to $\gamma \in \{s^*, p_x, p_y, d_{x^2-y^2}\}$.

For the γ-wave component of the superconducting order parameter, the following chain, similar to Eq. (B.58), holds:

$$\begin{aligned} w^{(\gamma)} &\equiv \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)} \langle \hat{\phi}_{\mathbf{k}}^\dagger \rangle \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)} \langle \hat{\Phi}_{\mathbf{k}}^\dagger \tau^+ \hat{\Phi}_{\mathbf{k}} \rangle \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)} \left[\langle \hat{s}_{\mathbf{k}}^x \rangle + i \langle \hat{s}_{\mathbf{k}}^y \rangle \right] \\ &= -\frac{1}{L_x L_y} \sum_{\mathbf{k}\in\text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)} \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta] \end{aligned} \tag{4.22}$$

where $\tau^+ \equiv \tau^x + i\tau^y$. We used Eqns. (4.5), (4.6) and (4.8) as well as the thermal factor defined in Eq. (4.9). The derivation above holds for all symmetries, including the s one as testifies Eq. (B.58). Explicitly, five self-consitency equations are then derived and listed in Tab. 4.4.

Of these, the singlet channel admits for non-zero fluctuations of the superconducting order parameter just in the s^* and d channels. This is because the gap function is inversion-symmetric and p_ℓ channels equations integrate it with an antisymmetric function.

4.4.2 Cooper o.s. contraction energy

The Cooper contraction energy is immediately derived from Eq. (4.21) by recognizing the harmonics of $w_{\mathbf{k}}$,

$$E_{\text{C}/V/\text{o.s.}}^{(\text{SC})} = -L_x L_y \times V \sum_\gamma \left| w^{(\gamma)} \right|^2$$

and is completed by its local counterpart

$$E_{\text{C}/U}^{(\text{SC})} = L_x L_y \times U \left| w^{(s)} \right|^2$$

discussed for the conventional HM in Eq. (B.40).

Symmetry	Self-consistency equation	Graph
s-wave	$w^{(s)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$	Fig. 1.4a
s^*-wave	$w^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\cos k_x + \cos k_y) \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$	Fig. 1.4b
p_x-wave	$w^{(p_x)} = \frac{i\sqrt{2}}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \sin k_x \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$	Fig. 1.4c
p_y-wave	$w^{(p_y)} = \frac{i\sqrt{2}}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \sin k_y \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$	Fig. 1.4d
$d_{x^2-y^2}$-wave	$w^{(d)} = \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} (\cos k_x - \cos k_y) \frac{\tilde{\Delta}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right)$	Fig. 1.4e

Table 4.4 | Symmetry resolved self-consistency equations for the harmonics of $w_{\mathbf{k}}$.

4.4.3 Cooper s.s. channel in the SC phase: analytical considerations

Consider Eq. (1.17) in the Cooper channel,

$$\begin{aligned}\hat{H}_V^{(\mathrm{s.s.})} \simeq\ & (\text{Hartree channel}) + (\text{Fock channel}) \\ & - \frac{V}{L_x L_y} \sum_{\sigma} \sum_{\mathbf{K},\mathbf{k},\mathbf{k}'} [\cos(\delta k_x) + \cos(\delta k_y)] \times \Big[\langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma} \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} \\ & + \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma} \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \langle \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} \rangle - \langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\sigma} \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\sigma} \rangle \langle \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} \rangle \Big]\end{aligned}$$

In principle, this pairing channel is legitimate and gives rise to "polarized" (same spin) Cooper class RWCs. This kind of spin pairing couples with antisymmetric spatial structures, working in the triplet pairing channel. However, we can safely ignore and set to zero these EVs, as is proven [**senarath2025mixed**], [**hutchinson2021mixed**]. The reason is simply that the superconducting phase preserves SU(2) spin symmetry, thus all three triplet pairing subspaces

$$z \text{ spin projection} \in \{-1, 0, 1\}$$

are degenerate and give rise to an identical solution. We can safely use the most convenient to us, the one with null spin projection, which can be mapped on the HM model of superconductivity discussed in Sec. B.2.

Anyhow, for the sake of completeness, the s.s. pairing channel is explicitly discussed in Sec. [Missing]. As is seen there, following the sketch of [**hutchinson2021mixed**], the resulting triplet of HFPs can be safely reduced to the simplified set of o.s. triplet HFPs discussed in previous sections.

4.5 Full MFT hamiltonian and anisotropic pairing

Let now the total contraction energy

$$E_{\mathrm{c}}^{(\mathrm{SC})} \equiv - \left[E_{\mathrm{H}/U}^{(\mathrm{SC})} + E_{\mathrm{C}/U}^{(\mathrm{SC})} + E_{\mathrm{H}/V}^{(\mathrm{SC})} + E_{\mathrm{F}/V}^{(\mathrm{SC})} + E_{\mathrm{C}/V/\mathrm{o.s.}}^{(\mathrm{SC})} \right]$$

By composing all three channels we are able to derive the final form of the MFT gran-canonical hamiltonian,

$$\hat{H} - \mu \hat{N} \simeq \sum_{\mathbf{k}\in\mathrm{BZ}} \tilde{\xi}_{\mathbf{k}} \left[\hat{c}^\dagger_{\mathbf{k}\uparrow} \hat{c}_{\mathbf{k}\uparrow} + \hat{c}_{-\mathbf{k}\downarrow} \hat{c}^\dagger_{-\mathbf{k}\downarrow} \right] - \sum_{\mathbf{k}\in\mathrm{BZ}} \left[\tilde{\Delta}_{\mathbf{k}} \hat{\phi}_{\mathbf{k}} + \tilde{\Delta}^*_{\mathbf{k}} \hat{\phi}^\dagger_{\mathbf{k}} \right] + E_{\mathrm{a}}^{(\mathrm{SC})} + E_{\mathrm{c}}^{(\mathrm{SC})}$$

having we included the "anticommutation energy" also defined for the conventional HM in Eq. (B.44),

$$E_{\mathrm{a}}^{(\mathrm{SC})} \equiv \sum_{\mathbf{k}\in\mathrm{BZ}} \tilde{\xi}_{\mathbf{k}}$$

coming from fermionic anticommutation relations that are employed in order to get the kinetic term. The renormalized bands are

$$\tilde{\xi}_{\mathbf{k}} = \epsilon_{\mathbf{k}} + V \sum_{\gamma\in\{s^*,d\}} u^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*} - \tilde{\mu}$$

and the full gap function by

$$\tilde{\Delta}_{\mathbf{k}\sigma} = -U w^{(s)} + V \sum_{\gamma} w^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*}$$

We can identify the gap harmonics by

$$\tilde{\Delta}^{(s)} = -U w^{(s)} \qquad \tilde{\Delta}^{(\gamma)} = V w^{(\gamma)} \quad \text{being} \quad \gamma \in \{s^*, p_x, p_y, d\}$$

As anticipated, the singlet channel admits three components only,

$$\text{Singlet channel} \quad : \quad \tilde{\Delta}_{\mathbf{k}} = \tilde{\Delta}^{(s)} + \tilde{\Delta}^{(s^*)}(\cos k_x + \cos k_y) + \tilde{\Delta}^{(d)}(\cos k_x - \cos k_y)$$

making the gap function purely real. An inverse statement holds for the triplet pairing, for which

$$\text{Triplet channel} \quad : \quad \tilde{\Delta}_{\mathbf{k}} = i\sqrt{2}\left[\tilde{\Delta}^{(p_x)} \sin k_x + \tilde{\Delta}^{(p_y)} \sin k_y\right]$$

In this case, the gap is purely imaginary. When working in a specific channel, the gap function is either purely real or purely imaginary. This lets us discuss the shape of the renormalized ground-state.

4.5.1 The relative phase in the zero temperature half-filled ground state

The conventional BCS ground state is widely known and derived for HM superconductivity in Sec. B.2.4. Jumping to Eq. (B.51) and extending it to the present context of the EHM, we get

$$|\Psi\rangle = \bigotimes_{\mathbf{k}\in\mathrm{BZ}} \left[\cos\tilde{\theta}_{\mathbf{k}} + e^{2i\tilde{\zeta}_{\mathbf{k}}} \sin\tilde{\theta}_{\mathbf{k}} \hat{\phi}_{\mathbf{k}}^{\dagger}\right] |\Omega_{\mathbf{k}}\rangle$$

a BCS state described by the RMPs. Within this short section, we just illustrate the most interesting features of this state. First, the phase factor angle is the gap "tilt" in the complex plane. This is evident by the facts

$$\begin{aligned}
\langle\Psi|\hat{s}_{\mathbf{k}}^{x}|\Psi\rangle &= \langle\Psi|\hat{\phi}_{\mathbf{k}} + \hat{\phi}_{\mathbf{k}}^{\dagger}|\Psi\rangle \\
&= i\sin\tilde{\theta}_{\mathbf{k}}\cos\tilde{\theta}_{\mathbf{k}}\left(e^{2i\tilde{\zeta}_{\mathbf{k}}} + e^{-2i\tilde{\zeta}_{\mathbf{k}}}\right) \\
&= -\sin(2\tilde{\theta}_{\mathbf{k}})\cos(2\tilde{\zeta}_{\mathbf{k}})
\end{aligned}
\qquad
\begin{aligned}
\langle\Psi|\hat{s}_{\mathbf{k}}^{y}|\Psi\rangle &= i\,\langle\Psi|\hat{\phi}_{\mathbf{k}} - \hat{\phi}_{\mathbf{k}}^{\dagger}|\Psi\rangle \\
&= i\sin\tilde{\theta}_{\mathbf{k}}\cos\tilde{\theta}_{\mathbf{k}}\left(e^{2i\tilde{\zeta}_{\mathbf{k}}} - e^{-2i\tilde{\zeta}_{\mathbf{k}}}\right) \\
&= -\sin(2\tilde{\theta}_{\mathbf{k}})\sin(2\tilde{\zeta}_{\mathbf{k}})
\end{aligned}$$

results that are coherent with Eqns. (4.5) as well as (4.6) and allow us to identify the phase with the pseudofield xy angle.

4.6 SC free energy density

Free energy density of the superconducting phase is derived as for the normal phase in Sec. 2.4. As for the AF phase of Sec. 3.6, two fermionic bands are present; however, recalling the antiferromagnet entropy density of Eq. (3.38), the key differences are here given by the fact that the chemical

potential inside the Fermi-Dirac factors is null and the sum is extended on the full BZ (but not later on spin index),

$$s^{(\pm)} \equiv -\frac{k_B}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \Big[\Big(1 - f(\pm\tilde{E}_{\mathbf{k}};\beta,0)\Big) \ln \Big(1 - f(\pm\tilde{E}_{\mathbf{k}};\beta,0)\Big) + f(\pm\tilde{E}_{\mathbf{k}};\beta,0) \ln f(\pm\tilde{E}_{\mathbf{k}};\beta,0)\Big] \quad (4.23)$$

with identical meaning of the notation. Using the relation

$$\frac{1}{e^x+1} + \frac{1}{e^{-x}+1} = 1$$

it's immediate to conclude that

$$s^{(-)} = s^{(+)} \quad \Longrightarrow \quad s \equiv s^{(-)} + s^{(+)} = 2s^{(+)}$$

being s the total entropy density.

The five contributions to free energy are:

1. Quasiparticles energy:

$$\begin{aligned} e_{\mathrm{g}}^{(\mathrm{SC})} &= \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \tilde{E}_{\mathbf{k}} \tilde{\mathrm{Th}}_{\mathbf{k}}^{(-)}[\beta] \\ &= -\frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \tilde{E}_{\mathbf{k}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2}\right) \end{aligned}$$

2. Anticommutation energy:

$$\begin{aligned} e_{\mathrm{a}}^{(\mathrm{SC})} &\equiv \frac{E_{\mathrm{a}}^{(\mathrm{SC})}}{L_x L_y} \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \tilde{\xi}_{\mathbf{k}} \end{aligned}$$

3. Contraction energy:

$$e_{\mathrm{c}}^{(\mathrm{SC})} = -U\left[n^2 + \left|w^{(s)}\right|^2\right] + V\left[2zn^2 - \sum_{\gamma}\left|u^{(\gamma)}\right|^2 + \sum_{\gamma}\left|w^{(\gamma)}\right|^2\right]$$

4. Entropic energy

$$e_{s}^{(\mathrm{SC})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \ln\Big(1 - f(\tilde{E}_{\mathbf{k}};\beta,0)\Big) - \frac{2}{L_x L_y} \sum_{\mathbf{k}\in\mathrm{BZ}} \tilde{E}_{\mathbf{k}} f(\tilde{E}_{\mathbf{k}};\beta,0)$$

5. Chemical potential correction

$$e_{n}^{(\mathrm{SC})} = \mu n$$

Compose everything

$$f_{\mathrm{MFT}}^{(\mathrm{SC})} \equiv e_{\mathrm{g}}^{(\mathrm{SC})} + e_{\mathrm{a}}^{(\mathrm{SC})} + e_{\mathrm{c}}^{(\mathrm{SC})} + e_{s}^{(\mathrm{SC})} + e_{n}^{(\mathrm{SC})}$$

noting that

We get

$$f_{\mathrm{MFT}}^{(\mathrm{SC})} \qquad = \qquad \ldots \quad (4.24)$$

BCS essentially relies on the insurgence of an effective free fermionic field, described by the Bogoliubov bands, and the condensation of Cooper pairs. Superconducting state is favored by the lowering of free energy granted by the shifting of much of the spectral weight to a lower-energy maximum [**zhou1992density**]. "Condensation energy" is simply the energy difference

between the superconducting state and the normal state, and its negativity indicates instability towards superconducting order. It's pretty straightforward to derive the ground state energy for the standard BCS state. When performing Wick's contractions,

$$\begin{aligned}\langle \hat{c}^\dagger_\alpha \hat{c}^\dagger_\beta \hat{c}_\gamma \hat{c}_\delta \rangle \sim \langle \hat{c}^\dagger_\alpha \hat{c}^\dagger_\beta \rangle \hat{c}_\gamma \hat{c}_\delta + \hat{c}^\dagger_\alpha \hat{c}^\dagger_\beta \langle \hat{c}_\gamma \hat{c}_\delta \rangle - \langle \hat{c}^\dagger_\alpha \hat{c}^\dagger_\beta \rangle \langle \hat{c}_\gamma \hat{c}_\delta \rangle \quad & \text{Cooper terms} \\ - \langle \hat{c}^\dagger_\alpha \hat{c}_\gamma \rangle \hat{c}^\dagger_\beta \hat{c}_\delta - \hat{c}^\dagger_\alpha \hat{c}_\gamma \langle \hat{c}^\dagger_\beta \hat{c}_\delta \rangle + \langle \hat{c}^\dagger_\alpha \hat{c}_\gamma \rangle \langle \hat{c}^\dagger_\beta \hat{c}_\delta \rangle \quad & \text{Fock terms} \\ + \langle \hat{c}^\dagger_\alpha \hat{c}_\delta \rangle \hat{c}^\dagger_\beta \hat{c}_\gamma + \hat{c}^\dagger_\alpha \hat{c}_\delta \langle \hat{c}^\dagger_\beta \hat{c}_\gamma \rangle - \langle \hat{c}^\dagger_\alpha \hat{c}_\delta \rangle \langle \hat{c}^\dagger_\beta \hat{c}_\gamma \rangle \quad & \text{Hartree terms}\end{aligned}$$

Form each of the three rows above, the last term is the "leftover" part which shifts energy. Thus it can be ignored in derivation, but becomes important when considering the energy in the end. The EHM hamiltonian can be written as:

$$\begin{aligned}\hat{H} = \sum_{\mathbf{k}} \xi_{\mathbf{k}} \left[\hat{c}^\dagger_{\mathbf{k}\uparrow} \hat{c}_{\mathbf{k}\uparrow} + \mathbb{I} - \hat{c}_{-\mathbf{k}\downarrow} \hat{c}^\dagger_{-\mathbf{k}\downarrow} \right] - \sum_{\mathbf{k},\mathbf{k}'} \left[V^{(s)} + V_{\mathbf{k}\mathbf{k}'} \right] \hat{\phi}^\dagger_{\mathbf{k}} \hat{\phi}_{\mathbf{k}'} \\ - \frac{2V}{L_x L_y} \sum_{\mathbf{k},\mathbf{k}'} \sum_{\sigma} \left[\cos(\delta k_x) + \cos(\delta k_y) \right] \hat{n}_{\mathbf{k}\sigma} \hat{n}_{\mathbf{k}'\sigma}\end{aligned} \tag{4.25}$$

as in Eq. (**??**). Following the scheme above, the "leftovers" of the MFT hamiltonian are just

$$\sum_{\mathbf{k},\mathbf{k}'} \Delta_{\mathbf{k}} \langle \hat{\phi}_{\mathbf{k}'} \rangle - \frac{2V}{L_x L_y} \sum_{\mathbf{k},\mathbf{k}'} \sum_{\sigma} \left[\cos(\delta k_x) + \cos(\delta k_y) \right] g_{\mathbf{k}} g_{\mathbf{k}'}$$

Further developing this result and applying Eqns. (**??**), (1.26), these last terms can be written as:

$$\sum_{\mathbf{k}} \frac{|\Delta_{\mathbf{k}}|^2}{2\tilde{E}_{\mathbf{k}}} \tanh\left(\frac{\beta \tilde{E}_{\mathbf{k}}}{2} \right) - 2V L_x L_y \sum_{\gamma} \left| g^{(\gamma)} \right|^2 \qquad \gamma \in \{s^*, d_{x^2-y^2}\} \tag{4.26}$$

as for Eq. (**??**). Notice the presence of a volume factor in the $\mathcal{O}\left(g^2\right)$ correction.

Now, we retrieve the expression for the MFT free energy density [**hutchinson2021mixed**] simply by adding four contributions:

1. Bogoliubov free quasiparticles thermal ground state energy density,

$$\begin{aligned}\frac{1}{L_x L_y} \sum_{\mathbf{k}} \tilde{E}_{\mathbf{k}} \left[f(\tilde{E}_{\mathbf{k}}; \beta, 0) - f(-\tilde{E}_{\mathbf{k}}; \beta, 0) \right] &= \frac{1}{L_x L_y} \sum_{\mathbf{k}} \tilde{E}_{\mathbf{k}} \left[f(\tilde{E}_{\mathbf{k}}; \beta, 0) - \left(1 - f(\tilde{E}_{\mathbf{k}}; \beta, 0) \right) \right] \\ &= \frac{2}{L_x L_y} \sum_{\mathbf{k}} \tilde{E}_{\mathbf{k}} f(\tilde{E}_{\mathbf{k}}; \beta, 0) - \frac{1}{L_x L_y} \sum_{\mathbf{k}} \tilde{E}_{\mathbf{k}}\end{aligned}$$

   having used the simple property of the Fermi-Dirac distribution $f(-x; \beta, 0) = 1 - f(-x; \beta, 0)$.

2. The term originated by the identity produced by fermionic anticommutation rules in Eq. (4.25),

$$\frac{1}{L_x L_y} \sum_{\mathbf{k}} \tilde{\xi}_{\mathbf{k}}$$

   averaged on the lattice.

3. The "leftovers" of Eq. (4.26), divided by $L_x L_y$.

4. The entropic free energy

$$-Ts$$

   with $T = 1/k_B \beta$ and s the free Fermi gas entropy density for the Bogoliubov quasiparticles,

$$s = -\frac{2k_B}{L_x L_y} \sum_{\mathbf{k}} \left[\left(1 - f(\tilde{E}_{\mathbf{k}}; \beta, 0) \right) \ln \left(1 - f(\tilde{E}_{\mathbf{k}}; \beta, 0) \right) + f(\tilde{E}_{\mathbf{k}}; \beta, 0) \ln f(\tilde{E}_{\mathbf{k}}; \beta, 0) \right]$$

We use the identity:

$$\ln\left(1-\frac{1}{e^x+1}\right)=x+\ln\left(\frac{1}{e^x+1}\right)$$

and reduce the above expression to:

$$s=-\frac{2k_B}{L_xL_y}\sum_{\mathbf{k}}\Big[\ln\left(1-f(\tilde{E}_{\mathbf{k}};\beta,0)\right)+f(\tilde{E}_{\mathbf{k}};\beta,0)\ln f(\tilde{E}_{\mathbf{k}};\beta,0)$$
$$-\beta\tilde{E}_{\mathbf{k}}f(\tilde{E}_{\mathbf{k}};\beta,0)-f(\tilde{E}_{\mathbf{k}};\beta,0)\ln f(\tilde{E}_{\mathbf{k}};\beta,0)\Big]$$

Second and fourth terms cancel out, while the third compensates the first one of contribution 1.

All together, the MFT averaged free energy looks like this:

$$f_{\mathrm{MFT}}[\Delta_{\mathbf{k}},g_{\mathbf{k}}]=\frac{1}{L_xL_y}\sum_{\mathbf{k}}\left[\tilde{\xi}_{\mathbf{k}}-\tilde{E}_{\mathbf{k}}+\frac{|\Delta_{\mathbf{k}}|^2}{2\tilde{E}_{\mathbf{k}}}\tanh\left(\frac{\beta\tilde{E}_{\mathbf{k}}}{2}\right)\right]$$
$$-2V\sum_{\gamma\in\{s^*,d\}}\left|g^{(\gamma)}\right|^2+\frac{2}{\beta L_xL_y}\sum_{\mathbf{k}}\ln\left(1-f(\tilde{E}_{\mathbf{k}};\beta,0)\right)\quad(4.27)$$

The two main differences with the commonly known expressions for f_{MFT} [**hutchinson2021mixed**, **senarath2025mixed**] are the presence of bands renormalization , the absence of $-\mu n$ [Why?], and the $\mathcal{O}\left(g^2\right)$ correction. The latter, not only is negative for attractive V, a feature that can lead to superconducting phase energy lowering and stabilisation, but also it depends explicitly on the spectral amplitude of the s^* and d-wave components of $g_{\mathbf{k}}$. Since as seen the d-wave part of $g_{\mathbf{k}}$ arises for mixed symmetries, this details seems to indicate an energetic preference for multi-symmetry phases.

4.7 Numerical simulations

[To be continued...]

4.7.1 HF iterative algorithm sketch

[To be continued...]

Appendix A

Superexchange and virtual hopping in Hubbard lattices

A key mechanism in AF phase formation in Hubbard lattice is superexchange. The AF phase is stabilized by spin fluctuations and second-order virtual hopping. The mechanism becomes clear enough by considering a 2-sites Hubbard toy model.

A.1 Virtual hopping in the 2-sites Hubbard lattice

Consider the toy model:

$$\hat{H} = -t\left\{\hat{c}^{\dagger}_{1\uparrow}\hat{c}_{2\uparrow} + \hat{c}^{\dagger}_{1\downarrow}\hat{c}_{2\downarrow} + \text{h.c.}\right\} + U\left\{\hat{n}_{1\uparrow}\hat{n}_{1\downarrow} + \hat{n}_{2\uparrow}\hat{n}_{2\downarrow}\right\}$$

with $i = 1, 2$ the site index. The two sites are represented in Fig. A.1. The two competing processes are:

1. electrons inter-sites hopping with amplitude $-t$;

2. local repulsion $+U$, acting when two anti-aligned electrons reside on the same site;

For an half-filled system, the Hilbert space is six-dimensional. I use the notation $|n_{1\uparrow}n_{1\downarrow}n_{2\uparrow}n_{2\downarrow}\rangle$ to indicate the six computational basis states:

$$\begin{array}{lll} |\psi_1\rangle \equiv |1010\rangle & |\psi_3\rangle \equiv |1001\rangle & |\psi_5\rangle \equiv |0011\rangle \\ |\psi_2\rangle \equiv |1100\rangle & |\psi_4\rangle \equiv |0110\rangle & |\psi_6\rangle \equiv |0101\rangle \end{array}$$

For example, the top panel of Fig. A.1 shows state $|\psi_2\rangle$.

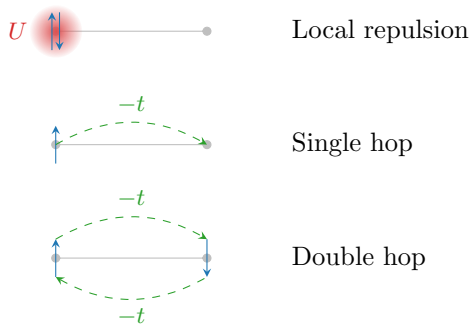

Figure A.1 | Two sites Hubbard model.

Structure	Eigenstate	Energy
Spin-1/2 singlet	$\frac{\lvert\phi_3\rangle - \lvert\phi_4\rangle}{\sqrt{2}}$	$E^- = \frac{U}{2} - \sqrt{\frac{U^2}{4} + 4t^2}$
Spin-1/2 triplet	$\lvert\phi_1\rangle, \frac{\lvert\phi_3\rangle + \lvert\phi_4\rangle}{\sqrt{2}}, \lvert\phi_6\rangle$	0
	$\frac{\lvert\phi_2\rangle - \lvert\phi_5\rangle}{\sqrt{2}}$	U
	$\frac{\lvert\phi_2\rangle + \lvert\phi_5\rangle}{\sqrt{2}}$	$E^+ = \frac{U}{2} + \sqrt{\frac{U^2}{4} + 4t^2}$

Table A.1 | List of exact eigenstates and relative energies for the 2-sites half-filled Hubbard model.

A.1.1 Exact solution of the half-filled model

The hamiltonian matrix is directly evaluated in this basis

$$H_{ij} = \langle\psi_i|\,\hat{H}\,|\psi_j\rangle \quad \Longrightarrow \quad H = \begin{bmatrix} 0 & & & & & \\ & U & -t & -t & & \\ & -t & & & -t & \\ & -t & & & -t & \\ & & -t & -t & U & \\ & & & & & 0 \end{bmatrix}$$

Empty slots in the matrix stand for zeros. Evidently the states $|\psi_1\rangle$ (both up) and $|\psi_6\rangle$ (both down) are zero-energy eigenstates. These states cannot realize electrons hopping because of Pauli principle. The internal 4×4 matrix is readily diagonalized by the means of a change of basis V,

$$V \begin{bmatrix} U & -t & -t & \\ -t & & & -t \\ -t & & & -t \\ & -t & -t & U \end{bmatrix} V^\dagger = \begin{bmatrix} E^- & & & \\ & 0 & & \\ & & U & \\ & & & E^+ \end{bmatrix}$$

Tab. A.1 shows the eigenvectors and relative eigenvalues obtained from diagonalization. The ground-state is the singlet state,

$$\frac{|\phi_3\rangle - |\phi_4\rangle}{\sqrt{2}} = \frac{|1010\rangle - |0101\rangle}{\sqrt{2}} = \frac{|\uparrow\downarrow\rangle - |\downarrow\uparrow\rangle}{\sqrt{2}}$$

of energy

$$E^- = \frac{U}{2} - \sqrt{\frac{U^2}{4} + 4t^2} \simeq -\frac{4t^2}{U}$$

the latter equality being true if $U \gg t$ (strong repulsion limit). The singlet state pairs with a spatially-symmetric (nodeless) wavefunction. The entire triplet (second row of Tab. A.1) remains at zero energy. Excited states are anti-symmetrized and symmetrized version of the polarized states $|\phi_1\rangle$ and $|\phi_6\rangle$.

A.1.2 Virtual hopping

The key feature of the singlet state is the one represented in the bottom panel of Fig. A.1: if the two electrons occupy separate sites and are anti-aligned, both "see" the other site as empty, thus free to hop to. [To be continued...]

Appendix B

Mean-Field Theory in Hubbard lattices

In this Appendix the MFT solutions to the conventional Hubbard hamiltonian of Eq. (**??**),

$$\hat{H} = -t \sum_{\langle ij \rangle} \sum_{\sigma} \left[\hat{c}^{\dagger}_{i\sigma} \hat{c}_{j\sigma} + \text{h.c.} \right] + U \sum_{i} \hat{n}_{i\uparrow} \hat{n}_{i\downarrow} \qquad t, U > 0 \tag{B.1}$$

are described. The discussion is limited to the two-dimensional square lattice. The results of ths appendix are relevant and used throughout the text as the groundwork to be extended by the means of MFT applied to the non-local part of the EHM.

B.1 Antiferromagnetic phase

We work in a commensurate AF phase ordering, which is, we explicitly break symmetry by realizing a SDW phase with spin density unevenly distributed on sites with periodicity of two sites, each direction. Recalling the discussion of Sec. 1.1, AF long-range ordering we deal with here is described by the composite SSB

$$\mathrm{SU}(2) \overset{\text{SSB}}{\to} \mathrm{U}^{z}(1)$$
$$\mathrm{T}^{(x)}_{1} \otimes \mathrm{T}^{(y)}_{1} \overset{\text{SSB}}{\to} \mathrm{T}^{(x)}_{2} \otimes \mathrm{T}^{(y)}_{2}$$

Recalling Tab. 1.3, for such a physical phase the only Wick contraction channel available is the Hartree one. Let us proceed in such sense. As in Eqns. (3.1), (3.2), it is useful to define the density and AF fluctuation operators:

$$\hat{n}_{\mathbf{k}\sigma} \equiv \hat{c}^{\dagger}_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma} \tag{B.2}$$
$$\hat{\psi}_{\mathbf{k}\sigma} \equiv \hat{c}^{\dagger}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \hat{c}_{\mathbf{k}\sigma} \tag{B.3}$$

whose EVs are relevant order parameters for the normal and AF phases.

B.1.1 MFT treatment of the Hartree channel

In terms of the physical magnetization m, the MFT Ansatz is given by

$$\langle \hat{n}_{\mathbf{r}\sigma} \rangle = n - (-1)^{x+y+\delta_{\sigma=\uparrow}} m \tag{B.4}$$

Decoupling the HM hamiltonian and substituting,

$$\begin{aligned} \hat{H} &\simeq -t \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \left[\hat{c}^{\dagger}_{i\sigma} \hat{c}_{j\sigma} + \text{h.c.} \right] + U \sum_{\mathbf{r}} \left[\hat{n}_{\mathbf{r}\uparrow} \langle \hat{n}_{\mathbf{r}\downarrow} \rangle + \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \hat{n}_{\mathbf{r}\downarrow} - \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \langle \hat{n}_{\mathbf{r}\downarrow} \rangle \right] \\ &= -t \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \left[\hat{c}^{\dagger}_{i\sigma} \hat{c}_{j\sigma} + \text{h.c.} \right] + nU \sum_{\mathbf{r}} \left[\hat{n}_{\mathbf{r}\uparrow} + \hat{n}_{\mathbf{r}\downarrow} \right] - mU \sum_{\mathbf{r}} (-1)^{x+y} \left[\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow} \right] - E^{(\mathrm{AF})}_{\mathrm{H}/U} \end{aligned} \tag{B.5}$$

with $E^{(\mathrm{AF})}_{\mathrm{H}/U}$ the HM Hartree contraction energy,

$$\begin{aligned} E^{(\mathrm{AF})}_{\mathrm{H}/U} &\equiv U \sum_{\mathbf{r}} \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \langle \hat{n}_{\mathbf{r}\downarrow} \rangle \\ &= U \sum_{\mathbf{r}} \left(n + (-1)^{x+y} m\right) \left(n - (-1)^{x+y} m\right) \\ &= L_x L_y \times U \left(n^2 - m^2\right) \end{aligned} \tag{B.6}$$

By a Fourier transform, the phase factor of Eq. (B.5) can be absorbed in the destruction operator inside of $\hat{n}_{\mathbf{r}\sigma}$:

$$\begin{aligned} \sum_{\mathbf{r}} (-1)^{x+y} \hat{n}_{\mathbf{r}\sigma} &= \sum_{\mathbf{r}} (-1)^{x+y} \hat{c}^\dagger_{\mathbf{r}\sigma} \hat{c}_{\mathbf{r}\sigma} \\ &\overset{\mathcal{F}}{=} \sum_{\mathbf{r}} e^{i\boldsymbol{\pi}\cdot\mathbf{r}} \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k}\in\mathrm{BZ}} e^{i\mathbf{k}\cdot\mathbf{r}} \hat{c}^\dagger_{\mathbf{k}\sigma} \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k}'\in\mathrm{BZ}} e^{-i\mathbf{k}'\cdot\mathbf{r}} \hat{c}_{\mathbf{k}'\sigma} \\ &= \sum_{\mathbf{k}\in\mathrm{BZ}} \sum_{\mathbf{k}'\in\mathrm{BZ}} \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}'\sigma} \frac{1}{L_x L_y} \sum_{\mathbf{r}} e^{-i[\mathbf{k}'-(\mathbf{k}+\boldsymbol{\pi})]\cdot\mathbf{r}} \\ &= \sum_{\mathbf{k}\in\mathrm{BZ}} \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \end{aligned} \tag{B.7}$$

where $\boldsymbol{\pi} = (\pi, \pi)$. It follows:

$$mU \sum_{\mathbf{r}} (-1)^{x+y} \left[\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}\right] = mU \sum_{\mathbf{k}\in\mathrm{BZ}} \left[\hat{c}^\dagger_{\mathbf{k}\uparrow} \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\uparrow} - \hat{c}^\dagger_{\mathbf{k}\downarrow} \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\downarrow}\right]$$

Note that the Hartree channel renormalizes chemical potential,

$$nU \sum_{\mathbf{r}} \left[\hat{n}_{\mathbf{r}\uparrow} + \hat{n}_{\mathbf{r}\downarrow}\right] = nU \times \hat{N} \qquad \Longrightarrow \qquad \mu \to \tilde{\mu} \equiv \mu - nU$$

an effect that is present also in the EHM. The kinetic part of the hamiltonian transforms as in Eq. (1.13),

$$-t \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \left[\hat{c}^\dagger_{\mathbf{r}\sigma} \hat{c}_{\mathbf{r}'\sigma} + \mathrm{h.c.}\right] \overset{\mathcal{F}}{=} \sum_{\mathbf{k}\in\mathrm{BZ}} \sum_{\sigma} \epsilon_{\mathbf{k}} \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma}$$

being $\epsilon_{\mathbf{k}}$ the bare bands of Eq. (1.14).

Take everything together. Using the property:

$$\begin{aligned} \sum_{\mathbf{k}\in\mathrm{BZ}} \hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} &= \sum_{\mathbf{k}\in\mathrm{MBZ}} \left[\hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} + \hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma} \hat{c}_{\mathbf{k}+2\boldsymbol{\pi}\sigma}\right] \\ &= \sum_{\mathbf{k}\in\mathrm{MBZ}} \left[\hat{c}^\dagger_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} + \hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma} \hat{c}_{\mathbf{k}\sigma}\right] \end{aligned}$$

and reduce Eq. (B.5) to its reciprocal form

$$\hat{H} \simeq \sum_{\mathbf{k}\in\mathrm{MBZ}} \sum_{\sigma} \epsilon_{\mathbf{k}} \left[\hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma}\right] - mU \sum_{\mathbf{k}\in\mathrm{MBZ}} (-1)^{\delta_{\sigma=\downarrow}} \left[\hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}^\dagger_{\mathbf{k}\sigma}\right] + nU\hat{N} - E^{(\mathrm{AF})}_{\mathrm{H}/U}$$

B.1.2 Nambu representation of the AF phase and diagonalization

We now map the reciprocal version of the HM onto a simpler problem. Throughout this section we use the notation $\epsilon_{\mathbf{k}} \to \epsilon_{\mathbf{k}\sigma}$ with identical meaning. Let the Nambu spinors:

$$\hat{\Psi}_{\mathbf{k}\sigma} \equiv \begin{bmatrix} \hat{c}_{\mathbf{k}\sigma} \\ \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \end{bmatrix}$$

Let also the gap function:

$$\Delta_{\mathbf{k}\sigma} = (-1)^{\delta_{\sigma=\downarrow}} mU$$

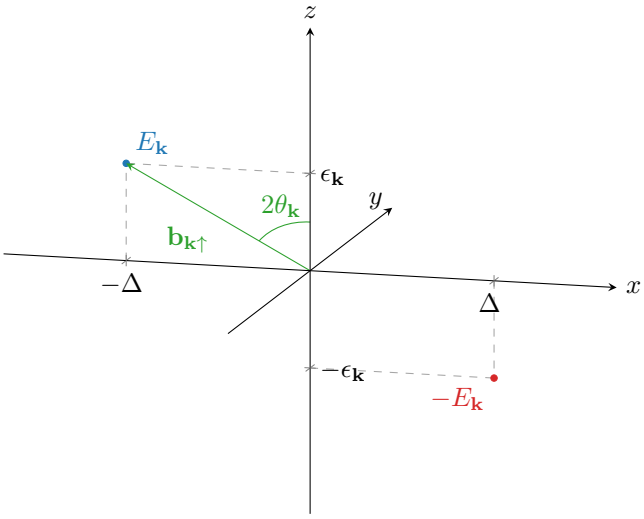

Figure B.1 | Pseudo-magnetic field originating from mean-field treatment of the square Hubbard hamiltonian. Here, only the $\sigma =\uparrow$ situation is plotted.

$$\hat{H} \simeq \sum_{\mathbf{k}\in\mathrm{MBZ}} \sum_{\sigma} \hat{\Psi}^{\dagger}_{\mathbf{k}\sigma} h_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} - E^{(\mathrm{AF})}_{\mathrm{H}/U} \quad \text{being} \quad h_{\mathbf{k}\sigma} \equiv \begin{bmatrix} \epsilon_{\mathbf{k}\sigma} & -\Delta^{*}_{\mathbf{k}\sigma} \\ -\Delta_{\mathbf{k}\sigma} & -\epsilon_{\mathbf{k}\sigma} \end{bmatrix} \tag{B.8}$$

Notice: the Nambu hamiltonian is a 2×2 matrix over the MBZ – which is half the full BZ, coherently with a solution which essentially bipartites the lattice giving back a double sized unit cell.

The system ground-state is obtained by the means of a Bogoliubov rotation. The hamiltonian maps onto the simple one of a spin in a magnetic field (the gap is purely real here),

$$h_{\mathbf{k}\sigma} = \epsilon_{\mathbf{k}\sigma}\tau^{z} - \Delta_{\mathbf{k}\sigma}\tau^{x}$$

being τ^{α} the Pauli matrices. Then, defining

$$\hat{s}^{\alpha}_{\mathbf{k}\sigma} \equiv \hat{\Psi}^{\dagger}_{\mathbf{k}\sigma}\tau^{\alpha}\hat{\Psi}_{\mathbf{k}\sigma} \quad \text{and} \quad \mathbf{b}_{\mathbf{k}\sigma} \equiv \begin{bmatrix} -\Delta_{\mathbf{k}\sigma} \\ 0 \\ \epsilon_{\mathbf{k}\sigma} \end{bmatrix}$$

one gets:

$$\hat{H} \simeq \sum_{\mathbf{k}\in\mathrm{MBZ}} \sum_{\sigma} \mathbf{b}_{\mathbf{k}\sigma} \cdot \hat{\mathbf{s}}_{\mathbf{k}\sigma} - E^{(\mathrm{AF})}_{\mathrm{H}/U} \quad \text{where} \quad \hat{\mathbf{s}}_{\mathbf{k}\sigma} = \begin{bmatrix} \hat{s}^{x}_{\mathbf{k}\sigma} \\ \hat{s}^{y}_{\mathbf{k}\sigma} \\ \hat{s}^{z}_{\mathbf{k}\sigma} \end{bmatrix} \tag{B.9}$$

The hamiltonian represents a system of spins subject to local magnetic fields, each tilted by an angle $\tan 2\theta_{\mathbf{k}\sigma} = \Delta_{\mathbf{k}\sigma}/\epsilon_{\mathbf{k}\sigma}$, as sketched in Fig. B.1. Evidently the following relations, also reported in Tab. 3.2, hold:

$$\hat{s}^{x}_{\mathbf{k}\sigma} = \hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}^{\dagger}_{\mathbf{k}\sigma} \tag{B.10}$$

$$\hat{s}^{y}_{\mathbf{k}\sigma} = i\left(\hat{\psi}_{\mathbf{k}\sigma} - \hat{\psi}^{\dagger}_{\mathbf{k}\sigma}\right) \tag{B.11}$$

$$\hat{s}^{z}_{\mathbf{k}\sigma} = \hat{n}_{\mathbf{k}\sigma} - \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \tag{B.12}$$

Let also:

$$\begin{aligned} \hat{\mathbb{I}}_{\mathbf{k}\sigma} &\equiv \hat{\Psi}^{\dagger}_{\mathbf{k}\sigma}\mathbb{I}_{2\times 2}\hat{\Psi}_{\mathbf{k}\sigma} \\ &= \hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \end{aligned} \tag{B.13}$$

Diagonalization of each $h_{\mathbf{k}\sigma}$ is obtained trivially by a simple rotation around the y axis:

$$d_{\mathbf{k}\sigma} = W_{\mathbf{k}\sigma} h_{\mathbf{k}\sigma} W^{\dagger}_{\mathbf{k}\sigma} \quad \text{with} \quad d_{\mathbf{k}\sigma} \equiv \begin{bmatrix} E_{\mathbf{k}\sigma} & \\ & -E_{\mathbf{k}\sigma} \end{bmatrix}$$

and where the diagonalization unitary matrix is simply a rotation by an angle $2\theta_{\mathbf{k}\sigma}$ around the y axis, counter-clockwise

$$\begin{aligned} W_{\mathbf{k}\sigma} &\equiv e^{-i\theta_{\mathbf{k}\sigma}\tau^y} \\ &= \cos\theta_{\mathbf{k}\sigma} - i\sin\theta_{\mathbf{k}\sigma}\tau^y \\ &= \begin{bmatrix} \cos\theta_{\mathbf{k}\sigma} & -\sin\theta_{\mathbf{k}\sigma} \\ \sin\theta_{\mathbf{k}\sigma} & \cos\theta_{\mathbf{k}\sigma} \end{bmatrix} \end{aligned} \tag{B.14}$$

Eigenvalues are:

$$E_{\mathbf{k}\sigma} \equiv \sqrt{\epsilon_{\mathbf{k}\sigma}^2 + |\Delta_{\mathbf{k}\sigma}|^2} \tag{B.15}$$

At any finite temperature, the ground-state of such a system is well-known: a thermal superposition of "down" spins with "up" spins. In the pseudospin picture, at each "site" ($\mathbf{k}\sigma$), the lowest-energy state is the one anti-aligned with the pseudo-magnetic field. It is useful now to define the thermal factors,

$$\mathrm{Th}_{\mathbf{k}\sigma}^{(\pm)}[\beta,\mu] \equiv f\left(E_{\mathbf{k}\sigma};\beta,\mu\right) \pm f\left(-E_{\mathbf{k}\sigma};\beta,\mu\right) \tag{B.16}$$

that will appear quite often. Then it's immediate to derive the various expectation values.

$$\langle \hat{s}_{\mathbf{k}\sigma}^x \rangle = -\frac{\mathrm{Re}\{\Delta_{\mathbf{k}\sigma}\}}{2E_{\mathbf{k}\sigma}} \mathrm{Th}_{\mathbf{k}\sigma}^{(-)}[\beta,\mu] \tag{B.17}$$

$$\langle \hat{s}_{\mathbf{k}\sigma}^y \rangle = -\frac{\mathrm{Im}\{\Delta_{\mathbf{k}\sigma}\}}{2E_{\mathbf{k}\sigma}} \mathrm{Th}_{\mathbf{k}\sigma}^{(-)}[\beta,\mu] \tag{B.18}$$

$$\langle \hat{s}_{\mathbf{k}\sigma}^z \rangle = \frac{\epsilon_{\mathbf{k}\sigma}}{2E_{\mathbf{k}\sigma}} \mathrm{Th}_{\mathbf{k}\sigma}^{(-)}[\beta,\mu] \tag{B.19}$$

Note that considering the gran canonical hamiltonian $\hat{K} \equiv \hat{H} - \mu\hat{N}$ and using Eq. (B.13) the diagonalizing matrix remains the same, being

$$-\mu\hat{N} = \sum_{\mathbf{k}\in\mathrm{MBZ}} \begin{bmatrix} -\mu & \\ & -\mu \end{bmatrix} \quad \Longrightarrow \quad W_{\mathbf{k}\sigma}\left[h_{\mathbf{k}\sigma} - \mu\mathbb{I}_{2\times 2}\right] W_{\mathbf{k}\sigma}^\dagger = d_{\mathbf{k}\sigma} - \mu\mathbb{I}_{2\times 2} \tag{B.20}$$

thus for non-null chemical potential (i.e. finite doping) the eigenvalues are just shifted, $\pm E_{\mathbf{k}} - \mu$. In other words, the new bands retain the same chemical potential of the bare bands. Notice also that the presence of an absolute value makes the eigenvalues independent of the σ index. Eigenvector fermion operators are obtained simply as:

$$\hat{\Gamma}_{\mathbf{k}\sigma} = W_{\mathbf{k}\sigma}\hat{\Psi}_{\mathbf{k}\sigma} \tag{B.21}$$

The $\hat{\Gamma}$ spinor operators are effectively free fermionic spinor fields and as such must be treated. Explicitly,

$$\begin{aligned} \hat{\Gamma}_{\mathbf{k}\sigma} &= \begin{bmatrix} \cos\theta_{\mathbf{k}\sigma} & -\sin\theta_{\mathbf{k}\sigma} \\ \sin\theta_{\mathbf{k}\sigma} & \cos\theta_{\mathbf{k}\sigma} \end{bmatrix} \begin{bmatrix} \hat{c}_{\mathbf{k}\sigma} \\ \hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \end{bmatrix} \\ &= \begin{bmatrix} \cos\theta_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma} - \sin\theta_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \\ \sin\theta_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma} + \cos\theta_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \end{bmatrix} \equiv \begin{bmatrix} \hat{\gamma}_{\mathbf{k}\sigma}^{(+)} \\ \hat{\gamma}_{\mathbf{k}\sigma}^{(-)} \end{bmatrix} \end{aligned} \tag{B.22}$$

The consequence of Eq. (B.20) is interesting by itself: within this HF solution, the gap opens always at $E = 0$. In other words, the bands sketched in Fig. **??** retain the same geometric features regardless of the doping, what changes is the bands width and the gap between them. The very key point here is that, being the two bands symmetric (thus containing each half of the electronic states) and defined over the MBZ, any finite doping $\delta > 0$ will produce a metallic behaviour, imposing that the chemical potential crosses the upper band. It is widely observed and confirmed by more refined numerical procedures, however, that AF establishes an insulating phase – here only reproduced at half-filling, where the chemical potential lies within the gap. As will be detailed in B.1.7, the commensurate nature of AF SSB at wavevector $\boldsymbol{\pi}$ of this self-consistent solution is highly unstable and atypical at finite doping [**singh1990collective**].

B.1.3 Explicit zero-temperature AF ground state at half-filling

The AF ground state can be expressed easily at $n = 1/2$ and $\beta \to +\infty$. Let $|\Uparrow_{\mathbf{k}\sigma}\rangle$ and $|\Downarrow_{\mathbf{k}\sigma}\rangle$ be respectively the "up" and "down" $\mathbf{k}$-th pseudospin states. Let $|\overline{\Downarrow}_{\mathbf{k}\sigma}\rangle$ be the "down" state in the tilted frame. The ground state is given by

$$|\Psi\rangle \equiv \bigotimes_{\sigma} \bigotimes_{\mathbf{k}\in\mathrm{MBZ}} |\overline{\Downarrow}_{\mathbf{k}\sigma}\rangle \tag{B.23}$$

We can link the "down" states via an inverse rotation,

$$\begin{aligned} |\overline{\Downarrow}_{\mathbf{k}\sigma}\rangle &= e^{-i\theta_{\mathbf{k}\sigma}\hat{s}^y_{\mathbf{k}\sigma}} |\Downarrow_{\mathbf{k}\sigma}\rangle \\ &= \cos\theta_{\mathbf{k}\sigma} |\Downarrow_{\mathbf{k}\sigma}\rangle - i\sin\theta_{\mathbf{k}\sigma}\hat{s}^y_{\mathbf{k}\sigma} |\Downarrow_{\mathbf{k}\sigma}\rangle \\ &= \cos\theta_{\mathbf{k}\sigma} |\Downarrow_{\mathbf{k}\sigma}\rangle - \sin\theta_{\mathbf{k}\sigma}(\hat{s}^+_{\mathbf{k}\sigma} - \hat{s}^-_{\mathbf{k}\sigma}) |\Downarrow_{\mathbf{k}\sigma}\rangle \\ &= \cos\theta_{\mathbf{k}\sigma} |\Downarrow_{\mathbf{k}\sigma}\rangle - \sin\theta_{\mathbf{k}\sigma} |\Uparrow_{\mathbf{k}\sigma}\rangle \end{aligned} \tag{B.24}$$

having we used

$$\hat{s}^{\pm}_{\mathbf{k}\sigma} \equiv \frac{\hat{s}^x_{\mathbf{k}\sigma} \pm i\hat{s}^y_{\mathbf{k}\sigma}}{2}$$

Use now Eqns. (B.13) and (B.12),

$$\frac{\hat{\mathbb{I}}_{\mathbf{k}\sigma} + \hat{s}^z_{\mathbf{k}\sigma}}{2} = \hat{n}_{\mathbf{k}\sigma} \qquad \frac{\hat{\mathbb{I}}_{\mathbf{k}\sigma} - \hat{s}^z_{\mathbf{k}\sigma}}{2} = \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma}$$

Evaluating the above operators on the "up" and "down" states, we get immediately

$$\begin{aligned} &\frac{1}{2}\langle\Uparrow_{\mathbf{k}\sigma}|\hat{\mathbb{I}}_{\mathbf{k}\sigma} + \hat{s}^z_{\mathbf{k}\sigma}|\Uparrow_{\mathbf{k}\sigma}\rangle = 1 \qquad &&\frac{1}{2}\langle\Uparrow_{\mathbf{k}\sigma}|\hat{\mathbb{I}}_{\mathbf{k}\sigma} - \hat{s}^z_{\mathbf{k}\sigma}|\Uparrow_{\mathbf{k}\sigma}\rangle = 0 \\ &\frac{1}{2}\langle\Downarrow_{\mathbf{k}\sigma}|\hat{\mathbb{I}}_{\mathbf{k}\sigma} + \hat{s}^z_{\mathbf{k}\sigma}|\Downarrow_{\mathbf{k}\sigma}\rangle = 0 \qquad &&\frac{1}{2}\langle\Downarrow_{\mathbf{k}\sigma}|\hat{\mathbb{I}}_{\mathbf{k}\sigma} - \hat{s}^z_{\mathbf{k}\sigma}|\Downarrow_{\mathbf{k}\sigma}\rangle = 1 \end{aligned}$$

Thus, up to a phase

$$|\Uparrow_{\mathbf{k}\sigma}\rangle \sim \hat{c}^\dagger_{\mathbf{k}\sigma} |\Omega_{\mathbf{k}\sigma}\rangle \qquad |\Downarrow_{\mathbf{k}\sigma}\rangle \sim \hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma} |\Omega_{\mathbf{k}\sigma}\rangle$$

being $|\Omega_{\mathbf{k}\sigma}\rangle$ the $(\mathbf{k}, \sigma)$ Hilbert subspace vacuum.

It follows that composing Eqns. (B.23) and (B.24) the ground state $|\Psi\rangle$ can be written as:

$$|\Psi\rangle = \bigotimes_{\sigma} \bigotimes_{\mathbf{k}\in\mathrm{MBZ}} \left[\sin\theta_{\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{k}\sigma} + e^{2i\zeta_{\mathbf{k}\sigma}}\cos\theta_{\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma}\right] |\Omega_{\mathbf{k}\sigma}\rangle \tag{B.25}$$

having we absorbed in the relative phase $e^{2i\zeta_{\mathbf{k}\sigma}}$ the two states phases differences as well as the original sign difference of Eq. (B.24). Now, inserting the explicit form of the ground state from equation above:

$$\begin{aligned} \langle\overline{\Downarrow}_{\mathbf{k}\sigma}|\hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}^\dagger_{\mathbf{k}\sigma}|\overline{\Downarrow}_{\mathbf{k}\sigma}\rangle &= \left(e^{2i\zeta_{\mathbf{k}\sigma}} + e^{-2i\zeta_{\mathbf{k}\sigma}}\right)\sin\theta_{\mathbf{k}\sigma}\cos\theta_{\mathbf{k}\sigma} \\ &= \cos 2\zeta_{\mathbf{k}\sigma}\sin 2\theta_{\mathbf{k}\sigma} \end{aligned}$$

but from Eq. (B.10)

$$\begin{aligned} \langle\overline{\Downarrow}_{\mathbf{k}\sigma}|\hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}^\dagger_{\mathbf{k}\sigma}|\overline{\Downarrow}_{\mathbf{k}\sigma}\rangle &= \langle\overline{\Downarrow}_{\mathbf{k}\sigma}|\hat{s}^x_{\mathbf{k}\sigma}|\overline{\Downarrow}_{\mathbf{k}\sigma}\rangle \\ &= \sin 2\theta_{\mathbf{k}\sigma} \end{aligned}$$

since the pseudofield has no y component. This implies necessarily

$$\cos 2\zeta_{\mathbf{k}\sigma} \quad \Longrightarrow \quad \zeta_{\mathbf{k}\sigma} = k\pi \quad \text{with} \quad k \in \mathbb{Z}$$

and lets us conclude from Eq. (B.25)

$$|\Psi\rangle = \bigotimes_{\sigma} \bigotimes_{\mathbf{k}\in\mathrm{MBZ}} \left[\sin\theta_{\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{k}\sigma} + \cos\theta_{\mathbf{k}\sigma}\hat{c}^\dagger_{\mathbf{k}+\boldsymbol{\pi}\sigma}\right] |\Omega_{\mathbf{k}\sigma}\rangle \tag{B.26}$$

For low-temperature physics, we can expect the ground-state density matrix to be highly dominated by this BCS-like zero-temperature ground-state, which highlights the essential features of the

system. Finally, using Eq. (B.22), we check that correctly the ground-state describes a perfect degenerate $\gamma^{(-)}$ quasiparticles Fermi gas,

$$|\Psi\rangle = \bigotimes_{\sigma} \bigotimes_{\mathbf{k}\in\mathrm{MBZ}} \gamma^{(-)\dagger}_{\mathbf{k}\sigma} |\Omega_{\mathbf{k}\sigma}\rangle \tag{B.27}$$

The AF phase can be thought of as a long-range coordination between fermionic states related by a $\boldsymbol{\pi}$ shift in reciprocal space, producing a new free gas where all interactions have been "condensed" in these AF pairs.

B.1.4 Spin degeneracy removal

Up to now, we wrote explicitly the σ index. However,

$$\epsilon_{\mathbf{k}\uparrow} = \epsilon_{\mathbf{k}\downarrow} \qquad \Delta_{\mathbf{k}\uparrow} = -\Delta_{\mathbf{k}\downarrow}$$

thus $E_{\mathbf{k}\uparrow} = E_{\mathbf{k}\downarrow}$. Since the gap function sign does has not a measurable impact, we might as well take the spin index as a pure degeneracy and from now on work in the $\sigma =\uparrow$ sector, dropping the σ index. We can further simplify by dropping all indices from the gap function,

$$\Delta_{\mathbf{k}\uparrow} = mU \equiv \Delta$$

being the latter purely s-wave. This is a property of the pure HM: for the EHM, the gap acquires a non-trivial topological structure.

B.1.5 Chemical potential and system density

Using the fact that

$$\left\langle \hat{\Gamma}^{\dagger}_{\mathbf{k}\sigma} \hat{\Gamma}_{\mathbf{k}\sigma} \right\rangle = \left\langle \hat{\Psi}^{\dagger}_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} \right\rangle$$

due to the $W_{\mathbf{k}\sigma}$ unitarity properties, the total number of electrons is given by

$$\begin{aligned} N &= \sum_{\mathbf{k}\sigma} \langle \hat{n}_{\mathbf{k}\sigma} \rangle \\ &= \sum_{\sigma} \sum_{\mathbf{k}\in\mathrm{MBZ}} \langle \hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\boldsymbol{\pi}\sigma} \rangle \\ &= \sum_{\sigma} \sum_{\mathbf{k}\in\mathrm{MBZ}} \left\langle \hat{\Gamma}^{\dagger}_{\mathbf{k}\sigma} \hat{\Gamma}_{\mathbf{k}\sigma} \right\rangle \\ &= 2 \sum_{\mathbf{k}\in\mathrm{MBZ}} \mathrm{Th}^{(+)}_{\mathbf{k}}[\beta, \mu] \end{aligned} \tag{B.28}$$

being f be the Fermi-Dirac distribution at inverse temperature β and chemical potential μ,

$$f(\epsilon; \beta, \mu) = \frac{1}{e^{\beta(\epsilon-\mu)} + 1}$$

The 2 prefactor appeared because of spin degeneracy. Since the gapped bands refer to the smaller MBZ, thus exhibit the periodicity

$$E_{\mathbf{k}} = E_{\mathbf{k}+\boldsymbol{\pi}}$$

it holds equivalently

$$N = \sum_{\mathbf{k}\in\mathrm{BZ}} \mathrm{Th}^{(+)}_{\mathbf{k}}[\beta, \mu] \tag{B.29}$$

as is obvious. The 2 prefactor was absorbed in doubling the integration region, MBZ $\to$ BZ. Next sections are devoted to simplify the above theoretical results in order to obtain an algorithmic estimation for the magnetization m, which is just the AF instability order parameter.

In Fig. B.2 the density $n(\mu)$ is plotted as a function of μ. As is evident, at nearly zero temperature ($\beta \to \infty$) the system is half filled for $-\Delta < \mu < \Delta$. In order to obtain a finite doping, it must be $|\mu| > \Delta$; which means, the chemical potential needs to cross the electronic bands. This HF solution leads invariably to a rather unusual metallic AF at any finite doping.

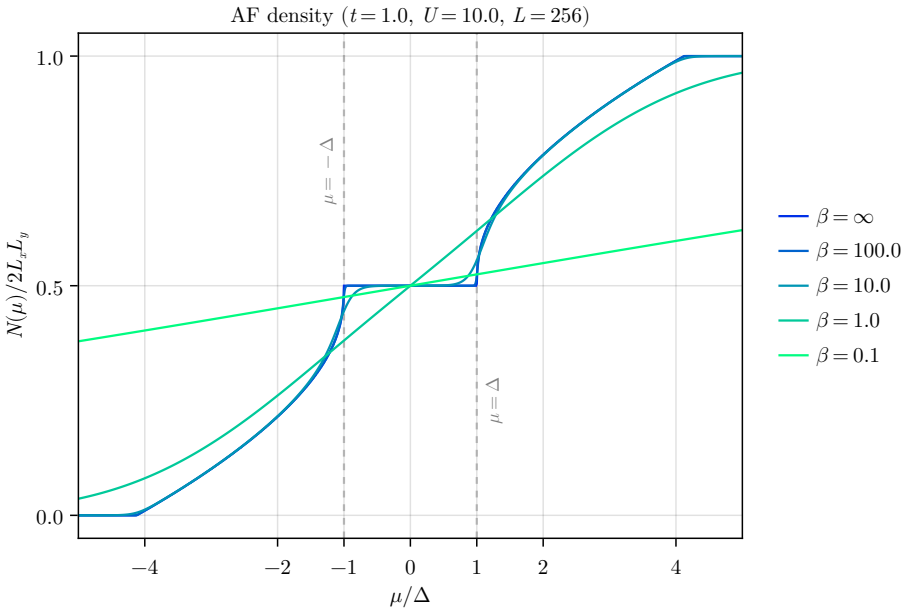

Figure B.2 | Electronic density in the AF phase as a function of the chemical potential, measured in relation to the gap $\Delta = mU$, at various temperatures.

B.1.6 Self-consistency gap equation and magnetization

A convergence algorithm can be designed to find the Hartree-Fock solution to the model. Ultimately, we aim to extract m self-consistently. Combining Eqns. (B.7), (B.1.1) and the definition of Eq. (B.3), we get

$$\frac{1}{2L_xL_y}\sum_{\mathbf{r}}(-1)^{x+y}\hat{n}_{\mathbf{r}\sigma} = \sum_{\mathbf{k}\in\mathrm{MBZ}}\left[\hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}^\dagger_{\mathbf{k}\sigma}\right]$$

thus

$$\begin{aligned} m &= \frac{1}{2L_xL_y}\sum_{\mathbf{r}}(-1)^{x+y}\langle\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}\rangle \\ &= \frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{MBZ}}\left\langle\left(\hat{\psi}_{\mathbf{k}\uparrow} + \hat{\psi}^\dagger_{\mathbf{k}\uparrow}\right) - \left(\hat{\psi}_{\mathbf{k}\downarrow} + \hat{\psi}^\dagger_{\mathbf{k}\downarrow}\right)\right\rangle \end{aligned}$$

Using now Eq. (B.10) we get the self-consistency equation for the HFP m,

$$\begin{aligned} m &= \frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{MBZ}}\left[\langle\hat{s}^x_{\mathbf{k}\uparrow}\rangle - \langle\hat{s}^x_{\mathbf{k}\downarrow}\rangle\right] \\ &= -\frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{MBZ}}\frac{\mathrm{Re}\{\Delta_{\mathbf{k}\uparrow}\} - \mathrm{Re}\{\Delta_{\mathbf{k}\downarrow}\}}{2E_{\mathbf{k}}}\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta,\mu] \\ &= -\frac{1}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{MBZ}}\frac{\Delta}{2E_{\mathbf{k}}}\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta,\mu] \end{aligned} \tag{B.30}$$

The magnetization m is the physical order parameter of the phase transition from the normal phase to the antiferromagnetic one. Within such phase transition, in fact, it is the expectation value

$$\langle\hat{c}^\dagger_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma}\rangle$$

that goes from zero (normal phase, free Fermi gas) to a non-zero value (AF). As is evident from equations above, m is just its (only) s-wave component.

Consider specifically the half-filled situation and multiply Eq. (**??**) on both sides by U. Since due to symmetry $\mu = 0$, we have the finite-temperature self-consistent equation

$$\Delta = \frac{U}{2L_xL_y}\sum_{\mathbf{k}\in\mathrm{MBZ}}\frac{\Delta}{\sqrt{\epsilon^2_{\mathbf{k}} + \Delta^2}}\tanh\left(\frac{\beta}{2}\sqrt{\epsilon^2_{\mathbf{k}} + \Delta^2}\right)$$

where we used the relation

$$\mathrm{Th}_{\mathbf{k}}^{(-)}[\beta, 0] = -\tanh\left(\frac{\beta E_{\mathbf{k}}}{2}\right)$$

In thermodynamic limit $L \to \infty$

$$\frac{1}{U} \simeq \frac{1}{2}\int_{\mathrm{MBZ}} \frac{\mathrm{d}\mathbf{k}}{(2\pi)^2} \frac{1}{\sqrt{\epsilon_{\mathbf{k}}^2 + \Delta^2}} \tanh\left(\frac{\beta}{2}\sqrt{\epsilon_{\mathbf{k}}^2 + \Delta^2}\right)$$

Substitute the momentum integral with an integral over energies, in the low temperature limit, $\beta \to \infty$ (thus approximate the hyperbolic tangent with 1)

$$\frac{1}{U} \simeq \frac{1}{2}\int_{\mathrm{bands}} \frac{\mathrm{d}\epsilon\rho(\epsilon)}{\sqrt{\epsilon^2 + \Delta^2}}$$

[To be continued...]

B.1.7 Instability of the commensurate AF solution and atypical metallic bands

A key point to be discussed is the known instability of the AF HF solution of the EHM. As is thoroughly discussed in [**singh1990collective**], the solution we presented above is only stable at half-filling, becoming hardly unstable at infinitesimal doping. This is due to the commensurate nature of the established AF phase: we impose SSB to take place at wavevector $\boldsymbol{\pi}$, shrinking the BZ to exactly half its size and giving back on the newly defined MBZ two bands $\pm E_{\mathbf{k}}$. This procedure actually works well for the half-filled case: the magnetization essentially depends on the scattering rate between points on the FS connected by a $\boldsymbol{\pi}$ vector. The half filled case, taking advantage of the natural nesting property of the bare bands,

$$\forall \mathbf{k} \in \partial\mathrm{MBZ}: \ \epsilon_{\mathbf{k}} = \epsilon_{\mathbf{k}+\boldsymbol{\pi}}$$

(being ∂MBZ the boundary of the MBZ) exhibits a magnetization at infinitesimal interaction. For a many body state resulting from continuous SSB, to establish a given phase means to show the presence of a stable gapless Goldstone mode associated to the broken symmetry. Such a Goldstone mode is essentially a sharp peak at zero frequency for some dressed response function. For the AF phase, it follows from the reduced $\mathrm{U}^z(1)$ rotational symmetry and is related to the proper transverse pseudospin-pseudospin response function, 2×2 matrix equation,

$$\tilde{\chi}_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\mathbf{k}, \omega) = \frac{\chi_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\mathbf{k}, \omega)}{1 - U\chi_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\mathbf{k}, \omega)} \tag{B.31}$$

being χ the free transverse response. The pseudospin hereby considered is the one of Eq. (B.9). As is shown in [**singh1990collective**], for the commensurate AF SSB at wavevector $\boldsymbol{\pi}$ the condition for the presence of a stable gapless mode reduces to a 2×2 matrix equation,

$$\text{Stability condition:} \qquad \mathbb{I}_{2\times 2} - U\left[\chi_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\boldsymbol{\pi}, 0)\right] \geq 0 \tag{B.32}$$

with $\left[\chi_{\hat{\mathbf{S}}^-\hat{\mathbf{S}}^+}(\boldsymbol{\pi}, \omega)\right]$ the response function matrix obtained by considering a matrix response function for a two-sites unit cell. The above equation is to be interpreted as a matricial equation [Explain better..]. Considering the eigenvalue of largest amplitude of the matrix λ_δ at filling δ, the one most prone to instabilities, it is found that

$$\begin{aligned} \lambda_0(\mathbf{k} \to \boldsymbol{\pi}, 0) &= \frac{1}{U} && \text{(half filling)} \\ \lambda_\delta(\mathbf{k} \to \boldsymbol{\pi}, 0) &= \frac{1}{U} + \frac{2\epsilon_{\mathrm{F}}}{\Delta} N(\epsilon_{\mathrm{F}}) && \text{(finite doping)} \end{aligned}$$

The reason for the distinction above is the intrinsic metallic nature of the system for infinitesimal doping. At half-filling the system is an insulator, therefore no Fermi energy is defined, as well as no FS. Evidently this implies

$$\begin{aligned} 1 - U\lambda_0(\mathbf{k} \to \boldsymbol{\pi}, 0) = 0 \quad &\text{(half filling)} \quad \Longrightarrow \quad \text{stable Goldstone mode} \\ 1 - U\lambda_\delta(\mathbf{k} \to \boldsymbol{\pi}, 0) < 0 \quad &\text{(finite doping)} \quad \Longrightarrow \quad \text{unstable Goldstone mode} \end{aligned}$$

For any finite doping, the commensurate AF phase becomes unstable and is destroyed by transverse spin fluctuations. Nevertheless, for the sake of completeness and because we noticed too late, we will study the metallic AF also at finite doping.

B.1.8 Hartree-Fock algorithm results in reciprocal space

The above sections offer a self-consistency equation for the only HFP m; W is determined by $\Delta = mU$ indeed. In an iterative HF fashion, Eq. (B.30) reads:

$$m_{i+1} = \frac{U}{2L_xL_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \frac{m_i}{2E_{\mathbf{k}}[\Delta_i]} \left[f(-E_{\mathbf{k}}[m_i];\beta,\mu) - f(E_{\mathbf{k}}[m_i];\beta,\mu)\right] \tag{B.33}$$

Then a self-consistent algorithm to search for a self consistent estimate of the magnetization may be sketched, following the general idea of Sec. 1.4:

1. Algorithm setup: initialize a counter $i = 1$ and choose:
   - the local repulsion U/t or equivalently the hopping amplitude t/U;
   - the coarse-graining of the BZ, which is, fix L_x and L_y. Then
     $$k_x = 2\pi n_x/L_x \qquad k_y = 2\pi n_y/L_y$$
     where $-L_j/2 \leq n_j \leq L_j/2$, $n_j \in \mathbb{Z}$;
   - the density n or equivalently the doping $\delta \equiv n - 0.5$;
   - the inverse temperature β;
   - the maximum number of iterations $p \in \mathbb{N}$;
   - the mixing parameter $g \in [0, 1]$;
   - the tolerance parameters $\delta_m, \delta_n \in \mathbb{R}$ (respectively for the HFP m and density);
2. Select a random starting value $m_i > 0$ for $i = 1$;
3. Find the optimal chemical potential μ as follows:
   a) Compute $\pm E_{\mathbf{k}}[\Delta_i, U]$;
   b) Define the function of the chemical potential μ,
   $$\delta n(\mu;\beta,m_i,U) \equiv \frac{1}{L_xL_y} \sum_{\mathbf{k}\in\mathrm{MBZ}} \left[f\left(-E_{\mathbf{k}}[U,m_i];\beta,\mu\right) + f\left(E_{\mathbf{k}}[U,m_i];\beta,\mu\right)\right] - n$$
   c) Find the root of δn,
   $$\delta n(\mu_i) = 0$$
   Then μ_i is the chemical potential which, at step i with HFP m_i, realizes the best approximation of density n;
4. Compute m_{i+1} using Eq. (B.33) with chemical potential μ_i and update the counter, $i \to i+1$;
5. Check if $|m_{i+1} - m_i| \leq \delta_m$:
   - If yes, halt;
   - If not: check if $i > p$
     - If yes, halt and consider choosing better tolerance and model parameters;
     - If not, define
     $$m_{i+1} \colon g m_{i+1} + (1-g)m_i$$
     (logical assignment notation used) and repeat from step 2.

The algorithm sketched hereby was ran with the following setup:

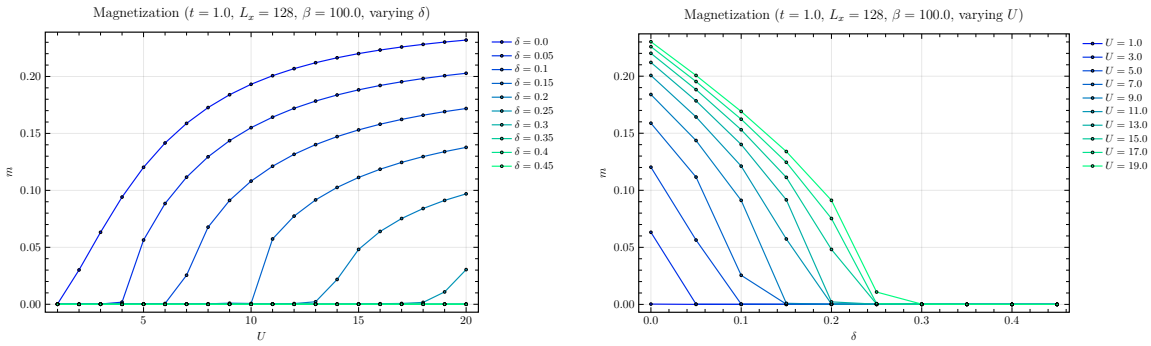

a | Local repulsion U/t depencence.

b | Doping $\delta = n - 0.5$ dependence.

Figure B.3 | Plots of the zero-temperature AF instability order parameter m as a function of both the local repulsion U/t (Fig. B.3a) and the doping $\delta = n - 1/2$ (Fig. B.3b).

```
UU = [U for U in 0.5:0.5:20.0]          # Local repulsions
LL = [256]                              # Lattice sizes
dd = [d for d in 0.0:0.05:0.45]         # Dopings
bb = [100.0, Inf]                       # Inverse temperatures
p = 100                                 # Max number of iterations
dm = 1e-4                               # Tolerance on magnetization
dn = 1e-2                               # Tolerance on density
g = 0.5                                 # Mixing parameter
```

In Fig. B.3 plots at $\beta = 100$ of the magnetization m is reported. As is evident in Fig. B.3a, doping disrupts AF ordering; the horizontal asymptote lowers as δ gets bigger, a mere consequence of the fact that the free space at each single-particle state in k-space shrinks as density increases; also, for $\delta > 0$, a finite magnetization m exists only for $U \geq U_c[\delta]$ (a critical value parametrically dependent on doping). Fig. B.3b shows the dependence of magnetization on doping at various fixed local repulsions U: once again, to dope the material disrupt AF ordering. Identical analysis have been performed for different temperatures, leading to analogous results as long as $\beta \gtrsim 10$ and to $m \simeq 0$ for higher temperatures (predictably).

B.2 (Impossibility of a stable) superconducting phase

Let us now move to the discussion of superconductivity in the HM. As for the AF phase, we use the results and analyses of this section as groundwork for the more sophisticated case of SC phase in the EHM. We anticipate here that BCS-like superconductivity cannot develop in the pure HM, due to the inherently repulsive nature of $\hat{H}_U$. BCS theory admits, for an half filled model, finite Cooper fluctuations for an infinitesimal attractive interaction. However, as will be discussed, by the means of MFT it is perfectly possible and coherent to derive a self-consistent superconducting solution to the HM. The point here is that such self-consistent solution sets to zero Cooper fluctuations.

As done for the AF phase in Sec. B.1 and following the introductory discussion of Sec. [Missing], let us start from the discussion of the phase symmetries. We aim to describe a uniform-density superconductor,

$$\langle \hat{n}_{i\sigma} \rangle = n$$

taking into account Cooper RWCs,

$$\langle \hat{c}^\dagger_{i\sigma} \hat{c}^\dagger_{i\overline{\sigma}} \rangle$$

which, having we broken $U^{\mathrm{c}}(1)$ charge symmetry, we allow to fluctuate to non-zero values. For the pure HM, we know from Tab. 1.3 that both Hartree and Cooper pairing channels contribute to the RWCs set. We handle them separately.

B.2.1 MFT treatment of the Hartree channel

For the Hartree channel, knowing the deal with a uniform-density phase, we can re-use the derivation of Sec. B.1.1 simply by setting $m = 0$. We immediately get from Eq. (B.5):

$$\begin{aligned}\hat{H}_U &\simeq U \sum_{\mathbf{r}} \left[\hat{n}_{\mathbf{r}\uparrow} \langle \hat{n}_{\mathbf{r}\downarrow}\rangle + \langle \hat{n}_{\mathbf{r}\uparrow}\rangle \hat{n}_{\mathbf{r}\downarrow} - \langle \hat{n}_{\mathbf{r}\uparrow}\rangle \langle \hat{n}_{\mathbf{r}\downarrow}\rangle\right] + (\text{Cooper channel}) \\ &= nU \times \hat{N} - E^{(\mathrm{SC})}_{\mathrm{H}/U} + (\text{Cooper channel})\end{aligned} \tag{B.34}$$

thus chemical potential renormalization $\tilde{\mu} \equiv \mu - nU$ is present also for the SC phase. The contraction energy comes immediately from Eq. (B.6),

$$E^{(\mathrm{SC})}_{\mathrm{H}/U} = L_x L_y \times n^2 U \tag{B.35}$$

We now move to Cooper channel.

B.2.2 MFT treatment of the Cooper channel

Recall the result of Eq. (1.21) which gave the Fourier-transformed version of the local repulsion, and perform a Cooper class Wick's contraction on it,

$$\begin{aligned}\hat{H}_U \simeq (\text{Hartree channel}) + \frac{U}{L_x L_y} \sum_{\mathbf{K},\mathbf{k},\mathbf{k}'} \Big[&\big\langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\downarrow}\big\rangle \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow} \\ &+ \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\downarrow} \big\langle \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow}\big\rangle - \big\langle \hat{c}^\dagger_{\mathbf{K}+\mathbf{k}\uparrow} \hat{c}^\dagger_{\mathbf{K}-\mathbf{k}\downarrow}\big\rangle \big\langle \hat{c}_{\mathbf{K}-\mathbf{k}'\downarrow} \hat{c}_{\mathbf{K}+\mathbf{k}'\uparrow}\big\rangle \Big]\end{aligned} \tag{B.36}$$

We are not breaking translational invariance, thus only Cooper fluctuations with net zero total momentum are allowed. This means only $\mathbf{K} = \mathbf{0}$ contributes. Define as in Eq. (**??**) the pairing operator

$$\hat{\phi}_{\mathbf{k}\uparrow} \equiv \hat{c}_{-\mathbf{k}\downarrow} \hat{c}_{\mathbf{k}\uparrow} \tag{B.37}$$

and define $w_{\mathbf{q}}$ as in Eq. (**??**),

$$w_{\mathbf{q}} \equiv \langle \phi^\dagger_{\mathbf{q}} \rangle$$

Its s-wave part is given by:

$$w^{(s)} \equiv \frac{1}{L_x L_y} \sum_{\mathbf{q}\in \mathrm{BZ}} w_{\mathbf{q}} \tag{B.38}$$

Let $\hat{n}_{\mathbf{k}\sigma}$ as in Eq. (B.2). Eq. (B.34) reduces to

$$\hat{H}_U \simeq (\text{Hartree channel}) + \frac{U}{L_x L_y} \sum_{\mathbf{q},\mathbf{q}'} \Big[\big\langle \hat{\phi}^\dagger_{\mathbf{q}} \big\rangle \hat{\phi}_{\mathbf{q}'} + \hat{\phi}^\dagger_{\mathbf{q}} \big\langle \hat{\phi}_{\mathbf{q}'} \big\rangle \Big] - E^{(\mathrm{SC})}_{\mathrm{C}/U} \tag{B.39}$$

being $E^{(\mathrm{SC})}_{\mathrm{C}/U}$ the HM Cooper contraction energy,

$$\begin{aligned}E^{(\mathrm{SC})}_{\mathrm{C}/U} &\equiv \frac{U}{L_x L_y} \sum_{\mathbf{q}\mathbf{q}'} \big\langle \hat{\phi}^\dagger_{\mathbf{q}} \big\rangle \big\langle \hat{\phi}_{\mathbf{q}'} \big\rangle \\ &= L_x L_y \times U \left| w^{(s)} \right|^2\end{aligned} \tag{B.40}$$

Let now

$$\Delta^{(s)} \equiv -U w^{(s)}$$

We finally reduce $\hat{H}_U$ to

$$\hat{H}_U \simeq (\text{Hartree channel}) - \sum_{\mathbf{q}\in \mathrm{BZ}} \Big[\Delta^{(s)} \hat{\phi}_{\mathbf{q}} + \Delta^{(s)*} \hat{\phi}^\dagger_{\mathbf{q}} \Big] - E^{(\mathrm{SC})}_{\mathrm{C}/U} \tag{B.41}$$

which can be easily mapped on a pseudospin model.

Composing Eqns. (B.34) and (B.41), we get the full MFT hamiltonian

$$\hat{H} \simeq \sum_{\mathbf{k}\in\mathrm{BZ}} \sum_{\sigma} \epsilon_{\mathbf{k}\sigma} \left[\hat{c}^{\dagger}_{\mathbf{k}\sigma}\hat{c}_{\mathbf{k}\sigma} - \hat{c}^{\dagger}_{\mathbf{k}+\boldsymbol{\pi}\sigma}\hat{c}_{\mathbf{k}+\boldsymbol{\pi}\sigma}\right] - \sum_{\mathbf{q}\in\mathrm{BZ}} \left[\Delta^{(s)}\hat{\phi}_{\mathbf{q}} + \Delta^{(s)*}\hat{\phi}^{\dagger}_{\mathbf{q}}\right] + nU \times \hat{N} - \left[E^{(\mathrm{SC})}_{\mathrm{H}/U} + E^{(\mathrm{SC})}_{\mathrm{C}/U}\right] \tag{B.42}$$

B.2.3 Nambu representation of the SC phase and diagonalization

We now proceed precisely as in Sec. B.1.2. Define the SC Nambu spinor

$$\hat{\Phi}_{\mathbf{k}} \equiv \begin{bmatrix} \hat{c}_{\mathbf{k}\uparrow} \\ \hat{c}^{\dagger}_{-\mathbf{k}\downarrow} \end{bmatrix}$$

Define the pseudospin operator:

$$\hat{s}^{\alpha}_{\mathbf{k}} \equiv \hat{\Phi}^{\dagger}_{\mathbf{k}}\tau^{\alpha}\hat{\Phi}_{\mathbf{k}}$$

and the shifted bare bands,

$$\xi_{\mathbf{k}} \equiv \epsilon_{\mathbf{k}} - \tilde{\mu}$$

Notice we are using the chemical potential RMP. We employ from the start the spin-independency of the bare bands, as well as their pure s^*-wave structure, since no Fock interaction in the present context chan change that. The following chain holds:

$$\begin{aligned} \hat{n}_{\mathbf{k}\uparrow} + \hat{n}_{-\mathbf{k}\downarrow} &= \hat{c}^{\dagger}_{\mathbf{k}\uparrow}\hat{c}_{\mathbf{k}\uparrow} + \hat{c}^{\dagger}_{-\mathbf{k}\downarrow}\hat{c}_{-\mathbf{k}\downarrow} \\ &= \hat{c}^{\dagger}_{\mathbf{k}\uparrow}\hat{c}_{\mathbf{k}\uparrow} - \hat{c}_{-\mathbf{k}\downarrow}\hat{c}^{\dagger}_{-\mathbf{k}\downarrow} + \hat{\mathbb{I}}_{\mathbf{k}} \\ &= \hat{\Phi}^{\dagger}_{\mathbf{k}}\tau^{z}\hat{\Phi}_{\mathbf{k}} + \hat{\mathbb{I}}_{\mathbf{k}} \\ &= \hat{s}^{z}_{\mathbf{k}} + \hat{\mathbb{I}}_{\mathbf{k}} \end{aligned} \tag{B.43}$$

Then, considering the kinetic part of the gran-canonical hamiltonian,

$$\begin{aligned} \hat{H}_t - \tilde{\mu}\hat{N} &= \sum_{\sigma}\sum_{\mathbf{k}\in\mathrm{BZ}} \left(\epsilon_{\mathbf{k}\sigma} - \tilde{\mu}\right)\hat{n}_{\mathbf{k}\sigma} \\ &= \sum_{\mathbf{k}\in\mathrm{BZ}} \left[\xi_{\mathbf{k}}\hat{n}_{\mathbf{k}\uparrow} + \xi_{-\mathbf{k}}\hat{n}_{-\mathbf{k}\downarrow}\right] \\ &= \sum_{\mathbf{k}\in\mathrm{BZ}} \xi_{\mathbf{k}}\hat{s}^{z}_{\mathbf{k}} + E^{(\mathrm{SC})}_{\mathrm{a}} \end{aligned}$$

being $E^{(\mathrm{SC})}_{\mathrm{a}}$ the "anticommutation energy" coming from the kinetic term,

$$E^{(\mathrm{SC})}_{\mathrm{a}} \equiv \sum_{\mathbf{k}\in\mathrm{BZ}} \xi_{\mathbf{k}} \tag{B.44}$$

The scalar term in the above equation is essential for estimating correctly the phase ground state free energy density. The full MFT gran-canonical hamiltonian in Nambu representation is obtained including Eq. (B.39),

$$\hat{H} - \mu\hat{N} \simeq \sum_{\mathbf{k}\in\mathrm{BZ}}\sum_{\sigma} \hat{\Phi}^{\dagger}_{\mathbf{k}} h_{\mathbf{k}} \hat{\Phi}_{\mathbf{k}} + E^{(\mathrm{SC})}_{\mathrm{a}} - \left[E^{(\mathrm{SC})}_{\mathrm{H}/U} + E^{(\mathrm{SC})}_{\mathrm{C}/U}\right] \tag{B.45}$$

(note the non-renormalized chemical potential on the left) being

$$h_{\mathbf{k}} \equiv \begin{bmatrix} \xi_{\mathbf{k}} & -\Delta^{*}_{\mathbf{k}} \\ -\Delta_{\mathbf{k}} & -\xi_{\mathbf{k}} \end{bmatrix}$$

while the off-diagonal gap is a constant,

$$\Delta_{\mathbf{k}} \equiv \Delta^{(s)}$$

This hamiltonian behaves as an ensemble of spins in local magnetic pseudofields

$$\mathbf{b}_{\mathbf{k}} \equiv \begin{bmatrix} -\operatorname{Re}\{\Delta_{\mathbf{k}}\} \\ -\operatorname{Im}\{\Delta_{\mathbf{k}}\} \\ \xi_{\mathbf{k}} \end{bmatrix} \qquad \tan 2\theta_{\mathbf{k}} \equiv \frac{\xi_{\mathbf{k}}}{\sqrt{\xi_{\mathbf{k}}^2 + |\Delta_{\mathbf{k}}|^2}} \qquad \tan 2\zeta_{\mathbf{k}} \equiv \frac{\operatorname{Im}\{\Delta_{\mathbf{k}}\}}{\operatorname{Re}\{\Delta_{\mathbf{k}}\}} \tag{B.46}$$

precisely as was for the AF phase, with the essential difference that now the chemical potential RMP lies inside the z component of the pseudofield itself. This is a consequence of the Nambu spinors definition. We have the spin hamiltonian

$$\hat{H} - \mu\hat{N} \simeq \sum_{\mathbf{k}\in\mathrm{BZ}} \mathbf{b}_{\mathbf{k}} \cdot \hat{\mathbf{s}}_{\mathbf{k}} + E_{\mathrm{a}}^{(\mathrm{SC})} - \left[E_{\mathrm{H}/U}^{(\mathrm{SC})} + E_{\mathrm{C}/U}^{(\mathrm{SC})}\right] \quad \text{where} \quad \hat{\mathbf{s}}_{\mathbf{k}} = \begin{bmatrix} \hat{s}_{\mathbf{k}}^x \\ \hat{s}_{\mathbf{k}}^y \\ \hat{s}_{\mathbf{k}}^z \end{bmatrix} \tag{B.47}$$

As was for the AF phase, to diagonalize the hamiltonian means essentially to align the spin z axis with the direction of the pseudofield. Then, we diagonalize the hamiltonian via a set of rotations similarly to Eq. (B.14). The main difference is that in general the pseudofield can have a y component, thus the diagonalizing matrix is made of a sequence of two rotations, both counter-clockwise, the first around the z axis by an angle $2\zeta_{\mathbf{k}}$ to place the pseudofield in the xz plane, the second around the new y axis by an angle $2\theta_{\mathbf{k}}$ to align the z axis with the pseudofield,

$$\begin{aligned} W_{\mathbf{k}} &\equiv e^{-i\theta_{\mathbf{k}}\tau^y} e^{-i\zeta_{\mathbf{k}}\tau^z} \\ &= \begin{bmatrix} \cos\theta_{\mathbf{k}} & -\sin\theta_{\mathbf{k}} \\ \sin\theta_{\mathbf{k}} & \cos\theta_{\mathbf{k}} \end{bmatrix} \begin{bmatrix} e^{-i\zeta_{\mathbf{k}}} & \\ & e^{i\zeta_{\mathbf{k}}} \end{bmatrix} \\ &= \begin{bmatrix} \cos\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} & -\sin\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \\ \sin\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} & \cos\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \end{bmatrix} \end{aligned} \tag{B.48}$$

obtaining the diagonal matrix

$$d_{\mathbf{k}} \equiv W_{\mathbf{k}} h_{\mathbf{k}} W_{\mathbf{k}}^\dagger \quad \text{where} \quad d_{\mathbf{k}} \equiv \begin{bmatrix} E_{\mathbf{k}} & \\ & -E_{\mathbf{k}} \end{bmatrix}$$

and the bands

$$E_{\mathbf{k}} \equiv \sqrt{\xi_{\mathbf{k}}^2 + |\Delta_{\mathbf{k}}|^2}$$

Finally, the Nambu spinor for Bogoliubov quasiparticles is given similarly to Eq. (B.21)

$$\hat{\Gamma}_{\mathbf{k}} = W_{\mathbf{k}} \hat{\Phi}_{\mathbf{k}} \tag{B.49}$$

Explicitly,

$$\begin{aligned} \hat{\Gamma}_{\mathbf{k}} &= \begin{bmatrix} \cos\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} & -\sin\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \\ \sin\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} & \cos\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \end{bmatrix} \begin{bmatrix} \hat{c}_{\mathbf{k}\uparrow} \\ \hat{c}_{-\mathbf{k}\downarrow}^\dagger \end{bmatrix} \\ &= \begin{bmatrix} \cos\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} \hat{c}_{\mathbf{k}\uparrow} - \sin\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \hat{c}_{-\mathbf{k}\downarrow}^\dagger \\ \sin\theta_{\mathbf{k}} e^{-i\zeta_{\mathbf{k}}} \hat{c}_{\mathbf{k}\uparrow} + \cos\theta_{\mathbf{k}} e^{i\zeta_{\mathbf{k}}} \hat{c}_{-\mathbf{k}\downarrow}^\dagger \end{bmatrix} \equiv \begin{bmatrix} \hat{\gamma}_{\mathbf{k}}^{(+)} \\ \hat{\gamma}_{\mathbf{k}}^{(-)} \end{bmatrix} \end{aligned} \tag{B.50}$$

These operators act as free fermion fields on the Bogoliubov bands $\pm E_{\mathbf{k}}$.

B.2.4 Explicit zero-temperature SC ground state at half-filling

Reasoning precisely as in Sec. B.1.3, we can extract the half-filling zero temperature ground state, commonly referred to as the "BCS state". Eqns. (B.23) and (B.24) hold equivalently (ignoring the σ index and extending momentum tensor product to the entire BZ),

$$|\Psi\rangle = \bigotimes_{\mathbf{k}\in\mathrm{BZ}} \left[\cos\theta_{\mathbf{k}} |\Downarrow_{\mathbf{k}}\rangle - \sin\theta_{\mathbf{k}} |\Uparrow_{\mathbf{k}}\rangle\right]$$

Using now Eq. (B.43), we have

$$\begin{aligned} \langle\Downarrow_{\mathbf{k}}|\hat{s}_{\mathbf{k}}^z + \hat{\mathbb{I}}_{\mathbf{k}}|\Downarrow_{\mathbf{k}}\rangle &= 0 \\ \langle\Uparrow_{\mathbf{k}}|\hat{s}_{\mathbf{k}}^z + \hat{\mathbb{I}}_{\mathbf{k}}|\Uparrow_{\mathbf{k}}\rangle &= 2 \end{aligned}$$

so up to a phase

$$|\Downarrow_{\mathbf{k}}\rangle \sim |\Omega_{\mathbf{k}}\rangle \qquad |\Uparrow_{\mathbf{k}}\rangle \sim \hat{\phi}^\dagger_{\mathbf{k}} |\Omega_{\mathbf{k}}\rangle$$

Hence, we have

$$|\Psi\rangle = \bigotimes_{\mathbf{k}\in\mathrm{BZ}} \left[\cos\theta_{\mathbf{k}} + e^{2i\zeta_{\mathbf{k}}} \sin\theta_{\mathbf{k}} \hat{\phi}^\dagger_{\mathbf{k}}\right] |\Omega_{\mathbf{k}}\rangle \tag{B.51}$$

The argument $2\zeta_{\mathbf{k}}$ of the phase factor is precisely the phase of the gap function, as can be shown easily.

B.2.5 Superconducting fluctuations suppression in the conventional HM

Let us report the SC analogous of the AF Eqns. (B.10) and (B.11):

$$\hat{s}^x_{\mathbf{k}} = \hat{\phi}_{\mathbf{k}} + \hat{\phi}^\dagger_{\mathbf{k}} \tag{B.52}$$

$$\hat{s}^y_{\mathbf{k}} = i\left(\hat{\phi}_{\mathbf{k}} - \hat{\phi}^\dagger_{\mathbf{k}}\right) \tag{B.53}$$

while the analogous of Eq. (B.12) was given in Eq. (B.43). Let also the thermal factor

$$\mathrm{Th}^{(\pm)}_{\mathbf{k}}[\beta] \equiv f\left(E_{\mathbf{k}};\beta,0\right) \pm f\left(-E_{\mathbf{k}};\beta,0\right) \tag{B.54}$$

and the EVs:

$$\langle \hat{s}^x_{\mathbf{k}}\rangle = -\frac{\mathrm{Re}\{\Delta_{\mathbf{k}}\}}{2E_{\mathbf{k}}}\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta] \tag{B.55}$$

$$\langle \hat{s}^y_{\mathbf{k}}\rangle = -\frac{\mathrm{Im}\{\Delta_{\mathbf{k}}\}}{2E_{\mathbf{k}}}\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta] \tag{B.56}$$

$$\langle \hat{s}^z_{\mathbf{k}}\rangle = \frac{\xi_{\mathbf{k}}}{2E_{\mathbf{k}}}\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta] \tag{B.57}$$

Up to now, the derivation was general. However, it is immediate to show that for the pure HM the SC phase can never establish. Recall Eq. (B.38): explicitly

$$\begin{aligned} w^{(s)} &= \frac{1}{L_x L_y}\sum_{\mathbf{k}\in\mathrm{BZ}} \langle \hat{\phi}^\dagger_{\mathbf{k}}\rangle \\ &= \frac{1}{L_x L_y}\sum_{\mathbf{k}\in\mathrm{BZ}} \langle \hat{\Phi}^\dagger_{\mathbf{k}}\tau^+\hat{\Phi}_{\mathbf{k}}\rangle \\ &= \frac{1}{L_x L_y}\sum_{\mathbf{k}\in\mathrm{BZ}} \frac{\langle \hat{s}^x_{\mathbf{k}}\rangle + i\langle \hat{s}^y_{\mathbf{k}}\rangle}{2} \\ &= -\frac{1}{2L_x L_y}\sum_{\mathbf{k}\in\mathrm{BZ}} \frac{\Delta_{\mathbf{k}}}{E_{\mathbf{k}}}\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta] \end{aligned} \tag{B.58}$$

Now: $\Delta_{\mathbf{k}} = \Delta^{(s)} = -Uw^{(s)}$, thus if we define

$$U_{\mathrm{c}}[\beta] \equiv \left[-\frac{1}{2L_x L_y}\sum_{\mathbf{k}\in\mathrm{BZ}} \frac{\mathrm{Th}^{(-)}_{\mathbf{k}}[\beta]}{E_{\mathbf{k}}}\right]^{-1}$$

(the reason for this notation will be clear in Sec. [Missing]) we end with the equation:

$$w^{(s)} = -\frac{U}{U_{\mathrm{c}}[\beta]} w^{(s)}$$

Since evidently $U_{\mathrm{c}}[\beta] > 0$ by definition (the thermal factor is negative by construction), the above equation can be solved in $\mathbb{C}$ only by $w^{(s)} = 0$. This implication terminates the argument: superconductivity cannot establish self-consistently at this level in the HM.