

# Numerical analysis of superconducting phases in the extended Hubbard model with non-local pairing

University of Pisa, a.y. 2025-2026

Alessandro Gori\*

Thesis for the Master's degree in Physics

## Abstract

[To be continued...]

- Appendix on  $s$ -wave SC ghost simulations on HM
- Set ComputerModern font in all CairoMakie figures

## Contents

|          |                                                                                  |           |
|----------|----------------------------------------------------------------------------------|-----------|
| <b>1</b> | <b>The normal phase</b>                                                          | <b>3</b>  |
| 1.1      | The “normal” phase and its symmetries . . . . .                                  | 3         |
| 1.2      | Hartree effects: chemical potential renormalization . . . . .                    | 4         |
| 1.2.1    | Hartree channel in the normal phase: analytic derivation . . . . .               | 4         |
| 1.2.2    | Hartree contraction energy . . . . .                                             | 5         |
| 1.3      | Fock effects: bare bands renormalization . . . . .                               | 6         |
| 1.3.1    | Fock channel in the normal phase: analytic derivation . . . . .                  | 6         |
| 1.3.2    | Fock contraction energy . . . . .                                                | 8         |
| 1.3.3    | Nematicity: extending hopping to $d$ -wave bands . . . . .                       | 9         |
| 1.4      | Normal free energy density . . . . .                                             | 10        |
| 1.5      | Theoretical constraints on the normal phase HFPs . . . . .                       | 11        |
| 1.5.1    | Constraints in presence of a robust $C_4$ symmetry and bands shrinking . . . . . | 13        |
| 1.5.2    | Natural suppression of nematicity within $C_2/\mathbb{Z}_2$ symmetry . . . . .   | 14        |
| 1.5.3    | Expected dependence on $\delta$ at low temperature . . . . .                     | 17        |
| 1.6      | Discussion of numeric results . . . . .                                          | 19        |
| 1.6.1    | Mott localisation effect . . . . .                                               | 20        |
| 1.6.2    | Solution free energy and entropy densities . . . . .                             | 21        |
| 1.6.3    | Convergence problems and mixing fine-tuning . . . . .                            | 23        |
| <b>2</b> | <b>Antiferromagnetic instability</b>                                             | <b>25</b> |
| 2.1      | The AF phase and its symmetries . . . . .                                        | 25        |
| 2.1.1    | Symmetries of the commensurate AF Ansatz . . . . .                               | 26        |
| 2.1.2    | The AF Ansatz in reciprocal space . . . . .                                      | 27        |
| 2.2      | Local Hartree effects: antiferromagnetism in the HM . . . . .                    | 29        |
| 2.2.1    | Local Hartree channel in the AF phase: analytic derivation . . . . .             | 29        |
| 2.2.2    | Local Hartree contraction energy . . . . .                                       | 30        |
| 2.2.3    | Antiferromagnetism in the HM . . . . .                                           | 31        |
| 2.2.4    | Features of the AF solution . . . . .                                            | 33        |
| 2.3      | Extension to the EHM . . . . .                                                   | 36        |

---

\*a.gori23@studenti.unipi.it / nepero27178@github.com

|       |                                                                                |           |
|-------|--------------------------------------------------------------------------------|-----------|
| 2.4   | Non-local Hartree effects: chemical potential renormalisation . . . . .        | 37        |
| 2.4.1 | Non-local Hartree channel in the AF phase: analytic derivation . . . . .       | 38        |
| 2.4.2 | Non-local Hartree contraction energy . . . . .                                 | 39        |
| 2.5   | Fock effects: gap and bands renormalisation . . . . .                          | 40        |
| 2.5.1 | Fock channel in the AF phase: analytic derivation . . . . .                    | 40        |
| 2.5.2 | Fock contraction energy . . . . .                                              | 43        |
| 2.6   | Full MFT hamiltonian and gap complexification . . . . .                        | 44        |
| 2.6.1 | The relative phase in the zero temperature half-filled ground state . . . . .  | 45        |
| 2.6.2 | AF phase flavours and spin degeneracy . . . . .                                | 46        |
| 2.7   | AF free energy density . . . . .                                               | 46        |
| 2.7.1 | Energetic constraints on the HFPs . . . . .                                    | 48        |
| 2.7.2 | Free energy at half-filling . . . . .                                          | 49        |
| 2.8   | Theoretical constraints on the AF phase HFPs . . . . .                         | 49        |
| 2.8.1 | Robust $C_4$ bands shrinking extension to AF phases . . . . .                  | 49        |
| 2.8.2 | HFPs vanishing in sAF phase . . . . .                                          | 50        |
| 2.8.3 | HFPs vanishing in aAF phase . . . . .                                          | 54        |
| 2.8.4 | Natural suppression of nematicity within $C_2/\mathbb{Z}_2$ symmetry . . . . . | 55        |
| 2.9   | Discussion of numeric results . . . . .                                        | 57        |
| 2.9.1 | Magnetization boost . . . . .                                                  | 57        |
| 2.9.2 | Bands shrinking . . . . .                                                      | 58        |
| 2.9.3 | Solution free energy and entropy densities . . . . .                           | 59        |
| 2.9.4 | Fixed-point interpretation of HF solution . . . . .                            | 61        |
|       | <b>Bibliography</b>                                                            | <b>63</b> |

---

### List of symbols and abbreviations

---

|                     |                                              |
|---------------------|----------------------------------------------|
| AF                  | Antiferromagnetic                            |
| BCS                 | Bardeen-Cooper-Schrieffer (theory)           |
| BZ                  | Brillouin zone                               |
| $\beta$             | Inverse temperature                          |
| $\Delta^{(\gamma)}$ | $\gamma$ -wave component of the gap function |
| DoF                 | Degree of freedom                            |
| EHM                 | Extended Hubbard model                       |
| EV(s)               | Expectation value(s)                         |
| FS                  | Fermi surface                                |
| HF                  | Hartree-Fock                                 |
| HFP(s)              | Hartree-Fock parameter(s)                    |
| HM                  | Hubbard model                                |
| $L_\ell$            | Number of lattice sites in direction $\ell$  |
| iHF                 | Iterative Hartree-Fock                       |
| LRT                 | Linear Response Theory                       |
| MBZ                 | Magnetic Brillouin zone                      |
| MFT                 | Mean-Field Theory                            |
| NBZ                 | Nematic Brillouin zone                       |
| NN(s)               | Nearest neighbor(s)                          |
| PH                  | Particle-hole                                |
| PHS                 | Particle-hole symmetry                       |
| RWC(s)              | Relevant Wick's contraction(s)               |
| RMP(s)              | Renormalized model parameter(s)              |
| SC                  | Superconductor                               |
| SDW                 | Spin-density wave                            |
| SSB                 | Spontaneous symmetry breaking                |
| $T_c$               | Critical temperature                         |

---





# Introduction

This thesis project is about my favorite ice cream flavor. [To be continued...]



# Chapter 1

## The normal phase

In this chapter we apply the HF methods sketched in Sec. ?? to the “normal phase”. We are studying the model in a state where no symmetry of those enumerated in Tab. ?? is broken. Even though this phase may appear not so interesting, it actually shows a significant physical difference with respect to the conventional perfectly degenerate Fermi gas.

HF methods applied in this context will lead us to a self-consistent hopping renormalisation effect. For certain values of the non-local attraction  $V$  and the doping level, a complete Mott localisation effect takes place. The resulting bands shrinking and flattening is the main net effect of the presence of  $\hat{H}_V$  in the EHM.

This chapter is divided in three main parts. First, we discuss the symmetries of the normal phase, following the general discussion of Chap. ??, and apply HF methods to derive the self-consistent approximated hamiltonian. Second, we impose some theoretical constraints on the self-consistent solution. Lastly, we present numeric results.

### 1.1 The “normal” phase and its symmetries

In the normal phase no symmetry is broken. Thus, the HF wavefunction approximating the ground state must exhibit the full  $U(2) \otimes C_4 \otimes T_1^{(x)} \otimes T_1^{(y)}$  symmetry discussed in Sec. ?. We take a slight detour from this, and instead allow for

$$C_4 \xrightarrow{\text{SSB}} C_2$$

This is the only potential SSB we consider. It will turn out in Sec. 1.5.2 that even allowing for breaking of rotational symmetry, the ground-state actually does not break  $C_4$ . This can be seen as a convoluted way to confirm that there is not a normal-nematic phase. While this may seem as an useless complication, the derivation will set grounds for actual nematic effects found in the superconducting phase.

Our HF method relies on the application of Wick’s theorem on the quartic part of the interacting hamiltonian, expressed in Eq. (??). We will decompose the quartic operators according to Eqns. (??), (??). Recalling Tabs. ?? and ??, for the normal phase we must consider the following contributions to the EVs of Eqns. (??), (??), (??):

|                           |                               |
|---------------------------|-------------------------------|
| $\hat{H}_U$               | Hartree contraction           |
| $\hat{H}_V$ (o.s. sector) | Hartree contraction           |
| $\hat{H}_V$ (s.s. sector) | Hartree and Fock contractions |

As we will see in detail and is summarised in Tab. 1.1, Hartree contractions give a chemical potential shift, while the unique Fock contraction effectively renormalises the bare bands.

In the normal phase, spin is a pure physical degeneracy, being the  $\uparrow$  and  $\downarrow$  sectors separated; moreover,  $\hat{H}$  is  $\mathbb{Z}_2$  invariant with respect to spin inversion,  $\sigma \leftrightarrow \bar{\sigma}$ . This implies that all physical quantities, as is for the normal phase, should not depend on the spin index. We will perform all computations leaving  $\sigma$  explicit and using this consideration at the end.

| Operator    | Sector | RWCs            | Net effect                                                         |
|-------------|--------|-----------------|--------------------------------------------------------------------|
| $\hat{H}_U$ |        | Hartree         | $\mu$ shift by $-nU$                                               |
| $\hat{H}_V$ | o.s.   | Hartree         | $\mu$ shift by $nzV$                                               |
|             | s.s.   | Hartree<br>Fock | $\mu$ shift by $nzV$<br>Bands renormalization and resymmetrization |

Table 1.1 | Relevant Wick’s contractions and net effect in the normal phase.

## 1.2 Hartree effects: chemical potential renormalization

Let us start by the analysis of the Hartree channel. The Hartree channel is defined as operator resulting from summing Hartree-like terms originating from Wick’s decomposition of the quartic parts of  $\hat{H}$ . Each quartic term decomposes as a sum of fully contracted pairs, as in Eq. (??).

In the final hamiltonian, the net effect originating from Hartree terms will be a renormalisation of  $\mu$ . To derive analytically this effect is only important to the ends of computing correctly the free energy density of the approximated ground state. As is discussed in Sec. ??, in the context of numerical simulations at fixed density, the chemical potential is determined self-consistently at each step; thus any net effect that shifts  $\mu$  is effectively ignored within (and limitedly to) the iterative algorithm.

### 1.2.1 Hartree channel in the normal phase: analytic derivation

The quartic part of  $\hat{H}$  is given by the the local repulsion  $\hat{H}_U$  and the non-local attraction  $\hat{H}_V$ . Applying HF methods to them, we get the decomposition of Eqns. (??), (??). Let us deal with the Hartree sector of both separately.

**Local repulsion.** In the normal phase, the local repulsion  $\hat{H}_U$  decomposes in Hartree channel as specified in Eq. (??)

$$\hat{H}_U \simeq U \sum_i [\langle \hat{n}_{i\uparrow} \rangle \hat{n}_{i\downarrow} + \hat{n}_{i\uparrow} \langle \hat{n}_{i\downarrow} \rangle - \langle \hat{n}_{i\downarrow} \rangle \langle \hat{n}_{i\uparrow} \rangle]$$

For a translationally invariant phase such as the normal phase, it holds

$$\langle \hat{n}_{i\sigma} \rangle = n \tag{1.1}$$

which gives

$$\begin{aligned} \hat{H}_U &\simeq nU \sum_i [\hat{n}_{i\uparrow} + \hat{n}_{i\downarrow}] - U \sum_i n^2 \\ &= nU \times \hat{N} - E_{\text{H}/U}^{(\text{N})} \end{aligned} \tag{1.2}$$

being  $\hat{N}$  the total number operator and  $E_{\text{H}/U}^{(\text{N})}$  the “contraction energy” (also known as double counting term). In Sec. 1.2.2 we deal with it. The chemical potential is corrected by

$$\mu \rightarrow \mu - nU \tag{1.3}$$

The non-local attraction further corrects  $\mu$ .

**Non-local attraction.** The non-local attraction is divided in two sectors, as in Eq. (??). From Eq. (??), its Hartree-like terms are:

$$\hat{H}_V \simeq \underbrace{-V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \hat{n}_{j\sigma} + \hat{n}_{i\sigma} \langle \hat{n}_{j\sigma} \rangle - \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\sigma} \rangle]}_{\text{s.s.}} - \underbrace{V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \hat{n}_{j\bar{\sigma}} + \hat{n}_{i\sigma} \langle \hat{n}_{j\bar{\sigma}} \rangle - \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\bar{\sigma}} \rangle]}_{\text{o.s.}} + (\text{all the rest}) \quad (1.4)$$

where “all the rest” collects all non-Hartree terms. Recalling the Ansatz of Eq. (1.1), we get

$$\hat{H}_V \simeq \underbrace{-nV \sum_{\langle ij \rangle} \sum_{\sigma} [\hat{n}_{j\sigma} + \hat{n}_{i\sigma}]}_{\text{s.s.}} - \underbrace{nV \sum_{\langle ij \rangle} \sum_{\sigma} [\hat{n}_{j\bar{\sigma}} + \hat{n}_{i\sigma}]}_{\text{o.s.}} - E_{\text{H/V}}^{(\text{N})} + (\text{all the rest})$$

with  $E_{\text{H/V}}^{(\text{N})}$  the normal state shift to energy brought by  $\hat{H}_V$ . Both sums above give a number operator. Note that we sum over NNs: each site is connected to  $z = 4$  sites. Including this combinatorial factor, we have

$$\hat{H}_V \simeq -2nzV \times \hat{N} - E_{\text{H/V}}^{(\text{N})} + (\text{all the rest}) \quad (1.5)$$

This accounts for the final Hartree shift of  $\mu$ ,

$$\mu \rightarrow \mu + 2znV \quad (1.6)$$

Considering the net shift to  $\mu$  due to both interactions by combining Eqns. (1.3), (1.6), we get the final RMP anticipated in Tab. 1.1,

$$\tilde{\mu} \equiv \mu + n(2zV - U) \quad (1.7)$$

This result will remain valid throughout all phases discussed in this text. For the AF phase, Sec. 2.4.1, the SDW character leaves this shift untouched. The SC phase, Sec. ??, we will discuss is inherently translational invariant, thus the computation will be the same as here.

### 1.2.2 Hartree contraction energy

The double counting terms accounting for energy shifts in the Hartree channel are, as anticipated:

$$\begin{aligned} E_{\text{H/U}}^{(\text{N})} &= \sum_i \langle \hat{n}_{i\downarrow} \rangle \langle \hat{n}_{i\uparrow} \rangle \\ &= L_x L_y \times n^2 U \end{aligned} \quad (1.8)$$

for the local repulsion and

$$\begin{aligned} E_{\text{H/V}}^{(\text{N})} &= -V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\sigma} \rangle + \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\bar{\sigma}} \rangle] \\ &= -2V \sum_{\langle ij \rangle} \sum_{\sigma} n^2 \\ &= -L_x L_y \times 2zn^2 V \end{aligned} \quad (1.9)$$

for the non-local attraction. In the last passage, we used Eq. (??) and spin degeneracy. The contraction energy is an extensive quantity. When computing total free energy density, we will use the contraction energy per site.

### 1.3 Fock effects: bare bands renormalization

Analysis of Fock terms will lead us to the effect that makes the normal phase interesting, when compared to the free Fermi gas on the square lattice. From Wick's decomposition of  $\hat{H}_V$ , the unique allowed Fock term comes from the same-spin sector. This selection rules is implied by the SU(2) symmetry of the normal phase. Then, from Eq. (??):

$$\hat{H}_V \simeq (\text{Hartree channel}) + V \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle \right] \quad (1.10)$$

Note the + sign in front of the displayed term: it originates from the - sign in Fock term of Eq. (??). A bond-wise hopping amplitude can be defined,

$$\tilde{t}_{ij\sigma} \equiv t - V \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle$$

The effective kinetic hamiltonian is given by

$$\begin{aligned} \hat{H}_{\tilde{t}} &= \hat{H}_t + V \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} + \text{h.c.} \right] \\ &= - \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \tilde{t}_{ij\sigma} \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} + \text{h.c.} \right] \end{aligned}$$

To proceed, it is useful to move to reciprocal space.

#### 1.3.1 Fock channel in the normal phase: analytic derivation

In reciprocal space, the effective hopping must be transformed as well. Consider the Fourier Transform  $\mathcal{F}$  given in Eq. (??), applied to the displayed part of Eq. (1.10),

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle \right] \\ \stackrel{\mathcal{F}}{=} \frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}, \mathbf{k}'} \sum_{\sigma} [\cos(\delta k_x) + \cos(\delta k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} - E_{\text{F}/V}^{(\text{N})} \end{aligned} \quad (1.11)$$

Here, the 2 prefactor comes from recognizing that the first two operators in square brackets in the first line generate identical contributions to the full sum (as is easy to see by performing trivial variables changes); the double counting energy shift is given by

$$E_{\text{F}/V}^{(\text{N})} \equiv \frac{V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}, \mathbf{k}'} \sum_{\sigma} [\cos(\delta k_x) + \cos(\delta k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \rangle \langle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} \rangle \quad (1.12)$$

Up to this point, this derivation is general and will be re-used in next chapters. Here the specificity of the physical phase settles in: if we assume the normal state to be a free degenerate Fermi gas with renormalized bands  $\tilde{\epsilon}_{\mathbf{k}}$ , we get


$$\langle \hat{c}_{\mathbf{k}_1\sigma_1}^\dagger \hat{c}_{\mathbf{k}_2\sigma_2} \rangle = \delta_{\mathbf{k}_1=\mathbf{k}_2} \delta_{\sigma_1=\sigma_2} f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \quad (1.13)$$

being  $f$  the Fermi-Dirac distribution,

$$f(\epsilon; \beta, \mu) \equiv \frac{1}{e^{\beta(\epsilon-\mu)} + 1}$$

It follows that Eq. (1.11) becomes

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle \right] \\ \stackrel{\mathcal{F}}{=} \frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}+\mathbf{k}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}-\mathbf{k}\sigma} - E_{\text{F}/V}^{(\text{N})} \end{aligned} \quad (1.14)$$

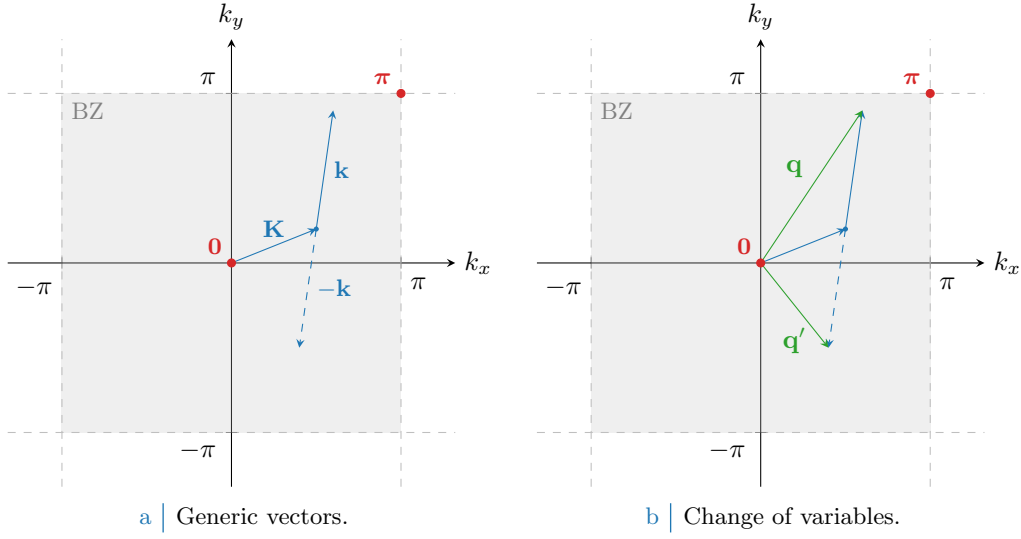

**Figure 1.1** Representation of the variable change employed to pass from Eq. (1.14) to (1.15). In Fig. 1.1a generic vectors are considered, cycling over all values of  $\mathbf{K}, \mathbf{k} \in \text{BZ}$ . In Fig. 1.1b is depicted the variables change to the new vectors  $\mathbf{q}, \mathbf{q}'$ .

since the only contribution comes from  $\mathbf{k}' = -\mathbf{k}$ .

Let now  $\mathbf{q} \equiv \mathbf{K} + \mathbf{k}$ ,  $\mathbf{q}' \equiv \mathbf{K} - \mathbf{k}$ . A representation of this variables change is given in Fig. 1.1. Being for  $\ell = x, y$

$$\begin{aligned} \delta q_\ell &\equiv q_\ell - q'_\ell \\ &= (K_\ell + k_\ell) - (K_\ell - k_\ell) \\ &= 2k_\ell \end{aligned}$$

we reduce Eq. (1.11) to

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} &\left[ \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle \right] \\ &\stackrel{\mathcal{F}}{=} \frac{2V}{L_x L_y} \sum_{\mathbf{q}, \mathbf{q}'} \sum_{\sigma} [\cos(\delta q_x) + \cos(\delta q_y)] \langle \hat{c}_{\mathbf{q}\sigma}^\dagger \hat{c}_{\mathbf{q}\sigma} \rangle \hat{c}_{\mathbf{q}'\sigma}^\dagger \hat{c}_{\mathbf{q}'\sigma} - E_{\text{F}/V}^{(\text{N})} \end{aligned} \quad (1.15)$$

Recall now the result of the symmetry channels decomposition of Eq. (??),

$$\cos(\delta q_x) + \cos(\delta q_y) = \frac{1}{2} \sum_{\gamma} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} \quad \text{for } \gamma \in \{s^*, p_x, p_y, d_{x^2-y^2}\}$$

Thanks to this handy property, we reduce Eq. (1.15) to

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} &\left[ \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^\dagger \hat{c}_{i\sigma} \rangle \right] \\ &\stackrel{\mathcal{F}}{=} \sum_{\gamma, \sigma} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} u_{\mathbf{q}\sigma} \right] \times V \sum_{\mathbf{q}' \in \text{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} \hat{c}_{\mathbf{q}'\sigma}^\dagger \hat{c}_{\mathbf{q}'\sigma} - E_{\text{F}/V}^{(\text{N})} \end{aligned} \quad (1.16)$$

where we defined the EV:

$$u_{\mathbf{q}\sigma} \equiv \langle \hat{c}_{\mathbf{q}\sigma}^\dagger \hat{c}_{\mathbf{q}\sigma} \rangle \quad u_{\mathbf{q}\sigma}^* = u_{\mathbf{q}\sigma}^* \quad (1.17)$$

The numeric value of  $u_{\mathbf{q}\sigma}$  is given by the Fermi-Dirac distribution, but leaving it implicit we can re-use this computation later. Let  $u_{\sigma}^{(\gamma)}$  be its  $\gamma$ -wave component,

$$u_{\sigma}^{(\gamma)} = \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{c}_{\mathbf{q}\sigma}^\dagger \hat{c}_{\mathbf{q}\sigma} \rangle$$

| Symmetry            | Self-consistency equation                                                                                                                  | Graph   |
|---------------------|--------------------------------------------------------------------------------------------------------------------------------------------|---------|
| $s^*$ -wave         | $u^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$ | Fig. ?? |
| $d_{x^2-y^2}$ -wave | $u^{(d)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x - \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$   | Fig. ?? |

Table 1.2 | Symmetry resolved self-consistency equations for the harmonics of  $u_{\mathbf{k}}$ .

The bare bands  $\epsilon_{\mathbf{k}}$  are  $s^*$ -wave symmetric,

$$\epsilon_{\mathbf{k}} = -2t(\cos k_x + \cos k_y) = -4t\varphi_{\mathbf{k}}^{(s^*)}$$

We used one function of those listed in Tab. ???. The renormalised bands  $\tilde{\epsilon}_{\mathbf{k}}$  can exhibit a more complex symmetry. In the normal phase inversion symmetry is unbroken, thus

$$u_{\mathbf{q}\sigma} = u_{-\mathbf{q}\sigma}$$

It follows that antisymmetric harmonics are zero,

$$u_{\sigma}^{(p\ell)} = 0 \quad \text{for } \ell \in \{x, y\}$$

The remaining  $s^*$  and  $d$  symmetries give legitimate HFPs with the respective self-consistency equations, reported in Tab. 1.2. Spin index is omitted due to spin degeneracy.

The two HFPs  $u_{\sigma}^{(s^*)}$  and  $u_{\sigma}^{(d)}$  are in general non-zero, since we are allowing for  $C_4 \xrightarrow{\text{SSB}} C_2$ . Note that when imposing  $C_4$  invariance the  $u_{\sigma}^{(d)}$  HFP vanishes, while in general  $u_{\sigma}^{(s^*)}$  is non-zero. From these considerations Eq. (1.16) becomes

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \langle \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^{\dagger} \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^{\dagger} \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^{\dagger} \hat{c}_{i\sigma} \rangle \right] \\ \stackrel{\mathcal{F}}{=} V \sum_{\mathbf{q} \in \text{BZ}} \sum_{\sigma} \left[ u_{\sigma}^{(s^*)} \varphi_{\mathbf{q}}^{(s^*)*} + u_{\sigma}^{(d)} \varphi_{\mathbf{q}}^{(d)*} \right] \hat{c}_{\mathbf{q}\sigma}^{\dagger} \hat{c}_{\mathbf{q}\sigma} - E_{\text{F}/V}^{(N)} \end{aligned} \quad (1.18)$$

Let

$$\tilde{\epsilon}_{\mathbf{k}\sigma} \equiv \epsilon_{\mathbf{k}\sigma} + u_{\sigma}^{(s^*)} V (\cos k_x + \cos k_y) + u_{\sigma}^{(d)} V (\cos k_x - \cos k_y) \quad (1.19)$$

This equation defines the bands renormalisation anticipated in Tab. 1.1, and is actually spin-independent. The fact that we have both  $s^*$  and a  $d$ -wave components introduces an anisotropy that is discussed in next section. However, we anticipate here that, as will result from Sec. 1.5.2, the  $d$ -wave harmonic will be suppressed. For now we keep this component ignoring these anticipations.

### 1.3.2 Fock contraction energy

Finally, let us derive the Fock contraction energy by expanding Eq. (1.12):

$$\begin{aligned} E_{\text{F}/V}^{(N)} &= \frac{V}{L_x L_y} \sum_{\mathbf{q}, \mathbf{q}'} \sum_{\sigma} [\cos(\delta q_x) + \cos(\delta q_y)] \langle \hat{c}_{\mathbf{q}\sigma}^{\dagger} \hat{c}_{\mathbf{q}'\sigma} \rangle \langle \hat{c}_{\mathbf{q}\sigma}^{\dagger} \hat{c}_{\mathbf{q}'\sigma} \rangle \\ &= L_x L_y \times \frac{V}{2} \sum_{\gamma, \sigma} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} u_{\mathbf{q}\sigma} \right] \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q}' \in \text{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} u_{\mathbf{q}'\sigma}^* \right] \\ &= L_x L_y \times \frac{V}{2} \sum_{\sigma} \left[ |u_{\sigma}^{(s^*)}|^2 + |u_{\sigma}^{(d)}|^2 \right] \end{aligned} \quad (1.20)$$

This expression gives the Fock contraction energy coming from the  $\hat{H}_V$  operator. The squared spectral amplitude of  $u_{\mathbf{k}\sigma}$  here is summed, and contributes to contraction energy linearly in  $V$ . This suggests that a mixed-symmetry band could be energetically preferred.



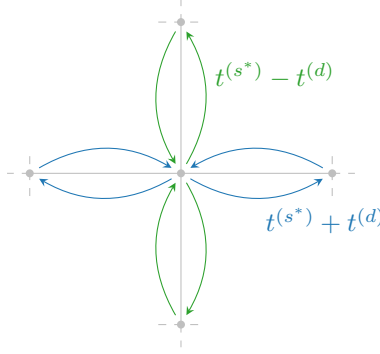


Figure 1.2 | Graphic rendition of anisotropic hopping, with a  $s^*$ -wave component (symmetric by  $\pi/2$  rotations) and a  $d$ -wave component (antisymmetric).

### 1.3.3 Nematicity: extending hopping to $d$ -wave bands

For the normal phase, there is no reason to expect nematic effects, nor to exclude them. They are observed in superconducting phase [23]. Thus, we allow the possibility.

From Tabs. ?? and ?? we can inverse-Fourier transform the form factors to get the full effective hopping,

$$\tilde{t}_{ij\sigma} = \sum_{\gamma \in \{s^*, d\}} t_{\sigma}^{(\gamma)} \varphi_{ij}^{(\gamma)}$$

with

$$t_{\sigma}^{(s^*)} = t - \frac{u_{\sigma}^{(s^*)} V}{2} \quad t_{\sigma}^{(d)} = -\frac{u_{\sigma}^{(d)} V}{2}$$

This is what we intend for “nematic effects”. The possibility that planar rotational symmetry is broken in such a way that the kinetic operators in  $x$  and  $y$  directions differ. A schematics of anisotropic hopping is given in Fig. 1.2: for each bond linking two sites, the hopping parameter can be a positive or negative combination of the two components, whether the link direction is vertical or horizontal. The solution needs to be invariant under exchange  $x \leftrightarrow y$ , thus the actual SSB is  $C_4 \xrightarrow{\text{SSB}} C_2/\mathbb{Z}_2$ .

The fact that hopping is here anisotropic does not break full translational invariance  $T_1^{(x)} \otimes T_1^{(y)}$ . Imposing a free degenerate Fermi gas ground state in Eq. (1.13) leads to a uniform density. This is proven by Fourier-transforming the site number operator according to the convention of Eq. (??),

$$\hat{c}_{\mathbf{r}\sigma}^\dagger \hat{c}_{\mathbf{r}\sigma} \stackrel{\mathcal{F}}{=} \frac{1}{L_x L_y} \sum_{\mathbf{k}, \mathbf{k}'} e^{i(\mathbf{k}-\mathbf{k}') \cdot \mathbf{r}} \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}'\sigma}$$

Then the on-site density EV is

$$\langle \hat{n}_{\mathbf{r}\sigma} \rangle = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} f(\epsilon_{\mathbf{k}}; \beta, \tilde{\mu})$$

A perfectly degenerate Fermi gas is always translational invariant and thus cannot exhibit non-uniform symmetry. The fact that hopping is allowed to be anisotropic does not interfere with that.

Note that for null HFPs,

$$u_{\sigma}^{(s^*)} = 0 \quad u_{\sigma}^{(d)} = 0$$

we have, recalling Tab. ??:

$$\tilde{t}_{\mathbf{r}\mathbf{r}'\sigma} = \frac{t}{2} \left[ \delta_{\mathbf{r}'=\mathbf{r}+\underline{x}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{x}} + \delta_{\mathbf{r}'=\mathbf{r}+\underline{y}} + \delta_{\mathbf{r}'=\mathbf{r}-\underline{y}} \right]$$

The fact that  $t/2$  appears here instead of  $t$  is a consequence of the equivalence:

$$-t \sum_{\langle ij \rangle} \sum_{\sigma} \left[ \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} + \text{h.c.} \right] = -\frac{t}{2} \sum_{i,j \in \mathcal{S}} \sum_{\sigma} \left[ \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} + \text{h.c.} \right]$$

where we including a prefactor that corrects double-counting. The RMP  $\tilde{t}_{ij\sigma}$  must be interpreted like the right-hand side of the above equation, with the kinetic operator becoming:

$$\hat{H}_{\tilde{t}} \equiv -\frac{1}{2} \sum_{i,j \in \mathcal{S}} \sum_{\sigma} \left[ \tilde{t}_{ij\sigma} \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} + \text{h.c.} \right]$$

To limit the sum to NNs is a matter of the symmetry structure of the function  $\tilde{t}_{ij\sigma}$ .

We can define the direction-dependent hopping as

$$\tilde{t}^{(x)} \equiv t - \frac{u^{(s^*)} - u^{(d)}}{2} V \quad (1.21)$$

$$\tilde{t}^{(y)} \equiv t - \frac{u^{(s^*)} + u^{(d)}}{2} V \quad (1.22)$$

Both components depend linearly on  $V$ . The HFP  $u^{(s^*)}$  is a measure of the direction-averaged hopping shift with respect to  $V$ , while  $u^{(d)}$  measures the anisotropy,

$$u^{(s^*)} = \frac{(t - \tilde{t}^{(x)}) + (t - \tilde{t}^{(y)})}{V} \quad u^{(d)} = \frac{\tilde{t}^{(y)} - \tilde{t}^{(x)}}{V}$$

This discussion is general, and not specific to the normal phase. In next chapters we will interpret phase renormalisation as in this section.

## 1.4 Normal free energy density

In the end, we want to compare phases. Thus we need a way to extract the free energy density of the approximated ground-state for each phase. The procedure sketched here will be re-used in next chapters. Let

$$f_{\text{MFT}}^{(\text{N})} \equiv \frac{F_{\text{MFT}}^{(\text{N})}}{L_x L_y}$$

being  $F_{\text{MFT}}$  the total free energy. Consider the complete hamiltonian

$$\hat{H} - \mu \hat{N} \simeq \sum_{\mathbf{k}, \sigma} \tilde{c}_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{k}\sigma} + E_c^{(\text{N})} - \tilde{\mu} \hat{N}$$

where  $E_c^{(\text{N})}$  is the (negative) total contraction energy for the normal phase,

$$E_c^{(\text{N})} \equiv - \left[ E_{\text{H}/U}^{(\text{N})} + E_{\text{H}/V}^{(\text{N})} + E_{\text{F}/V}^{(\text{N})} \right]$$

having included the various contraction energies from Eqns. (1.8), (1.9) and (1.20).

Let us now take together all terms. From now on, we will omit spin index  $\sigma$ , making use of the always present  $\mathbb{Z}_2$  spin inversion symmetry discussed in Sec. 1.1. For a free Fermi gas, the free energy density is made of four contributions:

1. The free particles ground state energy density,

$$e_g^{(\text{N})} = \frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

2. The contraction energy density,

$$\begin{aligned} e_c^{(\text{N})} &\equiv \frac{E_c^{(\text{N})}}{L_x L_y} \\ &= -n^2 U + V \left[ 2zn^2 - |u^{(s^*)}|^2 - |u^{(d)}|^2 \right] \end{aligned}$$

3. The entropic contribution to free energy

$$e_s^{(N)} \equiv -Ts$$

with  $T = 1/k_B\beta$  and  $s$  the free Fermi gas entropy density for a single spin sector [29],

$$s = -\frac{k_B}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} [(1 - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})) \ln(1 - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})) + f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \ln f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})] \quad (1.23)$$

We use the identity:

$$\ln \left( 1 - \frac{1}{e^x + 1} \right) = x + \ln \left( \frac{1}{e^x + 1} \right)$$

and, substituting  $x = \beta(\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu})$ , reduce the above expression to:

$$s = -\frac{k_B}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \left[ \ln(1 - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})) + f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \ln f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - \beta(\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu})f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \ln f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \right]$$

Second and fourth terms cancel out, and multiplying by  $-2T$  (taking care of spin degeneracy) we have

$$e_s^{(N)} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \ln(1 - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})) - \frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\tilde{\epsilon}_{\mathbf{k}} - \tilde{\mu})f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

4. The chemical potential correction

$$e_n^{(N)} = \mu n$$

Note here that we are using the “physical” value of  $\mu$ , not its RMP counterpart  $\tilde{\mu}$ . The reason for this is discussed in Sec. ??.

Thus, composing everything

$$\begin{aligned} f_{\text{MFT}}^{(N)} &\equiv e_g^{(N)} + e_c^{(N)} + e_s^{(N)} + e_n^{(N)} \\ &= \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \ln(1 - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})) - V \left[ |u^{(s^*)}|^2 + |u^{(d)}|^2 \right] + [\mu + n(2zV - U)] n \end{aligned}$$

In Sec. ?? we argued that our iterative scheme computes  $\tilde{\mu}$ , not  $\mu$ . Using Eq. (1.7), we see

$$\mu + n(2zV - U) = \tilde{\mu}$$

Then, the final expression is:

$$f_{\text{MFT}}^{(N)} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \ln(1 - f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})) - V \left[ |u^{(s^*)}|^2 + |u^{(d)}|^2 \right] + \tilde{\mu} n \quad (1.24)$$


including all effects.

## 1.5 Theoretical constraints on the normal phase HFPs

Within this section we discuss some theoretical constraints on the two HFPs of the normal phase. The discussion is divided in two parts: first we consider the simpler case of unviolated  $C_4$  symmetry, then we move to anisotropic hopping and  $C_4 \xrightarrow{\text{SSB}} C_2$ .

Before starting, it is useful to spend a few words on the spatial structure of a mixed  $s^* \otimes d$ -wave band. Let in general for notational simplicity

$$\tilde{\epsilon}_{\mathbf{k}} = \epsilon^{(s^*)}(\cos k_x + \cos k_y) + \epsilon^{(d)}(\cos k_x - \cos k_y)$$

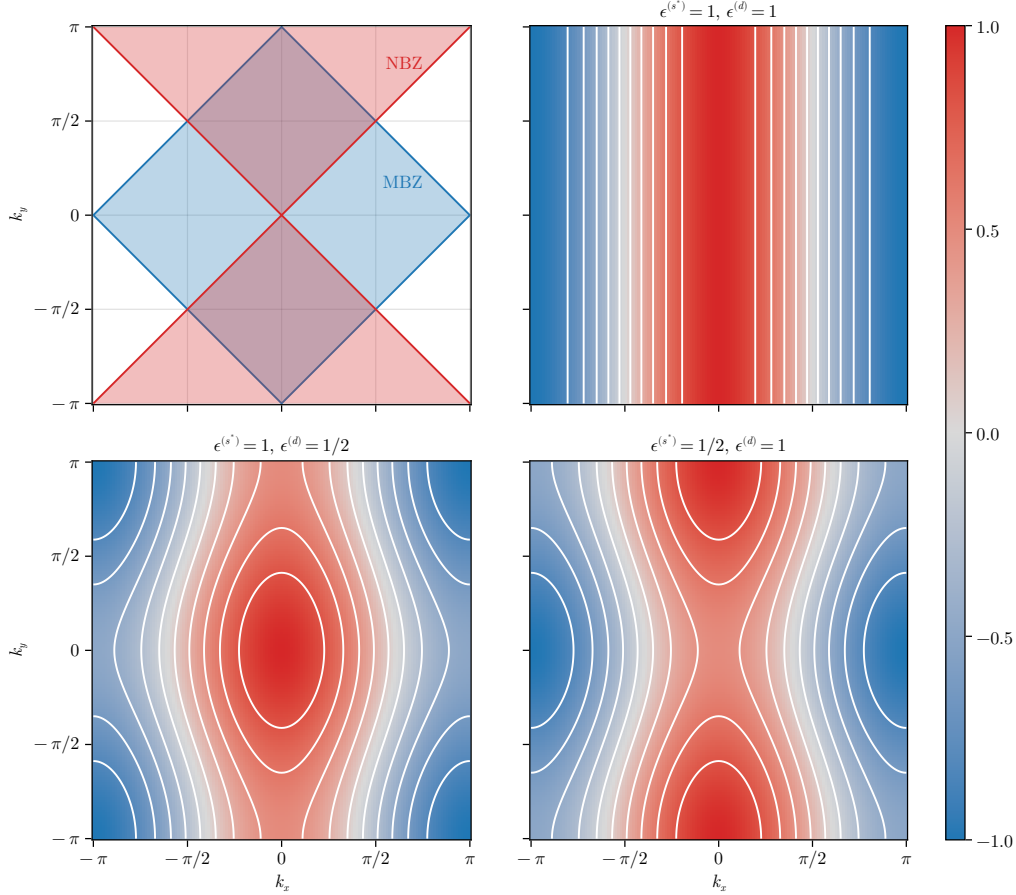

**Figure 1.3** | Theoretical representation of mixed-symmetry nematic bands for the normal phase. The white contour represent level lines. In top-left panel, the MBZ and NBZ are depicted. While these plots only account for positive-defined components, in text is described how to map each one on its counterpart with different sign.

It is the balance between the two components  $\epsilon^{(s^*)}$  and  $\epsilon^{(d)}$  that gives the main features of the renormalised band. Consider the  $s^*$ -wave and  $d$ -wave structure factors already presented in Fig. ??, and define the Magnetic Brillouin Zone (MBZ) and Nematic Brillouin Zone (NBZ) as follows:

$$\text{MBZ} \equiv \left\{ \mathbf{k} \in \text{BZ} \mid \varphi_{\mathbf{k}}^{(s^*)} \geq 0 \right\} \quad (1.25)$$

$$\text{NBZ} \equiv \left\{ \mathbf{k} \in \text{BZ} \mid \varphi_{\mathbf{k}}^{(d)} \geq 0 \right\} \quad (1.26)$$

represented in the top-left panel of Fig. 1.3. The reason for the name of the MBZ will be clear in Chap. 2. In the rest of the panels of Fig. 1.3 are reported examples of mixed symmetry bands, for positive components. The respective opposite sign plots are obtained by the following rules:

$$\epsilon^{(s^*)} < 0 \quad \text{and} \quad \epsilon^{(d)} < 0 \quad \implies \quad \text{Invert colors in Fig. 1.3}$$

$$\epsilon^{(s^*)} > 0 \quad \text{and} \quad \epsilon^{(d)} < 0 \quad \implies \quad \text{Rotate plots by } \pi/2 \text{ in Fig. 1.3}$$


$$\epsilon^{(s^*)} < 0 \quad \text{and} \quad \epsilon^{(d)} > 0 \quad \implies \quad \text{Rotate plots by } \pi/2 \text{ and invert colors in Fig. 1.3}$$

Let us focus on the MBZ and the NBZ. Starting from the intersections of the two zones, both can be factored in two sectors of interest,

$$\text{MBZ} = \mathcal{A} \cup \mathcal{B} \quad \text{NBZ} = \mathcal{A} \cup \mathcal{C}$$

being, accordingly to Fig. 1.4,

$$\mathcal{A} \equiv \mathcal{A}_1 \cup \mathcal{A}_2 \quad \mathcal{B} \equiv \mathcal{B}_1 \cup \mathcal{B}_2 \quad \mathcal{C} \equiv \mathcal{C}_1 \cup \mathcal{C}_2$$

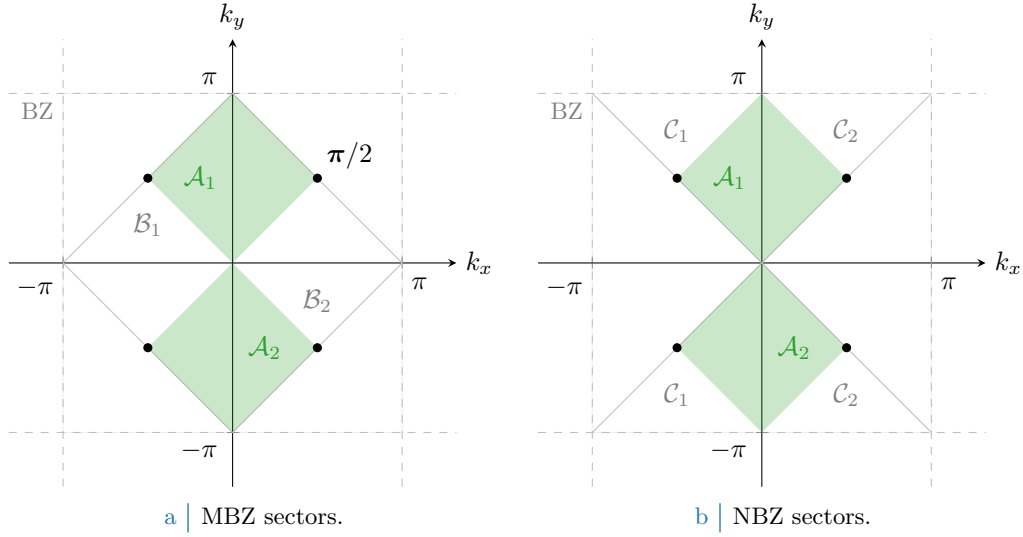

**Figure 1.4** | Depiction of the sectors composing the MBZ (Fig. 1.4a) and the NBZ (Fig. 1.4b), based on the divisions shown in the top-left panel of Fig. 1.3. The full green zone composes  $\mathcal{A}$ , the region where both the  $s^*$ -wave and  $d$ -wave structure factors are positive defined; its MBZ complementary white counterpart in the left panel gives  $\mathcal{B}$ , for which the  $s^*$ -wave structure factors is positive-definite while the  $d$ -wave is negative. Similarly the NBZ complementary white counterpart in the right panel gives  $\mathcal{C}$ , for which signs are exchanged. The black dots, at the contours intersection, are band nodes.

These domains satisfy:

$$\mathcal{A} \equiv \left\{ \mathbf{k} \in \text{BZ} \mid \varphi_{\mathbf{k}}^{(s^*)} \geq 0 \wedge \varphi_{\mathbf{k}}^{(d)} \geq 0 \right\} \quad (1.27)$$

$$= \text{MBZ} \cap \text{NBZ}$$

$$\mathcal{B} \equiv \left\{ \mathbf{k} \in \text{BZ} \mid \varphi_{\mathbf{k}}^{(s^*)} \geq 0 \wedge \varphi_{\mathbf{k}}^{(d)} \leq 0 \right\} \quad (1.28)$$

$$= \text{MBZ} \setminus \text{NBZ}$$

$$\mathcal{C} \equiv \left\{ \mathbf{k} \in \text{BZ} \mid \varphi_{\mathbf{k}}^{(s^*)} \leq 0 \wedge \varphi_{\mathbf{k}}^{(d)} \geq 0 \right\} \quad (1.29)$$

$$= \text{NBZ} \setminus \text{MBZ}$$

and will be used later on. Whatever the shape of the mixed band, the following equation always holds

$$|k_x| = \frac{\pi}{2} \quad \text{and} \quad |k_y| = \frac{\pi}{2} \quad \implies \quad \tilde{\epsilon}_{(k_x, k_y)} = 0$$

since only cosines are involved. This identifies four node points, represented as black dots in Fig. 1.4.

### 1.5.1 Constraints in presence of a robust $C_4$ symmetry and bands shrinking

Consider the simpler situation where  $C_4$  symmetry is imposed. This implies that the renormalised bands are

$$\tilde{\epsilon}_{\mathbf{k}} \equiv (u^{(s^*)}V - 2t)(\cos k_x + \cos k_y)$$

with a single self-consistency equation

$$u^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

The following chain of deductions leads us to a constraint on the possible values of  $u^{(s^*)}$ :

1. For  $t > 0$ , there is no self-consistent solution admitting  $u^{(s^*)} \leq 0$ . Let us prove this: suppose instead  $u^{(s^*)} \leq 0$ . For any function  $g_{\mathbf{k}}$  defined on the BZ:

$$\sum_{\mathbf{k} \in \text{BZ}} g_{\mathbf{k}} = \sum_{\mathbf{k} \in \text{MBZ}} [g_{\mathbf{k}} + g_{\mathbf{k}+\boldsymbol{\pi}}]$$

where we defined the vector  $\boldsymbol{\pi} \equiv (\pi, \pi)$ . The self-consistency equation thus reads

$$\begin{aligned} u^{(s^*)} &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y) [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) + f(\tilde{\epsilon}_{\mathbf{k}+\boldsymbol{\pi}}; \beta, \tilde{\mu})] \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y) [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})] \end{aligned} \quad (1.30)$$

having we used the antisymmetry of  $s^*$ -wave functions by  $\boldsymbol{\pi}$  shifts. Now, if  $u^{(s^*)} \leq 0$  the renormalised band  $\tilde{\epsilon}_{\mathbf{k}}$  is negative inside the MBZ and positive outside, implying

$$\forall \mathbf{k} \in \text{MBZ} \quad : \quad f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \geq f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

the equality only being satisfied on the MBZ contour. Then, since inside the MBZ it holds by definition  $\cos k_x + \cos k_y \geq 0$ , the above equations imply

$$u^{(s^*)} \leq 0 \quad \implies \quad u^{(s^*)} \geq 0$$

To exclude the possibility of  $u^{(s^*)} = 0$ , it suffices to notice that from the argument above such a situation only arises when the MBZ contour degenerates to the entirety of the MBZ itself – which is, when the band is flat. But that cannot be the case for  $u^{(s^*)} = 0$ , as long as  $t > 0$ . Thus we have proven that

$$u^{(s^*)} > 0$$

2. For  $t > 0$ , there is no self-consistent solution admitting  $u^{(s^*)} \geq 2t/V$ . We proceed exactly as did for the previous point, up to the passage:

$$u^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y) [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})]$$

Now, if  $u^{(s^*)} \geq 2t/V$  this means the prefactor in front of the renormalised bands is positive. Then  $\tilde{\epsilon}_{\mathbf{k}}$  is positive inside the MBZ and negative outside, implying

$$\forall \mathbf{k} \in \text{MBZ} \quad : \quad f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \leq f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

thus we have

$$u^{(s^*)} \geq 2t/V \quad \implies \quad u^{(s^*)} \leq 0$$

which is absurd. Thus

$$u^{(s^*)} < 2t/V$$

Collecting the two points above, we have the constraint on  $u^{(s^*)}$

$$C_4 \quad \implies \quad 0 < u^{(s^*)} < 2t/V \quad (1.31)$$


The effective hopping is smaller than the original hopping. We can denominate this net effect “bands shrinking”.

### 1.5.2 Natural suppression of nematicity within $C_2/\mathbb{Z}_2$ symmetry

Let us extend the arguments above to a weaker symmetry, allowing for

$$C_4 \xrightarrow{\text{SSB}} C_2/\mathbb{Z}_2$$

We work with the full, anisotropic band of Eq. (1.19). From the following chain of deductions we conclude that  $C_4$  is not broken:

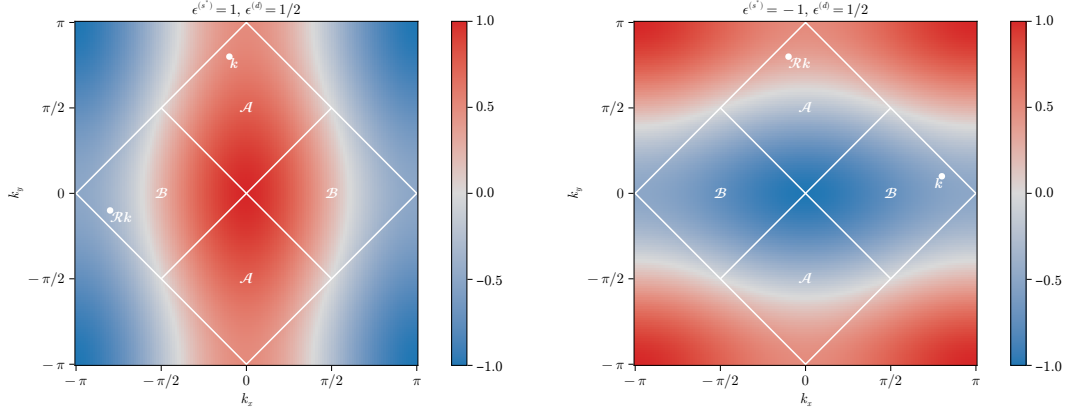

a | Same-sign mixed bands.

b | Opposite-sign mixed bands.

Figure 1.5 | Theoretical example of bands with  $u^{(s^*)} > 2t/V$ ,  $u^{(d)} > 0$  (top-left) and  $u^{(s^*)} < 0$ ,  $u^{(d)} > 0$  (top right). Two example points are reported, connected by a  $\pi/2$  rotation as given in Eqns. (1.34), (1.32).

1. Let for instance

$$u^{(s^*)} \geq 2t/V > 0 \quad u^{(d)} > 0 \quad \implies \quad \epsilon^{(s^*)} \geq 0 \quad \epsilon^{(d)} > 0$$

In Fig. 1.5a an example band is shown for  $\epsilon^{(s^*)} = 1$ ,  $\epsilon^{(d)} = 1/2$ . Note that if  $u^{(s^*)} = 2t/V$ , the renormalised band is purely  $d$ -wave since  $\epsilon^{(s^*)} = 0$ .

Recall Eq. (1.30), and separate in two sums over  $\mathcal{A}$  and  $\mathcal{B}$ :

$$\begin{aligned} u^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \mathcal{A}} (\cos k_x + \cos k_y) [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})] \\ + \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \mathcal{B}} (\cos k_x + \cos k_y) [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})] \end{aligned}$$

Consider the sum over  $\mathcal{B}$ . Looking at the bottom-left panel of Fig. 1.3, such a region contains nodal curves across which bands change sign. Let  $\mathcal{R}$  be the clockwise  $\pi/2$  rotation: then, any point in  $\mathcal{B}$  can be seen as the rotation of a point in  $\mathcal{A}$

$$\forall \mathbf{k}' \in \mathcal{B} \quad \exists \quad \mathbf{k} \in \mathcal{A} \mid \mathbf{k}' = \mathcal{R}\mathbf{k} \quad (1.32)$$

A graphical rendition of this idea is given in Fig. 1.5a. Then we can rewrite  $u^{(s^*)}$  as a single sum over  $\mathcal{A}$ ,

$$\begin{aligned} u^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \mathcal{A}} (\cos k_x + \cos k_y) \\ \times [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) + f(\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu})] \quad (1.33) \end{aligned}$$

From Eq. (1.27),  $\forall \mathbf{k} \in \mathcal{A}$  the form factors  $\cos k_x \pm \cos k_y$  are positive by construction. By hypothesis  $\epsilon^{(s^*)} \geq 0$  and  $\epsilon^{(d)} > 0$ . Hence:

$$\begin{aligned} \forall \mathbf{k} \in \mathcal{A} \quad : \quad \tilde{\epsilon}_{\mathbf{k}} &= \overbrace{\epsilon^{(s^*)} (\cos k_x + \cos k_y)}^{\geq 0} + \overbrace{\epsilon^{(d)} (\cos k_x - \cos k_y)}^{\geq 0} \\ \tilde{\epsilon}_{\mathcal{R}\mathbf{k}} &= \overbrace{\epsilon^{(s^*)} (\cos k_x + \cos k_y)}^{\geq 0} - \overbrace{\epsilon^{(d)} (\cos k_x - \cos k_y)}^{\geq 0} \end{aligned}$$

Summing the two equations above we have:

$$\forall \mathbf{k} \in \mathcal{A} \quad : \quad \tilde{\epsilon}_{\mathbf{k}} + \tilde{\epsilon}_{\mathcal{R}\mathbf{k}} \geq 0$$

thus  $\tilde{\epsilon}_{\mathbf{k}} \geq -\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}$ . The Fermi-Dirac distribution is monotonically descendent. Then:

$$\forall \mathbf{k} \in \mathcal{A} \quad : \quad \begin{aligned} f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) &\leq f(-\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu}) \\ f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) &\geq f(\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu}) \end{aligned}$$

This condition, inserted in Eq. (1.33), leads to an absurd:

$$u^{(s^*)} \geq 2t/V \quad u^{(d)} > 0 \quad \implies \quad u^{(s^*)} \leq 0$$

2. An identical argument, exchanging the roles of  $\mathcal{A}$  and  $\mathcal{B}$ , can be carried out to show that

$$u^{(s^*)} \geq 2t/V > 0 \quad u^{(d)} < 0 \quad \implies \quad u^{(s^*)} \leq 0$$

3. The two points above imply that it is possible to have  $u^{(s^*)} \geq 2t/V$  if and only if  $u^{(d)} = 0$ . But from Sec. 1.5.1, we conclude that the upper boundary  $u^{(s^*)} < 2t/V$  always holds.

4. Let for instance

$$u^{(s^*)} \leq 0 \quad u^{(d)} > 0 \quad \implies \quad \epsilon^{(s^*)} < 0 \quad \epsilon^{(d)} > 0$$

In Fig. 1.5b an example band is shown for  $\epsilon^{(s^*)} = -1$ ,  $\epsilon^{(d)} = 1/2$ .

Proceed as for the first point. Similarly to Eq. (1.32), Any point in  $\mathcal{A}$  can be obtained by rotating some point in  $\mathcal{B}$ ,

$$\forall \mathbf{k}' \in \mathcal{A} \quad \exists \quad \mathbf{k} \in \mathcal{B} \mid \mathbf{k}' = \mathcal{R}\mathbf{k} \quad (1.34)$$

An equation similar to Eq. (1.33) holds, the sum being performed over  $\mathcal{B}$

$$\begin{aligned} u^{(s^*)} &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \mathcal{B}} (\cos k_x + \cos k_y) \\ &\quad \times [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) + f(\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(-\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu})] \end{aligned} \quad (1.35)$$

From Eq. (1.28),  $\forall \mathbf{k} \in \mathcal{B}$  the form factor  $\cos k_x + \cos k_y$  is positive by construction; the form factor  $\cos k_x - \cos k_y$  is negative by construction. By hypothesis  $\epsilon^{(s^*)} < 0$  and  $\epsilon^{(d)} > 0$ . Hence:

$$\forall \mathbf{k} \in \mathcal{B} \quad : \quad \begin{aligned} \tilde{\epsilon}_{\mathbf{k}} &= \overbrace{\epsilon^{(s^*)} (\cos k_x + \cos k_y)}^{\leq 0} + \overbrace{\epsilon^{(d)} (\cos k_x - \cos k_y)}^{\leq 0} \\ \tilde{\epsilon}_{\mathcal{R}\mathbf{k}} &= \underbrace{\epsilon^{(s^*)} (\cos k_x + \cos k_y)}_{\leq 0} - \underbrace{\epsilon^{(d)} (\cos k_x - \cos k_y)}_{\leq 0} \end{aligned}$$

Summing the two equations above we have:

$$\forall \mathbf{k} \in \mathcal{B} \quad : \quad \tilde{\epsilon}_{\mathbf{k}} + \tilde{\epsilon}_{\mathcal{R}\mathbf{k}} \leq 0$$

thus  $\tilde{\epsilon}_{\mathbf{k}} \leq -\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}$ . The Fermi-Dirac distribution is monotonically descendent. Then:

$$\forall \mathbf{k} \in \mathcal{B} \quad : \quad \begin{aligned} f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) &\geq f(-\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu}) \\ f(-\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) &\leq f(\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu}) \end{aligned}$$

This condition, inserted in Eq. (1.33), leads to an absurd:

$$u^{(s^*)} \leq 0 \quad u^{(d)} > 0 \quad \implies \quad u^{(s^*)} > 0$$

5. can be carried out to show that

$$u^{(s^*)} \leq 0 \quad u^{(d)} < 0 \quad \implies \quad u^{(s^*)} > 0$$

6. The two points above imply that it is possible to have  $u^{(s^*)} \leq 0$  if and only if  $u^{(d)} = 0$ . But from Sec. 1.5.1, we conclude that the lower boundary  $u^{(s^*)} > 0$  always holds.



From the chain of derivations above, we can conclude self-consistently that also in the nematic structure the constraint of Eq. (1.31),

$$0 < u^{(s^*)} < 2t/V$$

holds. In the  $s^*$ -wave channel, partial breaking of rotational symmetry is not enough to modify the main effect identified under  $C_4$  symmetry, “bands shrinking”. What is missing is the behaviour of the  $d$ -wave channel when said effect takes place. Continuing the enumeration above,

7. Let  $0 < u^{(s^*)} < 2t/V$  and  $u^{(d)} > 0$ . Then  $\epsilon^{(d)} > 0$ . The self-consistency equation for  $u^{(d)}$  reads

$$\begin{aligned} u^{(d)} &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x - \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{NBZ}} (\cos k_x - \cos k_y) [f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) - f(\tilde{\epsilon}_{\mathcal{R}\mathbf{k}}; \beta, \tilde{\mu})] \end{aligned}$$

where we recognized, as is shown in Fig. 1.4b, that  $\text{BZ} \setminus \text{NBZ} = \mathcal{R}\text{NBZ}$ . It holds:

$$\forall \mathbf{k} \in \text{NBZ} \quad : \quad \begin{aligned} \tilde{\epsilon}_{\mathbf{k}} &= \epsilon^{(s^*)} (\cos k_x + \cos k_y) + \overbrace{\epsilon^{(d)} (\cos k_x - \cos k_y)}^{\geq 0} \\ \tilde{\epsilon}_{\mathcal{R}\mathbf{k}} &= \epsilon^{(s^*)} (\cos k_x + \cos k_y) - \underbrace{\epsilon^{(d)} (\cos k_x - \cos k_y)}_{\geq 0} \end{aligned}$$

thus  $\tilde{\epsilon}_{\mathcal{R}\mathbf{k}} < \tilde{\epsilon}_{\mathbf{k}}$ , and inserting this fact in the self-consistency equation above we get

$$0 < u^{(s^*)} < 2t/V \quad \text{and} \quad u^{(d)} > 0 \quad \implies \quad u^{(d)} < 0$$

which is absurd.

8. An identical argument, with inverted inequalities, can be carried out to show that

$$0 < u^{(s^*)} < 2t/V \quad \text{and} \quad u^{(d)} < 0 \quad \implies \quad u^{(d)} > 0$$

9. The two points above imply that it is possible to satisfy the constraint  $0 < u^{(s^*)} < 2t/V$  if and only if  $u^{(d)} = 0$ .

All the deductions above indicate that  $u^{(d)} = 0$  everywhere. Nematic effects are always absent,

$$0 < u^{(s^*)} < 2t/V \quad \text{and} \quad u^{(d)} = 0 \tag{1.36}$$

This is physically expected but non trivial. The normal phase does not break  $C_4$  and we can ignore  $u^{(d)}$  at all. In next section we identify the expected self-consistent value for  $u^{(s^*)}$ .

### 1.5.3 Expected dependence on $\delta$ at low temperature

We understood that  $u^{(d)} = 0$ . Moreover, the unique HFP  $u^{(s^*)}$  is independent of  $U$ , but in general it will depend in some way on the doping level. We work at low-temperature,  $\beta \rightarrow \infty$ . Consider the self-consistency equation of Tab. 1.2 as a function of temperature and chemical potential,

$$u^{(s^*)}(\beta, \tilde{\mu}) = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu})$$

in the zero-temperature limit, as long as the band is not flat, it holds

$$\lim_{\beta \rightarrow \infty} u^{(s^*)}(\beta, \tilde{\mu}) = \frac{1}{L_x L_y} \sum_{\epsilon_{\mathbf{k}} \leq \tilde{\mu}} (\cos k_x + \cos k_y)$$

Let  $\text{FS}(\delta)$  be the Fermi surface for a given doping level  $\delta$ . We denote with  $\text{Int}(\text{FS})$  be its internal part, the Fermi sea:

$$\begin{aligned}\text{FS} &= \{\mathbf{k} \in \text{BZ} \mid \tilde{\epsilon}_{\mathbf{k}} = \tilde{\mu}\} \\ \text{Int}(\text{FS}) &= \{\mathbf{k} \in \text{BZ} \mid \tilde{\epsilon}_{\mathbf{k}} \leq \tilde{\mu}\}\end{aligned}$$

At half filling, the Fermi surface coincides with the boundary of the MBZ:

$$\delta = 0 \quad \implies \quad \text{FS} = \partial\text{MBZ}$$

This is implied by the fact that renormalised bands are antisymmetric by  $\pi$  shifts,

$$\tilde{\epsilon}_{\mathbf{k}\sigma} = -\tilde{\epsilon}_{\mathbf{k}+\pi\sigma}$$

The portion of an  $s^*$ -wave band outside the MBZ is mirrored with respect to the portion inside the MBZ. This implies that half the states lie in the MBZ, half out.

At  $\delta > 0$  the FS expands in the region  $\text{BZ} \setminus \text{MBZ}$  where the form factor  $\cos k_x + \cos k_y$  becomes negative. This gives the self-consistency equation

$$\lim_{\beta \rightarrow \infty} u^{(s^*)}[\beta, \tilde{\mu}] \simeq \frac{1}{L_x L_y} \sum_{\epsilon_{\mathbf{k}} \leq 0} |\cos k_x + \cos k_y| - \frac{1}{L_x L_y} \sum_{0 < \epsilon_{\mathbf{k}} \leq \tilde{\mu}} |\cos k_x + \cos k_y|$$

which, being the sum of a positive and a negative term, is maximised whenever  $\tilde{\mu} = 0$ , at half filling. This holds as long as the band is not flat. Indeed, if the effective hopping is not zero, to rise the doping level means to

$$\delta_1 > \delta_2 \quad \implies \quad \text{Int}(\text{FS}_1) \subset \text{Int}(\text{FS}_2)$$

with obvious meaning of the notation. Using this property we conclude

$$\tilde{t} > 0 \quad \text{and} \quad \delta_1 > \delta_2 \quad \implies \quad \lim_{\beta \rightarrow \infty} u^{(s^*)}[\beta, \tilde{\mu}] \Big|_{\delta_1} < \lim_{\beta \rightarrow \infty} u^{(s^*)}[\beta, \tilde{\mu}] \Big|_{\delta_2}$$

This is the first expected behaviour of the self-consistent functional  $u^{(s^*)}$ : if there exists a region of parametric space where the shrinking effect is not strong enough to flatten the band, a rise in the doping level must lower  $u^{(s^*)}$ . Such a region must exist: at least all the segment ( $V = 0, \delta$ ) is included, since on said region of parametric space the model is just the common free electronic model.


Following this line of reasoning, we can extract the two low-temperature limits of  $u^{(s^*)}$  at half-filling and unitary filling.

1. At half-filling, the self-consistency equation reduces to

$$u^{(s^*)}[\beta, 0] \Big|_{\beta \gg 1} \simeq \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y)$$

In thermodynamic limit, performing integration on the MBZ shown in the top-left panel of Fig. 1.3:

$$\begin{aligned}\lim_{\beta \rightarrow \infty} u^{(s^*)}[\beta, 0] &\simeq \frac{1}{(2\pi)^2} \int_{-\pi}^{\pi} dk_y \int_{-\pi+|k_y|}^{\pi-|k_y|} dk_x \cos k_x + \frac{1}{(2\pi)^2} \int_{-\pi}^{\pi} dk_x \int_{-\pi+|k_x|}^{\pi-|k_x|} dk_y \cos k_y \\ &= \frac{1}{2\pi^2} \int_{-\pi}^0 dk_y \int_{-\pi-k_y}^{\pi+k_y} dk_x \cos k_x + \frac{1}{2\pi^2} \int_0^{\pi} dk_y \int_{-\pi+k_y}^{\pi-k_y} dk_x \cos k_x \\ &= \frac{1}{\pi^2} \int_{-\pi}^0 dk_y \sin(\pi + k_y) + \frac{1}{\pi^2} \int_0^{\pi} dk_y \sin(\pi - k_y) \\ &= \left(\frac{2}{\pi}\right)^2 \approx 0.405\end{aligned}\tag{1.37}$$

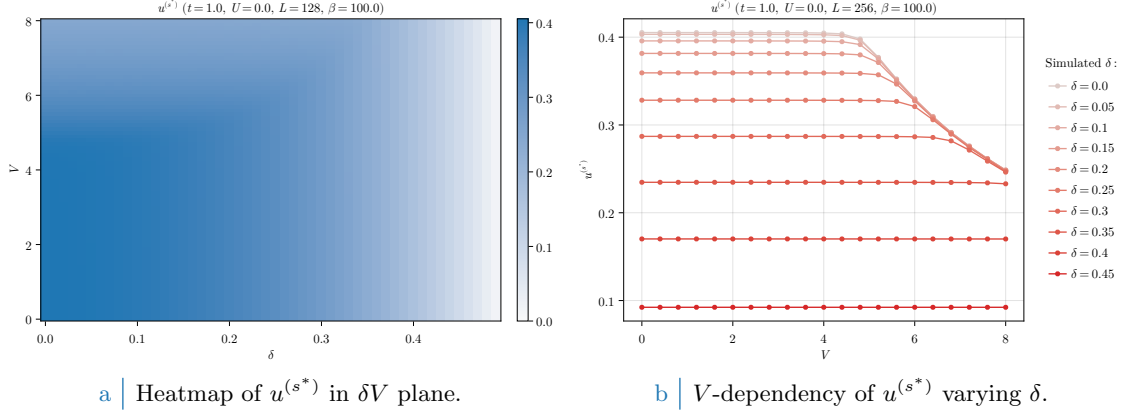

**Figure 1.6** | Plot of the self-consistent convergence values for the HFP  $u^{(s^*)}$  in the normal phase. To extract the data on the right side coarse-graining precision of the left-hand side data has been exchanged with higher lattice dimensions. As is evident, based on doping level  $u^{(s^*)}$  exhibits non-trivial regions of  $V$ -independence.

2. At unitary filling we have

$$\lim_{\beta \rightarrow \infty} u^{(s^*)} [\beta, 2\tilde{t}^{(s^*)}] = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) = 0$$

which vanishes due to the structure factor periodicity by  $\pi$ .

To summarise: around  $V = 0$ ,  $u^{(s^*)}$  is expected to descend monotonically from  $4/\pi^2$  to 0 at increasing doping.

## 1.6 Discussion of numeric results

In this section we present and discuss the numeric results, the physical relevance of the found phenomena and the boundaries of the algorithm. Let us start by sketching the algorithm used to determine self-consistently the mean-field structure of the normal phase in parameter space. For the normal phase, the HFPs “vector” defined in Sec. ?? has just one component:

$$\mathbf{v} = [u^{(s^*)}]$$

As before, we treat spin as a pure degeneracy. The only HFP is characterised by the first self-consistency equation of Tab. 1.2. The resulting model has two RMPs:

$$\begin{aligned} \tilde{t}_{ij} &\equiv \left( t - \frac{u^{(s^*)} V}{2} \right) \varphi_{ij}^{(s^*)} \\ \tilde{\mu} &\equiv \mu + n(2zV - U) \end{aligned}$$


the second one being only dependent on the model parameters and not on HFPs. Finally, the phase free energy is given by Eq. (1.24). The normal phase is completely independent of  $U$ . Because of this we present the results varying the other parameters, keeping everywhere  $U = 0$ . We ran simulations in the  $(V, \delta)$  plane, with the setup:

$$U = 0 \quad \Delta n = 10^{-2} \quad \Delta \mathbf{v} = [u^{(s^*)} : 5 \times 10^{-4}]$$

with  $\Delta \mathbf{v}$  the tolerance vector defined as in Sec. ??.

In Fig. 1.6a are reported the results obtained for the HFP  $u^{(s^*)}$  on a  $128 \times 128$  lattice and “low” temperature  $\beta = 100$ , varying the non-local attraction and the doping level

$$V = 0, 0.1, 0.2, \dots, 4.0 \quad \delta = 0, 0.01, 0.02, \dots, 0.49$$

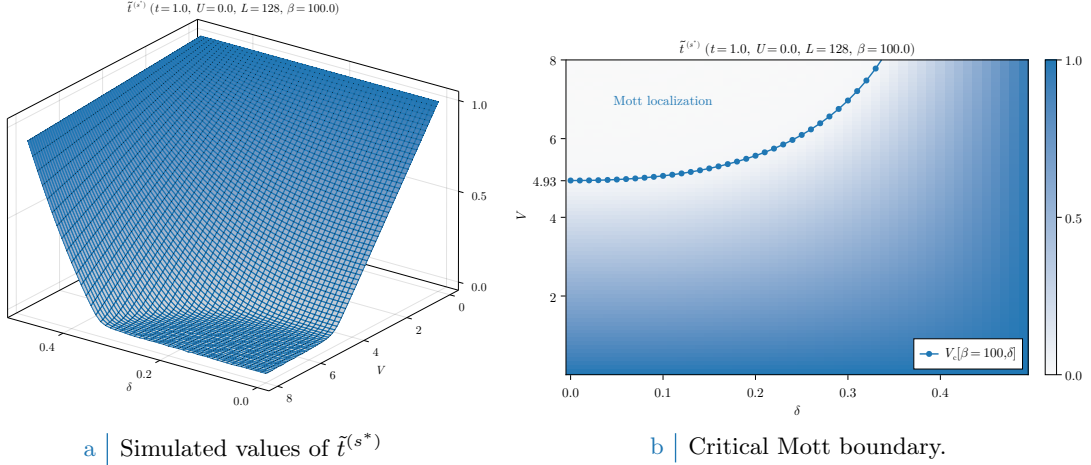

**Figure 1.7** | Plot of the self-consistent convergence values for the HFP  $u^{(s^*)}$  in the normal phase and the Mott-boundary  $V_c$ , computed as is described in text. In the right panel, the tick  $V = 4.93$  is specified explicitly as a graphic confirm of the computation of Eq. (1.38). For graphic reasons the points at  $V_c > 8$  have been omitted.

The expectations of Sec. 1.5.3 are satisfied: at low  $V$  (indicatively  $V \lesssim 5$ ) the trend is monotonically descendent at increasing doping. As  $V$  gets bigger, however,  $u^{(s^*)}$  starts decreasing in the top-left corner of Fig. 1.6a. This effect is more visible in Fig. 1.6b, where we doubled  $L$  and ran simulations with a smaller  $\delta$  resolution: the convergence value of  $u^{(s^*)}$  is approximately independent of  $V$  up to some point, where this behaviour is broken. Note that, as was expected from the discussion of Sec. 1.5.3, the half-filled convergence value of  $u^{(s^*)}$  in the  $V$ -independent region is approximately given by Eq. (1.37).

This effect can only be interpreted in one way, as we discuss in next section:  $u^{(s^*)}$  maintains a constant value at fixed doping, as is described in Sec. 1.5.3, as long as  $\tilde{t}^{(s^*)} > 0$ . When  $V$  gets large enough,  $u^{(s^*)}$  starts decreasing because of its constraints. The net effect is the nullification of  $\tilde{t}^{(s^*)}$ , which is, a total localisation effect.

### 1.6.1 Mott localisation effect

The most interesting result we obtained for the normal phase is the possibility of localising electrons by tuning the  $V/\delta$  ratio. In Fig. 1.6b, at low  $V$  the convergence value of  $u^{(s^*)}$  is approximately  $V$ -independent at sufficiently low temperatures. Let  $V_c[\beta, \delta]$  be the critical value such that

$$0 \leq V < V_c[\beta, \delta] \quad : \quad u^{(s^*)} \text{ is } V \text{ independent.}$$


Then within the entire segment  $[0, V_c]$  the convergence value is (approximately) the same obtained for  $V = 0$ . We can define in first instance the critical  $V$  as the value such that the hopping correction is maximized,

$$V_c[\beta, \delta] \equiv \frac{2t}{u^{(s^*)}[\beta, \tilde{\mu}(\delta)]|_{V=0}}$$

When  $V$  becomes larger than this critical value, the resulting RMP  $\tilde{t}^{(s^*)}$  drops to 0 and due to the constraint of Eq. (1.31) the convergence value of  $u^{(s^*)}$  is forced to decrease. Note that the constraint of Eq. (1.31) does not prevent  $u^{(s^*)}$  from saturating to its upper boundary from below. In Fig. 1.7a the converged values of  $\tilde{t}^{(s^*)}$ , extracted from the same data of Fig. 1.6a, are plotted in parametric space.

While to extract the value of  $V_c[\beta, \delta]$  is a non-trivial analytic problem due to the insurgence of elliptic integrals and the smearing effects of temperature, for the high- $\beta$  half-filled case it is immediate from Eq. (1.37) to see that

$$V_c[\beta \rightarrow \infty, 0] = \frac{2t}{(2/\pi)^2} \approx 4.93t \quad (1.38)$$

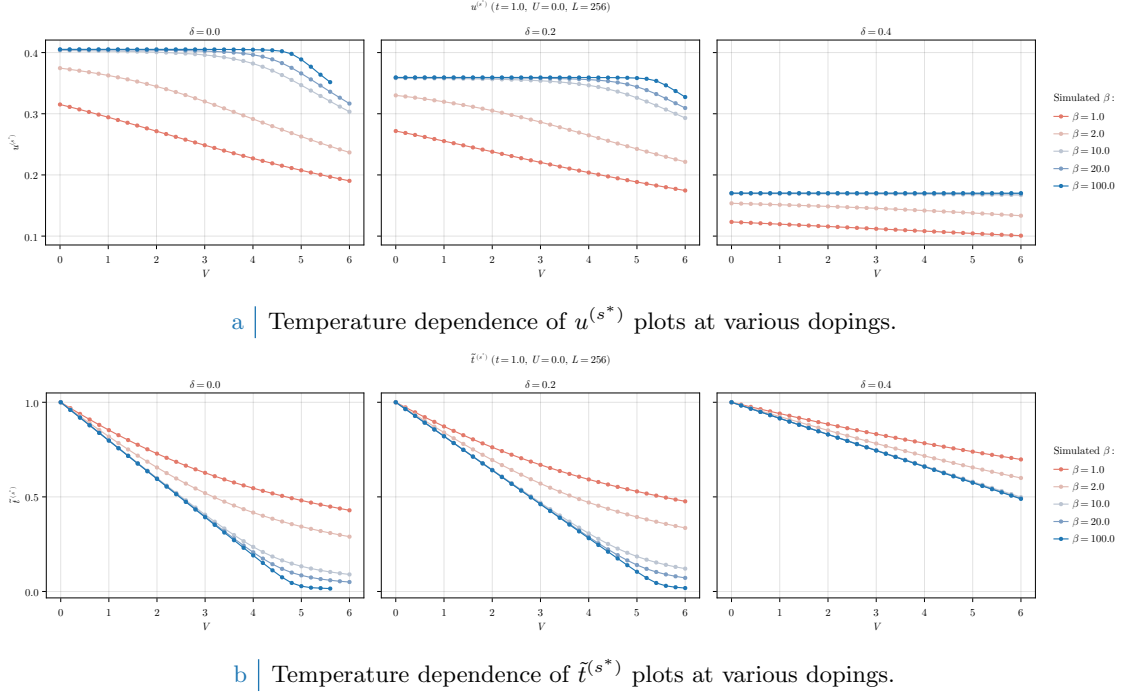

**Figure 1.8** | Comparative plots of the HFP  $u^{(s^*)}$  (top panel) and RMP  $\tilde{t}^{(s^*)}$  (bottom panel) in null-doped (left plots), “medium-doped” ( $\delta = 0.2$ , central plots) and “heavily-doped” ( $\delta = 0.4$ , right plots) contexts. Increasing temperature progressively destroys Mott localization, reducing the bands shrinking effect.

At half-filling, the effective bands amplitude reduction is so strong that small values of  $V$  (compared to  $t$ ) are sufficient to nullify kinetics. In Fig. 1.7b we report, superimposed, the convergence values of the RMP  $\tilde{t}^{(s^*)}$  and  $V_c[\beta = 100, \delta]$  computed with the simple procedure hereby described. Our prediction of the critical value for  $V$  approximates reasonably the localisation region.

Increasing temperature Mott localisation is suppressed. Also, our precedent argument were valid only at low temperature. In Fig. 1.8a we report results for the HFP  $u^{(s^*)}$  computed at decreasingly lower temperature and three example doping levels,

$$\beta = 1.0, 2.0, 10.0, 20.0, 100.0 \quad \delta = 0.0, 0.2, 0.4$$

At high temperature the  $V$ -independence region that was visible in Fig. 1.6b completely disappears, making  $u^{(s^*)}$  a monotonically descendent function. In Fig. 1.8a the same dataset is plotted with focus on the RMP  $\tilde{t}^{(s^*)}$ . Temperature increase disrupts localisation effects, at least at small values of  $V$ . However, the bands shrinking effect is still relevant at  $\beta = 1.0$ , the hopping parameter approximately halving at  $V \approx 5 \div 6$ .

## 1.6.2 Solution free energy and entropy densities

In order to compare phases, we need an estimation of free energy of each. The plots of Fig. 1.9 report our findings on the normal phase free energy, computed based on Eq. (1.24). For a non-flat band, doping increases energy because the band fills up and electrons populate higher energy levels.

Looking the data of Fig. 1.9a, at fixed  $\delta$  free energy density remains pretty much constant up to the Mott boundary. This is simply because as long as a band with non-zero amplitude is present, the HFP correction of Eq. (1.24) compensates the free energy increase due to bands shrinking,

$$\begin{aligned} -V|u^{(s^*)}|^2 &= -\frac{Vu^{(s^*)*}}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\epsilon_{\mathbf{k}} - \tilde{\epsilon}_{\mathbf{k}}) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \end{aligned}$$

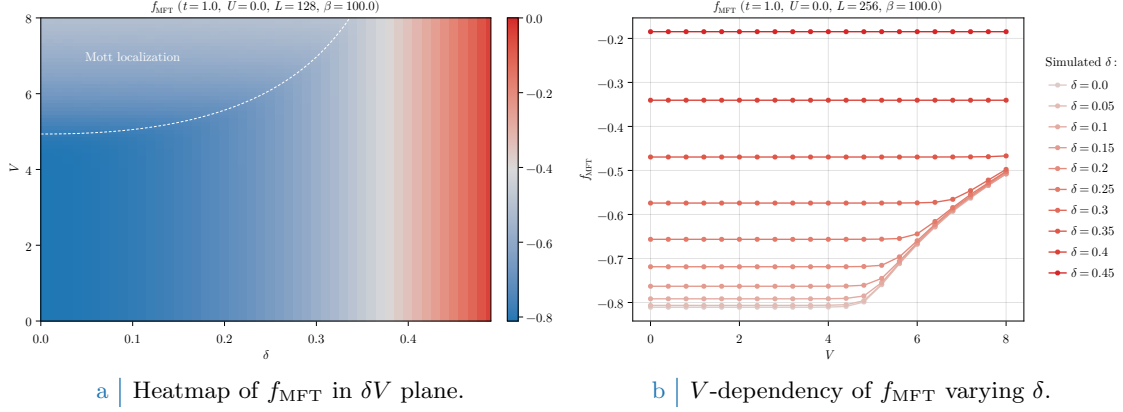


Figure 1.9 | Free energy density of the normal phase. On the left-side panel, the dashed white line has the same meaning as the dotted line of Fig. 1.7b, indicating the Mott transition.

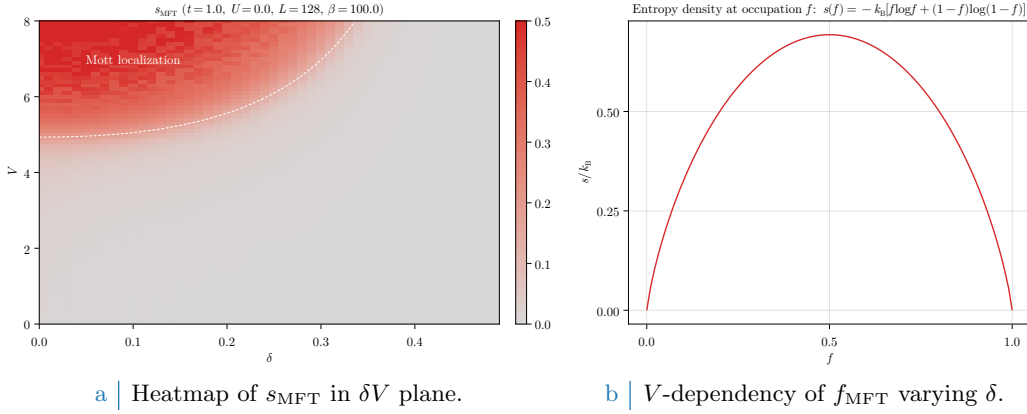


Figure 1.10 | Entropy density of the normal phase (left panel) and theoretical contribution to entropy for a state with occupation  $f$ . On the left-side panel, the dashed white line has the same meaning as the dotted line of Fig. 1.7b, indicating the Mott transition.

having we used in the second passage

$$\tilde{\epsilon}_{\mathbf{k}} = \tilde{\epsilon}_{\mathbf{k}} + u^{(s^*)} V (\cos k_x + \cos k_y)$$

Recalling the first point of the derivation of Sec. 1.4, to add the HFP correction to free energy is the same as removing the *tilde* sign from single-state energies, thus using the free model ( $V = 0$ ) free energy density expression.

Mott localisation is energetically expensive. This is visible in both panels of Fig. 1.9. The  $V$ -dependent energy increase is an entropic effect: indeed, for a flat band:

$$f(0; \beta, \tilde{\mu}(\delta)) = \frac{1}{2}$$

at any temperature. The expression for entropy density of a free Fermi gas [29] is given by

$$s(f) = -k_B [f \log f + (1 - f) \log(1 - f)]$$

represented in Fig. 1.10b. The maximum is located at  $f = 1/2$ , then a flat band realises the maximally entropic condition. The Mott insulating region can be seen as a degeneration of the FS interface to the entire BZ, a process that maximises entropy.

All of this holds, as all the rest, at low temperature: by lowering  $\beta$ , finite-temperature effects become more and more relevant and the statements above need to be corrected.

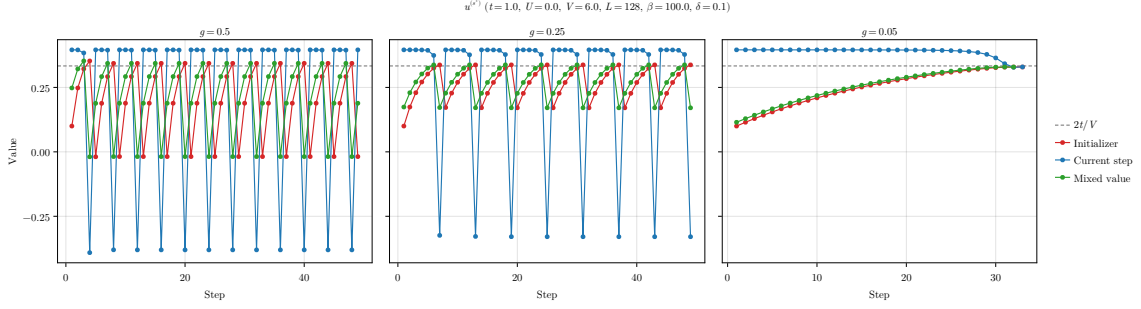


Figure 1.11 | Comparison of three example tracks for the single-valued HFPs vector of the normal phase, simulated at a “Mott-deep” point.

### 1.6.3 Convergence problems and mixing fine-tuning

The normal phase is simple enough to describe some of the typical convergence problems arising in HF iterative schemes anticipated in Sec. ?? . Bands flattening is a source of algorithmic instability: numerics can lead to values of  $u^{(s^*)}$ , during iterations, slightly out of bounds with respect to Eq. (1.31). Even if the numeric effect is small, the consequence can be vast. To heal this effect and extract the actual convergence values, it is necessary to optimise the mixing parameter  $g \in [0, 1]$ .

We defined  $g$  in Sec. ?? , and operatively in Eq. (??). This parameter controls deterministically how, from an initialiser (the HFPs vector we plug in the algorithm) and an output (the HFPs vector we get back from the algorithm) the new initialiser for the following step is generated. We show in Fig. 1.11 the evolutions at different mixing parameters of a simulation at

$$V = 6.0 \quad \delta = 0.1 \quad \beta = 100.0$$

This point is inside the Mott region, as can be checked in Fig. 1.6a. The HFP  $u^{(s^*)}$  needs to converge at  $2t/V = t/3$  in order to give complete localisation. The initialiser

$$\text{Step 1} \quad : \quad u^{(s^*)} = 0.1$$

was arbitrarily chosen. In each panel of Fig. 1.11, the red track represents the value of  $u^{(s^*)}$  we plug in the self-consistency equations, the blue the result of the self-consistent equation, the green one the mixed value of the two based on different  $g$ s. The gray dashed line is the theoretical convergence target.

In the first two panels, there is an evident infinite loop occurring whenever the green line crosses the threshold  $2t/V$ . At those steps, the green point is out of bounds with respect to Eq. (1.31). When this happens, the following red point gives a band with inverted sign, a feature that “breaks” the self-consistency equation and generates a blue point with no physical significance.

To overcome this problem it is necessary to move “slowly”. As is shown in the right panel, the choice of a small enough mixing parameter ensures convergence. In the track, each blue dot is above the target and would produce a band with inverted sign. Mixing blue and red dots with a 95% unbalance on the red ones, we ensure that the green track approaches the target from below. Note, however, that lowering  $g$  cannot be reiterated too many times. Indeed, for  $g \rightarrow 0$ , any point of our map becomes a fixed point.

This kind of problems can turn out to be pretty common for iHF schemes, and to understand how to knob the algorithmic parameters without sacrificing accurateness and precision, as well as avoiding computationally costly and frustrating infinite loops, was an essential part of this algorithm design.





## Chapter 2

# Antiferromagnetic instability


In this chapter we apply HF method to the AF phase, widely studied for the HM [31]. We focus on one particular realisation of antiferromagnetism, referred to as “commensurate”. It is inherently metallic and only physically sensed at half-filling.

For the commensurate antiferromagnet, the non-local attraction  $\hat{H}_V$  adds two main self-consistent effects. First, redefinition of the bands gap: an effect we denote “gap complexification” (Sec. 2.6) and later show is actually suppressed (Sec. 2.8). Second, bare bands shrinking (Sec. 2.5) similarly to what found for the normal phase.

As for the normal phase, this chapter is equally divided in the same three main parts. First: discussion of AF phase symmetries, based on Chap. ??, and implementation of HF methods. Second: theoretical constraints on the self-consistent solution. Third: numeric results.

### 2.1 The AF phase and its symmetries

The AF phase is not uniquely defined. Fig. 2.1 presents three (of many) types of antiferromagnets. We represent in the left panel the one we are interested in. The AF structure comes from an uneven and periodic distribution of spin densities with one site periodicity in both directions. The arrows in figure indicate what spin sector is most abundant on a given site. These SDW structures are 2-sites periodic, making the AF phase “commensurate”. The central one presents another simple commensurate AF with higher periodicity. The right panel shows a possible “striped” antiferromagnet, where AF is effectively established along one particular direction; the example we report is 2 sites periodic in  $y$  direction, but any other periodicity could work. Striped antiferromagnetism is studied in HM physics [3] as a possible long-range ordering energetically competing

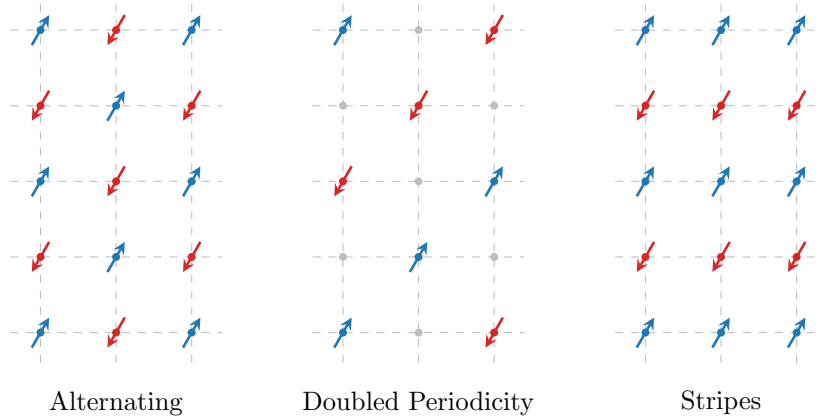

**Figure 2.1** | Three possible antiferromagnetic structures. Dots and arrows indicate spin abundance on a given site, while empty sites are intended as spin-balanced. Within this text we deal with the lowest-periodicity commensurate phase, the antiferromagnet on left panel.

with anisotropic superconductivity. Nematic antiferromagnets, establishing long-range magnetic ordering along one particular direction, are interesting due to competition and interplay against superconducting ordering at finite doping [24]. Geometrically non-trivial magnetic ordering are at the core of SDW formation in copper oxides at finite doping [25, 26].

In this thesis, the AF phase is described by simultaneous global spin rotation and translational symmetry SSBs:

$$\begin{aligned} \text{SU}(2) &\xrightarrow{\text{SSB}} \text{U}^z(1) \\ \text{T}_1^{(x)} \otimes \text{T}_1^{(y)} &\xrightarrow{\text{SSB}} \text{T}_2^{(x)} \otimes \text{T}_2^{(y)} \end{aligned}$$

We describe a SDW whose period is of two sites, as in the left panel of Fig. 2.1. As done for the normal phase, we allow

$$\text{C}_4 \xrightarrow{\text{SSB}} \text{C}_2$$

in order to capture the same theoretical nematic effects seen in Sec. 1.3.1. The theoretical reason to do so for AF phase relies in our previous discussion. As said, planar Hubbard lattices exhibits tendency towards nematic magnetic ordering, thus (even if our Ansatz is the simplest and non evidently nematic) nematic effects are not to be excluded *a priori*.

Commensurate antiferromagnetism is specified by the Ansatz:

$$\langle \hat{n}_{\mathbf{r}\sigma} \rangle = n - (-1)^{x+y+\delta_{\sigma=\uparrow}} m \quad n, m \in [0, 1] \quad (2.1)$$

This Ansatz captures the idea of the staggered distribution of spin populations shown in the left panel of Fig. 2.1. At site  $\mathbf{r} = (x, y)$  the two spin populations average to  $n$  and differ by  $2m$ . A detailed justification for this Ansatz in the HM is given in Sec. ???. Note that  $\langle \hat{n}_{\mathbf{r}\sigma} \rangle \leq 1$  due to Pauli exclusion principle. This argument is already sufficient to claim that doping disrupts commensurate antiferromagnetism.

### 2.1.1 Symmetries of the commensurate AF Ansatz

The Ansatz of Eq. (2.1) breaks translational invariance in each spin sector, but preserves  $\text{U}^z(1)$  and  $\text{U}^c(1)$  symmetries. Let us prove this. The Ansatz is defined by the following EV being non-zero,

$$\langle \hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow} \rangle = 2m \quad (2.2)$$

ignoring the local sign factor. SSB happens establishes when  $m \neq 0$ . Then:

- Recall the definitions of  $\hat{\Psi}_{\mathbf{r}}$  of Eq. (??)

$$\hat{\Psi}_{\mathbf{r}} = \begin{bmatrix} \hat{c}_{\mathbf{r}\uparrow} \\ \hat{c}_{\mathbf{r}\downarrow} \end{bmatrix}$$

and the local spin operators of Eq. (??),

$$\hat{S}_{\mathbf{r}}^+ = \frac{\hat{c}_{\mathbf{r}\uparrow}^\dagger \hat{c}_{\mathbf{r}\downarrow}}{2} \quad \hat{S}_{\mathbf{r}}^- = \frac{\hat{c}_{\mathbf{r}\downarrow}^\dagger \hat{c}_{\mathbf{r}\uparrow}}{2} \quad \hat{S}_{\mathbf{r}}^z = \frac{\hat{c}_{\mathbf{r}\uparrow}^\dagger \hat{c}_{\mathbf{r}\uparrow} - \hat{c}_{\mathbf{r}\downarrow}^\dagger \hat{c}_{\mathbf{r}\downarrow}}{2}$$

Consider Eq. (??) and its conjugate,

$$[\hat{c}_{\mathbf{r}\sigma}^\dagger, \hat{n}_{\mathbf{r}\sigma}] = -\hat{c}_{\mathbf{r}\sigma}^\dagger \quad [\hat{c}_{\mathbf{r}\sigma}, \hat{n}_{\mathbf{r}\sigma}] = \hat{c}_{\mathbf{r}\sigma}$$

The operators  $\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}$  and  $\hat{S}_{\mathbf{r}}^\pm$  do not commute. Indeed,

$$\begin{aligned} [\hat{S}_{\mathbf{r}}^+, \hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}] &= \frac{1}{2} [\hat{c}_{\mathbf{r}\uparrow}^\dagger, \hat{n}_{\mathbf{r}\uparrow}] \hat{c}_{\mathbf{r}\downarrow} - \frac{1}{2} \hat{c}_{\mathbf{r}\uparrow}^\dagger [\hat{c}_{\mathbf{r}\downarrow}, \hat{n}_{\mathbf{r}\downarrow}] \\ &= -\hat{c}_{\mathbf{r}\uparrow}^\dagger \hat{c}_{\mathbf{r}\downarrow} \\ [\hat{S}_{\mathbf{r}}^-, \hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}] &= \frac{1}{2} \hat{c}_{\mathbf{r}\downarrow}^\dagger [\hat{c}_{\mathbf{r}\uparrow}, \hat{n}_{\mathbf{r}\uparrow}] - \frac{1}{2} [\hat{c}_{\mathbf{r}\downarrow}^\dagger, \hat{n}_{\mathbf{r}\downarrow}] \hat{c}_{\mathbf{r}\uparrow} \\ &= \hat{c}_{\mathbf{r}\downarrow}^\dagger \hat{c}_{\mathbf{r}\uparrow} \end{aligned}$$

Instead,  $\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}$  and  $\hat{S}_{\mathbf{r}}^z$  commute, because all on-site density operators always do. Then, in order to have  $m \neq 0$  in Eq. (2.2),  $\text{SU}(2)$  needs to be broken while  $\text{U}^z(1)$  needs not.

- From Eq. (??) we know that on-site density operators are gauge-invariant separately in both spin sectors. Then no selection rule applies to  $\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}$ : its EV can be non-zero without breaking  $U^z(1)$ .

The chosen Ansatz is coherent with the symmetry requirements of Tab. ?? . Let us rephrase this in the language of HF methods. We need an HFPs vector  $\mathbf{v}$ , whose components  $v_i$  are equipped with self-consistency equations. Commensurate antiferromagnetism is described by those HFPs emerging from Wick's theorem applied to the EHM respecting symmetry requirement. Among these we include explicitly the spin averaged unbalance has a two-sites periodicity,

$$\forall \mathbf{r} = (x, y) \in \mathcal{L} \quad : \quad m \equiv (-1)^{x+y} \frac{\langle \hat{n}_{\mathbf{r}\uparrow} \rangle - \langle \hat{n}_{\mathbf{r}\downarrow} \rangle}{2} \quad (2.3)$$

By allowing for this EV to be non-zero we respect phase symmetry and impose antiferromagnetism to be commensurate. Setting  $m \neq 0$  is equivalent to imposing Eq. (2.1).

The on-site averaged density is given by:

$$\forall \mathbf{r} \in \mathcal{L} \quad : \quad n \equiv \frac{\langle \hat{n}_{\mathbf{r}\uparrow} \rangle + \langle \hat{n}_{\mathbf{r}\downarrow} \rangle}{2} \quad (2.4)$$

Despite of similarity with  $m$ , this is not an HFP. First, on-site density respect all EHM symmetries. Second, we are imposing average density as a parametrisation of the model. There is nothing to be searched self-consistently here.

Note that the quantities  $n$ ,  $m$  in Eqns. (2.4), (2.3) are  $\mathbf{r}$ -independent. Then it must hold

$$n = \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} \frac{\langle \hat{n}_{\mathbf{r}\uparrow} \rangle + \langle \hat{n}_{\mathbf{r}\downarrow} \rangle}{2} \quad (2.5)$$

$$m = \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} \frac{\langle \hat{n}_{\mathbf{r}\uparrow} \rangle - \langle \hat{n}_{\mathbf{r}\downarrow} \rangle}{2} \quad (2.6)$$

From the first equation we gain an operational method to compute density, from the second we get a self-consistency equation for magnetisation. Indeed, the ground-state depends on HFP  $m$  in some way to be determined explicitly. While this passage added nothing about the theoretical description of antiferromagnetism (we averaged constants over the lattice), it will be crucial in order to move the discussion to reciprocal space.

### 2.1.2 The AF Ansatz in reciprocal space

The core parts of the following derivations will be carried out in reciprocal space. It is then useful to comment the reciprocal structure of the AF Ansatz. First, let:

$$\hat{n}_{\mathbf{k}\sigma} \equiv \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}\sigma} \quad (2.7)$$

$$\hat{\psi}_{\mathbf{k}\sigma} \equiv \hat{c}_{\mathbf{k}+\pi\sigma}^\dagger \hat{c}_{\mathbf{k}\sigma} \quad (2.8)$$

Note that  $\hat{n}_{\mathbf{k}\sigma}$  is not the Fourier-transform of  $\hat{n}_{\mathbf{r}\sigma}$ . Recall also the  $\gamma$ -wave form factors of Tab. ?? . Then:

$$\hat{\psi}_{\mathbf{k}+\pi\sigma}^\dagger = \hat{\psi}_{\mathbf{k}\sigma} \quad (2.9)$$

$$\varphi_{\mathbf{k}+\pi}^{(\gamma)} = -\varphi_{\mathbf{k}}^{(\gamma)} \quad (2.10)$$

which, by the way, implies the property

$$\varphi_{\mathbf{k}+\pi}^{(\gamma)} \psi_{\mathbf{k}+\pi\sigma}^\dagger = -\varphi_{\mathbf{k}}^{(\gamma)} \psi_{\mathbf{k}\sigma} \quad (2.11)$$

that will result useful later.

In the AF phase, we have  $\langle \hat{n}_{\mathbf{k}\sigma} \rangle \neq 0$  and  $\langle \hat{\psi}_{\mathbf{k}\sigma} \rangle \neq 0$ . This is proven by the following chains of equations:

$$\begin{aligned}
\sum_{\mathbf{r} \in \mathcal{L}} \hat{n}_{\mathbf{r}\sigma} &= \sum_{\mathbf{r} \in \mathcal{L}} \hat{c}_{\mathbf{r}\sigma}^\dagger \hat{c}_{\mathbf{r}\sigma} \\
&\stackrel{\mathcal{F}}{=} \sum_{\mathbf{r} \in \mathcal{L}} \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k} \in \text{BZ}} e^{i\mathbf{k} \cdot \mathbf{r}} \hat{c}_{\mathbf{k}\sigma}^\dagger \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k}' \in \text{BZ}} e^{-i\mathbf{k}' \cdot \mathbf{r}} \hat{c}_{\mathbf{k}'\sigma} \\
&= \sum_{\mathbf{k} \in \text{BZ}} \sum_{\mathbf{k}' \in \text{BZ}} \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}'\sigma} \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} e^{-i(\mathbf{k}' - \mathbf{k}) \cdot \mathbf{r}} \\
&= \sum_{\mathbf{k} \in \text{BZ}} \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}\sigma} \\
&= \sum_{\mathbf{k} \in \text{BZ}} \hat{n}_{\mathbf{k}\sigma}
\end{aligned} \tag{2.12}$$

where we used Eq. (??). Thus:

$$\begin{aligned}
n &= \frac{1}{2} \sum_{\sigma} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} n + \overbrace{\frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} m}^{=0} \right] \\
&= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{r} \in \mathcal{L}} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \\
&= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{k} \in \text{BZ}} \langle \hat{n}_{\mathbf{k}\sigma} \rangle
\end{aligned} \tag{2.13}$$

We used the Ansatz of Eq. (2.1). Since  $n \neq 0$ , in the last sum  $\langle \hat{n}_{\mathbf{k}\sigma} \rangle \neq 0$  is impossible for all  $\mathbf{k}$ s. Similarly, for the oscillatory part:

$$\begin{aligned}
\sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} \hat{n}_{\mathbf{r}\sigma} &= \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} \hat{c}_{\mathbf{r}\sigma}^\dagger \hat{c}_{\mathbf{r}\sigma} \\
&\stackrel{\mathcal{F}}{=} \sum_{\mathbf{r} \in \mathcal{L}} e^{i\boldsymbol{\pi} \cdot \mathbf{r}} \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k} \in \text{BZ}} e^{i\mathbf{k} \cdot \mathbf{r}} \hat{c}_{\mathbf{k}\sigma}^\dagger \frac{1}{\sqrt{L_x L_y}} \sum_{\mathbf{k}' \in \text{BZ}} e^{-i\mathbf{k}' \cdot \mathbf{r}} \hat{c}_{\mathbf{k}'\sigma} \\
&= \sum_{\mathbf{k} \in \text{BZ}} \sum_{\mathbf{k}' \in \text{BZ}} \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}'\sigma} \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} e^{-i[\mathbf{k}' - (\mathbf{k} + \boldsymbol{\pi})] \cdot \mathbf{r}} \\
&= \sum_{\mathbf{k} \in \text{BZ}} \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k} + \boldsymbol{\pi}\sigma}
\end{aligned} \tag{2.14}$$

$$= \sum_{\mathbf{k} \in \text{BZ}} \hat{\psi}_{\mathbf{k}\sigma} \tag{2.15}$$

where we defined the AF vector  $\boldsymbol{\pi} \equiv (\pi, \pi)$ . Thus, again using the Ansatz of Eq. (2.1),

$$\begin{aligned}
(-1)^{\delta_{\sigma=\downarrow}} m &= \overbrace{\frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} n}^{=0} + \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{\delta_{\sigma=\downarrow}} m \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \langle \hat{\psi}_{\mathbf{k}\sigma} \rangle
\end{aligned} \tag{2.16}$$

where we used  $1 = ((-1)^{x+y})^2$ . If  $m \neq 0$ , in the last sum we cannot have  $\langle \hat{\psi}_{\mathbf{k}\sigma} \rangle \neq 0$  for all  $\mathbf{k}$ s. We

| Operator    | Sector | RWCs    | Net effect                                                       |
|-------------|--------|---------|------------------------------------------------------------------|
| $\hat{H}_U$ |        | Hartree | $\mu$ shift by $-nU$                                             |
|             | o.s.   | Hartree | $\mu$ shift by $nzV$                                             |
| $\hat{H}_V$ |        | Hartree | $\mu$ shift by $nzV$                                             |
|             | s.s.   | Fock    | Bands renormalisation and resymmetrization, gap complexification |

**Table 2.1** | Relevant Wick's contractions and net effect in the AF phase. Note the similarity with Tab. 1.1.

can restrict the sum to the MBZ and write it explicitly for both spins

$$m = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} [\hat{\psi}_{\mathbf{k}\uparrow} + \hat{\psi}_{\mathbf{k}\uparrow}^\dagger] \quad (2.17)$$

$$= -\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} [\hat{\psi}_{\mathbf{k}\downarrow} + \hat{\psi}_{\mathbf{k}\downarrow}^\dagger] \quad (2.18)$$

where we used the property of Eq. (2.9).

Recall now Tabs. ?? and ??: the relevant Wick's contractions are, for each sector,

|                           |                               |
|---------------------------|-------------------------------|
| $\hat{H}_U$               | Hartree contraction           |
| $\hat{H}_V$ (o.s. sector) | Hartree contraction           |
| $\hat{H}_V$ (s.s. sector) | Hartree and Fock contractions |

Their role is anticipated Tab. 2.1. In next sections we break down each one and derive the results by analytically applying HF methods.

## 2.2 Local Hartree effects: antiferromagnetism in the HM

For the AF phase, the derivation is more elaborated than for the normal phase. It is useful to separate the local and non-local interactions and apply to each one HF methods. Let us start from the local quartic interaction,

$$\hat{H}_U = U \sum_{\mathbf{r} \in \mathcal{L}} \hat{c}_{\mathbf{r}\uparrow}^\dagger \hat{c}_{\mathbf{r}\downarrow}^\dagger \hat{c}_{\mathbf{r}\downarrow} \hat{c}_{\mathbf{r}\uparrow}$$

We only need to analyse the Hartree contraction channel, as is reported in Tab. 2.1. The HF decomposition and the Hartree sectors are given in Eq. (??).

Before extending to the non-local attraction, we dedicate the end of this section to complete the theoretical description of antiferromagnetism in the conventional, locally repulsive Hubbard model. This will allow us to identify easily what changes due to the presence of  $\hat{H}_V$ .

### 2.2.1 Local Hartree channel in the AF phase: analytic derivation

The HF method, applied to a quartic operator, gives the decomposition of Eq. (??). Decompose  $\hat{H}_U$  in the Hartree channel:

$$\hat{H}_U \simeq U \sum_{\mathbf{r} \in \mathcal{L}} [\hat{n}_{\mathbf{r}\uparrow} \langle \hat{n}_{\mathbf{r}\downarrow} \rangle + \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \hat{n}_{\mathbf{r}\downarrow} - \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \langle \hat{n}_{\mathbf{r}\downarrow} \rangle]$$

Note that in the AF phase, as is reported in Tab. ??, the local repulsion decomposes just in the Hartree channel. Then no other term must be included in the above approximation of the quartic operator.

The one-body operators can be rewritten as:

$$\hat{n}_{\mathbf{r}\uparrow} \langle \hat{n}_{\mathbf{r}\downarrow} \rangle + \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \hat{n}_{\mathbf{r}\downarrow} = \frac{\langle \hat{n}_{\mathbf{r}\uparrow} \rangle + \langle \hat{n}_{\mathbf{r}\downarrow} \rangle}{2} (\hat{n}_{\mathbf{r}\uparrow} + \hat{n}_{\mathbf{r}\downarrow}) - \frac{\langle \hat{n}_{\mathbf{r}\uparrow} \rangle - \langle \hat{n}_{\mathbf{r}\downarrow} \rangle}{2} (\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow})$$

From Eqns. (2.3) and (2.4), we recognise  $n$  and the HFP  $m$ . We have the decomposition:

$$\hat{H}_U \simeq nU \sum_{\mathbf{r} \in \mathcal{L}} [\hat{n}_{\mathbf{r}\uparrow} + \hat{n}_{\mathbf{r}\downarrow}] - mU \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} [\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}] - E_{\text{H}/U}^{(\text{AF})} \quad (2.19)$$

with  $E_{\text{H}/U}^{(\text{AF})}$  the HM Hartree contraction energy, discussed in Sec. 2.2.2. The first term of Eq. (2.19) gives a number operator,

$$nU \sum_{\mathbf{r} \in \mathcal{L}} [\hat{n}_{\mathbf{r}\uparrow} + \hat{n}_{\mathbf{r}\downarrow}] = nU \times \hat{N}$$

Then we get the first renormalisation of chemical potential:

$$\mu \rightarrow \mu - nU \quad (2.20)$$

We partially anticipated it in Tab. 2.1. Another shift to  $\mu$  will come from the non-local attraction. In the second term of Eq. (2.19), apply Eq. (2.14). It follows:

$$mU \sum_{\mathbf{r} \in \mathcal{L}} (-1)^{x+y} [\hat{n}_{\mathbf{r}\uparrow} - \hat{n}_{\mathbf{r}\downarrow}] = mU \sum_{\mathbf{k} \in \text{BZ}} \left[ \hat{c}_{\mathbf{k}\uparrow}^\dagger \hat{c}_{\mathbf{k}+\pi\uparrow} - \hat{c}_{\mathbf{k}\downarrow}^\dagger \hat{c}_{\mathbf{k}+\pi\downarrow} \right]$$

Recall the definition of the MBZ given in Eq. (1.25). The full BZ can be seen as the sum of two MBZ shifted by  $\pi$ . Then, using  $2\pi$  periodicity, the following identity holds:

$$\begin{aligned} \sum_{\mathbf{k} \in \text{BZ}} \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}+\pi\sigma} &= \sum_{\mathbf{k} \in \text{MBZ}} \left[ \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}+\pi\sigma} + \hat{c}_{\mathbf{k}+\pi\sigma}^\dagger \hat{c}_{\mathbf{k}+2\pi\sigma} \right] \\ &= \sum_{\mathbf{k} \in \text{MBZ}} \left[ \hat{c}_{\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{k}+\pi\sigma} + \hat{c}_{\mathbf{k}+\pi\sigma}^\dagger \hat{c}_{\mathbf{k}\sigma} \right] \end{aligned} \quad (2.21)$$

We write everything in terms of the operators  $\hat{n}_{\mathbf{k}\sigma}$  and  $\hat{\psi}_{\mathbf{k}\sigma}$ , defined in Eqns. (2.7), (2.8). The local interaction is reduced to

$$\hat{H}_U \simeq -mU \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} (-1)^{\delta_{\sigma=\downarrow}} \left( \hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}_{\mathbf{k}\sigma}^\dagger \right) + nU \hat{N} - E_{\text{H}/U}^{(\text{AF})}$$

We define the gap function:

$$\Delta_{\mathbf{k}\sigma} = (-1)^{\delta_{\sigma=\downarrow}} mU$$

This new object allows us to rewrite the local repulsion as:

$$\hat{H}_U \simeq - \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \left( \Delta_{\mathbf{k}\sigma} \hat{\psi}_{\mathbf{k}\sigma} + \Delta_{\mathbf{k}\sigma}^* \hat{\psi}_{\mathbf{k}\sigma}^\dagger \right) + nU \hat{N} - E_{\text{H}/U}^{(\text{AF})} \quad (2.22)$$

The gap function is actually independent of  $\mathbf{k}$ . It is a constant in reciprocal space. However, we defined it as  $\Delta_{\mathbf{k}\sigma}$ : this notation will be useful later.

## 2.2.2 Local Hartree contraction energy

In last section we defined  $E_{\text{H}/U}^{(\text{AF})}$  as the local Hartree contraction energy,

$$\begin{aligned} E_{\text{H}/U}^{(\text{AF})} &\equiv U \sum_{\mathbf{r} \in \mathcal{L}} \langle \hat{n}_{\mathbf{r}\uparrow} \rangle \langle \hat{n}_{\mathbf{r}\downarrow} \rangle \\ &= U \sum_{\mathbf{r} \in \mathcal{L}} (n + (-1)^{x+y} m) (n - (-1)^{x+y} m) \end{aligned}$$

where we used the Ansatz of Eq. (2.1). Expanding the product above we get:

$$\begin{aligned} (n + (-1)^{x+y} m) (n - (-1)^{x+y} m) &= n^2 + ((-1)^{x+y} - (-1)^{x+y}) nm - ((-1)^{x+y})^2 m^2 \\ &= n^2 - m^2 \end{aligned}$$

The sum over  $\mathcal{L}$  gives  $L_x L_y$  identical terms, thus we get:

$$E_{\text{H}/U}^{(\text{AF})} = L_x L_y \times U (n^2 - m^2) \quad (2.23)$$

which is the contraction energy in the local Hartree channel.

### 2.2.3 Antiferromagnetism in the HM

One of the aims of this projects is to identify, theoretically, what changes for each phase due to the presence of the non-local attraction  $\hat{H}_V$  with respect to the conventional HM. In this section we give a description of antiferromagnetism in the conventional HM, and later we move to the EHM.

**Matrix representation.** The HM hamiltonian contains the kinetic operator and the local repulsion,

$$\hat{H}_t + \hat{H}_U$$

Let the reciprocal space spinors:

$$\hat{\Psi}_{\mathbf{k}\sigma} \equiv \begin{bmatrix} \hat{c}_{\mathbf{k}\sigma} \\ \hat{c}_{\mathbf{k}+\pi\sigma} \end{bmatrix}$$

Despite sharing a similar notation with the spinors of Eq. (??), they are inherently different objects. Recall Eq. (??): the kinetic sector is represented in reciprocal space by

$$\begin{aligned} \hat{H}_t &= \sum_{\mathbf{k} \in \text{BZ}} \sum_{\sigma} \epsilon_{\mathbf{k}} \hat{c}_{\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{k}\sigma} \\ &= \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \epsilon_{\mathbf{k}} \left( \hat{c}_{\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{k}\sigma} - \hat{c}_{\mathbf{k}+\pi\sigma}^{\dagger} \hat{c}_{\mathbf{k}+\pi\sigma} \right) \end{aligned}$$

where we used antiperiodicity by  $\pi$  of the bare bands  $\epsilon_{\mathbf{k}}$  defined in Eq. (??),

$$\epsilon_{\mathbf{k}} = -\epsilon_{\mathbf{k}+\pi}$$

The kinetic operator can be written in terms of the spinors  $\hat{\Psi}_{\mathbf{k}\sigma}$ ,

$$\hat{H}_t = \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Psi}_{\mathbf{k}\sigma}^{\dagger} \begin{bmatrix} \epsilon_{\mathbf{k}\sigma} & \\ & -\epsilon_{\mathbf{k}\sigma} \end{bmatrix} \hat{\Psi}_{\mathbf{k}\sigma}$$

The local repulsion  $\hat{H}_U$  of Eq. (2.22) can also be written in terms of these spinors:

$$\hat{H}_U = \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Psi}_{\mathbf{k}\sigma}^{\dagger} \begin{bmatrix} & -\Delta_{\mathbf{k}\sigma}^* \\ -\Delta_{\mathbf{k}\sigma} & \end{bmatrix} \hat{\Psi}_{\mathbf{k}\sigma} + nU\hat{N} - E_{\text{H/U}}^{(\text{AF})}$$

Collect everything. For the AF phase, the final form of the quadratic hamiltonian is

$$\hat{H}_t + \hat{H}_U \simeq \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Psi}_{\mathbf{k}\sigma}^{\dagger} h_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} + nU\hat{N} - E_{\text{H/U}}^{(\text{AF})} \quad (2.24)$$

where we defined the  $2 \times 2$  matrix:

$$h_{\mathbf{k}\sigma} \equiv \begin{bmatrix} \epsilon_{\mathbf{k}\sigma} & -\Delta_{\mathbf{k}\sigma}^* \\ -\Delta_{\mathbf{k}\sigma} & -\epsilon_{\mathbf{k}\sigma} \end{bmatrix}$$

This is a parametric hamiltonian. We need to identify its ground state for each choice of the parameters  $\Delta_{\mathbf{k}\sigma}$ . This is done by mapping the problem to the one of a set of spin subject to local magnetic fields: let us show this.

**Pseudospin representation.** The matrix  $h_{\mathbf{k}\sigma}$  can be written in term of the Pauli matrices  $\tau^{\alpha}$

$$h_{\mathbf{k}\sigma} = \epsilon_{\mathbf{k}\sigma} \tau^z - \Delta_{\mathbf{k}\sigma} \tau^x$$

Let us define the pseudospin operator  $\hat{\mathbf{s}}_{\mathbf{k}\sigma}$

$$\hat{s}_{\mathbf{k}\sigma}^{\alpha} \equiv \hat{\Psi}_{\mathbf{k}\sigma}^{\dagger} \tau^{\alpha} \hat{\Psi}_{\mathbf{k}\sigma} \quad \text{with} \quad \hat{\mathbf{s}}_{\mathbf{k}\sigma} = \begin{bmatrix} \hat{s}_{\mathbf{k}\sigma}^x \\ \hat{s}_{\mathbf{k}\sigma}^y \\ \hat{s}_{\mathbf{k}\sigma}^z \end{bmatrix}$$

| EV                                             | Meaning                                                                                   |
|------------------------------------------------|-------------------------------------------------------------------------------------------|
| $\langle \hat{s}_{\mathbf{k}\sigma}^x \rangle$ | $\langle \hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}_{\mathbf{k}\sigma}^\dagger \rangle$   |
| $\langle \hat{s}_{\mathbf{k}\sigma}^y \rangle$ | $i \langle \hat{\psi}_{\mathbf{k}\sigma} - \hat{\psi}_{\mathbf{k}\sigma}^\dagger \rangle$ |
| $\langle \hat{s}_{\mathbf{k}\sigma}^z \rangle$ | $\langle \hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\pi\sigma} \rangle$             |

**Table 2.2** | List of the various expectation values (EVs) of each pseudo-spin component and their meaning in terms of fermionic operators.

and the pseudofield  $\mathbf{b}_{\mathbf{k}\sigma}$ :

$$\mathbf{b}_{\mathbf{k}\sigma} \equiv \begin{bmatrix} -\Delta_{\mathbf{k}\sigma} \\ 0 \\ \epsilon_{\mathbf{k}\sigma} \end{bmatrix}$$

These operators satisfy a  $\mathfrak{su}(2)$  algebra up to a constant  $C$ ,

$$[\hat{s}_{\mathbf{k}\sigma}^\alpha, \hat{s}_{\mathbf{k}\sigma}^\beta] = C \times i \sum_{\gamma} \epsilon_{\alpha\beta\gamma} \hat{s}_{\mathbf{k}\sigma}^\gamma$$

The proof is conceptually identical to the one presented in Sec. ???. The actual value of  $C$  is irrelevant, as we will see in next paragraphs. **The two set of spin operators are unrelated.** Let us express the pseudospin operator in terms of the operators of Eqns. (2.7), (2.8):

$$\hat{s}_{\mathbf{k}\sigma}^x = \hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}_{\mathbf{k}\sigma}^\dagger \quad (2.25)$$

$$\hat{s}_{\mathbf{k}\sigma}^y = i \left( \hat{\psi}_{\mathbf{k}\sigma} - \hat{\psi}_{\mathbf{k}\sigma}^\dagger \right) \quad (2.26)$$

$$\hat{s}_{\mathbf{k}\sigma}^z = \hat{n}_{\mathbf{k}\sigma} - \hat{n}_{\mathbf{k}+\pi\sigma} \quad (2.27)$$

We report these relations also in Tab. 2.2. Let also:

$$\begin{aligned} \hat{\mathbb{I}}_{\mathbf{k}\sigma} &\equiv \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \mathbb{I}_{2 \times 2} \hat{\Psi}_{\mathbf{k}\sigma} \\ &= \hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\pi\sigma} \end{aligned} \quad (2.28)$$

In pseudospin representation we get:

$$\hat{H}_t + \hat{H}_U \simeq \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \mathbf{b}_{\mathbf{k}\sigma} \cdot \hat{\mathbf{s}}_{\mathbf{k}\sigma} + nU \hat{N} - E_{\text{H/U}}^{(\text{AF})} \quad (2.29)$$

The hamiltonian represents a system of spins subject to local magnetic fields. The field  $\mathbf{b}_{\mathbf{k}\sigma}$  is orthogonal to the  $y$  plane, and is tilted in the  $z$  plane by an angle  $2\theta_{\mathbf{k}\sigma}$  with:

$$\cos(2\theta_{\mathbf{k}\sigma}) = \frac{\epsilon_{\mathbf{k}\sigma}}{E_{\mathbf{k}\sigma}} \quad \sin(2\theta_{\mathbf{k}\sigma}) = \frac{\Delta_{\mathbf{k}\sigma}}{E_{\mathbf{k}\sigma}} \quad E_{\mathbf{k}\sigma} \equiv \sqrt{\epsilon_{\mathbf{k}\sigma}^2 + |\Delta_{\mathbf{k}\sigma}|^2}$$

A sketch of these angles and the pseudofield is given in Fig. 2.2.

**Diagonalisation.** To diagonalise the Hubbard hamiltonian  $\hat{H}_t + \hat{H}_U$  of Eq. (2.29) means to perform some unitary operation on the  $\hat{\Psi}_{\mathbf{k}\sigma}$  spinors which reduces the  $2 \times 2$  matrix to a diagonal form. This means to diagonalise each  $h_{\mathbf{k}\sigma}$ . This is obtained through a rotation around the  $y$  axis:

$$d_{\mathbf{k}\sigma} = W_{\mathbf{k}\sigma} h_{\mathbf{k}\sigma} W_{\mathbf{k}\sigma}^\dagger \quad \text{with} \quad d_{\mathbf{k}\sigma} \equiv \begin{bmatrix} E_{\mathbf{k}\sigma} & \\ & -E_{\mathbf{k}\sigma} \end{bmatrix} \quad (2.30)$$

The matrix  $W_{\mathbf{k}\sigma}$  is unitary, and gives a counter-clockwise rotation by an angle  $2\theta_{\mathbf{k}\sigma}$  around the  $y$  axis:

$$\begin{aligned} W_{\mathbf{k}\sigma} &\equiv e^{-i\theta_{\mathbf{k}\sigma} \tau^y} \\ &= \cos \theta_{\mathbf{k}\sigma} - i \sin \theta_{\mathbf{k}\sigma} \tau^y \\ &= \begin{bmatrix} \cos \theta_{\mathbf{k}\sigma} & -\sin \theta_{\mathbf{k}\sigma} \\ \sin \theta_{\mathbf{k}\sigma} & \cos \theta_{\mathbf{k}\sigma} \end{bmatrix} \end{aligned} \quad (2.31)$$



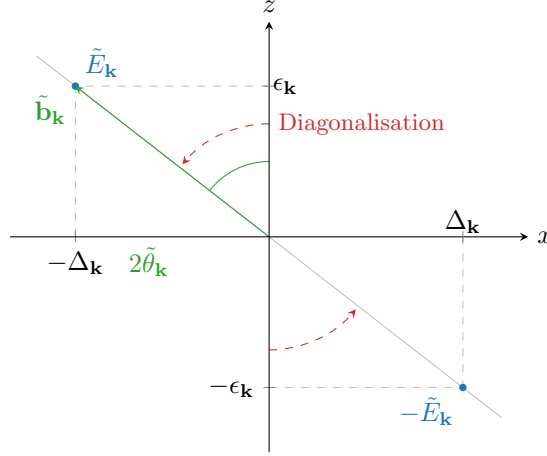


Figure 2.2 | Sketch of the diagonalisation procedure for the HM antiferromagnet. To diagonalise the HF hamiltonian, we align the  $z$  axis with the pseudo-field.

Its eigenvalues are  $\pm E_{\mathbf{k}\sigma}$ , with

$$E_{\mathbf{k}\sigma} = \sqrt{\epsilon_{\mathbf{k}\sigma}^2 + |\Delta_{\mathbf{k}\sigma}|^2} \quad (2.32)$$

In Fig. 2.2 we sketch the pseudo-magnetic field in the  $xz$  plane, and the diagonalisation procedure.  $W_{\mathbf{k}\sigma}$  is a rotation by an angle  $2\theta_{\mathbf{k}\sigma}$  around the  $y$  axis, and in the end aligns the original  $z$  axis with the pseudofield axis.

Applying the rotation matrix to the spinors we obtain new spinors of  $\gamma^{(\pm)}$  fermions,

$$\hat{\Gamma}_{\mathbf{k}\sigma} = W_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} = \begin{bmatrix} \hat{\gamma}_{\mathbf{k}\sigma}^{(+)} \\ \hat{\gamma}_{\mathbf{k}\sigma}^{(-)} \end{bmatrix} \quad (2.33)$$

In the end we have the non-interacting hamiltonian:

$$\begin{aligned} \hat{H}_t + \hat{H}_U &\simeq \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Psi}_{\mathbf{k}\sigma}^{\dagger} h_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} + (\dots) \\ &= \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Psi}_{\mathbf{k}\sigma}^{\dagger} W_{\mathbf{k}\sigma}^{\dagger} W_{\mathbf{k}\sigma} h_{\mathbf{k}\sigma} W_{\mathbf{k}\sigma}^{\dagger} W_{\mathbf{k}\sigma} \hat{\Psi}_{\mathbf{k}\sigma} + (\dots) \\ &= \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} \hat{\Gamma}_{\mathbf{k}\sigma}^{\dagger} d_{\mathbf{k}\sigma} \hat{\Gamma}_{\mathbf{k}\sigma} + (\dots) \\ &= \sum_{\mathbf{k} \in \text{MBZ}} \sum_{\sigma} E_{\mathbf{k}\sigma} \left( \hat{\gamma}_{\mathbf{k}\sigma}^{(+)\dagger} \hat{\gamma}_{\mathbf{k}\sigma}^{(+)} - \hat{\gamma}_{\mathbf{k}\sigma}^{(-)\dagger} \hat{\gamma}_{\mathbf{k}\sigma}^{(-)} \right) + (\dots) \end{aligned}$$

where we intend  $(\dots) = nU\hat{N} - E_{\text{H/U}}^{(\text{AF})}$ . The final non-interacting hamiltonian describes a free Fermi gas of  $\gamma^{(\pm)}$  fermions, respectively on the bands  $\pm E_{\mathbf{k}\sigma}$ . Note that these two bands are separated by a gap  $\Delta_{\mathbf{k}\sigma}$ .

We could redefine the pseudospin operators dividing them by an appropriate constant, in order to satisfy exactly the  $\mathfrak{su}(2)$  algebra, and at the same time multiply the pseudo-magnetic field by the same constant. The product  $\mathbf{b}_{\mathbf{k}\sigma} \cdot \hat{\mathbf{s}}_{\mathbf{k}\sigma}$  would be unchanged, and the diagonalisation matrix  $W_{\mathbf{k}\sigma}$  would be the same. Because of this, the aforementioned constant  $C$  is irrelevant.

#### 2.2.4 Features of the AF solution

This subsection is devoted to discussing briefly some features of the AF solution we found. It is organised as a series of unrelated paragraphs, each to derive a precise property or formula we use in the algorithmic computation. With these observations we conclude the part about the local repulsion and extend to full EHM.

**Pseudospin EVs.** The expectation value of the original pseudospin operators in the various directions can be expressed in terms of the tilted pseudospins  $\hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^\alpha \hat{\Gamma}_{\mathbf{k}\sigma}$ ,

$$\begin{aligned}\langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \tau^x \hat{\Psi}_{\mathbf{k}\sigma} \rangle &= -\sin 2\theta_{\mathbf{k}\sigma} \langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \\ \langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \tau^y \hat{\Psi}_{\mathbf{k}\sigma} \rangle &= 0 \\ \langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Psi}_{\mathbf{k}\sigma} \rangle &= \cos 2\theta_{\mathbf{k}\sigma} \langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle\end{aligned}$$

where we used the angular relations of Fig. 2.2. Moving to the tilted frame, the  $z$  component of the pseudo-spin is just a thermal superposition of “up” and “down” states

$$\langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle = f(E_{\mathbf{k}\sigma}; \beta, \tilde{\mu}) - f(-E_{\mathbf{k}\sigma}; \beta, \tilde{\mu}) \quad (2.34)$$

Let us define the thermal factors:

$$\text{Th}_{\mathbf{k}\sigma}^{(\pm)}[\beta, \mu] \equiv f(-E_{\mathbf{k}\sigma}; \beta, \mu) \pm f(E_{\mathbf{k}\sigma}; \beta, \mu) \quad (2.35)$$

which will often appear in computations. We have:

$$\langle \hat{s}_{\mathbf{k}\sigma}^x \rangle = \frac{\Delta_{\mathbf{k}\sigma}}{E_{\mathbf{k}\sigma}} \text{Th}_{\mathbf{k}\sigma}^{(-)}[\beta, \mu] \quad (2.36)$$

$$\langle \hat{s}_{\mathbf{k}\sigma}^y \rangle = 0 \quad (2.37)$$

$$\langle \hat{s}_{\mathbf{k}\sigma}^z \rangle = -\frac{e_{\mathbf{k}\sigma}}{E_{\mathbf{k}\sigma}} \text{Th}_{\mathbf{k}\sigma}^{(-)}[\beta, \mu] \quad (2.38)$$

Gauge invariance guarantees that we can rotate the pseudo-field on the  $xy$  plane, thus obtaining  $\langle \hat{s}_{\mathbf{k}\sigma}^y \rangle \neq 0$ . From these EVs, we get the expression of the self-consistency equation for  $m$ , and the self-consistent formula to compute the density. Note that  $E_{\mathbf{k}\sigma}$  is actually spin independent, and so is the thermal factor. We can neglect the spin index from both.

**Magnetisation self-consistency equation.** Using Eqns. (2.17), (2.18) we get:

$$m = \frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \left\langle \left( \hat{\psi}_{\mathbf{k}\uparrow} + \hat{\psi}_{\mathbf{k}\downarrow}^\dagger \right) - \left( \hat{\psi}_{\mathbf{k}\downarrow} + \hat{\psi}_{\mathbf{k}\uparrow}^\dagger \right) \right\rangle$$


From Tab. 2.2, we recognise a pseudospin EV in direction  $x$ . From Eq. (2.36)

$$\begin{aligned}m &= \frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} [\langle \hat{s}_{\mathbf{k}\uparrow}^x \rangle - \langle \hat{s}_{\mathbf{k}\downarrow}^x \rangle] \\ &= \frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\text{Re}\{\Delta_{\mathbf{k}\uparrow}\} - \text{Re}\{\Delta_{\mathbf{k}\downarrow}\}}{E_{\mathbf{k}}} \text{Th}_{\mathbf{k}}^{(-)}[\beta, \mu] \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\Delta_{\mathbf{k}\uparrow}}{E_{\mathbf{k}}} \text{Th}_{\mathbf{k}}^{(-)}[\beta, \mu]\end{aligned} \quad (2.39)$$

In last passage we used  $\Delta_{\mathbf{k}\uparrow} = -\Delta_{\mathbf{k}\downarrow}$ , which follows from the definition of the gap function. The last passage gives the operational self-consistency equation for the HFP  $m$ .

**Density.** Restricting the sum of Eq. (2.13) to the MBZ and extending to both spins, we have:

$$\begin{aligned}n &= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \langle \hat{n}_{\mathbf{k}\sigma} + \hat{n}_{\mathbf{k}+\pi\sigma} \rangle \\ &= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \hat{\Psi}_{\mathbf{k}\sigma} \rangle \\ &= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \\ &= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \left( \langle \hat{\gamma}_{\mathbf{k}\sigma}^{(+)\dagger} \hat{\gamma}_{\mathbf{k}\sigma}^{(+)} \rangle + \langle \hat{\gamma}_{\mathbf{k}\sigma}^{(-)\dagger} \hat{\gamma}_{\mathbf{k}\sigma}^{(-)} \rangle \right) \\ &= \frac{1}{2L_x L_y} \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \text{Th}_{\mathbf{k}\sigma}^{(+)}[\beta, \mu]\end{aligned}$$

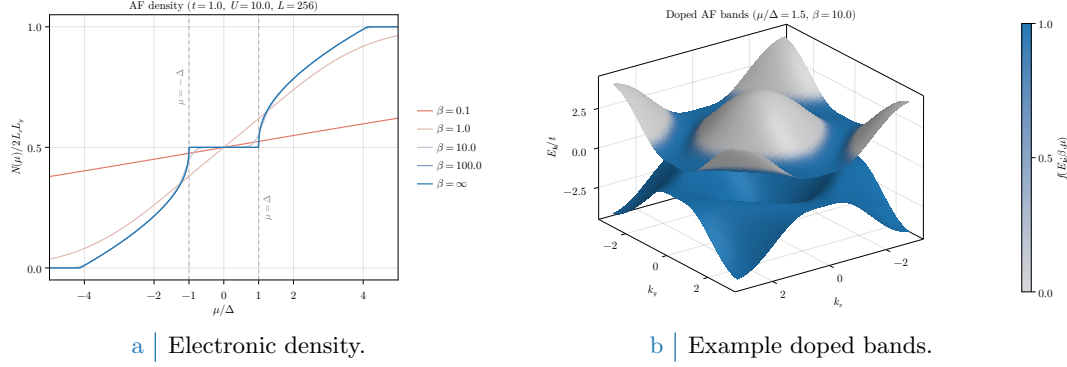

**Figure 2.3** Left panel: electronic density in the AF phase as a function of the chemical potential, measured in relation to the gap  $\Delta = mU$ , at various temperatures. Right panel: example doped bands, with  $\mu/\Delta = 1.5$  set arbitrarily and temperature set to  $\beta = 10$  to enhance smearing effects around FS. Single-state filling is proportional to color magnitude.

where we used unitarity of the  $\hat{\Psi} \rightarrow \hat{\Gamma}$  transformation.

The thermal factor is spin-independent. Moreover, the Bogoliubov bands  $E_{\mathbf{k}\sigma}$  are MBZ periodic. Thus we get the two equivalent formulas for density:

$$n = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \text{Th}_{\mathbf{k}\uparrow}^{(+)}[\beta, \mu] \quad (2.40)$$

$$= \frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \text{Th}_{\mathbf{k}\uparrow}^{(+)}[\beta, \mu] \quad (2.41)$$

The two are perfectly equivalent, but the second one is handier to implement in numeric computations. In Fig. 2.3a we sketch density as a function of the chemical potential. At low temperature, the gap plateau at zero energy is most visible. The lattice is half-filled for any chemical potential inside the plateau range.

**Unconventional metallicity.** Consider now the gran canonical hamiltonian  $\hat{K} \equiv \hat{H} - \mu\hat{N}$  and use Eq. (2.28). The diagonalising matrix remains the same, being

$$-\mu\hat{N} = \sum_{\mathbf{k} \in \text{MBZ}} \begin{bmatrix} -\mu & \\ & -\mu \end{bmatrix} \implies W_{\mathbf{k}\sigma} [h_{\mathbf{k}\sigma} - \mu\mathbb{I}_{2 \times 2}] W_{\mathbf{k}\sigma}^\dagger = d_{\mathbf{k}\sigma} - \mu\mathbb{I}_{2 \times 2} \quad (2.42)$$

thus for non-null chemical potential (i.e. finite doping) the eigenvalues are just shifted,  $\pm E_{\mathbf{k}} - \mu$ . These two bands have the same number of single-particle states. In Fig. 2.3b we sketch the bands  $\pm E_{\mathbf{k}\sigma}$ . Intense colour indicates an almost filled single-particle state, lighter gray colour an almost empty single-particle state. The gap is at zero energy, but at any finite doping  $\tilde{\mu}$  crosses the upper band.

**Instability of the doped antiferromagnet.** As we said at the beginning of this chapter, there exist several ways to realise an Hubbard antiferromagnet. For the conventional HM, it is known [1, 2] that the commensurate AF phase is unstable at any finite doping. This is discussed briefly in Sec. ?? . The key takeaway is that insulating antiferromagnets are stable with respect to spin fluctuations, while metallic antiferromagnets are not. The commensurate AF phase is insulating only at half-filling, because the chemical potential lies within the gap.

The mere existence of a self-consistent solution does not guarantee stability: indeed, when in Sec. ?? we derived the variational solution, we only required it to be a stationary point of the HF energy. In other words, there is no need for the solution to be a minimum. The commensurate AF phase is, in fact, a saddle point of HF energy [1] and any finite doping disrupts commensurate ordering towards uncommensurate phases.

These observations end the description of commensurate antiferromagnetism in the conventional HM. Some more details and observations are provided in App. ??.

### 2.3 Extension to the EHM

We now expand to the EHM, including the non-local interaction  $\hat{H}_V$ . Our strategy is to generalise the discussion of the section above. A formally identical solution with renormalised quantities,

$$\epsilon_{\mathbf{k}\sigma} \rightarrow \tilde{\epsilon}_{\mathbf{k}\sigma} \quad E_{\mathbf{k}\sigma} \rightarrow \tilde{E}_{\mathbf{k}\sigma} \quad \Delta_{\mathbf{k}\sigma} \rightarrow \tilde{\Delta}_{\mathbf{k}\sigma} \quad \mu \rightarrow \tilde{\mu}$$

is coherent by construction with the symmetry structure of the AF phase. Explicitly, the renormalised bands are  $\pm \tilde{E}_{\mathbf{k}\sigma}$ , with

$$\tilde{E}_{\mathbf{k}\sigma} \equiv \sqrt{\tilde{\epsilon}_{\mathbf{k}\sigma}^2 + |\tilde{\Delta}_{\mathbf{k}\sigma}|^2}$$

Moreover, we allow  $\Delta_{\mathbf{k}\sigma}$  to be a general complex function of  $\mathbf{k}$  and  $\sigma$ ,

$$\Delta_{\mathbf{k}\sigma} = \text{Re}\{\Delta_{\mathbf{k}\sigma}\} + i \text{Im}\{\Delta_{\mathbf{k}\sigma}\}$$

We define the renormalised angle  $\tilde{\theta}_{\mathbf{k}\sigma}$  through the relations:

$$\sin 2\tilde{\theta}_{\mathbf{k}\sigma} = \frac{|\tilde{\Delta}_{\mathbf{k}\sigma}|}{\tilde{E}_{\mathbf{k}\sigma}} \quad \cos 2\tilde{\theta}_{\mathbf{k}\sigma} = \frac{\tilde{\epsilon}_{\mathbf{k}\sigma}}{\tilde{E}_{\mathbf{k}\sigma}} \quad (2.43)$$

and similarly the angle  $\tilde{\zeta}_{\mathbf{k}\sigma}$ ,

$$\sin 2\tilde{\zeta}_{\mathbf{k}\sigma} = \frac{\text{Re}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}{|\tilde{\Delta}_{\mathbf{k}\sigma}|} \quad \cos 2\tilde{\zeta}_{\mathbf{k}\sigma} = \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}{|\tilde{\Delta}_{\mathbf{k}\sigma}|} \quad (2.44)$$

A sketch of these angles is given in Fig. 2.4. For a complex gap function, the new diagonalisation matrix is given by:

$$\begin{aligned} \tilde{W}_{\mathbf{k}\sigma} &\equiv e^{-i\tilde{\theta}_{\mathbf{k}\sigma}\tau^y} e^{-i\tilde{\zeta}_{\mathbf{k}\sigma}\tau^z} \\ &= \left( \cos \tilde{\theta}_{\mathbf{k}\sigma} - i \sin \tilde{\theta}_{\mathbf{k}\sigma} \tau^y \right) \left( \cos \tilde{\zeta}_{\mathbf{k}\sigma} - i \sin \tilde{\zeta}_{\mathbf{k}\sigma} \tau^z \right) \\ &= \begin{bmatrix} \cos \tilde{\theta}_{\mathbf{k}\sigma} & -\sin \tilde{\theta}_{\mathbf{k}\sigma} \\ \sin \tilde{\theta}_{\mathbf{k}\sigma} & \cos \tilde{\theta}_{\mathbf{k}\sigma} \end{bmatrix} \begin{bmatrix} e^{-i\tilde{\zeta}_{\mathbf{k}\sigma}} & \\ & e^{i\tilde{\zeta}_{\mathbf{k}\sigma}} \end{bmatrix} \\ &= \begin{bmatrix} \cos \tilde{\theta}_{\mathbf{k}\sigma} e^{-i\tilde{\zeta}_{\mathbf{k}\sigma}} & -\sin \tilde{\theta}_{\mathbf{k}\sigma} e^{i\tilde{\zeta}_{\mathbf{k}\sigma}} \\ \sin \tilde{\theta}_{\mathbf{k}\sigma} e^{-i\tilde{\zeta}_{\mathbf{k}\sigma}} & \cos \tilde{\theta}_{\mathbf{k}\sigma} e^{i\tilde{\zeta}_{\mathbf{k}\sigma}} \end{bmatrix} \end{aligned}$$

The following relations hold (*tilde* sign indicates the renormalised quantity):

$$\begin{aligned} \langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \tau^x \hat{\Psi}_{\mathbf{k}\sigma} \rangle &= -\sin 2\tilde{\theta}_{\mathbf{k}\sigma} \cos 2\tilde{\zeta}_{\mathbf{k}\sigma} \langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \\ \langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \tau^y \hat{\Psi}_{\mathbf{k}\sigma} \rangle &= -\sin 2\tilde{\theta}_{\mathbf{k}\sigma} \sin 2\tilde{\zeta}_{\mathbf{k}\sigma} \langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \\ \langle \hat{\Psi}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Psi}_{\mathbf{k}\sigma} \rangle &= \cos 2\tilde{\theta}_{\mathbf{k}\sigma} \langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle \end{aligned}$$

Let us extend Eq. (2.34) and define the renormalised thermal factors,

$$\langle \hat{\Gamma}_{\mathbf{k}\sigma}^\dagger \tau^z \hat{\Gamma}_{\mathbf{k}\sigma} \rangle = f(\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}) - f(-\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}) \quad (2.45)$$

$$\tilde{\text{Th}}_{\mathbf{k}\sigma}^{(\pm)}[\beta, \tilde{\mu}] \equiv f(-\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}) \pm f(\tilde{E}_{\mathbf{k}\sigma}; \beta, \tilde{\mu}) \quad (2.46)$$

which gives  $\langle \hat{s}_{\mathbf{k}\sigma}^z \rangle = -\tilde{\text{Th}}_{\mathbf{k}\sigma}^{(-)}[\beta, \mu]$ . Pseudospin expectation values are:

$$\langle \hat{s}_{\mathbf{k}\sigma}^x \rangle = \frac{\text{Re}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}{\tilde{E}_{\mathbf{k}\sigma}} \tilde{\text{Th}}_{\mathbf{k}\sigma}^{(-)}[\beta, \mu] \quad (2.47)$$

$$\langle \hat{s}_{\mathbf{k}\sigma}^y \rangle = \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}{\tilde{E}_{\mathbf{k}\sigma}} \tilde{\text{Th}}_{\mathbf{k}\sigma}^{(-)}[\beta, \mu] \quad (2.48)$$

$$\langle \hat{s}_{\mathbf{k}\sigma}^z \rangle = -\frac{\tilde{\epsilon}_{\mathbf{k}\sigma}}{\tilde{E}_{\mathbf{k}\sigma}} \tilde{\text{Th}}_{\mathbf{k}\sigma}^{(-)}[\beta, \mu] \quad (2.49)$$



opposite-spin sectors. Using Eq. (??) we get:

$$\hat{H}_V \simeq \overbrace{-V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \hat{n}_{j\sigma} + \hat{n}_{i\sigma} \langle \hat{n}_{j\sigma} \rangle - \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\sigma} \rangle]}^{\text{s.s.}} - \underbrace{V \sum_{\langle ij \rangle} \sum_{\sigma} [\langle \hat{n}_{i\sigma} \rangle \hat{n}_{j\bar{\sigma}} + \hat{n}_{i\sigma} \langle \hat{n}_{j\bar{\sigma}} \rangle - \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\bar{\sigma}} \rangle]}_{\text{o.s.}} + (\text{all the rest})$$

Let  $i \rightarrow \mathbf{r} = (x, y)$  and  $j \rightarrow \mathbf{r}' = (x', y')$ . We use Eq. (2.1), describing oscillatory density for each spin sector. This Ansatz is composed of two parts: the offset  $n$ , and the oscillatory part  $m$ . The algebraic derivation relative to  $n$  part is, of course, the same as for the normal phase. We now treat separately the “operatorial” part of the braced terms of Eq. (1.4),

$$-V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\langle \hat{n}_{\mathbf{r}\sigma} \rangle \hat{n}_{\mathbf{r}'\sigma} + \hat{n}_{\mathbf{r}\sigma} \langle \hat{n}_{\mathbf{r}'\sigma} \rangle] - V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\langle \hat{n}_{\mathbf{r}\sigma} \rangle \hat{n}_{\mathbf{r}'\bar{\sigma}} + \hat{n}_{\mathbf{r}\sigma} \langle \hat{n}_{\mathbf{r}'\bar{\sigma}} \rangle] \quad (2.52)$$

as well as the its scalar counterpart

$$V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \langle \hat{n}_{\mathbf{r}'\sigma} \rangle + V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \langle \hat{n}_{\mathbf{r}'\bar{\sigma}} \rangle \quad (2.53)$$

accounting for energy shift originated as “leftovers” of Wick’s contractions.

#### 2.4.1 Non-local Hartree channel in the AF phase: analytic derivation

Let us start from the operator of Expr. (2.52). By inserting the Ansatz of Eq. (2.1), we get

$$\overbrace{-nV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\hat{n}_{\mathbf{r}'\sigma} + \hat{n}_{\mathbf{r}\sigma}] + mV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} (-1)^{\delta_{\sigma=\uparrow}} \left[ (-1)^{x+y} \hat{n}_{\mathbf{r}'\sigma} + (-1)^{x'+y'} \hat{n}_{\mathbf{r}\sigma} \right]}^{\text{s.s.}} - \underbrace{-nV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\hat{n}_{\mathbf{r}'\bar{\sigma}} + \hat{n}_{\mathbf{r}\sigma}] + mV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \left[ (-1)^{x+y+\delta_{\sigma=\uparrow}} \hat{n}_{\mathbf{r}'\bar{\sigma}} + (-1)^{x'+y'+\delta_{\bar{\sigma}=\uparrow}} \hat{n}_{\mathbf{r}\sigma} \right]}_{\text{o.s.}}$$

For a square lattice, if  $\mathbf{r} = (x, y)$  and  $\mathbf{r}' = (x', y')$  are NNs, both the following identities are true

$$\begin{aligned} (-1)^{x'+y'} &= (-1)^{x+y+1} \\ (-1)^{\delta_{\bar{\sigma}=\uparrow}} &= (-1)^{\delta_{\sigma=\uparrow}+1} \end{aligned}$$

We obtain

$$\begin{aligned} &\overbrace{-nV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\hat{n}_{\mathbf{r}\sigma} + \hat{n}_{\mathbf{r}'\sigma}]}^{\text{s.s. (density)}} - \overbrace{mV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} (-1)^{x+y+\delta_{\sigma=\uparrow}} [\hat{n}_{\mathbf{r}\sigma} - \hat{n}_{\mathbf{r}'\sigma}]}^{\text{s.s. (magnetisation)}} \\ &\quad - \underbrace{nV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\hat{n}_{\mathbf{r}\sigma} + \hat{n}_{\mathbf{r}'\bar{\sigma}}]}_{\text{o.s. (density)}} + \underbrace{mV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} (-1)^{x+y+\delta_{\sigma=\uparrow}} [\hat{n}_{\mathbf{r}\sigma} + \hat{n}_{\mathbf{r}'\bar{\sigma}}]}_{\text{o.s. (magnetisation)}} \quad (2.54) \end{aligned}$$

In the above expressions we separated in “density” contributions and “magnetisation” ones. Let us deal with them separately.

**Density terms.** Consider s.s. and o.s. (density) terms of Expr. (2.54),

$$-nV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\hat{n}_{\mathbf{r}\sigma} + \hat{n}_{\mathbf{r}'\sigma}] - nV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} [\hat{n}_{\mathbf{r}\sigma} + \hat{n}_{\mathbf{r}'\bar{\sigma}}] \quad (2.55)$$

The discussion is identical to Sec. 1.2.1 for the normal phase, with renormalisation of  $\mu$  being the same of Eq. (1.7).

$$\tilde{\mu} \equiv \mu + n(2zV - U) \quad (2.56)$$

We already included the shift to  $\mu$  due to the local Hartree channel, anticipated in Eq. (2.20).

**Magnetization terms.** The magnetisation s.s. and o.s. terms of Expr. (2.54) perfectly cancel out:

$$mV \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} (-1)^{x+y+\delta_{\sigma=\uparrow}} [(\hat{n}_{\mathbf{r}\sigma} - \hat{n}_{\mathbf{r}'\sigma}) - (\hat{n}_{\mathbf{r}\sigma} + \hat{n}_{\mathbf{r}'\bar{\sigma}})] = 0$$

The Hartree channel only affects  $\mu$ .

### 2.4.2 Non-local Hartree contraction energy

We now collect double counting terms originated by Wick's contraction in Hartree sector. Consider the scalar Expr. (2.53): it's the sum of two parts, the first coming from s.s. sector, the second from o.s. sector. In computing the contraction energy from Hartree channel, being the operatorial result identical to the one obtained for the normal phase, we expect the same to happen for double counting terms.

**s.s. sector double counting energy.** For s.s. terms we get

$$\begin{aligned} V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \langle \hat{n}_{\mathbf{r}'\sigma} \rangle &= V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \overbrace{\left[ (n + (-1)^{x+y}m)(n + (-1)^{x'+y'}m) \right]}^{\sigma=\uparrow} \\ &\quad + V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \underbrace{\left[ (n - (-1)^{x+y}m)(n - (-1)^{x'+y'}m) \right]}_{\sigma=\downarrow} \end{aligned}$$

The mixed terms (those of order  $\mathcal{O}(n) \times \mathcal{O}(m)$ ) cancel out, and since sign factors necessarily alternate on neighbouring sites, the remainder is just

$$V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\sigma} \rangle = V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} 2(n^2 - m^2)$$

**o.s. sector double counting energy.** Proceeding identically on the o.s. sector, we get

$$\begin{aligned} V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \sum_{\sigma} \langle \hat{n}_{\mathbf{r}\sigma} \rangle \langle \hat{n}_{\mathbf{r}'\bar{\sigma}} \rangle &= V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \overbrace{\left[ (n + (-1)^{x+y}m)(n - (-1)^{x'+y'}m) \right]}^{\sigma=\uparrow} \\ &\quad + V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} \underbrace{\left[ (n - (-1)^{x+y}m)(n + (-1)^{x'+y'}m) \right]}_{\sigma=\downarrow} \end{aligned}$$

which gives

$$V \sum_{\langle ij \rangle} \sum_{\sigma} \langle \hat{n}_{i\sigma} \rangle \langle \hat{n}_{j\bar{\sigma}} \rangle = V \sum_{\langle \mathbf{r}\mathbf{r}' \rangle} 2(n^2 + m^2)$$

Hence, the total “contraction energy”, given by sum of both contributions, is identical to the normal one of Eq. (1.9) indeed:

$$E_{H/V}^{(\text{AF})} = -2V \sum_{\langle ij \rangle} \sum_{\sigma} n^2 = 4n^2 V \times \frac{z}{2} L_x L_y \quad (2.57)$$

the minus sign coming from the fact that we are subtracting this energy shift.

## 2.5 Fock effects: gap and bands renormalisation

We explored the Hartree channel. Let us now move to the effects originated by Fock contractions. We can use the very beginning of Sec. 1.3 derivation, up to Eq. (1.11),

$$\begin{aligned} V \sum_{\langle ij \rangle} \sum_{\sigma} & \left[ \langle \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} \rangle \hat{c}_{j\sigma}^{\dagger} \hat{c}_{i\sigma} + \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} \langle \hat{c}_{j\sigma}^{\dagger} \hat{c}_{i\sigma} \rangle - \langle \hat{c}_{i\sigma}^{\dagger} \hat{c}_{j\sigma} \rangle \langle \hat{c}_{j\sigma}^{\dagger} \hat{c}_{i\sigma} \rangle \right] \\ & \stackrel{\mathcal{F}}{=} \frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}, \mathbf{k}'} \sum_{\sigma} [\cos(\delta k_x) + \cos(\delta k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} - E_{F/V}^{(\text{N})} \end{aligned} \quad (2.58)$$

where  $E_{F/V}^{(\text{AF})}$  is defined as in Eq. (1.12), with the expectation value being computed on the AF (thermal) ground-state. As before, we discuss the operatorial part and the scalar part separately.

### 2.5.1 Fock channel in the AF phase: analytic derivation

The commensurate AF phase is described by two EVs being in principle non-zero,

$$|\langle \hat{n}_{\mathbf{k}\sigma} \rangle| \geq 0 \quad |\langle \hat{\psi}_{\mathbf{k}\sigma} \rangle| \geq 0$$

as we specified in Sec. 2.1.2. This implies only two contributions in Eq. (2.58) are non-zero:

$$\mathbf{k} = -\mathbf{k}' \quad \text{or} \quad \mathbf{k} + \boldsymbol{\pi} = -\mathbf{k}'$$

Then we get:

$$\begin{aligned} (\dots) & \stackrel{\mathcal{F}}{=} \frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \\ & \quad \left[ \underbrace{\langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}}_{\text{Diagonal terms}} - \underbrace{\langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma}}_{\text{Off-diagonal terms}} \right] \end{aligned} \quad (2.59)$$

Now, the above equation presents *diagonal* and *off-diagonal* terms.

**Diagonal terms.** The diagonal terms of Eq. (2.59) are products of  $\hat{n}_{\mathbf{k}\sigma}$  operators. Consider Fig. 1.1a:  $\hat{n}_{\mathbf{q}\sigma}$ , with  $\mathbf{q} \equiv \mathbf{K} + \mathbf{k}$ , is coupled to  $\langle \hat{n}_{\mathbf{q}'\sigma} \rangle$  with  $\mathbf{q}' \equiv \mathbf{K} - \mathbf{k}$ . Apply to the diagonal part of Eq. (2.59) this change of variables represented in Fig. 1.1

$$\begin{aligned} & \frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}\sigma} \\ & = \frac{2V}{L_x L_y} \sum_{\mathbf{q}, \mathbf{q}'} \sum_{\sigma} [\cos(\delta q_x) + \cos(\delta q_y)] \langle \hat{c}_{\mathbf{q}\sigma}^{\dagger} \hat{c}_{\mathbf{q}\sigma} \rangle \hat{c}_{\mathbf{q}'\sigma}^{\dagger} \hat{c}_{\mathbf{q}'\sigma} \\ & = \sum_{\gamma, \sigma} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{n}_{\mathbf{q}\sigma} \rangle \right] \times V \sum_{\mathbf{q}'} \varphi_{\mathbf{q}'}^{(\gamma)*} \hat{n}_{\mathbf{q}'\sigma} \end{aligned} \quad (2.60)$$

where in the last passage we substituted the decomposition of Eq. (??). Define as in Eq. (1.17) the EV

$$u_{\mathbf{q}\sigma} \equiv \langle \hat{n}_{\mathbf{q}\sigma} \rangle \quad (2.61)$$



| Symmetry            | Self-consistency equation                                                                                                                                                                                     | Graph   |
|---------------------|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------|
| $s^*$ -wave         | $u^{(s^*)} = -\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y) \frac{\tilde{\epsilon}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$ | Fig. ?? |
| $d_{x^2-y^2}$ -wave | $u^{(d)} = -\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x - \cos k_y) \frac{\tilde{\epsilon}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$   | Fig. ?? |

Table 2.3 | Symmetry and spin resolved self-consistency equations for the harmonics of  $u_{\mathbf{k}}$ .

The expression in square brackets of Eq. (2.60) is just its  $\gamma$  component, and is expanded in

$$\begin{aligned}
u_{\sigma}^{(\gamma)} &= \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{n}_{\mathbf{q}\sigma} \rangle \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \left[ \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{n}_{\mathbf{q}\sigma} \rangle + \varphi_{\mathbf{q}+\pi}^{(\gamma)} \langle \hat{n}_{\mathbf{q}+\pi\sigma} \rangle \right] \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \varphi_{\mathbf{q}}^{(\gamma)} [\langle \hat{n}_{\mathbf{q}\sigma} \rangle - \langle \hat{n}_{\mathbf{q}+\pi\sigma} \rangle] \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\Psi}_{\mathbf{q}\sigma}^{\dagger} \tau^z \hat{\Psi}_{\mathbf{q}\sigma} \rangle \\
&= -\frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \varphi_{\mathbf{q}}^{(\gamma)} \frac{\tilde{\epsilon}_{\mathbf{q}\sigma}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\text{Th}}_{\mathbf{q}\sigma}^{(-)}[\beta, \tilde{\mu}]
\end{aligned} \tag{2.62}$$

where, in the last passage, Eq. (2.49) has been used. We are not breaking inversion symmetry (and as a consequence, neither  $C_2$ ): this implies that, whatever the shape of the renormalised bands, it must be

$$\tilde{\epsilon}_{\mathbf{q}\sigma} = \tilde{\epsilon}_{-\mathbf{q}\sigma} \implies u_{\sigma}^{(p_{\ell})} = 0 \quad \text{with} \quad \ell \in \{x, y\}$$

Renormalised bare bands need to be symmetric functions of the moment. Hence for  $\gamma \in \{p_x, p_y\}$  the above sum vanishes. The remaining  $s^*$  and  $d$  symmetries give legitimate HFPs with relative self-consistency equations, reported in Tab. 2.3 using spin degeneracy.

Recognising harmonics, Eq. (2.60) becomes

$$\begin{aligned}
\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}\sigma} \\
= V \sum_{\mathbf{q}, \sigma} \left[ u_{\sigma}^{(s^*)} (\cos q_x + \cos q_y) + u_{\sigma}^{(d)} (\cos q_x - \cos q_y) \right] \hat{c}_{\mathbf{q}\sigma}^{\dagger} \hat{c}_{\mathbf{q}\sigma}
\end{aligned}$$

These two factors, together, define the full bands renormalisation

$$\tilde{\epsilon}_{\mathbf{k}\sigma} \equiv \epsilon_{\mathbf{k}\sigma} + u_{\sigma}^{(s^*)} V (\cos k_x + \cos k_y) + u_{\sigma}^{(d)} V (\cos k_x - \cos k_y) \tag{2.63}$$

as was for the normal phase in Eq. (1.19). In Sec. 1.3.3 we discussed appearance of anisotropic hopping with  $d$ -wave extension of bare bands: here theory predicts something identical. These RMPs are, as before, controlled linearly by  $V$  and in principle can lead to relevant changes in the kinetic sector of the hamiltonian.

**Off-diagonal terms.** Consider off-diagonal terms of Eq. (2.59). These contribute instead to full gap, being out of diagonal in the  $2 \times 2$  hamiltonian matrix of Eq. (2.24). In pseudo-spin picture, they account for a transverse field. Define  $\mathbf{q}, \mathbf{q}'$  as in Fig. 1.1b,

$$\mathbf{q} \equiv \mathbf{K} + \mathbf{k} \quad \mathbf{q}' \equiv \mathbf{K} - \mathbf{k}$$

and rewrite as for Eq. (2.60)

$$\begin{aligned}
& -\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} \\
& = -\sum_{\gamma, \sigma} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{q}\sigma}^\dagger \rangle \right] \times V \sum_{\mathbf{q}' \in \text{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} \hat{\psi}_{\mathbf{q}'\sigma}^\dagger
\end{aligned}$$

Now shift the first sum by an AF vector  $\boldsymbol{\pi}$  defining  $\mathbf{k} + \boldsymbol{\pi} \equiv \mathbf{q}$ , and use Eq. (2.11) as well as reciprocal space periodicity by a BZ,

$$\begin{aligned}
\frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{q}\sigma}^\dagger \rangle &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \varphi_{\mathbf{k}+\boldsymbol{\pi}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{k}+\boldsymbol{\pi}\sigma}^\dagger \rangle \\
&= -\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{k}\sigma} \rangle
\end{aligned}$$

which finally gives

$$\begin{aligned}
& -\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} \\
& = \sum_{\gamma, \sigma} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \right] \times V \sum_{\mathbf{q}' \in \text{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} \hat{\psi}_{\mathbf{q}'\sigma}^\dagger \quad (2.64)
\end{aligned}$$

Proceed as done previously: define the expectation value

$$v_{\mathbf{q}\sigma} \equiv i \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \quad (2.65)$$

(which is just the AF order parameter with a complex factor) and its  $\gamma$ -wave component, with  $\gamma \in \{s^*, d, p_x, p_y\}$ :

$$\begin{aligned}
v_{\sigma}^{(\gamma)} &= \frac{i}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \\
&= \frac{i}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \left[ \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle + \varphi_{\mathbf{q}+\boldsymbol{\pi}}^{(\gamma)} \langle \hat{\psi}_{\mathbf{q}+\boldsymbol{\pi}\sigma} \rangle \right] \\
&= \frac{i}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \varphi_{\mathbf{q}}^{(\gamma)} \left[ \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle - \langle \hat{\psi}_{\mathbf{q}\sigma}^\dagger \rangle \right] \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \varphi_{\mathbf{q}}^{(\gamma)} \langle \hat{\Psi}_{\mathbf{q}\sigma}^\dagger \tau^y \hat{\Psi}_{\mathbf{q}\sigma} \rangle \\
&= \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{MBZ}} \varphi_{\mathbf{q}}^{(\gamma)} \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{q}\sigma}\}}{\tilde{E}_{\mathbf{q}\sigma}} \tilde{\text{Th}}_{\mathbf{q}\sigma}^{(-)}[\beta, \tilde{\mu}] \quad (2.66)
\end{aligned}$$

where we used Eq. (2.11), Tab. 2.2 and Eq. (2.48). There is no particular reason to exclude one component or another. In Tab. 2.4 the four derived self-consistency equations are reported, ignoring spin index.

From structure factors definitions of Tab. ??, we see that:

$$v_{\sigma}^{(s^*)}, v_{\sigma}^{(d)} \in \mathbb{R} \quad v_{\sigma}^{(p_x)}, v_{\sigma}^{(p_y)} \in i\mathbb{R}$$

Getting back to Eq. (2.64) and inserting these components, we get

$$\begin{aligned}
& -\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}+\mathbf{k}+\boldsymbol{\pi}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^\dagger \hat{c}_{\mathbf{K}-\mathbf{k}-\boldsymbol{\pi}\sigma} \\
& = -iV \sum_{\gamma, \sigma} v_{\sigma}^{(\gamma)} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)*} \hat{\psi}_{\mathbf{q}\sigma}^\dagger \quad (2.67)
\end{aligned}$$

| Symmetry            | Self-consistency equation                                                                                                                                                                                               | Graph   |
|---------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------|
| $s^*$ -wave         | $v^{(s^*)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y) \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$ | Fig. ?? |
| $p_x$ -wave         | $v^{(p_x)} = \frac{i\sqrt{2}}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \sin k_x \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$      | Fig. ?? |
| $p_y$ -wave         | $v^{(p_y)} = \frac{i\sqrt{2}}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \sin k_y \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$      | Fig. ?? |
| $d_{x^2-y^2}$ -wave | $v^{(d)} = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x - \cos k_y) \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$   | Fig. ?? |

Table 2.4 | Symmetry and spin resolved self-consistency equations for the harmonics of  $v_{\mathbf{k}}$ .

We can restrict to MBZ as

$$\begin{aligned}
& -\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}+\pi\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}-\pi\sigma} \\
& = -iV \sum_{\gamma, \sigma} \sum_{\mathbf{q} \in \text{MBZ}} \left[ v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} \hat{\psi}_{\mathbf{q}\sigma}^{\dagger} + v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}+\pi}^{(\gamma)*} \hat{\psi}_{\mathbf{q}+\pi\sigma}^{\dagger} \right]
\end{aligned}$$

and use Eq. (2.11), exchanging terms positions

$$\begin{aligned}
& -\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}+\pi\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}-\pi\sigma} \\
& = iV \sum_{\gamma, \sigma} \sum_{\mathbf{q} \in \text{MBZ}} \left[ v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} \hat{\psi}_{\mathbf{q}\sigma} - v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} \hat{\psi}_{\mathbf{q}\sigma}^{\dagger} \right] \quad (2.68)
\end{aligned}$$

Now: recalling Tab. ??, for the four symmetries we are considering, form factors are real-valued for symmetries  $s^*$  and  $d$ , and purely imaginary for  $p_x$  and  $p_y$ . As mentioned before, the same holds for the  $v_{\sigma}^{(\gamma)}$  harmonics. Then

$$i v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} \in i\mathbb{R} \quad (2.69)$$

and to conjugate a purely imaginary number it suffices to put a minus sign in front of it,

$$-i v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} = \left( i v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} \right)^*$$

Therefore, we conclude

$$\begin{aligned}
& -\frac{2V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}} \sum_{\sigma} [\cos(2k_x) + \cos(2k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}+\pi\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}\sigma} \rangle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}-\pi\sigma} \\
& = V \sum_{\gamma, \sigma} \sum_{\mathbf{q} \in \text{MBZ}} \left[ i v_{\sigma}^{(\gamma)} \varphi_{\mathbf{q}}^{(\gamma)*} \hat{\psi}_{\mathbf{q}\sigma} + \text{h.c.} \right] \quad (2.70)
\end{aligned}$$

which is no surprise, since hamiltonian are hermitian operators.

### 2.5.2 Fock contraction energy

Let us now get back to  $E_{\text{F}/V}^{(\text{AF})}$ , the double counting energy of Eq. (2.58). As said before, its definition is the same as for the normal phase, Eq. (1.12), with averaging operation being performed on the AF ground state:

$$E_{\text{F}/V}^{(\text{AF})} \equiv \frac{V}{L_x L_y} \sum_{\mathbf{K}, \mathbf{k}, \mathbf{k}'} \sum_{\sigma} [\cos(\delta k_x) + \cos(\delta k_y)] \langle \hat{c}_{\mathbf{K}+\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}-\mathbf{k}'\sigma} \rangle \langle \hat{c}_{\mathbf{K}-\mathbf{k}\sigma}^{\dagger} \hat{c}_{\mathbf{K}+\mathbf{k}'\sigma} \rangle \quad (2.71)$$

Proceeding exactly as in Eq. (2.59) and making changing variables as in Fig. 1.1, we get

$$E_{F/V}^{(\text{AF})} = \frac{V}{L_x L_y} \sum_{\mathbf{q}, \mathbf{q}'} \sum_{\sigma} [\cos(\delta q_x) + \cos(\delta q_y)] \left[ \underbrace{\langle \hat{n}_{\mathbf{q}\sigma} \rangle \langle \hat{n}_{\mathbf{q}'\sigma} \rangle}_{\text{Diagonal terms}} - \underbrace{\langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \langle \hat{\psi}_{\mathbf{q}'\sigma} \rangle}_{\text{Off-diagonal terms}} \right]$$

Apply the decomposition of Eq. (??) and use Eqns. (2.61), (2.65),

$$E_{F/V}^{(\text{AF})} = \frac{V}{2L_x L_y} \sum_{\gamma, \sigma} \sum_{\mathbf{q}, \mathbf{q}'} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} [u_{\mathbf{q}\sigma} u_{\mathbf{q}'\sigma} + v_{\mathbf{q}\sigma} v_{\mathbf{q}'\sigma}] \quad (2.72)$$

Now: it holds

$$u_{\mathbf{q}\sigma} = \langle \hat{n}_{\mathbf{q}\sigma} \rangle \implies u_{\mathbf{q}\sigma} = u_{\mathbf{q}\sigma}^*$$

and then

$$\begin{aligned} \frac{1}{(L_x L_y)^2} \sum_{\mathbf{q}, \mathbf{q}'} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} u_{\mathbf{q}\sigma} u_{\mathbf{q}'\sigma} &= \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} u_{\mathbf{q}\sigma} \right] \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q}' \in \text{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} u_{\mathbf{q}'\sigma}^* \right] \\ &= |u_{\sigma}^{(\gamma)}|^2 \end{aligned}$$

At the same time, being  $\hat{\psi}_{\mathbf{q}+\pi\sigma} = \hat{\psi}_{\mathbf{q}\sigma}^\dagger$ ,

$$v_{\mathbf{q}\sigma} = i \langle \hat{\psi}_{\mathbf{q}\sigma} \rangle \implies v_{\mathbf{q}+\pi\sigma} = -v_{\mathbf{q}\sigma}^*$$

Since the form factors satisfy  $\varphi_{\mathbf{q}+\pi}^{(\gamma)} = -\varphi_{\mathbf{q}}^{(\gamma)}$ , we get:

$$\begin{aligned} \frac{1}{(L_x L_y)^2} \sum_{\mathbf{q}, \mathbf{q}'} \varphi_{\mathbf{q}}^{(\gamma)} \varphi_{\mathbf{q}'}^{(\gamma)*} v_{\mathbf{q}\sigma} v_{\mathbf{q}'\sigma} &= \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q} \in \text{BZ}} \varphi_{\mathbf{q}}^{(\gamma)} v_{\mathbf{q}\sigma} \right] \left[ \frac{1}{L_x L_y} \sum_{\mathbf{q}' \in \text{BZ}} \varphi_{\mathbf{q}'}^{(\gamma)*} v_{\mathbf{q}'\sigma} \right] \\ &= v_{\sigma}^{(\gamma)} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \varphi_{\mathbf{k}+\pi}^{(\gamma)*} v_{\mathbf{k}+\pi\sigma} \right] \\ &= v_{\sigma}^{(\gamma)} \left[ \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \varphi_{\mathbf{k}}^{(\gamma)*} v_{\mathbf{k}\sigma}^* \right] \\ &= |v_{\sigma}^{(\gamma)}|^2 \end{aligned}$$

where in the second passage we employed the change of variables  $\mathbf{q}' = \mathbf{k} + \pi$  and used BZ periodicity to map the original sum onto a new sum for  $\mathbf{k} \in \text{BZ}$ . Inserting above results in Eq. (2.72), the latter becomes:

$$E_{F/V}^{(\text{AF})} = L_x L_y \times \frac{V}{2} \sum_{\gamma, \sigma} \left[ |u_{\sigma}^{(\gamma)}|^2 + |v_{\sigma}^{(\gamma)}|^2 \right] \quad (2.73)$$

The new HFPs amplitudes contribute positively to contraction energy. The consequences of this fact will be discussed in Sec. 2.7.1.

## 2.6 Full MFT hamiltonian and gap complexification

Finally, it is time to collect everything in a single hamiltonian operator. The approximated hamiltonian is:

$$\begin{aligned} \hat{H} - \mu \hat{N} &\simeq \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \tilde{\epsilon}_{\mathbf{k}\sigma} [\hat{n}_{\mathbf{k}\sigma} - \hat{n}_{\mathbf{k}+\pi\sigma}] - \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \left[ \tilde{\Delta}_{\mathbf{k}\sigma} \hat{\psi}_{\mathbf{k}\sigma} + \tilde{\Delta}_{\mathbf{k}\sigma}^* \hat{\psi}_{\mathbf{k}\sigma}^\dagger \right] \\ &\quad - \tilde{\mu} \hat{N} - \left[ E_{H/U}^{(\text{AF})} + E_{H/V}^{(\text{AF})} + E_{F/V}^{(\text{AF})} \right] \end{aligned} \quad (2.74)$$

where renormalized bands are given by:

$$\tilde{\epsilon}_{\mathbf{k}\sigma} = \epsilon_{\mathbf{k}\sigma} + V \sum_{\gamma \in \{s^*, d\}} u_{\sigma}^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*}$$

and full gap function by

$$\tilde{\Delta}_{\mathbf{k}\sigma} = \Delta_{\mathbf{k}\sigma} - iV \sum_{\gamma} v_{\sigma}^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*} \quad (2.75)$$

The gap correction is purely imaginary, compared to HM gap  $\Delta_{\mathbf{k}\sigma} = (-1)^{\delta_{\sigma=\downarrow}} mU$ . Since there is no other contribution to the  $x$  pseudo-spin projections other than the pure HM ones, spin antisymmetry is preserved in this direction

$$\langle \hat{s}_{\mathbf{k}\sigma}^x \rangle = -\langle \hat{s}_{\mathbf{k}\bar{\sigma}}^x \rangle$$

This property confirms that Eq. (2.50) actually holds. Indeed, we anticipated that the self-consistency equation of the magnetisation should have been identical for the HM and the EHM. The fact that the  $x$  component EV of the pseudospin maintains this antisymmetry relation is a confirmation of that, since the proof that lead us to Eq. (2.39) for the HM was based on this property.

One of the net effects of  $\hat{H}_V$  on the AF phase, with respect to the conventional HM, is “gap complexification”. This is expressed by:

$$|\operatorname{Im}\{\Delta_{\mathbf{k}\sigma}\}| \geq 0 \quad \implies \quad |\langle \hat{s}_{\mathbf{k}\sigma}^y \rangle| \geq 0$$

while for HM the  $y$  pseudo-spin component was identically null.

### 2.6.1 The relative phase in the zero temperature half-filled ground state

In Sec. ??, we derive analytically the AF ground state on conventional HM at zero temperature, as a simple Bloch’s transform of a polarized (tilted) pseudo-spins collective pure state. Eq. (??) reports the final form of said ground-state. Said quantum state is in general pretty similar to conventional BCS state.

At half-filling and zero temperature we can extend that state to the new complexified gap. The HF approximation of the true ground-state is, in the AF sector,

$$|\Psi\rangle = \bigotimes_{\sigma} \bigotimes_{\mathbf{k} \in \text{MBZ}} \left[ \sin \tilde{\theta}_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}\sigma}^{\dagger} + e^{2i\tilde{\zeta}_{\mathbf{k}\sigma}} \cos \tilde{\theta}_{\mathbf{k}\sigma} \hat{c}_{\mathbf{k}+\pi\sigma}^{\dagger} \right] |\Omega_{\mathbf{k}\sigma}\rangle \quad (2.76)$$

The proof is identical to the one provided in Sec. ?? for the HM, apart from renormalisations. Let  $|\mathbf{k}\sigma\rangle \equiv \hat{c}_{\mathbf{k}\sigma}^{\dagger} |\Omega_{\mathbf{k}\sigma}\rangle$ . Then we can write

$$|\Psi\rangle = \bigotimes_{\sigma} \bigotimes_{\mathbf{k} \in \text{MBZ}} \left[ \sin \tilde{\theta}_{\mathbf{k}\sigma} + e^{2i\tilde{\zeta}_{\mathbf{k}\sigma}} \cos \tilde{\theta}_{\mathbf{k}\sigma} \hat{\psi}_{\mathbf{k}\sigma} \right] |\mathbf{k}\sigma\rangle$$

having we used  $|\Omega_{\mathbf{k}\sigma}\rangle = \{\hat{c}_{\mathbf{k}\sigma}, \hat{c}_{\mathbf{k}\sigma}^{\dagger}\} |\Omega_{\mathbf{k}\sigma}\rangle$ .

The angles appearing in above equations are the same of Eqns. (2.43), (2.44). The relative phase  $2\tilde{\zeta}_{\mathbf{k}\sigma}$  is the gap function angle in complex plane, since

$$\begin{aligned} \langle \Psi | \hat{s}_{\mathbf{k}\sigma}^x | \Psi \rangle &= \langle \Psi | \hat{\psi}_{\mathbf{k}\sigma} + \hat{\psi}_{\mathbf{k}\sigma}^{\dagger} | \Psi \rangle \\ &= \sin \tilde{\theta}_{\mathbf{k}\sigma} \cos \tilde{\theta}_{\mathbf{k}\sigma} \left( e^{-2i\tilde{\zeta}_{\mathbf{k}\sigma}} + e^{2i\tilde{\zeta}_{\mathbf{k}\sigma}} \right) \\ &= \sin 2\tilde{\theta}_{\mathbf{k}\sigma} \cos 2\tilde{\zeta}_{\mathbf{k}\sigma} \end{aligned}$$

$$\begin{aligned} \langle \Psi | \hat{s}_{\mathbf{k}\sigma}^y | \Psi \rangle &= i \langle \Psi | \hat{\psi}_{\mathbf{k}\sigma} - \hat{\psi}_{\mathbf{k}\sigma}^{\dagger} | \Psi \rangle \\ &= i \sin \tilde{\theta}_{\mathbf{k}\sigma} \cos \tilde{\theta}_{\mathbf{k}\sigma} \left( e^{-2i\tilde{\zeta}_{\mathbf{k}\sigma}} - e^{2i\tilde{\zeta}_{\mathbf{k}\sigma}} \right) \\ &= \sin 2\tilde{\theta}_{\mathbf{k}\sigma} \sin 2\tilde{\zeta}_{\mathbf{k}\sigma} \end{aligned}$$

These equations are coherent with Eqns. (2.47), (2.48), thus the involved angles (apart from irrelevant  $2\pi$  shifts) coincide.

| Phase | HFPs                                                 |
|-------|------------------------------------------------------|
| sAF   | $\{m, u^{(s*)}, u^{(d)}, v^{(s*)}, v^{(d)}\}$        |
| aAF   | $\{m, u^{(s*)}, u^{(d)}, -iv^{(p_x)}, -iv^{(p_y)}\}$ |

**Table 2.5** | Set of HFP for the two possible realization of the AF phase, respectively a symmetric and an antisymmetric imaginary part of the gap.

### 2.6.2 AF phase flavours and spin degeneracy

In this analysis, antiferromagnetism is realised without breaking inversion symmetry. This translates in the requirement that:

$$\tilde{E}_{\mathbf{k}\sigma} \stackrel{!}{=} \tilde{E}_{-\mathbf{k}\sigma}$$

We know that:

$$\tilde{E}_{\mathbf{k}\sigma} = \sqrt{\tilde{\epsilon}_{\mathbf{k}\sigma}^2 + \text{Re}^2\{\tilde{\Delta}_{\mathbf{k}\sigma}\} + \text{Im}^2\{\tilde{\Delta}_{\mathbf{k}\sigma}\}}$$

Renormalized bare bands as well as the real part of the gap satisfy said inversion symmetry requirement,

$$\tilde{\epsilon}_{\mathbf{k}\sigma} = \tilde{\epsilon}_{-\mathbf{k}\sigma} \quad \text{Re}\{\tilde{\Delta}_{\mathbf{k}\sigma}\} = \text{Re}\{\tilde{\Delta}_{-\mathbf{k}\sigma}\}$$

hence inversion symmetry is respected only if

$$\text{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\} = \pm \text{Im}\{\tilde{\Delta}_{-\mathbf{k}\sigma}\}$$

which is: either the imaginary part of the gap is inversion symmetric, or is antisymmetric. Based on this consideration, we are able to discard two of the four self-consistency equations for the  $v$ -related HFPs listed in Tab. 2.4:  $s^*$  and  $d$ -wave symmetries HFPs are nonzero if  $\text{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}$  is momentum-even;  $p_x$  and  $p_y$ -wave symmetries HFPs are nonzero if  $\text{Im}\{\tilde{\Delta}_{\mathbf{k}\sigma}\}$  is momentum-odd. The two options cannot coexist, and separate simulations can be implemented in the two symmetry sectors.

We name the two possible symmetries “sAF” (symmetric antiferromagnet) and “aAF” (antisymmetric antiferromagnet). The set of HFPs then restricts to these AF structures, and is reported for both cases in Tab. 2.5. The presence itself of two “AF flavours” is not-so-physical, given that up to now we have no clear physical interpretation for  $\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}$ . As we will discuss in Sec. 2.8, it is possible to prove that almost all these new HFPs actually vanish – a fact that is not directly inferrable right now, but can be seen only delving into the discussion of the non-linear map that defines the algorithm. For now, let us proceed integrally with all the HFPs we found and derive the results.

From now on we will omit  $\sigma$  index, working just in the  $\uparrow$  sector. As said in Sec. 2.1, the AF phase does not break  $\mathbb{Z}_2$  spin inversion symmetry, being the SDW ordering generated by a staggered but globally symmetric spin density distribution among sites. The approximated quadratic hamiltonian of Eq. 2.74 is invariant by a  $\sigma \leftrightarrow \bar{\sigma}$  exchange, thus all measurable physical quantities must be.

## 2.7 AF free energy density

In order to derive the free energy density expression for AF phase, we proceed precisely as in Sec. 1.4. The only notable difference is in the expression of entropy density: Eq. (1.23) is written for two opposite bands on MBZ

$$s = s^{(+)} + s^{(-)}$$

with

$$s^{(\pm)} \equiv -\frac{k_B}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \left[ \left(1 - f(\pm \tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu})\right) \ln \left(1 - f(\pm \tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu})\right) + f(\pm \tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \ln f(\pm \tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right] \quad (2.77)$$

Consider also that we are computing free energy on the gran-canonical hamiltonian

$$\hat{H} - \mu\hat{N} \simeq \sum_{\sigma} \sum_{\mathbf{k} \in \text{MBZ}} \left[ (\tilde{E}_{\mathbf{k}} - \tilde{\mu}) \hat{\gamma}_{\mathbf{k}\sigma}^{(+)\dagger} \hat{\gamma}_{\mathbf{k}\sigma}^{(+)} - (\tilde{E}_{\mathbf{k}} + \tilde{\mu}) \hat{\gamma}_{\mathbf{k}\sigma}^{(-)\dagger} \hat{\gamma}_{\mathbf{k}\sigma}^{(-)} \right] + E_c^{(\text{AF})}$$

being  $E_c^{(\text{AF})}$  the total AF contraction energy. Note that on the left-hand side we have  $\mu$  and on the right-hand side its RMP counterpart  $\tilde{\mu}$ .

With identical meaning of the notation with respect to Sec. 1.4, the free energy contributions are:

1. Quasiparticles energy, taking care of spin degeneracy:

$$e_g^{(\text{AF})} = \frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\tilde{E}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) - \frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\tilde{E}_{\mathbf{k}} + \tilde{\mu}) f(-\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu})$$

2. Contraction energy:

$$e_c^{(\text{AF})} = U(m^2 - n^2) + V \left[ 2zn^2 - \sum_{\gamma} \left( |u^{(\gamma)}|^2 + |v^{(\gamma)}|^2 \right) \right]$$

3. Entropic energy

$$e_s^{(\text{AF})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \ln \left( 1 - f(\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right) - \frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\tilde{E}_{\mathbf{k}} - \tilde{\mu}) f(\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \\ + \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \ln \left( 1 - f(-\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right) + \frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\tilde{E}_{\mathbf{k}} + \tilde{\mu}) f(-\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu})$$

4. Chemical potential correction

$$e_n^{(\text{AF})} = \mu n$$

Compose everything

$$f_{\text{MFT}}^{(\text{AF})} \equiv e_g^{(\text{AF})} + e_c^{(\text{AF})} + e_s^{(\text{AF})} + e_n^{(\text{AF})}$$

and we get

$$f_{\text{MFT}}^{(\text{AF})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \left[ \ln \left( 1 - f(\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right) + \ln \left( 1 - f(-\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right) \right] \\ + U m^2 - V \sum_{\gamma} \left[ |u^{(\gamma)}|^2 + |v^{(\gamma)}|^2 \right] + n [\mu + n(2zV - U)]$$

As was for the normal phase, contraction energy and chemical potential energy corrections build up the RMP  $\tilde{\mu}$  of Eq. (2.56),

$$f_{\text{MFT}}^{(\text{AF})} = \frac{2}{\beta L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \left[ \ln \left( 1 - f(\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right) + \ln \left( 1 - f(-\tilde{E}_{\mathbf{k}}; \beta, \tilde{\mu}) \right) \right] \\ + U m^2 - V \sum_{\gamma} \left[ |u^{(\gamma)}|^2 + |v^{(\gamma)}|^2 \right] + \tilde{\mu} n \quad (2.78)$$

In this expression, we see that  $u^{(\gamma)}$ s,  $v^{(\gamma)}$ s contribution is negative, while magnetisation contributes positively. At a first glance, this suggests that a system with no magnetisation and non-zero  $u^{(\gamma)}$ s,  $v^{(\gamma)}$ s would be energetically favoured. In that situation we would have a purely imaginary gap for a non-magnetised phase, which would be not so intuitive to explain physically. In next section we explain how the above expression for the free energy density can be used to give a constraint that proves that said situation is impossible. HFPs are interrelated and the physical solution cannot admit arbitrary values.

### 2.7.1 Energetic constraints on the HFPs

Let us derive a constraint from the free energy density expression. Collecting the terms directly related to the gap function, the following identity holds:

$$Um^2 - V \sum_{\gamma} |v^{(\gamma)}|^2 = \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{|\tilde{\Delta}_{\mathbf{k}}|^2}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] \quad (2.79)$$

The proof is simple and immediate: expanding right-hand side,

$$\begin{aligned} \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{|\tilde{\Delta}_{\mathbf{k}}|^2}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\text{Re}^2\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] \\ &\quad + \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\text{Im}^2\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] \end{aligned}$$

Now:

$$\text{Re}\{\tilde{\Delta}_{\mathbf{k}}\} = Um$$

which implies

$$\begin{aligned} \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\text{Re}^2\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] &= Um \times \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\text{Re}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] \\ &= Um^2 \end{aligned}$$

having we recognised the expression for the magnetisation from Eq. (2.50). Equivalently,

$$\begin{aligned} \text{Im}\{\tilde{\Delta}_{\mathbf{k}}\} &= -V \sum_{\gamma} v^{(\gamma)} \varphi_{\mathbf{k}}^{(\gamma)*} \\ &= -V \sum_{\gamma} v^{(\gamma)*} \varphi_{\mathbf{k}}^{(\gamma)} \end{aligned}$$

where we used Eq. (2.69) to exchange the conjugation operation in the last passage. This implies:

$$\begin{aligned} \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\text{Im}^2\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] &= -V \sum_{\gamma} v^{(\gamma)*} \sum_{\mathbf{k} \in \text{MBZ}} \varphi_{\mathbf{k}}^{(\gamma)} \frac{\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}^{(-)}[\beta, \tilde{\mu}] \\ &= -V \sum_{\gamma} v^{(\gamma)*} \times v^{(\gamma)} \\ &= -V \sum_{\gamma} |v^{(\gamma)*}|^2 \end{aligned}$$

where in second passage we recognised  $v^{(\gamma)}$  given in Eq. (2.66). Then Eq. (2.79) is verified.

A consequence of Eq. (2.79) is that, being the right-hand side positive, for  $V > 0$  the total amplitude of the “complexifiers” vector is maximised,

$$\sum_{\gamma} |v^{(\gamma)}|^2 \leq M \quad \text{being} \quad M^{(\text{AF})} \equiv m^2 \frac{U}{V} \quad (2.80)$$

The above constraint predicts that:

- In the strong coupling limit  $U \ll V$ , gap complexification is suppressed;
- If magnetisation is null, so is the imaginary part of the gap

$$\lim_{m \rightarrow 0} v^{(\gamma)} = 0$$

which is coherent with the entire derivation and takes us back to the normal phase.



Eq. (2.79) is also solved by a null magnetisation and thus null complexifiers. This can be interpreted by the fact that when the constraint is impossible to solve self-consistently, the gap must close.

Eq. (2.80) provides a neat graphic interpretation for the constraint on HFPs in both sAF and aAF phases. At any competition ratio  $U/V$ , the product  $m\sqrt{U/V}$  is the radius of a sphere. Inside this sphere must lie the vector defined by remaining  $v^{(\gamma)}$  HFPs. For our AF flavours, the sphere is actually a circle, being in both cases the total number of HFPs equal to 3, counting also  $m$ . Note that the solution:

$$\forall \gamma \quad : \quad v^{(\gamma)} = 0$$

solves the constraint of Eq. (2.80). These considerations do not imply gap complexification is an actual, observed effect.

### 2.7.2 Free energy at half-filling

Let us discuss the half-filling condition. We start with the identity:

$$\ln\left(1 - \frac{1}{e^x + 1}\right) + \ln\left(1 - \frac{1}{e^{-x} + 1}\right) = \ln\left[\frac{e^x}{(e^x + 1)^2}\right] \\ = x - 2\ln(1 + e^x)$$

Let now  $x = \beta\tilde{E}_{\mathbf{k}}$ . At low temperature for a band with no nodes, we can approximate  $x \rightarrow +\infty$  on the entire BZ. This gives

$$x - 2\ln(1 + e^x) \simeq -x$$

Hence we get the half-filling free energy density substituting ,

$$f_{\text{MFT}}^{(\text{AF})} \simeq -\frac{2}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \tilde{E}_{\mathbf{k}} + Um^2 - V \sum_{\gamma} \left[ |u^{(\gamma)}|^2 + |v^{(\gamma)}|^2 \right]$$

The first term in this sum gives the energy of the fully occupied lower band.

This approximation makes sense when  $\tilde{E}_{\mathbf{k}} \neq 0$  everywhere. This is always realised in AF phase: from the constraint of Eq. (2.80) we know magnetisation is necessary for all gap HFPs; for a magnetised system, whatever the symmetries,

$$\tilde{E}_{\mathbf{k}} = \sqrt{\tilde{\epsilon}_{\mathbf{k}}^2 + (Um)^2 + |\text{Im}\{\Delta_{\mathbf{k}}\}|^2} \geq Um$$

At half filling and low temperature, the system is well approximated by a completely filled electronic band  $-\tilde{E}_{\mathbf{k}}$ , and this correctly gives a simple  $f_{\text{MFT}}^{(\text{AF})}$  approximation.

## 2.8 Theoretical constraints on the AF phase HFPs

Up to now, all we derived was the most general HF mathematical description of a commensurate AF established on EHM, allowing for nematic spatial symmetry breaking as well as non-trivial renormalisation effects. This section, basically a clone of Sec. 1.5, is dedicated to understanding, given the algorithmic problem, how its solutions should behave. As we will see, based on this theoretical analysis we are able to reduce a lot the algorithmic complexity and limit the solution search to a tailored subspace of HFPs space.

We start from considering a robust  $C_4$  antiferromagnet, thus setting  $u^{(d)} = 0$  by hand, and show how the constraints on  $u^{(s^*)}$  mimic those posed for the normal phase in Eq. (1.31). Then we move to a rather convoluted but necessary analysis of the five-components HFPs vector, described for both AF flavours in Tab. 2.5. For the sake of generality, even if – as discussed in Sec. ?? – at finite doping the system is naturally unstable, we take on all calculations at generic  $\tilde{\mu}$ .

### 2.8.1 Robust $C_4$ bands shrinking extension to AF phases

For the normal phase, we saw that when  $C_4$  symmetry is preserved (Sec. 1.5.1) we can conclude immediately that bands renormalisation is actually a shrinking. An identical result holds here: if  $C_4$  symmetry is imposed onto the renormalized bands,

$$\tilde{\epsilon}_{\mathbf{k}\sigma} \equiv (u^{(s^*)}V - 2t)(\cos k_x + \cos k_y)$$

of  $u^{(\gamma)}$ , just the  $s^*$ -wave channel contributes with a single self-consistency equation

$$u^{(s^*)} = -\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (\cos k_x + \cos k_y) \frac{\tilde{\epsilon}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$$

In this situation, we are able to derive constraints for  $u^{(s^*)}$  by analysing the self-consistency equation. As we did for the normal phase:

1. If  $t > 0$  and  $u^{(s^*)} \leq 0$

$$\forall \mathbf{k} \in \text{MBZ} \quad : \quad \tilde{\epsilon}_{\mathbf{k}} \leq 0$$

the equality only holding on the MBZ contour. Looking at the self-consistency equation, all other objects inside the sum are positive-defined. Which gives

$$u^{(s^*)} \leq 0 \quad \implies \quad u^{(s^*)} \geq 0$$

But  $u^{(s^*)} \neq 0$  as long as  $t > 0$ , as can be seen by the self-consistency equation. We conclude necessarily

$$u^{(s^*)} > 0$$

2. If  $t > 0$  and  $u^{(s^*)} \geq 2t/V$

$$\forall \mathbf{k} \in \text{MBZ} \quad : \quad \tilde{\epsilon}_{\mathbf{k}} \geq 0$$

the equality only holding on the MBZ contour. Inverting inequalities from point above, we conclude necessarily

$$u^{(s^*)} < 2t/V$$

The final result,

$$0 < u^{(s^*)} < 2t/V \tag{2.81}$$

is identical to the constraint obtained for the normal phase. Also in AF phase the bare bands are effectively shrunk by  $\hat{H}_V$ .

### 2.8.2 HFPs vanishing in sAF phase

We applied HF methods to the EHM and obtained two flavours of antiferromagnetism, each of which involves five HFPs. The scenario appears to be rich. In this section we present an argument to prove that the actual number of HFPs is much smaller, as many of those are mathematically suppressed.

Let us start from the sAF phase, assuming

$$\text{C}_4 \xrightarrow{\text{SSB}} \text{C}_2$$

The system is described by the five HFPs on the first row of Tab. 2.5 and their self-consistency equations of Tabs. 2.3 and 2.4.

Let us define the functional

$$F[f(\mathbf{k})] \equiv \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]}{\tilde{E}_{\mathbf{k}}} f(\mathbf{k}) \tag{2.82}$$

The functional  $F$  is linear:

$$F[af(\mathbf{k}) + bg(\mathbf{k})] = aF[f(\mathbf{k})] + bF[g(\mathbf{k})] \tag{2.83}$$

being  $a, b \in \mathbb{C}$  and  $f, g$  two integrable functions in reciprocal space. Another handy property is the sign-preserving relation for sign-defined functions. Let for instance

$$\forall \mathbf{k} \quad : \quad f(\mathbf{k}) \geq 0 \quad \implies \quad F[f(\mathbf{k})] \geq 0 \tag{2.84}$$

The relation above is implied by the fact that both  $\tilde{\text{Th}}_{\mathbf{k}}^{(-)}$  and  $\tilde{E}_{\mathbf{k}}$  are positive-defined,

$$\tilde{\text{Th}}_{\mathbf{k}}^{(-)} = \frac{1}{e^{\beta(\tilde{E}_{\mathbf{k}} - \mu)} + 1} - \frac{1}{e^{\beta(-\tilde{E}_{\mathbf{k}} - \mu)} + 1} \geq 0 \quad \tilde{E}_{\mathbf{k}} = \sqrt{\tilde{\epsilon}_{\mathbf{k}}^2 + |\Delta_{\mathbf{k}\sigma}|^2} \geq 0$$

so, being the functional  $F$  essentially a weighted integral over MBZ, any positive-defined function has a positive image. An identical statement with inverted inequalities holds for negative-defined function.

Consider now the self-consistency equation for  $u^{(s^*)}$ : explicitly,

$$\begin{aligned} u^{(s^*)} &= -\frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} (c_x + c_y) \frac{\tilde{\epsilon}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}] \\ &= \frac{[2t - V u^{(s^*)}]}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]}{\tilde{E}_{\mathbf{k}}} (c_x + c_y)^2 - \frac{V u^{(d)}}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]}{\tilde{E}_{\mathbf{k}}} (c_x^2 - c_y^2) \end{aligned}$$

having we used the notation  $c_\ell \equiv \cos k_\ell$  and substituted the full bare bands

$$\tilde{\epsilon}_{\mathbf{k}} \equiv -\left[2t - u_\sigma^{(s^*)} V\right] (c_x + c_y) + u_\sigma^{(d)} V (c_x - c_y)$$

In terms of the functional  $F$ , we can rewrite:

$$\begin{aligned} u^{(s^*)} &= \left[2t - V u^{(s^*)}\right] \times F[(c_x + c_y)^2] - V u^{(d)} \times F[c_x^2 - c_y^2] \\ &= \left[2t - V u^{(s^*)}\right] \times \{F[c_x^2] + 2F[c_x c_y] + F[c_y^2]\} - V u^{(d)} \times \{F[c_x^2] - F[c_y^2]\} \end{aligned}$$

having we used the linearity property of Eq. (2.83) in last passage.

Let now:

$$A \equiv F[c_x^2] \quad B \equiv 2F[c_x c_y] \quad C \equiv F[c_y^2] \quad (2.85)$$

which allows us to rewrite the self-consistency equation as:

$$u^{(s^*)} = \left[2t - V u^{(s^*)}\right] (A + B + C) - V u^{(d)} (A - C)$$

Repeating an identical procedure on the three self-consistency equations for  $u^{(d)}$ ,  $v^{(s^*)}$  and  $v^{(d)}$ , we get the full system:

$$u^{(s^*)} = \left[2t - V u^{(s^*)}\right] (A + B + C) - V u^{(d)} (A - C) \quad (2.86)$$

$$u^{(d)} = \left[2t - V u^{(s^*)}\right] (A - C) - V u^{(d)} (A - B + C) \quad (2.87)$$

$$v^{(s^*)} = -V v^{(s^*)} (A + B + C) - V v^{(d)} (A - C) \quad (2.88)$$

$$v^{(d)} = -V v^{(s^*)} (A - C) - V v^{(d)} (A - B + C) \quad (2.89)$$

These equations define a four-components nonlinear map, whose parameters  $A, B, C$  depend on the HFPs themselves, being the functional  $F$  dependent on the HFPs. Because of this last point, the four equations are coupled to each other and the map does not decouple in two independent sub-maps. Note that the full map would include another equation for the magnetisation.

Aim of this section is to prove that no self-consistent solution exists with non-zero  $u^{(d)}$ ,  $v^{(s^*)}$  and  $v^{(d)}$ . Being the derivation convoluted and abstract enough, let us proceed by enumerating the relevant facts.

1. Let us start by applying a linear transform on the map: define the new “sum” and “difference” variables

$$S_u \equiv u^{(s^*)} + u^{(d)} \quad D_u \equiv u^{(s^*)} - u^{(d)} \quad S_v \equiv v^{(s^*)} + v^{(d)} \quad D_v \equiv v^{(s^*)} - v^{(d)}$$

whose matrix representation is

$$\begin{bmatrix} S_u \\ D_u \\ S_v \\ D_v \end{bmatrix} \equiv \begin{bmatrix} 1 & 1 & & \\ 1 & -1 & & \\ & & 1 & 1 \\ & & 1 & -1 \end{bmatrix} \begin{bmatrix} u^{(s^*)} \\ u^{(d)} \\ v^{(s^*)} \\ v^{(d)} \end{bmatrix}$$

The map transform is obtained by summing and subtracting two couples of equations: Eq. (2.86) and (2.87) (the first two) as well as Eq. (2.88) and (2.89) (the second two). By doing this we get the simplified system:

$$(1 + 2AV)S_u + BVD_u = 2t(2A + B) \quad (2.90)$$

$$(1 + 2CV)D_u + BVS_u = 2t(B + 2C) \quad (2.91)$$

$$(1 + 2AV)S_v + BVD_v = 0 \quad (2.92)$$

$$(1 + 2CV)D_v + BVS_v = 0 \quad (2.93)$$

2. Let  $S_v = 0$ . Then  $D_v = 0$ . From Eq. (2.93), using  $C = F[c_y^2] \geq 0$  implied by Eq. (2.84):

$$\underbrace{(1 + 2CV)}_{>0} D_v = 0 \implies D_v = 0$$

Identically, let  $D_v = 0$ . Then applying the same consideration on Eq. (2.92) with  $C \leftrightarrow A$ , we conclude  $S_v = 0$ . Either both are non-zero or both are zero.

3. Let  $S_v \neq 0$  and  $D_v \neq 0$ . Then  $B \neq 0$ . To prove this, consider for example Eq. (2.92): we are working at  $V > 0$ , thus

$$B = -\frac{1 + 2AV}{V} \frac{S_v}{D_v}$$

which is non-zero because  $A = F[c_x^2] \geq 0$ , the latter following from Eq. (2.84). We could have used identically Eq. (2.93).

4. Let  $S_v \neq 0$  and  $D_v \neq 0$ . Hence the following relation holds:

$$(BV)^2 = (1 + 2CV)(1 + 2AV) \quad (2.94)$$

To prove the latter, it is sufficient to multiply Eq. (2.92) by  $BV \neq 0$  (see point above),

$$BV(1 + 2AV)S_v + (BV)^2 D_v = 0$$

and substitute from Eq. (2.93)  $BVS_v = -(1 + 2CV)D_v$ ,

$$[-(1 + 2CV)(1 + 2AV) + (BV)^2] D_v = 0$$

Since  $D_v \neq 0$  by hypothesis, Eq. (2.94) is implied.

5. Let  $S_v \neq 0$  and  $D_v \neq 0$ . Hence the following relation holds:

$$B + 2C = V(B^2 - 4AC) \quad (2.95)$$

To prove this: multiply Eq. (2.90) by  $BV$  on both sides,

$$BV(1 + 2AV)S_u + (BV)^2 D_u = 2tBV(2A + B)$$

and substitute from Eq. (2.91)  $BVS_u = -(1 + 2CV)D_u + 2t(B + 2C)$ ,

$$\begin{aligned} -(1 + 2CV)(1 + 2AV)D_u + 2t(B + 2C)(1 + 2AV) + (BV)^2 D_u &= 2tBV(2A + B) \\ 2t(B + 2C)(1 + 2AV) &= 2tBV(2A + B) \\ B + 2ABV + 2C + 4ACV &= 2ABV + B^2V \end{aligned}$$

Passing from first to second line we used Eq. (2.94), and in the passage below  $t > 0$ . Last line implies Eq. (2.95).

6. Let  $S_v \neq 0$  and  $D_v \neq 0$ . Then  $B^2 \neq 4AC$ . Indeed, let  $B^2 = 4AC$ . Then from Eq. (2.94),

$$(BV)^2 = 1 + 2V(A + C) + 4ACV^2 \implies 1 + 2V(A + C) = 0$$

which is obviously absurd, being  $A \geq 0$ ,  $C \geq 0$  from Eq. (2.84). A consequence of this implication on Eq. (2.95) is that, at a given  $V$ , the map parameters should satisfy

$$V = \frac{B + 2C}{B^2 - 4AC} \quad (2.96)$$

7. Let  $S_v \neq 0$  and  $D_v \neq 0$ . Then  $A = C$ . To prove this, substitute Eq. (2.96) in Eq. (2.94),

$$\begin{aligned} (B^2 - 4AC) \left( \frac{B + 2C}{B^2 - 4AC} \right)^2 - 2 \frac{B + 2C}{B^2 - 4AC} (A + C) - 1 &= 0 \\ (B + 2C)^2 - 2(B + 2C)(A + C) - (B^2 - 4AC) &= 0 \\ B^2 + 4C^2 + 4BC - 2AB - 2BC - 4AC - 4C^2 - B^2 + 4AC &= 0 \end{aligned}$$

Simplifying all recurring terms, we get

$$2B(C - A) = 0$$

From previous points we know  $B \neq 0$ . Then  $A = C$ .

8. It's impossible to have  $S_v \neq 0$  and  $D_v \neq 0$ . To prove this, assume the contrary and use the point above to reduce Eq. (2.96) to

$$A = C \implies V = \frac{B + 2C}{B^2 - 4C^2} = \frac{1}{B - 2C}$$

Inserting the latter in Eq. (2.93),

$$\begin{aligned} \left( 1 + \frac{2C}{B - 2C} \right) D_v + \frac{B}{B - 2C} S_v &= 0 \\ \frac{B}{B - 2C} D_v + \frac{B}{B - 2C} S_v &= 0 \end{aligned}$$

which implies

$$D_v + S_v = 0 \implies v^{(s^*)} = 0$$

Recalling from Tab. 2.4 the explicit self-consistency equation for  $v^{(d)}$  and setting  $v^{(s^*)} = 0$ ,

$$v^{(d)} = -V v^{(d)} F[(c_x - c_y)^2]$$

and using the positivity rule of Eq. (2.84) we get

$$V > 0 \quad \text{and} \quad F[(c_x - c_y)^2] \geq 0 \implies v^{(d)} = 0$$

because no finite positive number can equal any finite negative number, and *viceversa*. Thus

$$S_v \neq 0 \quad \text{and} \quad D_v \neq 0 \implies v^{(s^*)} = v^{(d)} = 0 \implies S_v = D_v = 0$$

Absurd. We explored any possibility for  $S_v$ ,  $D_v$ : no stable solution with finite values of the HFPs  $v^{(s^*)}$ ,  $v^{(d)}$  exists, thus both must be zero and can be eliminated from the algorithm.

To gain full knowledge on the map fixed point's shape, we should analyze similarly the behaviour of the self-consistency equations for  $u^{(s^*)}$ ,  $u^{(d)}$ . This is done later in Sec. 2.8.4. For now, it suffices to note that – limitedly to the sAF phase – gap complexification is not present. This effect is not a consequence of HF derivation, which remains self-coherent and general; it is instead of the peculiar form of the non-linear map defined by the set of self-consistency equations.

### 2.8.3 HFPs vanishing in aAF phase

Let us discuss the sAF phase. It is described by the five HFPs on the second row of Tab. 2.5, as well as the self-consistency equations of Tabs. 2.3 and 2.4. We continue using the functional  $F$  as defined in Eq. (2.82). We also define  $A, B, C$  as in Eq. (2.85). Let  $s_\ell \equiv \sin k_\ell$ , and

$$P \equiv F[s_x^2] \quad Q \equiv 2F[s_x s_y] \quad R \equiv F[s_y^2] \quad (2.97)$$

Using these definitions, four of five self-consistency equations are given by

$$u^{(s^*)} = \left[2t - Vu^{(s^*)}\right] (A + B + C) - Vu^{(d)}(A - C) \quad (2.98)$$

$$u^{(d)} = \left[2t - Vu^{(s^*)}\right] (A - C) - Vu^{(d)}(A - B + C) \quad (2.99)$$

$$v^{(p_x)} = -Vv^{(p_x)}P - Vv^{(p_y)}Q \quad (2.100)$$

$$v^{(p_y)} = -Vv^{(p_x)}Q - Vv^{(p_y)}R \quad (2.101)$$

Let us prove that both  $v^{(p_\ell)} = 0$ .

1. For the aAF phase,  $Q = 0$ . We write  $Q$  explicitly

$$\begin{aligned} Q &= F[s_x s_y] \\ &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{MBZ}} \frac{\tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]}{\tilde{E}_{\mathbf{k}}} \sin k_x \sin k_y \\ &= \frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} \frac{\tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]}{\tilde{E}_{\mathbf{k}}} \sin k_x \sin k_y \\ &= \frac{1}{2L_x L_y} \sum_{k_x = -\pi}^{+\pi} \sin k_x \sum_{k_y = -\pi}^{+\pi} \frac{\tilde{\text{Th}}_{(k_x, k_y)}^{(-)}[\beta, \tilde{\mu}]}{\tilde{E}_{(k_x, k_y)}} \sin k_y \end{aligned}$$

From second to third line, we used MBZ periodicity. The  $k_y$  sum at last line is null: even if using antiperiodic harmonics for  $\text{Im}\{\tilde{\Delta}_{\mathbf{k}}\}$ , we did not break inversion symmetry neither in  $x$  nor  $y$  direction. Bogoliubov bands  $\tilde{E}_{\mathbf{k}}$  and thermal factors must show said symmetry. The product of a symmetric function ( $\tilde{\text{Th}}/\tilde{E}$ ) with  $\sin k_y$  integrates to zero. This ends the point.

2.  $v^{(p_x)} = 0$ . To see this, just plug  $Q = 0$  in Eq. (2.100),

$$v^{(p_x)} = -Vv^{(p_x)}F[s_x^2]$$

Using the positivity rule of Eq. (2.84) we get

$$V > 0 \quad \text{and} \quad F[s_x^2] \geq 0 \quad \implies \quad v^{(p_x)} = 0$$

3.  $v^{(p_y)} = 0$ . Same proof as point above.

This ends this short section and shows that also for the aAF phase all gap complexifiers actually vanish. This is coherent with the constraint of Eq. (2.80). As a consequence, there is no need to distinguish two AF phases,

$$\text{sAF} = \text{aAF}$$

and gap complexification is a completely “ghost” effect, even if theoretically allowed. All is left is to check for the behaviour of  $u^{(d)}$ .

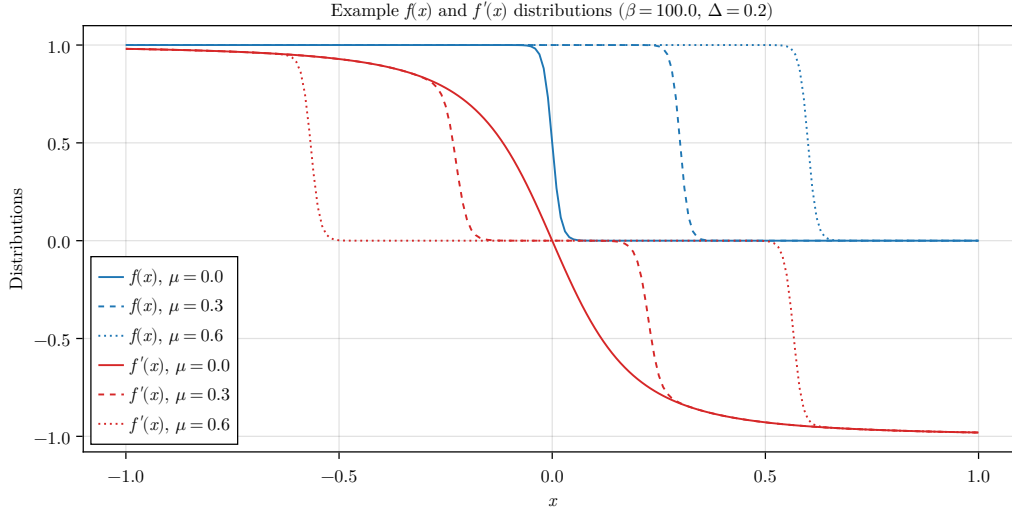


Figure 2.5 | Sketch of the Fermi-Dirac distribution  $f(x)$  and the pseudo-distribution  $f'(x)$  described in text for the normal phase. These example data have been plotted arbitrarily at  $mU = \Delta = 0.2$  for  $\mu = 0.0, 0.3, 0.6$ .

#### 2.8.4 Natural suppression of nematicity within $C_2/\mathbb{Z}_2$ symmetry

A consequence of the two sections above is that the gap function is purely real, non-renormalized and constant across all reciprocal space,

$$\tilde{\Delta}_{\mathbf{k}} = mU \quad \implies \quad \tilde{E}_{\mathbf{k}} = \sqrt{\tilde{\epsilon}_{\mathbf{k}}^2 + (mU)^2}$$

Bogoliubov bands maintain renormalisation through the  $u^{(\gamma)}$  HFPs channel. Aim of this section is to prove that, as was for the normal phase, no nematicity occurs in the AF phase, giving  $u^{(d)} = 0$ .

While the proof given in Sec. 1.5.2 was long and quite elaborated, this one is actually very short. Let us start from recalling the normal phase context:

$$\begin{aligned} \text{Normal phase:} \quad u^{(s^*)} &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \\ u^{(d)} &= \frac{1}{L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x - \cos k_y) f(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \end{aligned}$$

while, using  $\pi$  periodicity, in the present context we can re-write all equations doubling the integration domain,

$$\begin{aligned} \text{AF phase:} \quad u^{(s^*)} &= -\frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x + \cos k_y) \frac{\tilde{\epsilon}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}] \\ u^{(d)} &= -\frac{1}{2L_x L_y} \sum_{\mathbf{k} \in \text{BZ}} (\cos k_x - \cos k_y) \frac{\tilde{\epsilon}_{\mathbf{k}}}{\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}] \end{aligned}$$

Let us define the pseudo distribution

$$f'(\tilde{\epsilon}_{\mathbf{k}}; \beta, \tilde{\mu}) \equiv -\frac{\tilde{\epsilon}_{\mathbf{k}}}{2\tilde{E}_{\mathbf{k}}} \tilde{\text{Th}}_{\mathbf{k}}^{(-)}[\beta, \tilde{\mu}]$$

which, substituted in the self-consistency equations, makes them very similar to the normal ones, up to a  $f \rightarrow f'$  exchange.

The fact that  $u^{(d)} = 0$  follows from the simple consideration that in Sec. 1.5.2 (when showing the same for the normal phase) we never used the specific form of  $f$ ; instead, we only made use of it being monotonically descendent as a function of  $\epsilon_{\mathbf{k}}$ . If  $f'$  also is a monotonically descendent

function of  $\epsilon_{\mathbf{k}}$ , we can re-use the entire derivation of Sec. 1.5.2. Let us show that using a somewhat lighter notation,

$$\epsilon_{\mathbf{k}} \rightarrow x \quad mU \rightarrow \Delta$$

and omitting parametric arguments. The function  $f'$  is given by the product

$$f'(x) = g(x)h(x)$$

with

$$g(x) = -\frac{x}{\sqrt{x^2 + \Delta^2}}$$

$$h(x) = \left( \frac{1}{e^{\beta(\sqrt{x^2 + \Delta^2} - \mu)} + 1} - \frac{1}{e^{\beta(-\sqrt{x^2 + \Delta^2} - \mu)} + 1} \right)$$

The following points are true:

1. The function is antisymmetric about  $x = 0$ , because  $g(x)$  is antisymmetric, while  $h(x)$  is symmetric.
2.  $g(x)$  is monotonically descendent. Its derivative is given by

$$\begin{aligned} \frac{dg}{dx} &= -\frac{\sqrt{x^2 + \Delta^2} - x^2/\sqrt{x^2 + \Delta^2}}{x^2 + \Delta^2} \\ &= -\frac{\Delta^2}{(x^2 + \Delta^2)^{3/2}} \end{aligned}$$

which is always negative.

3. The product  $g(x)h(x)$  is monotonically descendent at positive finite doping. To prove this, we can compute the derivative of  $f'$ ,

$$\frac{df'}{dx} = \frac{dg}{dx}h(x) + g(x)\frac{dh}{dx}$$

We have  $h(x) > 0$ , and as we said  $dg/dx < 0$ , which makes the first term negative. The second is negative too: let

$$E(x) \equiv \sqrt{x^2 + \Delta^2} \quad \implies \quad \frac{dE}{dx} = \frac{x}{E(x)} = -g(x)$$

Then:

$$\begin{aligned} \frac{dh}{dx} &= \frac{d}{dx} \left[ \frac{1}{e^{\beta(-E(x)-\mu)} + 1} - \frac{1}{e^{\beta(E(x)-\mu)} + 1} \right] \\ &= \beta \frac{dE}{dx} \underbrace{\left[ \frac{e^{\beta(-E(x)-\mu)}}{[e^{\beta(-E(x)-\mu)} + 1]^2} + \frac{e^{\beta(E(x)-\mu)}}{[e^{\beta(E(x)-\mu)} + 1]^2} \right]}_{k(x)} \end{aligned}$$

The term in square brackets is obviously positive,  $k(x) > 0$ . Taking all together, we have

$$g(x)\frac{dh}{dx} = -\beta g^2(x)k(x) < 0 \quad \implies \quad \frac{df'}{dx} < 0$$

making  $f'$  descendent monotonicity proven.

These points end the proof: as anticipated,  $f'$  is a monotonically descendent function of  $\epsilon_{\mathbf{k}}$ , a feature that allows us to re-use the entire derivation of Sec. 1.5.2, and conclude that also for the AF phase


$$u^{(d)} = 0$$

while  $u^{(s^*)}$  remains constrained in the limits of Eq. (2.81). Starting from a rather complicated scenario, we were able to reduce all the AF HFPs down to the pair

$$m, u^{(s^*)}$$

Perhaps not-so-excitingly, the real net effect of the non-local extension of the HM is, once again, the shrinking effect on bands. Now it is a matter of numeric analysis to assess if Mott localization takes place.



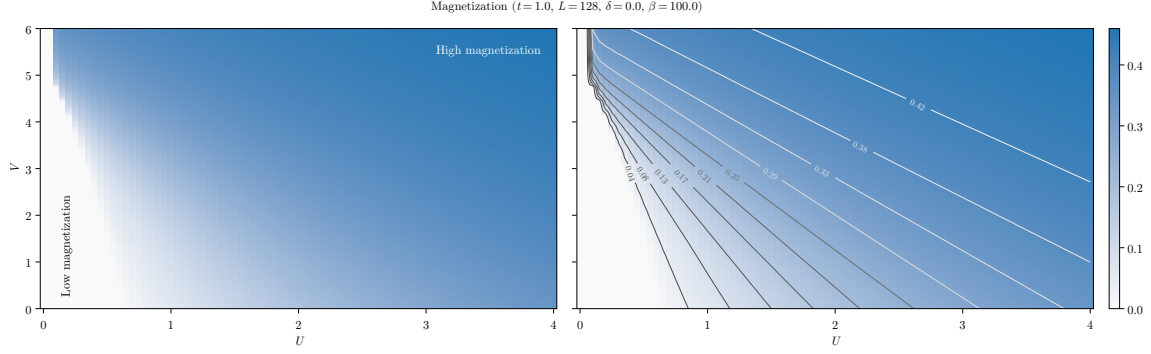

**Figure 2.6** | Plot of the self-consistent convergence values for  $m$  (left panel) and isomagnetic curves computed on the same data (right panel), along which magnetisation is constant. For the sake of graphic clarity, only the points at  $0 \leq U \leq 4$  and  $0 \leq V \leq 6$  are plotted. [Something broke at  $U = 0.05$ ,  $V \geq 5$ , change with new data.]

## 2.9 Discussion of numeric results

In this section we present numeric results. For the AF phase, the HFPs vector, as we thoroughly showed, has two components

$$\mathbf{v} = \begin{bmatrix} m \\ u^{(s^*)} \end{bmatrix} \quad \mathbf{v} = \mathbb{R}^2$$

The resulting model RMPs are, as before:

$$\begin{aligned} \tilde{t}_{ij} &\equiv \left( t - \frac{u^{(s^*)}V}{2} \right) \varphi_{ij}^{(s^*)} \\ \tilde{\mu} &\equiv \mu + n(2zV - U) \end{aligned}$$

In the end, the computational scenario is not so different from the normal phase. The only real difference is our choice of parametric boundaries for simulations:

$$U = 0, 0.05, 0.1, \dots, 8.0 \quad V = 0, 0.05, 0.1, \dots, 8.0 \quad \delta = 0.0$$

We set  $\delta = 0.0$ . As we anticipated in Sec. 2.2.4 (and discuss in Sec. ??), any finite doping implies immediate disruption of commensurate antiferromagnetism, a consideration that makes any simulation at  $\delta > 0$  of low physical significance. Following this consideration, we omit data at finite  $\delta \neq 0$ .

### 2.9.1 Magnetization boost

The convergence values for  $m$  computed in  $(U, V)$  plane are shown in the panels of Fig. 2.6, along with a level curves plot to identify isomagnetic curves (right panel). Note that, to increase graphic clarity in heatmaps bottom left sector, from the plots are omitted the points at  $U \geq 4$  and  $V \geq 6$ . Tolerances on density and HFPs have been set to

$$\Delta n = 10^{-2} \quad \Delta \mathbf{v} = \begin{bmatrix} m: 5 \times 10^{-4} \\ u^{(s^*)}: 5 \times 10^{-4} \end{bmatrix}$$

From heatmaps we see that  $\hat{H}_V$  actually boosts magnetisation. Since the only observable net effect of the non-local interaction is to lower  $t$  by shrinking bands, at any fixed point  $(t, U, V)$  the model can be effectively mapped to

$$\text{EHM: } (t, U, V) \rightarrow \text{HM: } (\tilde{t}, U, 0)$$

being  $\tilde{t}$  dependent on  $V$ . For the pure HM, magnetisation is controlled by the ratio  $U/t$ . To lower  $t$  is physically the same as to increase  $U$ , and from this comes the magnetisation precession visible in

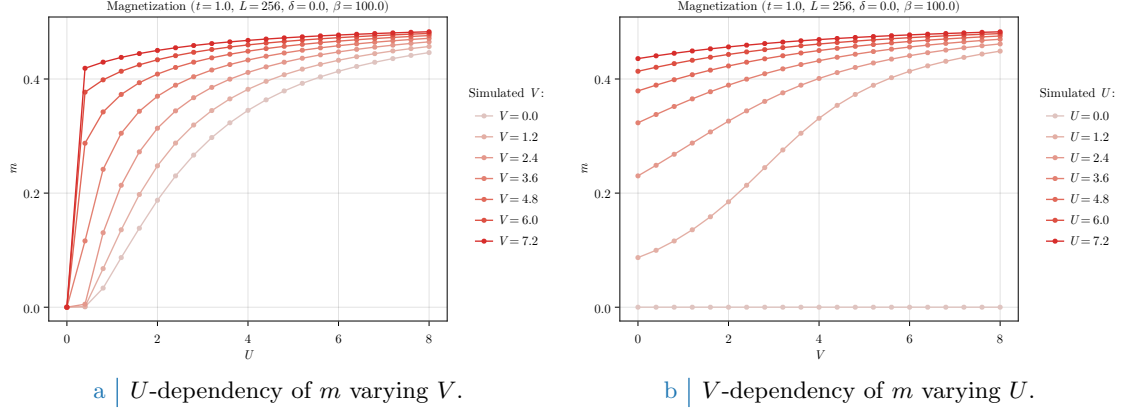


Figure 2.7 | Plot of the self-consistent convergence values for the HFPs  $m$  and  $u^{(s*)}$  in the AF phase.

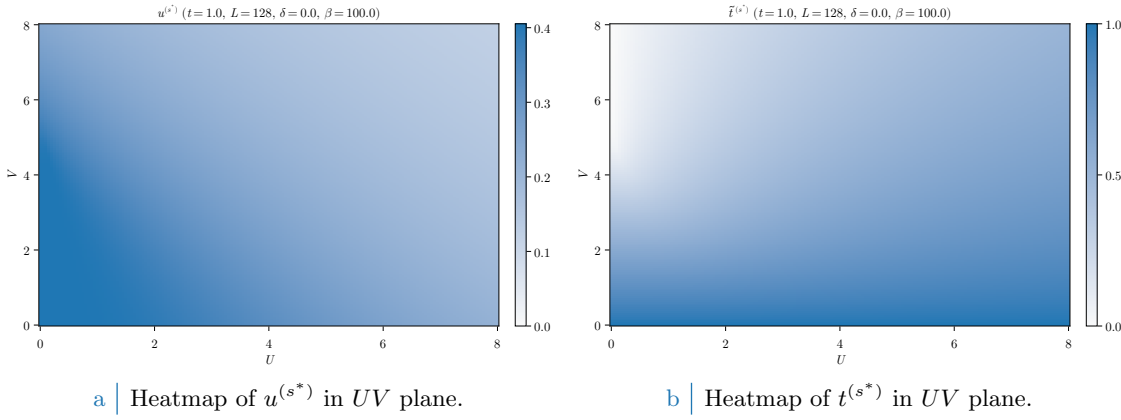


Figure 2.8 | Data for the HFP  $u^{(s*)}$  and  $\tilde{t}^{(s*)}$  varying both  $U$  and  $V$ .

Fig. 2.6. Isomagnetic lines on the right panel show, for  $U$  significantly greater than 0, linear trends whose angular coefficient depend on  $m$  itself. The low- $U$  limit of isomagnetic lines presents some oscillations that are imputable to numeric discretisation of parametric space. [Why isomagnetic curves are lines? Something about  $U/(V - V_c)$  ratio being constant?]

Data shown in Fig. 2.7 confirm clearly this  $V$ -controlled magnetisation “boost”. The effect is more enhanced at low values of  $U$ . As is visible from Fig. 2.7b, magnetisation does not always saturate the same way. For example, considering the curve at  $U = 1.2$ , magnetisation varies following a somewhat tilted sigmoid shape, making boost most effective around  $V \approx 2 \div 4$ . Because of  $m$  saturation, this behaviour is lost at higher  $U$ s.

## 2.9.2 Bands shrinking

The bands shrinking effect was discussed in Sec. 2.8.1 within  $C_4$  symmetry, and then confirmed in Sec. 2.8.4 when trying to extend to nematic structures. As was for the normal phase, we have proven that  $\hat{H}_V$  net effect on the hamiltonian kinetic part is to shrink bands,

$$t \rightarrow \tilde{t} < t$$

For the normal phase, in Sec. 1.6.1 we presented numeric results showing a Mott-localized region appears in  $(\delta, V)$  plane, whose  $\delta \rightarrow 0$  limit was approximately  $V = 4.93t$ , as shown in Fig. 1.7b.

The convergence values for the HFP  $u^{(s*)}$  are shown in Fig. 2.8a, and more in detail in the two panels of Fig. 2.9. In general,  $u^{(s*)}$  decreases monotonically both in  $U$  and in  $V$ . As we already discussed in normal phase, the  $U = 0$  data of Fig. 2.9b present a plateau up to a Mott-critical value. This effect is absent at positive  $U$ s. Both interactions disrupt the HFP; however, the two

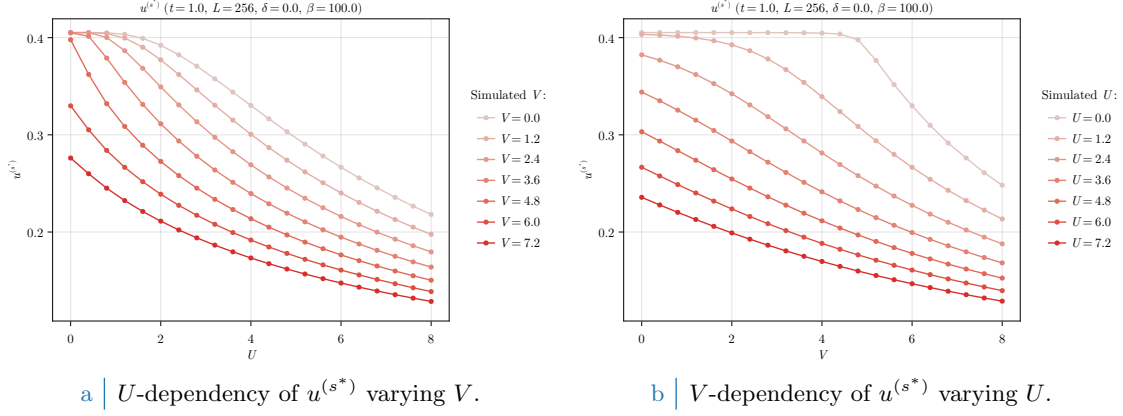


Figure 2.9 | Plot of the self-consistent convergence values for the HFPs  $m$  and  $u^{(s^*)}$  in the AF phase.

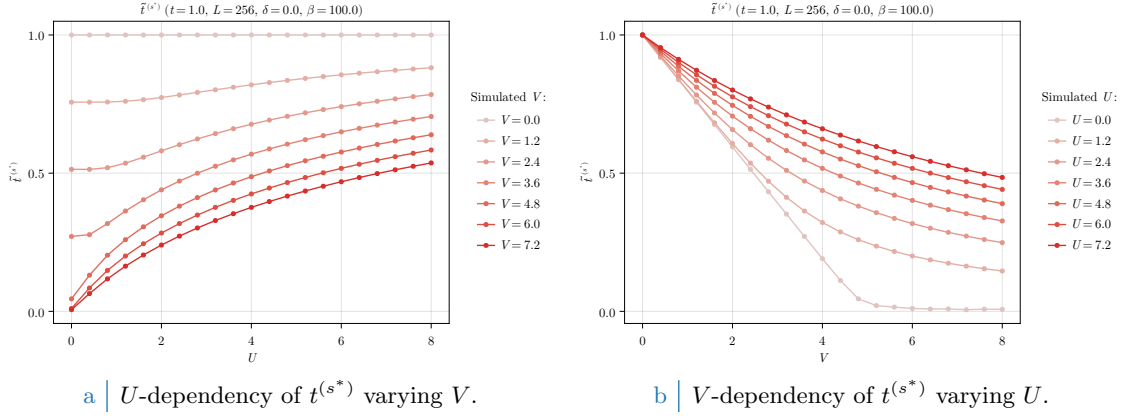


Figure 2.10 | Plot of the self-consistent convergence values for the HFPs  $m$  and  $u^{(s^*)}$  in the AF phase.

limits

$$U \gg 1 \quad \text{and} \quad V \gg 1$$

are much different. By computing the value of  $\tilde{t}^{(s^*)}$ ,

$$\tilde{t}^{(s^*)} = 2t - u^{(s^*)}V$$

we obtain the data of Fig. 2.8b. The limit  $U \gg 1$  taken at fixed  $V$ , also shown in Fig. 2.10a, provides “ $U$ -induced antiferromagnetism”, with bands shrinking effect being almost irrelevant as  $V$  lowers; on the contrary, the opposite limit  $V \gg 1$  taken at fixed  $U$ , also shown in Fig. 2.10b, shrinks bands strongly providing a “Mott-induced antiferromagnetism”.

In  $(U, V)$  space there is not Mott-localised region of the kind we had in  $(\delta, V)$  space for the normal phase (see Fig. 1.7b). At half filling, complete localisation only occurs at  $U = 0$ , as can be seen in the bottom left sector of Fig. 2.10a. Any finite value of  $U$  disrupts bands flattening, thus – being the local repulsion an essential ingredient in Hubbard antiferromagnetism – we can claim, based on numeric evidence, that bands flattening is incompatible with a commensurate AF phase on the half-filled EHM.

### 2.9.3 Solution free energy and entropy densities

In Fig. 2.11 the solution free energy is plotted. In the right panel, Fig. 2.11b, we see that antiferromagnetism becomes more stable at low  $V$ , high  $U$ . The opposite limit of weak local repulsion, strong non-local attraction (top-left corner of Fig. 2.11a) instead increases  $f_{\text{MFT}}$ , reaching zero

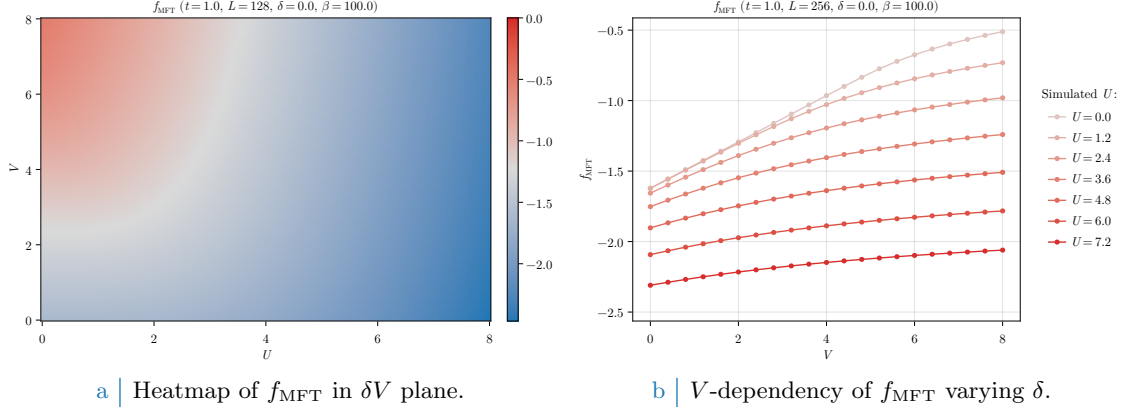


Figure 2.11 | Free energy density of the AF phase.

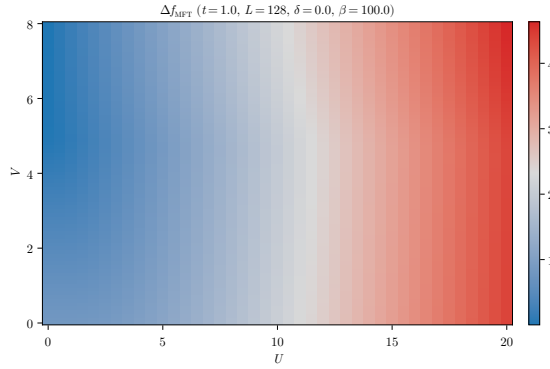


Figure 2.12 | Difference of free energies for the normal phase minus the AF phase.

energy at  $U = 0$ ,  $V > 4.93t$ . The latter is the critical value discussed in Sec. 1.6.1 and computed in Eq. (1.38).


It is then evident how, even if the macroscopic magnetic properties are the same along one isomagnetic line of those plotted in Fig. 2.6, right panel, and thus the realized state exhibits an identical value of  $m$ , much different is the energetic content of the state itself. While in the  $U \gg 1$ , fixed  $V$  limit free energy gain comes from gap amplification – which moves down the Bogoliubov bands  $\tilde{E}_{\mathbf{k}}$  –, in the  $V \gg 1$ , fixed  $U$  limit energies of the lower Bogoliubov band (full at low temperature) are shifted upwards via the Mott localization effect.

The AF phase is always energetically favoured at half-filling, with respect to the normal phase. Considering the energy difference,

$$\Delta f_{\text{MFT}} \equiv f_{\text{MFT}}^{(\text{N})} - f_{\text{MFT}}^{(\text{AF})}$$

shown for a slightly more coarse-grained dataset in Fig. 2.12, we see immediately how  $\Delta f_{\text{MFT}} \geq 0$  in all  $(U, V)$  plane. The normal phase data of Sec. 1.6 having been simulated at  $U = 0$  due to their intrinsic  $U$  independence. The AF phase is simulated in the same range  $0 \leq V \leq 8$ , but for  $0 \leq U \leq 10$ . The comparable normal phase dataset was just a repetition of the  $U = 0$  data at all  $Us$ . As we expect, in the  $V \gg 1$  and low  $U$  limit the energy difference is null: in this limit the two phases tend to coincide, since at  $U = 0.0$  no magnetisation is physically possible. Moreover, the  $U \gg 1$  limit makes the AF phase undoubtedly energetically favoured. Overall, at half filling the interesting free fermions Mott-localization effect is, at least when comparing these phases, existent but surpassed by the high energetic gain of establishing an AF structure at infinitesimal  $U$ . The situation could change at finite doping, a regime we do not investigate limitedly to AF Physics.

At low temperature and half filling, it is not worth plotting entropy density. Half-filled commensurate antiferromagnets are insulators, with two gapped Bogoliubov bands. At low temperature, electronic distribution fills completely the lower band and empties the upper one. Because of this, insulating gapped systems inherently are low entropic.

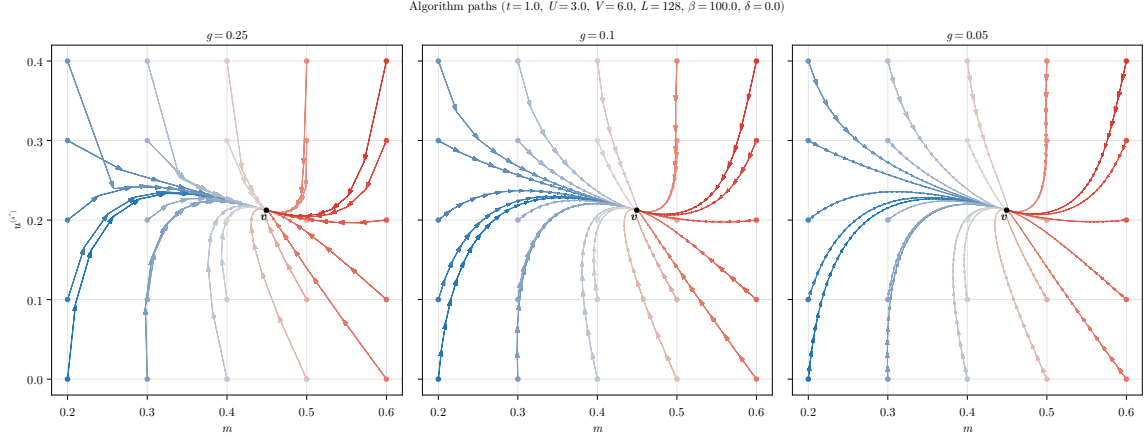

**Figure 2.13** | Quiver plot of algorithmic evolution in HFPs space at fixed model parametrization. The black dot  $\mathbf{v}$  represents the nonlinear map fixed point, while the colored paths the sequences of HFPs coordinates simulated via iterative HF procedure, starting from different HFPs initializers (colored dots).

### 2.9.4 Fixed-point interpretation of HF solution

As a final remark discussing the mathematical structure of the algorithm, we anticipated in Sec. ?? how the reject-mix-iterate scheme upon which our HF algorithm is built can be seen as an effective search for the singular fixed point of a nonlinear map. A physical solution is represented as a HFP vector  $\mathbf{v}$  such that the algorithm is a local identity,

$$A(\mathbf{v}) = \mathbf{v}$$

To predict for a given initializer  $\mathbf{v}_0$  the path it will follow through HFPs space is, in general, highly non-trivial due to the intrinsic nonlinearity of the algorithmic map defined by self-consistency equations for the various HFPs. An example of such nonlinearity is given in the derivation of Secs. 2.8.2, 2.8.3.

In Fig. 2.13 we sketch this concept in a practical situation. In figure are plotted various algorithmic paths through AF HFPs space, with operational setup at

$$U = 3 \quad V = 6 \quad L = 128 \quad \beta = 100 \quad \delta = 0$$

At this point, the self-consistent HF “fixed-point” solution is given by

$$m \approx 0.449 \quad u^{(s^*)} \approx 0.212$$

indicated in panels as the black dot. The three panels show different map evolutions varying the mixing parameter within three choices,  $g \in \{0.25, 0.1, 0.05\}$ . We chose various initializers in the set:

$$\mathbf{v}_0 = \begin{bmatrix} m_0 \\ u_0^{(s^*)} \end{bmatrix} : m_0 \in \{0.2, 0.3, \dots, 0.6\} \quad \text{and} \quad u_0^{(s^*)} \in \{0.0, 0.1, \dots, 0.4\}$$

In figures, different colours indicate different evolutions, while the tip size indicates the magnitude of the algorithmic step in passing from one iteration to the following.

All paths are able to converge to  $\mathbf{v}$ , and the quantity of steps necessary to reach the fixed point, a sort of attractor, increases as we lower  $g$ . To select the correct  $g$  turns out to be the real algorithm fine-tuning knob: as we saw for the normal phase, some model parametrisation could lead to unavoidable algorithmic instabilities. The problem is that we do not know beforehand where the instabilities will occur, and how. The correct  $g$  is the compromise between keeping low the number of steps (larger mixing) and moving slow enough to not diverge when encountering unstable points (smaller mixing). By recursively fine-tuning  $g$  repeating non-converged simulation with more care, we are essentially making the nonlinear map “softer” and curvier, as is in the right panel of Fig. 2.13. It’s not always resource convenient to do so, so for most simulations we stick to a rougher map (like the left panel one) by setting  $g = 0.5$ .



# Bibliography

- [1] Avinash Singh and Zlatko Tešanović. “Collective excitations in a doped antiferromagnet”. en. In: *Physical Review B* 41.1 (Jan. 1990), pp. 614–631. ISSN: 0163-1829, 1095-3795. DOI: [10.1103/PhysRevB.41.614](https://doi.org/10.1103/PhysRevB.41.614). URL: <https://link.aps.org/doi/10.1103/PhysRevB.41.614> (visited on 12/12/2025).
- [2] Avinash Singh, Zlatko Tešanović, and Ju H. Kim. “Doped Hubbard antiferromagnet: Instability and effective interactions”. en. In: *Physical Review B* 44.14 (Oct. 1991), pp. 7757–7759. ISSN: 0163-1829, 1095-3795. DOI: [10.1103/PhysRevB.44.7757](https://doi.org/10.1103/PhysRevB.44.7757). URL: <https://link.aps.org/doi/10.1103/PhysRevB.44.7757> (visited on 12/12/2025).
- [3] Alexander Wietek et al. “Stripes, Antiferromagnetism, and the Pseudogap in the Doped Hubbard Model at Finite Temperature”. en. In: *Physical Review X* 11.3 (July 2021), p. 031007. ISSN: 2160-3308. DOI: [10.1103/PhysRevX.11.031007](https://doi.org/10.1103/PhysRevX.11.031007). URL: <https://link.aps.org/doi/10.1103/PhysRevX.11.031007> (visited on 12/12/2025).
- [4] Eugene Kogan and Godfrey Gumbs. “Green’s Functions and DOS for Some 2D Lattices”. en. In: *Graphene* 10.01 (2021), pp. 1–12. ISSN: 2169-3439, 2169-3471. DOI: [10.4236/graphene.2021.101001](https://doi.org/10.4236/graphene.2021.101001). URL: <https://www.scirp.org/journal/paperinformation?paperid=104591> (visited on 03/26/2026).
- [5] J. G. Bednorz and K. A. Muller. “Possible high-T<sub>c</sub> superconductivity in the Ba-La-Cu-O system”. en. In: *Zeitschrift für Physik B Condensed Matter* 64.2 (June 1986), pp. 189–193. ISSN: 1431-584X. DOI: [10.1007/BF01303701](https://doi.org/10.1007/BF01303701). URL: <https://doi.org/10.1007/BF01303701> (visited on 04/03/2026).
- [6] Liangzi Deng et al. “Ambient-pressure 151 K superconductivity in HgBa<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>8</sub> via pressure quench”. In: *Proceedings of the National Academy of Sciences* 123.11 (Mar. 2026), e2536178123. DOI: [10.1073/pnas.2536178123](https://doi.org/10.1073/pnas.2536178123). URL: <https://www.pnas.org/doi/10.1073/pnas.2536178123> (visited on 04/03/2026).
- [7] B. Keimer et al. “From quantum matter to high-temperature superconductivity in copper oxides”. en. In: *Nature* 518.7538 (Feb. 2015), pp. 179–186. ISSN: 0028-0836, 1476-4687. DOI: [10.1038/nature14165](https://doi.org/10.1038/nature14165). URL: <https://www.nature.com/articles/nature14165> (visited on 03/15/2025).
- [8] D. J. Scalapino. “A common thread: The pairing interaction for unconventional superconductors”. en. In: *Reviews of Modern Physics* 84.4 (Oct. 2012), pp. 1383–1417. ISSN: 0034-6861, 1539-0756. DOI: [10.1103/RevModPhys.84.1383](https://doi.org/10.1103/RevModPhys.84.1383). URL: <https://link.aps.org/doi/10.1103/RevModPhys.84.1383> (visited on 04/03/2026).
- [9] Hari Padma et al. “Beyond-Hubbard pairing in a cuprate ladder”. en. In: *Physical Review X* 15.2 (May 2025), p. 021049. ISSN: 2160-3308. DOI: [10.1103/PhysRevX.15.021049](https://doi.org/10.1103/PhysRevX.15.021049). URL: <https://link.aps.org/doi/10.1103/PhysRevX.15.021049> (visited on 04/03/2026).
- [10] Antoine Georges et al. “Dynamical mean-field theory of strongly correlated fermion systems and the limit of infinite dimensions”. en. In: *Reviews of Modern Physics* 68.1 (Jan. 1996), pp. 13–125. ISSN: 0034-6861, 1539-0756. DOI: [10.1103/RevModPhys.68.13](https://doi.org/10.1103/RevModPhys.68.13). URL: <https://link.aps.org/doi/10.1103/RevModPhys.68.13> (visited on 03/15/2025).
- [11] J. E. Hirsch. “Two-dimensional Hubbard model: Numerical simulation study”. In: *Phys. Rev. B* 31 (7 Apr. 1985), pp. 4403–4419. DOI: [10.1103/PhysRevB.31.4403](https://doi.org/10.1103/PhysRevB.31.4403). URL: <https://link.aps.org/doi/10.1103/PhysRevB.31.4403>.

- [12] Robin Scholle et al. “Comprehensive mean-field analysis of magnetic and charge orders in the two-dimensional Hubbard model”. In: *Phys. Rev. B* 108 (3 July 2023), p. 035139. DOI: [10.1103/PhysRevB.108.035139](https://doi.org/10.1103/PhysRevB.108.035139). URL: <https://link.aps.org/doi/10.1103/PhysRevB.108.035139>.
- [13] Zhangkai Cao et al. “Dominant  $p$ -wave pairing induced by nearest-neighbor attraction in the square-lattice extended Hubbard model”. In: *Phys. Rev. B* 111 (2 Jan. 2025), p. 024509. DOI: [10.1103/PhysRevB.111.024509](https://doi.org/10.1103/PhysRevB.111.024509). URL: <https://link.aps.org/doi/10.1103/PhysRevB.111.024509>.
- [14] Daniel P. Arovas et al. “The Hubbard Model”. In: *Annual Review of Condensed Matter Physics* 13. Volume 13, 2022 (2022), pp. 239–274. ISSN: 1947-5462. DOI: [10.1146/annurev-conmatphys-031620-102024](https://doi.org/10.1146/annurev-conmatphys-031620-102024). URL: <https://www.annualreviews.org/content/journals/10.1146/annurev-conmatphys-031620-102024>.
- [15] Kazuyoshi Yoshimi, Takeo Kato, and Hideaki Maebashi. “Enhanced Spin Susceptibility toward the Charge-Ordering Transition in a Two-Dimensional Extended Hubbard Model”. In: *Journal of the Physical Society of Japan* 78.10 (Oct. 2009), p. 104002. ISSN: 0031-9015. DOI: [10.1143/JPSJ.78.104002](https://doi.org/10.1143/JPSJ.78.104002). URL: <https://journals.jps.jp/doi/10.1143/JPSJ.78.104002> (visited on 04/17/2026).
- [16] Ashvin Vishwanath. “Dirac Nodes and Quantized Thermal Hall Effect in the Mixed State of d-wave Superconductors”. In: *Physical Review B* 66.6 (Aug. 2002). arXiv:cond-mat/0104213, p. 064504. ISSN: 0163-1829, 1095-3795. DOI: [10.1103/PhysRevB.66.064504](https://doi.org/10.1103/PhysRevB.66.064504). URL: <http://arxiv.org/abs/cond-mat/0104213> (visited on 01/05/2026).
- [17] P. Senarath Yapa et al. “Mixed-symmetry superconductivity and the energy gap”. en. In: *Physica C: Superconductivity and its Applications* 633 (June 2025), p. 1354719. ISSN: 09214534. DOI: [10.1016/j.physc.2025.1354719](https://doi.org/10.1016/j.physc.2025.1354719). URL: <https://linkinghub.elsevier.com/retrieve/pii/S0921453425000723> (visited on 01/06/2026).
- [18] Joel Hutchinson and Frank Marsiglio. “Mixed temperature-dependent order parameters in the extended Hubbard model”. en. In: *Journal of Physics: Condensed Matter* 33.6 (Feb. 2021), p. 065603. ISSN: 0953-8984, 1361-648X. DOI: [10.1088/1361-648X/abc801](https://doi.org/10.1088/1361-648X/abc801). URL: <https://iopscience.iop.org/article/10.1088/1361-648X/abc801> (visited on 01/06/2026).
- [19] C. Zhou and H. J. Schulz. “Density of states and tunneling spectra in two-dimensional d-wave superconductors”. In: *Physical Review B* 45.13 (Apr. 1992). Publisher: American Physical Society, pp. 7397–7401. DOI: [10.1103/PhysRevB.45.7397](https://doi.org/10.1103/PhysRevB.45.7397). URL: <https://link.aps.org/doi/10.1103/PhysRevB.45.7397> (visited on 01/06/2026).
- [20] James F. Annett. “Symmetry of the order parameter for high-temperature superconductivity”. In: *Advances in Physics* 39.2 (Apr. 1990). Publisher: Taylor & Francis eprint: <https://doi.org/10.1080/00018739000101481>, pp. 83–126. ISSN: 0001-8732. DOI: [10.1080/00018739000101481](https://doi.org/10.1080/00018739000101481). URL: <https://doi.org/10.1080/00018739000101481> (visited on 01/06/2026).
- [21] R. Micnas, J. Ranninger, and S. Robaszkiewicz. “Superconductivity in narrow-band systems with local nonretarded attractive interactions”. In: *Reviews of Modern Physics* 62.1 (Jan. 1990). Publisher: American Physical Society, pp. 113–171. DOI: [10.1103/RevModPhys.62.113](https://doi.org/10.1103/RevModPhys.62.113). URL: <https://link.aps.org/doi/10.1103/RevModPhys.62.113> (visited on 01/06/2026).
- [22] Manfred Sgrist and Kazuo Ueda. “Phenomenological theory of unconventional superconductivity”. In: *Reviews of Modern Physics* 63.2 (Apr. 1991). Publisher: American Physical Society, pp. 239–311. DOI: [10.1103/RevModPhys.63.239](https://doi.org/10.1103/RevModPhys.63.239). URL: <https://link.aps.org/doi/10.1103/RevModPhys.63.239> (visited on 01/07/2026).
- [23] Anna E. Böhrer et al. “Nematicity and nematic fluctuations in iron-based superconductors”. en. In: *Nature Physics* 18.12 (Dec. 2022), pp. 1412–1419. ISSN: 1745-2481. DOI: [10.1038/s41567-022-01833-3](https://doi.org/10.1038/s41567-022-01833-3). URL: <https://www.nature.com/articles/s41567-022-01833-3>.



- [24] Simons Collaboration on the Many-Electron Problem et al. “Absence of Superconductivity in the Pure Two-Dimensional Hubbard Model”. In: *Physical Review X* 10.3 (July 2020), p. 031016. DOI: [10.1103/PhysRevX.10.031016](https://doi.org/10.1103/PhysRevX.10.031016). URL: <https://link.aps.org/doi/10.1103/PhysRevX.10.031016> (visited on 03/21/2026).
- [25] Jan Zaanen and Olle Gunnarsson. “Charged magnetic domain lines and the magnetism of high- $T_c$  oxides”. In: *Physical Review B* 40.10 (Oct. 1989), pp. 7391–7394. DOI: [10.1103/PhysRevB.40.7391](https://doi.org/10.1103/PhysRevB.40.7391). URL: <https://link.aps.org/doi/10.1103/PhysRevB.40.7391> (visited on 03/21/2026).
- [26] Masaru Kato et al. “Soliton Lattice Modulation of Incommensurate Spin Density Wave in Two Dimensional Hubbard Model -A Mean Field Study-”. In: *Journal of the Physical Society of Japan* 59.3 (Mar. 1990), pp. 1047–1058. ISSN: 0031-9015. DOI: [10.1143/JPSJ.59.1047](https://doi.org/10.1143/JPSJ.59.1047). URL: <https://journals.jps.jp/doi/10.1143/JPSJ.59.1047> (visited on 03/21/2026).
- [27] Eva Pavarini et al., eds. *Many-body physics: from Kondo to Hubbard: lecture notes of the Autumn School on Correlated Electrons 2015: at Forschungszentrum Jülich, 21-25 September 2015*. en. Band 5. Meeting Name: Autumn School on Correlated Electrons. Forschungszentrum Jülich, 2015. ISBN: 978-3-95806-074-6.
- [28] Piers Coleman. *Introduction to Many-Body Physics*. Cambridge University Press, 2015.
- [29] Giuseppe Grosso and Giuseppe Pastori Parravicini. *Solid State Physics*. Second Edition. Academic Press, 2014.
- [30] Gabriele Giuliani and Giovanni Vignale. *Quantum Theory of the Electron Liquid*. Cambridge University Press, 2005.
- [31] Michele Fabrizio. *A Course in Quantum Many-Body Theory*. Springer, 2022.