A New Catalytic Process for High-Efficiency Synthesis of p-xylene by Methylation of Toluene with CH3Br

5 AUTHORS, INCLUDING:

Shuangfeng Yin
Hunan University
15 PUBLICATIONS **29** CITATIONS

SEE PROFILE

Lang Chen
Hunan University
31 PUBLICATIONS **475** CITATIONS

SEE PROFILE

Chak Tong Au
Hong Kong Baptist University
409 PUBLICATIONS **7,734** CITATIONS

SEE PROFILE

A New Catalytic Process for High-Efficiency Synthesis of *p*-xylene by Methylation of Toluene with CH$_3$Br

Qiang Ouyang, Shuang-Feng Yin, Lang Chen, and Xiao-Ping Zhou

State Key Laboratory of Chemo/Biosensing and Chemometrics, College of Chemistry and Chemical Engineering,
Hunan University, Changsha 410082, Hunan, China

Chak-Tong Au

State Key Laboratory of Chemo/Biosensing and Chemometrics, College of Chemistry and Chemical Engineering,
Hunan University, Changsha 410082, Hunan, China

Dept. of Chemistry, Hong Kong Baptist University, Kowloon Tong, Hong Kong, P.R. China

A new catalytic process for p-*xylene synthesis from the methylation of toluene with CH$_3$Br was proposed. CH$_3$Br was prepared from the catalytic bromination of natural gas (CH$_4$), by using H$_2$O HBr O$_2$ as mediator over supported Rh catalyst. The methylation conditions were investigated using HZSM-5 or modified HZSM-5 catalyst. Under optimal reaction conditions,* p-*xylene selectivity is up to 93%, and* p-*xylene yield is more than 21% at 673 k over the SiP modified HZSM-5 catalyst. Compared to the processes using MeOH or dimethyl carbonate (DMC) as methylation agent, this new process is very attractive in an economic standpoint since CH$_4$ is much cheaper than MeOH and DMC. In addition, the process has other advantages, such as mild reaction conditions, simple operation, high-product yield, and so on. It is predicted that the process has good industrial potential for* para-*xylene production.* © 2012 American Institute of Chemical Engineers *AIChE J*, 59: 532–540, 2013
Keywords: bromomethane, p-Xylene, toluene, HZSM-5, methylation

Introduction

p-Xylene is an important aromatic molecule and is used as a raw material for the formation of terephthalic acid for the manufacture of polyester resins and fibers.[1] *p*-Xylene is mainly produced by toluene selective disproportionation,[2–5] adsorptive separation or crystallization from the other xylene isomers. Although these methods produce high-purity *p*-xylene, relatively high cost is required to obtain it in the desired purity. On the other hand, a considerable amount of benzene is produced as a byproduct in toluene selective disproportionation. In the past decades, many researchers have conducted studies on the synthesis of *p*-xylene by selective alkylation of toluene with methanol over various kinds of heterogeneous catalysts, e.g., ZSM-5,[6–8] zeolite X,[9] zeolite Y,[10] zeolite Beta,[11] modernite,[12] ZSM-12/ZSM-5,[13] and silicalite/HZSM-5.[14–16] Although the alkylation of toluene with methanol to prepare *p*-xylene is a promising synthetic method, a relatively high-reaction temperature (ca. 500°C) is needed, resulting in many side reactions and coke deposition on catalysts.[6] Moreover, the selectivity to and yield of *p*-xylene is not good. Very recently, Li et al.[17–18] reported the use of dimethyl carbonate (DMC) as an alkylation agent for the preparation of *p*-xylene from toluene. However, low-catalytic activity and poor *para*-selectivity were observed over the employed MgO/MCM-22 catalyst, and DMC is not cheap compared to methanol or CH$_4$.

In recent years, we conducted researches on aromatics preparation and natural gas conversion.[19–23] A route (Scheme 1) has been developed for the catalytic conversion of methane using HBr as mediator in the presence of oxygen and H$_2$O.[19–26] The method involves the conversion of methane into CH$_3$Br over a suitable catalyst, followed by the catalytic transformation of CH$_3$Br to higher hydrocarbons and/or other compounds. The steps are conducted at atmospheric pressure, and the HBr is recycled and reused. Because CH$_4$ is relatively cheap, it is highly desirable to develop a new catalytic process for the use of CH$_3$Br as an alkylation agent to transfer toluene into *p*-xylene.

In this article, a new process for preparation of *p*-xylene through the alkylation of toluene with CH$_3$Br is proposed (Scheme 2). In fact, CH$_4$ acts as indirect alkylation agent because HBr is recycled in the system. We examined different catalysts for this reaction and optimized the reaction conditions. In addition, different characterization techniques (e.g., XRD, SEM, NH$_3$-TPD, and BET), was employed to disclose the relationship between structure and surface properties of the catalysts as well as the critical factors influencing the *p*-xylene selectivity.

Experimental

Catalysts preparation

HZSM-5 zeolite with a Si/Al ratio of 50 which was synthesized by hydrothermal method was used as parent

---

Correspondence concerning this article should be addressed to S.-F. Yin at sf_yin@hnu.edu.cn.

Scheme 1. The route for catalytic conversion of meth-
ane using HBr as mediator in the presence
of oxygen and H_2O.

material. The molar ratio of the synthesis solution was 100
SiO_2:1 Al_2O_3:20 TPAOH:20 NaOH:4800 H_2O; and tetraethyl
orthosilicate and aluminum nitrate were used as silicon and
alumina source, respectively. The synthesis solution was
mixed and stirred for 60 min at room temperature and then
poured into a Teflon-lined stainless-steel autoclave for
hydrothermal treatment at 453 K for 24 h. The solid product
was separated by centrifugation, washed several times with
distilled water and ethanol, dried overnight at 383 K, and
calcined in air at 873 K for 7 h. Finally, NH_4-ZSM-5 was
obtained by ion exchange twice with 1 M ammonium nitrate
solution at 353 K for 3 h. Then the zeolite was washed thor-
oughly with deionized water, followed by drying at 383 K,
and calcining at 813 K for 4 h sequentially to form
H—ZSM-5 zeolite.

Most of the modified samples were prepared by the
impregnation method at ambient temperature for 4 h, fol-
lowed by drying at 353 K, and then calcining for 4 h at 813
K. The Si/HZSM-5 catalysts were obtained by impregnating
HZSM-5 samples with methyl silicon oil dissolved in cyclo-
hexane.

Catalyst characterization

The phase structure of the catalysts were characterized by
powder X-ray diffraction (XRD) analysis conducted on a
Rigaku automatic diffractometer (Rigaku D-MAX), with
monochromatized Cu K_α radiation (λ = 0.15406 nm) at a
setting of 40 kV and 80 mA. BET surface area, pore volume
and pore size were measured by using a Micrometrics 201°C
instrument. Scanning electron microscopy (SEM) was
employed to study the morphology and particle size of
HZSM-5 zeolite. Temperature-programmed desorption of
ammonia (NH_3-TPD) experiments were carried out on a
Micrometrics 2920 apparatus to analyze the acid property of
the catalysts. As described elsewhere,[27] the acidity of the
external surface of the catalyst was measured by cracking
1,3,5-triisopropylbenzene (1,3,5-TIPB) molecules which are
too large to enter into the pores of HZSM-5 zeolite. The pro-
cedure is: the catalysts (0.5 g) were installed in quartz glass
tube, and activated at 673 K for 1 h in a flow of nitrogen
before the introduction of 1,3,5-TIPB ($WHSV_{1,3,5-TIP}B$ = 1
h^{-1}) into the reactor tube at 623 K. The cracking products
were propylene, benzene, toluene, ethylbenzene, xylene, tri-
methylbenzene, and so on. The external surface acidity was
evaluated based on the conversion of 1,3,5-TIPB, i.e., (1 -
$TIPB_{unreacted}$/sum of products including benzene ring + TIP-
$B_{unreacted}$) × 100%.[28]
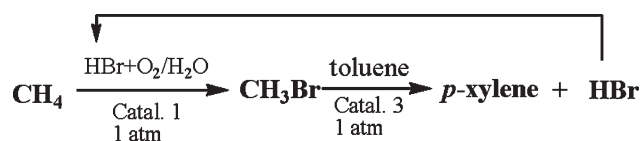
Scheme 2. Process for preparation of *p*-xylene from
the alkylation of toluene with CH_3Br.
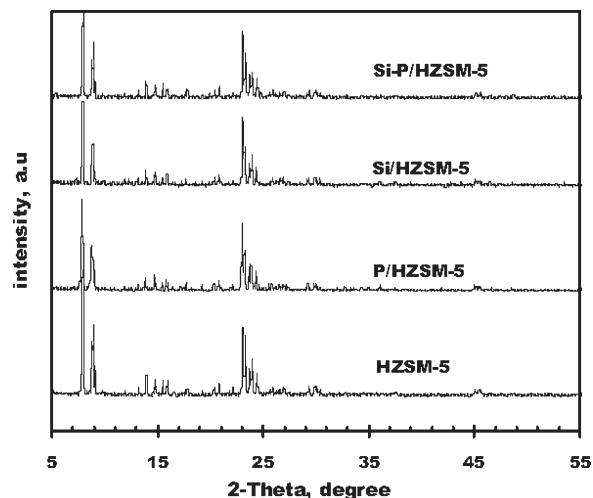
Figure 1. XRD patterns of unmodified and modified
catalysts.

Catalytic evaluation

The alkylation of toluene with CH_3Br was carried out
over a continuous fixed-bed quartz reactor, the experimental
setup is similar to that reported previously.[23] CH_3Br was
prepared from the catalytic bromination of natural gas (CH_4)
by using H_2O + HBr + O_2 as mediator over supported Rh
catalyst, as described elsewhere.[29] The synthesized CH_3Br
gas was separated and carried by N_2 into the methylation re-
actor, which was filled with HZSM-5 or its modified sam-
ples. Substrate of toluene was fed by a syringe pump. The
liquid products in the second hour were collected in an ice-
water condenser and qualitatively analyzed on a GC/MS
(6890N/5973N) using an Agilent HP-5MS capillary column
(30 m × 0.45 mm × 0.8 μm). For quantitative determina-
tion, the collected liquid products were analyzed on an Agi-
lent 7820A GC with FID and Agilent AB—FFAP capillary
column (30 m × 0.25 mm × 0.25 μm). The conversion of
CH_3Br and gaseous products were analyzed on an Agilent
6890N GC with TCD, and Agilent GS—GASPRO capillary
column (30 m × 0.32 mm × 0.25 μm).

Results and Discussion
Catalyst characterization

The XRD patterns of different catalysts are shown in Fig-
ure 1. It can be seen that there are no characteristic peaks
related to the corresponding oxides (P_2O_5, SiO_2) detected
over the modified samples, suggesting that the loaded oxides
are highly dispersed on the surface of HZSM-5. In addition,
there is no change of structure and relative crystallinity of
HZSM-5 after the modification treatment.

The morphology and crystal size of the synthesized
HZSM-5 is shown in Figure 2. The SEM image shows that
the crystals are hexagonal cylindrical in shape (average size:
0.6 × 0.9 × 1.5 μm).

The NH_3-TPD curves of unmodified and modified zeolites
are shown in Figures 3 and 4; the acid amount and strength
distribution of each catalyst are depicted in Table 1. It can
be seen from Figure 3 that there are two desorption peaks
detected over HZSM-5, one at high temperature (633 K),
and the other at low temperature (433 K), attributable to
strong and weak acid sites,[30] respectively. Over the phos-
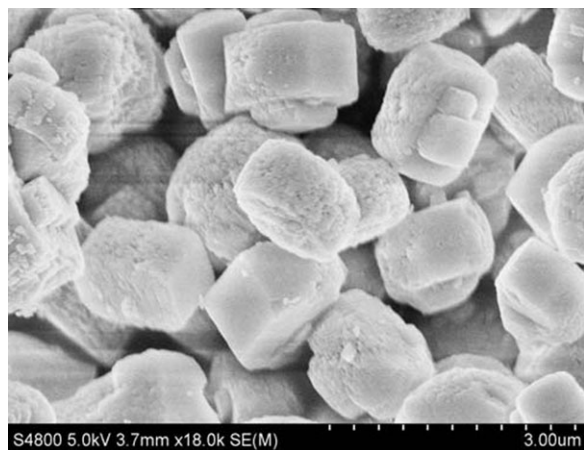phoric acid modified HZSM-5 catalysts, one can see that

Figure 2. SEM images of HZSM-5 crystals.

Figure 4. NH$_3$-TPD curves of HZSM-5, 4 wt % Si/HZSM-5, 8 wt % Si/HZSM-5 and 12 wt % Si/HZSM-5.

with the increase of P$_2$O$_5$ loading, there is rapid decrease in the amount of acid sites, especially the strong ones. At a P$_2$O$_5$ loading of 9 wt %, there is almost complete elimination of strong acid sites. Similar results were observed when HZSM-5 zeolite was modified with methyl silicon oil (depicted in Figure 4). However, the total amount of weak acid sites after silicon modification is more than that after phosphoric acid modification. It is plausible that the molecular diameter of methyl silicon oil is so much larger that Si deposition occurs only on the external surface of HZSM-5 zeolite, and the internal acid sites of HZSM-5 zeolite are not covered.

The changes of specific surface area and pore volume of HZSM-5 zeolite after modification are listed in Table 2. It is clear that HZSM-5 and Si/HZSM-5 are similar in micropores volume. It can be deduced that because the molecules of methyl silicon oil are larger than the pore size of HZSM-5 zeolite, they could not penetrate into the channels of HZSM-5. However, because phosphoric acid can enter into the channels of HZSM-5, modification of zeolite with phosphoric acid leads to a decline of pore volume (from 0.149 to 0.127 cm^3), and surface area (from 385.9 to 373.6 m^2/g).

Catalyst screening

In recent decades, toluene methylation to prepare *p*-xylene is considered to be a promising process and has been studied
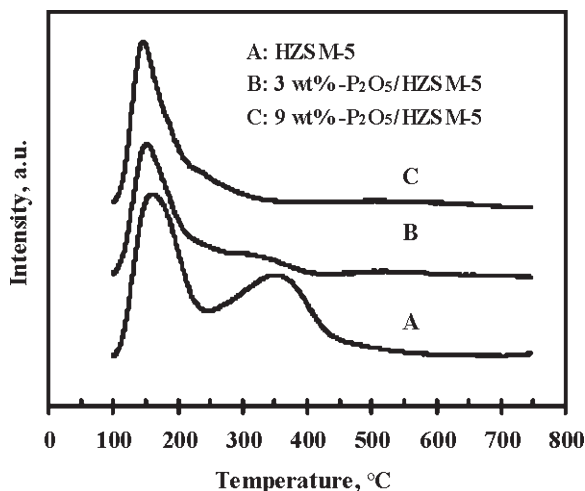
extensively.[14–18,31–38] ZSM-5 zeolite, owing to its unique structure possessing pores of intermediate size (0.5–0.6 nm), has been used extensively as shape-selective catalyst, and lots of measures have been carried out to improve *para*-selectivity, such as modification with metallic[31–34] or nonmetallic agents,[35–36] surface silanation,[37–38] use of ZSM-5/silicalite composites,[14–16] and by optimization of the process variables.[34,36] In this study, we chose HZSM-5 zeolite as parent catalyst and screen the modifiers that were reported in toluene methylation with methanol.

Table 3 summarizes the conversion of toluene, *p*-xylene yield and *para*-xylene selectivity detected over a range of modified catalysts. Compared to unmodified HZSM-5, all the modified HZSM-5 catalysts give a higher *para*-selectivity at the cost of decreasing the conversion of toluene. In terms of *para*-selectivity, P$_2$O$_5$, SiO$_2$, MgO, La$_2$O$_3$, and Sb$_2$O$_3$ are good promoters, especially for P$_2$O$_5$ which is well-known as a good modifier for toluene disproportionation and methylation.[35] However, with the loading of MgO, La$_2$O$_3$, or Sb$_2$O$_3$, there is significant decrease in toluene conversion. It is clear that among the catalysts tested, P/HZSM-5 shows the highest *p*-xylene selectivity (up to 83.5%). The Si/HZSM-5 catalyst is somewhat less-selectivity (51.7% to *p*-xylene), but gives a higher *p*-xylene yield (20.6%).

Effect of methyl silicon oil modification

Surface silanation is an effective method to enhance *para*-selectivity in toluene methylation (using CH$_3$OH as methylating agent) and disproportionation.[39] Table 4 shows the effects of methyl silicon oil content on the activity and

Figure 3. NH$_3$-TPD curves of HZSM-5, 3 wt % P$_2$O$_5$/HZSM-5 and 9 wt % P$_2$O$_5$/HZSM-5.

Table 1. Acidity of HZSM-5 and its Modified Samples

Catalysts	Total amount of acid sites	Weak acid sites (mmol/g)	*p* (%)	Strong acid sites (mmol/g)	*p* (%)
HZSM-5	0.945	0.473	50.1	0.472	49.9
4 wt% Si/HZSM-5	0.568	0.347	61.1	0.221	38.9
8 wt% Si/HZSM-5	0.507	0.393	77.5	0.114	22.5
12 wt% Si/HZSM-5	0.485	0.426	87.8	0.059	12.2
3 wt% P$_2$O$_5$/HZSM-5	0.448	0.417	93.1	0.031	6.9
9 wt% P$_2$O$_5$/HZSM-5	0.434	0.431	99.3	0.03	0.7

p (%) stands for site amount in percentage.

Table 2. Specific Surface Area and Pore Volume of Different Catalysts

Catalyst	S_{BET} (m^2/g)	Total pore volume (cm^3/g)	Micropore volume (cm^3/g)
HZSM-5	385.9	0.213	0.149
Si/HZSM-5[a]	391.9	0.215	0.149
P/HZSM-5[b]	373.6	0.190	0.127

[a]methyl silicon oil content is 12 wt %,
[b]phosphorus pentoxide content is 9 wt %.

para-selectivity in the methylation reaction of toluene with CH$_3$Br. One can see that the conversion of toluene decreases with the rise of methyl silicon oil loading, and with methyl silicon oil content exceeding 12 wt %, *para*-selectivity stabilizes. From the NH$_3$-TPD results of the Si/HZSM-5 catalysts, it is clear that with the rise of methyl silicon oil content there is almost proportional reduction in the amount of acid sites. The strong acid sites on the external surface and at the pore mouths are completely eliminated when the content of methyl silicon oil reaches 12 wt %. Because it is impossible for methyl silicon oil to penetrate into the channels of HZSM-5 zeolite, the acid sites located on the internal surface are not altered and there are still strong acid sites after the modification. We, hence, deduce that the selectivity to *p*-xylene depends on the weak acid sites, and the strong acid sites are favorable for the isomerization of *p*-xylene.

Effect of phosphorus modification

P$_2$O$_5$ has been regarded to be an effective modifier for the reaction of toluene methylation with methanol.[35] We modified HZSM-5 zeolite with phosphoric acid and studied the effect of P$_2$O$_5$ content on catalytic reactivity over the P/HZSM-5 catalyst. The content of P$_2$O$_5$ was varied from 3 to 9 wt %, and the evaluation results are depicted in Table 5. With the increase of P$_2$O$_5$ loading, toluene conversion decreases from 22.0 to 5.4%, and *para*-selectivity increases from 76.7 to nearly 100%. Obviously, when HZSM-5 was modified by P$_2$O$_5$ there was a significant rise of *para*-selectivity. The results of NH$_3$-TPD experiments show that the amount of acid sites decreases with an increase of P$_2$O$_5$ loading. It is well-known that toluene methylation is a typical acid-catalyzed Friedel-Crafts reaction. Therefore, it is easy to explain why the activity of P/HZSM-5 catalysts decreases with rise of P$_2$O$_5$ content. We know that the dimension of H$_3$PO$_4$ is smaller than the pore size of HZSM-5, so the loaded H$_3$PO$_4$ distributed on the outer surface as

well as inside the channels, altering the entire acidity of HZSM-5. As stated before, about 100% *para*-selectivity is observed when strong acid sites are almost eliminated completely at a P$_2$O$_5$ content of 9 wt %. It is known that at such P$_2$O$_5$ content, there is no change in terms of micropores volume and most probable pore size (shown in Table 5). Therefore, the experimental results further confirm that the enhanced *para*-selectivity in the reaction of toluene with CH$_3$Br is mainly due to the elimination of strong acid sites.

The cracking of 1,3,5-TIPB is a suitable probe reaction for determining the activities of external surface of HZSM-5 zeolite. Because a 1,3,5-TIPB molecule is too large to enter into the zeolite pores, the cracking of 1,3,5-TIPB takes place on the external surface. Consequently, the activity of catalysts for the cracking of 1,3,5-TIPB corresponds to the number of acid sites on the external. Figure 5 shows the effect of phosphoric acid and methyl silicon oil modification on cracking 1,3,5-TIPB. It is clear that the external surface acid sites are completely inactivated because there is nearly no 1,3,5-TIPB cracking when methyl silicon oil content is 12 wt %. However, the conversion of 1,3,5-TIPB is 2.1% over 9 wt % P$_2$O$_5$/HZSM-5 catalyst, indicating that the acid sites on the external surface are not completely inactivated.

Van Vu et al.[16] studied toluene methylation with methanol over ZSM-5/silicalite composites and suggested that the high *para*-selectivity is due to the removal of the acid sites on the external surface by silicalite layer and the suppression of *p*-xylene isomerization. In this study, however, the *para*-selectivity is not improved to a satisfactory extent when the acid sites on the external surface are removed by modification with methyl silicon oil; the results demonstrated that the *para*-selectivity mainly depends on the nature rather than on the distribution of the acid sites.

As stated before, high *para*-selectivity but low activity was observed over P/HZSM-5, whereas high activity but low *para*-selectivity could be obtained over Si/HZSM-5. Satisfactory results cannot be obtained by modification of HZSM-5 zeolite with H$_3$PO$_4$ or methyl silicon oil only. To develop high activity and high *para*-selectivity catalyst, combinational modification was carried out using phosphoric acid and methyl silicon oil. The content of methyl silicon oil and P$_2$O$_5$ were 8 and 3 wt %, respectively. It was observed (Figure 6) that Si—P/HZSM-5 performed better (93.1% *para*-selectivity, 27.7% toluene conversion) than 3 wt % P$_2$O$_5$/HZSM-5 or 8 wt % Si/HZSM-5 under equal reaction conditions.

Table 3. Toluene Conversion, *p*-xylene Yield and Selectivity over Different MO/HZSM-5 Catalysts

Catalysts	X(Toluene)%	Y(p-Xylene)%	Xylene fraction, %		
			p-Xylene	*m*-Xylene	*o*-Xylene
HZSM-5	63	10.0	24.3	53.2	22.5
P/HZSM-5	18.6	13.1	85.3	9.5	5.2
B/HZSM-5	41.0	9.0	30.8	49.6	19.6
Si/HZSM-5	56.5	20.6	51.7	33.9	14.4
Mg/HZSM-5	23.5	8.7	54.6	19.0	26.4
Ca/HZSM-5	18.9	5.7	37.8	46.9	15.3
Al/HZSM-5	53.0	12.7	33.7	41.9	17.4
Zn/HZSM-5	56.7	9.5	26.5	51.3	20.2
La/HZSM-5	43.3	13.9	54.7	29.2	17.1
Pb/HZSM-5	55.2	14.7	39.4	42.0	18.6
Fe/HZM-5	41.6	13.3	40.5	41.6	18.9
Sb/HZSM-5	38.5	16.0	57.9	28.3	13.8
Bi/HZSM-5	54.6	12.7	28.4	51.5	20.1

Reaction conditions: T = 673 K, WHSV$_{toluene}$ = 1.5 h^{-1}, n(CH$_3$Br):n(toluene) = 2:1, the oxide content is 5 wt %, N$_2$ flow 10 mL/min.

Table 4. The Effect of Methyl Silicon Oil Content on Toluene Conversion and Products Distribution

Catalysts	0 wt%	4 wt%	8 wt%	12 wt%	16 wt%
Toluene Conv.,%	63	56.5	53.3	46.4	38.2
CH_3Br Conv.,%	90.1	78.4	71.7	63.2	54.6
Product composition, %					
Benzene	3.7	0.6	0.4	0.2	0.1
Ethyl benzene	0.2	0.2	0.2	0.1	0
p-Xylene	10.0	20.6	23.4	22.7	19.7
m-Xylene	21.9	13.5	10.1	6.3	4.7
o-Xylene	9.3	5.8	4.9	4.3	3.8
Trimethylbenzenes	13.5	13.4	12.2	10.8	8.4
C_{10+}	4.5	2.4	2.1	2.0	1.5
Xylene fraction, %					
p-Xylene	24.3	51.7	60.9	68.1	69.8
m-Xylene	53.2	33.9	26.4	19.0	16.7
o-Xylene	22.5	14.4	12.7	12.9	13.5

Reaction conditions: T = 673 K, $WHSV_{toluene}$ = 1.5 h^{-1}, n(CH_3Br):n(toluene) = 2:1, N_2 flow 10 mL/min.

Effect of Reaction Conditions

Effect of reaction temperature

Toluene methylation with CH_3Br was carried out over Si—P/HZSM-5 catalysts in the 643–733 K range. The CH_3Br/toluene molar ratio was fixed at 2. As shown in Table 6, the conversion of toluene increases with the rise of reaction temperature, whereas *para*-selectivity changes significantly and irregularly between 643 and 733 K, resulting in a maximum of *p*-xylene yield at about 673 K. However, toluene conversion and *p*-xylene yield decrease with further rise of temperature. The conversion of toluene in the methylation reaction may be related to CH_3Br conversion, toluene disproportionation and catalyst deactivation. It was observed that CH_3Br conversion decreases at high temperature (Table 6), implying less participation of CH_3Br in toluene methylation, and, hence, lower conversion of toluene. In addition, the content of benzene increases with the rise of temperature (Table 6), indicating that high temperature is favorable for toluene disproportionation. Catalyst deactivation will lead to the decline of toluene conversion, and coke deposition would narrow the channels and pore mouths of the catalysts, consequently, enhancing *p*-xylene diffusion and improving *para*-selectivity. However, the *para*-selectivity does not increase,

Table 5. Effect of P_2O_5 Content on Toluene Conversion and Products Distribution

Catalysts	0 wt%	3 wt%	6 wt%	9 wt%
Toluene Conv., %	63.1	22.0	13.1	5.4
CH_3Br Conv., %	90.1	45.0	23.9	14.4
Product composition, %				
Benzene	3.7	0.4	0.3	0.1
Ethyl benzene	0.2	0.1	0	0
p-Xylene	10.0	14.4	10.6	5.0
m-Xylene	21.9	3.2	0.7	0.1
o-Xylene	9.3	1.2	0.3	0.
Trimethylbenzenes	13.5	1.7	1.0	0.3
C_{10+}	4.5	1.0	0.2	0
Xylene fraction, %				
p-Xylene	24.3	76.7	91.9	98
m-Xylene	53.2	16.7	5.9	2
o-Xylene	22.5	6.6	2.2	0

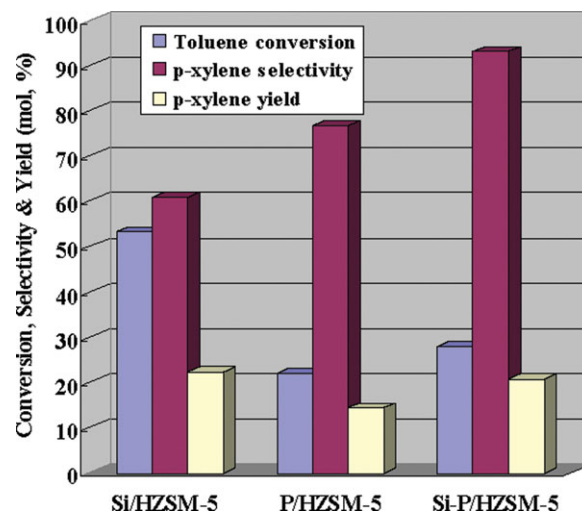Reaction conditions: T = 673 K, $WHSV_{toluene}$ = 1.5 h^{-1}, n(CH_3Br):n(toluene) = 2:1, N_2 flow 10 mL/min.
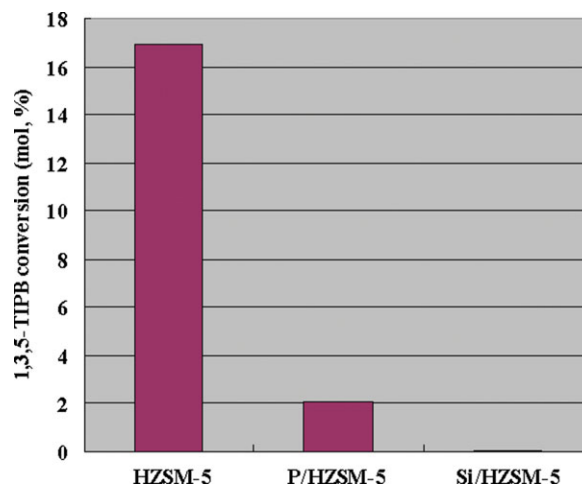
Figure 5. Conversion of 1,3,5-TIPB over HZSM-5, 9 wt % P_2O_5/HZSM-5 and 12 wt % Si/HZSM-5 catalysts.

[Color figure can be viewed in the online issue, which is available at wileyonlinelibrary.com.]

but reduces at high-reaction temperature. So, it is speculated that the decrease of toluene conversion at high temperature is mainly due to the conversion of CH_3Br and toluene disproportionation rather than to catalyst deactivation. When studied the alkylation of toluene with methanol over H_3PO_4/ZSM-5, Ghiaci et al.[35] observed *para*-selectivity decrease at high temperature but provided no explanation. The same phenomenon was observed in this study, we deduced that the decrease of *para*-selectivity at high temperature is due to *p*-xylene isomerization.

Effect of $WHSH_{toluene}$

The effect of toluene weight hourly space velocity ($WHSV_{toluene}$) on toluene conversion and *para*-xylene selectivity was studied at 673 K, with the feed ratio of CH_3Br:toluene = 2:1 over Si—P/HZSM-5 catalyst. The results

Figure 6. Catalytic performance comparison of P/HZSM-5, Si/HZSM-5 and Si—P/HZSM-5 (reaction conditions: n(CH_3Br):n(toluene) = 2:1, $WHSV_{toluene}$ = 1.5 h^{-1}, T = 673 K, N_2 flow 10 mL/min).

[Color figure can be viewed in the online issue, which is available at wileyonlinelibrary.com.]

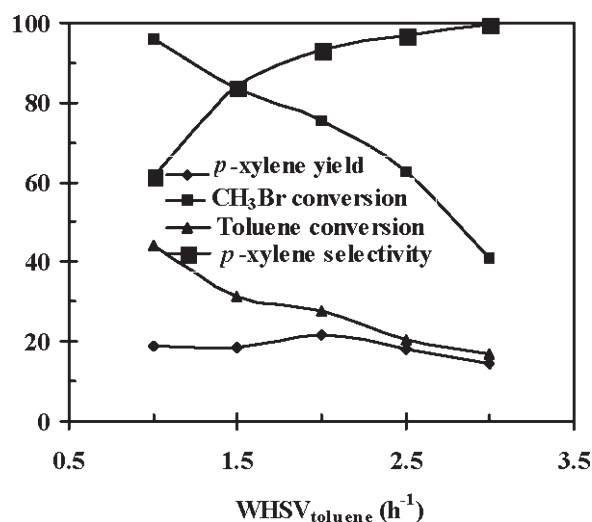**Table 6. Effect of Temperature on the Reaction of Toluene Methylation with CH₃Br**

Temperature (K)	643	673	703	733
Conversion of toluene (%)	25.7	27.7	35.6	30.9
Conversion of CH₃Br (%)	47.9	75.6	57.3	43.2
Product composition (%)				
Benzene	0.1	0.2	0.6	1.0
Ethyl benzene	0.1	0.1	0.2	0.1
xylenes	19.9	23.1	28.8	25.5
Trimethyl benzenes	4.4	3.5	4.8	2.8
C_{10+}	1.2	0.8	1.0	1.5
Fraction of xylenes (%)				
p-xylene	78.7	93.1	74.2	72.1
m-xylene	15.0	5.1	18.7	20.6
o-xylene	6.3	1.8	7.1	7.3

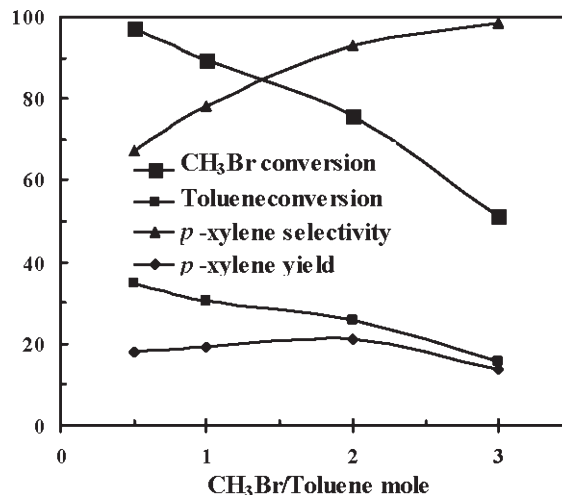Reaction conditions: $WHSV_{toluene}$ = 2 h^{-1}, n(CH₃Br):n(toluene) = 2:1, N₂ flow 10 mL/min.

obtained are summarized in Figure 7. It is clear that the conversion of toluene decreases from 44% to 16.9% when the WHSV of toluene increases from 1 to 3 h^{-1}, and the selectivity to p-xylene increases with the rise of toluene WHSV from 61.5% to 99.5%. Ghiaci et al.[35] and Breen et al.[36] observed the same phenomena in the methylation of toluene with methanol. As $WHSV_{toluene}$ increases, the contact time between toluene and catalysts declines. It is plausible that a large number of toluene and CH₃Br molecules passed through the reactor without actually contacting the active sites of the catalysts, resulting in low toluene and CH₃Br conversions. On the other hand, there is fast diffusion of p-Xylene out of the catalysts, and p-Xylene isomerization over strong acid sites is, hence, limited (leading to the increase of *para*-selectivity).

Effect of feed molar ratio

The effect of varying the CH₃Br/toluene molar ratio from 0.5 to 3 was studied over Si—P/HZSM-5 at 673 K and at toluene space velocity = 2 h^{-1}. The results are depicted in Figure 8. One can see that with the CH₃Br/toluene increases from 0.5 to 3, the conversion of toluene declines from 34.7% to 15.5% and *para*-selectivity increases from 67.1% to 98.6%, whereas p-xylene yield reaches a maximum
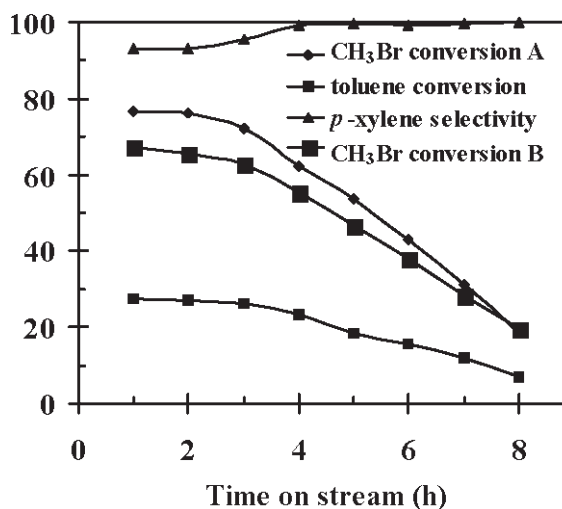

Figure 8. Effect of n(CH₃Br):n(toluene) on the performance of Si—P/HZSM-5 catalyst (Reaction conditions: T = 673 K, $WHSV_{toluene}$ = 2 h^{-1}, N₂ flow 10 mL/min).

(21.5%) at CH₃Br/toluene = 2. The decline of toluene conversion can be explained by the fact that the active sites (especially the strong acid sites) are mostly occupied by the redundant CH₃Br, and only a small amount of toluene can be activated over the catalyst. Although with increase of CH₃Br/toluene molar ratio, there is reduction in CH₃Br conversion (shown in Figure 8), there is however increase in terms of total CH₃Br conversion. Our previous study[40] demonstrated that CH₃Br conversion requires moderate surface acidity over HZSM-5. Therefore, with increase of CH₃Br/toluene molar ratio, more strong acid sites on Si—P/HZSM-5 would be involved in CH₃Br activation, and there is relatively less participation of strong acid sites in p-xylene isomerization. The result is enhancement in *para*-selectivity.

Effect of time on stream

A time on stream study was carried out over Si—P/HZSM-5 under optimal conditions (673 K, $WHSV_{toluene}$ = 2 h^{-1}, n(CH₃Br):n(toluene) = 2:1). As shown in Figure 9, there is

Figure 7. Effect of reaction temperature on the performance of Si—P/HZSM-5 catalyst (Reaction conditions: n(CH₃Br):n(toluene) = 2:1, $WHSV_{toluene}$ = 2 h^{-1}, N₂ flow 10 mL/min).

Figure 9. Time on stream of toluene methylation and CH₃Br catalytic conversion (reaction conditions: T = 673 K, $WHSV_{toluene}$ = 2 h^{-1}, $WHSV_{CH3B}$r = 4.1 h^{-1}, N₂ flow 10 mL/min).

Table 7. Products Distribution in CH₃Br Catalytic Conversion over Si—P/HZSM-5

		liquid phase products, %					gas phase products, %						Xylene fraction, %		
X, %	Y, %	C_6	C_7	C_8	C_9	C_{10+}	C_2	$C_2=$	C_3	$C_3=$	C_4	$C_4=$	*p*-xylene	*m*-xylene	*o*-xylene
64.6	21.3	2.2	23.4	57.5	5.9	11.0	31.8	9.5	26.5	1.1	37.3	3.8	90.1	6.5	3.4

Reaction conditions: T = 673 K, WHSV$_{CH3Br}$ = 4.1 h^{-1}, N₂ flow 10 mL/min.
X: CH₃Br conversion, Y: Aromatics yield.

Table 8. Products Distribution in Toluene Methylation with CH₃Br over Si—P/HZSM-5

	liquid phase products, %					gas phase products, %				
C_6	C_7	C_8	C_9	C_{10+}	C_2	$C_2=$	C_3	$C_3=$	C_4	$C_4=$
0.7	0.5	83.5	12.6	2.7	23.8	7.5	2.6	2.3	60.8	3.0

Reaction conditions: T = 673 K, WHSV$_{toluene}$ = 2 h^{-1}, n(CH₃Br):n(toluene) = 2:1, N₂ flow 10 mL/min.

almost no change in both CH₃Br (marked as CH₃Br conversion A) and toluene conversions in the first 3 h (respectively staying at about 26% and 75%). When the reaction time is further extended, CH₃Br conversion decreases significantly (from 75% to 18%), and toluene conversion decreases from 26% to 7%, whereas the *para*-selectivity increases to an admirable value (>99%) and remains rather stable. It is clear that the decline rate of CH₃Br conversion is much larger than that of toluene. As discussed before, the conversion of toluene over Si—P/HZSM-5 catalyst is mainly due to the conversion of CH₃Br. To disclose the relationship between CH₃Br conversion and the activity (toluene conversion) of Si—P/HZSM-5, we investigated the catalytic conversion of CH₃Br separately (marked as CH₃Br conversion B) over Si—P/HZSM-5. The conversion and products (liquid products were collected in the first 2 h) distribution are depicted in Figure 9 and Table 7, respectively. One can see that the change of CH₃Br conversion in the catalytic reaction is similar to that in toluene methylation. In both reactions the conversion of CH₃Br is stable in the first 3 h, and declines significantly in the next 5 h. The results of CH₃Br conversion, aromatics yield as well as products distribution in the liquid and gas phases in CH₃Br catalytic conversion over Si—P/HZSM-5 are somewhat different from those reported before.[23,40] In addition, the distribution of gas phase products in CH₃Br catalytic conversion is also different from those (shown in Table 8) in the reaction of toluene methylation with CH₃Br. The different results may be attributed to the variation of surface acidity across the catalysts. We found that CH₃Br conversion needs an appropriate ratio of strong and weak acid sites.[40] Based on the overall results of these two reactions (toluene methylation and CH₃Br catalytic conversion in this study), one comes to the awareness that the conversion of CH₃Br has much to do with the catalytic activity (toluene conversion) of the catalyst. We deduce that CH₃Br is first activated on the strong acid sites, yielding intermediates such as CH₃⁺ or CH₂, then the intermediates move to the weak acid sites and undergo methylation, oligomerization and coking reactions. The formed coke covers the active sites, especially the strong acid sites, and reduces the conversion of toluene and CH₃Br. On the other hand, the blocking of strong acid sites by coke improves *para*-selectivity.

The possible reaction mechanism

Kaeding et al.[41] studied the reaction of toluene methylation with methanol over modified HZSM-5 catalyst and proposed a mechanism: first, methanol or methyl ether (formed by methanol dehydration over modified HZSM-5 catalyst) adsorbed on the acid sites of catalyst and formed the corresponding oxonium ion. Then the methyl group transferred to the aromatic ring and a proton transferred back to the catalyst site. According to the results of this study and the mechanism reported by Kaeding et al. we propose a possible mechanism of toluene methylation with CH₃Br over Si—P/HZSM-5 (Scheme 3). First, CH₃Br chemisorbed on the strong acid sites and yields methyl cations. Then the electrophilic agents attack toluene to form *p*-xylene on the weak acid sites. Hereafter, the isomerization of *p*-xylene takes place on the strong acid sites and a mixture of all xylene (*p*-xylene, *m*-xylene and *o*-xylene) are produced. With a sufficient supply of CH₃Br, xylene further methylates to produce tri- and tetramethylbenzenes. At the same time, toluene disproportionation undergoes over the Brønsted acid sites of the catalysts. According to the results shown in Table 6, the conversion of CH₃Br (75.6%) is much higher than that of toluene (27.7%) under optimal reaction conditions, indicating that there is considerable CH₃Br depletion due to oligomerization and/or coking reactions. As shown in Table 7, toluene (23.4%), and xylenes (57.5%), are dominant liquid-phase
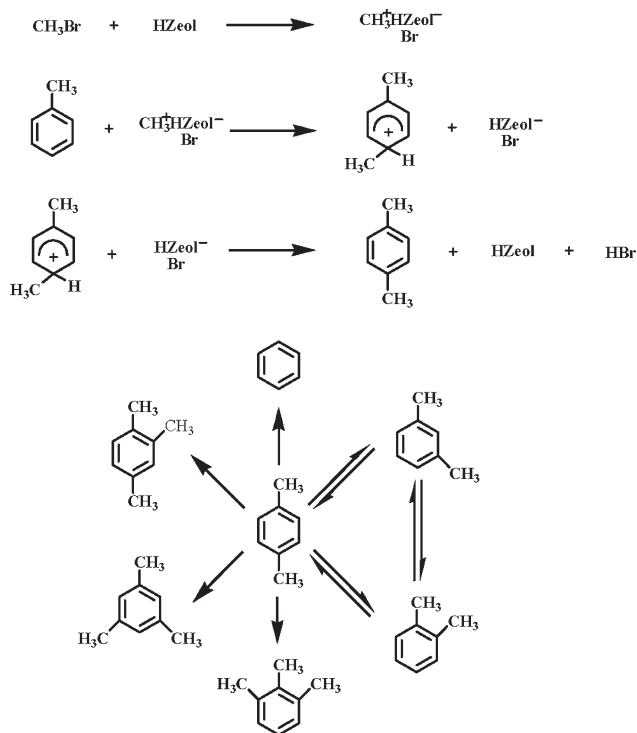
Scheme 3. Plausible reaction mechanism over Si—P/HZSM-5 catalyst.

products in CH_3Br oligomerization, and the gas-phase products are mainly C_2 (41.3%) and C_4 (41.4%). The *para*-selectivity in CH_3Br catalytic conversion (90.1%) is close to that in toluene methylation (93.1%). In view of the product distribution, we consider that the mechanism of side reactions is similar to those reported elsewhere,[23,40] caused only by CH_3Br in toluene methylation.

Conclusion

A new catalytic process for *p*-xylene synthesis from toluene methylation with CH_3Br was found feasible. The process has advantages such as mild reaction conditions, simple operation, high-product yield, and so on. It was found that Si—P/HZSM-5 is an excellent catalyst for selective formation of *p*-xylene in toluene methylation with CH_3Br. The catalyst is highly active and selective and the yield of *p*-xylene is up to 21%. It was found that toluene conversion depends on the concentration of total acid sites, whereas the *para*-selectivity depends on the relative ratio of strong to weak acid sites: decline in strong acid sites would mean better *para*-selectivity. Furthermore, the isomerization of *p*-xylene to other xylene isomers does not depend on whether the strong acid sites are inside or on the external surface of the zeolite, and elimination of strong acid sites in either location increases *para*-selectivity. The deactivation of Si—P/HZSM-5 in toluene methylation with CH_3Br is mainly due to CH_3Br oligomerization and coke formation.

Literature Cited

1. Jahn SL, Cardoso D. Influence of the Si/Al ratio and ZSM-5 crystallite size on the methylation of toluene. *Catal Today*. 1989;5:515–521.
2. Haag WO, Olson DH. Selective production of para dialkyl substituted benzenes. US Patent 4,117,026. 1978.
3. Haag WO, Olson DH. Selective disproportionation of toluene. US Patent 4,097,543 1978.
4. Chang CD, Shihabi S. Catalyst and process for the selective production of *para*-dialkyl substituted benzenes. US Patent 5,243,117 1993.
5. Chen QL, Xie ZK. Advance on the research and development of catalysts for toluene disproportionation and C_9 aromatics transalkylation. *J Nat Gas Chem*. 2001;10:61–70.
6. Chen NY, Kaeding WW, Dwyer FG. Para-directed aromatic reactions over shape- selective molecular sieve zeolite catalysts. *J Am Chem Soc*. 1979;101:6783–6784.
7. Mirth G, Lercher JA. On the role of product isomerization for shape selective toluene methylation over HZMS-5. *J Catal*. 1994;147:199–206.
8. Cejka J, Zilkova N, Wichterlova B, Elder-Mirth G, Lercher JA. Decisive role of transport rate of products for zeolite para-selectivity: Effect of coke deposition and external surface silylation on activity and selectivity of HZSM-5 in alkylation of toluene. *Zeolites*. 1996;17:265–271.
9. Palomares AE, Elder-Mirth C, Lercher JA. Technique for power ramp tests in the ISABELLE 1 loop of the OSIRIS reactor. *J Catal*. 1997;168:293–303.
10. Dumitriu E, Hulea V, Kaliaguine S, Huang MM. Transalkylation of the alkylaromatic hydrocarbons in the presence of ultrastable Y zeolites transalkylation of toluene with trimethylbenzenes. *Appl Catal A*. 1996;135:57–81.
11. Yashima T, Yamazaki K, Ahmad H, Katsuta M, Hara N. Alkylation on synthetic zeolites: II. Selectivity of p-xylene formation. *J Catal*. 1970;16:151–156.
12. Mantha R, Bhatia S, Rao MS. Kinetics of deactivation of methylation of toluene over H—ZSM-5 and hydrogen mordenite catalysts. *Ind Eng Chem Res*. 1991;30:281–286.
13. Joshi PN, Niphadkar PS, Desai PA, Patil R, Bolade VV. Toluene alkylation to selective formation of p-xylene over Co-crystalline ZSM-12/ZSM-5 catalyst. *J Nat Gas Chem*. 2007;16:37–41.
14. Miyamoto M, Kamei T, Nishiyama N, Egashira Y, Ueyama K. Single crystals ZSM-5/silicalite composites. *Adv Mater*. 2005;17:1985–1988.
15. Van-Vu D, Miyamoto M, Nishiyama N, Egashira Y, Ueyama K. Selective formation of para-xylene over H—ZSM-5 coated with polycrystalline silicalite crystals. *J Catal*. 2006;243:389–394.
16. Van-Vu D, Miyamoto M, Nishiyama N, Ichikawa S, Egashira Y, Ueyama K. Catalytic activities and structures of silicalite-1/ H—ZSM-5 zeolite composites. *Micropor Mesopor Mat*. 2008;115:106–112.
17. Xue B, Li YX, Deng LJ. Selective synthesis of p-xylene by alkylation of toluene with dimethyl carbonate over MgO-modified MCM-22. *Catal Commun*. 2009;10:1609–1614.
18. Xue B, Xu J, Xu CF, Wu RZ, Li YX, Zhang K. A novel, shape-selective H—MCM-22/MCM-41 composite catalyst: Synthesis, characterization and catalytic performance. *Catal Commun*. 2010;12:95–99.
19. Zhou XP, Yilmaz A, Yilmaz GA, Lorkovic IM, Laverman LE, Weiss M, Sherman JH, McFarland EW, Stucky GD, Ford PC. An integrated process for partial oxidation of alkanes. *Chem Commun*. 2003;2294–2295.
20. Zhou XP, Lorkovic IM, Stucky GD, Ford PC, Sherman JH, Grosso P. Integrated process for synthesizing alcohols and ethers from alkanes. US Patent 6,462,243 B1. 2002.
21. Zhou XP, Lorkovic IM, Sherman JH. Integrated process for synthesizing alcohols, ethers, and olefins from alkanes. US Patent 6,486,368 B1. 2002.
22. Yilmaz A, Zhou XP, Lorkovic IM, Yilmaz GA, Laverman L, Weiss M, Sun S, Schaefer D, Sherman JH, McFarland EW, Ford PC, Stucky GD. Bromine mediated partial oxidation of ethane over nanostructured zirconia supported metal oxide/bromide. *Micropor Mesopor Mat*. 2005;79:205–214.
23. Tao L, Chen L, Yin SF, Luo SL, Ren YQ, Li WS, Zhou XP, Au CT. Catalytic conversion of CH3Br to aromatics over PbO-modified HZSM-5. *Appl Catal A*. 2009;367:99–107.
24. Lorkovic IM, Yilmaz A, Yilmaz GA, Zhou XP, Laverman LE, Sun S, Schaefer DJ, Weiss M, Noy ML, Cutler CI, Sherman JH, McFarland EW, Stucky GD, Ford PC. C_1 oxidative coupling via bromine activation and tandem catalytic condensation and neutralization over CaO/zeolite composites: II. Product distribution variation and full bromine confinement. *Catal Today*. 2004;98:589–594.
25. Schweizer AE, Jones ME, Hickman DA. Oxidative halogenation of C_1 hydrocarbons to halogenated C_1 hydrocarbons and integrated processes related thereto. US Patent 6,452,058 B1. 2002.
26. Lorkovic IM, Noy M, Weiss M, Sherman J, McFarland E, Stucky GD, Ford PC. C_1 Coupling via bromine activation and tandem catalytic condensation and neutralization over CaO/zeolite composites. *Chem Commun*. 2004;566–267.
27. Namba S, Inaka A, Yashima T. Effect of selective removal of aluminium from external surfaces of HZSM-5 zeolite on shape selectivity. *Zeolite*. 1986;6:107–110.
28. Kim JH, Kunieda T, Niwa M. Generation of shape-selectivity of p-xylene formation in the synthesized ZSM-5 zeolite. *J Catal*. 1998;173:433–439.
29. Liu Z, Li WS, Zhou XP. Product oriented oxidative bromination of methane over Rh/SiO2 catalysts. *J Nat Gas Chem*. 2010;19:522–529.
30. Lin XY, Fan Y, Liu ZH, Shi G, Liu HY, Bao XJ. A novel method for enhancing on-stream stability of fluid catalytic cracking (FCC) gasoline hydro-upgrading catalyst: Post-treatment of HZSM-5 zeolite by combined steaming and citric acid leaching. *Catal Today*. 2007;125:185–191.
31. Li YG, Xie WH, Yong S. The acidity and catalytic behavior of Mg-ZSM-5 prepared via a solid-state reaction. *Appl Catal A*. 1997;150:231–242.
32. Aboul-Gheit AK, Abdel-Hammid SM, Emam EA. Catalytic para-xylene maximization II - alkylation of toluene with methanol on platinum loaded H—ZSM-5 zeolite catalysts prepared via different routes. *Appl Catal A*. 1999;179:107–115.
33. Zheng S, Jentys A, Lercher J. On the enhanced para-selectivity of HZSM-5 modified by antimony oxide. *J Catal*. 2003;219:310–319.

34. Breen J, Burch R, Kulkarni M, Collier P, Golunski S. Enhanced *para*-xylene selectivity in the toluene alkylation reaction at ultralow contact time. *J Am Chem Soc*. 2005;127:5020–5021.
35. Ghiaci M, Abbaspur A, Arshadi M, Aghabarari B. Internal versus external surface active sites in ZSM-5 zeolite: Part 2: Toluene alkylation with methanol and 2-propanol catalyzed by modified and unmodified H_3PO4/ZSM-5. *Appl Catal A*. 2007; 316:32–46.
36. Breen JP, Burch R. Kulkarni M, Mclaughlin D, Collier PJ, Golunski SE. Improved selectivity in the toluene alkylation reaction through understanding and optimising the process variables. *Appl Catal A*. 2007;316:53–60.
37. Cavallaro S, Pino L, Tsiakaras P, Giordano N, Rao BS. Alkylation of toluene with methanol III: Para-selectivity on modified ZSM-5 zeolites. *Zeolites*. 1987;7:408–411.
38. Čejka J, Žilková N, Wichterlová B, Eder-Mirth G, Lercher JA. Decisive role of transport rate of products for zeolite para-selectivity: Effect of coke deposition and external surface silylation on activity and selectivity of HZSM-5 in alkylation of toluene. *Zeolites*. 1996;17:265–271.
39. Zheng S, Heydenrych HR, Röfer HP, Jentya A, Lercher JA. On the enhanced selectivity of HZSM-5 modified by chemical liquid deposition. *Top Catal*. 2003;22:101–106.
40. Tao L, Li GS, Yin SF, Ou-Yang Q, Luo SL, Zhou XP, Au CT. Synthesis and characterization of H─ZSM-5 zeolites and their catalytic performance in CH_3Br conversion to aromatics. *Reac Kinet Mech Cat*. 2011;103:191–207.
41. Kaeding WW, Chu C, Young LB, Weinstein B, Butter SA. Selective alkylation of toluene with methanol to produce *para*-xylene. *J Am Chem Soc*. 1981;67:159–174.