

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/238625699>

Opening a Perovskite to Valence Manipulation: Two-Step Topotactic Route to a New Mixed- Valence Titanate, $\text{Na}_{1-x+y}\text{Ca}_{x/2}\text{LaTiO}_4$

ARTICLE in JOURNAL OF THE AMERICAN CHEMICAL SOCIETY · JANUARY 1998

Impact Factor: 12.11 · DOI: 10.1021/ja971299x

CITATIONS

34

READS

29

5 AUTHORS, INCLUDING:



Alexander U Falster

University of New Orleans

374 PUBLICATIONS 702 CITATIONS

SEE PROFILE



John Wiley

University of New Orleans

147 PUBLICATIONS 2,118 CITATIONS

SEE PROFILE

Opening a Perovskite to Valence Manipulation: Two-Step Topotactic Route to a New Mixed-Valence Titanate, $\text{Na}_{1-x+y}\text{Ca}_{x/2}\text{LaTiO}_4$

Robert A. McIntyre,[†] Alexander U. Falster,[‡] Sichu Li,[†] William B. Simmons, Jr.,[‡] Charles J. O'Connor,[†] and John B. Wiley^{*,†}

Departments of Chemistry and Geology and
Geophysics and Advanced Materials Research Institute
University of New Orleans
New Orleans, Louisiana 70148-2820

Received April 24, 1997

Revised Manuscript Received November 12, 1997

Mixed-valence oxides with perovskite-related structures are known to exhibit a range of important properties including high-temperature superconductivity, colossal magnetoresistance, and catalytic activity.¹ While many of these materials are traditionally synthesized by direct reaction with aliovalent metal oxides at elevated temperatures, mild low-temperature routes are also desirable in that they may lead to new metastable materials with improved properties. Reductive intercalation with alkali metals is one topotactic method known to be effective in the low-temperature preparation of some select mixed-valence perovskites.^{2–4} For this approach to be successful, however, the A-site in Ruddlesden–Popper perovskites, $\text{A}_2[\text{A}_{m-1}\text{B}_m\text{O}_{3m+1}]$, (A = alkali, alkaline earth, and/or rare earth; B = transition metal; $m = 1, 2, 3$, or ∞) must be partially or completely vacant. Since most perovskites are stoichiometric with respect to A, methods that create vacancies on this site are appealing in that they would, when used in combination with reductive intercalation techniques, offer a significant new approach to the preparation of mixed-valence compounds.

We and others^{5,6} have investigated the exchange of multivalent cations for monovalent ones in receptive hosts. When a multivalent cation is exchanged into a compound, it is accompanied by the formation of one or more vacancies depending on the cation charge. The creation of these vacancies opens the host structure to further chemistry. In the case of reductive intercalation, it should be possible to insert alkali metal ions into the vacancies thereby producing mixed valency in the host. Herein we describe the use of this strategy in the manipulation of NaLaTiO_4 .⁷ This

Ruddlesden–Popper phase ($m = 1$, K_2NiF_4 structure)⁸ consists of LaTiO_4 layers separated by ion-exchangeable sodium ions.⁹ Because the A-sites are fully occupied, direct reductive intercalation cannot occur. Initially NaLaTiO_4 is opened to intercalation by ion exchange with a divalent cation and then the interlayer vacancies created are utilized by alkali metal ions on intercalation. This simple two-step procedure readily results in a new mixed-valence titanate with a perovskite-related structure.

NaLaTiO_4 was prepared by literature methods.^{8,10} Sodium ions were replaced in a two-for-one exchange by reacting stoichiometric amounts of anhydrous $\text{Ca}(\text{NO}_3)_2$ with NaLaTiO_4 in an evacuated, sealed Pyrex tube for 3 days at 350 °C.¹¹ The NaNO_3 byproduct, observed by X-ray powder diffraction, was readily removed with a water wash. The exchange product was then reacted with sodium metal vapor for several days at 300 °C.¹² During this time, the oxide turned from white to dark black. Relative amounts of sodium and calcium in both products were determined by spectroscopic methods.¹³ Values were found to correspond to an 86% sodium exchange, $x = 0.86$ in $\text{Na}_{1-x}\text{Ca}_{x/2}\text{LaTiO}_4$, and an 88% sodium intercalation, $y = 0.38$ in $\text{Na}_{1-x+y}\text{Ca}_{x/2}\text{LaTiO}_4$.¹⁴

Compounds were characterized by both X-ray powder diffraction and magnetic susceptibility.¹⁵ Figure 1 presents the powder patterns of the ion exchange and intercalated products in comparison to both the parent, NaLaTiO_4 , and a simulated pattern for $\text{Na}_{0.51}\text{Ca}_{0.43}\text{LaTiO}_4$.¹⁶ The NaLaTiO_4 structure is maintained in both products. The simulation, modeled after the parent^{8a} with sodium and calcium ions statistically distributed over the same site, is in good agreement with the observed pattern of the intercalate.¹⁷ Lattice parameters along with cell volumes are presented in Table 1. For the exchange material, a slight reduction in cell size is observed that is attributed to the smaller ionic radius of calcium (1.32 Å) versus that of sodium (1.38 Å).¹⁸ A more dramatic variation in the cell is seen in the intercalated compound; the a parameter is found to expand by ~ 0.1 Å while the c

(8) (a) Zhu, W. J.; Feng, H. H.; Hor, P. H. *Mater. Res. Bull.* **1996**, *31*, 107. (b) Toda, K.; Kameo, Y.; Kurita, S.; Sato, M. *J. Alloys Compd.* **1996**, *234*, 19. (c) Byeon, S.-H.; Park, K.; Itoh, M. *J. Solid State Chem.* **1996**, *121*, 430.

(9) (a) Toda, K.; Kurita, S.; Sato, M. *Solid State Ionics* **1995**, *31*, 107. (b) Byeon, S.-H.; Yoon, J.-J.; Lee, S.-O. *J. Solid State Chem.* **1996**, *127*, 119.

(10) Stoichiometric amounts of La_2O_3 (Aldrich, 99.99%) and TiO_2 (Aldrich, 99.99%) and a 30% excess of Na_2CO_3 (Aldrich, 99.99%) were heated in an alumina crucible in air at 930 °C for 72 h. Interstitial grindings were performed every 24 h with the addition of a further 30% excess of Na_2CO_3 . The resultant white powder was thoroughly washed with distilled water and dried at 160 °C. The unit cell parameters are in good agreement with the literature (Table 1).

(11) Typically a stoichiometric amount of the nitrate (Aldrich, 99%) was combined with 1.57 g (5.7 mmol) of NaLaTiO_4 in a tube (12 mm od). The product was white in color.

(12) An excess of sodium metal (0.3 g, 13.0 mmol, Aldrich, 99.999%) was weighed out on a piece of Pyrex tubing (6 mm od) for ease of handling, the combination was placed in a Pyrex tube (12 mm od) along with 0.3 g (1.1 mmol) of sample, and the tube was sealed under vacuum. The excess sodium partly compensated the loss due to reaction with the glass; unreacted sodium was distilled away from the product by heating the sample tube in a temperature gradient. The intercalation reagents and products were all handled in an argon-filled drybox. *Caution: Sodium metal can explosively react with water. Excess sodium should be safely disposed of by reacting it with an alcohol.* The intercalation product degrades very slowly on exposure to air.

(13) Calcium and sodium contents were determined commercially by inductively coupled plasma spectrometry (ICP) and atomic absorption (AA), respectively.

(14) This formulation does not account for the possibility of oxygen nonstoichiometry.

(15) Digitized X-ray diffraction patterns were collected on a Philips-Norelco diffractometer equipped with $\text{Cu K}\alpha$ radiation ($\lambda = 1.5418$ Å) and a graphite monochromator. Cell parameters were refined by a least-squares method. Room-temperature susceptibility measurements were performed on a Quantum Design MPMS-5S SQUID susceptometer.

(16) The pattern of $\text{Na}_{0.51}\text{Ca}_{0.43}\text{LaTiO}_4$ was calculated with the LAZY-PULVERIX FORTRAN program (Yvon, K.; Jeitschko, W.; Parthe, E. Laboratoire de Crystallographie Aux Rayon-X; University of Geneva: Geneva, Switzerland, 1977).

[†] Department of Chemistry and Advanced Materials Research Institute.
[‡] Department of Geology and Geophysics.

(1) For example, see: (a) Sleight, A. W. *Science* **1988**, *242*, 1519. (b) Jin, S.; Tiefel, T. H.; McCormack, M.; Fastnacht, R. A.; Ramesh, R.; Chen, L. H. *Science* **1994**, *264*, 413. (c) Tejuca, L. G.; Fierro, J. L. G. *Adv. Catal.* **1989**, *36*, 237.

(2) *Intercalation Chemistry*; Whittingham, M. S., Jacobson, A. J., Eds.; Academic Press: New York, 1982.

(3) (a) Hagenmuller, P.; Delmas, C. *Mater. Res. Soc. Symp. Proc.* **1991**, *210*, 323. (b) Nadiri, A.; Le Flem, G.; Delmas, C. *J. Solid State Chem.* **1988**, *73*, 338.

(4) Armstrong, A. R.; Anderson, P. A. *Inorg. Chem.* **1994**, *33*, 4366.

(5) For example, see: (a) Barrer, R. M. *Hydrothermal Chemistry of Zeolites*; Academic Press: New York, 1982. (b) Laudelout, H.; Van Bladel, R.; Bolt, G. H.; Page, A. L. *Trans. Faraday Soc.* **1968**, *64*, 1477. (c) Clearfield, A.; Hagiwara, H. *J. Inorg. Nucl. Chem.* **1978**, *40*, 907. (d) Grandin, A.; Borel, M. M.; Raveau, B. *Mater. Res. Bull.* **1985**, *20*, 1279. (e) Izawa, H.; Kikkawa, S.; Koizumi, M. *J. Solid State Chem.* **1987**, *69*, 336. (f) Kalogirou, O. J. *Solid State Chem.* **1993**, *102*, 318. (g) Clearfield, A.; Troup, J. M. *J. Phys. Chem.* **1970**, *74*, 2578. (h) Clearfield, A.; Saldarriaga, C. H.; Buckley, R. C. In *Proceedings of the 3rd International Conference on Molecular Sieves*; Uytterhoeven, J. B., Ed.; University of Leuven Press: Leuven, Belgium, 1973; p. 241. (i) Sattar, S.; Ghosal, B.; Underwood, M. L.; Mertwoy, H.; Saltzberg, M. A.; Frydrych, W. S.; Rohrer, G. S.; Farrington, G. C. *J. Solid State Chem.* **1986**, *65*, 231.

(6) Cushing, B. L.; Falster, A. U.; Simmons, W. B., Jr.; Wiley, J. B. *J. Chem. Soc., Chem. Commun.* **1996**, 2635.

(7) Blasse, G. *J. Inorg. Nucl. Chem.* **1968**, *30*, 656.

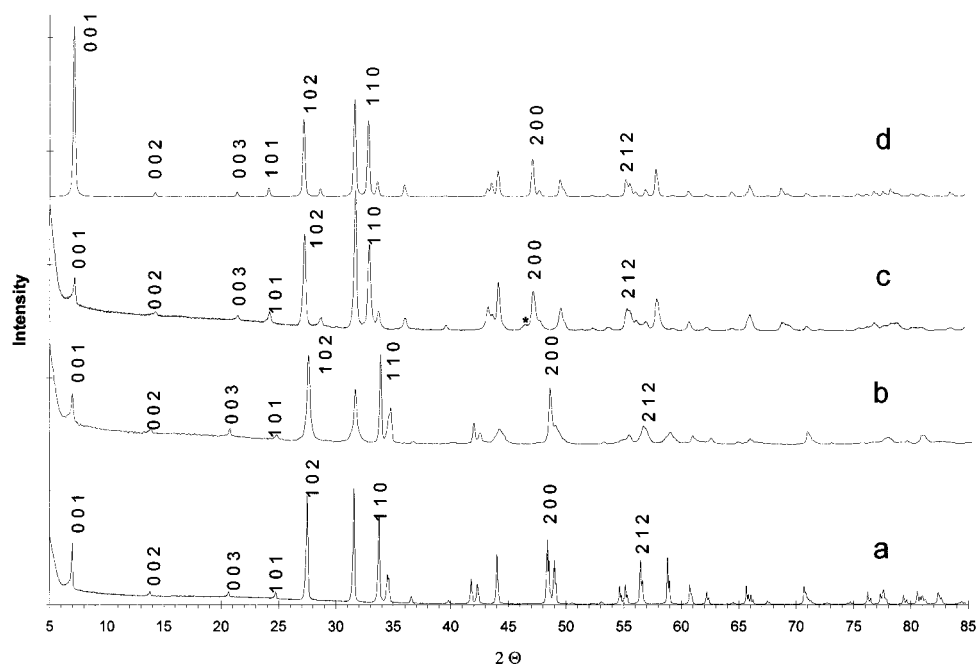


Figure 1. X-ray powder diffraction patterns of (a) NaLaTiO₄, (b) the calcium ion exchange product, (c) the intercalation product, and (d) a simulated pattern of intercalation product with composition, Na_{0.51}Ca_{0.43}LaTiO₄. Miller indices are indicated for select reflections. Unindexed reflection (*).¹⁷

Table 1. Tetragonal Cell Parameters for the Parent, NaLaTiO₄, and the Exchange and Intercalation Products

cmpd	unit cell (Å)	cell vol. (Å ³)	lit. cell (Å)
NaLaTiO ₄	<i>a</i> = 3.7731(6) <i>c</i> = 13.021(2)	185.37	<i>a</i> = 3.7759(1) <i>c</i> = 13.022(1) ^{9a}
Na _{0.13} Ca _{0.43} LaTiO ₄ ¹³	<i>a</i> = 3.764(2) <i>c</i> = 12.945(6)	183.40	this work
Na _{0.51} Ca _{0.43} LaTiO ₄ ¹³	<i>a</i> = 3.8627(4) <i>c</i> = 12.484(2)	186.27	this work

parameter contracts by ~ 0.46 Å. These lattice changes in *a* and *c* are attributed to the larger size of Ti³⁺ (0.81 Å) versus that of Ti⁴⁺ (0.75 Å)¹⁸ and the greater electrostatic attraction between the more highly charged perovskite sheets and the interlayer cations, respectively. Comparable behavior has been observed after reductive intercalation of other layered perovskites such as those with the Dion–Jacobson structure type, A[A_{*m*−1}B_{*m*}O_{3*m*+1}].¹⁹ Room-temperature magnetic measurements are consistent with the formation of Ti³⁺; a positive susceptibility (1.8μ_B), greater than the theoretical value of 1.0μ_B (spin only, 38% Ti³⁺), is observed. Variable-temperature magnetic and electronic studies as a function of composition will be reported elsewhere.

Initial results indicate that control over the extent of mixed-valency is best exercised in the ion exchange step. By simply using less than stoichiometric amounts of Ca(NO₃)₂, lower values of *x* in Na_{1−*x*}Ca_{*x*/2}LaTiO₄ and correspondingly fewer vacancies can be introduced into the host, whereby on subsequent intercala-

tion a smaller fraction of the titanium is reduced. Controlling valency by lowering the amount of sodium metal available for intercalation appears less effective in that the resulting product will sometimes contain unreacted starting material.

Na_{1−*x*+*y*}Ca_{*x*/2}LaTiO₄ represents a new mixed-valence titanate²⁰ with a perovskite-related structure. The combination of multivalent ion exchange and reductive intercalation used in its preparation offers an effective strategy for valence manipulation. Because many mixed metal oxides^{5d–f,6,21} and nonoxides²² are known to undergo, or are likely to undergo, ion exchange with multivalent cations, it should be possible to extend this two-step approach to a variety of compounds. The ability to carry out such successive reactions on a host, especially at relatively low temperatures, then becomes especially significant in that it may result in a greater degree of control over structure and properties than afforded by more traditional single-step high-temperature processing. Molecular chemists routinely draw from their reaction libraries to direct the construction of a targeted molecule by the sequential, multistep manipulation of some parent. Similar abilities for solid-state chemists could result in a more routine approach to the rational design and construction of new nonmolecular materials. Two-step strategies such as that presented here should serve in the development of such methods.

Acknowledgment. The financial support provided by the Louisiana Education Quality Support Fund (LEQSF(1994-1997)-RD-A-35), the Petroleum Research Fund (ACS-PRF 30522-G5), and the DOD (DARPA MDA972-97-1-0003) is gratefully acknowledged.

JA971299X

(17) A small, broad reflection (<3%) is observed at 46.3° 2θ. This is attributed to a minor impurity that forms on intercalation. The phase is likely an intercalated, defect perovskite, Na_{*x*}La_{1−*y*}TiO₃ (0.33 ≤ *y* ≤ 0.5, *x* ≤ *y*). Though it is thought that this perovskite is initially present as an amorphous impurity in the parent compound, the possibility it is a decomposition product has not yet been ruled out. Note however, that the small amount of this impurity does not increase if the intercalation step is carried out for longer times or at higher temperatures; this would not be expected if the impurity was from decomposition.

(18) Shannon, R. D. *Acta Crystallogr.* **1976**, A32, 751.

(19) (a) Jones, R.; McKinnon, W. R. *Solid State Ionics* **1991**, 45, 173. (b) Sato, M.; Jin, T.; Ueda, H. *Chem. Lett.* **1994**, 161.

(20) Some other examples include: (a) Sweedler, A. R.; Raub, C.; Matthias, B. T. *Phys. Lett.* **1965**, 15, 108. (b) Johnston, D. C.; Prakash, H.; Zachariasen, W. H.; Viswanathan, R. *Mater. Res. Bull.* **1973**, 8, 777. (c) Wang, S.; Hwu, S.-J.; Paradis, J. A.; Whangbo, M.-H. *J. Am. Chem. Soc.* **1995**, 117, 5515. (d) Murphy, D. W.; Greenblatt, M.; Zahurak, S. M.; Cava, R. J.; Wassczak, J. V.; Hull, G. W.; Hutton, R. S. *Rev. Chim. Miner.* **1982**, 19, 441. (e) Maazaz, A.; Delmas, C.; Hagenmuller, P. *J. Inclusion Phenom.* **1983**, 1, 45.

(21) (a) Gradin, A.; Borel, M. M.; Raveau, B. *Ann. Chim. Fr.* **1988**, 13, 51. (b) Nedjar, R.; Borel, M. M.; Raveau, B. *Ann. Chim. Fr.* **1988**, 13, 155.

(22) Boller, H. *Monatsh. Chem.* **1978**, 109, 975.