

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/45651268>

# Rheological and Chemical Analysis of Reverse Gelation in a Covalently Cross-Linked Diels-Alder Polymer Network

ARTICLE *in* MACROMOLECULES · DECEMBER 2008

Impact Factor: 5.8 · DOI: 10.1021/ma801863d · Source: PubMed

---

CITATIONS

74

READS

66

---

## 5 AUTHORS, INCLUDING:



Brian Adzima

Autodesk

21 PUBLICATIONS 558 CITATIONS

[SEE PROFILE](#)



Hector Alan Aguirre Soto

Massachusetts Institute of Technology

9 PUBLICATIONS 91 CITATIONS

[SEE PROFILE](#)



Christopher J Kloxin

University of Delaware

48 PUBLICATIONS 1,141 CITATIONS

[SEE PROFILE](#)



Timothy F. Scott

University of Michigan

49 PUBLICATIONS 1,482 CITATIONS

[SEE PROFILE](#)



# NIH Public Access

## Author Manuscript

*Macromolecules.* Author manuscript; available in PMC 2010 August 13.

Published in final edited form as:  
*Macromolecules.* 2008 December 9; 41(23): 9112–9117. doi:10.1021/ma801863d.

## Rheological and chemical analysis of reverse gelation in a covalently crosslinked Diels-Alder polymer network

Brian J. Adzima<sup>†</sup>, H. Alan Aguirre<sup>†</sup>, Christopher J. Kloxin<sup>†</sup>, Timothy F. Scott<sup>†,‡</sup>, and Christopher N. Bowman<sup>†,\*</sup>

<sup>†</sup>Department of Chemical and Biological Engineering, University of Colorado, Boulder, CO 80309-0424, USA

### Abstract

A network polymer, incorporating dynamic and reversible crosslinks, was synthesized using the Diels-Alder reaction. Fourier transform infrared (FTIR) spectroscopy was used to characterize the reaction rate and thermodynamic equilibrium over a broad temperature range. Equilibrium conversion of the furan and maleimide varied from 74% at 85°C to 24% at 155°C, demonstrating significant depolymerization via the retro-Diels-Alder reaction. The gel point temperature, as determined by rheometry using the Winter-Chambon criterion, was 92°C, corresponding to a gel-point conversion of 71%, consistent with the Flory-Stockmayer equation. The scaling exponents for the complex moduli, viscosity, and plateau modulus, in the vicinity of the gel-point, were determined and compared with experimental and theoretical literature values. Further, the material exhibited a low frequency relaxation owing to dynamic rearrangement of crosslinks by the Diels-Alder and retro-Diels-Alder reactions.

### Introduction

Traditionally, thermosets are irreversibly crosslinked polymeric networks possessing essentially infinite molecular weight that cannot be melted, molded, or dissolved.<sup>1</sup> Such materials are durable and find use in a wide array of applications such as adhesives,<sup>2, 3</sup> coatings,<sup>4, 5</sup> dental materials,<sup>6, 7</sup> and composites.<sup>8, 9</sup> In contrast, the incorporation of reversibly labile functionalities into the polymer backbone enables manipulation of network connectivity and allows behavior analogous to melting, molding, and dissolution through depolymerization to low molecular weight species. This reversion significantly extends the capabilities and utility of these crosslinked materials, at the expense of thermal stability. Furthermore, polymers that contain reversible linkages have been used to create stimulus responsive polymers that display novel properties such as shape memory,<sup>10, 11</sup> crack healing,<sup>12, 13</sup> and stress relief.<sup>14</sup>

In principle, most polymerizations are reversible; however, realizing depolymerization often leads to complete and irreversible degradation of the polymer network. Certain polymers, including those created by radical and ionic polymerization, often depolymerize when heated above a ceiling temperature. Ceiling temperatures are typically quite high and, at such temperatures, irreversible degradation of other molecular structures generally occurs; however, a few polymers, including poly( $\alpha$ -methyl styrene) and poly(isobutene), display more moderate ceiling temperatures (61°C and 50°C, respectively).<sup>15</sup> In condensation

\*E-mail: christopher.bowman@colorado.edu.

<sup>†</sup>Current address: Center for Bioengineering, Department of Mechanical Engineering, University of Colorado, Boulder, Colorado 80309-0427, USA.

polymerizations, condensate removal favors the forward reaction, thus the retro-reaction is only achieved when the condensate is present in significant quantities. Consequently, polymers such as polyacrylhydrazones undergo dynamic network rearrangement, but do not revert to monomer,<sup>16</sup> and exotic approaches are required to create systems that undergo a sol-gel transition, but do not exhibit dynamic network rearrangement in the gel state.<sup>17</sup>

The Diels-Alder (DA) reaction, a [4+2] cycloaddition between a diene (e.g., furan) and dieneophile (e.g., maleimide), is thermally reversible via the retro-Diels-Alder (rDA) reaction (Scheme 1).<sup>18</sup> The DA reaction is attractive as a reversible linkage as the rDA reaction occurs at moderate temperatures and does not liberate a small molecule. The subject of more than 17,000 papers, the DA reaction is well studied,<sup>19</sup> but its use in polymer chemistry is comparatively limited. Nevertheless, a variety of macromolecular structures have been synthesized utilizing the DA reaction of maleimides and furans, including linear polymers,<sup>20</sup> networks,<sup>12, 13, 21, 22</sup> hydrogels,<sup>23</sup> and dendrimers.<sup>24</sup> Moreover, DA adducts have been incorporated into monomers bearing other polymerizable functionalities, allowing DA/rDA reactions to be exploited in materials polymerized via common mechanisms such as the reaction between epoxy and amine functionalities,<sup>25</sup> and free-radical (meth)acrylate polymerizations.<sup>26, 27</sup>

Network reversibility owing to the rDA reaction has been demonstrated through solubility studies;<sup>21, 25, 28</sup> however, the temperature dependence of the equilibrium constant, and therefore conversion, in these networks remains relatively unexplored. Typically, polymers above their glass transition temperature have sufficient molecular mobility to reach thermodynamic equilibrium when sufficient time is allowed for completion of the reaction. Accordingly, in polymers formed by the DA reaction, the final conversion is a function of temperature, as demonstrated in linear polymers crosslinked by the DA reaction.<sup>29</sup>

The molecular weight evolution during a step-growth polymerization, such as a DA polymerization, proceeds geometrically and is accompanied by an exponential increase in viscosity. Moreover, for systems capable of crosslinking, the material undergoes gelation, a critical point that occurs when a single macromolecule first spans the sample, and the material transitions from a liquid sol to a solid gel. The creation of a macromolecular gel is accompanied by a divergence in the viscosity and an emergence of an elastic modulus. Typically, as the reaction proceeds, the elastic modulus increases until complete conversion is achieved or the material vitrifies. The mechanical properties of all polymeric materials vary with temperature as they pass through transitions such as crystallization, glass transition, or other molecular relaxations. Unlike conventional, non-reversible networks, the crosslink density of polymers containing DA adducts is dependent on the temperature, leading to the establishment of a gel point temperature.

The gel-point conversion for the step-growth polymerization between maleimide and furan monomers is well-predicted by the Flory-Stockmayer equation,

$$p_g = \frac{1}{\sqrt{r(1 - f_M)(1 - f_F)}}, \quad (1)$$

where  $p_g$  is the gel-point conversion,  $r$  is the stoichiometric ratio, and  $f_M$  and  $f_F$  are the degree of functionality for the maleimide and furan monomers, respectively.<sup>30,31</sup> The gel-point conversion is shifted by changing either the monomer functionality or the stoichiometric ratio and determined experimentally using rheometry to compare with the predicted value. Observation of a material's complex response to an oscillatory shear stress allows application of the Winter-Chambon criterion,

$$G'(\omega) \sim G''(\omega) \sim \omega^u, \quad (2)$$

which states that the real and imaginary moduli follow identical power law frequency scaling at the gel-point, for  $\omega < 1/\tau_0$  where  $\tau_0$  is the characteristic relaxation time of the smallest molecular species.<sup>32</sup> The gel-point conversion for an irreversible polymerization is typically determined by quenching the reaction, leading to a trial-and-error process. Nevertheless, several researchers have performed accurate mechanical measurements near the gel-point, validating the Winter-Chambon criterion in a rheometer.<sup>33–35</sup> Others have utilized off-stoichiometric monomer ratios so that the gel-point is achieved near the final conversion.<sup>36</sup> Khan et al. monitored the polymerization of thiol-ene resins using rheometry and inferred the conversion at the gel-point by IR spectroscopy.<sup>37</sup> In contrast, DA-based networks display inherent coupling of conversion and temperature, thereby allowing fine and reversible control of the conversion near the gel-point, all within a single sample.

Here, the reversible reaction between furan and maleimide functionalities is exploited to examine the complex interplay between the Diels-Alder equilibrium, kinetic limitations associated with the mobility in the crosslinked network, the glass transition, and the sol-gel transition using IR spectroscopy and rheometry over a broad temperature range. The mechanical properties of the material are also examined using rheometry as a function of temperature, and therefore conversion, which facilitates the examination of several theoretical descriptions of the gelation process.

## Experimental Section

### Materials

Pentaerythritol propoxylate triacrylate (PPTA), 1,1'-(methylenedi-4,1-phenylene) bismaleimide (DPBM), furfuryl mercaptan, triethyl amine, and dichloromethane were obtained from Sigma-Aldrich and used without further preparation.

### Synthesis of pentaerythritol propoxylate tris(3-(furfurylthio)propionate) (PPTF)

**(PPTF)**—To a mixture of 10.0 g (0.019 mol) of PPTA and 7.1 g (0.063 mol) of furfuryl mercaptan, a catalytic amount of triethyl amine was added, heated to 40°C, and allowed to react for 24 hours while stirring. The triethylamine and residual furfuryl mercaptan were removed under vacuum (0.2 mm Hg) at 45°C. Absence of peaks in the <sup>1</sup>H-NMR spectrum of the product due to residual acrylate (6.35, 6.06, and 5.82 ppm) or thiol (1.91 ppm) confirmed complete reaction and subsequent purification of PPTF.

**Polymer Synthesis**—Polymer samples were prepared by combining PPTF and DPBM at a 1:1 furan to maleimide ratio. The material was briefly heated (less than 5 minutes) to ~155°C to melt the DPBM, and mixed until homogeneous. Upon cooling, a glassy yellow solid, insoluble in common organic solvents, was formed. The solid material visibly reverted to a liquid upon heating to ~110°C.

### FTIR Spectroscopy

Spectroscopic studies were performed with a Nicolet Magna 750 series II Fourier-transform infrared (FTIR) spectrometer equipped with a MCT detector and a horizontal transmission temperature-controlled stage (accurate to 0.1°C). Samples for IR spectroscopy were produced by casting a thin film of a freshly prepared solution of PPTF and DPBM in dichloromethane (at a 1:1 furan to maleimide functional group stoichiometric ratio) onto a NaCl crystal and rapidly evaporating the solvent under vacuum. Typically, less than three minutes elapsed between mixing and the initial spectra collection. Reaction during the

sample preparation was assumed to be negligible as the DA reaction between furan and maleimide proceeds slowly at ambient temperature. The number of scans per spectrum (between 16 and 512) was adjusted based on the reaction rate. Conversion of the furan and maleimide functionalities was evaluated by monitoring the evolution of the furan peak area, centered at  $1010\text{ cm}^{-1}$ , and the maleimide peak area, centered at  $690\text{ cm}^{-1}$ .<sup>38, 39</sup>

### Rheometry

Rheological measurements were performed using an ARES rheometer (TA Instruments), configured with a parallel-plate geometry. The lower fixture incorporated a Peltier plate, providing temperature control, while the upper fixture was equipped with a poly(*p*-phenylene sulfide) (PPS) plate to minimize the temperature gradient across the sample. The polymeric material was heated on the Peltier plate at  $115^\circ\text{C}$ , liquefying the material and enabling intimate contact with both plates. Above and below the gel-point temperature, strain sweeps were conducted from 0.1 to 10 rad/s to verify the material was in the linear viscoelastic regime. Viscosity experiments were conducted over a strain rate ramp from 1.0 to 500 1/s to verify the material was strain rate independent.

## Results and Discussion

### FTIR Spectroscopy

Furan conversion (as determined by FTIR spectroscopy) versus time for PPTF-DPBM copolymerizations at several temperatures is shown in Figure 1A. FTIR spectroscopy enables facile determination of both furan and maleimide conversion independently and simultaneously; however, as the functionalities are consumed at equal rates in the DA reaction, for clarity, maleimide conversions are not shown. Whereas the polymerization reaction rate increases monotonically with cure temperature, the ultimate conversion is not monotonically dependent on the temperature. As the polymerization proceeds, there is an increase in the crosslinking density and the glass transition temperature ( $T_g$ ); however, once the  $T_g$  of the polymerizing material equals or exceeds the temperature ( $T_{cure}$ ), mobility limitations become significant and thus the polymerization rate is severely reduced, i.e., the network vitrifies. Typically, higher cure temperatures result in greater conversions until  $T_{cure}$  exceeds the ultimate attainable  $T_g$  at full conversion.<sup>40</sup> The increased maximum conversion when the polymerization temperature is raised from ambient to  $60^\circ\text{C}$  (see Figure 1A) is attributed to a delay in the onset of vitrification at the higher temperature. While it might be expected that vitrification should be further delayed at  $80^\circ\text{C}$  (Figure 1A), a decrease in the maximum conversion is observed. As the polymerization temperature is increased above approximately  $45^\circ\text{C}$ , the reaction transitions from kinetic control (a consequence of vitrification) to thermodynamic control associated with the attainment of the equilibrium reaction extent as dictated by the thermodynamics of the DA reaction. This transition can be inferred from Figure 1B where, below  $45^\circ\text{C}$ , vitrification limits the attainable conversion; whereas, above  $45^\circ\text{C}$ , the DA reaction is at or near thermodynamic equilibrium.

Figure 1B illustrates that, above  $45^\circ\text{C}$ , as the temperature is raised, the equilibrium is increasingly driven from the DA adduct to the reactants, via the rDA reaction. The gel-point conversion, as predicted by the Flory-Stockmayer equation (1), is 0.707 for bismaleimide-trifuran polymerization; from the conversion data, the gel-point temperature can be estimated to be  $92.5 \pm 0.5^\circ\text{C}$  (Figure 1B). Moreover, the temperature range neighboring the gel-point temperature is well within the thermodynamically controlled reaction regime, allowing facile examination of the gel-point without complications associated with vitrification.

The equilibrium conversion is further decreased to 24% at 155°C; however, an irreversible side reaction becomes apparent at higher temperatures. At long residence times, above 120°C, the maleimide peak area begins to decrease, while the furan peak area increases. This decrease in the maleimide peak area likely can be attributed to maleimide homopolymerization, initiated at high temperature as demonstrated by Hopewell et al.,<sup>41</sup> which is accompanied by a corresponding increase in furan concentration as the loss of maleimide drives the equilibrium further towards the reactants.

The equilibrium constant for the reaction between a maleimide (M) and a furan (F), producing a DA adduct (A),

$$K = \frac{[A]}{[M][F]} = \frac{p}{c_0(1-p)^2}, \quad (3)$$

can be calculated for a stoichiometric mixture of reactants using the conversion,  $p$  (see Figure 1B), and the initial concentration of either reactant,  $c_0$ . A plot of the natural logarithm of the equilibrium constant versus inverse temperature, Figure 2, allows the heat of reaction ( $\Delta H_r^\circ$ ) and entropy of reaction ( $\Delta S_r^\circ$ ) to be determined from the slope and intercept. The heat and entropy of reaction were found to be  $-40 \pm 1$  kJ/mol and  $-106 \pm 3$  J/mol/s, respectively. This calculated heat of reaction is significantly lower than the reported values (ranging from  $-84$  to  $-104$  kJ/mol) given for reactions between substituted furans with maleic anhydride,<sup>42</sup> however, it compares favorably with an estimate of  $\sim 32$  kJ/mol for the kinetically favored endo conformation of a furan-maleimide adduct.<sup>43</sup>

The rate of consumption of furan by reaction with the maleimide is written as

$$\frac{d[F]}{dt} = -k_f[F][M] + k_r[A], \quad (4)$$

where  $k_f$  and  $k_r$  are the forward and reverse rate constants, respectively. For a stoichiometric mixture of furan and maleimide, the reverse rate constants were determined at 25, 45, 60, and 80°C (see Supporting Information). The pre-exponential factor and activation energy for the retro DA reaction are determined from an Arrhenius plot to be  $5.6 \pm 0.3 \times 10^9$  s<sup>-1</sup> and  $88 \pm 2$  kJ/mol, respectively (see Figure 3). Activation energies of 102 to 114 kJ/mol have been measured for substituted furans and benzoquinones,<sup>44</sup> suggesting that the measured value is reasonable. The Arrhenius parameter determination allows for the adduct half-life to be expressed as a function of temperature,

$$t_{1/2} = \frac{\ln(2)}{k_r} = \frac{\ln(2)}{A_r \exp(-E_a/RT)}. \quad (5)$$

The adduct half-life, and thus the half-life of a crosslink, at the gel-point (i.e., 92.5°C) is calculated to be approximately 600 seconds, demonstrating the dynamic nature of the DA crosslink. The Arrhenius temperature dependence significantly decreases the reaction rate, and at 66°C the adduct half-life is approximately one order of magnitude longer. At room temperature the adduct half-life is on the order of days.

## Rheometry

The application of a small-amplitude sinusoidal deformation to a material yields a complex response, where the modulus is separable into the storage or elastic modulus,  $G'$ , and the

loss or viscous modulus,  $G''$ . Here, the behavior of the DA material at low temperatures, or high conversions, is that of a typical crosslinked polymer,<sup>45</sup> demonstrating a constant value for the elastic modulus at low frequency (i.e., a plateau modulus,  $G_p$ ) as seen in a frequency sweep at 75°C for the PPTF/DPBM network (Figure 4). As temperature increases, a drop-off in the low-frequency modulus occurs (Figure 4), and a cross-over in the elastic and viscous moduli is observed (Figure 5), demonstrating liquid-like behavior and relaxation at long timescales. Typical chemical gels form irreversible bonds; however, DA crosslinks are dynamic, constantly breaking and reforming over timescales dictated by the DA reaction kinetics and mobility restrictions, resulting in continuous network rearrangement on timescales associated with the temperature-dependent kinetics described above for the DA and rDA reactions. This low frequency behavior is analogous to that displayed by physical gels, such as gelatin,<sup>46</sup> which are connected by chain entanglements and other weak associations such as hydrogen bonds or ionic interactions, allowing network relaxation at long timescales. Network rearrangement has the consequence of adding a lower frequency bound to the Winter-Chambon criterion (2), corresponding to the longest relaxation time of the network,  $\tau_L$ . It should be noted that the relaxation in the DA network, as determined by the  $G'-G''$  cross-over at 87°C, occurs on the same order of magnitude,  $10^2 - 10^3$  s, as the half-life of the adduct determined from the kinetics.

Several distinguishing mechanical properties of the DA material, readily observed by rheometry, can be used to characterize its sol and gel states (see Figure 5). When the DA material is heated to 95°C, above the gel-point temperature (i.e., below the gel-point conversion), the viscous modulus is greater than the elastic modulus, characteristic of a liquid-like sol. Conversely, the elastic modulus is greater than the viscous modulus at 87°C for most of the frequency range, characteristic of a solid-like gel. At 91°C, the elastic and viscous moduli exhibit similar frequency scaling at higher frequencies, indicating that the material is near the gel-point as defined by the Winter-Chambon criterion, eq. (2); however, unlike typical chemical gels, the moduli exhibit liquid-like scaling at lower frequency owing to network relaxation.

The Winter-Chambon criterion, eq. (2), can be re-expressed in terms of the ratio of the viscous to elastic modulus (i.e.,  $\tan \delta$ ) which, at the gel-point, demonstrates frequency independence. A plot of constant frequency  $\tan \delta$  curves versus temperature (Figure 6) reveals an intersection that precisely marks the gel-point. The gel-point temperature was thus determined from several data sets to be  $92.1 \pm 0.2^\circ\text{C}$ , corresponding to a conversion of  $70.9 \pm 0.5\%$ , in excellent agreement with the gel-point conversion predicted by the Flory-Stockmayer equation (1). Whereas other researchers have demonstrated some extent of reverse polymerization at raised temperatures, to our knowledge, this is the first clear demonstration of a temperature controlled sol-gel transition in crosslinked DA polymers, in the absence of a solvent. For example, high temperature <sup>13</sup>C-NMR spectroscopy performed on crack-healing DA materials demonstrated reversion to 70% conversion; however, the tetrafurran-trimaleimide system used in that work would require a reversion to 40.1% conversion to achieve reverse gelation, indicating that “softening” and “remendability” was achieved exclusively through network rearrangement rather than liquid flow.<sup>12</sup>

The frequency cross-over in  $\tan \delta$  determines the frequency scaling of the storage and loss moduli,  $u$ , through the relationship,<sup>47</sup>

$$\delta = \frac{u \cdot \pi}{2}, \quad (6)$$

yielding  $u = 0.56 \pm 0.02$ . As the conversion approaches the gel-point from the sol phase (i.e., the liquid side of Figure 7), the viscosity divergence is described by the power law,

$$\eta \sim |\varepsilon|^{-s}, \quad (7)$$

while the emergence of a plateau modulus, beyond the gel-point (i.e., the solid side of Figure 7), is described by the power law,

$$G_p \sim |\varepsilon|^t, \quad (8)$$

where  $\varepsilon$  is the relative distance from the gel point,

$$\varepsilon \equiv \frac{p - p_{gel}}{p_{gel}}, \quad (9)$$

and  $s$  and  $t$  are characteristic scaling exponents.

The diverging and subsequent emerging nature of the viscosity and modulus, respectively, in the vicinity of the gel-point are shown in Figure 7. A zero shear modulus is not observed in DA networks owing to their long-time relaxation, and is thus supplanted by the corresponding plateau modulus as determined by the inflection point in the elastic modulus. The plateau modulus was normalized by the temperature to eliminate the entropic contribution ( $G \sim T$ , i.e., via rubber elasticity) and fit to equation (8) (dashed line, Figure 7), yielding  $t = 1.23 \pm 0.03$ . The viscosity was fit to equation (7) (solid line, Figure 7) and normalized by the activation energy (i.e.,  $\eta \sim \exp(E_a/RT)|\varepsilon|^{-s}$ ), yielding  $s = 1.4 \pm 0.2$ .

The scaling exponents  $u$ ,  $s$ , and  $t$  are the foundation for a universal description of gelation. Several theories attempt to predict these exponents, an overview of which is shown in Table 1. Mean field approaches have been used, but are typically successful only at high values of  $\varepsilon$  or when the distances between branch points are large, e.g., vulcanization.<sup>31, 48, 49</sup> De Gennes' electrical-mechanical analogy establishes an equivalent scaling of the modulus and macroscopic conductivity and, unlike mean field theory, predicts the divergence of the viscosity.<sup>50</sup> The Rouse model describes linear polymers as a series of identical beads and springs, and assumes hydrodynamic interactions are screened at sizes smaller than the monomer level. The Rouse model can be extended to describe networks and has been shown to predict the scaling exponents successfully when the distance between network junctions is small.<sup>51, 52</sup>

For the DA material, the frequency scaling of the elastic and viscous moduli at the gel-point,  $u$ , is most similar to the Rouse model prediction. For other systems, experimental values have been observed to be in the range of 0.19 to 0.92.<sup>54, 55</sup> Deviations of  $u$  from the Rouse model prediction have been suggested to occur because of chain overlap,<sup>49, 52</sup> and the discrepancy between the measured value and the Rouse model may occur because the molecular weight of the PPTF monomer is sufficient to allow chain overlap. Such behavior would be manifest by a value of  $u$  less than that predicated by the Rouse model.

The viscosity scaling exponent  $s$  agrees well with both the Rouse model prediction and literature values.<sup>34, 56</sup> It should be noted, however, that the error indicated for  $s$  only reflects random error and not the systematic error in the gel-point conversion, which can have considerable impact on the scaling determination. As the scaling exponents (i.e.,  $u$ ,  $s$ , and  $t$ ) are interdependent and are related through

$$t = \frac{su}{1-u},^{49,52,55} \quad (10)$$

the experimentally determined values for the exponents  $u$  and  $s$  can be used to calculate the plateau modulus exponent, yielding  $t = 1.8 \pm 0.3$ . This value is inconsistent with the experimentally determined value for  $t$  (see Table 1), which could simply be due to the sensitivity of the exponents to the precise location of the gel-point conversion.

## Conclusions

A crosslinked polymer was formed by the DA reaction between furan and maleimide moieties, and the furan conversion was measured using FTIR spectroscopy. Below 45°C, vitrification limited the ultimate attainable conversion, while above 45°C, the final conversion is determined by the thermodynamic equilibrium. At sufficiently elevated temperatures, the equilibrium shift through the retro-DA reaction results in depolymerization and reverse gelation. The gel-point temperature of the material was determined by the Winter-Chambon criteria to be  $92.1 \pm 0.2^\circ\text{C}$ , which, in conjunction with spectroscopic data, is consistent with the gel-point predicted by the Flory-Stockmayer equation for trifuran-bismaleimide system. The DA adduct half-life was on the same order of magnitude as the longest relaxation time for the network at 87°C, further illustrating the dynamic nature of the DA crosslink. The rapid and temperature dependent reversible DA reaction enables facile manipulation of conversion and thus allows the scaling exponents  $u$ ,  $s$ , and  $t$  to be determined in the vicinity of the gel-point. These exponents were found to be similar to other values in the literature; however, they were not consistent with values predicted from mean field theory, electrical-mechanical analogy, or the Rouse model.

Networks formed by the Diels-Alder reaction have been proposed for remendability, recyclability, and removability, properties that are not accessible in conventional thermosets. The crack healing ability of these networks can be attributed to the constant breaking and reforming of crosslinks, which allows affected areas to form new crosslinks. Furthermore, because the reaction is controlled by thermodynamics over a large temperature range, the crosslinking density can be controlled and these materials can be removed and recycled by reversion to low molecular weight species. These results not only demonstrate the utility of the Diels-Alder reaction in polymer science, but they also illustrate the potential of reversibly labile crosslinks for the creation of novel materials.

## Supplementary Material

Refer to Web version on PubMed Central for supplementary material.

## Acknowledgments


The authors acknowledge funding from the Department of Education GAANN Fellowship (BJA) ; NSF REU (HAA); and the National Institutes of Health NIH Grant DE 10959 (CJK, TFS, and CNB).


## References

1. Billmeyer, et al. Textbook of Polymer Science. New York: John Wiley and Sons; 1984.
2. Kloosterboer JG. Adv. Polym. Sci 1988;84:1–61.
3. Hoyle CE, Lee TY, Roper T. J. Polym. Sci., Part A: Polym. Chem 2004;42:5301–5338.
4. Oshima, A.; Abe, K.; Kameda, N. Process for producing abrasion-resistant cast article. U.S. Patent. 3978178. 1976.

5. Decker C. *Macromol. Rapid Commun.* 2002;23:1067–1093.
6. Anseth KS, Newman SM, Bowman CN. Polymeric dental composites: Properties and reaction behavior of multimethacrylate dental restorations. *Biopolymers* 1995;Vol. 122:177–217.
7. Lu H, Stansbury JW, Bowman CN. *Dent. Mater.* 2004;20:979–986. [PubMed: 15501327]
8. Urabe H, Wakasa K, Yamaki M. *J. Mater. Sci. - Mater. Med.* 1990;1:163–170.
9. LeBaron PC, Wang Z, Pinnavaia TJ. *Appl. Clay Sci.* 1999;15:11–29.
10. Inoue K, Yamashiro M, Iji M. *Kobunshi Ronbunshu* 2005;62:261–267.
11. Lendlein A, Jiang HY, Junger O, Langer R. *Nature* 2005;434:879–882. [PubMed: 15829960]
12. Chen XX, Dam MA, Ono K, Mal A, Shen HB, Nutt SR, Sheran K, Wudl F. *Science* 2002;295:1698–1702. [PubMed: 11872836]
13. Chen XX, Wudl F, Mal AK, Shen HB, Nutt SR. *Macromolecules* 2003;36:1802–1807.
14. Scott TF, Schneider AD, Cook WD, Bowman CN. *Science* 2005;308:1615–1617. [PubMed: 15947185]
15. Odian, G. *Principles of Polymerization*. 3rd ed.. New York: John Wiley and Sons, Inc.; 1991.
16. Ono T, Nobori T, Lehn JM. *Chem. Commun.* 2005:1522–1524.
17. Yurke B, Lin DC, Langrana NA. Use of DNA nanodevices in modulating the mechanical properties of polyacrylamide gels. *DNA Computing* 2006;Vol. 3892:417–426.
18. March, J. *Advanced Organic Chemistry: Reactions, Mechanisms, and Structure*. New York: John Wiley and Sons; 1992. p. 830
19. Fringuelli, F.; Taticchi, A. *The Diels-Alder Reaction*. New York: John Wiley and Sons; 2002.
20. Gousse C, Gandini A. *Polym. Int.* 1999;48:723–731.
21. Canary SA, Stevens MP. *J. Polym. Sci., Part A: Polym. Chem.* 1992;30:1755–1760.
22. Imai Y, Itoh H, Naka K, Chujo Y. *Macromolecules* 2000;33:4343–4346.
23. Chujo Y, Sada K, Saegusa T. *Macromolecules* 1990;23:2636–2641.
24. Szalai ML, McGrath DV, Wheeler DR, Zifer T, McElhanon JR. *Macromolecules* 2007;40:818–823.
25. McElhanon JR, Russick EM, Wheeler DR, Loy DA, Aubert JH. *J. Appl. Polym. Sci.* 2002;85:1496–1502.
26. Heath WH, Palmieri F, Adams JR, Long BK, Chute J, Holcombe TW, Zieren S, Truitt MJ, White JL, Willson CG. *Macromolecules* 2008;41:719–726.
27. Long BK, Keitz BK, Willson CG. *J. Mater. Chem.* 2007;17:3575–3580.
28. Gousse C, Gandini A, Hodge P. *Macromolecules* 1998;31:314–321.
29. Chang, BTA.; Dubois, DA.; Ming, F.; Gelles, DL.; Iyer, SR.; Mohindra, S.; Tutunjian, PN.; Wong, PK.; Wright, WJ. CARIVERSE resin: a thermally reversible network polymer for electronic applications; Electronic Components and Technology Conference. 1999 Proceedings. 49th; p. 49-55.
30. Flory PJ. *J. Am. Chem. Soc.* 1941;63:3083–3090.
31. Stockmayer WH. *J. Chem. Phys.* 1943;11:45–55.
32. Winter HH. *Polym. Eng. Sci.* 1987;27:1698–1702.
33. Adolf D, Martin JE, Wilcoxon JP. *Macromolecules* 1990;23:527–531.
34. Hodgson DF, Amis EJ. *J. Non-Cryst. Solids* 1991;131:913–920.
35. Lairez D, Adam M, Emery JR, Durand D. *Macromolecules* 1992;25:286–289.
36. Lairez D, Adam M, Raspaud E, Emery JR, Durand D. *Prog. Colloid Polym. Sci.* 1992;90:37–42.
37. Chiou BS, English RJ, Khan SA. *Macromolecules* 1996;29:5368–5374.
38. Decker C, Bianchi C, Jonsson S. *Polymer* 2004;45:5803–5811.
39. Tarducci C, Badyal JPS, Brewer SA, Willis C. *Chem. Commun.* 2005:406–408.
40. Enns JB, Gillham JK. *J. Appl. Polym. Sci.* 1983;28:2567–2591.
41. Hopewell JL, Hill DJT, Pomery PJ. *Polymer* 1998;39:5601–5607.
42. Dewar MJS, Pierini AB. *J. Am. Chem. Soc.* 1984;106:203–208.


43. Rulisek L, Sebek P, Havlas Z, Hrabal R, Capek P, Svatos A. *J. Org. Chem* 2005;70:6295–6302.  
[PubMed: 16050690]
44. Jurczak J, Kawczynski AL, Kozluk T. *J. Org. Chem* 1985;50:1106–1107.
45. Ferry, JD. Viscoelastic Properties of Polymers. 3 ed.. John Wiley and Sons; 1980.
46. Nijenhuis KT. Thermoreversible networks - Viscoelastic properties and structure of gels. *Thermoreversible Networks* 1997;Vol. 130
47. Michon C, Cuvelier G, Launay B. *Rheol. Acta* 1993;32:94–103.
48. de Gennes, PG. Scaling Concepts in Polymer Physics. Ithaca and London: Cornell University Press; 1979.
49. Lusignan CP, Mourey TH, Wilson JC, Colby RH. *Phys. Rev. E* 1999;60:5657–5669.
50. de Gennes PG. *J. Phys. - Paris* 1976;37 L-1.
51. Rubenstein, M.; Colby, RH.; Gillmor, JR. Dynamic Scaling for Polymer Gelation. In: Tanaka, F.; Doi, M.; Ohta, T., editors. *Space-Time Organization in Macromolecular Fluids*. Vol. Vol. 30. Berlin: Springer-Verlag; 1989.
52. Lusignan CP, Mourey TH, Wilson JC, Colby RH. *Phys. Rev. E* 1995;52:6271–6280.
53. Devreux F, Boilot JP, Chaput F, Malier L, Axelos MAV. *Phys. Rev. E* 1993;47:2689–2694.
54. Scanlan JC, Winter HH. *Macromolecules* 1991;24:47–54.
55. Durand D, Delsanti M, Adam M, Luck JM. *Europhys. Lett* 1987;3:297–301.
56. Guo L, Colby RH, Lusignan CP, Howe AM. *Macromolecules* 2003;36:10009–10020.

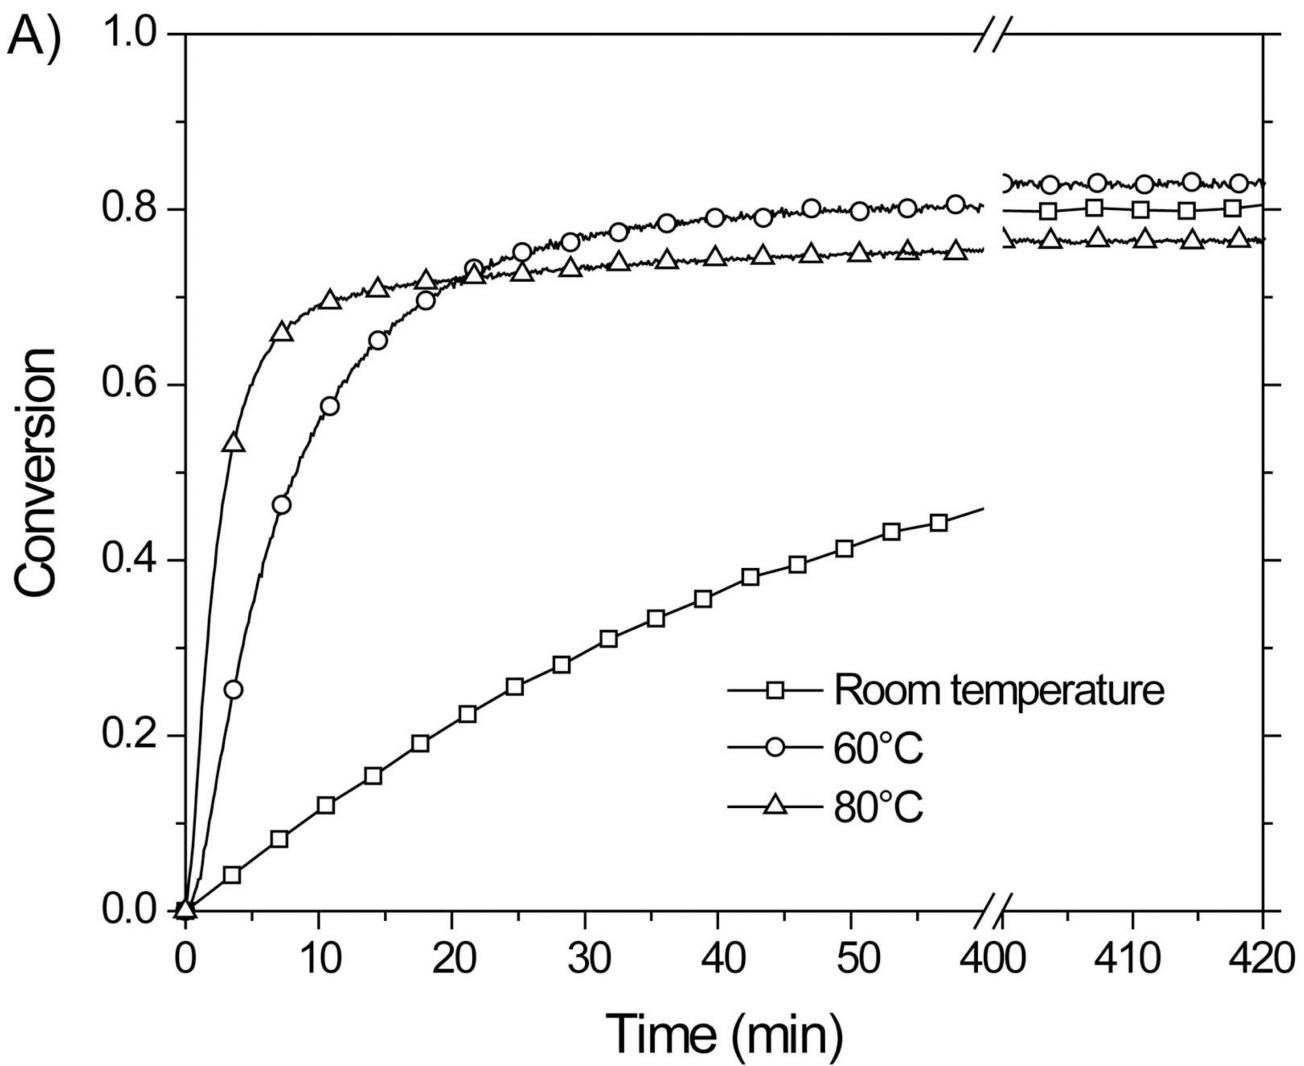

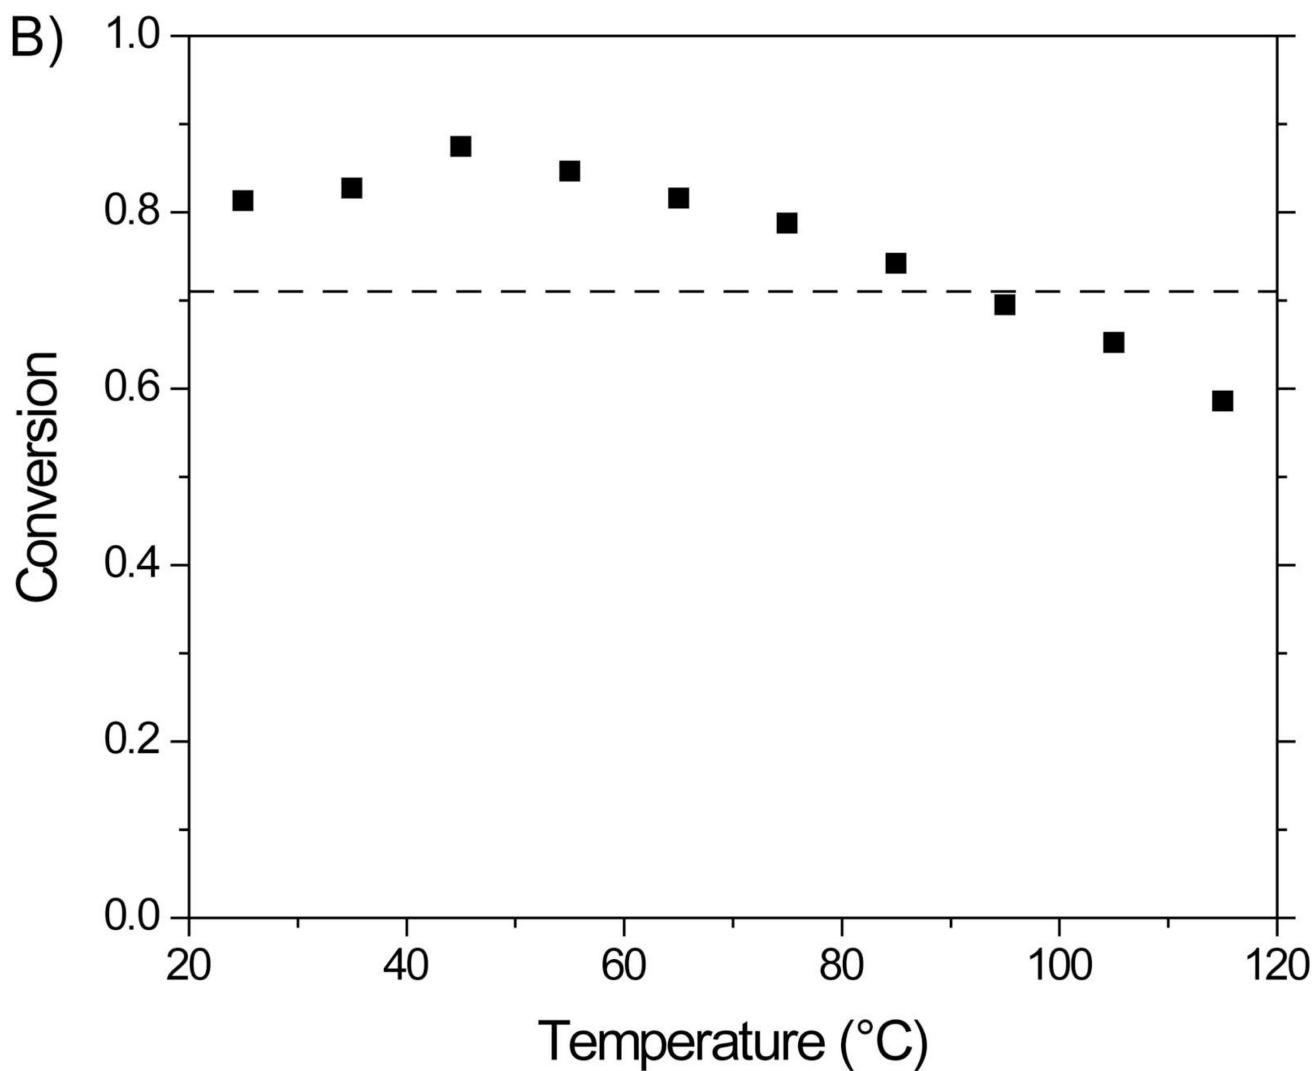


**Figure 1.**

(A) Fractional furan conversion during isothermal polymerizations of 1:1 stoichiometric mixtures of PPTF and DPBM, at various temperatures.  
(B) Ultimate furan conversion after PPTF-DPBM polymerization. The dashed line represents the gel-point conversion predicted by the Flory-Stockmayer equation, where  $f_M = 2$  and  $f_F = 3$  (i.e., bismaleimide and trifuran). Maleimide conversions are identical and not plotted for clarity.

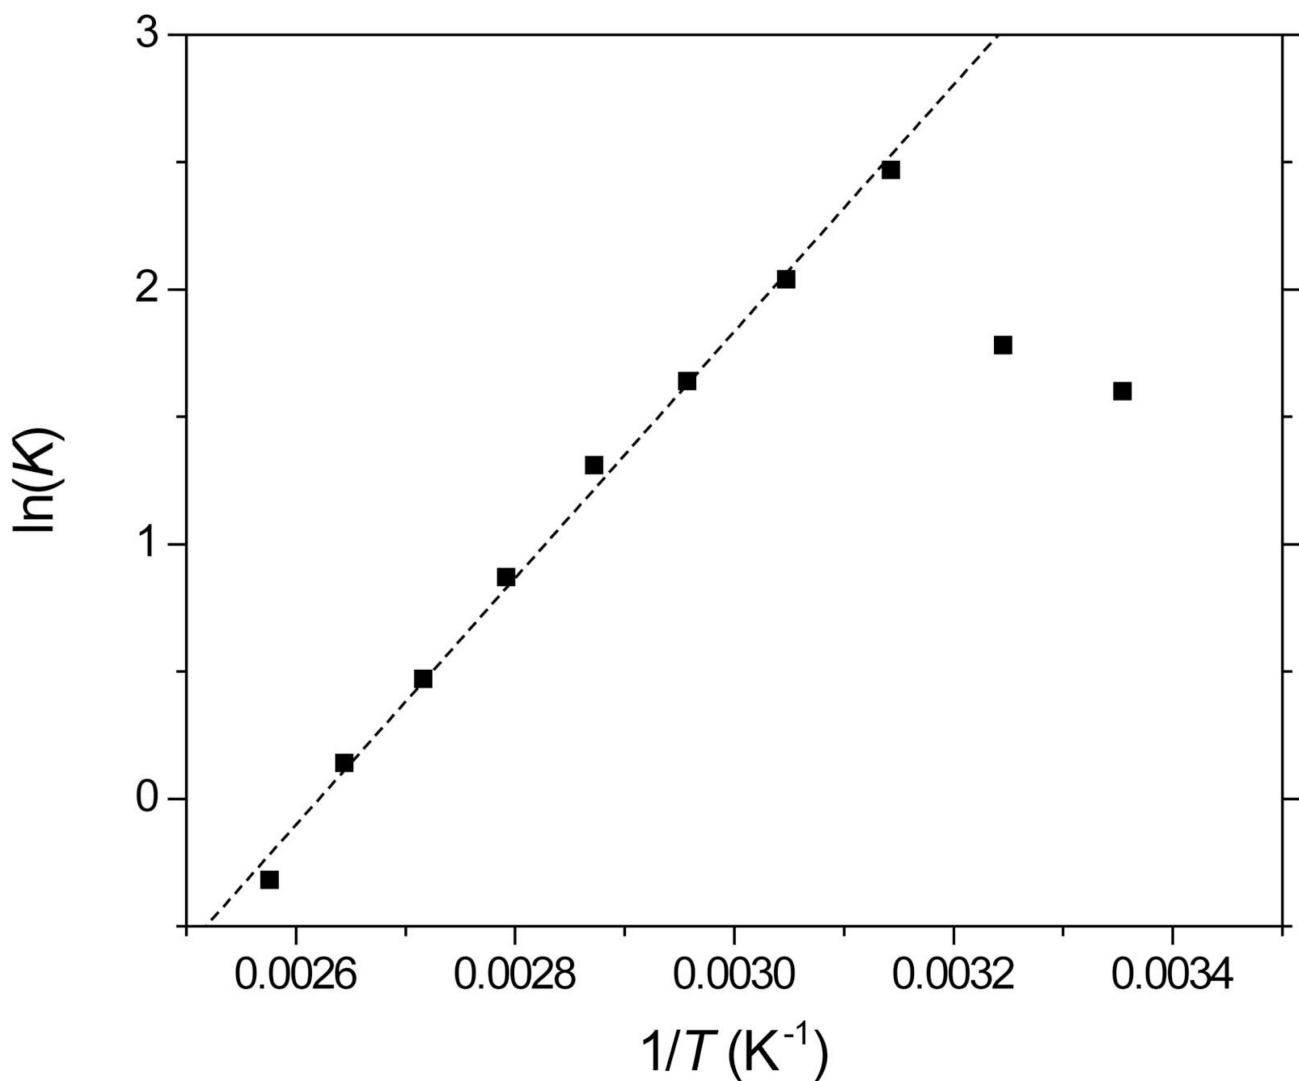
**Figure 2.**

A plot of the natural logarithm of the equilibrium constant (in  $M^{-1}$ ) versus reciprocal temperature, allows determination of the heat and entropy of reaction through the van't Hoff equation. The fit excludes the data at low temperature where vitrification is evident, preventing the DA reaction equilibrium from being achieved.

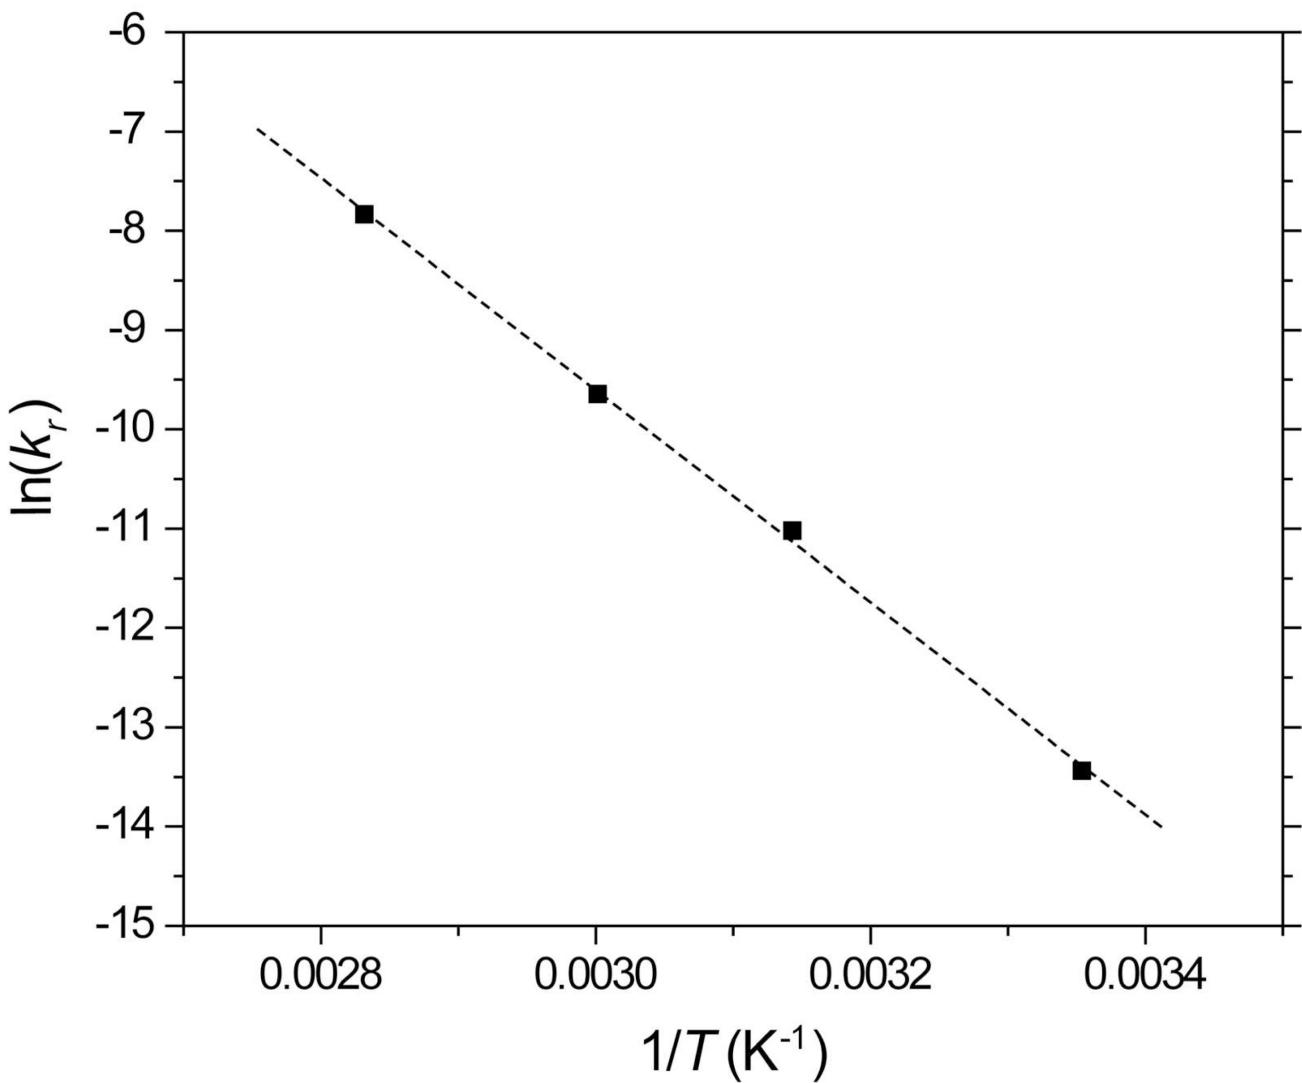


**Figure 3.**

Arrhenius plot of the natural logarithm of the reverse DA rate constant (in s<sup>-1</sup>) versus inverse temperature. The dashed line represents a fit of the data that allows the pre-exponential factor and activation energy to be determined from the intercept and slope, respectively.

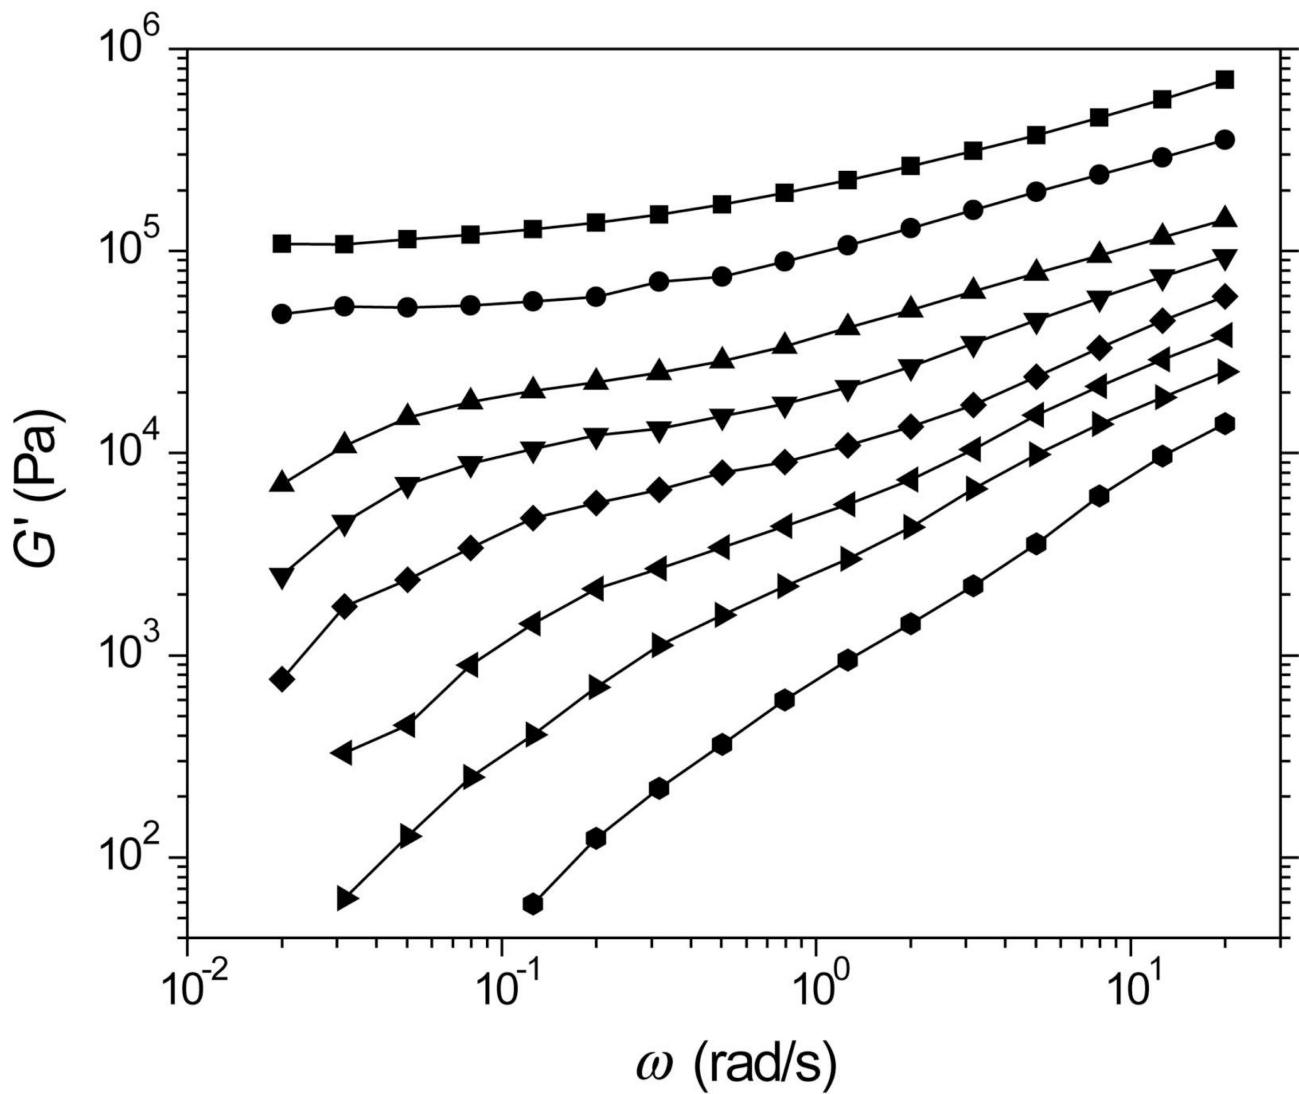


**Figure 4.**

Elastic modulus versus frequency for a PPTF/DPBM network. Frequency sweeps were performed at 75 (■), 80 (●), 85 (▲), 87 (▼), 89 (◆), 91 (◀), 93 (▶), and 95°C (○).

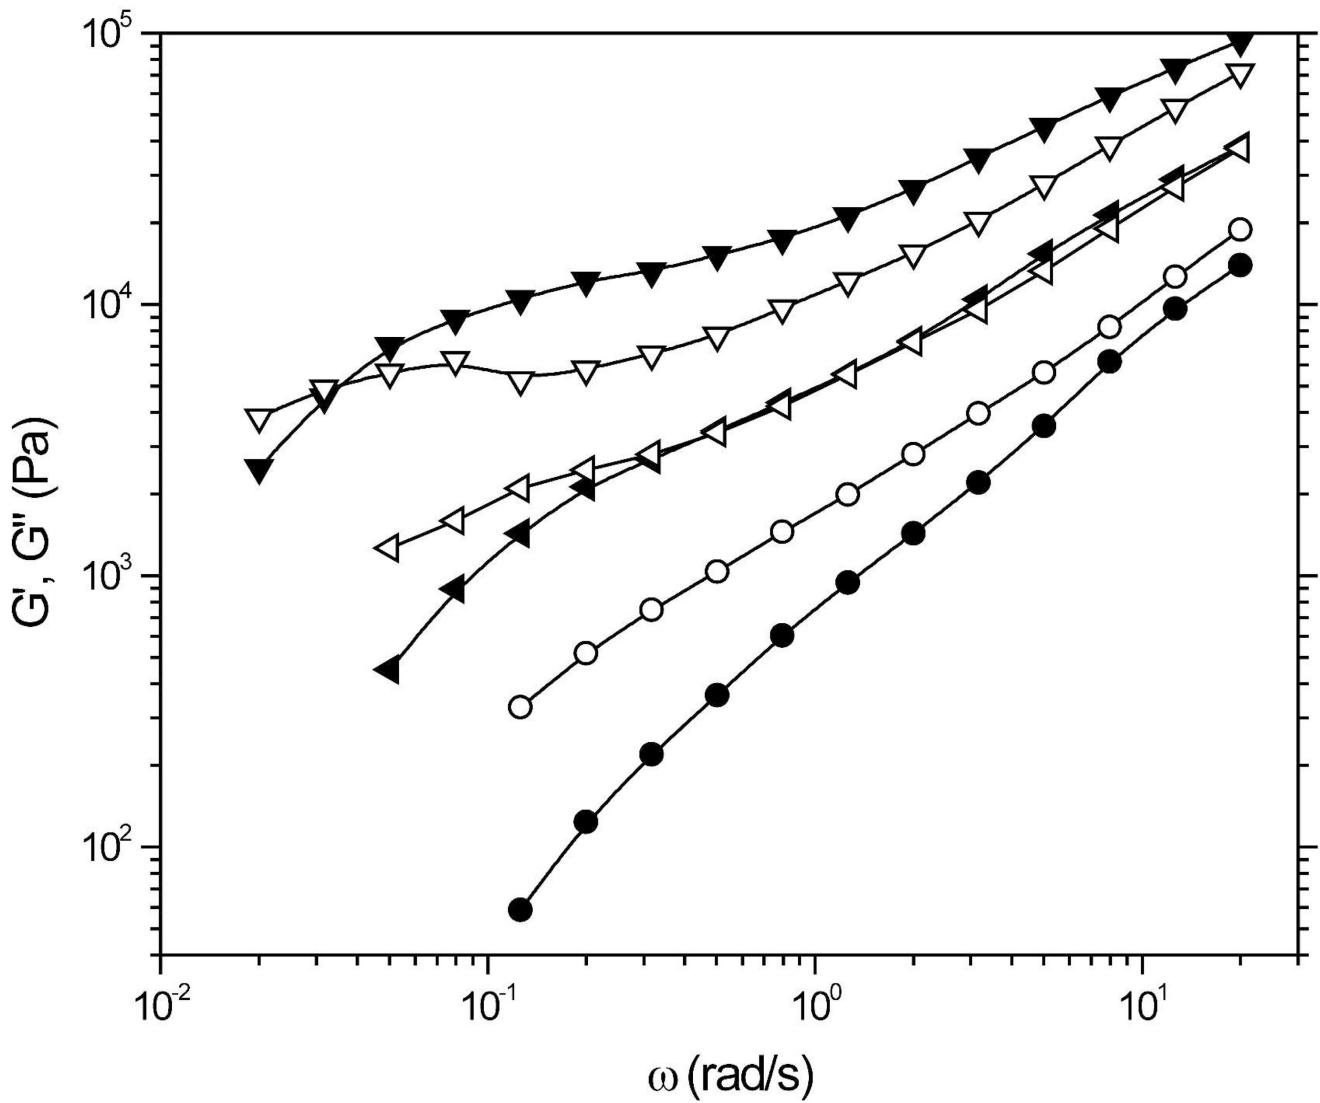


**Figure 5.**

Elastic (filled symbols) and viscous (open symbols) moduli versus frequency at temperatures above (95°C,), near (91°C,), and below (87°C,) the gel-point temperature.

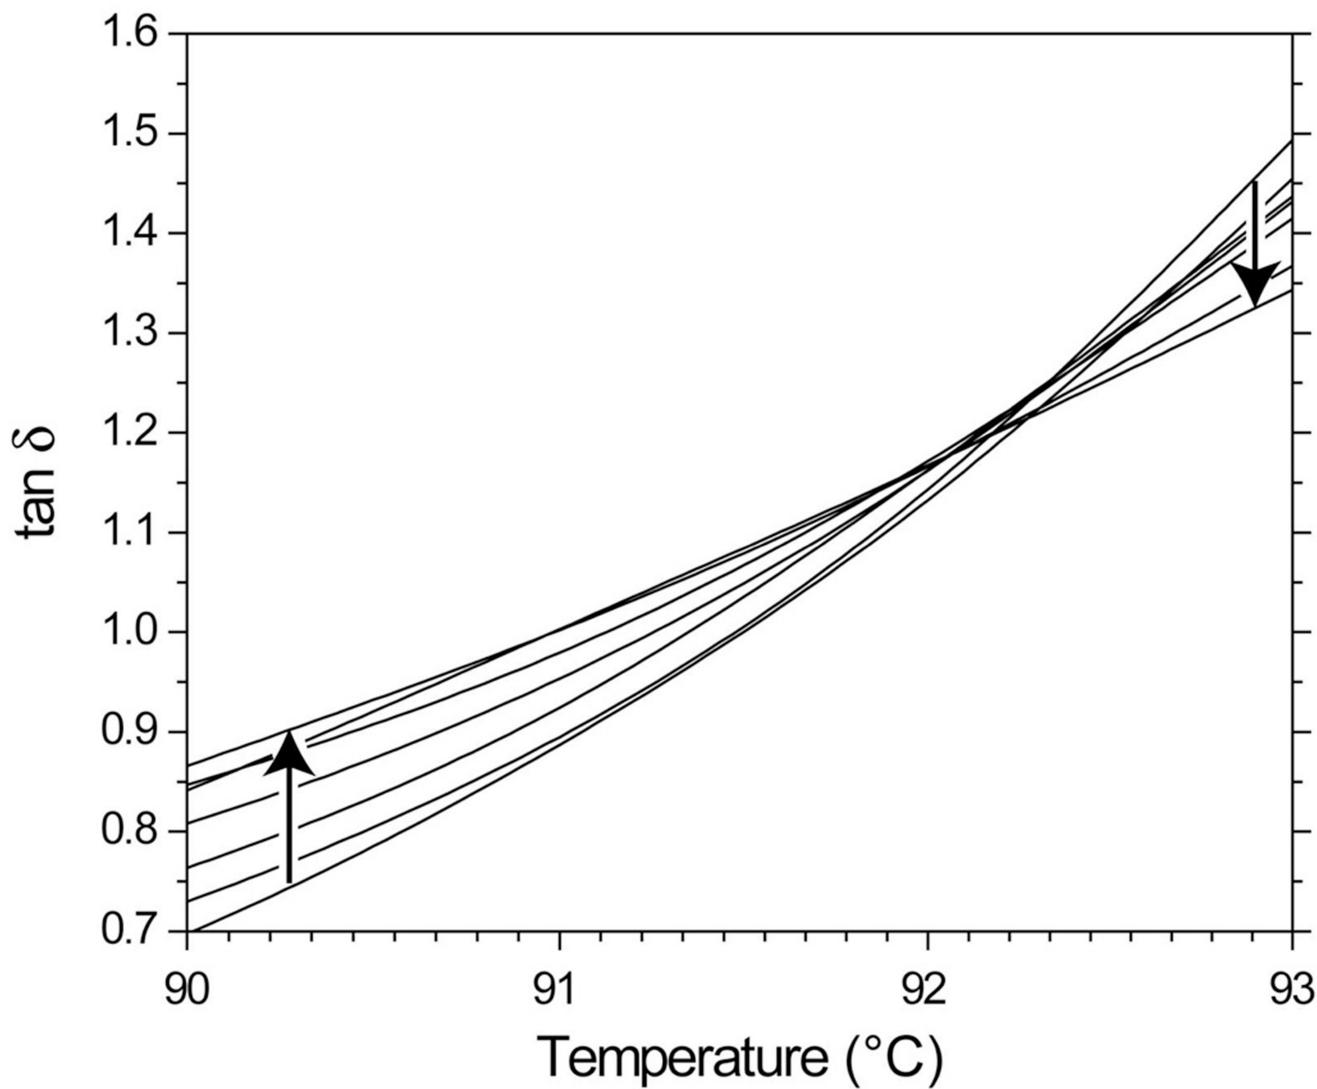


**Figure 6.**

Tan  $\delta$  for several frequencies between 0.63 and 10 rad/s versus temperature, demonstrating frequency independence (i.e., a cross-over) at 92.1°C. The upper and lower frequency limits are within the valid range of the Winter-Chambon criterion, where  $1/\tau_L < \omega < 1/\tau_0$ . Direction of arrows indicate increasing frequency.

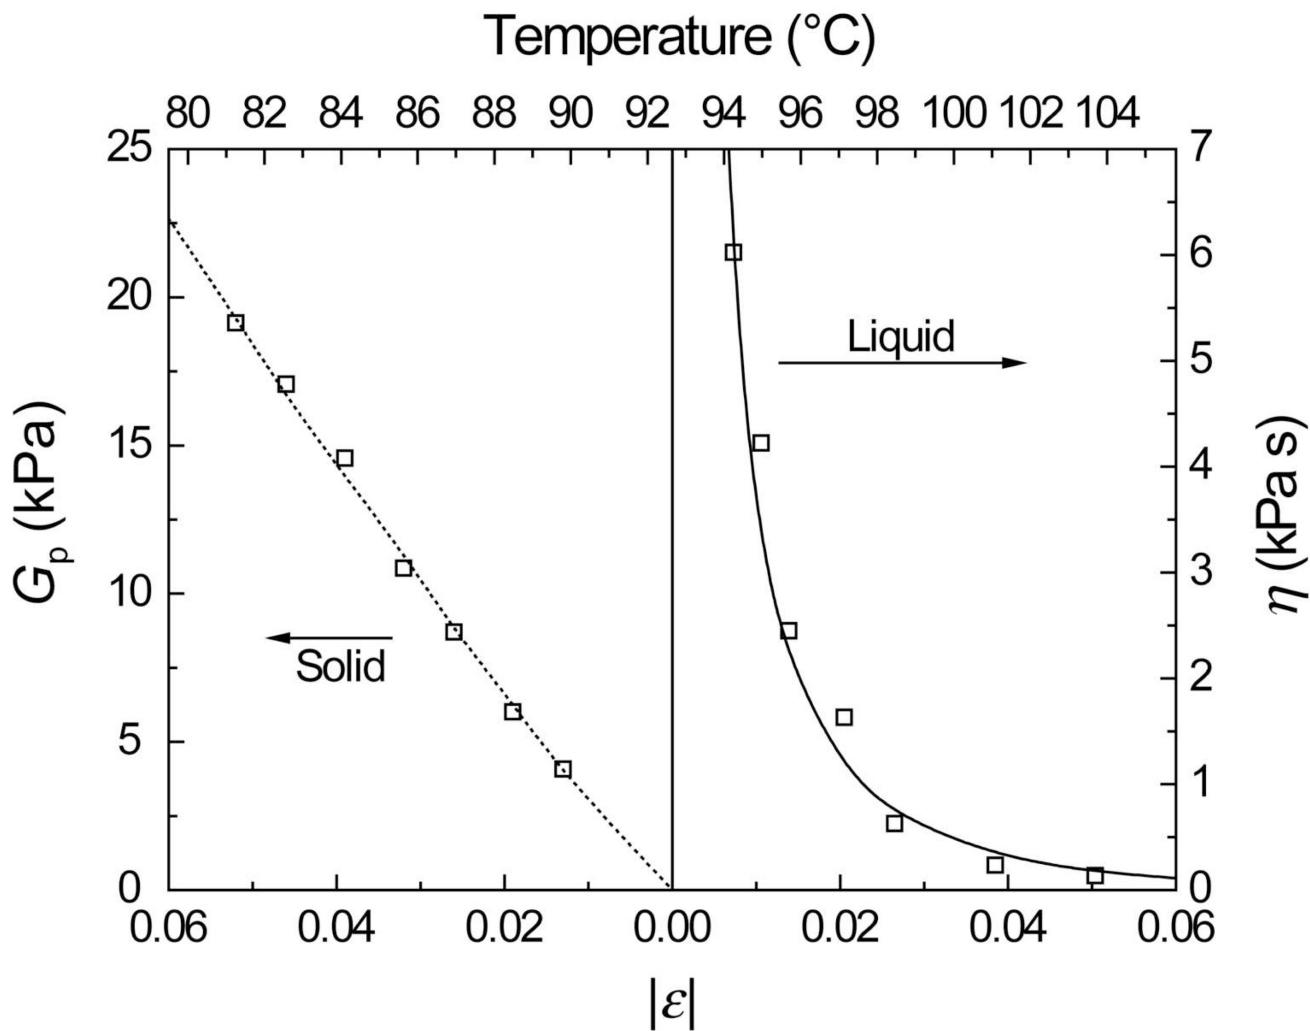


**Figure 7.**

The plateau modulus (left) and the viscosity (right) as a function of the relative distance from the gel point and temperature. The lines indicate the fits of the data to (7) and (8) on the liquid- and solid-side, respectively.

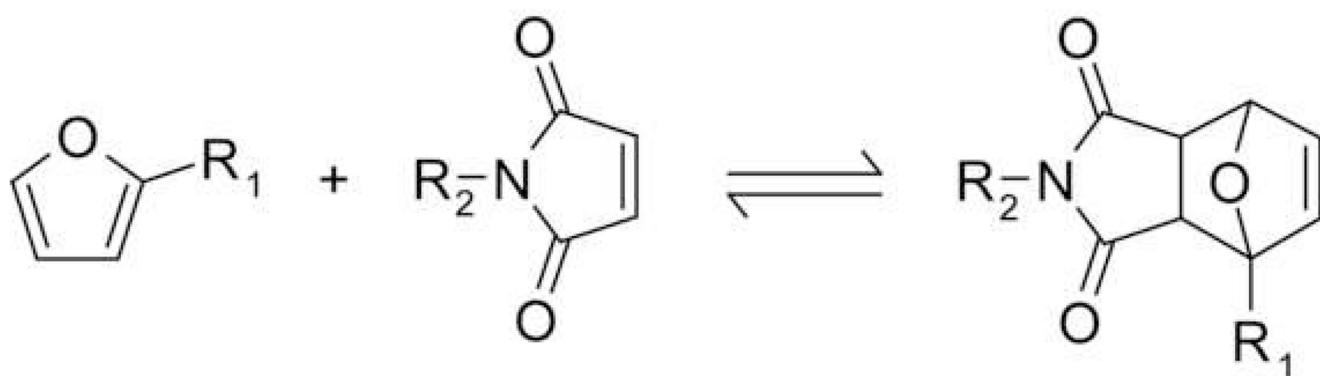

**Scheme 1.**

Diels-Alder/retro-Diels-Alder reaction between a furan and maleimide. Polymer networks are formed when the Diels-Alder pathway is utilized in monomers with multiple reactive functionalities.

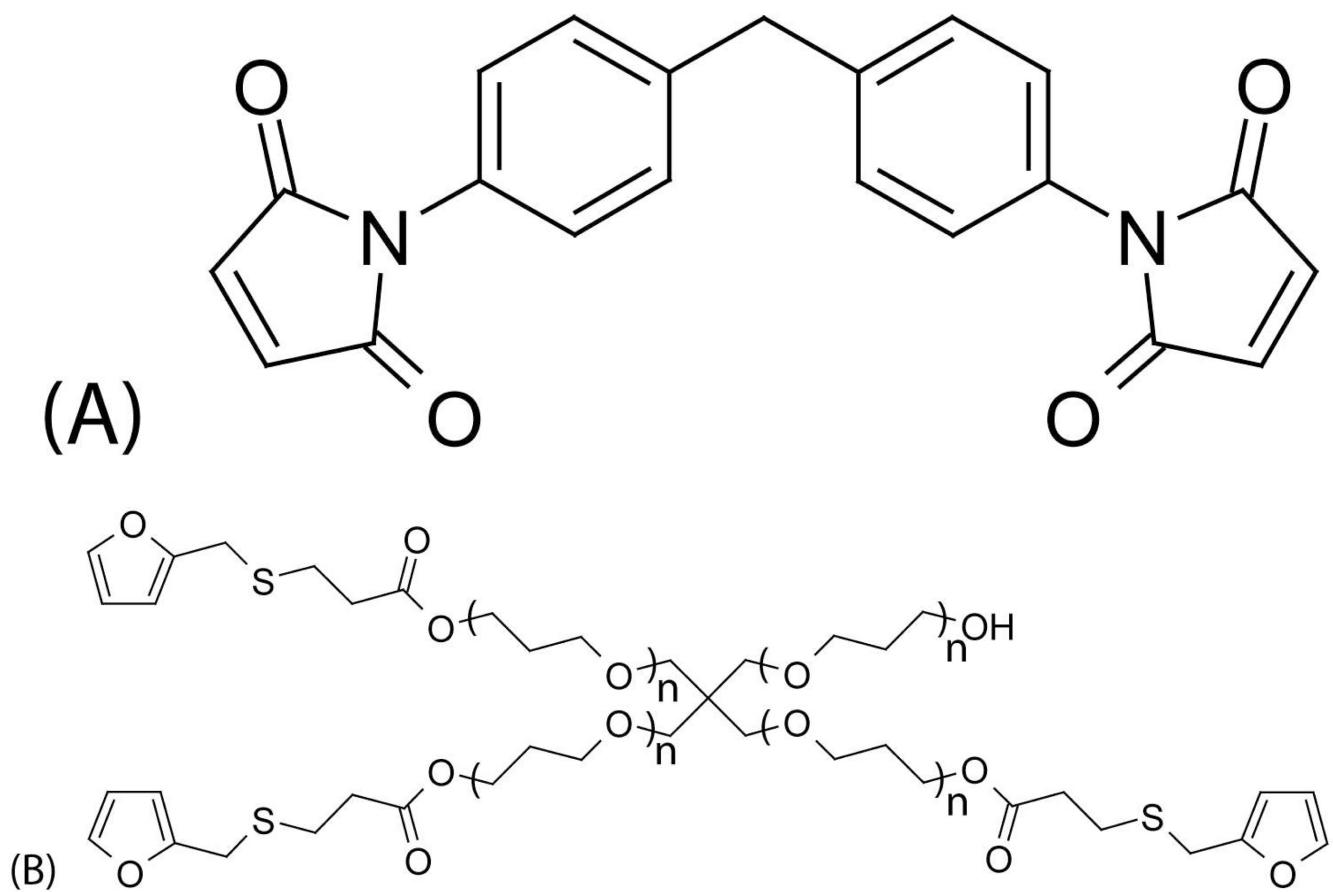

**Scheme 2.**

Monomers used for copolymerization: (A) DPBM, and (B) PPTF, where  $n \sim 1$ .

**Table 1**

Experimental and theoretical values of scaling exponents associated with gelation.

	<i>u</i>	<i>s</i>	<i>t</i>	Ref.
<b>Mean Field</b>	1	0	3	31,53
<b>Electrical-Mechanical Analogy</b>	0.72	0.75	1.9	50, 53
<b>Rouse Model</b>	0.67	1.3	2.6	51
<b>Experiment</b>	$0.56 \pm 0.02$	$1.4 \pm 0.2$	$1.23 \pm 0.03$	-