

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/221819011>

# Syntheses, Structures, and Magnetic Analyses of a Family of Heterometallic Hexanuclear $[\text{Ni}_4\text{M}_2]$ (M = Gd, Dy, Y) Compounds: Observation of Slow Magnetic Relaxation in the Dy-III Deri...

ARTICLE *in* INORGANIC CHEMISTRY · FEBRUARY 2012

Impact Factor: 4.76 · DOI: 10.1021/ic202699k · Source: PubMed

---

CITATIONS

45

---

READS

26

4 AUTHORS, INCLUDING:



Hongshan Ke

Northwest University

28 PUBLICATIONS 498 CITATIONS

SEE PROFILE



Lang Zhao Dr

Chinese Academy of Sciences

62 PUBLICATIONS 1,593 CITATIONS

SEE PROFILE

# Syntheses, Structures, and Magnetic Analyses of a Family of Heterometallic Hexanuclear $[\text{Ni}_4\text{M}_2]$ ( $\text{M} = \text{Gd}, \text{Dy}, \text{Y}$ ) Compounds: Observation of Slow Magnetic Relaxation in the $\text{Dy}^{\text{III}}$ Derivative


Hongshan Ke,<sup>†,‡</sup> Lang Zhao,<sup>†</sup> Yang Guo,<sup>†</sup> and Jinkui Tang<sup>\*,†</sup>

<sup>†</sup>State Key Laboratory of Rare Earth Resource Utilization, Changchun Institute of Applied Chemistry, Chinese Academy of Sciences, Changchun 130022, People's Republic of China

<sup>‡</sup>Graduate School of the Chinese Academy of Sciences, Beijing 100039, People's Republic of China

## S Supporting Information

**ABSTRACT:** We described the syntheses, crystal structures, and magnetic behavior of a novel series of heterometallic  $[\text{Ni}_4\text{M}_2]$  ( $\text{M} = \text{Gd}$  (1),  $\text{Dy}$  (2) and  $\text{Y}$  (3)) hexanuclear compounds afforded by the reaction of rare-earth(III) nitrate, nickel(II) acetate, and Schiff-base ligand 2-(2-hydroxy-3-methoxybenzylideneamino)phenol ( $\text{H}_2\text{L}$ ) in a mixture of ethanol and dichloromethane in the presence of triethylamine. Single-crystal X-ray diffraction measurements reveal that all three compounds have a metal core made up of two  $\text{Ni}_2\text{MO}_4$  defective cubanes. The magnetic properties of all compounds have been studied. Solid-state direct-current magnetic susceptibility analyses demonstrate competing antiferromagnetic and ferromagnetic interactions within both compounds 1 and 3. Solid-state alternating-current magnetic susceptibility investigations show a frequency-dependent out-of-phase signal for compound 2 below 4 K, suggestive of slow magnetic relaxation.

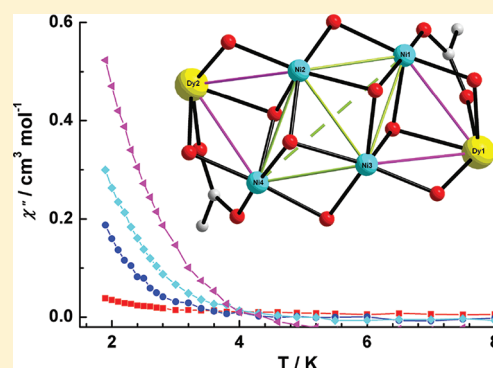

## INTRODUCTION


The design, synthesis, and magnetic investigation of single-molecule-magnets (SMMs)<sup>1</sup> have attracted widespread attention in the past 2 decades because each individual molecule of SMMs can act as a single-domain nanomagnet at a certain blocking temperature in the absence of an external magnetic field, retaining its magnetization once magnetized.<sup>1</sup> SMMs have been considered as potential candidates for the development of information storage and quantum computing devices.<sup>2</sup> Initially, efforts devoted to the quest for SMMs have mainly concentrated on transition-metal<sup>3</sup> clusters, with the majority of them Mn clusters<sup>4</sup> and, in particular, some  $\text{Mn}^{\text{III}}$  centers,<sup>5</sup> which have uniaxial anisotropy in its high-spin state. Moreover, SMMs incorporating  $\text{Fe}^{\text{II/III}}$ ,<sup>6</sup>  $\text{Co}^{\text{II}}$ ,<sup>7</sup> and  $\text{Ni}^{\text{II/III}}$  ions have also been reported. Frustratingly, the blocking temperature of these described SMMs remained low. As a result, intense current interest to construct SMMs with higher blocking temperatures tends to be focused on mixed-metal systems containing both lanthanide and transition-metal ions.<sup>8</sup> Thus, a number of 3d–4f heterometallic clusters showing SMM properties have been documented, varying in nuclearity numbers from 2<sup>9</sup> to 32<sup>10</sup> and displaying a variety of structure topologies ranging from linear,<sup>11</sup> diamond,<sup>12</sup> star,<sup>13</sup> cyclic,<sup>14</sup> ring,<sup>15</sup> to dicubanes,<sup>16</sup> tricubanes,<sup>17</sup> bell,<sup>18</sup> double-propeller<sup>19</sup> as well as other aesthetically unusual and irregular structural motifs.<sup>20</sup> The majority of these SMMs have involved  $\text{Ln}^{\text{III}}-\text{Mn}^{\text{II/III/IV}}$ ,<sup>12,16a,18</sup>  $\text{Ln}^{\text{III}}-\text{Fe}^{\text{II/III}}$ ,<sup>9a,11a</sup>  $\text{Ln}^{\text{III}}-\text{Co}^{\text{II}}$ ,<sup>11c</sup>  $\text{Ln}^{\text{III}}-\text{Ni}^{\text{II/III}}$ ,<sup>9d,11a,13a,16d,21</sup> and

$\text{Ln}^{\text{III}}-\text{Cu}^{\text{II}}$ .<sup>11b,14,22</sup> In particular, most of such systems presented so far contain heavy lanthanides such as  $\text{Tb}^{\text{III}}$  or  $\text{Dy}^{\text{III}}$ , which possess significant inherent magnetic anisotropy arising from the large unquenched orbital angular momentum as well as several unpaired spins.<sup>23</sup> It is noteworthy that syntheses of  $\text{Ln}^{\text{III}}-\text{Ni}^{\text{II}}$ -based SMMs remain relatively scarce.<sup>9d,11a,13a,16d,21</sup> Moreover, the  $\text{Ln}^{\text{III}}-\text{Ni}^{\text{II}}$  combination is an appealing candidate for SMMs because  $\text{Ni}^{\text{II}}$  ions generally exhibit large anisotropy due to its second-order orbital angular momentum.<sup>16d,24</sup>

It is well recognized that the selection of the ligand is crucial to the preparation of 3d–4f heterometallic compounds. A typical approach is based on a one-pot procedure, involving a mixture of 3d and 4f metal salts, and a carefully chosen ligand features distinct functionalities for preferential binding of the 3d and 4f ions. Polydentate chelating Schiff-base ligands are appealing for mixed-metal systems because the chemical characteristics of the polydentate (N and O atoms) can fulfill the coordination affinities to 3d and 4f metal ions for N and O atoms. In fact, there are several examples of 3d–4f compounds derived from this class of ligands.<sup>9c,d,11c,17a,21a</sup> In the present work, we have employed (*E*)-2-(2-hydroxy-3-methoxybenzylideneamino)phenol ( $\text{H}_2\text{L}$ ; Scheme 1) in  $\text{Ni}-\text{M}$  ( $\text{M}$  stands for rare-earth metal ions) cluster chemistry. This

Received: December 15, 2011

Published: February 9, 2012

Scheme 1. Structure of the H<sub>2</sub>L Ligand

ligand had been used previously to prepare homometallic clusters<sup>25</sup> and had very recently been exploited in 3d–M heterometallic systems.<sup>16d</sup> Herein we report a family of Ni<sub>4</sub>M<sub>2</sub> clusters consisting of two Ni<sub>2</sub>MO<sub>4</sub> defective cubanes with unusual structural features and magnetic properties, including slow magnetic relaxation for the Ni<sub>4</sub>Dy<sub>2</sub> member.

## EXPERIMENTAL SECTION

**Materials and Synthesis.** All starting materials were of analytical reagent grade and were used as received without further purification. 2-(2-Hydroxy-3-methoxybenzylideneamino)phenol (H<sub>2</sub>L) was prepared by condensation of 2-aminophenol and *o*-vanillin in a 1:1 molar ratio in hot ethanol according to a modified procedure reported previously.<sup>26</sup> All reactions were carried out under aerobic conditions.

**Preparation of Compound [Ni<sub>4</sub>Gd<sub>2</sub>(μ<sub>3</sub>-OH)<sub>2</sub>(L)<sub>4</sub>(OAc)<sub>2</sub>(NO<sub>3</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>2</sub>·5C<sub>2</sub>H<sub>5</sub>OH·H<sub>2</sub>O (1).** A methanolic solution of triethylamine (0.65 mL, 0.30 mmol) was added to the Schiff-base H<sub>2</sub>L ligand (0.15 mmol, 40 mg) dissolved in 8 mL of ethanol. The reaction mixture was stirred for 40 min. Next, solid gadolinium nitrate hexahydrate (0.15 mmol, 66 mg) was added to the above mixture, and the resulting solution was stirred for 3 h. Solid nickel acetate tetrahydrate (0.15 mmol, 40 mg) was added and further stirred for 2 h. A total of 8 mL of dichloromethane was subsequently added, and the reaction mixture was filtered and then left unperturbed to allow the slow evaporation of the solution. Brown block single crystals, suitable for X-ray diffraction analysis, were obtained after 3 weeks. These crystals were collected by filtration, washed with cold ethanol, and dried in air. Yield: 26 mg (33%, based on the ligand). Elem. anal. Calcd for C<sub>70</sub>H<sub>88</sub>N<sub>6</sub>O<sub>32</sub>Ni<sub>4</sub>Gd<sub>2</sub>: C, 40.52; H, 4.27; N, 4.05. Found: C, 40.24; H, 3.91; N, 3.95. IR (KBr, cm<sup>-1</sup>): 3383(m), 3061(m), 2947(m), 1617(s), 1587(s), 1556(s), 1489(s), 1463(s), 1435(s), 1387(s), 1310(s), 1295(m), 1279(w), 1255(m), 1229(s), 1183(s), 1112(w), 1095(w), 1076(w), 1037(w), 968(m), 878(w), 858(w), 824(m), 783(w), 739(s), 661(w), 642(m), 618(w), 579(w), 555(w), 516(m), 444(w).

**Preparation of Compound [Ni<sub>4</sub>Dy<sub>2</sub>(μ<sub>3</sub>-OH)<sub>2</sub>(L)<sub>4</sub>(OAc)<sub>2</sub>(NO<sub>3</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>2</sub>·4C<sub>2</sub>H<sub>5</sub>OH·2H<sub>2</sub>O (2).** This compound was obtained as brown block crystals according to the procedure for **1**, using Dy(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O (0.20 mmol, 96 mg) in place of Gd(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O. Yield: 23 mg (28%, based on the ligand). Elem. anal. Calcd for C<sub>68</sub>H<sub>84</sub>N<sub>6</sub>O<sub>32</sub>Ni<sub>4</sub>Dy<sub>2</sub>: C, 39.70; H, 4.11; N, 4.09. Found: C, 39.51; H, 3.75; N, 3.94. IR (KBr, cm<sup>-1</sup>): 3412(m), 3062(m), 1616(s), 1587(m), 1556(m), 1484(s), 1463(s), 1385(s), 1307(m), 1230(s), 1184(m), 1112(w), 1095(w), 1076(w), 1036(w), 967(m), 877(w), 857(w), 822(m), 739(m), 663(w), 642(w), 579(w), 517(w), 444(w).

**Preparation of Compound [Ni<sub>4</sub>Y<sub>2</sub>(μ<sub>3</sub>-OH)<sub>2</sub>(L)<sub>4</sub>(OAc)<sub>2</sub>(NO<sub>3</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>2</sub>·5C<sub>2</sub>H<sub>5</sub>OH·CH<sub>3</sub>OH (3).** This compound was prepared as olive plate crystals following the procedure for **1**, except that Y(NO<sub>3</sub>)<sub>3</sub>·5H<sub>2</sub>O (0.15 mmol, 58 mg) was used instead of Gd(NO<sub>3</sub>)<sub>3</sub>·6H<sub>2</sub>O. Yield: 20 mg (27%, based on the ligand). Elem. anal. Calcd for C<sub>71</sub>H<sub>90</sub>N<sub>6</sub>O<sub>32</sub>Ni<sub>4</sub>Y<sub>2</sub>: C, 43.68; H, 4.65; N, 4.31. Found: C, 43.62; H, 4.30; N, 4.21. IR (KBr, cm<sup>-1</sup>): 3401(m), 3060(m), 2944(m), 1615(s), 1586(s), 1555(s), 1489(s), 1463(s), 1435(s), 1385(s), 1339(w), 1309(s), 1294(m), 1279(m), 1258(m), 1228(s), 1183(s), 1166(w), 1150(w), 1111(w), 1095(m), 1076(w), 1046(w), 960(m), 877(w), 858(w), 825(m), 781(w), 751(m), 738(s), 662(w), 642(m), 618(w), 591(w), 578(w), 554(w), 515(m), 444(w).

**Physical Measurements.** Elemental analyses for C, H, and N were performed with a VarioEL element analyzer. The IR measurements were recorded on a Vertex 70 Fourier transform infrared spectrophotometer using the reflectance technique (4000–300 cm<sup>-1</sup>); the samples were prepared as KBr disks. Magnetic measurements were performed from 2 to 300 K, using a Quantum Design MPMS XL-7


SQUID magnetometer equipped with a 7 T magnet. The diamagnetic corrections for the compounds were estimated using Pascal's constants, and magnetic data were corrected for the diamagnetic contribution of the sample holder. For magnetization experiments, the temperature was set from 2.0 to 5.0 K and the field was varied from 0 to 7 T. Alternating-current (ac) susceptibility measurements were taken of powdered **1–3** to determine the in-phase and out-of-phase components of the magnetic susceptibility. The data were collected by decreasing the temperature from 30.0 to 2.0 K, with no applied external direct-current (dc) field and a drive frequency of 3.0 Oe, with frequencies between 1 and 1000 Hz.

**X-ray Crystal Structure Determinations.** Suitable single crystals with dimensions of 0.32 × 0.28 × 0.25, 0.25 × 0.21 × 0.19, and 0.23 × 0.21 × 0.18 mm<sup>3</sup> for **1–3** were selected for single-crystal X-ray diffraction analysis. Crystallographic data were collected at a temperature of 191 K for **1–3** on a Bruker Apex II CCD diffractometer with graphite-monochromated Mo Kα radiation (λ = 0.710 73 Å). Data processing was accomplished with the SAINT processing program. The structure was solved by direct methods and refined on F<sup>2</sup> by full-matrix least squares using SHELXTL97.<sup>27</sup> The locations of the heaviest atoms (Ni and rare-earth) were easily determined, and the O, N, and C atoms were subsequently determined from the difference Fourier maps. The non-H atoms were refined anisotropically. The H atoms were introduced in calculated positions and refined with fixed geometry with respect to their carrier atoms.

Selected bond lengths and angles of **13** are summarized in Table S1 in the Supporting Information. CCDC numbers 842927 (**1**), 842928 (**2**), and 842929 (**3**) contain the supplementary crystallographic data for this paper. These data can be obtained free of charge from the Cambridge Crystallographic Data Center via [www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif).

## RESULTS AND DISCUSSION

The reaction of rare-earth nitrate salts and nickel acetate with H<sub>2</sub>L in a mixture of ethanol and dichloromethane in a 1:1 molar ratio, in the presence of triethylamine, leads to the formation of hexanuclear heterometallic Ni<sub>4</sub>M<sub>2</sub> clusters, namely, [Ni<sub>4</sub>M<sub>2</sub>(μ<sub>3</sub>-OH)<sub>2</sub>(L)<sub>4</sub>(OAc)<sub>2</sub>(NO<sub>3</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>2</sub>]·kC<sub>2</sub>H<sub>5</sub>OH·mCH<sub>3</sub>OH·nH<sub>2</sub>O [M = Gd<sup>III</sup> with k = 5 and n = 1 (**1**), Dy<sup>III</sup> with k = 4 and n = 2 (**2**), and Y<sup>III</sup> with k = 5 and m = 1 (**3**)]. Compounds **13** have analogous molecular structures of clusters, differing in the number and variety of solvent molecules of crystallization; therefore, a full description of the structure of **2** is described here as representative for the whole series. Compounds **1** and **2** crystallize in the monoclinic space group C2/c, and the molecular structure of **2** is shown in Figure 1, while that of **3** is found to crystallize in the triclinic space group P $\bar{1}$  (Table 1). Selected bond lengths and angles of **13** are summarized in Table S1 in the Supporting Information. The complex core can be described as two Ni<sub>2</sub>DyO<sub>4</sub> defective cubane subunits held together by two hydroxyl groups, two acetate anions, and the O atoms from two deprotonated 3.2211 and two deprotonated 4.3211 coordination-mode<sup>28</sup> ligands. Peripheral ligations are provided by two nitrate anions and two coordinated water molecules. Each Ni<sub>2</sub>DyO<sub>4</sub> subunit comprises two Ni ions and one Dy ion arranged as a defective cubane with one missing vertex, in which the three metallic ions are connected to each other by means of three phenoxo groups and one hydroxyl group. In addition, it is worth noting that the phenoxo groups adopt two types of coordination modes connecting the metallic ions. Two of three phenoxo groups adopt a doubly bridged mode, and each connects one Ni ion and one Dy ion, whereas the remaining one adopts a triply bridged mode binding three Ni ions, among which one Ni ion stems from the adjacent

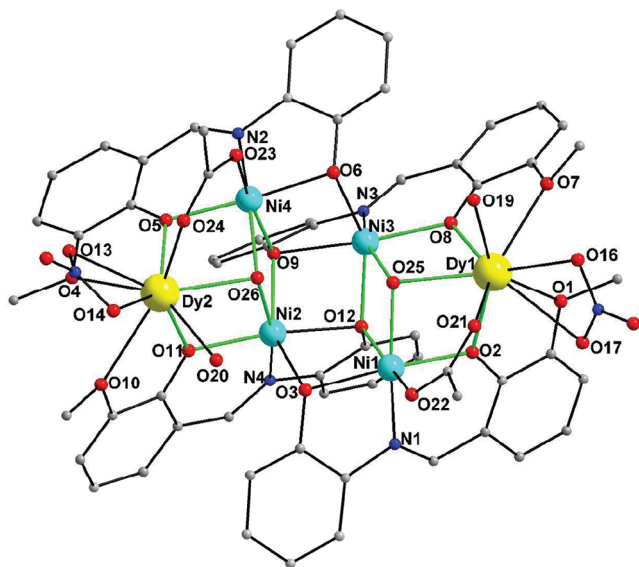

**Figure 1.** Molecular structure of **2** highlighting the  $[\text{Ni}_2\text{DyO}_4]$  heterometallic defective cubane subunits in bright-green lines. The noncoordinated solvent molecules and H atoms are omitted for clarity.

cubane subunit. Meanwhile, the hydroxyl group just adopts a triply bridged mode linking two Ni ions and one Dy ion.

All four Ni ions are six-coordinated with the  $\text{NO}_3$  environment, and the coordination polyhedron can be viewed as distorted octahedral geometry. The equatorial positions of Ni1 and Ni4 are occupied by  $\text{NO}_3$  donor atoms from one 3.2211<sup>28</sup> coordination-mode ligand and one  $\mu_3$ -hydroxyl group, as well as two O atoms from one 4.3211<sup>28</sup> coordination-mode ligand and one acetate anion in the axial positions. Furthermore, the acetate anion binds Ni and Dy ions in a


2.11<sup>28</sup> coordination fashion. The equatorial planes of Ni2 and Ni3 are also composed of  $\text{NO}_3$  atoms from one 4.3211<sup>28</sup> ligand and one  $\mu_3$ -hydroxyl group, and the axial positions are occupied by two O atoms arising from two 3.2211<sup>28</sup> ligands. The Ni–O and Ni–N bond lengths cover ranges 1.998(7)–2.235(6) and 2.000(9)–2.049(9) Å, respectively. All of the Ni ion pairs are connected through either phenoxo or hydroxyl groups, forming five edge-sharing  $\text{Ni}_2\text{O}_2$  planes. Similar tetranuclear nickel topology can be found in other nickel complexes.<sup>29</sup> The values of Ni···Ni separation are in the range 3.0434(18)–5.1628(17) Å. The Ni–O–Ni angles range from 89.1(2) to 105.2(3)°. Dy1 and Dy2 ions have the same nine-coordinated environment, bound by one 3.2211 and one 4.3211 coordination-mode<sup>28</sup> ligand, one coordinated water molecule, one nitrate anion and one acetate anion, as well as one  $\mu_3$ -hydroxyl group. The Dy–O bond lengths fall in the range of 2.237(7)–2.735(8) Å. Each Dy ion is linked through phenoxo groups and the hydroxyl group toward the central two Ni ions, resulting in a  $\text{Ni}_2\text{DyO}_4$  defective cubane; these are further bridged by phenoxo groups to adjacent cubane, thus affording a  $\text{Ni}_4\text{Dy}_2\text{O}_{10}$  core with two edge-to-edge  $\text{Ni}_2\text{DyO}_4$  defective cubanes. The Ni···Dy distances range from 3.3104(15) to 5.9855(13) Å.

**Magnetic Properties.** The temperature dependence of the direct-current (dc) magnetic susceptibilities of compounds **1–3** under a constant magnetic field of 1000 Oe was measured in the 2–300 K temperature range. The results are represented in Figure 2 as a  $\chi_M T$  versus  $T$  curve ( $\chi_M$  being the molar magnetic susceptibility per  $\text{Ni}^{\text{II}}_4\text{M}^{\text{III}}_2$  heterohexanuclear unit). The curves reveal a similar behavior for **1–3**. At room temperature, the product of  $\chi_M T$  for **3** is  $5.25 \text{ cm}^3 \text{ K mol}^{-1}$ , which is in very good agreement with the presence of four independent  $S = 1$   $\text{Ni}^{\text{II}}$  ions ( $S = 1$ ,  $C = 1.32 \text{ cm}^3 \text{ K mol}^{-1}$  with  $g = 2.30$ ) and two diamagnetic  $\text{Y}^{\text{III}}$  ions. This value stays unchanged with

**Table 1.** Crystal Data and Structure Refinement for Compounds **1–3**

	1	2	3
empirical formula	$\text{C}_{70}\text{H}_{88}\text{N}_6\text{O}_{32}\text{Ni}_4\text{Gd}_2$	$\text{C}_{68}\text{H}_{84}\text{N}_6\text{O}_{32}\text{Ni}_4\text{Dy}_2$	$\text{C}_{71}\text{H}_{90}\text{N}_6\text{O}_{32}\text{Ni}_4\text{Y}_2$
$F_w$ ( $\text{g mol}^{-1}$ )	2074.80	2057.25	1952.15
cryst syst	monoclinic	monoclinic	triclinic
space group	$C2/c$	$C2/c$	$P\bar{1}$
cryst color	brown	brown	olive
cryst size ( $\text{mm}^3$ )	$0.32 \times 0.28 \times 0.25$	$0.25 \times 0.21 \times 0.19$	$0.23 \times 0.21 \times 0.18$
temp (K)	191(2)	191(2)	191(2)
$a$ (Å)	37.0762(19)	36.961(2)	12.8089(9)
$b$ (Å)	23.3078(13)	23.3603(15)	15.9790(11)
$c$ (Å)	22.8546(12)	22.8104(14)	21.7263(15)
$\alpha$ (deg)	90	90	69.7450(10)
$\beta$ (deg)	124.2130(10)	124.1640(10)	89.5670(10)
$\gamma$ (deg)	90	90	85.7050(10)
$V$ (Å <sup>3</sup> )	16332.4(15)	16296.3(18)	4159.4(5)
$\rho_{\text{calcd}}$ ( $\text{Mg m}^{-3}$ )	1.688	1.677	1.559
$\mu$ ( $\text{mm}^{-1}$ )	2.591	2.802	2.352
$F(000)$	8368	8272	2008
$\theta$ for data collection (deg)	1.10–26.06	1.10–25.06	1.36–24.54
collected reflns	45 017	45 137	20 332
indep reflns	16 123	14 413	13 738
$R_{\text{int}}$	0.0378	0.0949	0.0338
$R$ [ $I > 2\sigma(I)$ ]	0.0385	0.0610	0.0623
$wR$ (all data)	0.1192	0.1945	0.1988
GOF on $F^2$	1.036	0.998	1.040
largest diff peak and hole ( $\text{e Å}^{-3}$ )	−0.881 and 3.231	−1.182 and 3.365	−0.743 and 2.866



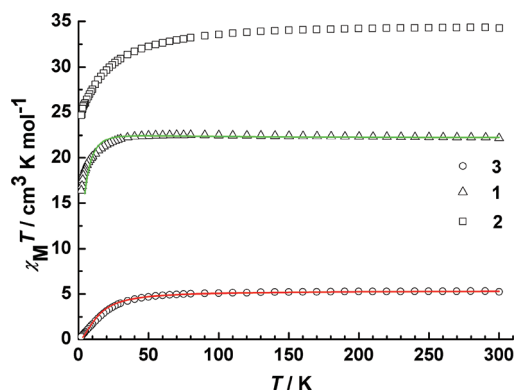


**Figure 2.** Temperature dependence of the  $\chi_M T$  products at 1000 Oe for compounds **1** (triangles), **2** (squares), and **3** (circles). The color lines correspond to the calculated behavior of compounds **1** and **3** (see the text for details).

decreases in temperature until about 50 K, where it decreases to  $0.28 \text{ cm}^3 \text{ K mol}^{-1}$  at 2 K. This indicates that the coupling within the cluster is predominantly antiferromagnetic in character. The low-temperature  $\chi_M T$  value of  $0.28 \text{ cm}^3 \text{ K mol}^{-1}$  is consistent with an  $S = 0$  ground state. We were able to successfully simulate the magnetic susceptibility data using the four- $J$  models as shown in Scheme 2 (left). Using the MAGPACK<sup>30</sup> program and employing the Hamiltonian in eq 1

$$\begin{aligned} \hat{H} = & -2J_1(\hat{S}_1 \cdot \hat{S}_2 + \hat{S}_3 \cdot \hat{S}_4) - 2J_2(\hat{S}_1 \cdot \hat{S}_3 + \hat{S}_2 \cdot \hat{S}_4) \\ & - 2J_3(\hat{S}_2 \cdot \hat{S}_3) - 2J_4(\hat{S}_1 \cdot \hat{S}_4) \end{aligned} \quad (1)$$

afforded the parameters  $J_1 = 1.4 \text{ cm}^{-1}$ ,  $J_2 = -4.4 \text{ cm}^{-1}$ ,  $J_3 = 1.5 \text{ cm}^{-1}$ ,  $J_4 = -0.45 \text{ cm}^{-1}$ , and  $g = 2.32$ . Obviously, the value of  $J_1$  is almost equal to that of  $J_3$ . Alternatively, adopting three- $J$  models can also work well in this simulation procedure. Previous literature reported that Ni–O–Ni angles between any two  $\text{Ni}^{\text{II}}$  ions that are smaller than  $98^\circ$  are expected to result in ferromagnetic coupling. Angles larger than  $98^\circ$  are expected to lead to antiferromagnetic coupling between  $\text{Ni}^{\text{II}}$  ions.<sup>31</sup> In the three cases ( $J_1$ ,  $J_2$ , and  $J_3$ ), both  $J_1$  and  $J_3$  correspond to the bridging angles smaller than  $98^\circ$ ; thus, their values are positive. Moreover,  $J_2$  corresponds to the bridging angles larger than  $98^\circ$ ,

and its value is negative. Obviously, our results are in very good agreement with the literature report. The antiferromagnetic nature of  $J_2$  may be attributed to countercomplementarity effects<sup>32</sup> between the phenoxo and hydroxyl groups. Magnetic analysis on compound **3** reveals that the exchange coupling is weak and the best fits give weakly coupled exchange couplings that are both ferro- and antiferromagnetic in nature. The magnetization of **3** at 2 K shows a roughly linearly shaped isothermal  $M$  versus  $H$  plot, reaching  $2.76 \mu_B$ , up to 7 T (Figure 3). ac susceptibility measurements performed in the 2–30 K

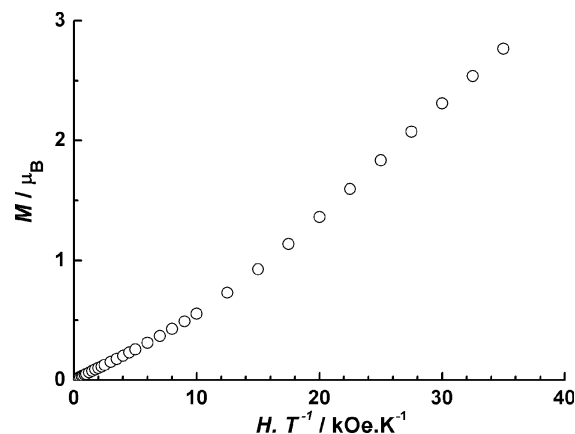


**Figure 3.** Field dependence of magnetization of compound **3** at 2 K.

range in a zero applied dc field and a 3 Oe ac field oscillating at 997 Hz show the complete absence of an out-of-phase component above 2 K (Figure S1 in the Supporting Information).

The  $\chi_M T$  value of  $22.17 \text{ cm}^3 \text{ K mol}^{-1}$  at 300 K for **1** is close to the expected value of  $21.03 \text{ cm}^3 \text{ K mol}^{-1}$  for four uncoupled  $\text{Ni}^{\text{II}}$  ions ( $S = 1$ ,  $C = 1.32 \text{ cm}^3 \text{ K mol}^{-1}$  with  $g = 2.30$ ) and two uncoupled  $\text{Gd}^{\text{III}}$  ions ( $^8S_{7/2}$ ,  $S = 7/2$ , and  $g = 2$ ). The  $\chi_M T$  product remains essentially constant upon lowering of the temperature until 15 K and below, at which it decreases, reaching a value of  $16.40 \text{ cm}^3 \text{ K mol}^{-1}$  at 2 K. The decrease of  $\chi_M T$  at low temperature obviously indicates the presence of dominantly intramolecular antiferromagnetic interaction within the molecule. To describe this behavior, fitting the experimental

**Scheme 2.** Magnetic Exchange Interactions Four- $J$  and Five- $J$  Models Employed To Simulate the Susceptibilities of Compounds **3** (Left) and **1** (Right)

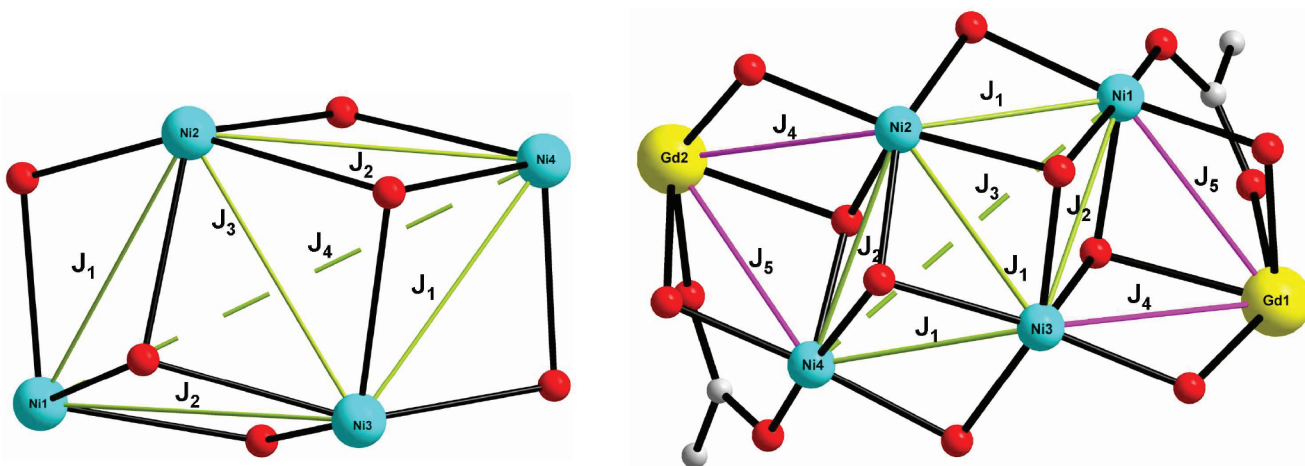

data was attempted by employing the MAGPACK<sup>30</sup> program with the Hamiltonian in eq 2. Five-*J* models were employed in order to avoid overparameterization in the simulation procedure, taking the simulation result of compound 3 and the exchange interactions between Ni2...Gd1 and Ni3...Gd2 as negligible into account.

$$\begin{aligned} \hat{H} = & -2J_1(\hat{S}_1 \cdot \hat{S}_2 + \hat{S}_3 \cdot \hat{S}_4) - 2J_2(\hat{S}_1 \cdot \hat{S}_3 + \hat{S}_2 \cdot \hat{S}_4) \\ & - 2J_1(\hat{S}_2 \cdot \hat{S}_3) - 2J_3(\hat{S}_1 \cdot \hat{S}_4) - 2J_4(\hat{S}_2 \cdot \hat{S}_{\text{Gd2}}) \\ & + \hat{S}_3 \cdot \hat{S}_{\text{Gd1}} - 2J_5(\hat{S}_1 \cdot \hat{S}_{\text{Gd1}} + \hat{S}_4 \cdot \hat{S}_{\text{Gd2}}) \end{aligned} \quad (2)$$

The calculation yielded the fit parameters  $J_1 = 1.6 \text{ cm}^{-1}$ ,  $J_2 = -4.0 \text{ cm}^{-1}$ ,  $J_3 = -0.30 \text{ cm}^{-1}$ ,  $J_4 = 0.78 \text{ cm}^{-1}$ ,  $J_5 = -0.31 \text{ cm}^{-1}$ , and  $g = 2.12$ . The results indicate that both ferro- and antiferromagnetic interactions coexist between Ni and Gd ions. In the two cases ( $J_4$  and  $J_5$ ),  $J_5$  between Ni1...Gd1 and Ni4...Gd2 is triply mediated by one phenoxo group and one hydroxyl group as well as one acetate anion, whereas  $J_4$  between Ni3...Gd1 and Ni2...Gd2 is doubly mediated by one phenoxo group and one hydroxyl group. The antiferromagnetic nature of  $J_5$  may be mainly attributed to the acetate anion.<sup>33</sup>

The magnetization of 1 has also been performed at 2 K (Figure 4). The magnetization at 2 K shows an increase at low

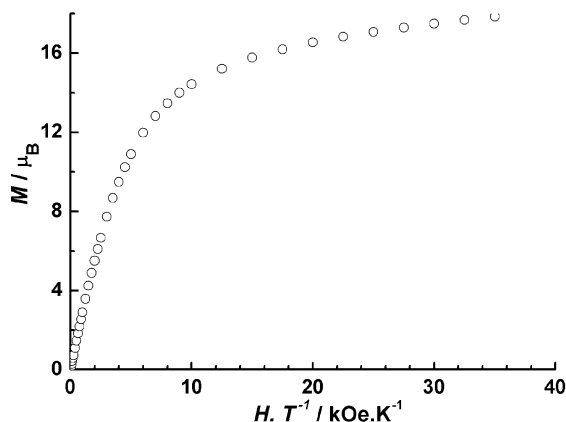


Figure 4. Field dependence of magnetization of compound 1 at 2 K.

field followed by an almost linear increase without clear saturation even at 7 T, in which it reaches  $17.85 \mu_B$ . This value is lower than expected ( $22 \mu_B$ ) for two  $\text{Gd}^{\text{III}}$  ( $S = 7/2$ ) ions and four  $S = 1$   $\text{Ni}^{\text{II}}$  ions, which are uncoupled, consistent with the presence of important antiferromagnetic interactions. ac susceptibility measurements performed in the 2–30 K range in a zero applied dc field and a 3 Oe ac field oscillating at 997 Hz show the complete absence of an out-of-phase component above 2 K (Figure S2 in the Supporting Information), which is to be expected because of the isotropic nature of the Gd ion. Extrapolation of the  $\chi'_M T$  plot to 0 K gives a value of  $20.3 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$ , suggesting a possible spin ground state of  $S = 6$  (Figure S3 in the Supporting Information).<sup>34</sup>

At 300 K, the measured  $\chi_M T$  value for 2 is  $34.28 \text{ cm}^3 \text{ K mol}^{-1}$ , which is in agreement with the calculated value of  $33.62 \text{ cm}^3 \text{ K mol}^{-1}$  for four  $\text{Ni}^{\text{II}}$  ions ( $S = 1$ ,  $C = 1.32 \text{ cm}^3 \text{ K mol}^{-1}$  with  $g = 2.30$ ) and two magnetically independent  $\text{Dy}^{\text{III}}$  ions ( $^6\text{H}_{15/2}$ ,  $S = 5/2$ ,  $L = 5$ ,  $J = 15/2$ , and  $g = 4/3$ ). Upon cooling, the  $\chi_M T$  value decreases slowly up to 100 K, where it reaches a value of  $34.02 \text{ cm}^3 \text{ K mol}^{-1}$ , and then decreases rapidly down to 2 K, reaching a minimum value of  $24.69 \text{ cm}^3 \text{ K mol}^{-1}$ . The

decrease of  $\chi_M T$  is most likely due to the combination of the thermal depopulation of the Dy ion excited states (Stark sublevels of the  $^6\text{H}_{15/2}$  state) and the possible antiferromagnetic interactions between metal centers. The field dependence of magnetization of 2 was collected at low temperatures, as shown in Figure 5. The curves are not all superimposed on a single

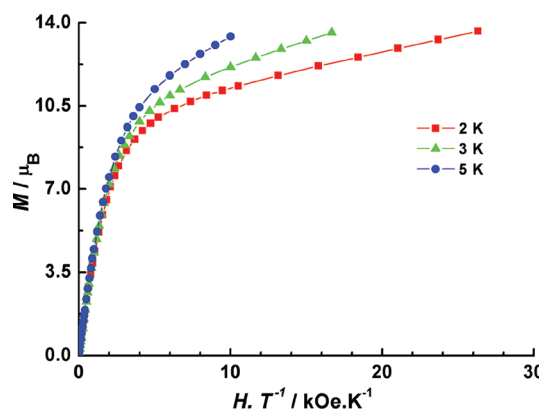


Figure 5. Plot of  $M$  versus  $H/T$  for 2 in the temperature range below 5 K.

master curve, implying the presence of significant magnetic anisotropy and/or low-lying excited states. The magnetization eventually reaches the value of  $13.65 \mu_B$  for 2 at 2 K and 50 kOe without clear saturation.

The dynamic magnetic properties of compound 2 were further probed by alternating-current (ac) measurements. ac magnetic susceptibility studies were performed on 2 in the 2–8 K temperature range in a zero applied dc field and a 3 Oe ac field oscillating at frequencies in the 1–1200 Hz range (Figure 6). 2 exhibited a frequency-dependent out-of-phase ( $\chi''$ ) signal

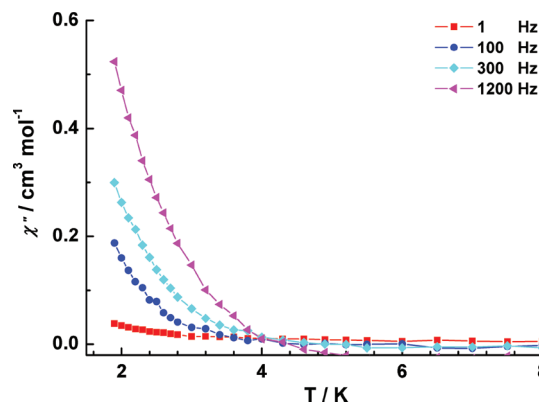


Figure 6. Temperature dependences of out-of-phase ( $\chi''$ ) ac susceptibilities of 2 at different frequencies in a zero dc field and a 3 Oe ac field.

below 4 K, but no peaks were found at frequencies lower than 1200 Hz until 1.9 K. Obviously, the slow relaxation of magnetization is evident from ac susceptibility data of 2. Because no out-of-phase signals were observed for compounds 1 and 3, we can conclude that the magnetic slow relaxation behavior of compound 2 arises largely from the presence of the anisotropic Dy ion. It is worth mentioning that the dynamic magnetic behavior of 2 is quite different from that of recently reported defective dicubane  $\text{Ni}_2\text{Dy}_2$  compounds. Indeed, the

Ni<sub>2</sub>Dy<sub>2</sub> compounds are ferromagnetically coupled and are found to be SMMs, while compound **2** shows only a slow magnetic relaxation of magnetization. The strictly planar butterfly core with two Ni<sup>II</sup> ions in the body positions and each Dy<sup>III</sup> ion in the wing positions of the Ni<sub>2</sub>Dy<sub>2</sub> compounds can be described as the fusion of two Ni<sub>2</sub>Dy triangles with shared edges through Ni1 and NiA atoms. However, the dihedral angle between the two separate Ni<sub>2</sub>Dy triangles in compound **2** is 68.033°. As observed in compounds **1** and **3**, the presence of additional Ni...Ni edges in **2** compared to the Ni<sub>2</sub>Dy<sub>2</sub> compounds might introduce significant antiferromagnetic interactions within the molecules. It is well-known that the magnetic anisotropy of an exchange-coupled system depends not only on the individual anisotropies of the metal ions but also on the relative orientation of the local axes. The distinct anisotropy of the Dy<sup>III</sup> ions determined by the different coordination environments (eight-coordinated in Ni<sub>2</sub>Dy<sub>2</sub> compounds and nine-coordinated in **2**) and ligand fields around the Dy<sup>III</sup> ion and/or the different relative orientation of the local axes within **2** and Ni<sub>2</sub>Dy<sub>2</sub> is mostly responsible for the distinctive relaxation dynamics observed.<sup>16d,35</sup>

## CONCLUSION

We have reported the syntheses, crystal structures, and magnetic analyses of a new family of heterometallic hexanuclear Ni<sub>4</sub>M<sub>2</sub> clusters. The metal core of each cluster is composed of two Ni<sub>2</sub>MO<sub>4</sub> defective cubanes. Compound **1** (M = Gd) displays a combination of antiferro- and ferromagnetic coupling pathways, with no SMM features. On the other hand, the incorporation of an anisotropic ion such as Dy in compound **2** led to the observation of slow magnetic relaxation, as demonstrated by a frequency-dependent out-of-phase ac signal. Magnetic analysis on compound **3** indicates Ni...Ni antiferromagnetic exchange interactions competing with ferromagnetic exchange interactions, which is mainly affected by the Ni–O–Ni bridging angles. Efforts to construct other fascinating structures by reacting the H<sub>2</sub>L ligand with other rare-earth(III) salts as well as other transition-metal salts are continuing in our laboratory.

## ASSOCIATED CONTENT

### Supporting Information

Selected bond lengths and angles for compounds **1**–**3** (Table S1) and additional magnetic data for **1** and **3** (Figures S1–S3). This material is available free of charge via the Internet at <http://pubs.acs.org>.

## AUTHOR INFORMATION

### Corresponding Author

\*E-mail: [tang@ciac.jl.cn](mailto:tang@ciac.jl.cn).

### Notes

The authors declare no competing financial interest.

## ACKNOWLEDGMENTS

This work was supported by the National Natural Science Foundation of China (Grants 20871113, 91022009, and 20921002).

## REFERENCES

- (1) (a) Christou, G.; Gatteschi, D.; Hendrickson, D. N.; Sessoli, R. *MRS Bull.* **2000**, 25, 66–71. (b) Gatteschi, D.; Sessoli, R. *Angew. Chem., Int. Ed.* **2003**, 42, 268–297.
- (2) (a) Bogani, L.; Wernsdorfer, W. *Nat. Mater.* **2008**, 7, 179–186. (b) Leuenberger, M. N.; Loss, D. *Nature* **2001**, 410, 789–793.
- (3) (a) Aromi, G.; Brechin, E. K. *Struct. Bonding (Berlin)* **2006**, 122, 1–67. (b) Glaser, T. *Chem. Commun.* **2011**, 47, 116–130.
- (4) Kostakis, G. E.; Ako, A. M.; Powell, A. K. *Chem. Soc. Rev.* **2010**, 39, 2238–2271.
- (5) (a) Wernsdorfer, W.; Aliaga-Alcalde, N.; Hendrickson, D. N.; Christou, G. *Nature* **2002**, 416, 406–409. (b) Manoli, M.; Inglis, R.; Manos, M. J.; Nastopoulos, V.; Wernsdorfer, W.; Brechin, E. K.; Tasiopoulos, A. J. *Angew. Chem., Int. Ed.* **2011**, 50, 4441–4444. (c) Newton, G. N.; Yamashita, S.; Hasumi, K.; Matsuno, J.; Yoshida, N.; Nihei, M.; Shiga, T.; Nakano, M.; Nojiri, H.; Wernsdorfer, W.; Oshio, H. *Angew. Chem., Int. Ed.* **2011**, 50, 5716–5720. (d) Beedle, C. C.; Stephenson, C. J.; Heroux, K. J.; Wernsdorfer, W.; Hendrickson, D. N. *Inorg. Chem.* **2008**, 47, 10798–10800. (e) Dreiser, J.; Schnegg, A.; Holldack, K.; Pedersen, K. S.; Schau-Magnussen, M.; Nehrkorn, J.; Tregenna-Piggott, P.; Mutka, H.; Weihe, H.; Bendix, J.; Waldmann, O. *Chem.—Eur. J.* **2011**, 17, 7492–7498. (f) Tomsa, A.-R.; Martínez-Lillo, J.; Li, Y.; Chamoireau, L.-M.; Boubekeur, K.; Farias, F.; Novak, M. A.; Cremades, E.; Ruiz, E.; Proust, A.; Verdager, M.; Gouzerh, P. *Chem. Commun.* **2010**, 46, 5106–5108. (g) Stamatatos, T. C.; Foguet-Albiol, D.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *Chem. Commun.* **2011**, 47, 274–276. (h) Tasiopoulos, A. J.; Vinslava, A.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *Angew. Chem., Int. Ed.* **2004**, 43, 2117–2121. (i) Stamatatos, T. C.; Abboud, K. A.; Wernsdorfer, W.; Christou, G. *Angew. Chem., Int. Ed.* **2006**, 45, 4134–4137. (j) Ako, A. M.; Hewitt, I. J.; Mereacre, V.; Clérac, R.; Wernsdorfer, W.; Anson, C. E.; Powell, A. K. *Angew. Chem., Int. Ed.* **2006**, 45, 4926–4929. (k) Stamatatos, T. C.; Abboud, K. A.; Wernsdorfer, W.; Christou, G. *Angew. Chem., Int. Ed.* **2008**, 47, 6694–6698. (l) Heroux, K. J.; Rheingold, A. L.; Hendrickson, D. N. *Eur. J. Inorg. Chem.* **2009**, 3541–3544. (m) Li, D.; Wang, H.; Pan, S. W. Y.; Li, C.; Dou, J.; Song, Y. *Inorg. Chem.* **2011**, 49, 3688–3690. (n) Taylor, S. M.; Karotsis, G.; McIntosh, R. D.; Kennedy, S.; Teat, S. J.; Beavers, C. M.; Wernsdorfer, W.; Piligkos, S.; Dalgarno, S. J.; Brechin, E. K. *Chem.—Eur. J.* **2011**, 17, 7521–7530.
- (6) (a) Gregoli, L.; Danieli, C.; Barra, A.-L.; Neugebauer, P.; Pellegrino, G.; Poneti, G.; Sessoli, R.; Cornia, A. *Chem.—Eur. J.* **2009**, 15, 6456–6467. (b) Boudalis, A. K.; Sanakis, Y.; Clemente-Juan, J. M.; Donnadieu, B.; Nastopoulos, V.; Mari, A.; Coppel, Y.; Tuchagues, J.-P.; Perlepes, S. P. *Chem.—Eur. J.* **2008**, 14, 2514–2526. (c) Schlegel, C.; Burzuri, E.; Luis, F.; Moro, F.; Manoli, M.; Brechin, E. K.; Murrie, M.; Slagereen, J. V. *Chem.—Eur. J.* **2010**, 16, 10178–10185. (d) Zhang, Y.-Z.; Wang, B.-W.; Sato, O.; Gao, S. *Chem. Commun.* **2010**, 46, 6959–6961. (e) Cremades, E.; Ruiz, E. *Inorg. Chem.* **2011**, 50, 4016–4020. (f) Ako, A. M.; Mereacre, V.; Lan, Y.; Wernsdorfer, W.; Clérac, R.; Anson, C. E.; Powell, A. K. *Inorg. Chem.* **2010**, 49, 1–3. (g) Weismann, D.; Sun, Y.; Lan, Y.; Wolmershäuser, G.; Powell, A. K.; Sitzmann, H. *Chem.—Eur. J.* **2011**, 17, 4700–4704.
- (7) (a) Galloway, K. W.; Whyte, A. M.; Wernsdorfer, W.; Sanchez-Benitez, J.; Kamenev, K. V.; Parkin, A.; Peacock, R. D.; Murrie, M. *Inorg. Chem.* **2008**, 47, 7438–7442. (b) Murrie, M. *Chem. Soc. Rev.* **2010**, 39, 1986–1995. (c) Ibrahim, M.; Lan, Y.; Bassil, B. S.; Xiang, Y.; Suchopar, A.; Powell, A. K.; Kortz, U. *Angew. Chem., Int. Ed.* **2011**, 50, 4708–4711. (d) Ferguson, A.; Parkin, A.; Sanchez-Benitez, J.; Kamenev, K.; Wernsdorfer, W.; Murrie, M. *Chem. Commun.* **2007**, 3473–3475. (e) Wu, D.; Guo, D.; Song, Y.; Huang, W.; Duan, C.; Meng, Q.; Sato, O. *Inorg. Chem.* **2009**, 48, 854–860. (f) Moubaraki, B.; Murray, K. S.; Hudson, T. A.; Robson, R. *Eur. J. Inorg. Chem.* **2008**, 4525–4529.
- (8) Andruh, M.; Costes, J.-P.; Diaz, C.; Gao, S. *Inorg. Chem.* **2009**, 48, 3342–3359.
- (9) (a) Ferbinteanu, M.; Kajiwar, T.; Choi, K.-Y.; Nojiri, H.; Nakamoto, A.; Kojima, N.; Cimpoesu, F.; Fujimura, Y.; Takaishi, S.; Yamashita, M. *J. Am. Chem. Soc.* **2006**, 128, 9008–9009. (b) Costes, J.-P.; Dahan, F.; Wernsdorfer, W. *Inorg. Chem.* **2006**, 45, 5–7. (c) Kajiwar, T.; Nakano, M.; Takaishi, S.; Yamashita, M. *Inorg. Chem.* **2008**, 47, 8604–8606. (d) Colacio, E.; Ruiz-Sanchez, J.; White, F. J.; Brechin, E. K. *Inorg. Chem.* **2011**, 50, 7268–7273. (e) Murugesu,



- M.; Mishra, A.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *Polyhedron* **2006**, *25*, 613–625.
- (10) Baskar, V.; Gopal, K.; Helliwell, M.; Tuna, F.; Wernsdorfer, W.; Winpenny, R. E. P. *Dalton Trans.* **2010**, *39*, 4747–4750.
- (11) (a) Pointillart, F.; Bernot, K.; Sessoli, R.; Gatteschi, D. *Chem.—Eur. J.* **2007**, *13*, 1602–1609. (b) Mori, F.; Nyui, T.; Ishida, T.; Nogami, T.; Choi, K.-Y.; Nojiri, H. *J. Am. Chem. Soc.* **2006**, *128*, 1440–1441. (c) Chandrasekhar, V.; Pandian, B. M.; Azhakar, R.; Vittal, J. J.; Clérac, R. *Inorg. Chem.* **2007**, *46*, 5140–5142.
- (12) Mishra, A.; Wernsdorfer, W.; Parsons, S.; Christou, G.; Brechin, E. K. *Chem. Commun.* **2005**, 2086–2088.
- (13) (a) Efthymiou, C. G.; Stamatatos, T. C.; Papatriantafyllopoulou, C.; Tasiopoulos, A. J.; Wernsdorfer, W.; Perlepes, S. P.; Christou, G. *Inorg. Chem.* **2010**, *49*, 9737–9739. (b) Chilton, N. F.; Langley, S. K.; Moubaraki, B.; Murray, K. S. *Chem. Commun.* **2010**, *46*, 7787–7789.
- (14) Osa, S.; Kido, T.; Matsumoto, N.; Re, N.; Pochaba, A.; Mrozinski, J. *J. Am. Chem. Soc.* **2004**, *126*, 420–421.
- (15) Schray, D.; Abbas, G.; Lan, Y.; Mereacre, V.; Sundt, A.; Dreiser, J.; Waldmann, O.; Kostakis, G. E.; Anson, C. E.; Powell, A. K. *Angew. Chem., Int. Ed.* **2010**, *49*, 5185–5188.
- (16) (a) Mereacre, V.; Ako, A. M.; Clérac, R.; Wernsdorfer, W.; Hewitt, I. J.; Anson, C. E.; Powell, A. K. *Chem.—Eur. J.* **2008**, *14*, 3577–3584. (b) Shiga, T.; Onuki, T.; Matsumoto, T.; Nojiri, H.; Newton, G. N.; Hoshino, N.; Oshio, H. *Chem. Commun.* **2009**, 3568–3570. (c) Saha, A.; Thompson, M.; Abboud, K. A.; Wernsdorfer, W.; Christou, G. *Inorg. Chem.* **2011**, *50*, 10476–10485. (d) Mondal, K. C.; Kostakis, G. E.; Lan, Y.; Wernsdorfer, W.; Anson, C. E.; Powell, A. K. *Inorg. Chem.* **2011**, *50*, 11604–11611.
- (17) (a) Aronica, C.; Pilet, G.; Chastanet, G.; Wernsdorfer, W.; Jacquot, J.-F.; Luneau, D. *Angew. Chem., Int. Ed.* **2006**, *45*, 4659–4662. (b) Zeng, Y.-F.; Xu, G.-C.; Hu, X.; Chen, Z.; Bu, X.-H.; Gao, S.; Sañudo, E. C. *Inorg. Chem.* **2010**, *49*, 9734–9736.
- (18) (a) Mereacre, V. M.; Ako, A. M.; Clérac, R.; Wernsdorfer, W.; Filoti, G.; Bartolomé, J.; Anson, C. E.; Powell, A. K. *J. Am. Chem. Soc.* **2007**, *129*, 9248–9249. (b) Holyńska, M.; Premužić, D.; Jeon, I.-R.; Wernsdorfer, W.; Clérac, R.; Dehnen, S. *Chem.—Eur. J.* **2011**, *17*, 9605–9610. (c) Rigaux, G.; Inglis, R.; Morrison, S.; Prescimone, A.; Cadiou, C.; Evangelisti, M.; Brechin, E. K. *Dalton Trans.* **2011**, *40*, 4797–4799. (d) Langley, S. K.; Moubaraki, B.; Murray, K. S. *Dalton Trans.* **2010**, *39*, 5066–5069.
- (19) Novitchi, G.; Wernsdorfer, W.; Chibotaru, L. F.; Costes, J.-P.; Anson, C. E.; Powell, A. K. *Angew. Chem., Int. Ed.* **2009**, *48*, 1614–1619.
- (20) (a) Mishra, A.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *J. Am. Chem. Soc.* **2004**, *126*, 15648–15649. (b) Zaleski, C. M.; Depperman, E. C.; Kampf, J. W.; Kirk, M. L.; Pecoraro, V. L. *Angew. Chem., Int. Ed.* **2004**, *43*, 3912–3914. (c) Ako, A. M.; Mereacre, V.; Clérac, R.; Wernsdorfer, W.; Hewitt, I. J.; Anson, C. E.; Powell, A. K. *Chem. Commun.* **2009**, 544–546. (d) Liu, J.-L.; Guo, F.-S.; Meng, Z.-S.; Zheng, Y.-Z.; Leng, J.-D.; Tong, M.-L.; Ungur, L.; Chibotaru, L. F.; Heroux, K. J.; Hendrickson, D. N. *Chem. Sci.* **2011**, *2*, 1268–1272. (e) Papatriantafyllopoulou, C.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *Inorg. Chem.* **2011**, *50*, 421–423. (f) Zou, L.-F.; Zhao, L.; Guo, Y.-N.; Yu, G.-M.; Guo, Y.; Tang, J.; Li, Y.-H. *Chem. Commun.* **2011**, *47*, 8659–8661.
- (21) (a) Pasatou, T. D.; Etienne, M.; Madalan, A. M.; Andruh, M.; Sessoli, R. *Dalton Trans.* **2010**, *39*, 4802–4808. (b) Gao, Y.; Zhao, L.; Xu, X.; Xu, G.-F.; Guo, Y.-N.; Tang, J.; Liu, Z. *Inorg. Chem.* **2011**, *50*, 1304–1308.
- (22) (a) Iasco, O.; Novitchi, G.; Jeanneau, E.; Wernsdorfer, W.; Luneau, D. *Inorg. Chem.* **2011**, *50*, 7373–7375. (b) Langley, S. K.; Ungur, L.; Chilton, N. F.; Moubaraki, B.; Chibotaru, L. F.; Murray, K. S. *Chem.—Eur. J.* **2011**, *17*, 9209–9218. (c) Costes, J.-P.; Shova, S.; Wernsdorfer, W. *Dalton Trans.* **2008**, 1843–1849.
- (23) Sessoli, R.; Powell, A. K. *Coord. Chem. Rev.* **2009**, *253*, 2328–2341.
- (24) Singh, S. K.; Tibrewal, N. K.; Rajaraman, G. *Dalton Trans.* **2011**, *40*, 10897–10906.
- (25) (a) Dong, J.-F.; Li, L.-Z.; Ji, Z.-Z.; Cui, H.; Wang, D.-Q. *Acta Crystallogr., Sect. E* **2007**, *E63*, m1578. (b) Kannappan, R.; Tooke, D. M.; Spek, A. L.; Reedijk, J. *Inorg. Chim. Acta* **2006**, *359*, 334–338. (c) Bolzati, C.; Porchia, M.; Bandoli, G.; Boschi, A.; Malag, E.; Uccelli, L. *Inorg. Chim. Acta* **2001**, *315*, 205–212.
- (26) Pettinari, C.; Marchetti, F.; Pettinari, R.; Martini, D.; Drozdov, A.; Troyanov, S. *Inorg. Chim. Acta* **2001**, *325*, 103–114.
- (27) Sheldrick, G. M. *Acta Crystallogr., Sect. A* **2008**, *64*, 112–122.
- (28) Coxall, R. A.; Harris, S. G.; Henderson, D. K.; Parsons, S.; Tasker, P. A.; Winpenny, R. E. P. *J. Chem. Soc., Dalton Trans.* **2000**, 2349.
- (29) (a) Katsenis, A. D.; Kessler, V. G.; Papaefstathiou, G. S. *Dalton Trans.* **2011**, *40*, 4590–4598. (b) Lin, S.-Y.; Xu, G.-F.; Zhao, L.; Guo, Y.-N.; Tang, J.; Wang, Q.-L.; Liu, G.-X. *Inorg. Chim. Acta* **2011**, *373*, 173–178. (c) Serna, Z.; Pinta, N. D. L.; Urriaga, M. K.; Lezama, L.; Madariaga, G.; Clemente-Juan, J. M.; Coronado, E.; Cortés, R. *Inorg. Chem.* **2010**, *49*, 11541–11549. (d) Zhang, S.-H.; Li, N.; Ge, C.-M.; Feng, C.; Ma, L.-F. *Dalton Trans.* **2011**, *40*, 3000–3007.
- (30) Borrás-Almenar, J. J.; Clemente-Juan, J. M.; Coronado, E.; Tsukerblat, B. S. *Inorg. Chem.* **1999**, *38*, 6081–6089.
- (31) Feltham, H. L. C.; Clérac, R.; Brooker, S. *Dalton Trans.* **2009**, 2965–2973.
- (32) Peristeraki, T.; Samios, M.; Siczek, M.; Lis, T.; Milios, C. J. *Inorg. Chem.* **2011**, *50*, 5175–5185.
- (33) Fondo, M.; Ocampo, N.; García-Deibe, A. M.; Cano, J.; Sanmartín, J. *Dalton Trans.* **2010**, *39*, 10888–10899.
- (34) (a) Saha, A.; Thompson, M.; Abboud, K. A.; Wernsdorfer, W.; Christou, G. *Inorg. Chem.* **2011**, *50*, 10476–10485. (b) Chakov, N. E.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *Inorg. Chem.* **2004**, *43*, 5919–5930. (c) Manoli, M.; Prescimone, A.; Bagai, R.; Mishra, A.; Murugesu, M.; Parsons, S.; Wernsdorfer, W.; Christou, G.; Brechin, E. K. *Inorg. Chem.* **2007**, *46*, 6968–6979.
- (35) Mereacre, V.; Baniodeh, A.; Anson, C. E.; Powell, A. K. *J. Am. Chem. Soc.* **2011**, *133*, 15335–15337.