



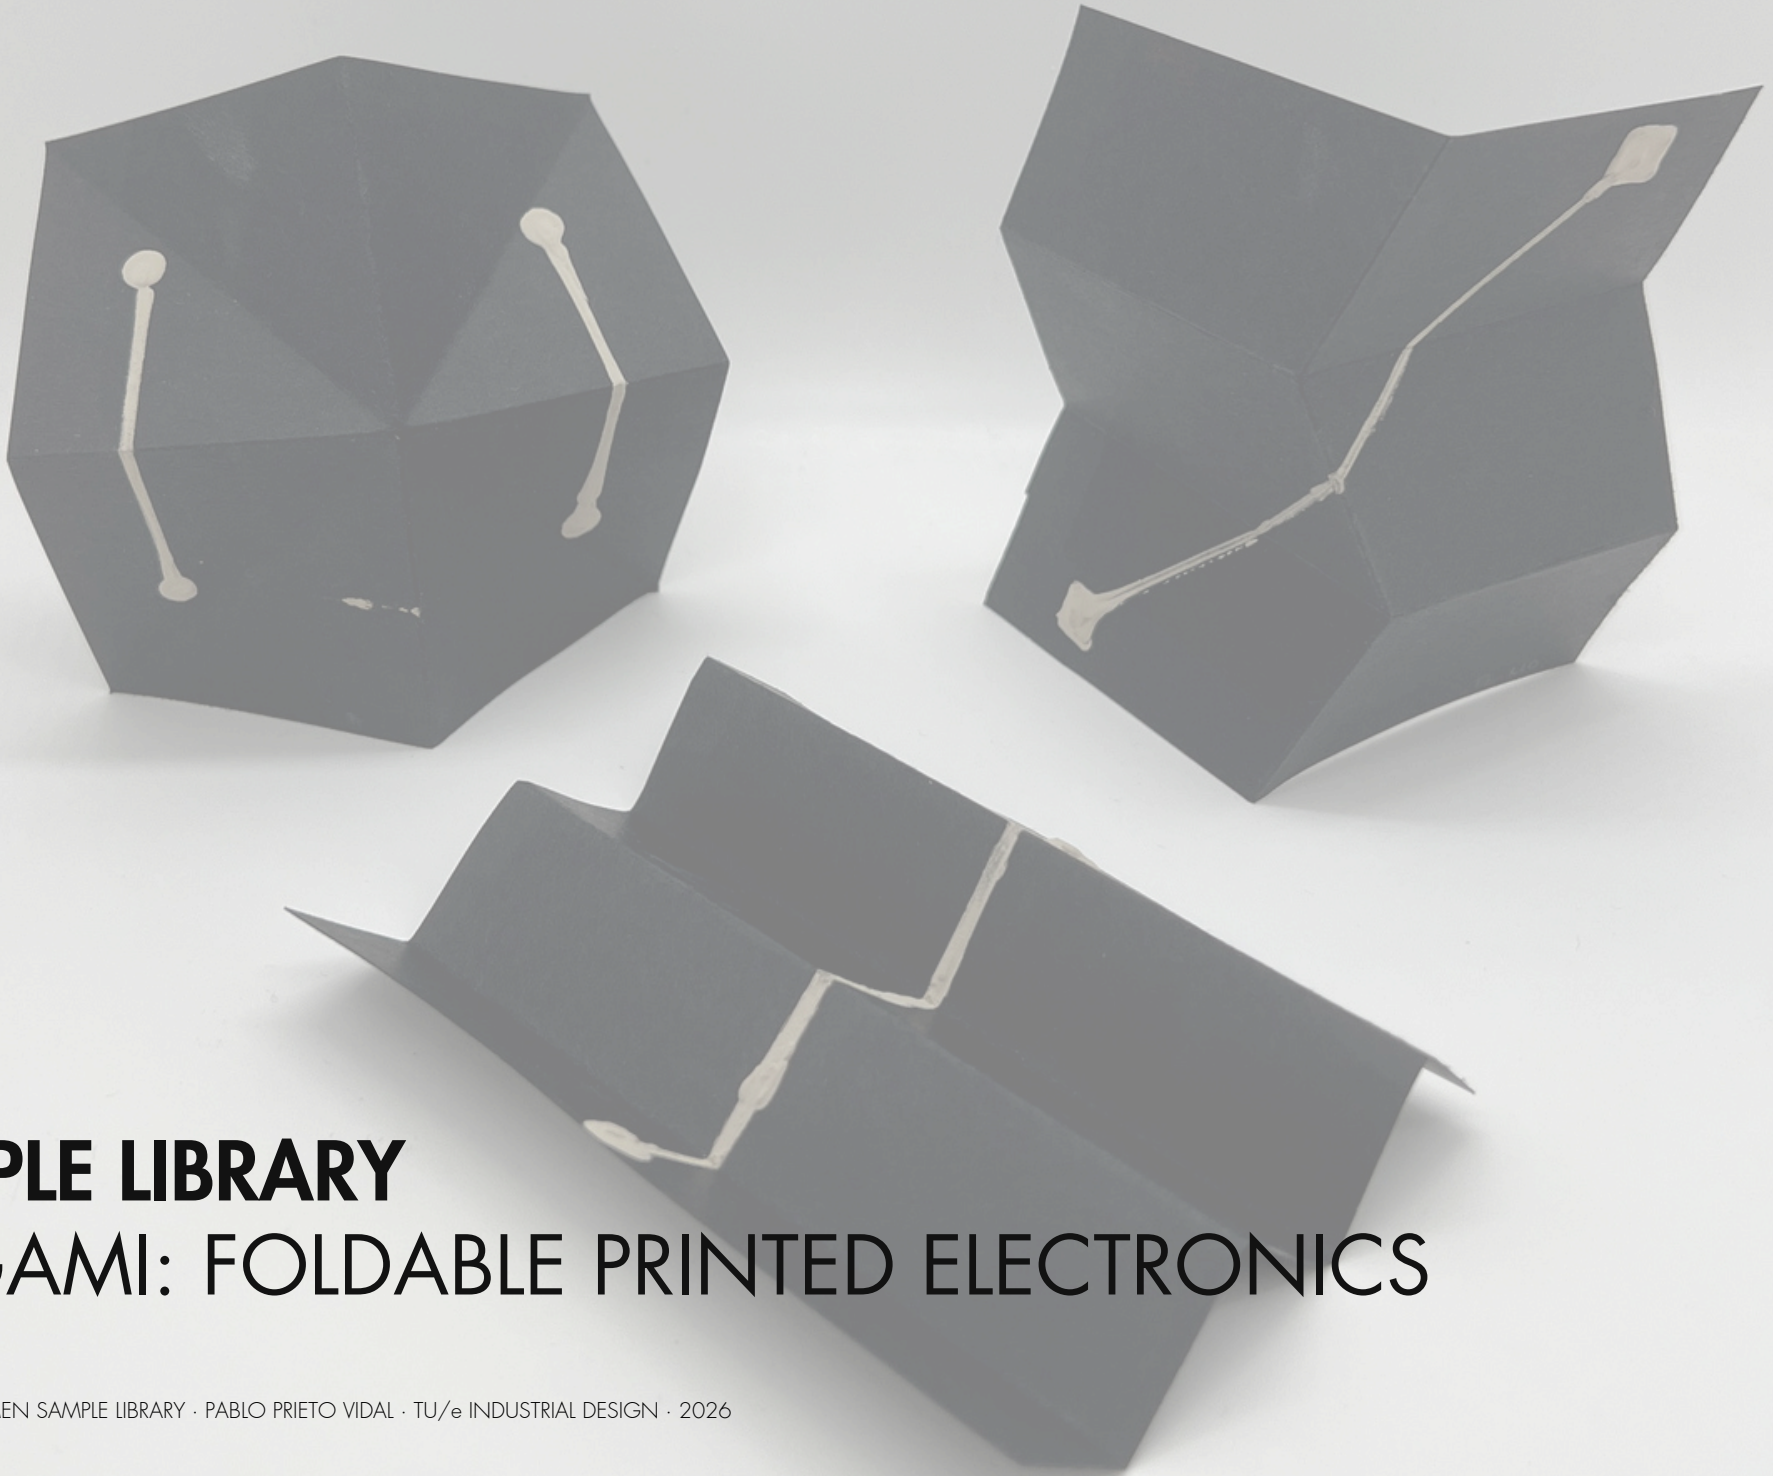

SAMPLE LIBRARY

E-RIGAMI: FOLDABLE PRINTED ELECTRONICS

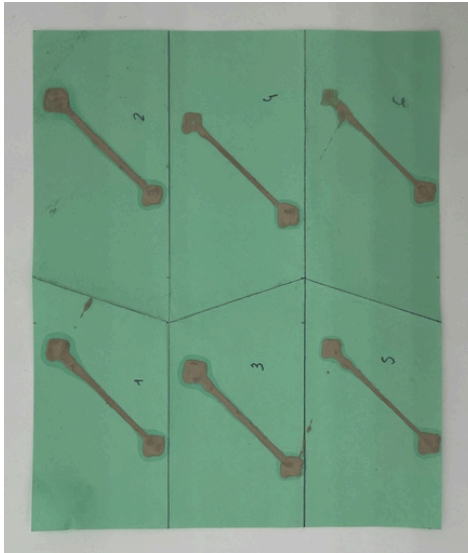

SAMPLE PHOTO

MO_45_UNCUT

Miura-Ori Sample

ATTRIBUTES



	45° Diagonal		80g/m ² Cellulose
	Face		Miura-Ori


ELECTROMECHANICAL DATA

R_0 flat (Ω)	6,38
$\Delta R/R_0$ @100c	0,050
Fold cycles	>100

EXCELLENT

DETAIL PHOTOS

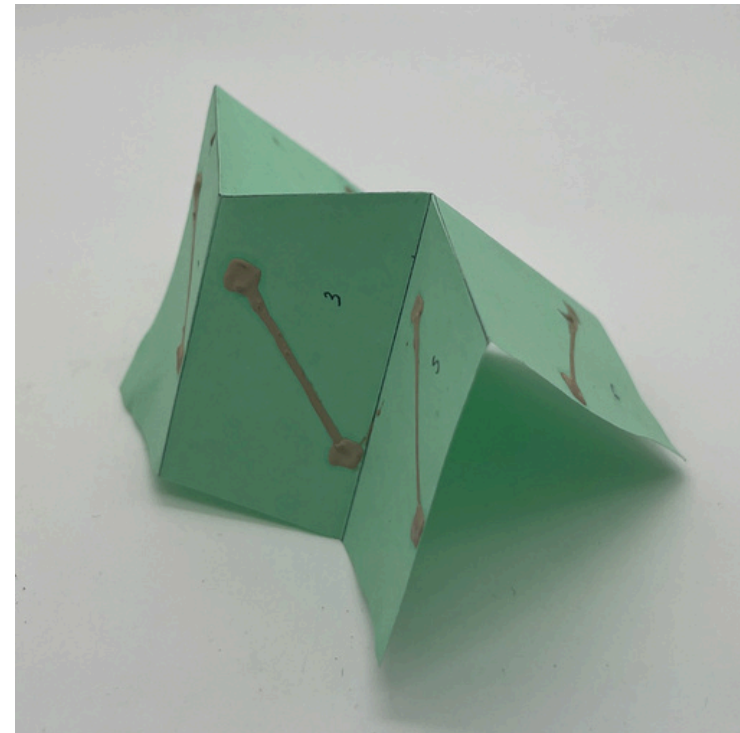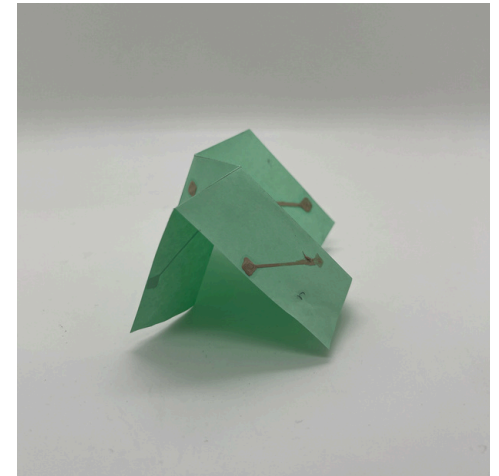

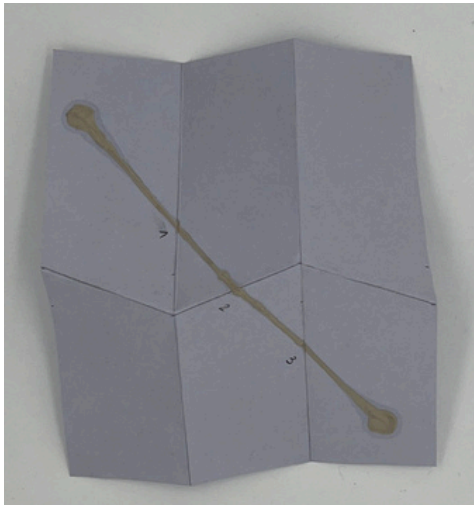

SAMPLE PHOTO

MO_45_CUT

Miura-Ori Sample

ATTRIBUTES

80g/m²
Cellulose

ELECTROMECHANICAL DATA



R ₀ flat (Ω)	27,05
ΔR/R ₀ @100c	0,051
Fold cycles	>100


EXCELLENT

DETAIL PHOTOS



160 G/M² CELLULOSE PHOTOS

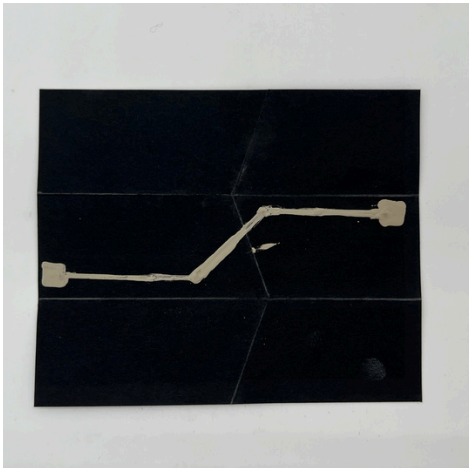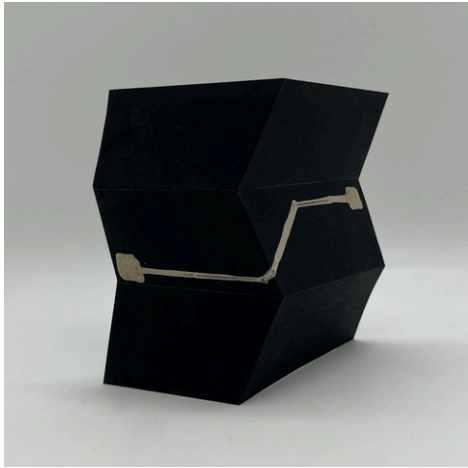

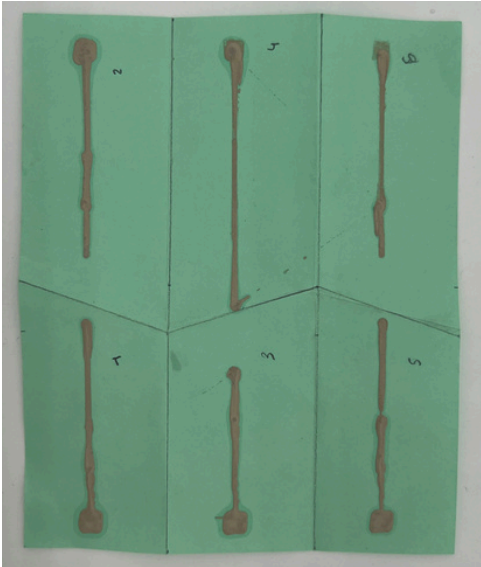

SAMPLE PHOTO

MO_0_UNCUT

Miura-Ori Sample

ATTRIBUTES



0°



80g/m²
Cellulose



Face






Miura-Ori


ELECTROMECHANICAL DATA

R ₀ flat (Ω)	6,14
ΔR/R ₀ @100c	0,824
Fold cycles	>100

MARGINAL

DETAIL PHOTOS

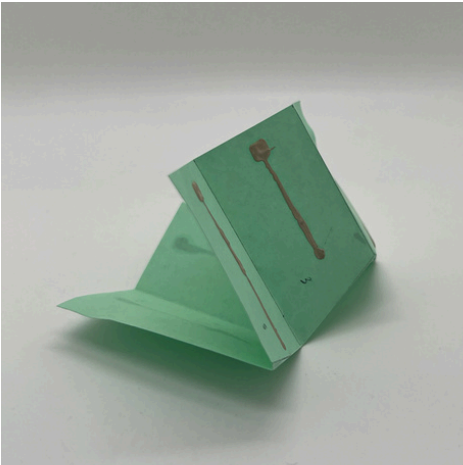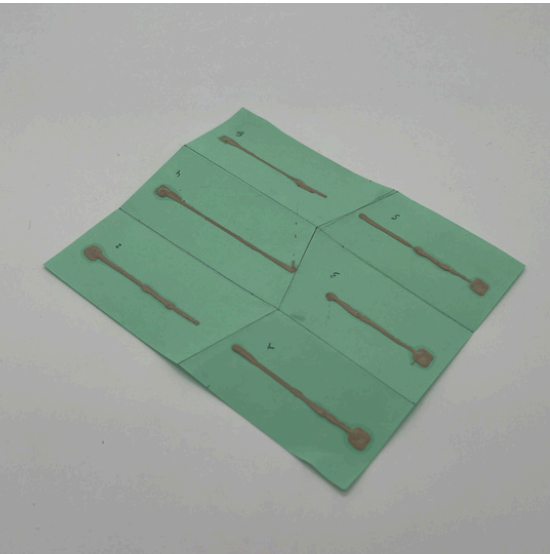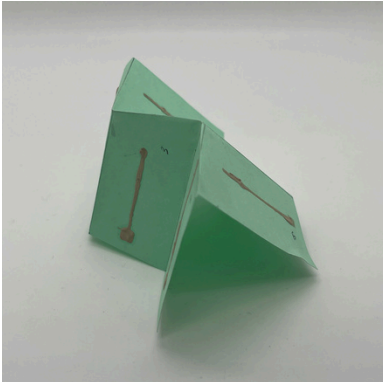

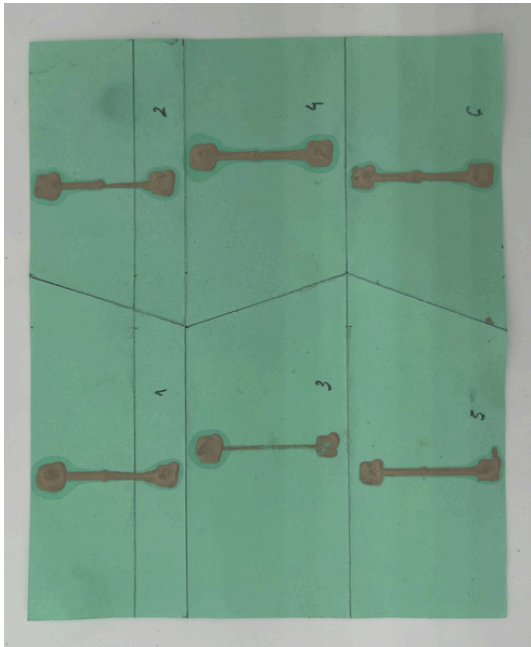

SAMPLE PHOTO

MO_90_UNCUT

Miura-Ori Sample



ATTRIBUTES


ELECTROMECHANICAL DATA

R_0 flat (Ω)	2,71
$\Delta R/R_0$ @100c	0,577
Fold cycles	>100

ACCEPTABLE

DETAIL PHOTOS

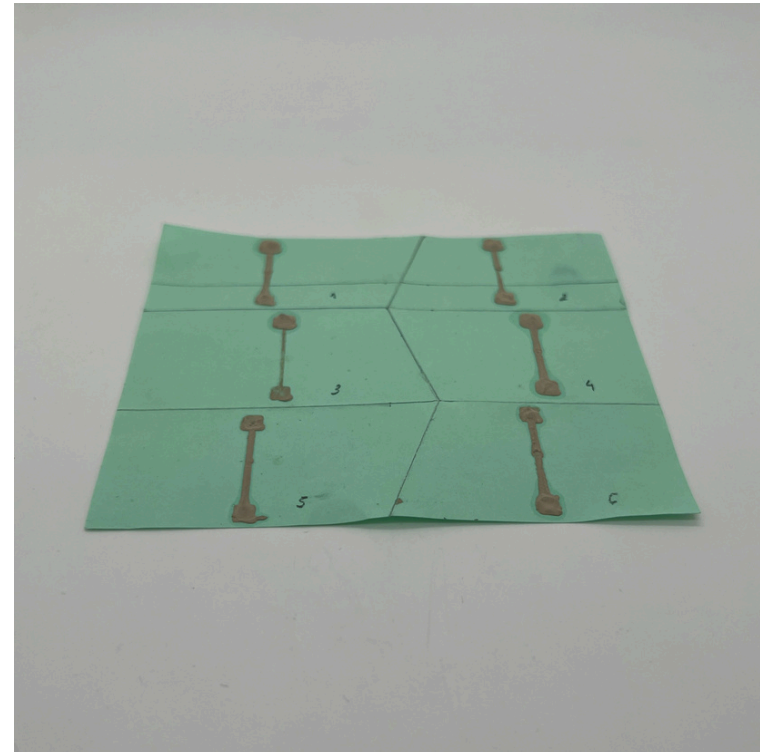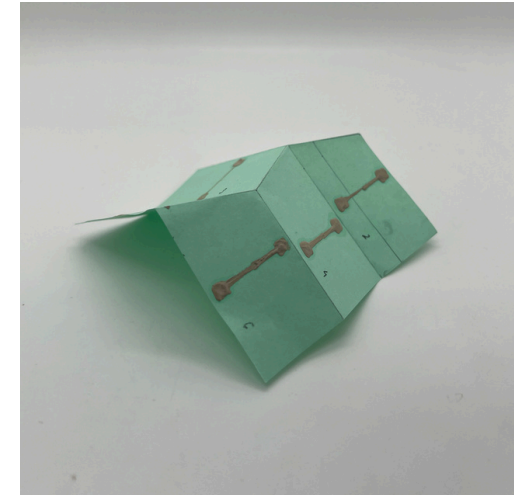

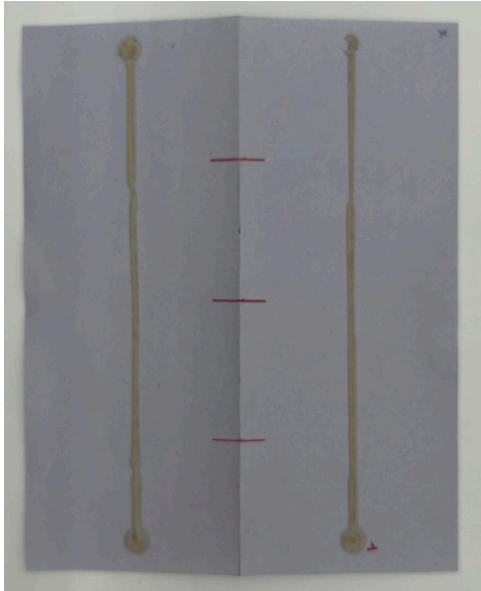

SAMPLE PHOTO

KR_0_5

Kirigami Sample

ATTRIBUTES



0° - 5mm cuts



80g/m²
Cellulose



Crease




Kirigami


ELECTROMECHANICAL DATA

R_0 flat (Ω)	73,70
$\Delta R/R_0$ @100c	0,502
Fold cycles	>100

ACCEPTABLE

DETAIL PHOTOS

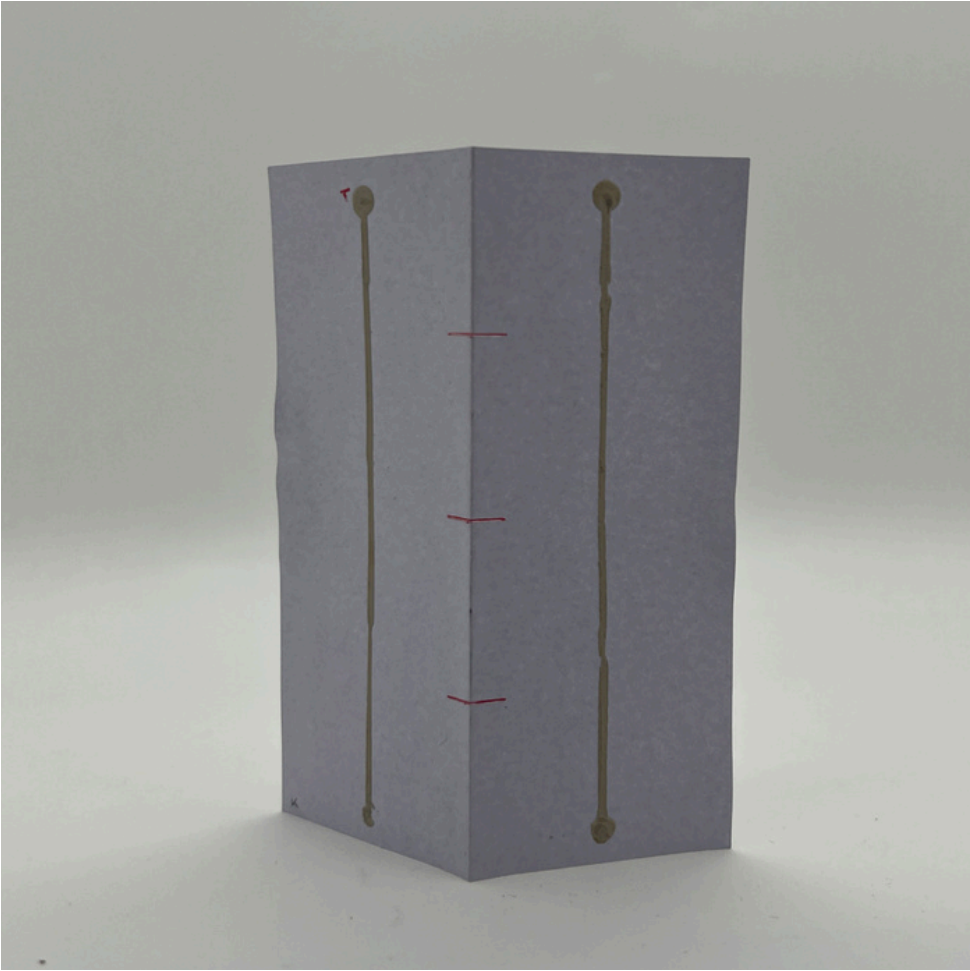

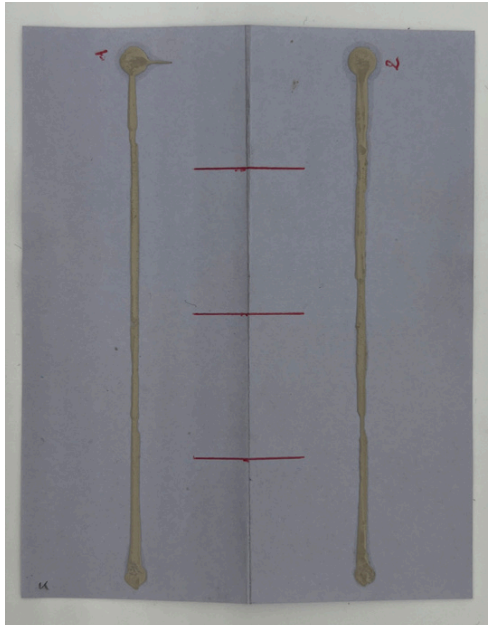

SAMPLE PHOTO

KR_0_10_L1 & L2

Kirigami Sample

ATTRIBUTES

	0° - 10mm cuts		80g/m ² Cellulose
	Crease		Kirigami

ELECTROMECHANICAL DATA


R_0 flat (Ω) 40,50 | 31,08


$\Delta R/R_0$ @100c 1,186 | 1,278

Fold cycles >100

DEGRADED

DETAIL PHOTOS

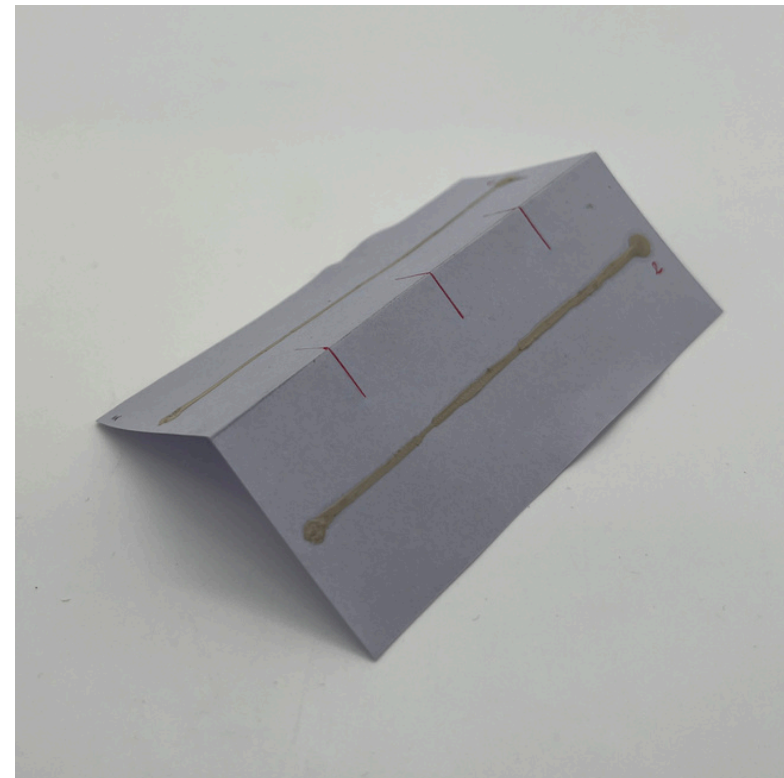

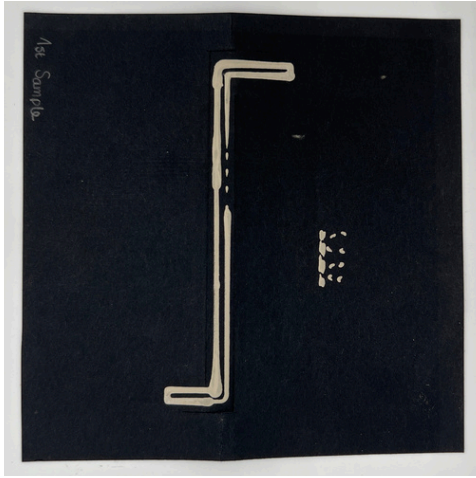

SAMPLE PHOTO

KR_TWISTING

Kirigami Sample

ATTRIBUTES

0° - 95mm cuts

160g/m²
Cellulose

Crease


Kirigami


ELECTROMECHANICAL DATA

R ₀ flat (Ω)	114,51
ΔR/R ₀ @100c	1,008
Fold cycles	>100

DEGRADED

DETAIL PHOTOS

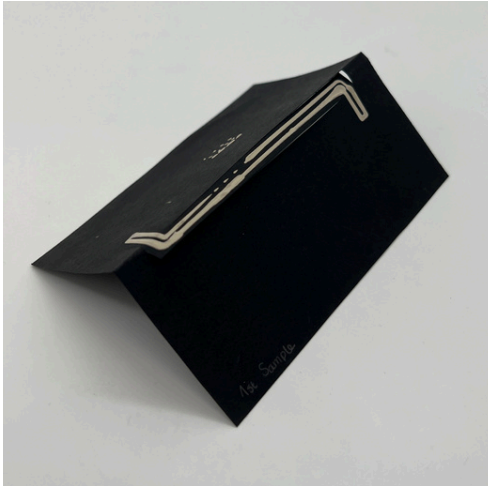

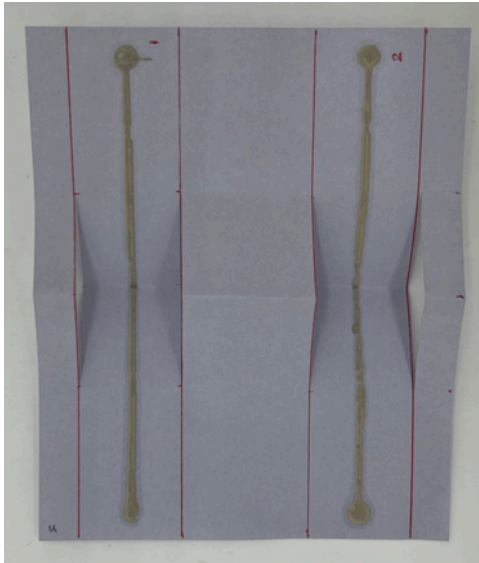

SAMPLE PHOTO

KR_90_BRIDGE_L1 & L2

Kirigami Sample

ATTRIBUTES



90° - Bridge



80g/m²
Cellulose



Valley



Kirigami

ELECTROMECHANICAL DATA



R₀ flat (Ω) 15,17 | 17,37


ΔR/R₀ @100c 22,53 | FAIL

Fold cycles <25 | <10

FAIL

DETAIL PHOTOS

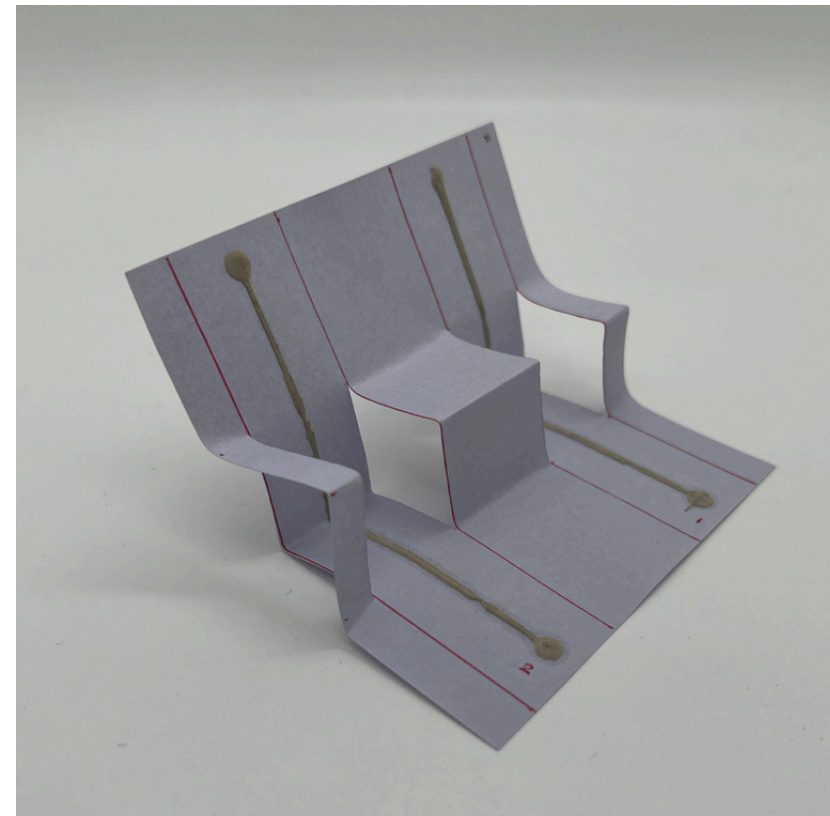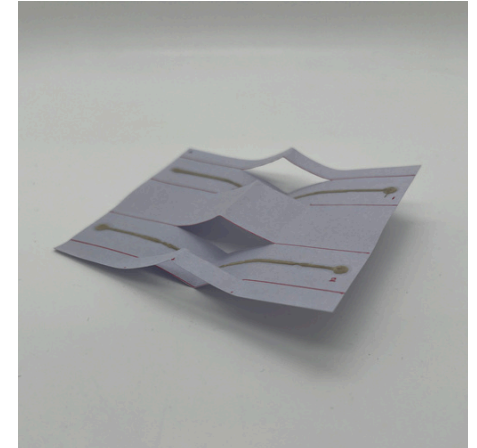

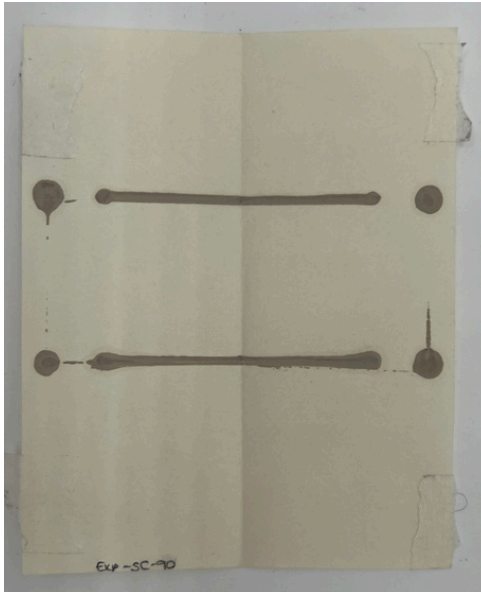

SAMPLE PHOTO

SC_90_L1 & L2

Single Crease Sample

ATTRIBUTES



90°



80g/m²
Cellulose



Valley



Single Crease


ELECTROMECHANICAL DATA

R_0 flat (Ω)	60,09 20,80
$\Delta R/R_0$ @100c	2,056 0,870
Fold cycles	>100

DEGRADED

MARGINAL

DETAIL PHOTOS

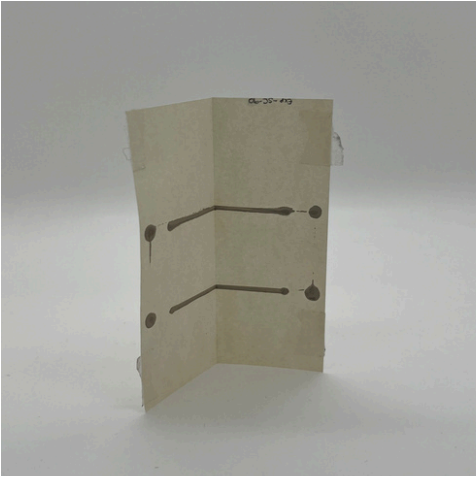

160 G/M² CELLULOSE PHOTOS





SAMPLE PHOTO

SC_0_L1 & L2

Single Crease Sample

ATTRIBUTES

 0°	 80g/m² Cellulose
 Valley	 Single Crease

ELECTROMECHANICAL DATA

R_0 flat (Ω) 59,80 | 20,80

$\Delta R/R_0$ @100c 2,071 | 0,870


Fold cycles >100

DEGRADED

MARGINAL

DETAIL PHOTOS



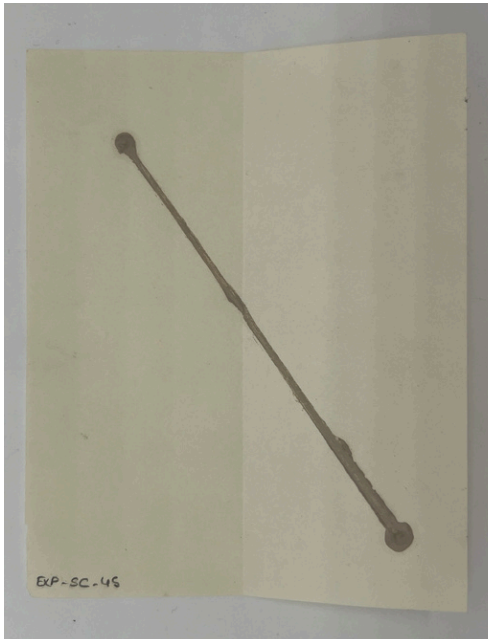

SAMPLE PHOTO

SC_45

Single Crease Sample

ATTRIBUTES

45°

80g/m²
Cellulose

Valley


Single Crease

ELECTROMECHANICAL DATA

R_0 flat (Ω)	91,46
$\Delta R/R_0$ @100c	FAIL
Fold cycles	<10


FAIL

DETAIL PHOTOS

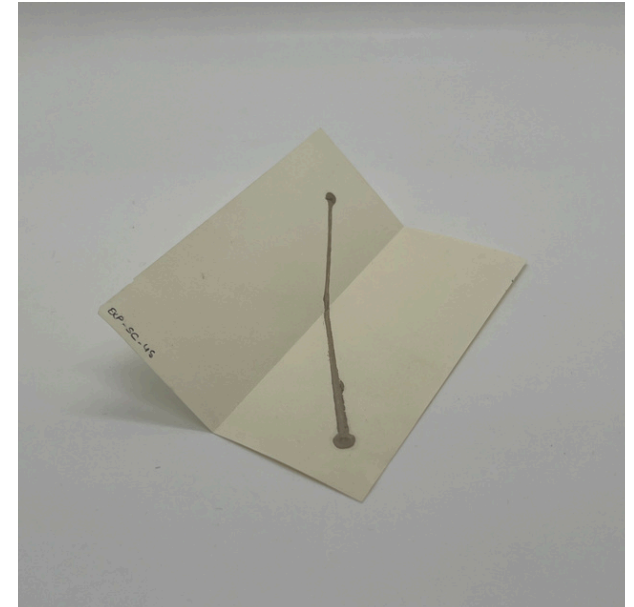

160 G/M² CELLULOSE PHOTOS



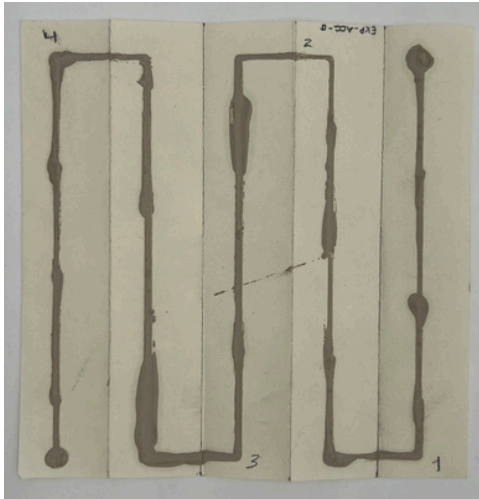

SAMPLE PHOTO

ACC_90_L1 & L2

Accordion Sample

ATTRIBUTES

90°	80g/m² Cellulose
Crease	Accordion



ELECTROMECHANICAL DATA


R_0 flat (Ω)	26,66 221
$\Delta R/R_0$ @100c	1,927 FAIL
Fold cycles	>100 <10

DEGRADED

FAIL

DETAIL PHOTOS

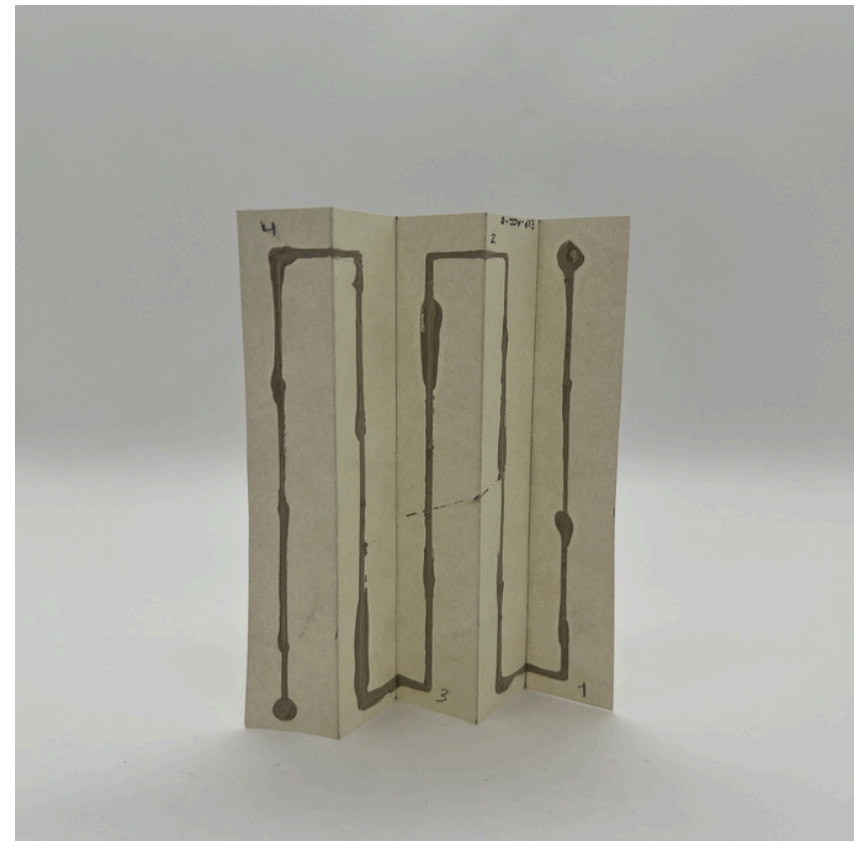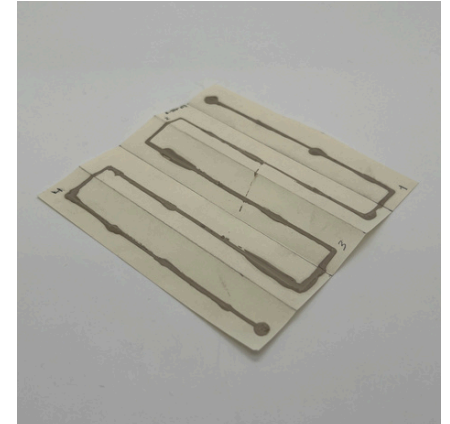

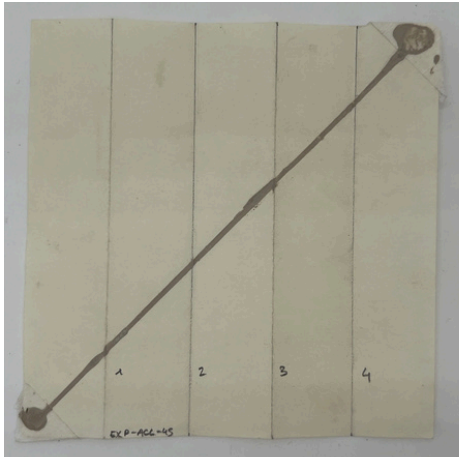

SAMPLE PHOTO

ACC_45_L1

Accordion Sample

ATTRIBUTES

90°
45°

80gr
80g/m²
Cellulose

Crease


Accordion


ELECTROMECHANICAL DATA

R ₀ flat (Ω)	18,07
ΔR/R ₀ @100c	2,688
Fold cycles	>100

DEGRADED

DETAIL PHOTOS

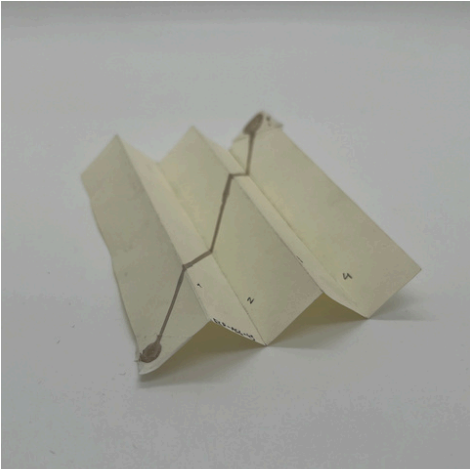

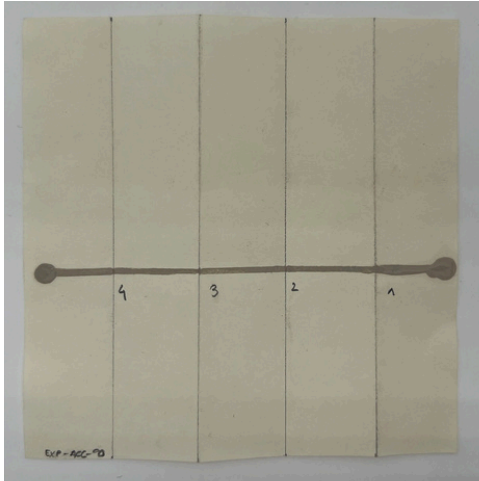


SAMPLE PHOTO

ACC_0_L1 & L4

Accordion Sample


ATTRIBUTES




0°



80g/m²
Cellulose



Valley



Accordion

ELECTROMECHANICAL DATA



R₀ flat (Ω) 49,17 | 106,19

ΔR/R₀ @100c 1,332 | 3,597


Fold cycles <25


FAIL

DETAIL PHOTOS

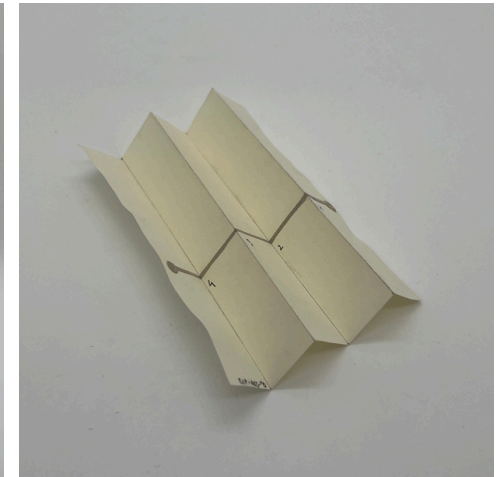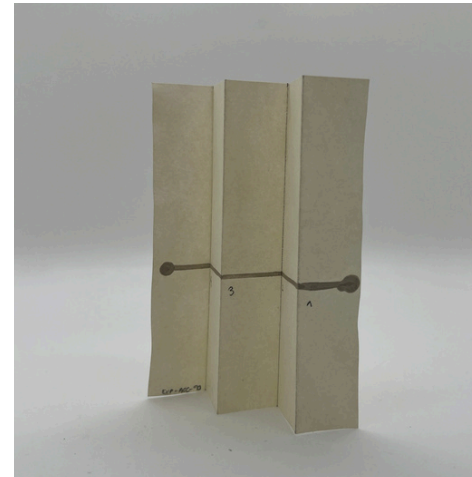

160 G/M² CELLULOSE PHOTOS

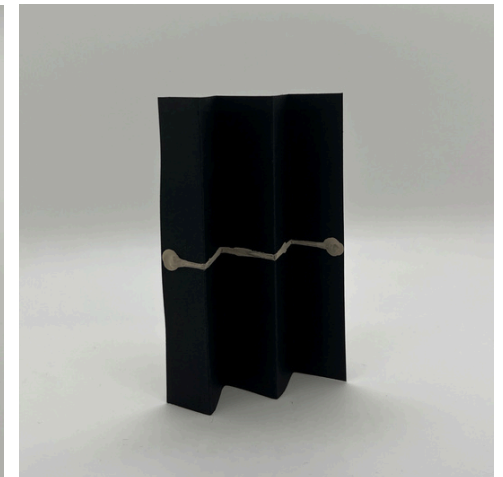

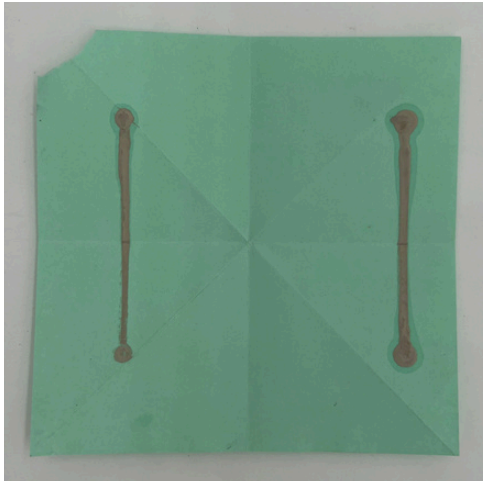

SAMPLE PHOTO

WB_VALLEY

Water Bomb Sample

ATTRIBUTES

90°

80g/m²
Cellulose

Valley



Water Bomb

ELECTROMECHANICAL DATA

R ₀ flat (Ω)	36,65
ΔR/R ₀ @100c	1,037
Fold cycles	<25

FAIL

DETAIL PHOTOS

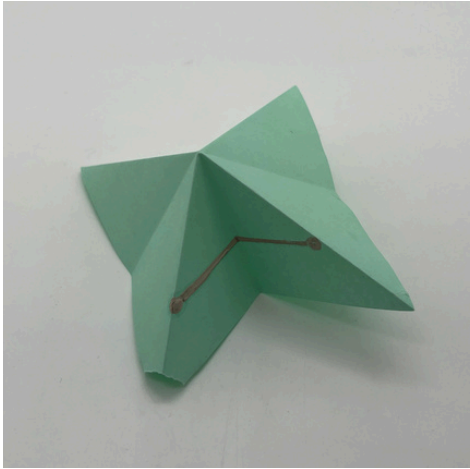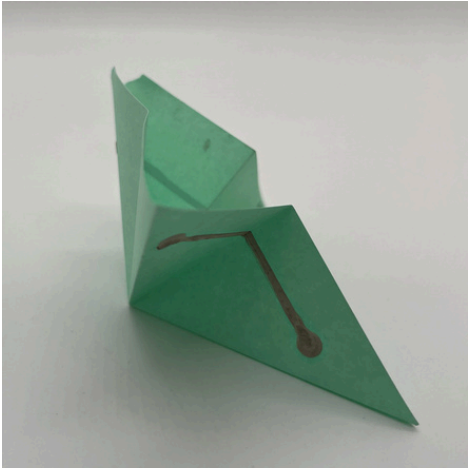

160 G/M² CELLULOSE PHOTOS

