

Video-Based Prediction of In-Flight Particle Characteristics in Atmospheric Plasma Spraying

Abhijeet Praveen¹, Sareh Soleimani¹, Cormac Cureton¹, Aman Sidhu¹, Kintak Raymond Yu², Cristian Cojocaru², and Narges Armanfard¹

¹ Department of Electrical and Computer Engineering, McGill University, Montreal, QC H2X 2G6, Canada, and Mila – Quebec AI Institute, Montreal, QC H2S 3H1, Canada

² National Research Council Canada, Boucherville, QC J4B 6G4, Canada

Abstract. Atmospheric plasma spraying (APS) is a widely used coating process in which in-flight particle temperature and velocity strongly influence coating quality. However, these particle characteristics are difficult to monitor continuously during operation, motivating the development of non-invasive data-driven diagnostic methods. In this work, we investigate the predictive potential of high-speed video observations of the plasma plume for estimating in-flight particle characteristics in APS. We introduce three different video-derived feature representations and evaluate them using Tabular Prior-Data Fitted Networks (TabPFN), convolutional neural networks (CNN), and classical regression baselines including Random Forest, Gradient Boosting, Support Vector Regression, and XGBoost. Experiments are conducted using grouped leave-one-out cross-validation on 126 labeled pre- and post-spray video recordings from 63 APS spray runs. Across the engineered feature experiments, TabPFN achieves the most consistent performance for temperature prediction, reaching $R^2 = 0.86$ using the combined feature representation. CNN models particularly perform stronger for velocity prediction, achieving R^2 of 0.81. In addition, we evaluate models operating directly on raw video frames using pretrained CNNs and find that the highest performance is achieved by a pretrained CNN with a regression head with R^2 of 0.90 and 0.82 for temperature and velocity, respectively. The results demonstrate that video-derived plume information provides a promising and scalable foundation for non-invasive APS diagnostics and real-time process monitoring.

Keywords: Atmospheric Plasma Spraying · Video-Based Diagnostics · TabPFN · Industrial Process Monitoring · Video Feature Extraction

1 Introduction

Atmospheric plasma spray (APS) is a popular thermal spray technique for enhancing surface material properties through application-specific coatings [29]. APS utilizes a plasma torch to generate a high-temperature, high-velocity plasma jet that melts and propels feedstock powder particles onto a substrate, forming the coating upon impact [28, 32].

However, consistently creating high-quality coatings requires precise control during the spray process [29]. Specifically, the properties of the final coating are directly influenced by the in-flight characteristics such as temperature and velocity of the particles as they are accelerated by the spray plume prior to impact [28]. Particles that are insufficiently heated or improperly accelerated result in poor adhesion and high porosity [32]. Therefore, ensuring that particle temperature and velocity remain within a desired operating range is considered critical for reducing variability in coating properties caused by process variations [14]. The relationship between input spray process parameters, such as gas flow rates, electrical power, and standoff distance, and the resulting in-flight particle characteristics is inherently non-linear and sensitive to spray operating conditions, thereby requiring substantial expert knowledge to maintain consistent output quality [24, 34]. Compounding this challenge, the in-flight particle temperature and velocity are not directly observable during production, making real-time control and monitoring difficult for maintaining coating quality [28]. Although dedicated diagnostic systems such as DPV-2000 and Accuraspray have been widely used to measure individual in-flight particle temperatures and velocities via optical methods [26], these setups are typically expensive and are not designed for dynamic, real-time monitoring during active spraying [25].

Beyond the spray process parameters, recent work has demonstrated that factors external to the spray inputs can have a significant influence on coating quality. In particular, electrode usage, referring to the gradual erosion of the cathode and anode within the plasma torch over its operational lifetime, has been shown to alter the characteristics of the plasma jet and consequently the in-flight particle properties, even when all commanded process parameters remain unchanged [24, 34]. This means that a spray system operating under optimal parameter settings may still produce poor coatings as electrodes age, thereby introducing a form of process drift that is not captured by parameter-based predictive models. Therefore, models that can capture these process variations and reflect the evolving physical state of the spray process, beyond the commanded inputs are critical for robust prediction of APS particle characteristics.

Despite growing interest in data-driven approaches to APS process modeling, a gap remains in the literature with respect to the use of spray video recordings for predicting in-flight particle characteristics. Existing machine learning methods for predicting in-flight particle characteristics have largely relied on scalar process parameters alone, and while some have incorporated independent plume images for in-process fault detection [3] or spray target classification [25], none have exploited the rich spatial and temporal information available from video observations of the spray plume. Non-invasive, camera-based diagnostics of the plasma jet and spray plume offer a complementary source of process state information, capturing phenomena such as plume shape, luminosity distribution, and jet instabilities, that are not reflected in process parameters alone [33]. Therefore, the integration of video-derived features represents an underexplored but promising direction for improving the accuracy and robustness of real-time prediction and monitoring of particle characteristics in APS environments.

This work investigates the use of video observations of the plasma spray plume to predict in-flight particle characteristics, specifically particle temperature and velocity in APS. To leverage the information contained in plume observations, we first derive multiple feature representations from recorded videos. These include spectro-temporal descriptors that capture temporal intensity dynamics, plume motion, and boundary variability, as well as geometric descriptors that characterize the spatial structure and morphology of the plasma plume. These descriptors are computed either over temporal windows of video frames or averaged across the entire video segment.

We conduct the first phase of experiments using these engineered feature representations, where several machine learning models are evaluated for predicting particle characteristics. In particular, we investigate the use of Tabular Prior-Data Fitted Networks (TabPFN), a transformer-based model trained on synthetic tabular tasks that enables high-capacity tabular prediction in low-data regimes through in-context learning (ICL) [18]. This property is particularly advantageous for APS applications, where experimental datasets are typically limited and costly to obtain. In addition, we evaluate several classical regression baselines including Random Forest [4], Gradient Boosting [13], Support Vector Regression (SVR) [12], and XGBoost [5]. We also evaluate a lightweight Convolutional Neural Network (CNN) trained directly on the engineered feature representations.

In the second phase of experiments, we explore an alternative modeling strategy that directly leverages raw video observations of the spray plume. In this phase, visual features are extracted using a ResNet18 [16] CNN pretrained on the ImageNet dataset [9], which serves as a fixed feature extractor. Two architectures are evaluated, including a frozen pretrained CNN followed by a regression head, and a frozen pretrained CNN combined with a Long Short-Term Memory (LSTM) network to also capture temporal dependencies across video frames [17, 10]. This comparison allows us to assess whether explicit temporal modeling of plume dynamics provides additional predictive benefit.

In summary, the primary contributions of this work are as follows:

1. The introduction of a video-based monitoring approach for APS particle diagnostics that leverages visual observations of the spray plume and enables the potential deployment of real-time monitoring models in industrial APS environments.
2. The design and evaluation of multiple video-derived feature representations, including spectro-temporal windowed features, geometric windowed features, and geometric averaged features, for capturing plume dynamics relevant to particle temperature and velocity.
3. A comprehensive comparison of several tabular and deep learning models for predicting particle characteristics across two experimental phases using engineered feature representations and raw video recordings.
4. Experimental results demonstrating that video-derived information provides strong predictive signals for particle characteristics, and that both engineered

feature models and raw-video deep learning architectures can achieve strong predictive performance in the data-limited APS setting.

The remainder of this paper is organized as follows. Section 2 reviews prior research on APS diagnostics and machine learning approaches for predicting particle characteristics. Section 3 presents the methodological framework of this study, including the APS experimental setup and the video-derived feature representations used for modeling. Section 4 describes the two experimental phases, including models applied to engineered feature representations and models operating directly on raw video frames, along with the evaluation metrics and the experimental results. Section 5 interprets the experimental findings and discusses the implications for APS video-based monitoring. Finally, Section 6 presents the conclusions of this study and outlines directions for future research.

2 Related Work

The use of machine learning (ML) and artificial intelligence (AI) to model and predict in-flight particle characteristics in APS has been an active area of research for over two decades [21, 1, 6, 7, 35, 22, 36, 15, 23, 30, 8]. Early contributions established foundational frameworks for applying neural networks to thermal spray processes. For example, Guessasma *et al.* [15] provided early empirical insight into the influence of APS parameters on adhesion properties, laying the groundwork for later machine learning approaches. This includes work by Kanta *et al.* [21], demonstrating that artificial neural networks (ANNs) could learn complex, nonlinear relationships between APS power parameters and in-flight particle characteristics such as temperature and velocity, enabling forward prediction of coating structural attributes. Recently, Bobzin *et al.* [1] presented a comprehensive ML-based framework targeting the prediction of in-flight particle properties directly from plasma spray process parameters, with the goal of constructing a digital twin of the thermal spray process. While their results reinforced prior findings that careful feature selection and high-quality training data are critical for reliable prediction, the motivation to their paper underpins a key problem with existing data-driven methods. Specifically, as noted in [31], most models are trained on very small datasets, anywhere from fewer than 20 to at most 38 samples [19], requiring particle spray prediction to operate in a data-limited regime. These limitations motivate the need for learning approaches that remain effective in data-limited regimes while exploiting richer sources of process information.

Alongside ML modeling of the spray process, a complementary line of research has explored imaging and video analysis for monitoring and characterising thermal spray processes [33], as studies have shown that high-speed imaging can provide valuable insights into particle plume dynamics [25]. Bobzin *et al.* [2] used high-speed videography to analyze plasma jet instability and fluctuations during the spray process, demonstrating that temporally resolved imaging contains rich process-state information.

Building on this direction, imaging has also been used for in-process fault detection in cold spray additive manufacturing. Bokade *et al.* [3] introduced ThermoAnoNet, a deep unsupervised learning framework that monitors substrate temperature profiles from thermal imaging to detect process anomalies such as increased deposition rates or nozzle clogging, demonstrating the potential of non-invasive imaging for real-time process monitoring.

More recently, [25] proposed a multi-modal approach incorporating video features for spray plume classification using a pre-trained YOLO model. However, this work treats each observation independently and does not exploit the temporal structure of the data, thereby discarding contextual information that is critical for capturing the evolving dynamics of the spray plume. Moreover, their approach focuses on classification rather than regression-based prediction of particle characteristics.

3 Methodology

This section describes the APS experimental setup, video pre-processing and feature extraction methods used for predicting in-flight particle characteristics.

3.1 APS Experimental Setup

All experiments were conducted using an Axial3Plus APS torch (Northwest Mettech Corp., Vancouver, BC, Canada). The system was configured with three pairs of new electrodes and operated with a powder feeder speed of 1 RPM. Experiments were performed using three nozzle diameters (3/8", 1/2", and 5/16"), while the torch current was maintained at a constant value of 125 A.

Particle diagnostic measurements were obtained using an Accuraspray 4.0 system (Tecnar, St-Bruno, QC, Canada), which provides optical measurements of in-flight particle temperature and velocity. Video recordings of the plasma plume were captured using a fixed RGB scientific camera.

Each experiment followed an identical spray procedure. After plasma ignition and stabilization, powder injection was initiated and a stationary diagnostic measurement was recorded prior to deposition (pre-spray). The torch then executed five spray passes across the substrate to deposit the coating. Upon completion of the deposition process, the torch returned to a stationary position where a second diagnostic measurement was collected (post-spray).

Particle temperature and velocity labels were obtained separately for the pre-spray and post-spray intervals using the mean value of the diagnostic measurements within each interval. Corresponding video recordings were captured during both diagnostic phases, allowing each video to be associated with a particle characteristic label.

Five spray configurations with different gas flow rates were used as summarized in Table 1. In total, 63 labeled spray runs were collected, resulting in 126 video recordings (63 pre-spray and 63 post-spray), each with corresponding diagnostic measurements and video data.

Table 1. Spray Conditions Used for Data Collection (Gas Flow Rates in LPM)

Condition #	Argon	Nitrogen	Hydrogen
1	125	75	50
2	175	50	25
3	200	25	25
4	187	37.5	25
5	187	25	37.5

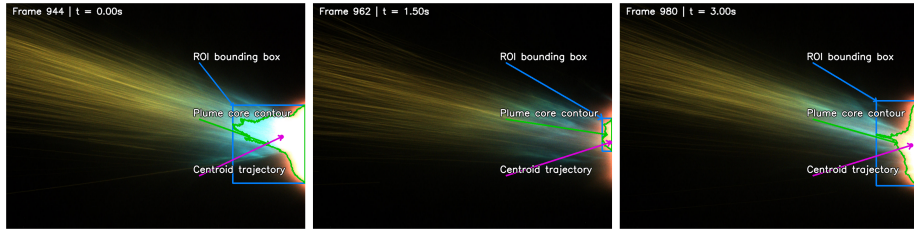


Fig. 1. Representative first, second and third temporal frames from APS plume videos (from left to right), illustrating the visual information available in the spray recordings. The overlays show the segmented plume core, the region of interest (ROI) used for feature extraction, and the centroid trajectory used to characterize plume motion. These visual cues form the basis for the engineered video feature representations described in Section 3.2.

All experiments were implemented in Python and executed using an NVIDIA RTX 5000 Ada Generation GPU (32 GB, CUDA 12.6).

3.2 Video Feature Representations

Pre-processing. To ensure consistency across experiments, each video was first converted to grayscale and each recorded interval was temporally cropped to the active torch period. The videos were recorded at 15 frames per second (FPS) and each interval was processed as a fixed-duration six-second spray segment. Video durations varied slightly across experiments, therefore the segment length was selected based on the shortest usable interval in the dataset. This ensured that all videos were represented using a consistent temporal footprint for feature extraction and learning. Frames were then extracted from the cropped video interval. To reduce redundancy and computational cost, videos were downsampled by keeping every k -th frame, where $k = 5$ in our implementation. Feature extraction was then performed either over the entire video segment or over a set of fixed temporal windows. For the windowed representations, each video was divided into three equal-length windows, of two seconds each, in the downsampled frame domain. Figure 1 shows representative frames from the three temporal windows of a sample video. These frames illustrate temporal variations in plume

size and shape, motivating the use of representations that capture both global plume geometry and short-term temporal dynamics.

To capture these different aspects of plume behavior, we construct three complementary video-derived feature representations: Geometric Averaged (GA), Geometric Windowed (GW), and Spectro-Temporal Windowed (STW).

Geometric Averaged (GA). The GA representation captures global plume morphology by computing frame-level geometric descriptors and averaging them across the full video segment. Two types of measurements are included. First, intensity-distribution features are extracted using five pixel intensity bins: 0–50, 50–100, 100–150, 150–200, and 200–255. These bins quantify the fraction of pixels within different brightness ranges and provide a coarse description of the plume’s radiative structure. Second, geometric shape descriptors are computed from a thresholded plume mask, including plume area, perimeter, vertical extent, and horizontal extent. Averaging these nine descriptors across all frames yields a compact representation of the overall plume structure for a given spray video.

Geometric Windowed (GW). While GA summarizes the plume over the full video, GW preserves temporal variation by computing the same geometric descriptors separately within three short windows and concatenating them across time, resulting in 27 features per video.

Spectro-Temporal Windowed (STW). The STW representation is designed to describe short-term temporal dynamics of the plume. For each of the three windows, frame-level intensity and contour measurements are first computed from the plume ROI. These frame-level measurements are then converted into temporal descriptors that characterize oscillatory behavior, coherence, motion, and boundary variation over time. This windowed dataset results in 24 features per video. The extracted STW descriptors include: (i) temporal dominant frequency, obtained from the Fourier spectrum of the plume intensity signal; (ii) band power in the 5–20 Hz range, which captures mid-frequency oscillatory energy; (iii) auto-correlation time, which measures temporal persistence in the intensity sequence; (iv) centroid speed, derived from frame-to-frame motion of the segmented plume centroid; (v) centroid along ratio, which quantifies whether motion is primarily aligned with the spray axis or perpendicular to it; (vi) perimeter difference standard deviation, which captures short-term variability of the plume boundary; (vii) the 90th percentile of detected streak lengths, used as a proxy for persistent elongated flow structures; and (viii) mean intensity, which summarizes overall brightness within the window. Together, these features provide a compact description of both plume motion and temporal intensity dynamics. These spectro-temporal descriptors are commonly used in dynamic texture and spatio-temporal video analysis to characterize time-varying visual phenomena [11, 20].

The three feature sets capture complementary information. GA provides a stable global summary of plume structure, GW preserves time-localized geometric evolution, and STW focuses on dynamic temporal behavior that reflects tran-

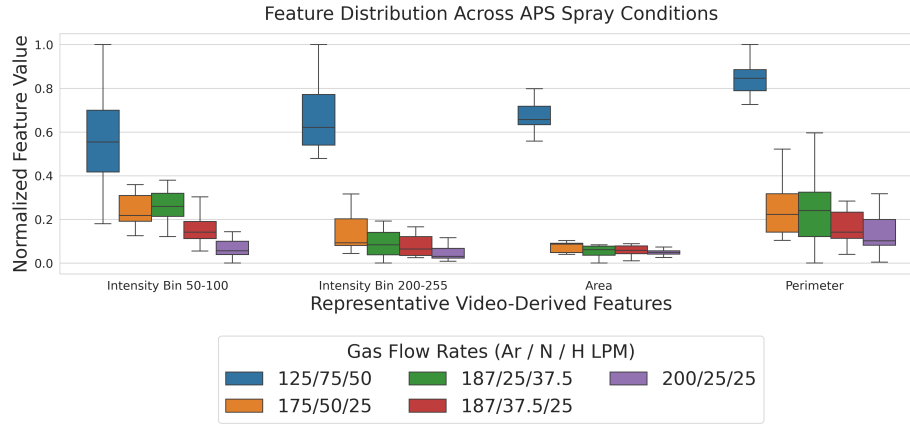


Fig. 2. Distribution of representative video-derived plume features across APS spray conditions. Each grouped boxplot compares the normalized distributions of selected intensity-based and geometric descriptors under different gas flow configurations (Argon/Nitrogen/Hydrogen in LPM).

sient flow instabilities and particle transport effects. Figure 2 presents the distributions of several representative video-derived features across the five APS spray conditions. The selected descriptors include both intensity-based and geometric plume measurements, normalized to allow comparison across features. Consistent shifts in feature distributions are observed across different gas flow configurations, suggesting that the extracted plume descriptors capture condition-dependent variations in plume structure. These results provide qualitative evidence that video-derived features contain physically meaningful information related to APS operating parameters.

4 Experiments

This section describes the modeling approaches used in this study and their evaluation. We first present the models applied to engineered feature representations, followed by models operating directly on raw video frames. We then evaluate these approaches to assess their effectiveness in predicting in-flight particle temperature and velocity.

4.1 Models and Baselines for Engineered Feature Representations

In the first phase of experiments, we evaluate both tabular machine learning models and deep learning approaches on the engineered video feature representations described in Section 3.2. The goal of this comparison is to assess whether the proposed plume descriptors can be effectively exploited by different learning

paradigms in the data-limited APS setting. We consider several tabular regression models, including TabPFN and classical models such as Random Forest, Gradient Boosting, Support Vector Regression, and XGBoost. In addition, we evaluate a CNN applied to the engineered windowed feature representations.

TabPFN. TabPFN is a transformer-based tabular model designed for small tabular datasets, where it has been shown to perform strongly through in-context learning rather than conventional task-specific training [18, 27]. This makes it particularly attractive in the APS setting, where labeled experiments are limited and collecting additional data is costly. Instead of learning solely through gradient updates on the target dataset, TabPFN leverages knowledge acquired from synthetic prior tasks and adapts to the target problem at inference time. In this study, separate single-task TabPFN regressors are used for particle temperature and particle velocity prediction.

CNN Architecture. Motivated by prior work demonstrating the effectiveness of convolutional neural networks for monitoring thermal spray processes [25], we also implement a CNN architecture to model the engineered feature representations extracted from multiple temporal windows of video data. Each sample is represented as a tensor of shape $[B, F, T]$, where B denotes the batch size, F the number of engineered features, and $T = 3$ the number of temporal windows corresponding to the first, second, and third temporal windows of the analyzed video. This representation allows the network to learn relationships between features across neighboring temporal windows. The CNN architecture consists of three stacked one-dimensional convolutional layers with 64 hidden channels. The first convolution uses a kernel size of 2 with padding 1, the second uses a kernel size of 3 with padding 1, and the third uses a kernel size of 2 without additional padding. Each convolutional layer is followed by a ReLU activation function. These convolutional filters operate along the temporal dimension and enable the network to capture short-range interactions and transitions between adjacent windows. After the convolutional layers, an adaptive average pooling layer aggregates the temporal dimension to produce a fixed-length representation. The resulting feature vector is then passed to a regression head composed of two fully connected layers with a ReLU activation between them, specifically $\text{Linear}(64, 64)$ followed by $\text{Linear}(64, 1)$, to produce the final scalar prediction corresponding to either particle temperature or particle velocity. Model hyperparameters were selected through validation experiments during model development, with the final configuration using the Adam optimizer, a learning rate of 1×10^{-3} , batch size 16, and 100 training epochs.

4.2 Raw Video Modeling

In the second phase of experiments, we also evaluate deep learning models that operate directly on raw video frames of the plasma plume. This phase aims to assess whether visual representations learned directly from plume imagery

can capture predictive information related to particle temperature and velocity without relying on manually engineered descriptors.

For each experiment, the video segment corresponding to the measurement interval is extracted using the start and end timestamps of the active period provided in the dataset. To keep the experiment uniform, 24 frames were extracted from a fixed length of six seconds across all videos, as the full video lengths varied across all available samples. Each frame is resized to a fixed spatial resolution of 224×224 pixels and normalized before being passed to the neural network models.

To leverage existing visual representations while maintaining stability in the small-data APS setting, we employ a pretrained convolutional neural network as a fixed feature extractor. Specifically, we use ResNet18 [16], pretrained on the ImageNet dataset [9], which processes each frame independently and produces a compact feature embedding representing the spatial structure and intensity patterns of the plasma plume.

Two architectures are evaluated using these extracted visual embeddings. The first architecture consists of a frozen pretrained CNN followed by a regression head. In this configuration, the CNN backbone remains fixed and only the final fully connected layers are trained to map the extracted visual features to the target particle characteristic. The regression head uses the same architecture as the CNN model described in Section 4.1, consisting of two fully connected layers with ReLU activation between them (Linear(64, 64) followed by Linear(64, 1)). This architecture evaluates whether frame-level spatial representations alone are sufficient for predicting particle temperature and velocity.

The second architecture extends this framework by introducing temporal modeling through a Long Short-Term Memory (LSTM) network. While the frozen CNN extracts spatial features from individual frames, plume dynamics in plasma spraying evolve continuously over time, and these temporal fluctuations may contain additional information related to particle temperature and velocity. To capture such sequential dependencies, each frame of a video sample is first processed by the frozen pretrained CNN to produce a sequence of frame-level embeddings. These embeddings are then passed to a single-layer LSTM network that models temporal relationships across the frame sequence. The final hidden state of the LSTM is used as the aggregated video representation and is subsequently passed through the same two-layer regression head to generate the final prediction. LSTM networks are generally well suited for modeling sequential data and long-range temporal dependencies [17], and CNN-LSTM architectures have been widely used for modeling temporal dynamics in video data [10].

4.3 Evaluation Metrics

All models are evaluated using grouped leave-one-out cross-validation (LOOCV). In each fold, all samples associated with one spray experiment identifier are held out for testing, while the remaining experiments are used for training. Therefore, each fold holds out both the pre-spray and post-spray videos from one spray run.

This grouping is necessary because each spray experiment contributes multiple related video samples, corresponding to the pre-spray and post-spray intervals. Splitting these related samples across training and testing would introduce information leakage. Grouped LOOCV therefore provides a more realistic estimate of generalization to unseen spray runs while remaining appropriate for the limited dataset size.

Model performance is reported separately for temperature and velocity prediction using the coefficient of determination (R^2) and the Percentage Accuracy Metric (PAM) as shown in (1) and (2), respectively. For a set of n true labels y_i and corresponding predictions $\hat{y}_i$, R^2 is defined as:

$$R^2 = 1 - \frac{\sum_{i=1}^n (y_i - \hat{y}_i)^2}{\sum_{i=1}^n (y_i - \bar{y})^2} \quad \text{where } \bar{y} = \frac{1}{n} \sum_{i=1}^n y_i \quad (1)$$

The Percentage Accuracy Metric at tolerance $\delta\%$, denoted PAM@ $\delta\%$, is defined as the proportion of predictions whose relative error is within $\delta\%$ of the ground truth:

$$\text{PAM@}\delta\% = \frac{1}{n} \sum_{i=1}^n \mathbb{1} \left(\left| \frac{\hat{y}_i - y_i}{y_i} \right| \leq \frac{\delta}{100} \right) \quad (2)$$

Where $\mathbb{1}(\cdot)$ is the indicator function, which equals 1 if the condition holds and 0 otherwise. We report PAM@2.5%, PAM@5%, and PAM@10% in addition to R^2 . While R^2 captures overall goodness of fit, PAM provides a more application-oriented measure of predictive reliability by quantifying how often predictions fall within practically meaningful tolerance bands. This is particularly useful in APS, where the temperature and velocity targets differ substantially in magnitude and where relative prediction error is often more informative than absolute error alone.

4.4 Experimental Results and Analysis

The predictive performance of the proposed video-based APS modeling approaches under both experimental phases was evaluated using the R^2 and PAM metrics defined in Section 4.3.

Performance Analysis

First Phase. Table 2 compares the primary modeling approaches across engineered feature representations. As shown in Table 2, TabPFN achieves the highest performance for particle temperature prediction when using the combined feature set (STW+GW+GA), reaching an R^2 of 0.86. In contrast, the CNN model achieves the best performance for particle velocity prediction across all four feature sets considered in the table. In particular, CNN attains its strongest velocity prediction performance when using the GW representation, with an

Table 2. Model performance comparison across all the engineered feature representations for particle temperature and velocity prediction.

Model	Temperature Prediction				Velocity Prediction			
	R^2	PAM _{2.5}	PAM ₅	PAM ₁₀	R^2	PAM _{2.5}	PAM ₅	PAM ₁₀
STW								
Random Forest	0.51	0.23	0.40	0.63	0.07	<u>0.19</u>	0.29	<u>0.57</u>
Gradient Boosting	0.43	0.24	<u>0.44</u>	<u>0.66</u>	-0.04	0.14	0.29	0.49
SVR	-0.06	0.21	0.38	0.51	<u>0.12</u>	0.12	0.23	0.44
XGBoost	0.48	0.21	0.40	0.65	<u>0.04</u>	0.13	0.26	0.52
TabPFN	<u>0.58</u>	0.34	0.54	0.79	0.09	0.13	<u>0.33</u>	0.52
CNN	0.71	<u>0.32</u>	<u>0.44</u>	<u>0.66</u>	0.50	0.25	0.44	0.68
GW								
Random Forest	0.86	<u>0.43</u>	0.67	<u>0.89</u>	0.36	0.22	0.46	0.67
Gradient Boosting	<u>0.85</u>	<u>0.43</u>	0.70	0.90	0.28	<u>0.22</u>	0.44	0.68
SVR	0.32	0.28	0.44	0.58	0.29	0.14	0.31	0.58
XGBoost	0.82	0.40	<u>0.72</u>	0.88	0.31	0.18	0.44	0.69
TabPFN	0.83	0.53	0.75	0.88	<u>0.54</u>	<u>0.22</u>	<u>0.52</u>	<u>0.74</u>
CNN	0.73	0.30	0.45	0.68	0.81	0.48	0.67	0.85
GA								
Random Forest	0.79	0.41	0.63	<u>0.79</u>	<u>0.27</u>	<u>0.17</u>	<u>0.36</u>	0.52
Gradient Boosting	0.75	0.35	0.54	0.75	0.21	0.15	0.33	<u>0.55</u>
SVR	0.34	0.27	0.43	0.57	0.25	0.09	0.30	0.52
XGBoost	0.72	0.29	0.51	0.75	0.16	0.10	0.26	0.52
TabPFN	<u>0.78</u>	<u>0.40</u>	<u>0.59</u>	0.81	0.45	0.22	0.41	0.61
STW+GW+GA								
Random Forest	<u>0.80</u>	<u>0.42</u>	<u>0.71</u>	0.85	0.52	<u>0.25</u>	0.46	0.67
Gradient Boosting	0.77	0.36	0.65	<u>0.87</u>	0.51	0.24	0.40	0.66
SVR	0.24	0.27	0.42	0.57	0.28	0.14	0.25	0.53
XGBoost	0.75	0.37	0.68	<u>0.87</u>	0.49	0.18	0.44	0.66
TabPFN	0.86	0.52	0.74	0.90	<u>0.64</u>	<u>0.25</u>	<u>0.52</u>	<u>0.74</u>
CNN	0.78	0.33	0.58	0.79	0.65	0.42	0.62	0.75

For each performance metric, the best result within each feature-set block is shown in **bold** and the second-best result is underlined.

Abbreviations: GA (Geometric Averaged), GW (Geometric Windowed), STW (Spectro-Temporal Windowed).

Table 3. Comparison of raw video-based pretrained CNN models for particle temperature and velocity prediction.

Model	Temperature Prediction				Velocity Prediction			
	R^2	PAM _{2.5}	PAM ₅	PAM ₁₀	R^2	PAM _{2.5}	PAM ₅	PAM ₁₀
CNN+RH	0.90	0.75	0.88	0.95	0.82	0.60	0.73	0.88
CNN+LSTM	0.75	0.63	0.77	0.84	0.81	0.49	0.70	0.87

For each performance metric, the best result is shown in **bold**.

Abbreviations: RH (Regression Head).

R^2 of 0.81. The combined feature representation also performs well, suggesting that CNN models benefit from richer feature inputs that capture complementary aspects of plume dynamics. Results for the CNN model using the GA representation are not reported, as this configuration produced very poor performance. This behavior is likely due to the fact that GA features are temporally averaged summaries that remove the local temporal structure required by convolutional filters to capture meaningful patterns across adjacent temporal windows.

Second Phase. Table 3 presents the performance of models that operate directly on raw video frames using pretrained convolutional feature extractors. In this setting, both evaluated architectures achieve strong predictive performance for particle temperature and velocity. Notably, the frozen pretrained CNN followed by a regression head (RH) achieves the strongest overall results, with $R^2 = 0.90$ for temperature prediction and $R^2 = 0.82$ for velocity prediction. This suggests that spatial representations extracted from plume imagery already contain substantial information related to particle characteristics. The CNN+LSTM architecture also achieves competitive performance, although its performance remains slightly below that of the simpler CNN+RH model.

We also evaluated an alternative architecture in which both the CNN architecture and LSTM layers were trained end-to-end on raw video frames. However, this configuration produced significantly worse performance. This behavior is likely due to the relatively small dataset size available for APS experiments.

5 Discussion

Across the engineered feature experiments, TabPFN consistently achieves the strongest or near-strongest predictive performance for particle temperature. This is particularly notable given that TabPFN requires no task-specific training or hyperparameter optimization, in contrast to the other evaluated models, which require explicit optimization of parameters such as learning rate, regularization strength, tree depth, or network architecture. Although TabPFN is limited to tabular inputs and therefore cannot be applied directly to raw video data, it provides an efficient and effective modeling approach once structured feature representations have been constructed. In our setting, this makes the feature engineering pipeline especially valuable, as it enables the use of high-performing tabular foundation models while avoiding task-specific retraining and hyperparameter optimization.

The engineered feature results also highlight the importance of representation design. While individual feature sets such as STW, GW, and GA already provide useful predictive signals, combining them consistently yields stronger performance, suggesting that geometric and spectro-temporal descriptors capture complementary aspects of plume behavior. CNN models trained on the engineered feature sets also perform strongly, particularly for particle velocity prediction. This reflects the suitability of CNNs for the windowed representation, where convolutional filters capture local cross-window interactions without

requiring long-range temporal modeling. Consistent with this observation, the resulting performance remains close to that obtained when models are trained directly on raw video frames.

The raw video experiments further show that direct visual representations of the plasma plume contain strong predictive information for particle characteristics. Both pretrained CNN-based architectures achieve strong performance for temperature and velocity prediction, indicating that spatial plume structure captured from video frames is highly informative.

These results indicate that both engineered feature pipelines and raw video representations are viable for APS particle prediction, with each offering distinct advantages.

6 Conclusion

This work demonstrates that video-derived plume information can be used to reliably predict key particle characteristics in atmospheric plasma spraying. Using engineered video feature representations, TabPFN achieves the strongest and most consistent performance for particle temperature, while CNN models perform particularly well for particle velocity.

In addition to engineered features, this study also evaluates pretrained CNN-based models operating directly on raw video frames. These models achieve strong performance for both temperature and velocity prediction, showing that plume imagery itself contains highly informative signals for APS diagnostics.

These findings show that accurate prediction of APS particle characteristics can be achieved with relatively small datasets when suitable visual representations and learning paradigms are employed. More broadly, the results support the use of video-based monitoring as a promising non-invasive approach for scalable, data-efficient process monitoring and predictive diagnostics in thermal spray manufacturing environments.

Future work will explore multimodal fusion with additional sensing modalities, such as acoustic signals and process parameters, to further enhance predictive accuracy and improve generalization across diverse plasma spray operating conditions. Additionally, future research will investigate the potential for deploying such video-based predictive models in real APS environments. In practical settings, predictions may only need to operate within narrower operating regimes corresponding to specific spray parameters, which could allow models to achieve higher reliability for real-time monitoring and process control.

Disclosure of Interests. The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Declaration of Generative AI in the writing process. During the preparation of this work, the authors used generative AI tools to assist with formatting, language refinement, and readability improvements. After using these tools, the authors carefully reviewed and edited the content and take full responsibility for the accuracy and integrity of the final content.

References

1. Bobzin, K., Wietheger, W., Heinemann, H., Dokhanchi, S.R., Rom, M., Visconti, G.: Prediction of particle properties in plasma spraying based on machine learning. *Journal of Thermal Spray Technology* **30**, 1751–1764 (2021)
2. Bobzin, K., Öte, M., Knoch, M., Alkhasli, I., Heinemann, H.: High-speed video analysis of the process stability in plasma spraying. *Journal of Thermal Spray Technology* **30**(4), 987–1000 (2021)
3. Bokade, R., Müftü, S., Özdemir, O.Ç., Jin, X.: Thermal imaging based non-destructive testing for fault detection in cold spray additive manufacturing. *Journal of Manufacturing Processes* **134**, 1057–1068 (2025)
4. Breiman, L.: Random forests. *Machine Learning* **45**(1), 5–32 (2001)
5. Chen, T., Guestrin, C.: Xgboost: A scalable tree boosting system. In: *Proceedings of the ACM SIGKDD International Conference on Knowledge Discovery and Data Mining (KDD)*. pp. 785–794 (2016)
6. Choudhury, T., Berndt, C., Man, Z.: An extreme learning machine algorithm to predict the in-flight particle characteristics of an atmospheric plasma spray process. *Plasma Chemistry and Plasma Processing* **33**(5), 993–1023 (2013)
7. Choudhury, T.A., Berndt, C., Man, Z.: Modular implementation of artificial neural network in predicting in-flight particle characteristics of an atmospheric plasma spray process. *Engineering Applications of Artificial Intelligence* **45** (2015)
8. Citarella, A.A., Carrino, L., De Marco, F., Di Biasi, L., Perna, A.S., Viscusi, A., Tortora, G.: Ai data-driven optimization of cold spray coating manufacturing. *IEEE Transactions on Industrial Informatics* (2025)
9. Deng, J., Dong, W., Socher, R., Li, L.J., Li, K., Fei-Fei, L.: Imagenet: A large-scale hierarchical image database. *Proceedings of the IEEE Conference on Computer Vision and Pattern Recognition (CVPR)* pp. 248–255 (2009)
10. Donahue, J., Hendricks, L.A., Guadarrama, S., Rohrbach, M., Venugopalan, S., Saenko, K., Darrell, T.: Long-term recurrent convolutional networks for visual recognition and description. In: *Proceedings of the IEEE Conference on Computer Vision and Pattern Recognition (CVPR)*. pp. 2625–2634 (2015)
11. Doretto, G., Soatto, S., Wu, Y., Chiuso, A.: Dynamic textures. *International Journal of Computer Vision* **51**(2), 91–109 (2003)
12. Drucker, H., Burges, C.J.C., Kaufman, L., Smola, A., Vapnik, V.: Support vector regression machines. *Advances in Neural Information Processing Systems* **9** (1997)
13. Friedman, J.H.: Greedy function approximation: A gradient boosting machine. *Annals of Statistics* **29**(5), 1189–1232 (2001)
14. Friis, M., Persson, C.: Control of thermal spray processes by means of process maps and process windows. *Journal of Thermal Spray Technology* **12**, 44–52 (2003)
15. Guessasma, S., Montavon, G., Coddet, C.: Analysis of the influence of atmospheric plasma spray (aps) parameters on adhesion properties of alumina-titania coatings. *Journal of adhesion science and technology* **18**(4), 495–505 (2004)
16. He, K., Zhang, X., Ren, S., Sun, J.: Deep residual learning for image recognition. In: *Proceedings of the IEEE Conference on Computer Vision and Pattern Recognition (CVPR)*. pp. 770–778 (2016)
17. Hochreiter, S., Schmidhuber, J.: Long short-term memory. *Neural Computation* **9**(8), 1735–1780 (1997)
18. Hollmann, N., et al.: Accurate predictions on small data with a tabular foundation model. *Nature* **637**, 319–326 (2025)

19. Hudomalj, U.: Monitoring, Modelling and Control for Increasing Repeatability of Thermal Spraying. Ph.D. thesis, ETH Zurich (2024). <https://doi.org/10.3929/ethz-b-000673305>
20. Jansson, Y., Lindeberg, T.: Dynamic texture recognition using time-causal and time-recursive spatio-temporal receptive fields. *Journal of Mathematical Imaging and Vision* **60**(9), 1369–1398 (Jun 2018)
21. Kanta, A.F., Montavon, G., Planche, M.P., Coddet, C.: Artificial neural networks implementation in plasma spray process: Prediction of power parameters and in-flight particle characteristics vs. desired coating structural attributes. *Surface and Coatings Technology* **203**, 3361–3369 (2009)
22. Kanta, A.F., Montavon, G., Berndt, C.C., Planche, M.P., Coddet, C.: Intelligent system for prediction and control: Application in plasma spray process. *Expert systems with applications* **38**(1), 260–271 (2011)
23. Kanta, A.F., Montavon, G., Planche, M.P., Coddet, C.: Artificial intelligence computation to establish relationships between aps process parameters and alumina-titania coating properties. *Plasma Chemistry and Plasma Processing* **28**(2), 249–262 (2008)
24. Leblanc, L., Moreau, C.: The long-term stability of plasma spraying. *Journal of Thermal Spray Technology* **11**, 380–386 (2002)
25. Malamousi, K., Delibasis, K., Kamnis, S.: Real-time thermal spray process monitoring using convolution neural network deep learning architectures. *Journal of Thermal Spray Technology* **33**, 17–32 (2024)
26. Moreau, C.: Towards a better control of thermal spray processes. In: *Proceedings of the International Thermal Spray Conference*. vol. 2, pp. 1681–1693 (1998)
27. Müller, S., Hollmann, N., Arango, S.P., Grabocka, J., Hutter, F.: Transformers can do bayesian inference. In: *International Conference on Learning Representations* (2022)
28. Nikiforov, A., Chen, Z. (eds.): *Atmospheric Pressure Plasma: From Diagnostics to Applications*. CRC Press, Boca Raton, FL, USA (2019)
29. Prasad, C.D., Tiwari, A., Suryawanshi, S.R., Dileep, B.P., Gowda, A.C., Masum, H., Dutt, K.M., Sunil Prashanth Kumar, S., Bavan, S.: Overview of thermal spray coating on additive manufacturing. *Progress in Additive Manufacturing* **10**, 4327–4347 (2025)
30. Savangouder, R.V., Patra, J.C., Palanisamy, S.: A machine learning technique for prediction of cold spray additive manufacturing input process parameters to achieve a desired spray deposit profile. *IEEE Transactions on Industrial Informatics* **20**, 12275–12283 (2024)
31. Sha, W.: Comment on ‘modelling of the aps plasma spray process using artificial neural networks: Basis, requirements and an example’ by guessasma et al. *Computational Materials Science* **50**, 805–809 (2010)
32. Singh, H., Sidhu, B., Puri, D., Prakash, S.: Use of plasma spray technology for deposition of high temperature oxidation/corrosion resistant coatings—a review. *Materials and Corrosion* **58**(2), 92–102 (2007)
33. Vattulainen, J., Hämäläinen, E., Hernberg, R., Vuoristo, P., Mäntylä, T.: Novel method for in-flight particle temperature and velocity measurements in plasma spraying using a single ccd camera. *Journal of Thermal Spray Technology* **10**, 94–104 (2001)
34. Yu, K.R., Cojocaru, C.V., Ilinca, F., Irissou, E.: Ensemble methods for aps in-flight particle temperature and velocity prediction considering torch electrodes ageing. *Journal of Thermal Spray Technology* **32**, 175–187 (2023)

35. Zhu, J., Wang, X., Kou, L., Zheng, L., Zhang, H.: Prediction of control parameters corresponding to in-flight particles in atmospheric plasma spray employing convolutional neural networks. *Surface and Coatings Technology* **394**, 125862 (2020)
36. Zhu, J., Wang, X., Kou, L., Zheng, L., Zhang, H.: Application of combined transfer learning and convolutional neural networks to optimize plasma spraying. *Applied Surface Science* **563**, 150098 (2021)