

Predictive 3D modelling of free oblique cutting introducing an ANN-based material flow law with experimental validation over a wide range of conditions

François Ducobu^{a,*}, Olivier Pantalé^b, Bert Lauwers^c

^a*Machine Design and Production Engineering Lab, Research Institute for Science and Material Engineering, UMONS, Belgium*

^b*Laboratoire Génie de Production, INP/ENIT, Université de Toulouse, Tarbes, France*

^c*Department of Mechanical Engineering, KU Leuven & Flanders Make@KU Leuven-MaPS, Belgium*

Abstract

Modelling of the cutting process needs to move from 2D to 3D configurations to get closer to industrial applications. This study introduces a predictive 3D finite element model of free orthogonal and oblique cutting with an Artificial Neural Network (ANN)-based material flow law and experimental validation in strictly the same conditions (cutting and geometrical). The flow law based on a neural network allows simulating the cutting process based on data coming from the material characterization tests without requiring any postulate concerning the expression of the flow law. The developments are applied to the formation of continuous chips for the titanium alloy Ti6Al4V and an unseen broad range of 36 cutting conditions is considered: 2 cutting edge inclinations, 3 uncut chip thicknesses and 6 cutting speeds. The predictive performance of the model (i.e., the evaluation of the trends of fundamental variables with the absence of tuning of both numerical parameters and model features when cutting conditions are significantly modified) is high for the forces, mainly cutting and passive, and the chip thickness ratio on all 36 cutting conditions. The accuracy of the main cutting force is excellent: the average difference with the experiments is 4 %, within the experimental dispersion. No significant degradation of the results is brought by the apparition of the third, out-of-plane, force, which shows the ability of the model to handle orthogonal and oblique cutting configurations.

*Corresponding author. Tel.: +32 65 45 68

Email address: Francois.Ducobu@umons.ac.be (François Ducobu)

Keywords:

Oblique cutting, Finite element method (FEM), Predictive model, Artificial Neural Network (ANN), Material flow law

1. Introduction

Selection of the tools and the cutting conditions in machining are still difficult to achieve because of the high level of complexity and the related nonlinear phenomena. Comprehension of the influence of the process parameters on the quality of a component and its optimization are also a challenge for the same reasons. In the frame of digital manufacturing and Industry 4.0, modelling the cutting process supports them, while remaining a challenging task. As highlighted by Arrazola et al. [1], most finite element (FE) models are developed in 2D (orthogonal cutting configuration usually) although industrial applications require 3D modelling.

The behaviour of the machined material is one of the key aspects of a FE model [1, 2]. Research is very intense in this area, leading to a growing number of constitutive material models ranging from empirical models to physical models, some including microstructure effects [2]. The empirical thermo-elasto-viscoplastic Johnson-Cook (JC) model [3] is still the most widely used to this day:

$$\sigma^y = \left(A + B \varepsilon^{p^n} \right) \left(1 + C \ln \frac{\dot{\varepsilon}^p}{\dot{\varepsilon}_0^p} \right) \left(1 - \left[\frac{T - T_{\text{room}}}{T_{\text{melt}} - T_{\text{room}}} \right]^m \right) \quad (1)$$

In this model, the flow stress, σ^y , is a function of the plastic strain, ε^p , the plastic strain rate, $\dot{\varepsilon}^p$, and the temperature, T . It is composed of 3 terms describing independently the plastic, viscous and thermal aspects. One of the points in favour of its adoption is the rather limited number of parameters to be identified, 5: A , B , C , m and n . Here, $\dot{\varepsilon}_0^p$ is the reference plastic strain rate, while T_{room} and T_{melt} are respectively the ambient (room) and melting temperatures. More recent models developed on this basis, such as that of Calamaz et al. [4], increase this number of parameters (for the particular Calamaz model to 9). Other authors have also used Zerilli-Armstrong model to simulate cutting processes [5]. The best description (in theory) of the behaviour is obtained at the cost of a greater complexity of the identification process and a reduction of the link with the physical meaning of the model.

One of the problems of modelling material behaviour for cutting simulation is the identification of parameters, especially as the experimental equipment does not allow the high levels of strain, strain rate and temperature of machining to be

31 achieved [2]. Inverse identification is an alternative, but the uniqueness of the so-
32 lution is not always guaranteed [1, 2]. Early work by Özel and Altan [6] used the
33 least squares method to identify the input parameters of a FE model in an inverse
34 manner. Shrot and Bäker [7] then used the Levenberg-Marquardt algorithm for
35 their identification of the material parameters. They showed that similar results
36 (cutting forces and chip morphology) could be obtained by different sets of pa-
37 rameters and thus highlighted the non-uniqueness of the solution of the inverse
38 problem. In addition to the flow stress parameters, Klocke et al. [8] also identi-
39 fied the damage parameters. In more recent work, such as Bosetti et al. [9] and
40 Denkena et al. [10], the approach to the inverse identification problem is shifting
41 from optimization to Artificial Intelligence (AI) based methods. The Downhill
42 Simplex Algorithm (DSA) is adopted by Bergs et al. [11] and by Hardt et al. [12]
43 for AISI 1045. Stampfer et al. [13] also chose DSA when treating AISI 4140
44 quenched at 3 different temperatures. In [14], Hardt et al. showed that Parti-
45 cle Swarm Optimization (PSO) was more efficient in solving the inverse problem
46 than DSA, even though the computational time is still significant. In order to re-
47 duce the computational time, an Efficient Global Optimization algorithm (EGO)
48 was recently introduced by Kugalur Palanisamy et al. [15]. They identified simul-
49 taneously the parameters of the material constitutive model and the friction model
50 for Ti6Al4V. The identified parameters showed good performance when applied
51 to a different FE model [16]. Most of these works highlight the non-uniqueness
52 of the identification and they all require the definition of the analytical expression
53 of the constitutive model.

54 ANN (Artificial Neural Network)-based material models have been introduced
55 to avoid postulating or knowing the analytical expression of the material be-
56 haviour. Gorji et al [17] recently reviewed the use of recurrent neural networks
57 for material models, while Jamli and Farid [18] reviewed their application in FE
58 simulation of material forming. When compared to classical analytical and em-
59 pirical models, such as JC model, they proved to be more powerful to represent
60 the experimental behaviour [19]. Use of these ANN-based models in FE simula-
61 tion of forming processes also turned out to provide better results than the classical
62 JC model [20] and to handle complex phenomena such as dynamic recrystallisa-
63 tion [21]. No application of these ANN-based models in FE simulation of cutting
64 currently exists.

65 Lagrangian and Eulerian formulations are the most used for FE modelling of
66 the cutting process. Combinations of formulations, such as Arbitrary Lagrangian-
67 Eulerian (ALE) and Coupled Eulerian-Lagrangian (CEL), are increasingly being
68 used to avoid (or reduce) mesh distortions [22]. The CEL formulation has recently

been successfully applied to the modelling of cutting (in 2D orthogonal configuration): it provides accurate results with realistic chip shape and no mesh distortion. The first 3D applications are found in recent works [23–27]. They cover orthogonal (free) cutting or a simple 3D operation, while free oblique cutting has yet to be studied.

Experimental validation of a model is a crucial step in modelling the cutting process. The experimental configuration should be as close as possible to the simulation. For the validation of orthogonal cutting, a rotational motion usually generates the cutting speed. This is often done in turning [28] or milling [23] and the diameter of the rotating workpiece must be large enough to reduce the influence of curvature on the results. Experimental configurations under strictly orthogonal cutting conditions are less often adopted, for example on broaching machines [29] or milling machines [30, 31]. If they remove the assumptions related to the rotary cutting motion, they generally allow lower cutting speeds (except on a dedicated machine, as in Afrasiabi et al. [32]). Free oblique cutting with a straight cutting edge has not yet been studied: all efforts have been concentrated on orthogonal cutting (mainly for validation of 2D FE models).

This paper fills the gap in the oblique cutting literature by investigating both orthogonal and free oblique 3D cutting configurations, both experimentally and numerically. An ANN, introduced in Pantalé et al. [33], is implemented in a FE cutting model for the first time in place of the JC analytical law. A wide range of cutting speeds (6), uncut chip thicknesses (3) and cutting edge inclination angles (2) resulting in 36 different conditions are considered to demonstrate the predictive capability of the FE model for the fundamental variables. The developments are applied to the formation of continuous chips of the titanium alloy Ti6Al4V.

2. Experimental setup

A 3-axis GF Mikron VCE 600 Pro milling machine is used to perform dry orthogonal and oblique cutting tests on Ti6Al4V (grade 5 annealed at 750 °C for 1 h followed by air cooling) with the same kinematics as a shaper. As shown in Figure 1, the tungsten carbide tool (modified LCGN160602-0600-FG, CP500 from SECO) is fixed on a dedicated holder (modified CFHN-06 from SECO) and the sample to be cut is clamped in the spindle (no rotation is allowed during the test). The top of the sample has 3 ribs of 1 mm width (the width of the tool is 6 mm) and 10 mm length. The test consists of removing the top layer (its height is the uncut chip thickness, h) of a rib at the prescribed cutting speed, v_c . The cutting speed is provided by the feed rate, v_f , of the machine (maximum value of 40 m/min). The

105 tool cutting edge inclination, λ_s , results from the relative angular orientation of
 106 the tool and the sample. Table 1 shows the cutting conditions: 6 cutting speeds, 3
 107 uncut chip thicknesses and 2 inclination angles, each repeated 3 times. An incli-
 108 nation angle of 6° is the typical value when turning Ti6Al4V, while cutting speeds
 109 and uncut chip thicknesses values in accordance with recommended ranges by
 110 SECO for the standard tool [34] are adopted.

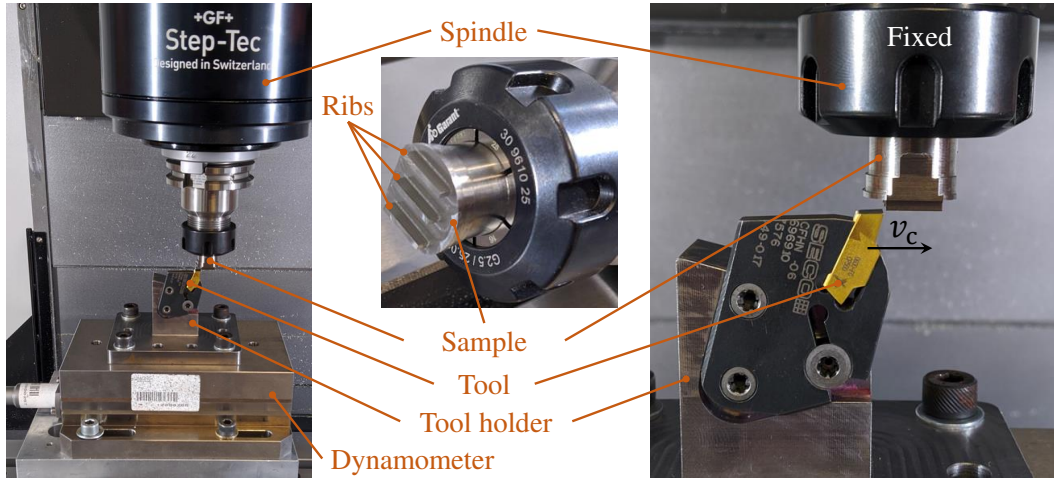


Figure 1: Experimental setup

Table 1: Cutting conditions of the study

Parameter	Values
Cutting speed, v_c (m/min)	5, 7.5, 10, 20, 30, 40
Uncut chip thickness, h (μm)	40, 60, 80
Cutting edge inclination, λ_s ($^\circ$)	0, 6
Width of the workpiece (mm)	1
Length of the workpiece (mm)	10
Width of the cutting edge (mm)	6 (1.1 in the model)
Cutting edge radius, r_β (μm)	20
Rake angle, γ_0 ($^\circ$)	15
Clearance angle, α_0 ($^\circ$)	2

111 Forces are measured with a 3-component Kistler 9257B dynamometer and

are amplified by a Kistler 5070A charge amplifier. Acquisition is performed at 3 kHz using a Kistler 5697A2 data acquisition system and DynoWare software. The recorded forces are then filtered with a second-order low-pass Bessel filter at 750 Hz before calculating the average value of the steady state signal.

All chips are collected and observed with a Dino Lite digital microscope AM7013MZT (5 MP, magnification 20× – 250×). Each chip is measured 3 times along its length in order to obtain an average value representative of the whole chip.

3. Finite element model

3.1. Modelling choices

The main objectives of a predictive model are the accurate modelling of trends in results as conditions change and the good agreement of predicted values with experimental values (exact values are not expected due to experimental dispersions of at least 10 % around the mean values). This type of model is intended to support future choices and developments without the need for experimental data. No assumptions are made about the geometry of the workpiece in the model (i.e., its width is the same as in experiments), while keeping the calculation time relevant for industrial applications. The CEL formulation is adopted to model the dry orthogonal and free oblique cutting tests with Abaqus/Explicit 2020. The 3D model is composed of a fixed Lagrangian tool and a Eulerian part (Figure 2). Chip formation occurs by plastic flow through the Eulerian domain without mesh distortion. The Eulerian formulation allows for chip formation without damage properties, by removing modelling assumptions. These two features contribute to the cutting models providing accurate results and realistic chips [22].

As shown in Figure 3, the full width of the workpiece (1 mm), i.e., one rib in the experiments, is modelled. To allow for chip formation and lateral flow, the Eulerian domain is wider (it includes the volume in which the material can move). The volume above the initial part is also meshed with Eulerian elements for the same reasons. As in the experiments and to satisfy the assumption of an orthogonal and oblique free cut, the tool is wider than the workpiece (it is 1.1 mm in the model and 6 mm in the experiments). It is very important to note that the models are the same for both inclination angles: they differ only in the rotation of the tool by 6° around the Y axis as in the experiments (Figure 3). This, together with the absence of assumptions when developing the models, contributes to make the models predictive: no input is changed when the cutting conditions are changed.

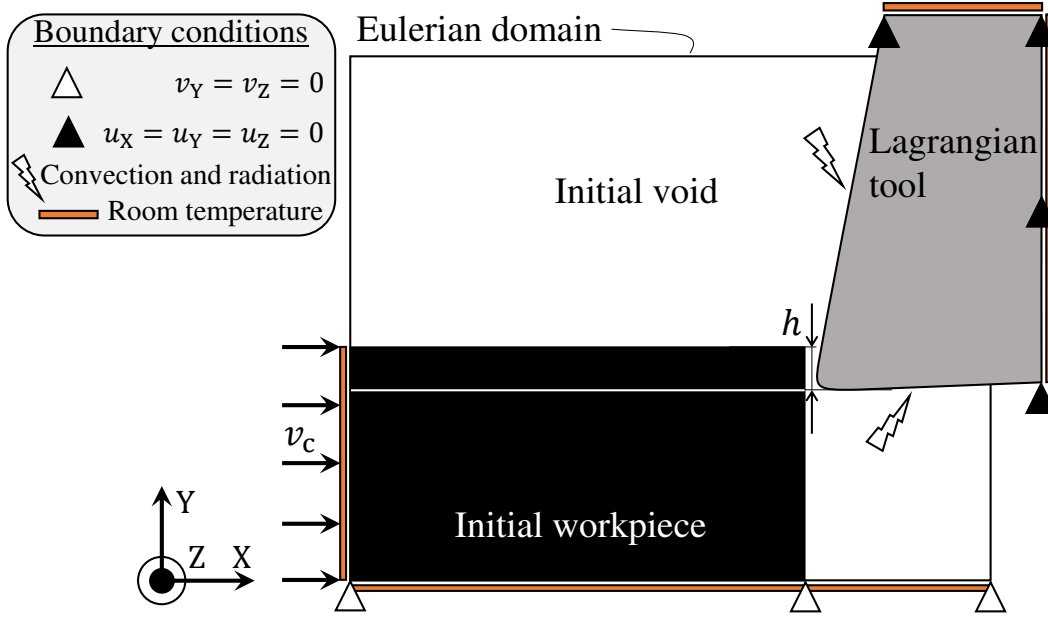


Figure 2: Boundary conditions and schematic initial geometry of the model

148 According to a previous sensitivity study of the mesh in orthogonal cutting
 149 with the CEL formulation [24], the edge size of the elements is $5\mu\text{m}$ in the
 150 plane parallel to the cutting speed. In the direction perpendicular to this plane,
 151 it is $5\mu\text{m}$ in the areas close to the lateral boundaries of the Eulerian domain
 152 and $50\mu\text{m}$ in the middle of the part. To reduce the computation time, the size
 153 of the model depends on the value of the uncut chip thickness. This results
 154 in a Eulerian domain (EC3D8RT 8-node 3D linear Eulerian elements, coupled
 155 mechanical-thermal behaviour and reduced integration) composed of 216 550 to
 156 273 350 nodes and a Lagrangian domain (C3D8T 8-node 3D linear Lagrangian
 157 elements, coupled mechanical-thermal behaviour) of 4650 nodes.

158 The Ti6Al4V part is assumed to be thermo-elasto-viscoplastic (isotropic) and
 159 the inelastic thermal fraction is 0.9. The JC parameters set of Seo et al. [35]
 160 is adopted because the value of A corresponds to the value of the typical yield
 161 strength of Ti6Al4V and this set was found to provide the best results among the
 162 20 sets available in the literature [36]. The TiN coated tungsten carbide (WC) tool
 163 is assumed to have linear elasticity. The material properties are given in Table 2.

164 According to the experimental results of Rech et al. [39], it is assumed that
 165 Coulomb friction occurs at the tool-piece interface and that the coefficients of

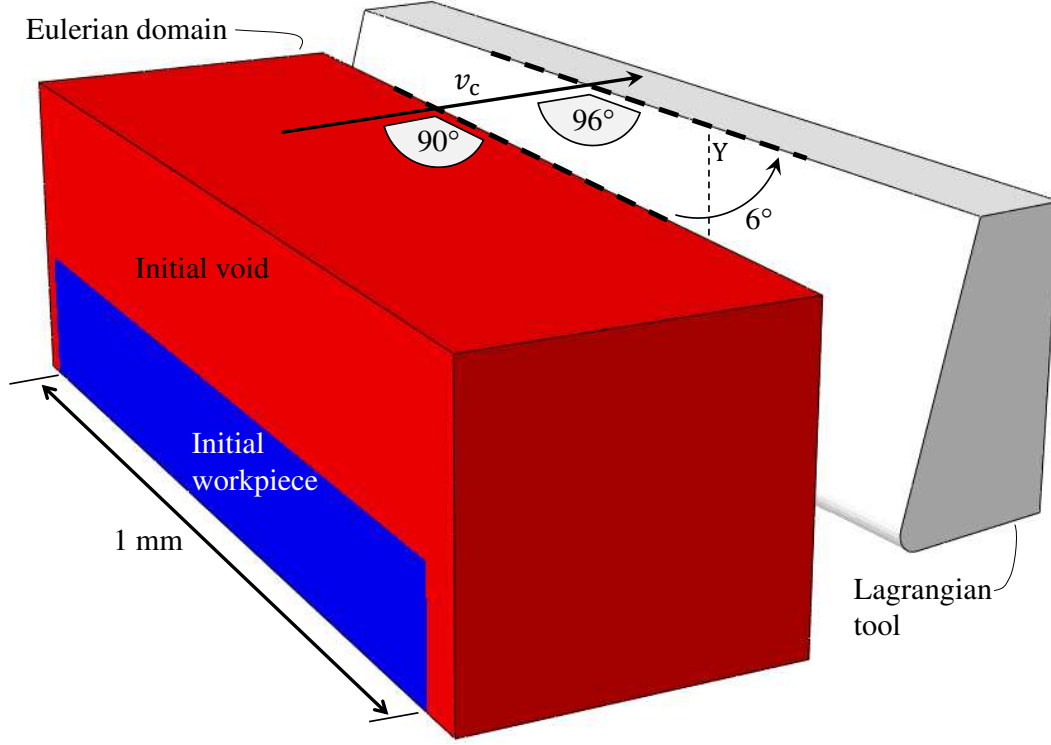


Figure 3: Configuration of the FE model for $\lambda_s = 6^\circ$

friction, μ , and heat partition, β , depend on the cutting speed. The limiting shear stress, τ_{\max} , is included and is given by:

$$\tau_{\max} = \frac{\text{yield stress}}{\sqrt{3}} = \frac{A}{\sqrt{3}} \quad (2)$$

All the friction energy is converted into heat. Table 3 shows the friction coefficients adopted in this study.

An ambient temperature of 293 K is imposed on the top and right surfaces of the tool and on the left and bottom surfaces of the workpiece (Figure 2). It is assumed that radiation and convection occur on the rake and clearance faces of the tool. The initial temperature of the tool and workpiece is set to the room temperature (293 K). The heat transfer coefficients are provided in Table 3.

3.2. Material model of Ti6Al4V

The material model of Ti6Al4V used in all the numerical simulations proposed in the section 4 is a thermo-elasto-viscoplastic law using a flow criterion

Table 2: Materials properties [35, 37, 38]

Young's modulus, E (GPa)	Ti6Al4V	113.8 [†]
	WC	650
Poisson's ratio, ν	Ti6Al4V	0.34
	WC	0.2
Density, ρ (kg/m ³)	Ti6Al4V	4430
	WC	14 850
Conductivity, k (W/m K)	Ti6Al4V	6.3 [†]
	WC	100
Expansion, α (1/K)	Ti6Al4V	8.6E−6 [†]
	WC	5E−6
Specific heat, c_p (J/kg K)	Ti6Al4V	531 [†]
	WC	202
JC flow stress	A (MPa)	997.9
	B (MPa)	653.1
	C	0.0198
	m	0.7
	n	0.45
	$\dot{\epsilon}_0$ (1/s)	1
	T_{room} (K)	293
	T_{melt} (K)	1873

[†]: Dependence on the temperature, value provided at 293 K

178 based on an Artificial Neural Network (ANN) identified for the chosen material
179 and implemented in the Abaqus/Explicit code via a Fortran subroutine VUHARD
180 as proposed by Pantalé et al. in [33]. The principle of this approach consists in
181 replacing the analytical formulation of the flow law, based on a Johnson-Cook or
182 Zerilli-Armstrong type model, and allowing the calculation of the flow stress σ^y
183 as a function of the plastic strain ϵ^p , the plastic strain rate, $\dot{\epsilon}^p$, and the temperature
184 T , by a multi-layer ANN serving as universal approximator. Thus, the parameters
185 of the neural network can be directly identified from the experimental data with-
186 out having to postulate a behavioural model, which simplifies the procedure and
187 allows greater flexibility in the definition of the model. The proposed approach
188 also allows, as shown in Pantalé et al. [33], to compute the three derivatives of the
189 flow stress σ^y with respect to the three input variables of the model, a necessary
190 step to implement this model as a flow law in the form of a VUHARD subroutine

Table 3: Friction and heat transfer coefficients [37, 39]

Cutting speed, v_c (m/min)	μ	β
5	0.24	1
7.5	0.22	0.89
10	0.21	0.80
20	0.19	0.63
30	0.18	0.55
40	0.17	0.50
Limiting shear stress, τ_{\max} (MPa)	576	
Convection, U (W/m ² K)	50	
Radiation, ϵ	0.3	

191 in the FEM code Abaqus/Explicit, using the exact same network architecture and
 192 identified trained parameters as the one used to compute the flow stress σ^y .

193 In order to verify the influence of the neural network complexity on the nu-
 194 merical results of the simulation and on the computation time, several ANN archi-
 195 tectures are tested afterwards (in 3.4). The chosen global architecture has 2 hidden
 196 layers with a variable number of neurons for the first hidden layer ($\zeta = 9$ to 17)
 197 and 7 neurons for the second hidden layer, 3 inputs (the plastic strain, ε^p , the plas-
 198 tic strain rate, $\dot{\varepsilon}^p$, and the temperature, T) and one output (the yield strength, σ^y).
 199 The global architecture of this type of ANN is given in Figure 4 for 9 neurons in
 200 the first hidden layer. According to Pantal  et al. [33], this ANN is referred to as
 201 ANN 3-9-7-1-sig, as it has 3 inputs, 9 neurons in the first hidden layer, 7 neurons
 202 in the second hidden layer, 1 output and a sigmoid activation function.

203 In a preliminary phase, after having selected the global architecture of the neu-
 204 ral network, it is necessary to proceed to its training from some inputs. The inputs
 205 for this application were generated from the Johnson-Cook flow law expression
 206 reported in Equation (1) and the identified parameters reported in Table 2. This
 207 approach was chosen to demonstrate the ability of the neural network flow law to
 208 replace a classically formulated flow law such as Johnson-Cook’s for the simu-
 209 lation of metal cutting. In future developments, experimental tests on a Gleeble
 210 thermomechanical simulator will be used to generate this network training data.
 211 The training data, presented in the form of a data table containing the plastic strain
 212 ε^p , the plastic strain rate $\dot{\varepsilon}^p$, the temperature T and the flow stress σ^y , is processed

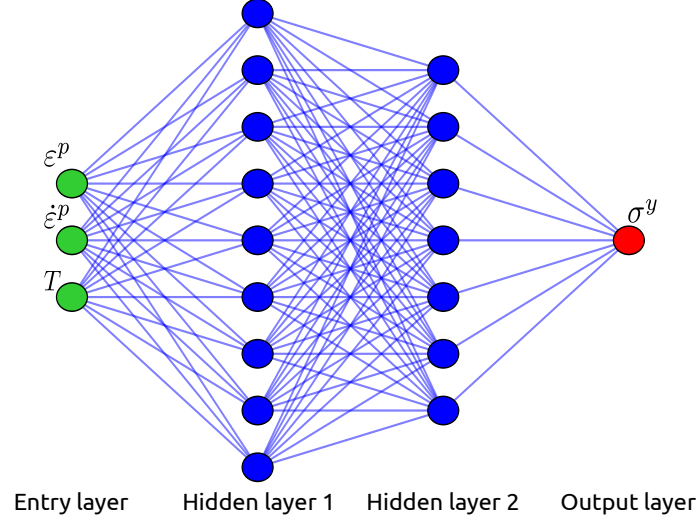


Figure 4: Architecture of the ANN 3-9-7-1-sig used for the flow law

213 by a learning algorithm, developed at LGP, in Python, using the Tensorflow li-
 214 brary. One hour of training on a Dell XPS13 7390 laptop running Ubuntu 20.04
 215 64 bits with 16 GiB of Ram and an Intel 4-core i7-10510U processor allow ob-
 216 taining the converged parameters of the ANN model.

217 Once this learning phase is completed, the neural network parameters result-
 218 ing from the learning process are used directly by a Python program, in charge
 219 of automatically generating the Fortran source code of the VUHARD subroutine
 220 in order to compute the flow stress σ^y and its three derivatives, required for the
 221 explicit Abaqus FEM code.

222 The main advantage of this approach (the use of an ANN), after the learning
 223 phase, is that, for example, the output σ^y of the network is now linked to the inputs
 224 ε^p , $\dot{\varepsilon}^p$, and T by the equations (3) to (7) for a two hidden layers neural network
 225 with a sigmoid activation function as proposed previously.

226 Thus, in the VUHARD subroutine, the computation of the flow stress σ^y from
 227 the 3 input variables ε^p , $\dot{\varepsilon}^p$, and T is performed using the following procedure.
 228 The first step is to scale the input data to the interval $[0, 1]$ using the following
 229 equation:

$$\vec{x} = \begin{cases} x_1 = \frac{\varepsilon^p - [\varepsilon^p]_{min}}{[\varepsilon^p]_{max} - [\varepsilon^p]_{min}} \\ x_2 = \frac{\ln(\dot{\varepsilon}^p) - [\ln(\dot{\varepsilon}^p)]_{min}}{[\ln(\dot{\varepsilon}^p)]_{max} - [\ln(\dot{\varepsilon}^p)]_{min}} \\ x_3 = \frac{T - [T]_{min}}{[T]_{max} - [T]_{min}} \end{cases} \quad (3)$$

where quantities $[]_{min}$ and $[]_{max}$ are the boundaries of the range of the corresponding field during the training phase. Corresponding values, for the proposed case, are given in Appendix A. According to the architecture of the network, the outputs of the neurons of the first hidden layer \vec{y}_1 are given by the following equation:

$$\vec{y}_1 = \text{sig}\left(\mathbf{w}_1 \cdot \vec{x} + \vec{b}_1\right) \quad (4)$$

where, \mathbf{w}_1 and \vec{b}_1 are the weights and biases associated with the first hidden layer and $\text{sig}()$ is the sigmoid activation function defined by the equation (5) :

$$\text{sig}(x) = \frac{1}{1 + e^{-x}} \quad (5)$$

Then, the output of the neurons of the second hidden layer is given by the equation (6) :

$$\vec{y}_2 = \text{sig}\left(\mathbf{w}_2 \cdot \vec{y}_1 + \vec{b}_2\right) \quad (6)$$

where, \mathbf{w}_2 and \vec{b}_2 are the weights and biases associated with the second hidden layer. Finally, the σ^y output of the ANN is thus given by the equation (7) :

$$\sigma^y = ([\sigma^y]_{max} - [\sigma^y]_{min})\left(\vec{w}^T \cdot \vec{y}_2 + b\right) + [\sigma^y]_{min} \quad (7)$$

where, \vec{w} and b are the weights and the bias associated with the output layer.

On the other hand, the three derivatives of the yield stress σ^y with respect to the three input variables ε^p , $\dot{\varepsilon}^p$, and T are given by the equation (8):

$$\begin{cases} \partial\sigma^y/\partial\varepsilon^p = s'_1 \frac{[\sigma^y]_{max} - [\sigma^y]_{min}}{[\varepsilon^p]_{max} - [\varepsilon^p]_{min}} \\ \partial\sigma^y/\partial\dot{\varepsilon}^p = s'_2 \frac{[\sigma^y]_{max} - [\sigma^y]_{min}}{[\dot{\varepsilon}^p]_{max} - [\dot{\varepsilon}^p]_{min}} \\ \partial\sigma^y/\partial T = s'_3 \frac{[\sigma^y]_{max} - [\sigma^y]_{min}}{[T]_{max} - [T]_{min}} \end{cases} \quad (8)$$

where s'_i is the i^{th} component of the vector \vec{s}' defined by the equation (9):

$$\vec{s}' = \mathbf{w}_1^T \cdot \left[\mathbf{w}_2^T \cdot \left(\frac{\vec{w} \circ e^{-\vec{y}_2}}{[1 + e^{-\vec{y}_2}]^2} \right) \circ \left(\frac{e^{-\vec{y}_1}}{[1 + e^{-\vec{y}_1}]^2} \right) \right] \quad (9)$$

and \circ is the elements-wise product, known as the Hadamard product. In equations (3) to (9), quantities \mathbf{w}_1 , \mathbf{w}_2 , \vec{w} , \vec{b}_1 , \vec{b}_2 and b are evaluated by the training

247 procedure of the ANN. Corresponding values for an ANN containing 9 neurons
 248 in the first hidden layer and 7 neurons in the second hidden layer are reported in
 249 Appendix A. The set of equations (3) to (9), together with the network param-
 250 eters identified in the learning phase, is automatically translated into a VUHARD
 251 Fortran subroutine used by the FEM code Abaqus to simulate the cutting model.

252 Because of the large number of identified parameters for all the ANN models
 253 (from 114 to 202 for 9 and 17 neurons for the first hidden layer, respectively), the
 254 other 4 sets of ANN parameters used in this publication can be found in [40].

255 3.3. Sensitivity study of the results to mass scaling

256 FE modelling of the cutting process is very expensive in terms of CPU time
 257 due to the coupling of many nonlinear phenomena and the large amount of tiny
 258 finite elements. Mass scaling (MS) is introduced into the model to reduce the CPU
 259 computation time while checking that it does not influence the results (forces and
 260 energies) via a mass scaling sensitivity study. MS factors, MS_f , ranging from
 261 1E6 (theoretical CPU time scale of $\sqrt{MS_f} = 1000$) to 1 (no scale) were used for
 262 a cutting condition ($\lambda_s = 0^\circ$, $v_c = 30$ m/min and $h = 60$ μ m). The same signal
 263 processing procedure is applied to the numerical forces as to the experimental
 264 forces (cf. 2): they are filtered with a second-order low-pass Bessel filter at 750 Hz
 265 before calculating the steady state average value. Table 4 gives the results of the
 266 model with MS normalized (\hat{F}_i) by those of the model without MS:

$$\hat{F}_i = \frac{F_i \text{ with MS}}{F_i \text{ without MS}} \quad (10)$$

267 with $i = c$ for the cutting force and $i = f$ for the feed force. As expected, the
 268 real speed-up does not increase linearly with the MS_f , but it remains significant.
 269 A MS_f of 1E6 leads to an unstable computation and a MS_f of 1E5 leads to erratic
 270 force evolutions. These results are confirmed by high values of the ratio of the
 271 kinetic (KE) to the internal (IE) energies (it should not exceed a few % [41, 42]).
 272 A value of MS_f of 1E3 is chosen as it offers a good balance between reducing the
 273 computation time and the impact on the forces, while keeping the $\frac{KE}{IE}$ below 1 %.
 274 To provide an order of magnitude of CPU computation time, between 10 h and
 275 50 h (depending on the value of h) are required on 4 cores of an Intel i7-5700HQ
 276 CPU at 2.7–3.5 GHz.

277 3.4. Sensitivity study of the results to the number of neurons

278 The number of neurons in the hidden layers may influence the results. A
 279 sensitivity study on the number of neurons of the first hidden layer, ζ , is performed

Table 4: MS sensitivity study (selected MS factor, MS_f , in bold, \hat{F}_c : normalized cutting force, \hat{F}_f : normalized feed force, KE : kinetic energy, IE : internal energy)

MS_f	CPU scaling	Speed-up	\hat{F}_c	\hat{F}_f	$\frac{KE}{IE}$ (%)
1	1	1	1	1	2.3E−4
1E2	10	9	1.006	0.982	2.2E−2
1E3	32	21	1.008	0.940	2.2E−1
1E4	100	61	1.012	0.921	2.4
1E5	316	173	Erratic	Erratic	22
1E6	1000	207	Unstable	Unstable	58

in order to select the ANN offering the best balance between CPU computation time and quality of the results. The results of the study are provided in Table 5. \check{F}_i corresponds to the results of the model with ANN normalized by those of the model with the built-in JC model:

$$\check{F}_i = \frac{F_i \text{ with ANN}}{F_i \text{ with JC}} \quad (11)$$

They show no influence on the numerical results for the forces compared to the built-in Johnson-Cook model, only the computation time is influenced by the number of neurons in the first hidden layer and increases with it. This increase in computation time is not only due to the increasing complexity of the neural network with the number of neurons, but also to the need to go through a VUHARD user subroutine. A first hidden layer of 9 neurons is therefore selected as it leads to the smallest increase in CPU computation time, without influence on the final result.

4. Experimental and numerical results

An example of the temporal evolution of the numerical and experimental forces is plotted for the 3 directions in Figure 5 at $\lambda_s = 6^\circ$, $v_c = 10$ m/min and $h = 40$ m/min. The FE models are calculated up to a few microseconds after the stationary state is reached. Then, a linear extrapolation (dashed line between the last two markers in Figure 5) is used to provide numerical values for the same time range as the experimental values. The average and standard deviation (2σ) are calculated from the 3 experimental values. The resulting dispersion is shown in Figure 5 around the average values of each force. Steady state takes longer to

Table 5: Sensitivity of the forces to the number of neurons of the first layer, ζ (selection in bold, \check{F}_c : normalized cutting force, \check{F}_f : normalized feed force)

ζ	Time increase (%)	\check{F}_c	\check{F}_f
Built-in	0	1.000	1.000
9	6	1.000	0.999
11	6	1.001	1.000
13	7	1.000	0.998
15	8	1.001	1.001
17	10	1.000	1.000

be reached for the experiments than for the numerical model, in particular for the cutting force. The dispersion around the evolution of the average force is greater for the feed force than for the cutting force, while the average value of the feed force is 46 % of the average value of the cutting force. The numerical cutting force is very close to the experimental average cutting force; it is only 4 % higher. This difference, Δj , is calculated by :

$$\Delta j = \frac{|j^{(\text{sim})} - j^{(\text{exp})}|}{j^{(\text{exp})}} \times 100 \quad (12)$$

where j is the cutting force, the feed force, the passive force or the chip thickness. $j^{(\text{sim})}$ is the average value from the simulation, while $j^{(\text{exp})}$ is the average experimental value.

The numerical feed force is underestimated by the model, but is within the 95 % experimental confidence interval. The numerical passive force difference is also underestimated and is not within the narrower experimental dispersion. The difference between the average values of the experimental and numerical feed and passive forces is 25 %. A less well modelled feed force than the cutting force is typical of FE models of the cutting process and the difference with the experimental value is similar to other studies for a narrower range of cutting conditions [32, 43–46]. Hardt and Bergs [27] also obtained larger differences for feed and passive force than for cutting force. The difference for passive force was higher than for feed force, which is the opposite observation of this work.

Numerical chips at $v_c = 10$ m/min and $h = 40$ μm for $\lambda_s = 0^\circ$ and $\lambda_s = 6^\circ$ are provided in Figures 6 and 7. When the inclination of the cutting edge is 0° , both sides of the chip are identical and a symmetry plane can be drawn in the middle of

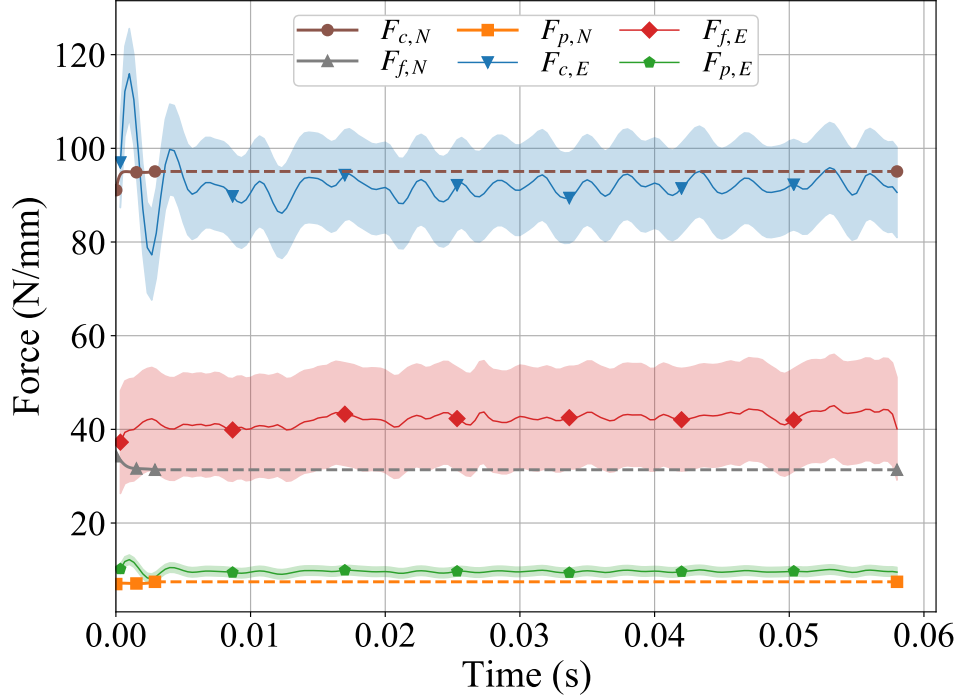


Figure 5: Temporal evolutions of experimental (E) and numerical (N) forces at $\lambda_s = 6^\circ$, $v_c = 10$ m/min and $h = 40$ μ m with dispersion around average experimental values (linear extrapolation of numerical values in dashed)

the workpiece (Figure 7 (a)). On the other hand, for an inclination of the cutting edge of 6° , the chip is no longer aligned with the workpiece. The chip bends to one side due to the orientation of the tool and symmetry is lost in both the geometry and the thermal and mechanical fields, as shown in figure 7 (b). This produces helical chips for the inclination angle of 6° as in the experiments. Figure 8 shows the variation of the chip thickness across its width: it is thicker in the middle (i.e., the body of the chip) than on its sides. This underlines the importance of 3D modelling, even for the orthogonal cutting configuration as highlighted earlier [24]. The 3D modelling also allows reproducing the lateral flow that occurs in the experiments for both values of cutting edge inclination (Figure 6), unlike a 2D model [23–25]. Although this leads to higher computation times, future cutting models should be in 3D, even when orthogonal cutting is considered. In this

case, it is recommended to take advantage of the symmetry of the configuration to reduce the computation time. This simplification has not been included in this study to avoid any difference in the FE models between the 2 inclinations of the cutting edge.

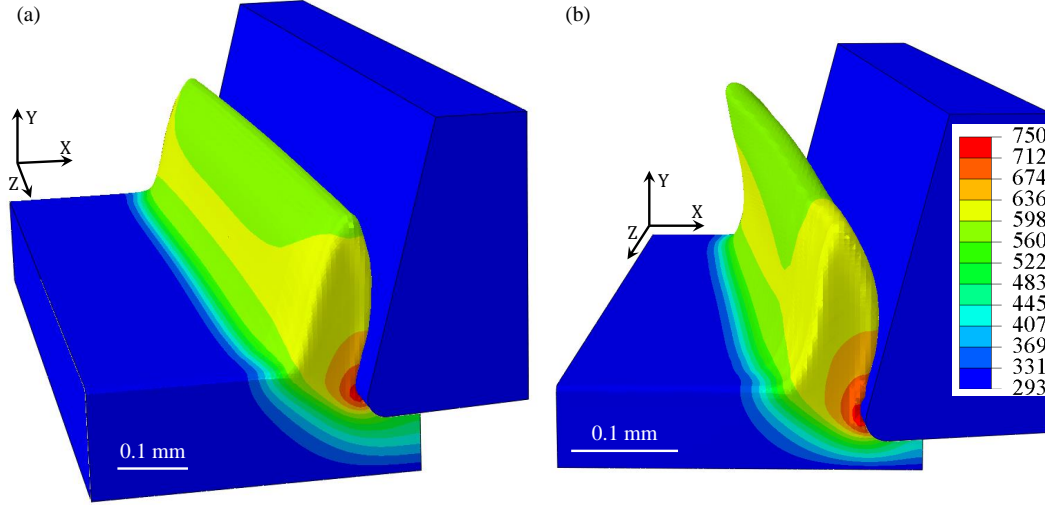


Figure 6: Temperature contours (in K) of the numerical chip after 1.5 ms at $v_c = 10$ m/min, $h = 40$ μ m and (a) $\lambda_s = 0^\circ$, (b) $\lambda_s = 6^\circ$

Average values of the experimental forces and their dispersion are shown in Figures 9 to 13 together with the average numerical values. Passive force values are of course only plotted for $\lambda_s = 6^\circ$ as they are equal to zero when $\lambda_s = 0^\circ$.

The increase in cutting force with uncut chip thickness is clearly observed in Figures 9 and 10 for both experimental and numerical results at the 2 inclination angles, as well as the decrease in force with increasing cutting speed. This shows that temperature softening dominates strain rate hardening for Ti6Al4V and is accurately modelled. Increasing the inclination angle from 0° to 6° slightly reduces the cutting force; this is well captured by the model. For cutting speeds of 20–40 m/min and an inclination angle of 0° , F_c is almost constant with cutting speed for uncut chip thicknesses of 40 μ m and 60 μ m, while it decreases slightly for 80 μ m; this small stabilization is less marked for the model.

An increase in the deviation around the average value with the cutting speed is noted for values above 10 m/min. All numerical values are within 95 % confidence of the experiments (35 of the 36 conditions are within 68 % confidence). The average difference with the experiments is 4 %, which is remarkable, also

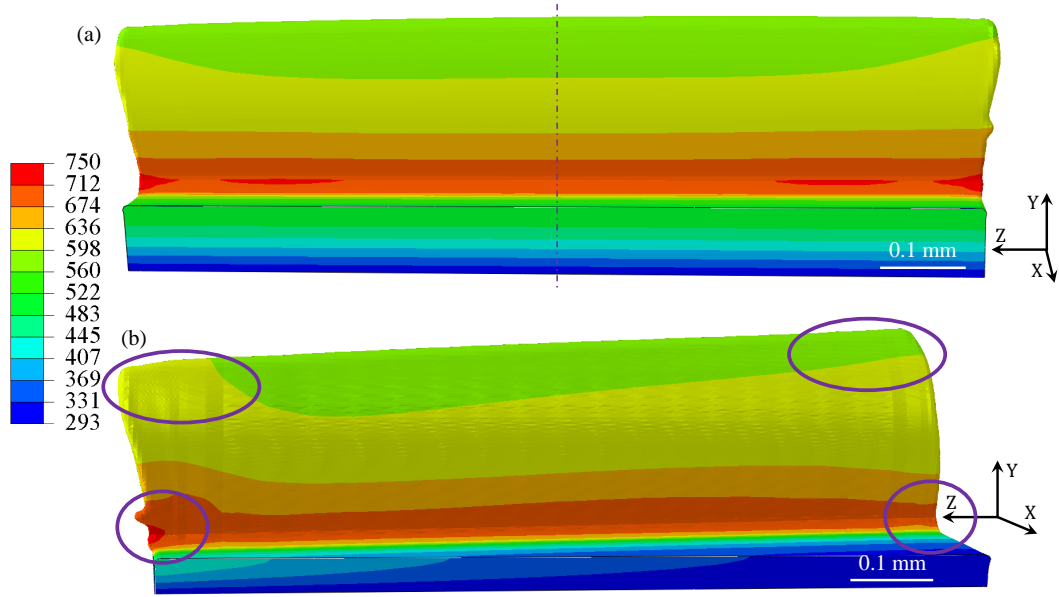


Figure 7: Temperature contours (in K) of the back of the numerical chip (tool is removed) after 1.5 ms at $v_c = 10$ m/min, $h = 40$ μ m and (a) $\lambda_s = 0^\circ$, (b) $\lambda_s = 6^\circ$

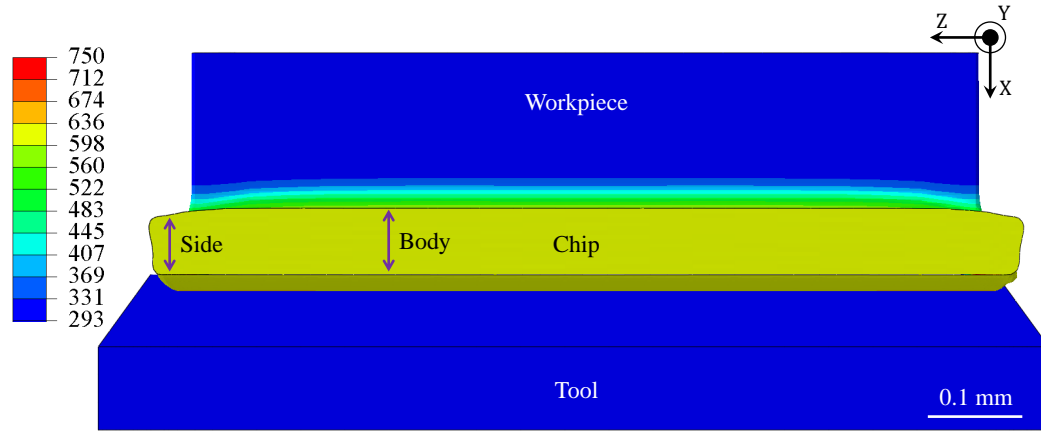


Figure 8: Temperature contours (in K) of the top of the numerical chip after 1.5 ms at $v_c = 10$ m/min, $h = 40$ μ m and $\lambda_s = 0^\circ$

354 considering the wide range of cutting conditions considered and the absence of
 355 model tuning. This underlines the predictive ability and accuracy of the FE model
 356 for both inclination angles.

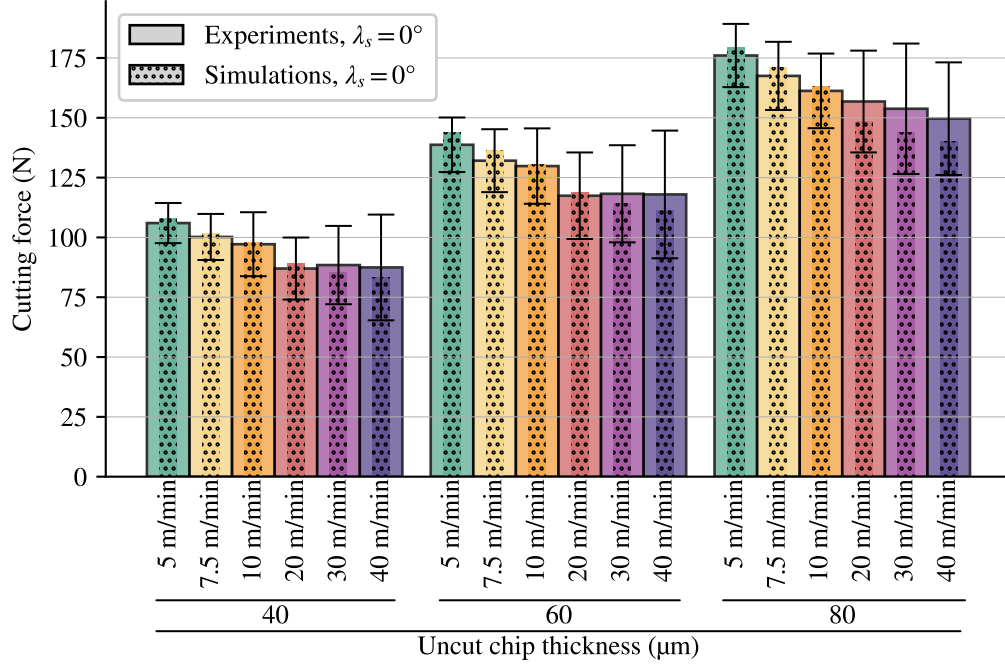


Figure 9: Comparison of experimental and numerical cutting forces at the cutting edge inclination of 0° for the 3 uncut chip thicknesses and the 6 cutting speeds

357 Figures 11 and 12 show the results for the feed force, where the two clearest
 358 trends for the experiments are its decrease with the inclination angle and its in-
 359 crease with the uncut chip thickness (even though it is lower than expected). For
 360 $80 \mu\text{m}$, F_f decreases overall with v_c in the experiments. For $40 \mu\text{m}$ and $60 \mu\text{m}$, the
 361 force decreases at lower v_c , then increases for 0° , while a decrease is observed at
 362 all v_c for 6° (the experimental dispersion is high for both inclination angles, but the
 363 average trend with cutting speed is clear at 6° , not at 0°). For the numerical values,
 364 the overall trend is the same for the 3 uncut chip thicknesses and the two inclina-
 365 tion angles: a decrease for the lowest values of v_c and then an increase. It should
 366 be noted that the numerical model does not correctly handle the trends of the feed
 367 forces: as Figure 12 clearly shows, the numerical forces have an overall increas-
 368 ing trend with the cutting speed, while their average value mainly decreases when
 369 the uncut chip thickness increases. The differences between the average numeri-
 370 cal and experimental values increase with the uncut chip thickness: the forces are
 371 closer at $40 \mu\text{m}$ than at $80 \mu\text{m}$. The numerical values are generally not within the
 372 95 % confidence interval (they do not clearly change with the cutting conditions).

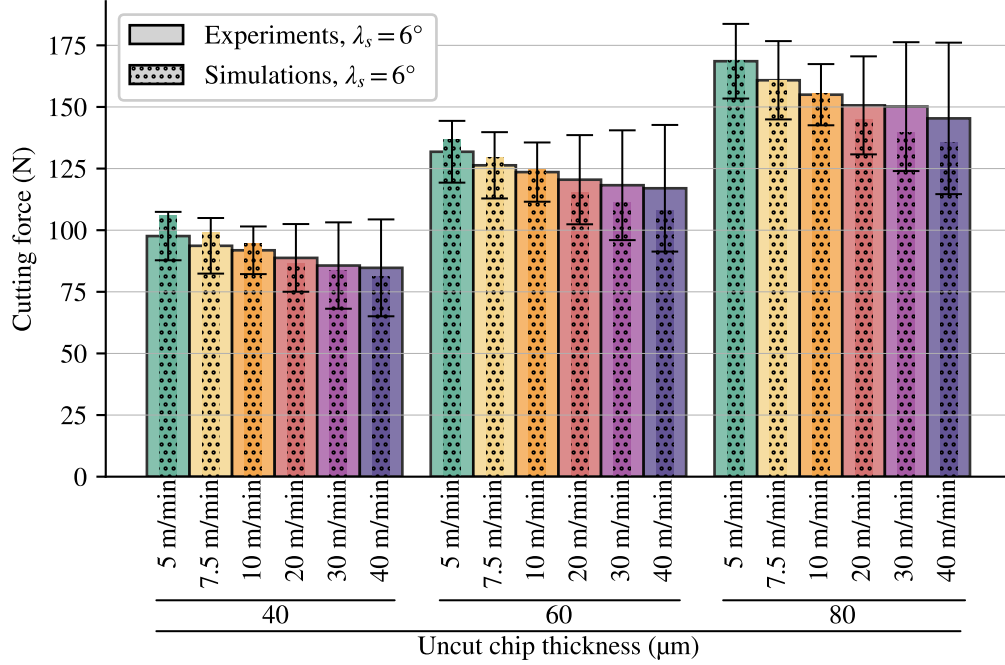


Figure 10: Comparison of experimental and numerical cutting forces at the cutting edge inclination of 6° for the 3 uncut chip thicknesses and the 6 cutting speeds

373 Coupled with the differences in trends, this shows that F_f is less well modelled
374 (the average difference is 39 %) than F_c as usual in FE modelling of the cutting
375 process and even more so in 3D [27]. The influence of the uncut chip thickness
376 on the feed force should therefore be improved. The parameters of the material
377 model are known to have an impact on the forces (and on the chip morphology)
378 [15, 36]. The friction model should also be improved to strengthen the results
379 [27].

380 The passive force is non-zero for the inclination angle of 6° (Figure 13). Like
381 the cutting force, it increases with the uncut chip thickness and decreases with
382 the cutting speed. The comparison with experiments is broadly the same as for
383 F_c , except for a greater difference in the magnitude of F_p (the average difference
384 is 26 %, but it is small in absolute terms – less than 5 N). Most of the numerical
385 values do not fall within the experimental 95 % confidence interval. A lower mag-
386 nitude of the passive force from the simulation than from the experiments with
387 the correct trends when the cutting conditions change was also observed by Hardt
388 and Bergs [27]. The differences were mainly attributed to differences in cutting

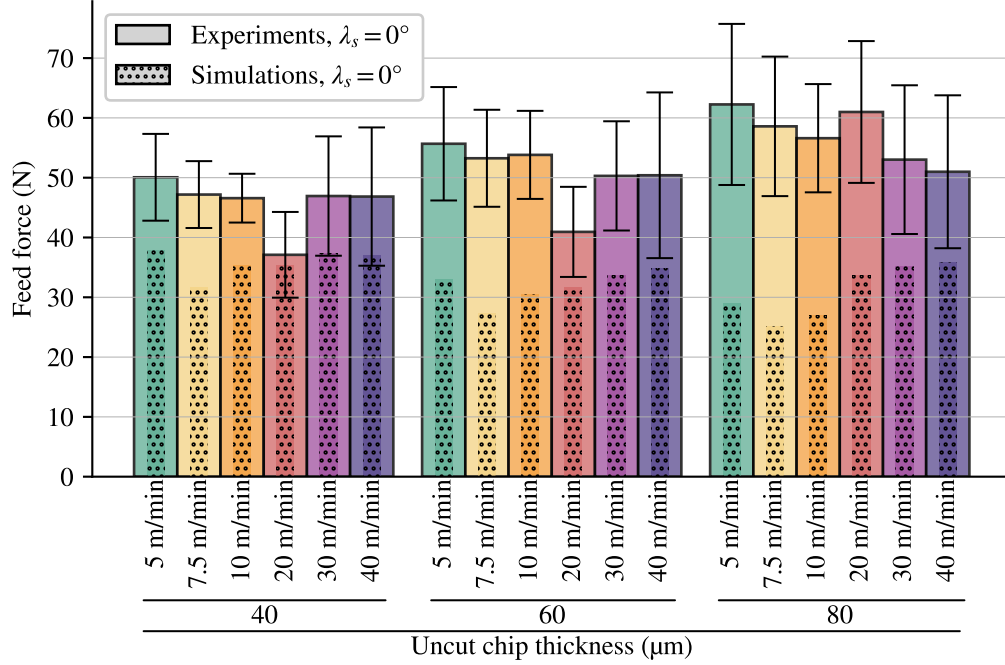


Figure 11: Comparison of experimental and numerical feed forces at the cutting edge inclination of 0° for the 3 uncut chip thicknesses and the 6 cutting speeds

edge radius, friction modelling and material model. In this work, the impact of the cutting edge radius can be neglected as it is the same in the model as in the experiments.

As far as the chip morphology is concerned, all chips are continuous. For both the simulation and the experiments, the chip thickness ratio, λ_h :

$$\lambda_h = \frac{h'}{h} \quad (13)$$

with h the uncut chip thickness and h' the chip thickness, is almost independent of the uncut chip thickness (Figures 14 and 15). It is slightly reduced from $\lambda_s = 0^\circ$ to $\lambda_s = 6^\circ$, which means that the chip thickness decreases with the inclination angle. This influence is underestimated by the model: the reduction of λ_h is smaller than in the experiments. The average difference between the experimental and numerical λ_h is 17 % over the whole range of cutting conditions. The chip thickness ratio decreases with cutting speed due to the reduction in friction, which is correctly accounted for by the model. As with the feed force, the results should be improved

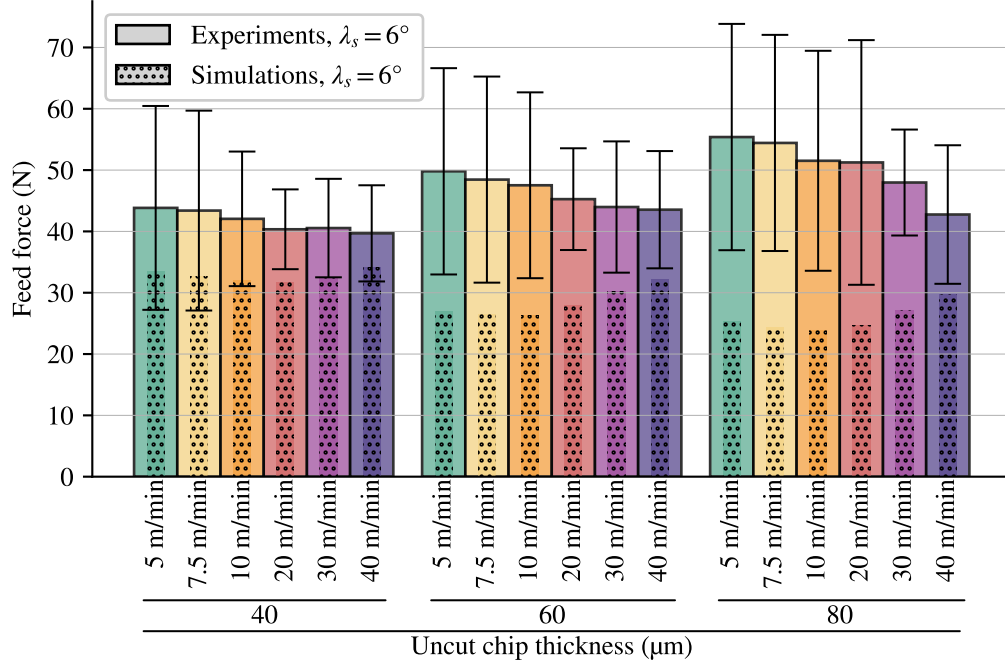


Figure 12: Comparison of experimental and numerical feed forces at the cutting edge inclination of 6° for the 3 uncut chip thicknesses and the 6 cutting speeds

by more complex friction models and a set of material parameters for which the identification includes forces and chip thickness: [15].

The differences calculated according to the equation (12) are presented in Table 6 to provide a quantitative overview of the results. The cutting force is the best modelled quantity as observed in the literature. This result was to be expected as the parameter set of the material model was selected mainly due to its good approximation of the cutting force [36]. As this selection was made with a 2D model, the results show the ability of the model to correctly handle the third (passive) force. Based on the average differences, the performance of the model is very close for the cutting and feed forces for both cutting edge inclinations, although a small degradation (1 % and 2 %, respectively) is noted for 6° . This degradation is more important (7 %) for the chip thickness ratio and must be linked to the difference in passive force. Indeed, the chip thickness and out-of-plane force models are deeply linked. Improving the friction at the tool-workpiece interface should be a key point. It should be noted that the chip thickness is very well modelled under certain cutting conditions with a minimum difference of 2 %. The difference

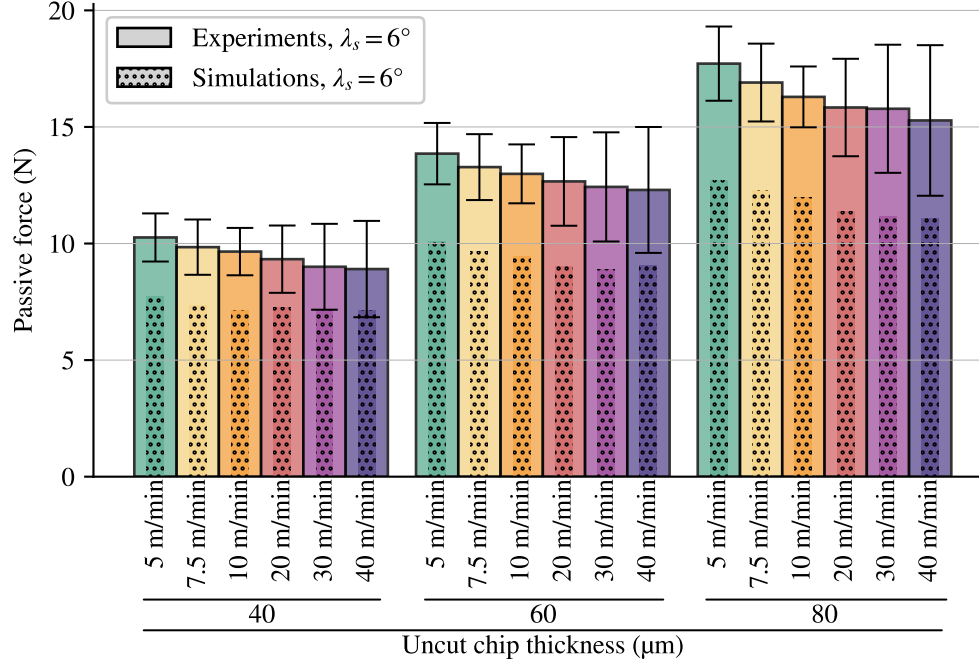


Figure 13: Comparison of experimental and numerical passive forces at the cutting edge inclination of 6° for the 3 uncut chip thicknesses and the 6 cutting speeds

is larger for the feed force than for the passive force, a trend opposite to that of Hardt and Bergs [27]. The average and range (min – max) of the differences are larger for the feed force. The smaller range of the passive force confirms a shift for all cutting conditions, similar to the results of Hardt and Bergs [27]. Again, the friction modelling should be the first aspect of the model to be improved in future developments.

5. Conclusions

An experimental and numerical study of the orthogonal and oblique free cutting of Ti6Al4V was carried out for a wide range of cutting conditions using an ANN-based flow law. The following main conclusions are drawn:

- The experimental study was carried out with the same set-up in free orthogonal and free oblique cutting for the titanium alloy Ti6Al4V (the only change is the cutting edge inclination). This is a reference to evaluate the

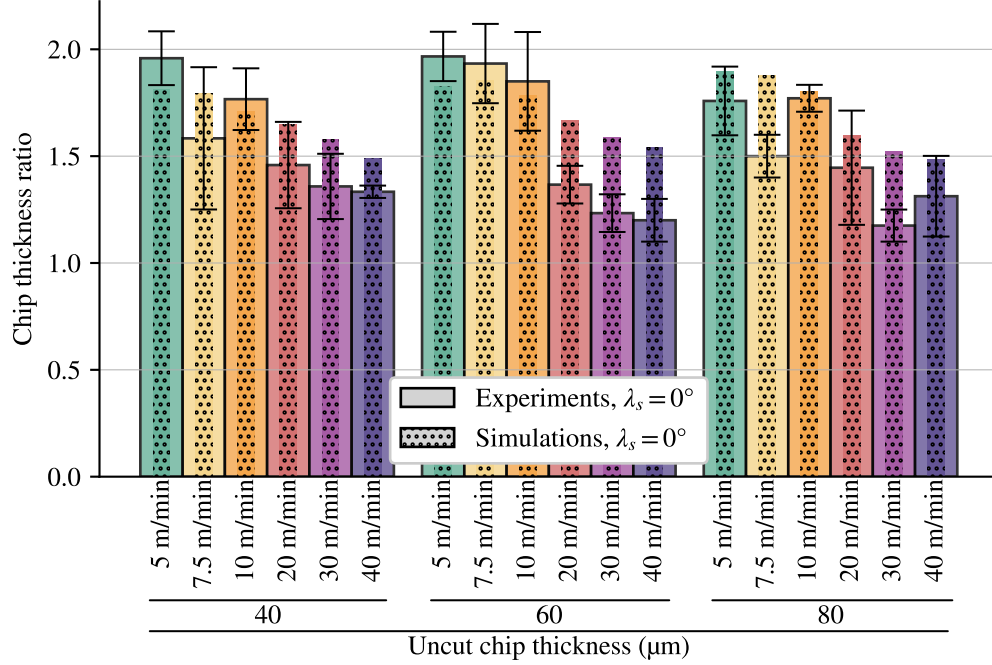


Figure 14: Comparison of experimental and numerical chip thickness ratios at the cutting edge inclination of 0° for the 3 uncut chip thicknesses and the 6 cutting speeds

Table 6: Synthetic quantitative overview of the results: differences between the experimental and the numerical results (average difference for each cutting edge inclination, and maximal, minimal and average differences for all the conditions) for the cutting force, ΔF_c , the feed force, ΔF_f , the passive force, ΔF_p , and the chip thickness ratio, $\Delta \lambda_h$

Difference	ΔF_c (%)	ΔF_f (%)	ΔF_p (%)	$\Delta \lambda_h$ (%)
Average $\lambda_s = 0^\circ$	3	38	–	14
Average $\lambda_s = 6^\circ$	4	40	26	21
Max. global	10	60	29	38
Min. global	1	10	19	2
Average global	4	39	26	17

performance of the FE 3D model introducing an ANN-based flow law developed under the same conditions. An unpreviously seen wide range of cutting conditions, 36, is considered, including 2 cutting edge inclinations.

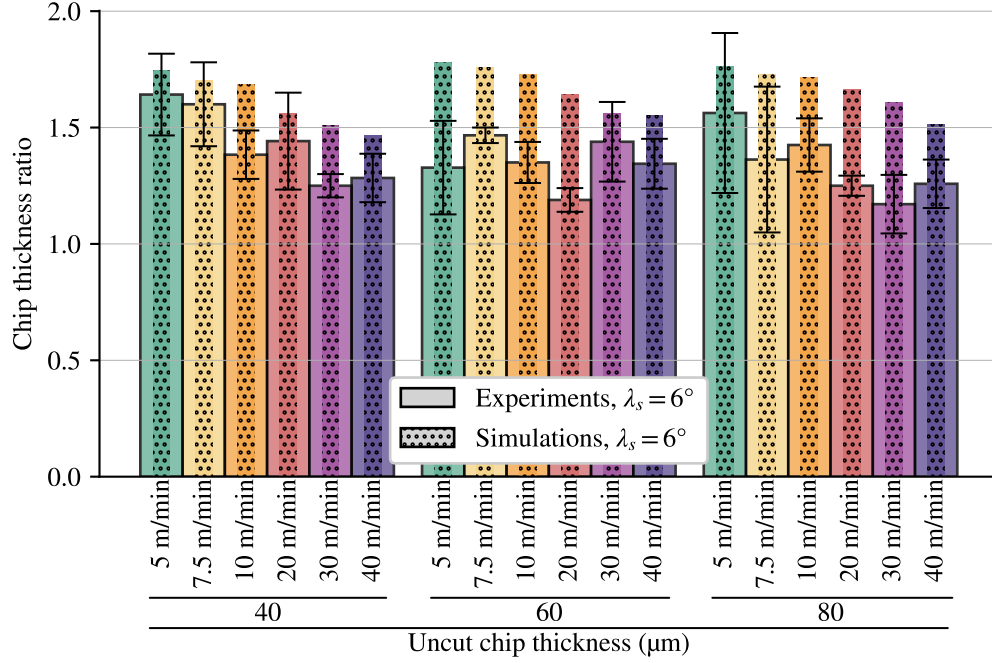


Figure 15: Comparison of experimental and numerical chip thickness ratios at the cutting edge inclination of 6° for the 3 uncut chip thicknesses and the 6 cutting speeds

- A major novelty of this work is the accurate evaluation of the fundamental variables and their trends in 3D, without the need to adjust the numerical parameters and the model characteristics when the cutting conditions and the inclination angle are changed significantly. The mere fact of changing the inclination angle from free orthogonal cutting to oblique cutting while maintaining the quality of the results has no equivalent in the current literature, especially since no studies (experimental or numerical) on free oblique cutting are available.
- Taking into account the material's flow law by means of a neural network makes it possible to overcome the limitations of conventional flow laws and to reduce the approximations associated with the establishment of an analytical formulation of the flow law as conventionally adopted. The numerical model is then able to better reproduce the real behaviour of the material and to take into account thermomechanical transformations which are sources of non-linearities, difficult to take into account with an analytical flow law

model. Current work, using a Gleeble thermomechanical simulator, on the behaviour of a modified carbon alloy AISI P20 shows the advantages of this approach compared to models in the literature such as Johnson-Cook, Zerilli-Armstrong [5] or Hansel-Spittel [47], insofar as one is then able to better reproduce more complex material behaviours.

- The cutting force is the best modelled quantity with an average difference of 4 % with the experiments. Chip thickness ratio and passive force show a larger deviation from the experiments (17 % and 26 %, respectively), but their trends as the cutting conditions change are accurate. This is in line with the expected results provided by a predictive model. The deviation for feed force is higher (39 %), and opposite trends compared to the experimental reference are observed. The lack of influence of uncut chip thickness on friction in the model seems to be one of the aspects to be included as a priority in future work. The model is found to handle the occurrence of the third force, out of plane, well without significant degradation of the results.
- The predictive capabilities of the model make it suitable for the development of straight-edged tools, for example. This work also demonstrates the ability to model material behaviour with ANN and opens up possibilities in this promising direction.

6. Statements & Declarations

Funding

The authors declare that this research received no external funding.

Competing Interests

The authors have no relevant financial or non-financial interests to disclose.

Author Contributions

François Ducobu contributed to Data curation, Formal analysis, Investigation, Methodology, Software, Supervision, Validation, Visualization, Writing – original draft and review & editing (focussing on non ANN-related aspects). Olivier Pantalé contributed to Data curation, Formal analysis, Investigation, Methodology, Software, Validation, Visualization, Writing – original draft and review & editing (focussing on ANN-related aspects). Bert Lauwers contributed to Supervision and Writing – review & editing. All authors read and approved the final manuscript.

References

- [1] P. J. Arrazola, T. Özel, D. Umbrello, M. Davies, I. S. Jawahir, Recent advances in modelling of metal machining processes, *CIRP Annals* 62 (2013) 695–718.
- [2] S. N. Melkote, W. Grzesik, J. Outeiro, J. Rech, V. Schulze, H. Attia, P.-J. Arrazola, R. M'Saoubi, C. Saldana, Advances in material and friction data for modelling of metal machining, *CIRP Annals* 66 (2017) 731–754.
- [3] G. Johnson, W. Cook, A constitutive model and data for metals subjected to large strains, high strain rates and high temperatures, in: *Proc. 7th International Symposium on Ballistics*, volume 21, The Hague, The Netherlands, pp. 541–547.
- [4] M. Calamaz, D. Coupard, F. Girot, A new material model for 2D numerical simulation of serrated chip formation when machining titanium alloy Ti–6Al–4V, *International Journal of Machine Tools and Manufacture* 48 (2008) 275–288.
- [5] M. M. Gurusamy, B. C. Rao, On the performance of modified Zerilli-Armstrong constitutive model in simulating the metal-cutting process, *Journal of Manufacturing Processes* 28 (2017) 253–265.
- [6] T. Özel, T. Altan, Determination of workpiece flow stress and friction at the chip–tool contact for high-speed cutting, *International Journal of Machine Tools and Manufacture* 40 (2000) 133–152.
- [7] A. Shrot, M. Bäker, Determination of Johnson–Cook parameters from machining simulations, *Computational Materials Science* 52 (2012) 298–304.
- [8] F. Klocke, D. Lung, S. Buchkremer, I. S. Jawahir, From Orthogonal Cutting Experiments towards Easy-to-Implement and Accurate Flow Stress Data, *Materials and Manufacturing Processes* 28 (2013) 1222–1227.
- [9] P. Bosetti, C. Maximiliano Giorgio Bort, S. Bruschi, Identification of Johnson–Cook and Tresca's Parameters for Numerical Modeling of AISI-304 Machining Processes, *Journal of Manufacturing Science and Engineering* 135 (2013).

- 514 [10] B. Denkena, T. Grove, M. A. Dittrich, D. Niederwestberg, M. Lahres, In-
515 verse Determination of Constitutive Equations and Cutting Force Modelling
516 for Complex Tools Using Oxley's Predictive Machining Theory, *Procedia*
517 *CIRP* 31 (2015) 405–410.
- 518 [11] T. Bergs, M. Hardt, D. Schraknepper, Determination of Johnson-Cook mate-
519 rial model parameters for AISI 1045 from orthogonal cutting tests using the
520 Downhill-Simplex algorithm, *Procedia Manufacturing* 48 (2020) 541–552.
- 521 [12] M. Hardt, D. Schraknepper, T. Bergs, Investigations on the Application of
522 the Downhill-Simplex-Algorithm to the Inverse Determination of Material
523 Model Parameters for FE-Machining Simulations, *Simulation Modelling*
524 *Practice and Theory* 107 (2021) 102214.
- 525 [13] B. Stampfer, G. González, E. Segebade, M. Gerstenmeyer, V. Schulze, Ma-
526 terial parameter optimization for orthogonal cutting simulations of AISI4140
527 at various tempering conditions, *Procedia CIRP* 102 (2021) 198–203.
- 528 [14] M. Hardt, D. Jayaramaiah, T. Bergs, On the Application of the Particle
529 Swarm Optimization to the Inverse Determination of Material Model Pa-
530 rameters for Cutting Simulations, *Modelling* 2 (2021) 129–148.
- 531 [15] N. Kugalur Palanisamy, E. Rivière Lorphèvre, M. Gobert, G. Briffoteaux,
532 D. Tuytens, P.-J. Arrazola, F. Ducobu, Identification of the Parameter Val-
533 ues of the Constitutive and Friction Models in Machining Using EGO Algo-
534 rithm: Application to Ti6Al4V, *Metals* 12 (2022) 976.
- 535 [16] F. Ducobu, N. K. Palanisamy, P.-J. Arrazola, E. Rivière-Lorphèvre, Appli-
536 cation of material constitutive and friction models parameters identified with
537 AI and ALE to a CEL orthogonal cutting model, *Procedia CIRP* 117 (2023)
538 311–316.
- 539 [17] M. B. Gorji, M. Mozaffar, J. N. Heidenreich, J. Cao, D. Mohr, On the po-
540 tential of recurrent neural networks for modeling path dependent plasticity,
541 *Journal of the Mechanics and Physics of Solids* 143 (2020) 103972.
- 542 [18] M. R. Jamli, N. M. Farid, The sustainability of neural network applications
543 within finite element analysis in sheet metal forming: A review, *Measure-*
544 *ment* 138 (2019) 446–460.

- 545 [19] P. Tize Mha, P. Dhondapure, M. Jahazi, A. Tongne, O. Pantalé, Interpolation
546 and Extrapolation Performance Measurement of Analytical and ANN-Based
547 Flow Laws for Hot Deformation Behavior of Medium Carbon Steel, *Metals*
548 13 (2023) 633.
- 549 [20] O. Pantalé, Development and Implementation of an ANN Based Flow Law
550 for Numerical Simulations of Thermo-Mechanical Processes at High Tem-
551 peratures in FEM Software, *Algorithms* 16 (2023) 56.
- 552 [21] P. Tize Mha, P. Dhondapure, M. Jahazi, A. Tongne, O. Pantalé, Artificial
553 Neural Network-Based Critical Conditions for the Dynamic Recrystalliza-
554 tion of Medium Carbon Steel and Application, *Metals* 13 (2023) 1746.
- 555 [22] F. Ducobu, E. Rivière-Lorphèvre, E. Filippi, Application of the Coupled
556 Eulerian-Lagrangian (CEL) method to the modeling of orthogonal cutting,
557 *European Journal of Mechanics, A/Solids* 59 (2016) 58–66.
- 558 [23] X. Xu, J. Outeiro, J. Zhang, B. Li, W. Zhao, Simulation of material side flow
559 using a 3D coupled Eulerian-Lagrangian approach and a constitutive model
560 considering the stress state, *Procedia CIRP* 102 (2021) 441–446.
- 561 [24] F. Ducobu, E. Rivière-Lorphèvre, E. Filippi, Finite element modelling of 3D
562 orthogonal cutting experimental tests with the Coupled Eulerian-Lagrangian
563 (CEL) formulation, *Finite Elements in Analysis and Design* 134 (2017) 27–
564 40.
- 565 [25] D. Ambrosio, A. Tongne, V. Wagner, G. Dessein, O. Cahuc, A new damage
566 evolution criterion for the coupled Eulerian-Lagrangian approach: Applica-
567 tion to three-dimensional numerical simulation of segmented chip formation
568 mechanisms in orthogonal cutting, *Journal of Manufacturing Processes* 73
569 (2022) 149–163.
- 570 [26] A. Vovk, J. Sölter, B. Karpuschewski, Finite element simulations of the
571 material loads and residual stresses in milling utilizing the CEL method,
572 *Procedia CIRP* 87 (2020) 539–544.
- 573 [27] M. Hardt, T. Bergs, Three Dimensional Numerical Modeling of Face Turn-
574 ing Using the Coupled-Eulerian-Lagrangian Formulation, *Procedia CIRP*
575 102 (2021) 162–167.

- 576 [28] M. Agmell, V. Bushlya, S. V. A. Laakso, A. Ahadi, J.-E. Ståhl, Development
577 of a simulation model to study tool loads in pcBN when machining AISI
578 316L, *The International Journal of Advanced Manufacturing Technology* 96
579 (2018) 2853–2865.
- 580 [29] M. Abouridouane, T. Bergs, D. Schraknepper, G. Wirtz, Friction behavior
581 in metal cutting: Modeling and simulation, *Procedia CIRP* 102 (2021) 405–
582 410.
- 583 [30] F. Ducobu, E. Rivière-Lorphèvre, E. Filippi, Experimental contribution to
584 the study of the Ti6Al4V chip formation in orthogonal cutting on a milling
585 machine, *International Journal of Material Forming* 8 (2015) 455–468.
- 586 [31] A. Sela, G. Ortiz-de-Zarate, D. Soler, G. Germain, P. Aristimuño, P. J. Arra-
587 zola, Measurement of plastic strain and plastic strain rate during orthogonal
588 cutting for Ti-6Al-4V, *International Journal of Mechanical Sciences* 198
589 (2021) 106397.
- 590 [32] M. Afrasiabi, J. Saelzer, S. Berger, I. Iovkov, H. Klippel, M. Röthlin,
591 A. Zabel, D. Biermann, K. Wegener, A Numerical-Experimental Study on
592 Orthogonal Cutting of AISI 1045 Steel and Ti6Al4V Alloy: SPH and FEM
593 Modeling with Newly Identified Friction Coefficients, *Metals* 11 (2021)
594 1683.
- 595 [33] O. Pantalé, P. Tize Mha, A. Tongne, Efficient implementation of non-linear
596 flow law using neural network into the Abaqus Explicit FEM code, *Finite
597 Elements in Analysis and Design* 198 (2022) 103647.
- 598 [34] SECO TOOLS AB, Turning catalog and technical guide 2012, 2011.
- 599 [35] S. Seo, O. Min, H. Yang, Constitutive equation for Ti–6Al–4V at high tem-
600 peratures measured using the SHPB technique, *International Journal of Im-
601 pact Engineering* 31 (2005) 735–754.
- 602 [36] F. Ducobu, E. Rivière-Lorphèvre, E. Filippi, On the importance of the choice
603 of the parameters of the Johnson-Cook constitutive model and their influence
604 on the results of a Ti6Al4V orthogonal cutting model, *International Journal
605 of Mechanical Sciences* 122 (2017) 143–155.
- 606 [37] GRANTA EduPack 2020, Granta Design Limited, 2020.

- 607 [38] N. Milošević, I. Aleksic, Thermophysical properties of solid phase Ti-6Al-
608 4V alloy over a wide temperature range (2012).
- 609 [39] J. Rech, P. J. Arrazola, C. Claudin, C. Courbon, F. Pusavec, J. Kopac, Char-
610 acterisation of friction and heat partition coefficients at the tool-work mate-
611 rial interface in cutting, *CIRP Annals* 62 (2013) 79–82.
- 612 [40] O. Pantalé, Coefficients of an ANN constitutive flow law of a Ti6-Al-4V
613 material for dynamic applications, *Zenodo* (2022).
- 614 [41] L. Wang, H. Long, Investigation of material deformation in multi-pass con-
615 ventional metal spinning, *Materials & Design* 32 (2011) 2891–2899.
- 616 [42] F. Ducobu, E. Rivière-Lorphèvre, E. Filippi, On the introduction of adap-
617 tive mass scaling in a finite element model of Ti6Al4V orthogonal cutting,
618 *Simulation Modelling Practice and Theory* 53 (2015) 1–14.
- 619 [43] M. Sima, T. Özel, Modified material constitutive models for serrated chip
620 formation simulations and experimental validation in machining of titanium
621 alloy Ti–6Al–4V, *International Journal of Machine Tools and Manufacture*
622 50 (2010) 943–960.
- 623 [44] F. Ducobu, E. Rivière-Lorphèvre, E. Filippi, Material constitutive model and
624 chip separation criterion influence on the modeling of Ti6Al4V machining
625 with experimental validation in strictly orthogonal cutting condition, *Inter-
626 national Journal of Mechanical Sciences* 107 (2016) 136–149.
- 627 [45] Y. Karpát, Temperature dependent flow softening of titanium alloy Ti6Al4V:
628 An investigation using finite element simulation of machining, *Journal of
629 Materials Processing Technology* 211 (2011) 737–749.
- 630 [46] Y. C. Zhang, T. Mabrouki, D. Nelias, Y. D. Gong, Chip formation in orthog-
631 onal cutting considering interface limiting shear stress and damage evolution
632 based on fracture energy approach, *Finite Elements in Analysis and Design*
633 47 (2011) 850–863.
- 634 [47] K. Chadha, D. Shahriari, M. Jahazi, An Approach to Develop Hansel–Spittel
635 Constitutive Equation during Ingot Breakdown Operation of Low Alloy
636 Steels, in: M. Muruganant, A. Chirazi, B. Raj (Eds.), *Frontiers in Materials
637 Processing, Applications, Research and Technology*, Springer, Singapore,
638 2018, pp. 239–246.

639 Appendix A. Coefficients of the ANN 3-9-7-1-sig

640 In this appendix, we present the values obtained after the training phase of an
 641 ANN containing 9 neurons in the first hidden layer and 7 neurons in the second
 642 hidden layer. Conforming to [33], this one is referred ANN-3-9-7-1-sig. The
 643 training of the neural network was performed using a dataset containing 3430
 644 data points defined by:

- 645 • 70 equidistant values for $\varepsilon^p \in [0, 3]$, so that $[\varepsilon^p]_{min} = 0$ and $[\varepsilon^p]_{max} = 3$.
- 646 • 7 plastic strain rates $\dot{\varepsilon}^p \in [1/s, 10/s, 50/s, 500/s, 5000/s, 50\,000/s, 500\,000/s]$,
 647 so that $[\ln(\dot{\varepsilon}^p)]_{min} = 0$ and $[\ln(\dot{\varepsilon}^p)]_{max} = 13.12236$.
- 648 • 7 temperatures $T \in [293\text{ K}, 400\text{ K}, 500\text{ K}, 700\text{ K}, 900\text{ K}, 1200\text{ K}, 1500\text{ K}]$, so
 649 that $[T]_{min} = 293\text{ K}$ and $[T]_{max} = 1500\text{ K}$.

650 Stresses in the training dataset ranges from $[\sigma^y]_{min} = 171.4\text{ MPa}$ to $[\sigma^y]_{max} =$
 651 2606.1 MPa . The results of the training process are given here after for the ANN
 652 quantities \mathbf{W}_1 , \mathbf{W}_2 , \vec{w} , \vec{b}_1 , \vec{b}_2 and b . The weight matrix for the first hidden layer
 653 \mathbf{W}_1 is a 9×3 matrix:

$$\mathbf{W}_1 = \begin{bmatrix} -0.87229 & -0.47675 & -1.50771 \\ -0.95762 & -0.25619 & 1.65222 \\ -10.61660 & 0.22003 & -0.11539 \\ 3.67883 & 0.37146 & -1.51069 \\ -63.39468 & 0.15466 & -0.95431 \\ 0.54807 & 0.25959 & -5.44355 \\ -1.33883 & 0.36089 & -1.66735 \\ -0.68125 & 1.02121 & 0.34242 \\ 0.08740 & 0.18764 & -41.32542 \end{bmatrix}$$

654 The weight matrix for the second hidden layer \mathbf{W}_2 is a 7×9 matrix:

$$\mathbf{w}_2^T = \begin{bmatrix} 1.66285 & -0.59645 & -3.17333 & 0.20706 & 1.18760 & 2.01250 & -0.82147 \\ -0.26237 & -2.50330 & -1.45941 & -1.59833 & 4.05169 & -1.21146 & 1.05610 \\ -0.12958 & 0.67119 & -5.85989 & -2.55061 & 4.85245 & 4.31876 & 3.24070 \\ -2.12890 & 0.68296 & 0.71183 & 0.81706 & -0.09405 & 0.34919 & -1.41223 \\ 2.33631 & -0.08089 & 14.65789 & 0.12531 & 23.66363 & 2.55872 & 2.15338 \\ 0.11567 & 1.77629 & -1.80448 & 0.77825 & -1.58254 & 1.90442 & 1.23152 \\ 1.49265 & 0.41821 & -3.53803 & -0.48705 & -0.23671 & 0.75887 & -0.37441 \\ 0.95990 & 0.69041 & 0.43870 & 0.28393 & -1.40101 & -0.64569 & -0.38964 \\ 5.89937 & -0.13015 & 2.99264 & 1.78534 & -3.90189 & 1.17494 & -3.78854 \end{bmatrix}$$

655 The weight vector for the output layer \vec{w} is a 7 components vector:

$$\vec{w} = \begin{bmatrix} 0.34701 \\ 1.42079 \\ -0.96564 \\ 0.62467 \\ -0.56322 \\ 0.40960 \\ -0.42810 \end{bmatrix}$$

656 The biases of the first hidden layer \vec{b}_1 is a 9 components vector:

$$\vec{b}_1 = \begin{bmatrix} 2.57141 \\ 0.22673 \\ -1.16985 \\ -0.11246 \\ -0.82210 \\ -2.13264 \\ 0.78794 \\ 1.20434 \\ -3.48681 \end{bmatrix}$$

657 The biases of the second hidden layer \vec{b}_2 is a 7 components vector:

$$\vec{b}_2 = \begin{bmatrix} -0.36566 \\ -1.14445 \\ -0.79065 \\ -0.50670 \\ 1.30136 \\ 0.04521 \\ -0.29995 \end{bmatrix}$$

658 The bias of the output layer b is a scalar:

$$b = 0.04213$$

659 The corresponding coefficients for the other networks identified during this
660 work (ANN-3-11-7-1-sig, ANN-3-13-7-1-sig, ANN-3-15-7-1-sig and ANN-3-17-
661 7-1-sig) can be found in [40].