

Ti-6Al-4V, Cast

(A) Annealed in full section size: 1300F, 2 hrs., AC.

(B) Solution treated and aged in full section size: 1750F, 25 min., WQ + 1000F, 4 hrs., AC.

(A) Annealed

(B) Solution Treat

+ Age

— — Δ

— — $\blacktriangle$

10 lbs castings from Manufacturer No. 1; section thickness from 0.2 in to 2.0 ins., specimens selected randomly from both thickness extremes and at random orientations with respect to casting geometry.

— — $\bullet$ 1-lb casting from Manufacturer No. 2; section thickness 0.43 in.; all specimens parallel to longitudinal axis of casting.

Note: Each manufacturer used different heat.

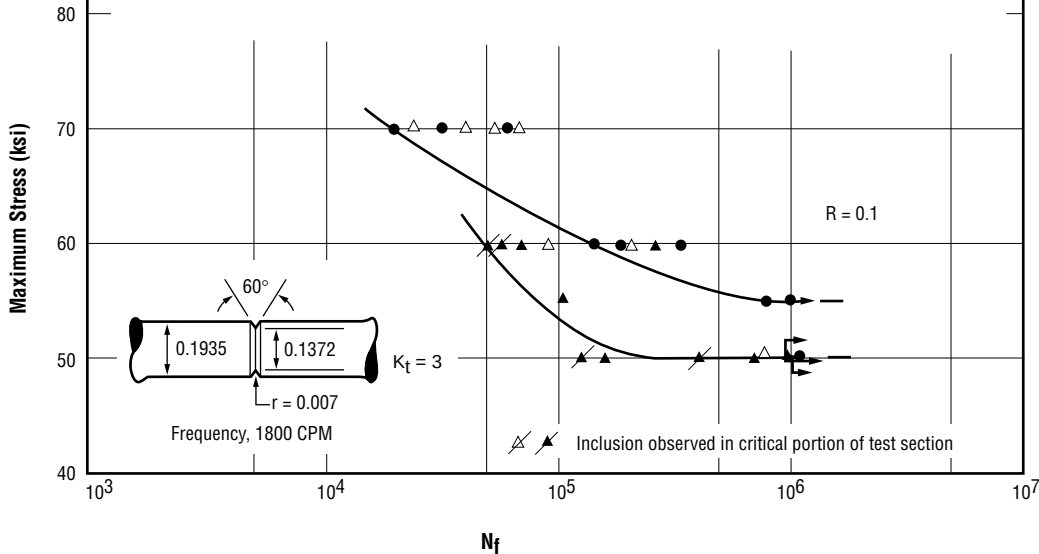


Figure 3.5.1.6 Room temperature mild-notch fatigue properties of annealed and solution treated and aged castings from two casting manufacturers (Ref. 8)