SBI	ใบรับวัตถุดิบ (Incoming Material Acception)	Inspector	Checked	Approved

Receive Date : 02/03/69 **Supplier (ผู้จำหน่าย):** San En

Grade of Material : HSCM 420 HV **Maker (ผู้ผลิต) :** DAI

No.	Heat No.	Q'ty	Data Inspection						
			Specification	Tool	Tol.	1	2	3	4
1	4037 A	35	Ø 30 mm.	Vernier	±0.3	30.22	30.25	30.18	30.20
			L 5500 mm.	ตลับเมตร	±50	5525	5530	5520	5530
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
2	4037 A	40	Ø 30 mm.	Vernier	±0.3	30.14	30.29	30.25	30.26
			L 5500 mm.	ตลับเมตร	±50	5530	5520	5525	5530
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
3	4037 A	40	Ø 30 mm.	Vernier	±0.3	30.21	30.24	30.27	30.20
			L 5500 mm.	ตลับเมตร	±50	5525	5530	5525	5530
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
4			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
5			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
6			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					

Reference :

1. ใบรายการตรวจรับเหล็กเส้น (PO or Packing List)
2. ตรวจ Spec ส่วนผสมเหล็ก ตามมาตรฐาน SBI-PC-S01
3. รูปแบบการบรรจุ

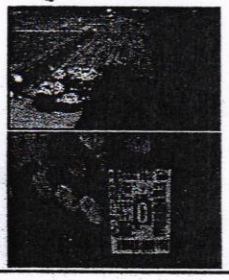

ตรวจสอบสภาพการบรรจุ (Package)

หัวข้อการตรวจสอบ	ผลการตรวจสอบ	
1. มัดเหล็กเส้นไม่ขาดจากกัน	☑ OK	☐ NG
2. การจัดเรียงหัว-ท้ายเหล็กเส้นเสมอกัน	☑ OK	☐ NG
3.มีการชี้บ่งที่มัดเหล็กเส้นทุกมัด	☑ OK	☐ NG

H420HV
30D
4037A

Comment : Appearance

- No Crack
- No Burr
- No Bend
- No Oval

Remark :

SYMBOL FOR JUDGE MENT

O = OK

Δ = SPECIAL ACCEPT

X = NO GOOD

ต้นฉบับ

INSPECTION CERTIFICATE

It is hereby certified that the above results are true and correct in every detail.

Chita Plant.
Daido Steel Co. Ltd.

Chief of Quality Assurance Section
T. Usami

Messrs; HONDA TRADING CORPORATION. Date ; MAY., 15, 2025 Packing List No; 5-0444 (4EJ060)

Contract No; CAD0053002 (BB540577-00 01) Customer No; Condition; HOT ROLLED

	NO	Type of Steel	Heat No.	Size(MM)	Length(MM)	P'cs	Weight (KGS)	Body Hardness ( )
Quantity	A101- A102	HSCM420HV	4037A	DIA 30	4,000- 5,500	69	2,152	
	A201- A203	"	4037A	"	"	140	4,354	
				TOTAL	5 BUNDLES	209	6,506	

Chemical Composition

Heat No. / Items	C	SI	MN	P	S	CU	NI	CR	MO	N	AL	O					Decarburization	Grain Size	Hardenability ℃
Unit	% 100	% 100	% 100	% 1000	% 1000	% 100	% 100	% 100	% 100	% 1000	% 1000	% 10000	%	%	%	%			
Specification	17 -23	15 -35	55 -90	MAX 30	10 -30	MAX 30	MAX 25	85 -125	10 -25	MIN 10	MIN 15	MAX 15							
4037A	21	21	85	19	11	13	8	113	10	17	33	5							

Hardenability (End Quenching Method.)

Heat No. / MM	1.5	3	5	7	9	11	13	15	20	30	40	50
4037A	46	45	41	36	32	30	28	27	25	22	20	19

Non Metallic Inclusion

	ASTM							
	AT	AH	BT	BH	CT	CH	DT	DH
	1.0	0.5	0.0	0.0	0.0	0.0	0.5	0.0

Mechanical Properties (Type of Specimen)

Heat No. / Items	Yield Point Strength	Tensile Strength	Elongation	Reduction of Area	Hardness	Impact Value	Heat Treatment
Unit			%	%	HB		
Specification							

Heat No. / Items	Macro structure	Streak Flaw	Micro structure	Upsetting Test	Ultrasonic Test	Size Tolerance (MM)
4037A					GOOD	

H420HV
3 0 D
4037A

PASS
02 / 03 / 69
ผู้ตรวจสอบ.....
หัวหน้าแผนก.....

Remarks