SBI	ใบรับวัตถุดิบ (Incoming Material Acception)	Inspector	Checked	Approved

Receive Date : 02/03/69 **Supplier (ผู้จำหน่าย):** TOYOTA

Grade of Material : S48C **Maker (ผู้ผลิต) :** SHI

No.	Heat No.	Q'ty	Data Inspection						
			Specification	Tool	Tol.	1	2	3	4
1	2514643	33	Ø 40 mm.	Vernier	±0.3	40.21	40.14	40.19	40.25
			L 5,800 mm.	ตลับเมตร	±50	5,830	5,825	5,830	5,825
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
2			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
3			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
4			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
5			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
6			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					

Reference :

1. ใบรายการตรวจรับเหล็กเส้น (PO or Packing List)
2. ตรวจ Spec ส่วนผสมเหล็ก ตามมาตรฐาน SBI-PC-S01
3. รูปแบบการบรรจุ

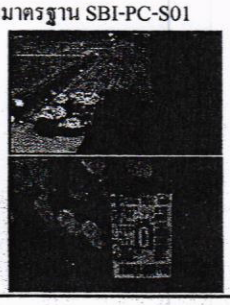

ตรวจสอบสภาพการบรรจุ (Package)

หัวข้อการตรวจสอบ	ผลการตรวจสอบ	
1. มัดเหล็กเส้นไม่ขาดจากกัน	☑ OK	☐ NG
2. การจัดเรียงหัว-ท้ายเหล็กเส้นเสมอกัน	☑ OK	☐ NG
3.มีการชี้บ่งที่มัดเหล็กเส้นทุกมัด	☑ OK	☐ NG

Steel grade S48C
Heat No. 2514643
Size Φ40 mm
MADE IN CHINA

Comment : Appearance

- No Crack
- No Burr
- No Bend
- No Oval

Remark :

SYMBOL FOR JUDGE MENT

O = OK

Δ = SPECIAL ACCEPT

X = NO GOOD

คัมฉบับ

石钢®

SHIJIAZHUANG IRON & STEEL CO.,LTD

NO. 25086724

SG-MES-PZ-1001

Customer's contract No.	ZTH25713	Customer	TOYOTA TSUSHO (THAILAND) CO., LTD.		Shape of Product	Round Bar	Standard	SXY2039-2022	Steel grade	S48C	Certificate No.	2510280314
Heat No.	2514643	Rolling plan No.	B112571330		Delivery condition	Hot rolled	Size(mm)	DIA.40	Weight(MT)	49.67	Bundles	26

Chemical Composition (%)

Item	C	Si	Mn	P	S	Cr	Ni	Cu	O	SP1
Ladle Result	0.47	0.23	0.77	0.014	0.006	0.08	0.04	0.06	0.0004	0.12

Scattered porosity	Center porosity	Ingot shape segregation	Yield strength	Tensile strength	Elongation	Reduction of area	Hardness	dA	d(B+C)	Decarburized layer	Austenite grain size	Inspection	Surface quality & Shape size
Grade	Grade	Grade	ReL MPa	Rm MPa	A %	Z %	HBW	%	%	mm	Grade		
0.5	1.5	0	420	672	23.0	50	202	0.02	0.01	0.14	7.5	Qualified	Qualified
0.5	1	0	415	665	22.5	50	200	0.02	0.01	0.14			
							201						

Note: SP1-Cr+Ni;

PASS

02/03/69

ผู้ตรวจสอบ.....

หัวหน้าแผนก.....

石家庄钢铁有限责任公司 Shijiazhuang Iron & Steel Co., Ltd.
Steel grade S48C
Heat No. 2514643
Size ϕ40 mm
MADE IN CHINA

Signature

石家庄钢铁有限责任公司 质量检验专用章 检验专用

MADE IN CHINA

HBIS 河钢集团石钢公司 HBIS GROUP SHISTEEL COMPANY

Quality department director: ZhangYongjun Address: Hebei, Shijiazhuang, China 363 Heping dongliu, Code:050031, Tel:(0311) 86913195