SBI	ใบรับวัตถุดิบ (Incoming Material Acception)	Inspector	Checked	Approved

Receive Date : 05/03/69 **Supplier (ผู้จำหน่าย):** San En.

Grade of Material : HSCM 415 HV **Maker (ผู้ผลิต) :** DAI

No.	Heat No.	Q'ty	Data Inspection						
			Specification	Tool	Tol.	1	2	3	4
1	9C70A	42	Ø 32 mm.	Vernier	±0.3	32.21	32.15	32.19	32.24
			L 5,500 mm.	ตลับเมตร	±50	5,525	5,530	5,520	5,520
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
2	9C70A	43	Ø 32 mm.	Vernier	±0.3	32.27	32.20	32.22	32.26
			L 5,500 mm.	ตลับเมตร	±50	5,530	5,530	5,525	5,520
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
3	9C70A	52	Ø 32 mm.	Vernier	±0.3	32.20	32.15	32.10	32.21
			L 5,500 mm.	ตลับเมตร	±50	5,525	5,520	5,530	5,520
			Appearance	Visual		ok	ok	ok	ok
				Judgement		O	O	O	O
4			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
5			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					
6			Ø mm.	Vernier	±0.3				
			L mm.	ตลับเมตร	±50				
			Appearance	Visual					
				Judgement					

Reference :

1. ใบรายการตรวจรับเหล็กเส้น (PO or Packing List)
2. ตรวจ Spec ส่วนผสมเหล็ก ตามมาตรฐาน SBI-PC-S01
3. รูปแบบการบรรจุ

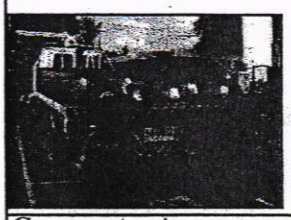

ตรวจสอบสภาพการบรรจุ (Package)

หัวข้อการตรวจสอบ	ผลการตรวจสอบ	
1. มัดเหล็กเส้นไม่ขาดจากกัน	☑ OK	☐ NG
2. การจัดเรียงหัว-ท้ายเหล็กเส้นเสมอกัน	☑ OK	☐ NG
3.มีการชี้บ่งที่มัดเหล็กเส้นทุกมัด	☑ OK	☐ NG

H415HV
32 D
9C70A

Comment : Appearance

- No Crack
- No Burr
- No Bend
- No Oval

Remark :

SYMBOL FOR JUDGE MENT

O = OK

Δ = SPECIAL ACCEPT

X = NO GOOD

ต้นฉบับ

INSPECTION CERTIFICATE

It is hereby certified that the above results are true and correct in every detail.

Chita Plant.
Daido Steel Co. Ltd.

Chief of Quality Assurance Section
T. Usami

Messrs; HONDA TRADING CORPORATION. Date ; NOV., 10, 2025 Packing List No; N-0244 (XEJ020)

Contract No; CAD0057491 (BB5X0501-00 01) Customer No; Condition; HOT ROLLED

	NO	Type of Steel	Heat No.	Size(MM)	Length(MM)	P'cs	Weight (KGS)	Body Hardness ( )
Quantity	A101- A105	HSCM415HV	9C70A	DIA 32	4,000- 5,500	241	8,516	
				TOTAL	5 BUNDLES	241	8,516	

Chemical Composition

Heat No. / Items	C	SI	MN	P	S	CU	NI	CR	MO	AL	O	N					Decarburization	Grain Size	Hardenability
Unit	% 100	% 100	% 100	% 1000	% 1000	% 100	% 100	% 100	% 100	% 1000	% 10000	% 1000	%	%	%	%			℃
Specification	12 -18	15 -35	55 -90	MAX 30	10 -30	MAX 30	MAX 25	85 -125	10 -25	MIN 15	MAX 15	MIN 10							
9C70A	15	23	77	21	12	24	9	111	10	38	7	18							

Hardenability (End Quenching Method.)

Heat No. / MM	1.5	3	5	7	9	11	13	15	20	30	40	50
9C70A	43	42	35	30	27	25	24	22	19	14	11	9

Non Metallic Inclusion

ASTM	AT	AH	BT	BH	CT	CH	DT	DH
9C70A	1.5	0.5	0.0	0.0	0.0	0.0	1.0	0.0

Mechanical Properties (Type of Specimen)

Heat No. / Items	Yield Point Strength	Tensile Strength	Elongation	Reduction of Area	Hardness	Impact Value	Heat Treatment
Unit			%	%	HB		
Specification							

Heat No. / Items	Macro structure	Streak Flaw	Micro structure	Upsetting Test	Ultrasonic Test	Size Tolerance (MM)
9C70A					GOOD	

H415HV
32 D
9C70A

PASS
05 / 03 / 69
ผู้ตรวจสอบ.....
หัวหน้าแผนก.....

Remarks