Table of Contents

NEW RELEASE AGENT EVALUATION
Release agent : YP - PELICOAT
YEC instruction with UD #: MFSK3862



Device evaluated : NP364-110-182 #LB
Date evaluated : June 28, 2019
Quantity Inspected : 100 shots
Lot Number : D190628-M

Table of Contents

Page	Special Note	Date Prepared
1	**Front Page (Table of Contents)**	**July 1, 2019**
2	**Evaluation Result**	**July 1, 2019**
3	**Application for Evaluation**	**July 1, 2019**
4	**UD No. MFSK3862**	**July 1, 2019**
5	**Activities Done**	**July 1, 2019**
6~11	**Evaluation Data Sheet**	**June 30, 2019**
12	**Injection Machine Data Sheet**	**June 28, 2019**
13	**WI - Washing Activity**	**June 25, 2019**

Prepared :
Adrian R. Diwata
PPS Process Jr.Engineer

Conformed :
7/1/19
Belen B. Perez
LQC Sr. Supervisor

Checked:
Arnold P. Martinez
PPS-CN OIC

Initial Approved:
7/2/19
Reddie P. Martinez
PPS Section Head

Hidekazu Imano
PPS Technical Adviser

YEC Approved: :

承　認 APPROVED	確　認 CHECK	担　当 CHARGE

Final Approved:
Joel C. Padullo
Vice President

EVALUATION REPORT

PPS-8000-090

Device Name :	NP364-110-182 #LB	U.D. No. :	MFSK3862
Lot No. :	D190628-M	Date Prepared :	July 1, 2019
Qty. :	100 shots	Material :	PES (GF) SGF2030 BLK
Cavity Qty. :	2	Drawing No./ Rev. :	B128227-001 / D

Purpose of Evaluation

☐ New Die Set ☐ Parts Changed ☐ - Modified ☐ - Repaired

☐ New Material ☐ Longevity ☐ - Coma Change

Release agent : From YPZ to YP


☐ Retry _____ ☐ Non-Longevity ■ - Others **SPRAY MAT'L. EVALUATION**

Evaluation Contents


■ - Dimension Checking ■ - Appearance Checking

Illustration



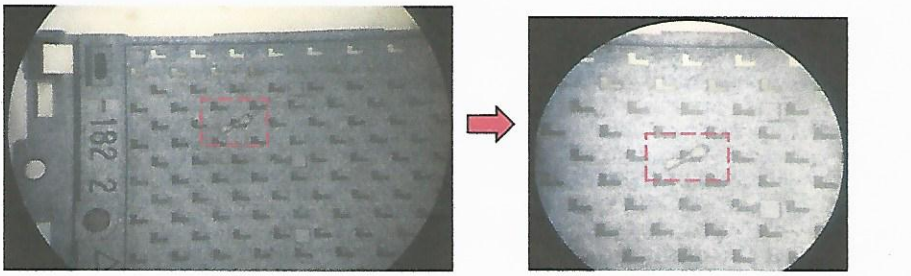

Evidence of residue can be seen clearly

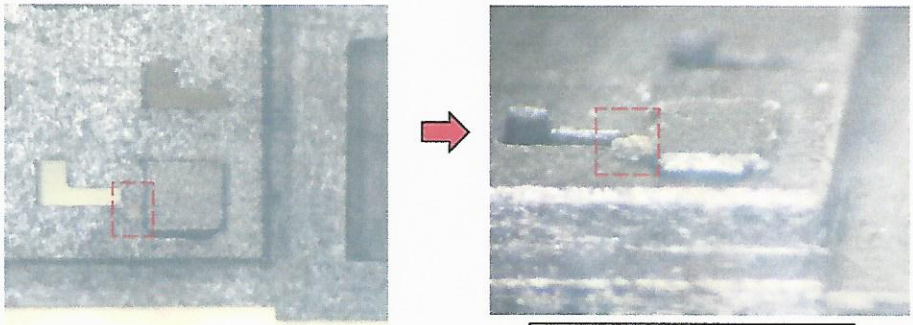

Units inspected did not undergo washing process.

Evaluation Result

Dimension Checking (OK) NG

Appearance Checking OK (NG)

Japan Marking With (Without)

Remarks

- Plastic stuck occurred 3 times during evaluation, location was at the fixed side of die-set.
  Note : Plastic stuck-up not related to YP spray application
- 100 shots of NP364-110-182 #LB were produced, traces of residue still visible on some units
- Spray time used is 0.2 seconds.
- Result of spray application : 12% (12pcs) with evidence of residue (unlocational area)
- Recommendation to apply standard washing activity (refer to attached) — UNDER UD K3450

Judgment

■ - OK for Production ☐ - For Re-try

Reworking ■ With ☐ Without

Prepared	Checked	Approved
A. Diwata	A. Martinez	R. Martinez

Product Application for Evaluation

Control No.	UD No. MFSK3862	
Date :	July 1, 2019	
In-charge	Recognition	Approved
A. Diwata	A. Martinez	R. Martinez

Device Name :

NP364-110-182 #LB

PURPOSE OF VERIFICATION

- ☐ - New Dieset
- ☐ - Renewal Dieset
- ■ - New Material
  Release agent : From YPZ to YP
- ☐ - Extended Dieset Life
- ☐ - Additional Dieset
- ☐ - Repaired Dieset
- ☐ - Retry _____
- ■ - Others **SPRAY MAT'L. EVALUATION**

VERIFICATION CONTENTS

- ■ 1. Appearance Inspection
- ☐ With ☑ Without 1a. Japan Marking
- ■ 2. Dimension Inspection

Produced Quantity	:	100 shots
Applied Quantity	:	100 shots
Lot Number	:	D190628-M

Remarks :

- Plastic stuck occurred 3 times during evaluation, location was at the fixed side of die-set.
  Note: Plastic stuck-up not related to YP spray application.

- 100 shots produced , apply in device of NP364-110-182 #LB were produced, traces of residue
- Spray time used is 0.2 seconds.
- Result of spray application : 12% (12pcs) with evidence of residue (unlocational area)
- **Recommendation to apply standard washing activity (refer to attached)**

UNDER UD K3450

LQC ENTRY

Drawing : B128227-001 Rev. D Date Received : 06/17/2019

Remarks :

~ With direction from YEC in reference to UD #: MFSK3862 (see attached)

- ☐ RETRY
- ☐ SPECIAL AUTHORIZATION APPLICATION

In-charge	Recognition	Approved
A. Diwata	A. Martinez	R.Martinez

緊急指示書（Urgent Directions）

様式：YSN20-010(Rev:F)

区分	追加工指示(Addition Processing)

発行日(Date)	2019/6/26
指示No	MFSK3862
更新No	REV(　　)

緊急対応として、標準工程を暫定的に変更し、生産することを要請します。
(Change provitionally the standard process in order to complete the appointed date and to avoid a loss.)

※指示Noと更新No.は指示部門毎に記入

①指示部門(Directions Section)

山一電機株式会社	
部門	製造部成形製造課
承認(Approval)	担当(Charge)
成形製造課 '19/06/26 課長 野崎	成形製造課 '19/06/26 主任 野崎

③宛先(Destination)

社名(Company)	部門(Section)	担当(Charge)
Pricon Microelectronics, Inc	PMI	Mr.IMANO

適用範囲 (Adapted limit)

製品名(Product name)	図面(Drawing)	Rev
YP	*	

対象ロット (Object Lot)

☐ 数量限定 (QTY Limit)	* pc
☐ 指図書 (P/O Limit)	No. No. No.
☐ 期間限定 (Period)	End of DATE ／ ／
☑ その他 (Others)	YPZ使用金型

原因 (Cause)

内容(Content)	原因ﾓｰﾄﾞ(Cause Mode)
試作検証	☐ 部品不具合(Parts NG) ☐ 組立不具合(Assy NG) ☐ 設計不具合(Design NG) ☑ その他(Others)

②責任部門(Responsibility Section)

部門	PPS
承認(Approval)	担当(Charge)

(指示部門と責任部門が異なる場合のみ)

費用負担 (Expense burden)

- ☐ ①指示部門にて負担 (Expense burden by Directions Section)
- ☐ ②責任部門にて負担 (Expense burden by Responsibility Section)
- ☑ ③指示先部門にて負担 (Expense burden by Destination)
- ☐ 別途、協議結果による (Separately, it decides by deliberations)

※指示先部門は作業完了報告及び見積又は請求書を費用負担部門へ提出して下さい。
Directions section should submit the completion report of work, QUOTATION or DEBIT to expense burden section.

指示内容 (Indication contents)

【離型剤試作】
Confirming the change due to the termination of PERICOAT YPZ production Trial using YEC free of charge with 24 cans of PERICOAT YP provided free of charge YEC Please switch to YP with the mold currently used.
(Checklist)
1, mold release agent remaining → remove if it occurs
2. Release deformation → If it occurs, stop using it and use Z to continue using it and manage it so that the quality level does not change. Monitor and switch so as not to generate a double shot due to mold release deformation or removal. (When there is no mold during trial production, it is responsible in case of emergency)

指示図 (Indication Drawing)

試作検証を実施した結果報告願います。
品名 及び 切り替え可否 リスト化し
週次で報告願います
- Please report the results of evaluation and verification.
- Please list the product name and the possibility of switching.

【本指示書の流れ】 (指示部門)→指示先(宛先)　※ 指示部門は、責任部門と生産管理部へPdf回付のこと。

【注】 ①費用負担の明記がない場合は、本内容は無効とします。(no specification of an expense burden＝Refusal)
②費用請求する場合は、本状を添付により請求のこと。(Attach these documents at the time of expense claim)
③本指示書の(承認)は課長/G責/Mgr 以上とし、日付が判る承認印又は、日付記載のサインとする。
(This data needs the recognition more than a manager.)


ACTIVITIES DONE

Activities conducted before YP spray evaluation:

Autoben Overhaul / Cleaning




ASSTR Cleaning

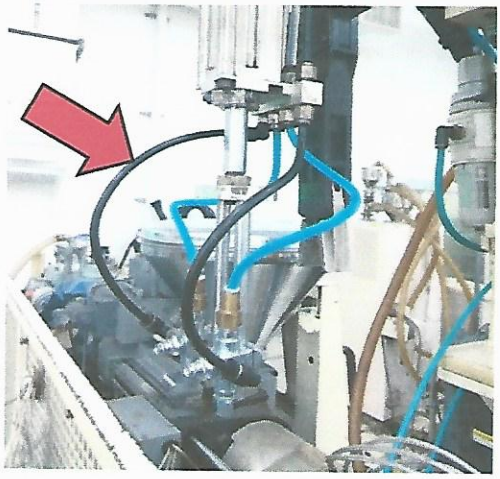


Spray Hoses Cleaning



Spray Nozzle Cleaning

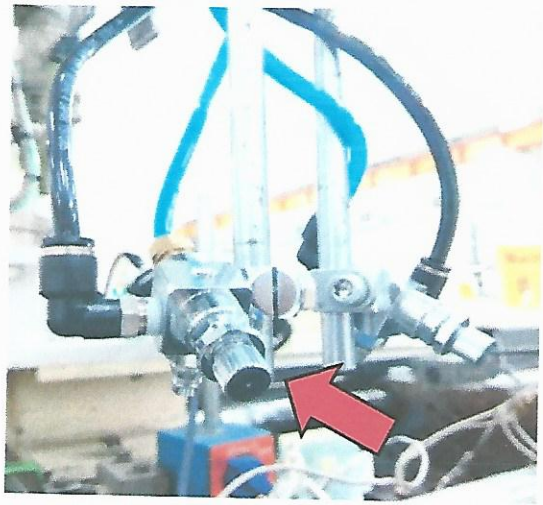

Mold Overhaul / Cleaning

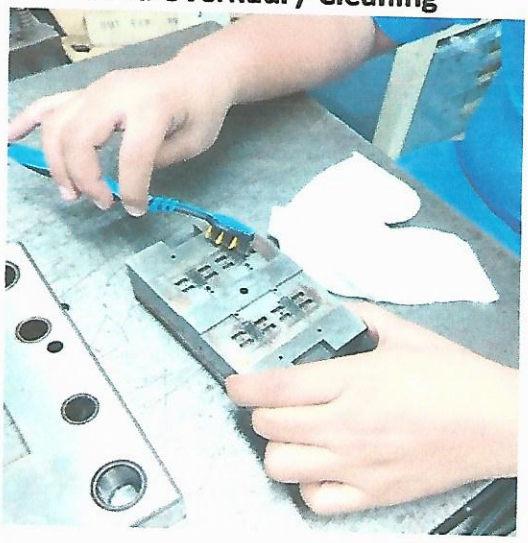

EVALUATION DATA SHEET

Part Name	NP364-110-182 #LB	Date	30-Jun-2019
Drwg No	B128227-001	Material	PES (GF) SGF2030 BLACK
Revision	D	Dieset No.	-
Lot Number	D190628-M	No.of Cavities	2
Quantity	2 Shots		

	PREP'D	CHECK	APPR'D
	FOR: C. DAUZ	A. DIWATA	A. MARTINEZ

TOOL	D	D	D	D	D	D	D	D	D	D
POINT	2	2	3	3	4	4	4	4	4	4
	UP	DOWN	LEFT	RIGHT	UP LEFT	UP CENTER	UP RIGHT	CENTER LEFT	CENTER CENTER	CENTER RIGHT
SPECS	12.040	12.040	21.910	21.910	0.600	0.600	0.600	0.600	0.600	0.600
UP LIMIT	0.000	0.000	0.000	0.000	0.020	0.020	0.020	0.020	0.020	0.020
LOW LIMIT	-0.030	-0.030	-0.030	-0.030	0.000	0.000	0.000	0.000	0.000	0.000
SPECIAL UP			0.000	0.000	0.030	0.030	0.030	0.030	0.030	0.030
SPECIAL LOW			-0.060	-0.060	0.000	0.000	0.000	0.000	0.000	0.000
MAX SPECS	12.040	12.040	21.910	21.910	0.630	0.630	0.630	0.630	0.630	0.630
MIN SPECS	12.010	12.010	21.850	21.850	0.600	0.600	0.600	0.600	0.600	0.600
EVAL'N SAMPLE 1										
CAV.1	12.035	12.040	21.871	21.860	0.615	0.624	0.623	0.623	0.617	0.622
CAV.2	12.038	12.038	21.888	21.866	0.616	0.618	0.623	0.625	0.629	0.618
Max	12.038	12.040	21.888	21.866	0.616	0.624	0.623	0.625	0.629	0.622
Min	12.035	12.038	21.871	21.860	0.615	0.618	0.623	0.623	0.617	0.618
Range	0.003	0.002	0.017	0.006	0.001	0.006	0.000	0.002	0.012	0.004
Ave	12.0365	12.0390	21.8795	21.8630	0.6155	0.6210	0.6230	0.6240	0.6230	0.6200
St Dev	0.0021	0.0014	0.0120	0.0042	0.0007	0.0042	0.0000	0.0014	0.0085	0.0028
Cp	2.3570	3.5355	*0.8319*	2.3570	7.0711	*1.1785*		3.5355	*0.5893*	1.7678
CpK	*0.5500*	*0.2357*	*0.8180*	*1.0214*	6.8354	*0.7071*	#VALUE!	1.4142	*0.2750*	*1.1785*
Judgment	OK	OK	OK	OK	OK	OK	OK	OK	OK	OK

Remarks:

NEW DIESET EVALUATION

TOOL LEGEND:	Machine No 01A
A- Caliper (Width,Heigth, Depth)	n/a
B- Micrometer (Width)	n/a
C- Digimatic Indicator(Heigth)	n/a
D- XY Measurescope (Plane)	8
E- HISOMET (Z)	n/a
F- Pin Gauge	n/a

EVALUATION DATA SHEET

Part Name	NP364-110-182 #LB	Date	30-Jun-2019	PREP'D	CHECK	APPR'D
Drwg No	B128227-001	Material	PES (GF) SGF2030 BLACK	FOR: C. DAUZ	A. DINATA	A. MARTINEZ
Revision	D	Dieset No.	-			
Lot Number	D190628-M	No.of Cavities	2			
Quantity	2 Shots					

TOOL	D	D	D	D	D	D	D	D	D	D
POINT	4 DOWN LEFT	4 DOWN CENTE	4 DOWN RIGHT	5 UP LEFT	5 UP CENTER	5 UP RIGHT	5 CENTER LEFT	5 CENTER CENTER	5 CENTER RIGHT	5 DOWN LEFT
SPECS	0.600	0.600	0.600	0.130	0.130	0.130	0.130	0.130	0.130	0.130
UP LIMIT	0.020	0.020	0.020	0.020	0.020	0.020	0.020	0.020	0.020	0.020
LOW LIMIT	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000
SPECIAL UP	0.030	0.030	0.030	0.030	0.030	0.030	0.030	0.030	0.030	0.030
SPECIAL LOW	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000
MAX SPECS	0.630	0.630	0.630	0.160	0.160	0.160	0.160	0.160	0.160	0.160
MIN SPECS	0.600	0.600	0.600	0.130	0.130	0.130	0.130	0.130	0.130	0.130
EVAL'N SAMPLE 1										
CAV.1	0.627	0.619	0.615	0.151	0.148	0.150	0.146	0.144	0.152	0.145
CAV.2	0.625	0.630	0.608	0.156	0.144	0.149	0.151	0.152	0.152	0.147
Max	0.627	0.630	0.615	0.156	0.148	0.150	0.151	0.152	0.152	0.147
Min	0.625	0.619	0.608	0.151	0.144	0.149	0.146	0.144	0.152	0.145
Range	0.002	0.011	0.007	0.005	0.004	0.001	0.005	0.008	0.000	0.002
Ave	0.6260	0.6245	0.6115	0.1535	0.1460	0.1495	0.1485	0.1480	0.1520	0.1460
St Dev	0.0014	0.0078	0.0049	0.0035	0.0028	0.0007	0.0035	0.0057	0.0000	0.0014
Cp	3.5355	*0.6428*	*1.0102*	1.4142	1.7678	7.0711	1.4142	*0.8839*		3.5355
CpK	*0.9428*	*0.2357*	*0.7745*	*0.6128*	1.6499	4.9497	*1.0842*	*0.7071*	#VALUE!	3.2998
Judgment	OK	OK	OK	OK	OK	OK	OK	OK	OK	OK

Remarks:

NEW DIESET EVALUATION

TOOL LEGEND:	Machine No 01A
A- Caliper (Width,Heigth, Depth)	n/a
B- Micrometer (Width)	n/a
C- Digimatic Indicator(Heigth)	n/a
D- XY Measurescope (Plane)	8
E- HISOMET (Z)	n/a
F- Pin Gauge	n/a

EVALUATION DATA SHEET

Part Name	NP364-110-182 #LB			Date		30-Jun-2019		PREP'D	CHECK	APPRV'D
Drwg No	B128227-001			Material		PES (GF) SGF2030 BLACK		FOR: C. DAUZ	A. DIWATA	A. MARTINEZ
Revision	D			Dieset No.		-				
Lot Number	D190628-M			No.of Cavities		2				
Quantity	2 Shots									
TOOL	D	D	D	D	D	D	D	D	D	D
POINT	5	5	6	6	6	6	7	7	8	8
	DOWN CENTE	DOWN RIGHT	WARP UP	WARP DOWN	WARP LEFT	WARP RIGHT	LEFT	RIGHT	UP	CENTER
SPECS	0.130	0.130	0.000	0.000	0.000	0.000	19.600	19.600	9.600	9.600
UP LIMIT	0.020	0.020	0.030	0.030	0.030	0.030	0.050	0.050	0.030	0.030
LOW LIMIT	0.000	0.000	0.000	0.000	0.000	0.000	0.000	0.000	-0.030	-0.030
SPECIAL UP	0.030	0.030					0.120	0.120		
SPECIAL LOW	0.000	0.000					0.000	0.000		
MAX SPECS	0.160	0.160	0.030	0.030	0.030	0.030	19.720	19.720	9.630	9.630
MIN SPECS	0.130	0.130	0.000	0.000	0.000	0.000	19.600	19.600	9.570	9.570
EVAL'N SAMPLE 1										
CAV.1	0.151	0.145	0.013	0.010	0.010	0.012	19.705	19.713	9.609	9.607
CAV.2	0.145	0.157	0.015	0.017	0.018	0.016	19.718	19.714	9.607	9.611
Max	0.151	0.157	0.015	0.017	0.018	0.016	19.718	19.714	9.609	9.611
Min	0.145	0.145	0.013	0.010	0.010	0.012	19.705	19.713	9.607	9.607
Range	0.006	0.012	0.002	0.007	0.008	0.004	0.013	0.001	0.002	0.004
Ave	0.1480	0.1510	0.0140	0.0135	0.0140	0.0140	19.7115	19.7135	9.6080	9.6090
St Dev	0.0042	0.0085	0.0014	0.0049	0.0057	0.0028	0.0092	0.0007	0.0014	0.0028
Cp	*1.1785*	*0.5893*	3.5355	*1.0102*	*0.8839*	1.7678	2.1757	28.2843	7.0711	3.5355
CpK	*0.9428*	*0.3536*	3.2998	*0.9091*	*0.8250*	1.6499	*0.3082*	3.0641	5.1854	2.4749
Judgment	OK	OK	OK	OK	OK	OK	OK	OK	OK	OK

Remarks:

NEW DIESET EVALUATION

TOOL LEGEND:	Machine No 01A
A- Caliper (Width,Heigth, Depth)	n/a
B- Micrometer (Width)	n/a
C- Digimatic Indicator(Heigth)	n/a
D- XY Measurescope (Plane)	8
E- HISOMET (Z)	n/a
F- Pin Gauge	n/a

EVALUATION DATA SHEET

Part Name	NP364-110-182 #LB			Date		30-Jun-2019		PREP'D	CHECK	APPRV'D
Drwg No	B128227-001			Material		PES (GF) SGF2030 BLACK		RE: C. DAUZ	A. DIWATA	A. MARTINEZ
Revision	D			Dieset No.		-				
Lot Number	D190628-M			No.of Cavities		2				
Quantity	2 Shots									
TOOL	D	D	D	D	D	D	D	D	D	D
POINT	8 DOWN	9 UP LEFT	9 UP CENTER	9 UP RIGHT	9 CENTER LEFT	9 CENTER CENTE	9 CENTER RIGHT	9 DOWN LEFT	9 DOWN CENTER	9 DOWN RIGHT
SPECS	9.600	0.800	0.800	0.800	0.800	0.800	0.800	0.800	0.800	0.800
UP LIMIT	0.030	0.020	0.020	0.020	0.020	0.020	0.020	0.020	0.020	0.020
LOW LIMIT	-0.030	-0.020	-0.020	-0.020	-0.020	-0.020	-0.020	-0.020	-0.020	-0.020
SPECIAL UP										
SPECIAL LOW										
MAX SPECS	9.630	0.820	0.820	0.820	0.820	0.820	0.820	0.820	0.820	0.820
MIN SPECS	9.570	0.780	0.780	0.780	0.780	0.780	0.780	0.780	0.780	0.780
EVAL'N SAMPLE 1										
CAV.1	9.609	0.802	0.809	0.804	0.799	0.807	0.803	0.796	0.816	0.796
CAV.2	9.602	0.813	0.804	0.803	0.798	0.796	0.819	0.793	0.800	0.790
Max	9.609	0.813	0.809	0.804	0.799	0.807	0.819	0.796	0.816	0.796
Min	9.602	0.802	0.804	0.803	0.798	0.796	0.803	0.793	0.800	0.790
Range	0.007	0.011	0.005	0.001	0.001	0.011	0.016	0.003	0.016	0.006
Ave	9.6055	0.8075	0.8065	0.8035	0.7985	0.8015	0.8110	0.7945	0.8080	0.7930
St Dev	0.0049	0.0078	0.0035	0.0007	0.0007	0.0078	0.0113	0.0021	0.0113	0.0042
Cp	2.0203	*0.8571*	1.8856	9.4281	9.4281	*0.8571*	*0.5893*	3.1427	*0.5893*	1.5713
CpK	1.6499	*0.5357*	*1.2728*	7.7782	8.7210	*0.7928*	*0.2652*	2.2785	*0.3536*	*1.0214*
Judgment	OK	OK	OK	OK	OK	OK	OK	OK	OK	OK

Remarks:

NEW DIESET EVALUATION

TOOL LEGEND:	Machine No 01A
A- Caliper (Width,Heigth, Depth)	n/a
B- Micrometer (Width)	n/a
C- Digimatic Indicator(Heigth)	n/a
D- XY Measurescope (Plane)	8
E- HISOMET (Z)	n/a
F- Pin Gauge	n/a

EVALUATION DATA SHEET

Part Name	NP364-110-182 #LB			Date		30-Jun-2019		PREP'D	CHECK	APPRVD
Drwg No	B128227-001			Material		PES (GF) SGF2030 BLACK		FOR: C. DAUZ	A. DIWATA	A. MARTINEZ
Revision	D			Dieset No.		-				
Lot Number	D190628-M			No.of Cavities		2				
Quantity	2 Shots									
TOOL	D	D	D	D	D	D	D	D	D	D
POINT	10 LEFT	10 CENTER	10 RIGHT	11 UP LEFT	11 UP CENTER	11 UP RIGHT	11 CENTER LEFT	11 CENTER CENTER	11 CENTER RIGHT	11 DOWN LEFT
SPECS	12.800	12.800	12.800	0.800	0.800	0.800	0.800	0.800	0.800	0.800
UP LIMIT	0.030	0.030	0.030	0.020	0.020	0.020	0.020	0.020	0.020	0.020
LOW LIMIT	-0.030	-0.030	-0.030	-0.020	-0.020	-0.020	-0.020	-0.020	-0.020	-0.020
SPECIAL UP										
SPECIAL LOW										
MAX SPECS	12.830	12.830	12.830	0.820	0.820	0.820	0.820	0.820	0.820	0.820
MIN SPECS	12.770	12.770	12.770	0.780	0.780	0.780	0.780	0.780	0.780	0.780
EVAL'N SAMPLE 1										
CAV.1	12.775	12.798	12.793	0.801	0.799	0.801	0.799	0.808	0.805	0.818
CAV.2	12.798	12.793	12.805	0.807	0.804	0.807	0.804	0.812	0.789	0.810
Max	12.798	12.798	12.805	0.807	0.804	0.807	0.804	0.812	0.805	0.818
Min	12.775	12.793	12.793	0.801	0.799	0.801	0.799	0.808	0.789	0.810
Range	0.023	0.005	0.012	0.006	0.005	0.006	0.005	0.004	0.016	0.008
Ave	12.7865	12.7955	12.7990	0.8040	0.8015	0.8040	0.8015	0.8100	0.7970	0.8140
St Dev	0.0163	0.0035	0.0085	0.0042	0.0035	0.0042	0.0035	0.0028	0.0113	0.0057
Cp	0.6149	2.8284	1.1785	1.5713	1.8856	1.5713	1.8856	2.3570	0.5893	1.1785
CpK	0.3382	2.4042	1.1392	1.2571	1.7442	1.2571	1.7442	1.1785	0.5009	0.3536
Judgment	OK	OK	OK	OK	OK	OK	OK	OK	OK	OK

Remarks:

NEW DIESET EVALUATION

TOOL LEGEND:	Machine No 01A
A- Caliper (Width,Heigth, Depth)	n/a
B- Micrometer (Width)	n/a
C- Digimatic Indicator(Heigth)	n/a
D- XY Measurescope (Plane)	8
E- HISOMET (Z)	n/a
F- Pin Gauge	n/a

EVALUATION DATA SHEET

Part Name	NP364-110-182 #LB	Date	30-Jun-2019	PREP'D	CHECK	APPRV'D
Drwg No	B128227-001	Material	PES (GF) SGF2030 BLACK	FOR:		
Revision	D	Dieset No.	-			
Lot Number	D190628-M	No.of Cavities	2	C. DAUZ	A. DIMATA	A. MARTINEZ
Quantity	2 Shots					

TOOL	D	D
POINT	11 DOWN CENTE	11 DOWN RIGHT
SPECS	0.800	0.800
UP LIMIT	0.020	0.020
LOW LIMIT	-0.020	-0.020
SPECIAL UP		
SPECIAL LOW		
MAX SPECS	0.820	0.820
MIN SPECS	0.780	0.780
EVAL'N SAMPLE 1		
CAV.1	0.796	0.807
CAV.2	0.803	0.818
Max	0.803	0.818
Min	0.796	0.807
Range	0.007	0.011
Ave	0.7995	0.8125
St Dev	0.0049	0.0078
Cp	1.3469	*0.8571*
CpK	*1.3132*	*0.3214*
Judgment	OK	OK

Remarks:

NEW DIESET EVALUATION

TOOL LEGEND:	Machine No 01A
A- Caliper (Width,Heigth, Depth)	n/a
B- Micrometer (Width)	n/a
C- Digimatic Indicator(Heigth)	n/a
D- XY Measurescope (Plane)	8
E- HISOMET (Z)	n/a
F- Pin Gauge	n/a

INJECTION MACHINE DATA SHEET

MO 6 DAY 29 YR 19

NISSEI UH-1000

DEVICE NAME	NP364-110-182	MATERIAL NAME	PES SGF 2030 BLK	MATERIAL MIXING RATIO	80% V , 20% R
TYPE	# LB	NO. OF CAVITY	2	DRYER USED	OVEN / (DHD)
MACH. NO.	13	1 SHOT WEIGHT	3.721g	UNIT WEIGHT	0.378 gms

MOLD CLOSE

HI V.	MID SLOW	LOW L.	OBSTACLE CHECK TM
40 %	%	12 %	sec

SLOW START	SLOW END	LVLP	HPCL
mm	mm	30 mm	1 mm

MID SLW P.	LOW P.	HI P.
%	30 % →	60 %

EJECTOR

EJ PRES	FWD EVI	FWD STOP	BWD STOP	COUNT	PATTERN
12 %	9 %	44 mm	30 mm	3	3

INC. PRS. NOZ PRS	FWD
80	%

INC. PRS: (ON) OFF

SIGNATURE

MOLD OPEN

OPEN END V.	HI VELOCITY 2	HI VELOCITY 1	OPEN V.	TMP STOP TIME
10 %	%	30 %	310 %	sec

OPEN STOP	SLOW DISTANCE	HI VELOCITY 1	HI VELOCITY 2	TMP STOP POS.
231 mm	20 mm	20 mm	mm	mm

HEATER

NOZZLE	FRONT	MID	REAR
385 C	385 C	380 C	370 C

MOLD HEATER	MOLD 1	MOLD 2
	120 °C	120 °C

INJECTION VELOCITY

V6	V5	V4	V3	V2	V1	VELOC. NO.
			60	70	70 mm/S	3

INJECT TIME	COOLING TIME	CYC START
1	10	0.10 sec

SV5	SV4	SV3	SV2	SV1	SM	SD
			6	7 mm	9.50 mm	3 mm

V P

HOLDING PRESSURE

Pp3	Pp2	Pp1
	100	200 kg/cm²

Tp2	Tp1	PRESS NO.
	0.30 sec	2

POS CHANGE MODE: 4 mm

VS	PB
35 %	120 kg/cm²

Pv3	Pv2	Pv1
2000	2000	2000

Sp2	Sp1
9	16 mm

INJECTION STAB

Rv6	Rv5	Rv4	Rv3	Rv2	Rv1	
0	0	0	0	0	0 sec	VELOCITY SELECT
			RP3 0.30	RP2 0.30	RP1 0.30 sec	PRESSURE SELECT

FILL TIME	PLAST TIME	CYCLE TIME	SPRAY TYPE	SPRAY	SPRAY MODE	SPRAY SIDE	SPRAY TIME
0 1 4 0	0 0 8 1	2 1 1 6	POWDER Z (YP) NO	1-1	(AUTO) MANUAL	(MOVE) FIXED	0.2 sec

SCREW MOST FWD	INJ END POS.	AIRBLOW START TIME	AIRBLOW BLOW TIME	CCD	EJ. PIN CHECKER	PUNCH	PUNCH	SPRAY PORTION
1.69	5.34			(YES) NO	(YES) NO	HARD SOFT		CENTER ONLY / WHOLE AREA

MATERIAL DRY TEMP REQUIREMENT	MATERIAL DRY TIME REQUIREMENT	MATERIAL DRY TIME REQUIREMENT
150°C	4 hrs.	150°C

設定項目(Item)	設定箇所	単位 (Unit)	標準値 (Std)	変更幅 Range	設定項目(Item)	設定箇所	単位 (Unit)	標準値 (Std)	変更幅 (Range)
金型温度 Mold Temp.	Mold temp. 1	℃	120.00	固 定	保圧 Hold Pressure	HP1	kg/cm²	200.00	固 定
	Mold temp. 2	℃	120.00	固 定		HP2	kg/cm²	100.00	固 定
樹脂温度 Barrel Temp.	NOZZLE	℃	385.00	固 定	Holding Time	HP3	kg/cm²		固 定
	HEAD	℃		固 定		HT1	sec	0.30	固 定
	FRONT	℃	385.00	固 定		HT2	sec		固 定
	MID	℃	380.00	固 定		HT3	sec		固 定
	REAR	℃	370.00	固 定	冷却時間	Cooling TM	sec	10.00	固 定
射出速度 Injection Speed	V1	mm/sec	70.00	60.00~80.00	計量	SM	mm	9.50	8.50~10.50
	V2	mm/sec	70.00	60.00~80.00	V-P切替	V-P	mm	4.00	固 定
	V3	mm/sec	60.00	50.00~70.00					
	V4	mm/sec							
	V5	mm/sec							
	V6	mm/sec							

成形条件調整優先手順Adjustment Priority

充填不足 (ショートショット) Shortshot	→ 射出速度 Speed UP	→ 計量 SM UP
バリ Bari	→ 射出速度 Speed DOWN	→ 計量 SM DOWN
ヒケ Sinkmark	→ 計量 SM UP	→ 速度 Speed DOWN
反り ネジレ Warping/Twist	→ 計量 SM UP DOWN	

成形条件の変更幅は上記変更幅以内とする。Data adjusment must be within the Range.

YEC承認	YEC作成

Div. / Dep't.	Product:	PRICON MICROELECTRONICS, INC.	Document No:	Revision No.	Page No.
PPS	TS- MOLDING PRODUCTS		WI-MDGEN-099		
Model:	ALL TS-MOLDED PRODUCTS	WORK INSTRUCTION	Effectivity:	00	1/1
Station:	PRODUCTION AREA		25-Jun-19		

Process: **WASHING PROCESS OF TS - MOLDED PRODUCTS**

Materials Needed	PPE	Tools / Jigs / Equipment Needed	Description of Change			
1. Product to wash	1. Face mask	1. Ultrasonic washer	Rev No.	Revision History	Originator	Effectivity Date
2. IPA	2. Eye protection	2. Oven	*0*	*Initial release*	*R.BITGUE / A.DIWATA*	*25-Jun-19*

SAFETY INSTRUCTIONS :


1. Always use prescribed PPE during operation.
2. PPE must be worn when performing washing activity.

GENERAL INSTRUCTIONS :

1. This instruction is applicable to :
   - 1.1 Molding products contaminated with oil, spray residue and other checmicals.
   - 1.2 Products that have UD for washing
2. Use of ULTRASONIC WASHER is for products that need intensive cleaning.
3. Prepare product to wash, tools and materials needed.
4. Check portable lavatory if there are water leakages.
5. Always maintain a good house keeping in work area.

Note: Emergency treatment :
In case of eye irritation due to accidental chemical eye spill,use the eye wash located near the die maintenanace area.

WASHING INSTRUCTION USING ULTRASONIC WASHER

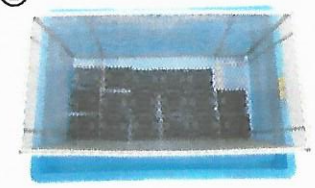① 

1. Arrange the units into the strainer.
   - Units should not be stacked with each other

② 

2. Set the ultrasonic washing machine timer at 20minutes with temp. of 40°

   Washing time: 20 mins
   Temp: 40°C ~ 50°C

③ 

3. Soak the units into washing machine with IPA . Unit should be totally soak into the IPA. Remove the units from the IPA after 20 minutes.


   NOTE: Replace IPA every 4hrs. of continous operation

④ 


4. Arrange the washed units into stainless steel tray.

⑤ 

5. Dry the units into the oven at 90°C temp. setting for 30 minutes.

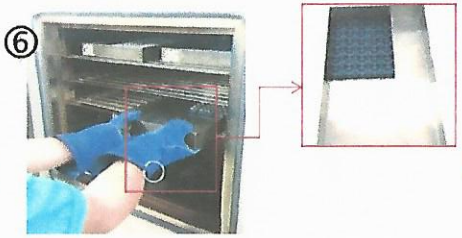⑥ 

6. Pull-out the units after 30 minutes and let it cooldown for 5 minutes .

⑦ 

7. Carefully transfer and arrange the units into slotted trays.

Prepared by:	Checked by:		Conformed by:	Approved by:	
Original Signed	Original Signed	Original Signed	Original Signed	Original Signed	Original Signed
R. Bitgue	A. Martinez	M. Laural	B. Perez	H.Imano	R. Martinez
PPS-Process Jr. Engineers	PPS-CN OIC	PPS-Prod'n Sr. Supervisor	PPS-QC Sr. Supervisor	PPS-Technical Adviser / PPS-Section Head	