



NATIONAL TEXTILE UNIVERSITY

KARACHI CAMPUS

ST-2/1, Sector 30,
Korangi Industrial Area,
Karachi-74900
Pakistan.

☎ (92-21) 35060400
✉ info.kc@ntu.edu.pk
✉ ind.serviceskc@ntu.edu.pk
🌐 www.ntu.edu.pk/kc

TEST REPORT

JOB NO. PD. Lab. 5436/2236/25 **REPORT NO.** 5436/001

DATED 22.09.2025

CLIENT'S NAME Everlast Plastic (Pvt.) Ltd.

ADDRESS Plot No. W1/27 & 28 Fozia Wahab Road Near FFC Port Qasim Karachi

REFERENCE NO. Visiting Card

SAMPLE DETAILS:

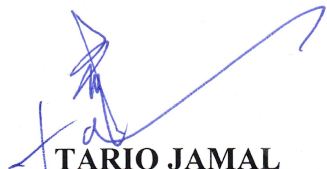
A Sample of **UPVC Window/Door Profile Panels**, tested for Density, Charpy Impact Strength, Vi-cat Softening Point, Heat Reversion, Tensile & Elongation, Flexural Modulus of Elasticity, Thermal Conductivity, Coefficient of Thermal Expansion, RoHS, Weld Strength and Limiting Oxygen Index.

Average readings are reported.

TEST RESULTS

Density (g/cm ³)	1.46
Charpy Impact Strength @23±2°C	No Crack Found (Pass)
Longitudinal Heat Reversion (%)	0.60
Vicat Softening Temperature (°C)	90.00
Tensile Strength @ Yield (Kgf/cm ²)	329.53
Elongation @ Break (%)	100.21
Flexural Modulus of Elasticity (N/mm ²)	2250.00
Thermal Conductivity	LOW
Coefficient of Thermal Expansion (mm/mk)	0.074
RoHS	No Hazardous Substance Detected
Weld Strength (Kgf/cm ²)	181.36
Limiting Oxygen Index (%)	45.00

TARIQ JAMAL
Associate Professor
Head of Industrial Services
NATIONAL TEXTILE UNIVERSITY
Karachi Campus


TARIQ JAMAL
ASSOCIATE PROFESSOR

Tested as per Standard: - Tensile & Elongation: D-638-03, Density: ASTM D 792-00, Impact Strength: ASTM 256-05 & Vi-Cat.: ASTM D 1525-00, Flexural Modulus: EN-12608, Coefficient of Thermal Expansion: ASTM D696-08 & LOI: ASTM D2863,

PLEASE NOTE THAT :

● This report is for private use only and not meant for publicity and cannot be pressed in use in any legal proceedings. ● This report has been prepared in strict observance of accuracy of measurements and is based upon diligent interpretations pertaining to relevant sample(s) supplied. This however carries neither guarantee nor legal liability occasioned by errors or omissions and/or consequential damages arising there for. ● Sampling forming basis or the report has been under taken at the clients end, therefore, National Textile University Karachi Campus (NTU-KC) is not responsible for conformity of the subsequent production or part thereof with the sample in question. ● Accuracy of result and practical validity thereof is subject to the limit and scope of available methodology and NTU-KC assumes no responsibility. I This report shall be not be reproduced in any way, except in full and with the approval of NTU-KC. ● The sample will be preserved on for 30 days unless mentioned, from the date of issue of test report.