Reports on Progress in Physics

REVIEW ARTICLE

Spin glasses: redux: an updated experimental/materials survey

To cite this article: J A Mydosh 2015 *Rep. Prog. Phys.* **78** 052501

View the article online for updates and enhancements.

Related content

- Disorder-driven non-Fermi liquid behaviour of correlated electrons
E Miranda and V Dobrosavljevi
- Quantum frustration in organic Mott insulators: from spin liquids to unconventional superconductors
B J Powell and Ross H McKenzie
- Quantum phase transitions
Matthias Vojta

Recent citations

- Static and dynamic magnetic properties of K3CrO4
Liliia D. Kulish and Graeme R. Blake
- Competing magnetic interactions and magnetoresistance anomalies in cubic intermetallic compounds, Gd4RhAl and Tb4RhAl , and enhanced magnetocaloric effect for the Tb case
Ram Kumar *et al*
- Tuning the flat bands of the kagome metal CoSn with Fe, In, or Ni doping
B. C. Sales *et al*

IOP ebooks™

Bringing together innovative digital publishing with leading authors from the global scientific community.

Start exploring the collection–download the first chapter of every title for free.

This content was downloaded from IP address 144.213.253.16 on 05/07/2021 at 11:16

IOP Publishing Reports on Progress in Physics
Rep. Prog. Phys. 78 (2015) 052501 (25pp) doi:10.1088/0034-4885/78/5/052501

Review Article

Spin glasses: redux: an updated experimental/materials survey

J A Mydosh

Kamerlingh Onnes Laboratory and Institute Lorentz, Leiden University, PO Box 9504, 2300RA Leiden, The Netherlands

E-mail: mydosh@physics.leidenuniv.nl

Received 27 August 2014, revised 26 January 2015
Accepted for publication 26 January 2015
Published 15 April 2015

Abstract

This article reviews the 40+ year old spin-glass field and one of its earliest model interpretations as a spin density wave. Our description is from an experimental phenomenological point of view with emphasis on new spin glass materials and their relation to topical problems and strongly correlated materials in condensed matter physics. We first simply define a spin glass (SG), give its basic ingredients and explain how the spin glasses enter into the statistical mechanics of classical phase transitions. We then consider the four basic experimental properties to solidly characterize canonical spin glass behavior and introduce the early theories and models. Here the spin density wave (SDW) concept is used to explain the difference between a short-range SDW, i.e. a SG and, in contrast, a long-range SDW, i.e. a conventional magnetic phase transition. We continue with the present state of SG, its massive computer simulations and recent proposals of chiral glasses and quantum SG. We then collect and mention the various SG 'spin-off's'. A major section uncovers the fashionable unconventional materials that display SG-like freezing and glassy ground states, such as (high temperature) superconductors, heavy fermions, intermetallics and Heuslers, pyrochlor and spinels, oxides and chalogenides and exotics, e.g. quasicrystals. Some conclusions and future directions complete the review.

Keywords: spin glass, phase transition, new materials

(Some figures may appear in colour only in the online journal)

1. Introduction: What is a spin glass?

Can a random distribution of magnetic moments interact in such a way so as to create a classical phase transition at a distinct critical temperature? The answer is yes: the spin-glass phase! And all the concepts, models and mathematics of statistical mechanics can be brought to bear on the problem, notwithstanding the enormous and patient experimentation on ideal systems. So we offer a simple definition of a spin glass (SG) as a novel, yet classical, phase transition at a given temperature into a a new state of matter: a frozen glass of spins. This change of state has theoretical models with solutions now available for the continuous SG phase transition. Therefore, the SG is an unexpected example of spontaneous symmetry breaking. In contrast, real (window) glasses have no simple model solutions or encompassing theory. Thus they do not conform to spontaneous symmetry breaking. And the field of statistical mechanics always loves a solvable model (Fischer and Hertz 1991), hence the great interest and generalizations of the SG.

SG became a prominent area of research interest in the early 1970's when ac-susceptibility measurements showed evidence for a magnetic phase transition in a series of randomly diluted magnetic alloys (Cannella and Mydosh 1972). This experimental behavior stimulated theoretical attention and a few years later led to novel modeling attempts in order

 © 2015 IOP Publishing Ltd Printed in the UK

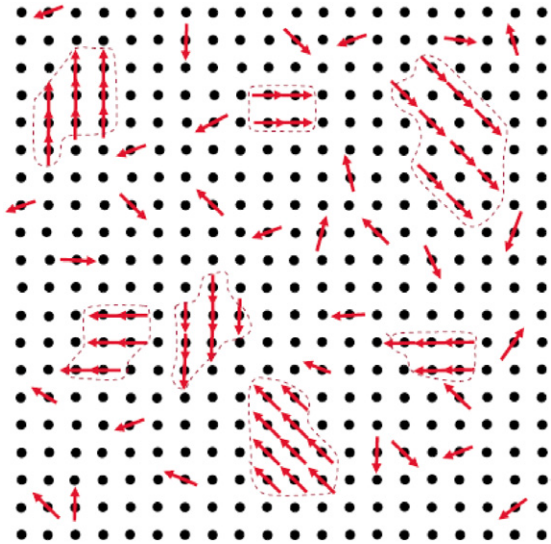

Figure 1. Random-site model in 2D with the inclusion of the ferromagnetic 'cluster glass'. Note the SG phase transition involves the cooperative freezing of the individual spins without the cluster glass. Typical examples of random-site materials are $Cu_{1-x}Mn_x$ and $Eu_xSr_{1-x}S$ for $x < 0.1$. See Mydosh (1993).

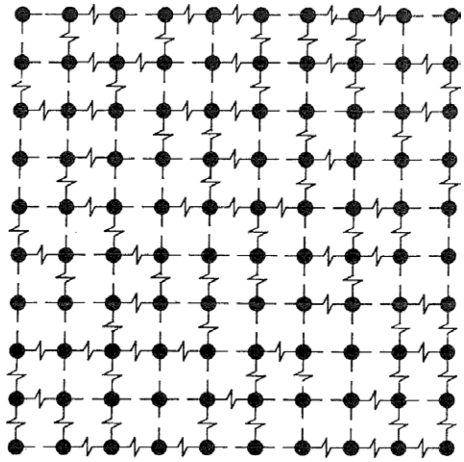

Figure 2. Random-bond spin glass model in 2D where **dashed** bonds denotes ferromagnetic (F) coupling and **zig–zag** bonds represent antiferromagnetic (AF) coupling. The number of (F) bonds is equal to the number of (AF) ones. Note the magnetic atoms are completely ordered on the lattice while the exchange bonds are randomly distributed between F and AF. Typical examples of random-bond materials are $Fe_{1-x}Mn_xTiO_3$ and URh_2Ge_2. See Mydosh (1993) and Süllow *et al* (1997).

to describe the unexpected SG phase transition. For, earlier dc-susceptibility experiments indicated a gradual 'blocking' of spins similar to the slow freezing of a real glass (Lutes and Schmit 1962). As in a conventional phase transition a SG has a unique order parameter and breaks time reversal symmetry. Therefore, a critical temperature appears denoted as T_f (Binder and Young 1986).

A vast surge of theoretical work began in the mid-1970's (Edwards and Anderson 1975) and generated for about 20 years an intense effort towards understanding the SG. Commensurate exertion continued along experimental lines that deeply probed the phase transition and its glassy low-temperature behavior. Here many new materials were discovered to exhibit SG effects and a separation began to distinguish canonical SG, i.e. those exhibiting the 4 basic experimental criteria illuminated in section 3 and those not but still showing some SG-like behavior (Mydosh 1993). Yet, even today, there still remains some 'loose ends' for a full understanding of the SG problem. And furthermore, a present stream of new unconventional and strongly correlated magnetic materials continues to drive SG research.

Figure 1 sketches a 2D random-site SG formed by a non-magnetic host and a random distribution of magnetic impurities, e.g. **Au**Fe or **Cu**Mn. When frozen the spins can lock into all orientations, a Heisenberg universality class. Also shown are cluster of spins which appear at larger concentrations of magnetic impurities, thus their freezing is given the name 'cluster glass'. For the low concentrations, yet interacting individual spins, we have the cooperative freezing of all spins that represents the SG phase transition. The simpler Ising class is the random freezing of only up–down spins

Figure 2 illustrates the main theoretical or random-bond model where the exchange interactions between the ordered-magnetic-species lattice are varied by the intervening ligands or by two differently interacting magnetic elements. Here there is no site disorder between the magnetic species, all are placed on the same lattice sites.

Figure 3 defines frustration on a square plaquette of Ising (up–down) spins. Although the square lattice is not frustrated, depending on the distribution of bonds, magnetic frustration can result. The 2D situation becomes geometrical or lattice frustration for magnetic atoms in a Kagome or hexagonal crystal structure.

Figure 4 shows the oscillating RKKY interaction (Mydosh 1993). Note the ferromagnetic (F) and antiferromagnetic (AF) couplings depending on the distance between the magnetic atoms. This mixed interaction which could also be due to different superexchange couplings that create the competition between the parallel (F) and antiparrallel (AF) alignments.

Collectively we have introduced the three basic ingredients, viz., randomness, frustration and competing interactions needed to create an 'ideal' SG . These ingredients form the basis or starting point for the theoretical models and their solutions. But what about if some of these basic ingredients are missing in real physical systems? Suppose we have all AF interactions coupled with randomness and frustration, but missing F interactions? Here we would expect a good SG state that cannot be easily modeled. On the other hand, we could fabricate a material with frustration and competing interactions without the randomness. Now we would expect a complicated but long-range ordered conventional magnetic state. A third case are the pyrochlors with strong frustration, AF-only interactions but no observable randomness. A spin-liquid ground state is usually found, however, a slight amount of even subtle disorder will allow the above good SG state to form. So where is the disorder or randomness necessary to create a SG? For such strongly frustrated materials a weak, random variation in the exchange interactions could be the cause. Andreanov *et al* (2010) have proposed such a mechanism and showed it is generated by tiny amounts of defect

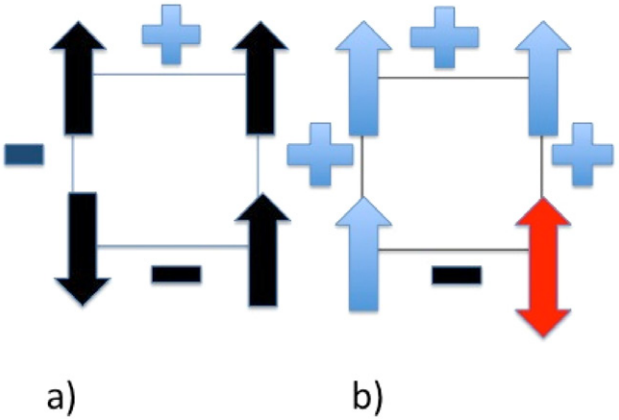

Figure 3. Squares with mixed Ising interactions: + (F) and − (AF). (*a*) Unfrustrated plaquette with the four-bond product $\Phi = 1$, (*b*) Frustrated plaquette with the four-bond product $\Phi = -1$.

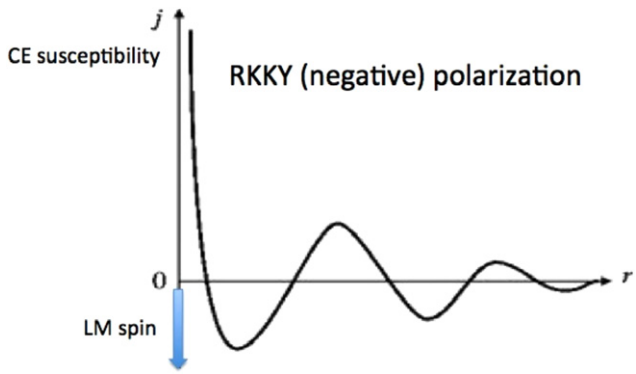

Figure 4. The polarization of the conduction electrons emanating from a local magnetic moment placed at the origin. Here the coupling between LM and CE is negative and follows $\approx \cos(2k_F r)/(2k_F r)^3$ large distance dependence. The '*j*' ordinate could represent the Friedel charge oscillations when a different valence element is inserted into a host.

bonds, random strains, vacancies, etc. Their theoretical calculations (analytic and numerical) with such disorder illustrate the formation of canonical SG with experimental examples.

In order to draw a comparison between the conventional (long-range) ordered magnetic phases and the SG state we show in figure 5 the two valley landscape for F and AF alignments. Note the AF alignments require a propagation **Q**-vector and a spin polarization **e** vector. However, a multivalley landscape is required for SG as given in figure 6. Now there are a multitude of metastable valleys or states available as the SG freezes and time, temperature and magnetic-field dependent hopping is allows between these valleys as the system continuously searches for its final ground state. Figure 6 thereby conveys the essence of the SG frozen phase and is substantiated by the theoretical solutions.

In summary we have the combination of randomness, frustration and competing interactions in a magnetic material that leads to the unique and unconventional phase transition of a SG. If the material meets these three requirements and can be describable by the theoretical models, i.e. dimension, universality class and distribution of exchange interactions, it can be considered 'ideal'. And here there are only a few such ideal materials with which to test in detail the theoretical predictions, e.g. the critical exponents (Mydosh 1993). A further designation 'canonical' SG is that the system exhibits closely the four experimental criteria discussed below in section 3.

Nevertheless, many more materials exist that do not fully possess these three ideal or four canonical criteria, yet they exhibit many of the characteristics of a SG. Here we distinguish between a 'good' SG with indications of a phase transition and SG-like or glassy behavior without a clear SG phase transition. So the experimentalist must then separate or discriminate between long-range F or AF ordering and the non-interacting superparamagnetic systems, i.e. gradual blocking of spin clusters without a phase transition. Somewhere in the middle lies the canonical SG. For material purposes it is not necessary that a new random magnetic magnetic system meets all the above criteria. Still, it is important that a freezing-like behavior occurs distinctly different from the long-range order of the F and AF magnets. In what follows we will illuminate the criteria for establishing a good, canonical or even an ideal SG but first some historical developments.

2. History of spin glasses

During the 1960's (50 or more years ago) the topic of particular interest in condensed matter physics (CMP) was the Kondo effect (Kondo 1964). This was the problem of a single magnetic impurity in a metal interacting with its conduction electrons. Already in 1934 there was the observation of an unexplained upturn in the low-temperature electrical resistivity of the noble metals (de Haas and van den Berg 1934). Figure 7 shows the electrical resistivity for a series of **AuCu**Fe alloys that exhibit the upturn with its intermediate logarithmic temperature dependence. When this effect was established as due magnetic impurities, Kondo (1964) used higher-order perturbation theory to solve the scattering rate between conduction electrons and magnetic impurity. His result showed indeed a logarithmic temperature-dependent increase in the resistivity when spin-flip scattering was considered. Figure 8 sketches the essential behavior of the Kondo interaction. First is shown the conduction electron—impurity spin flip and then the temperature formation of the Kondo compensated bound state. Here the Kondo temperature T_K is defined as the middle point of this crossover to compensated spins. Note that as $T \to 0$ the net spin should disappear.

The Kondo problem, see collection of works in Kondo (2005) and in his recent book Kondo (2013), was the first many body effect in CMP which then opened the way to the modern area of strongly correlated electron physics in which the Kondo effect plays a dramatic role (Wilson 1975, Andrei *et al* 1983, Hewson 1993).

In this period the Kondo problem was all consuming with enormous theoretical efforts and many low-temperature experiments on a variety of impurity doped magnetic materials (Daybell and Steyert 1968). However, the interactions between the impurities (RKKY) were mainly neglected by reducing the impurity concentration c but still going to lower temperatures T to detect the logarithmic resistivity.

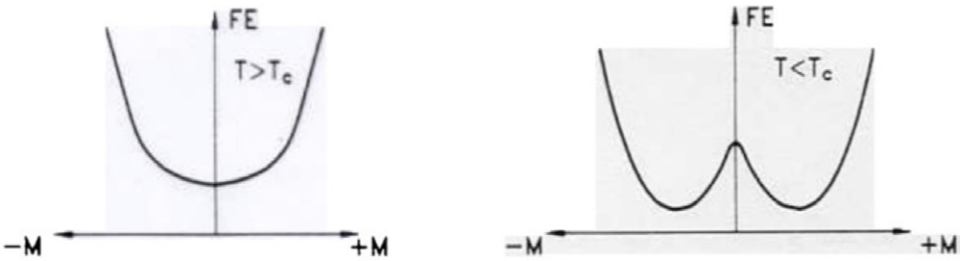

Figure 5. The simple double-valley landscape is most useful for ferromagnetic (F) and all antiferromagnetic (AF) types of long-range order. Note the (AF) structures requires a propagation vector **Q** (could be within a simple two sub-lattice) and a spin polarization alignment vector **e** (could be Ising and perpendicular to propagation direction). The needed factor for various types of AF's is **e**[exp(i **Q**·**r**)].

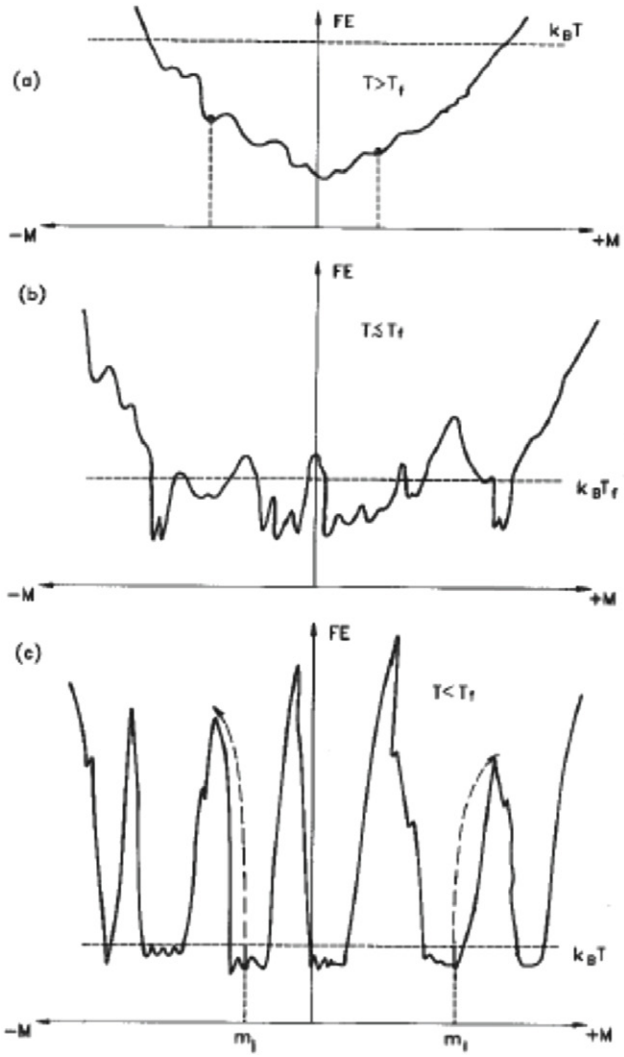

Figure 6. Temperature development of a multivalley landscape, giving the key cartoon description of a SG freeezing transition into one of its multiply allowed valleys of phase space. The dashed arrows indicate the hopping among the metastable valleys as the SG seeks its true equilibrium ground state.

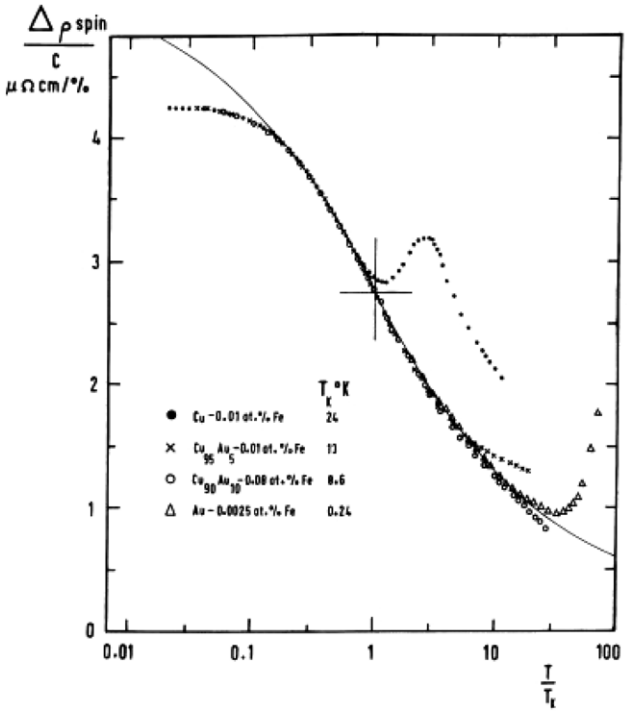

Figure 7. Impurity spin resistivity for a series of mixed ($Au_{1-y}Cu_y$) Fe_x alloys with varying Kondo temperatures from 24 K to 0.24 K. Note the logarithmic temperature behavior surrounding $T/T_K = 1$ and the approaching $[1 - (T/T_K)^2]$ limit as $T \to 0$, where the unitary Fermi-liquid behavior occurs. According to Loram *et al* (1970).

Yet a finite number of magnetic spins is needed to show an experimental effect. The two are related by a scaling factor c/T (at.percent/K) and only for $c/T \ll 1$ can impurity effect be neglected. Nevertheless, the impurity interaction effects will always dominate at low temperatures which are required to determine the unitarity limit of the Kondo effect. Here the hope is that a large Kondo temperature will compensate the magnetic moment so that the RKKY interaction becomes ineffective. The classical example of such behavior is **Cu**Fe with its $T_K = 25$ K where one finds the Fermi liquid $\rho = \rho_o(1 - aT^2)$ resistivity behavior with ρ_o the unitarity or maximum Kondo scattering, see figure 7.

With the possibility of a SG phase transition the emphasis shifted towards the impurity interactions and their cooperative behavior. And thus began the SG problem in 1972 (Cannella and Mydosh 1972). Figure 9 shows the sharp cusps in the low-field, low-frequency ac-susceptibility for **Au**Fe at various concentrations. Figure 10 exhibits the field dependence of the cusps which become already smeared-out in rather low fields, the disturbing problem of high-field dc-susceptibility measurements. So we require a short-time (ac) measurement in a

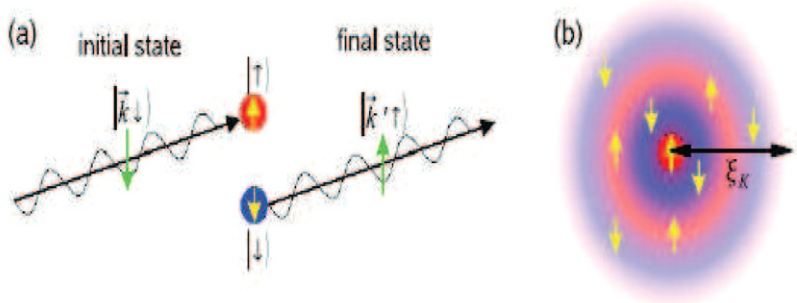

Figure 8. Sketch of the Kondo effect. (*a*) The spin flip scattering of a conduction electron CE(**k**) by a local magnetic spin (LM). (*b*) The resulting bound state of the CE and LM leading to the spin compensated Kondo cloud of radius ξ_K.

tiny external field (few G) to detect the cusp, i.e. the SG phase transition. We now know that the true divergent SG phase transition is represented by the non-linear susceptibility with critical exponent γ (Suzuki 1977).

A few years after the ac-, tiny-field experiments, Edwards and Anderson (1975) used a dynamical description to defined a SG order parameter (OP):

$$q_{\mathrm{EA}} = \lim_{t\to\infty} \lim_{N\to\infty} [< S_i(t_0) S_i(t_0 + t) >]_{\mathrm{av}}. \tag{1}$$

In these limits of ∞-time and ∞-system the SG freezing, i.e. non-zero q_{EA}, is confined to a single valley which is then averaged over all possible valleys. In terms of thermal and configurational averages

$$q_{\mathrm{EA}} = [< S_i >^2]_{\mathrm{av}}. \tag{2}$$

Note the two types of averaging $<\ldots>$ for thermal and [...] for configurational (here a random variable). This breaking of ergodicity gives the local, non-equiblibrium magnetization that is related to the ac-susceptibility via a mean-field-like temperature dependence $q_{\mathrm{EA}}(T) = q^o_{\mathrm{EA}}[1 - (T/T_f)^2]$.

The EA–OP is only non-zero when the system is forever trapped in one of the valleys of our multivalley landscape. Thus q_{EA} represents a single valley non-ergodic, non-equilblium short-time description. Therefore, to obtain the long-time or equilibrium SG state, all the valleys must be scanned, so we require a new and different OP 'q' averaged as the system explores the many possible valleys or phases by hopping from valley to valley. Note $q_{\mathrm{EA}} \neq q$ and the difference $q_{\mathrm{EA}} - q$ is a measure of the degree of broken ergodicity. Experimentally, our ac-susceptibility detects the local 'stuck' valley short-time magnetization via q_{EA}. And if we use field cooling to mimic the equilibrium, ∞-time state we are then detecting the q-OP with a flat ferromagnetic-like magnetization for $T < T_f$ that is time independent. Edwards and Anderson (1975) used a Gaussian distribution of $+/-$ exchange interactions and the replica method (Fischer and Hertz 1991) to calculated the free energy and thermodynamic properties. Figure 11 illustrates the calculated susceptibility and its field dependence for both classical and quantum spins using q_{EA}. Note the clear cusp-like peak at T_f. Erroneously a 'cusp' has been predicted for the specific heat.

The EA model was immediately followed by Sherrington and Kirkpatrick (1975) using an Ising mean-field model

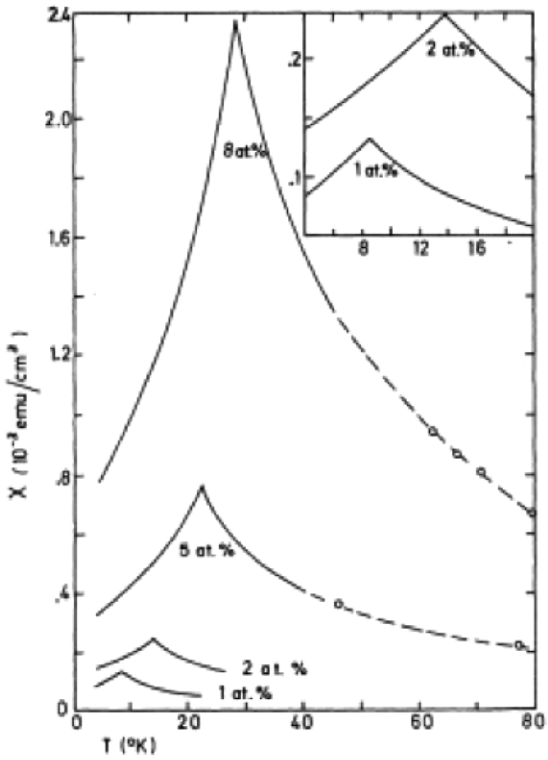

Figure 9. ac-susceptibility in very low driving fields for various concentration AuFe alloys. Note the sharp cusp at the freezing temperature T_f. According to Cannella and Mydosh (1972).

with an infinite-range interaction between all the spins. Here SK derived the SG phase transition through the replica trick with a single OP based on q_{EA}. An experimental realization of this model was carried out by Verbeek *et al* (1978). So was the SG problem solved with EA or SK models? No, because soon afterwards the SK solution was shown to be unstable with negative entropy (de Almeida and Thouless 1978). It took a few years for Parisi (1979), Parisi (1980) to find a stable solution that breaks the replica symmetry of the SK model. This then required a new continuous OP '$q(x)$' that detected the many overlaps of the valleys in the multi-valley landscape (see figure 6). More recent reviews of the SG problem are given by Kawamura (2010) and Campbell and Petit (2010). Some current books on the subject of SG are de Dominicis and Giardina (2006) and Stein and Newman (2013).

3. Basic experimental properties

Here we illustrated the four key, yet simple, bulk measurements which determine a magnetic material to be a 'canonical' SG. First and foremost is the ac-susceptibility (see figure 12) which should be extended to include not only the real χ' part but also the smaller imaginary or dissipative χ'' part. A wide range of frequencies is required to determine how the cusp temperature T_f shifts with frequency ω.

A tiny shift $\Delta T_f/(T_f \ln\omega)$ means a strongly interacting, cooperative freezing SG. Figure 12 (inset) illustrates the expanded behavior of the ac-susceptibility for **Cu**Mn. Note the enlarged data give a frequency shift of 0.005. This tiny frequency shift establishes that **Cu**Mn is a canonical SG. For superparamagnets (a gradual blocking) the frequency shift is much larger ≈0.1–0.3.

The second criterion is the dc-magnetization (M) in the field-cooled (FC) and zero-field-cooled (ZFC) states. After ZFC to a $T \ll T_f$, a small external field is applied to the $M = 0$ state. Here there is a small jump in the M and the beginning a time-dependent creep upwards in $M(H)$. Figure 13 shows the crucial difference between time-dependent ZFC and static FC. For the canonical SG the irreversible temperature, where the first deviation between ZFC and FC occurs, coincides with the T_f from the cusp. Upon FC a displaced (shifted to negative fields) hysteresis loop ensues; this is in contrast to the ZFC symmetric loop around the origin. Note we have mimicked the ∞-time equilibrium SG state by FC in constant field.

The third measurement of the magnetic specific heat C_m is used to distinguish conventional F or AF transitions from that of a SG using the entropy dependence of the phase transition. Figure 14 illustrates the low T linear dependence of C_m related to the intrinsic spin disorder. Here a two-level-system model was used to calculate the disorder caused linearity (Anderson *et al* 1972). The magnetic specific heat breaks away from its linear-in-T dependence at T_f followed by a broad maximum 20–40 percent above T_f. There is then a C_m(T) fall-off usually related roughly to $1/T$ behavior. This slow decrease indicates a smeared-out entropy persisting to $T \gg T_f$, so that 70–80 percent of the spin degrees of freedom are lost above T_f. Thus the SG phase transition is unique compared to the sharp specific heat divergence and dramatic loss of entropy at a F or AF critical point.

A final criterion is used to detect the unique metastable SG state through its aging process. Figure 15 sketches the protocol of FC or ZFC cooling a SG and then waiting a length of time t_w before reducing or increasing the field H. After 10^2–10^4 s of t_w there are significant change in the metastable relaxation rates of $M(t)$. Figure 16 shows the different behavior as a function of t_w. When the relaxation is plotted as $S(t) = (1/H)\partial M/\partial \ln t$, a maximum is found at t_w (Koper and Hilhorst 1988, Koper and Hilhorst 1989). The waiting-time effect is a unique characteristic of the SG phase. For a recent description of the effects of thermal quenching on the SG aging, see Rodriguez *et al* (2013). The modeling used here is that the dT/dt quenching rate shuffles the barrier heights separating the metastable states and thereby affects the aging and decay times.

4. Early theories and models

Since there have been extensive treatments, overviews and reviews of SG theory, here we only list the main historical trends with a digest of references. The three early treatises focusing on SG theory are: Binder and Young (1986), Mezard, Parisi and Virasolo (1986) and Fischer and Hertz (1991). As the field was evolving a series of topical conferences took place that delved into various aspects of the SG problem. We mention here: The Rome Conference on Disordered Systems and Localization (Castellani *et al* 1981), Heidelberg Colloquium on Spin Glasses (van Hemmen and Morgenstern 1983) and Heidelberg Colloquium on Glassy Dynamics (van Hemmen and Morgenstern 1986). A more recent collection of SG contributions is by Young (1997).

The first issue after Parisi's (1979, 1980) mainly mathematical replica symmetry breaking model was to determine its physical significance and create a simple intuitive picture for the experimentalists. This was only accomplished later with the multivalley sketch (see figure 6) and by calculating the overlaps or correlations of local magnetization states and their quest to reach the equilibrium ground state (Mezard *et al* 1986). Parisi's continuous order parameter $q(x)$, where $0 \leqslant x \leqslant 1$, is a function of temperature and field that only reaches q_{EA} as $x \to 1$, i.e. the largest overlaps. The continuum of possible overlaps between the phases can be calculated by an overlap distribution probability $P(q)$. However, $q(x)$ and $P(q)$ are impossible to directly measure and can only be indirectly inferred from dynamical experiments.

An alternative dynamical interpretation of this replica symmetry breaking model was proposed by Sompolinsky and Zippelius (1981). Now the order parameter became time dependent with a continuous time variable representing the vast distribution of relaxation rates $1/\tau$. The physical picture here is a sudden jump at T_f in the distribution function of relaxation times $P(\tau)$ from fast and sharp to slow and broad. Accordingly, the SG phase is characterized by time dependences in both the spin correlation and the response function that exhibit weak algebraic time decays.

The hectic theoretical efforts continued into the mid-1980's with the advent of the short-range SG droplet model (Fisher and Huse 1986) contrasting to the infinite-range Ising models discussed above. Here a simple scaling *Ansatz* was proposed based on the result of domain-wall renormalization-group numerics (Bray and Moore 1985). Then the decay of the static and dynamic correlation functions, which are dominated by low-energy droplet excitations, were tracked at large distances. For a droplet of reversed spins within the frozen SG matrix, its free energy is $F_L \approx Y(T)\, L^{\theta}$, where Y is the spin stiftness and L the scale of the low-lying droplet excitations. If $\theta < 0$, e.g. that expected for a 2D SG, then the low-lying excitations can be created on longer length scales thereby destroying the SG phase. However, when θ is positive a SG phase transitions can be found in 3D, characterized by a diverging non-linear susceptibility. The key prediction of the droplet model is that the de Almeida–Thouless (AT) line (H versus T phase line) does not represent a phase transition, as it does in the replica symmetry breaking (RSB) model, but, in contrast, is a dynamical crossover. Even today (Young 2013)

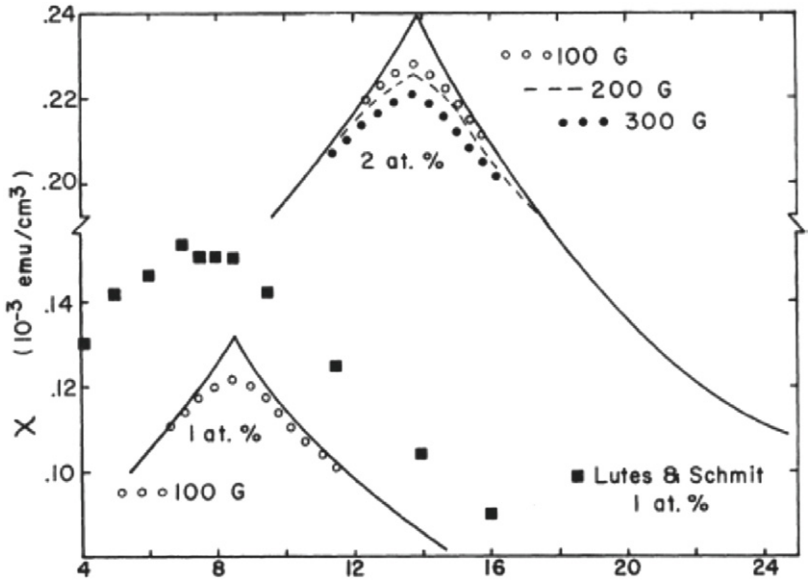

Figure 10. Field dependence of the ac-susceptibility for two AuFe alloys. Note the rapid field smearing even in very small external fields. This is the reason why Lutes and Schmid missed the SG phase transition. According to Cannella and Mydosh (1972).

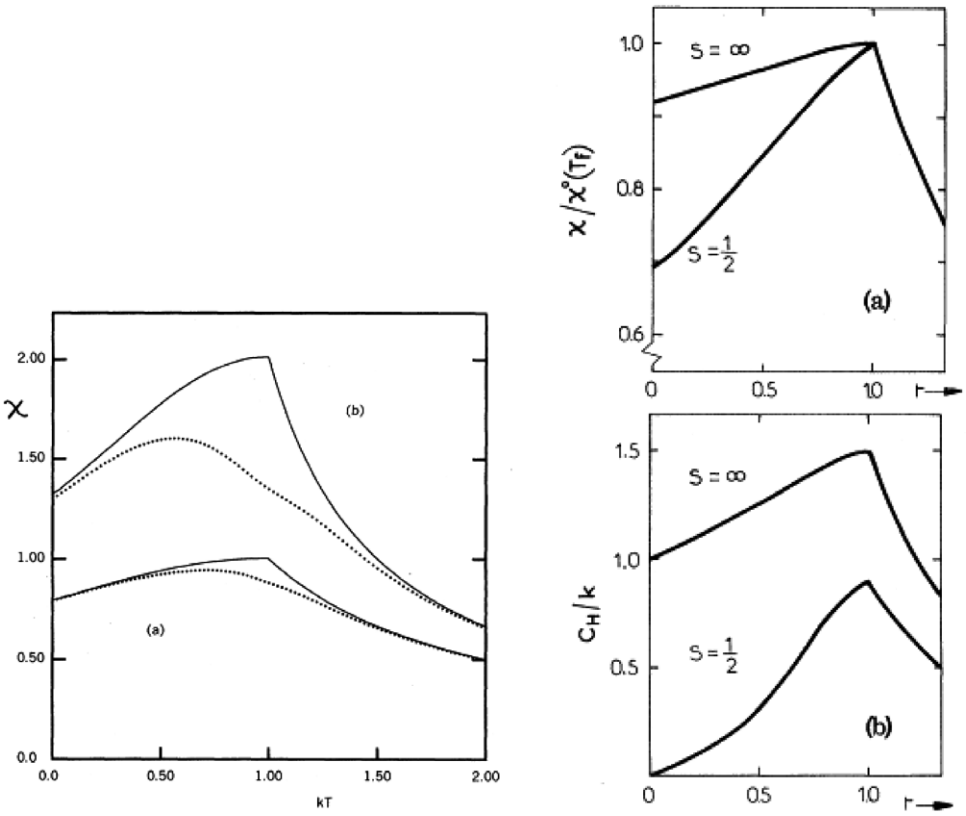

Figure 11. Left: Theoretical calculations of differential susceptibility from SK model for different values, (*a*) and (*b*), of the Gaussian distribution of exchange coupling. Note the clear smearing of the cusp with an applied magnetic field (dotted line). According to Sherrington and Kirkpatrick (1975). Right: Susceptibility and specific heat calculations from the EA model for classical and quantum spins. Note the cusp in the specific heat which latter experiment and theory showed to be incorrect due to the large spin fluctuations and short-range order preceding T_f. According to Fischer (1975). For more description, see Mydosh (1993).

this distinction is still being debated with experiment favoring a dynamical crossover yet new, beyond the mean field theory, RSB results do predict a SG phase transition (Leuzzi *et al* 2009). So the controversy continues with disputes over exactly how to perform the finite-size scaling, see section 6.1 below.

5. The SDW model

Many years ago Overhauser (1959) proposed a new type of excited collective state of the conduction electron gas, i.e. a Fermi surface (FS) instability due to nested portions of the

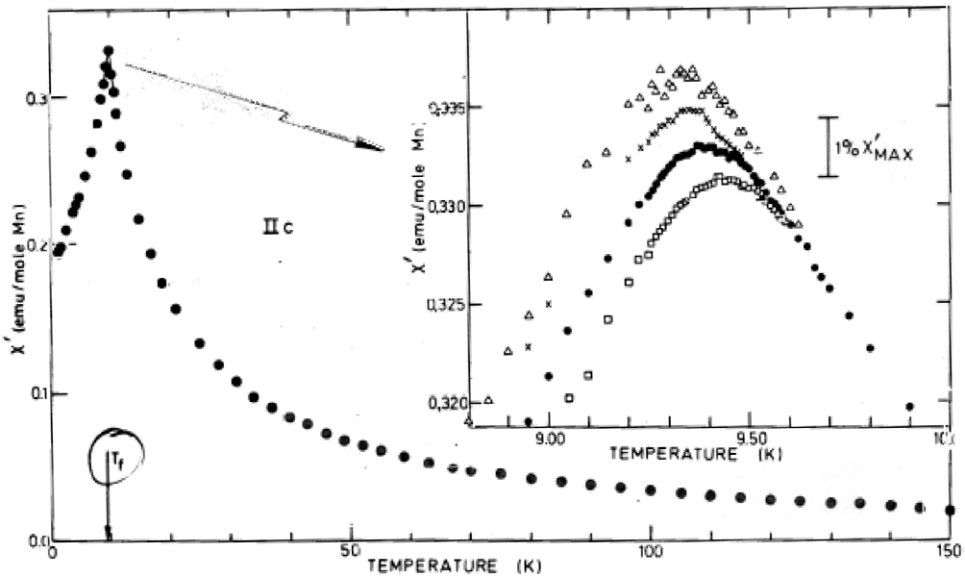

Figure 12. Real part of the ac-susceptibility versus T for **Cu**Mn. Inset: greatly expanded view of the SG cusp near T_f. The sharp cusp at T_f is greatly expanded to show the subtle frequency dependence in the inset. Here the frequency shift is 0.005 signifying a strongly cooperative SG phase transition. According to Mulder *et al* (1981) and see Mydosh (1993).

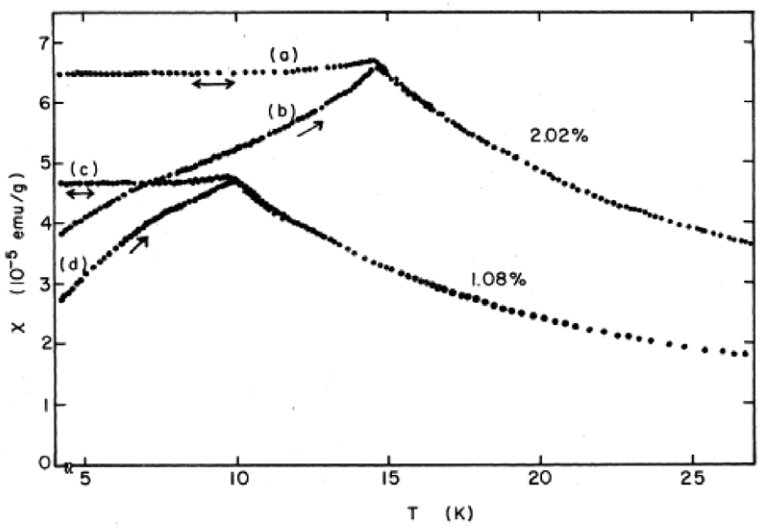

Figure 13. FC and ZFC of static susceptible ($\chi = M/H$) for **Cu**Mn alloys in a field of 6 Oe. Note that the ZFC magnetization becomes time-dependent as the temperature is increased, while the FC magnetization is reversible. According to Nagata *et al* (1979) and see Mydosh (1993).

FS. This then became know as a spin or charge density wave. Now almost 55 years later the SDW and CDW concepts have been fully incorporated into many aspects of condensed matter physics. For Cr the SDW picture (Overhauser 1962) has become universal, yet still debated in its fine points and recently a CDW was added to the Cr behavior. The key feature here is that the SDW or CDW can be related to a nesting vector $\mathbf{Q}_{FS}$ between the Fermi surface shapes and not to the reciprocal lattice vector of the Bravais lattice $\mathbf{Q}_{\mathrm{BL}}$.

When the spin glasses appeared to manifest a phase transition, Cable *et al* (1982) began characterizing it as a SDW and their model system was **Cu**Mn. This alloy was of particular interest to the neutron scattering community and they provided the experimental evidence for a SDW-like description (Cable *et al* 1984).

The SDW model exhibits a modulated conduction wave density

$$\mathbf{s}(\mathbf{R}) = bN\epsilon \cos(\mathbf{q}\cdot\mathbf{R}), \tag{3}$$

with b the SDW order parameter, N the number of conduction electrons for, e.g. Cu and ϵ their polarization. $\mathbf{q}$ represents the propagation direction and inverse wavelength in the lattice $\mathbf{R}$. However, energy is required for the SDW formation: $W = 8NCb^2/9\zeta$. Here C is the Fermi gas correlation length and ζ an inverse measure of the electron–electron interaction exchange integral J. The paramagnetic Mn impurity spins $\mathbf{S}_j(\mathrm{R}_j)$ will now interact with the SDW via the $s-d$ (or $s-f$) exchange interactions G. These spins then experience an effective field

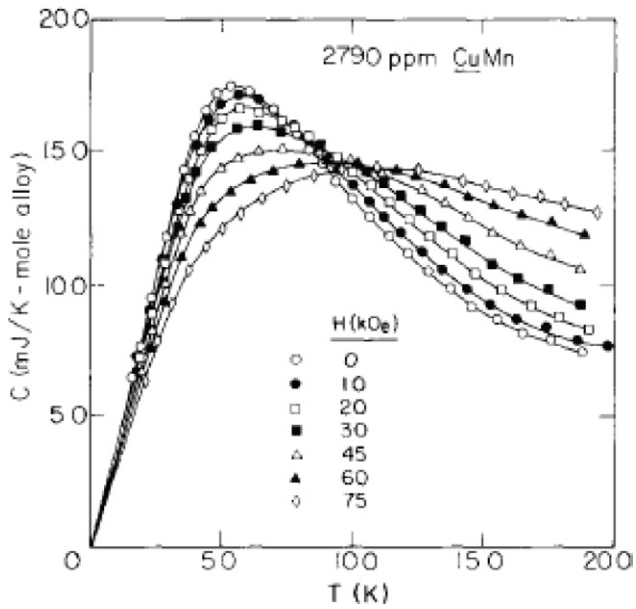

Figure 14. Magnetic contribution to the specific heat (C_m) of **Cu**Mn (0.3 at.% Mn) versus temperature in various magnetic fields Although T_f is 3.0 K the maximum in C is at 5 K only by plotting $C_m/T = dS_m/dT$ do we find some indications of T_f. Theory indicates a large negative critical α exponent which would produce a broad maximum at T_f. Due to short-range correlation above T_f it is most difficult to detect the freezing temperature in specific heat measurements. This non-effect is a true characteristic of the canonical SG behavior. According to Brodale *et al* (1983) and see Mydosh (1993).

$$\mathbf{H}_j(R_j) = Gb\epsilon \cos(\mathbf{q}\cdot\mathbf{R_j}). \tag{4}$$

Thus the interaction energy needed for the formation of a SDW in, e.g. **Cu**Mn is $-\boldsymbol{H}_j\cdot\mathbf{S}_j \gtrsim W$. So we have a putative magnetic impurity induced SDW.

The neutron scattering does indeed show a long-periodic modulation at an incommensurate wave vector (Cable *et al* 1984)). Figure 17 for $Cu_{0.75}$ $Mn_{0.25}$ exhibits this magnetic (spin-flip) intensity along with the non-magnetic nuclear scattering that is commensurate. Based upon the former we can model a long-period SDW modulation of wave vector

$$\mathbf{Q}_\mathrm{M} = 2\pi[\mathbf{b}_1 + (1/2 \pm \delta)\mathbf{b}_3], \tag{5}$$

representing a sinusoidal modulation along z with period $a_o/(1/2 - \delta)$. δ represents the incommensurability factor. In the x–y plane

$$\mathbf{S}_{x,y}(R) = P_\mathrm{R} S_\mathrm{Mn}[\cos, \sin(\mathbf{Q}_\mathrm{M}\cdot\mathrm{R} + \phi)], \tag{6}$$

with P_R the polarization of impurity spin S_Mn.

By substituting the spin–spin correlation function into the quasi-elastic paramagnetic scattering cross section Cable *et al* (1984) were able to find good agreement with experiment. However, note that the primary scattering peak at $(1, 0, 1/2 - \delta)$ is not resolution limited, thus it is not a true Braag peak or signature of long-range order. The peak halfwidth is $\Gamma = 0.045\ \pi/a_o$, thereby giving a Gaussian correlation range $\xi = 2(\sqrt{\ln 2})/\Gamma \approx 20$ Å depending on the Mn concentration x. Therefore the SDW is truncated and becomes short range by changing its propagation $\mathbf{Q_M}$ directions according to the multiple nesting vectors associated with the eight extended necks of the Cu–FS in an fcc lattice. This randomness of **Q** creates the SG state. If there were a single propagation vector as in hcp YGd, then a long-range SDW transition would occur. Figure 18 illustrates and contrasts the behavior of SG **Cu**Mn, i.e. a 'short-range SDW', with the generic or conventional SDW transition of **Y**Gd (Mydosh 1988). This comparative result (SR-SDW versus LR-SDW) is firmly based on on bulk measurements, e.g. susceptibility, specific heat and resistivity along with neutron scattering (Wenger *et al* 1986). Note that this short-range SDW model is currently being used to describe the coexistence of pnictide superconductivity and SDW, see section 8.1.

6. Present state of SG behavior

6.1. Large scale computer simulations

As mentioned in section 1 despite more than four decades of research efforts on spin glasses there still remain various controversies so that a complete understanding of the SG state has not yet been attained. In order to alleviate these remaining, mainly theoretical, issues present-day research has focused on numerical calculations using large scale simulations from special-purpose computers and massive parallel-processing machines (Yavors'kii and Weigel 2012). Early on it was found that Monte Carlo (MC) methods were ideal for computational simulations of SG (Binder and Young 1986, Mydosh 1993, Young 2002). Now a cottage industry has developed for MC simulations of the EA SG according to their dimensionality (upper and lower), universality class (Ising, x–y and Heisenberg) and with an applied field the AT (Ising spins) and GT (vector spins) lines (Larson *et al* 2013). Recent simulation results agree on a clear, large finite-temperature SG phase transition for Ising 3D but with $T = 0$ in 2D. The x–y and Heisenberg SG are more uncertain in 3D with a much lower, yet finite T, phase transition at $T_f \to 0$ (Sharma and Young 2011a, 2011b).

The key to discriminating a SG phase transition from the MC simulations is the use of the finite size scaling (FSS) function Υ:

$$\xi_L^\mathrm{SG}/L = \Upsilon\left\{L^{1/\nu}[T - T_f(H_r)]\right\}, \tag{7}$$

where ξ_L^SG is the correlation length of a finite system of size L, ν is the correlation length exponent and T_f the freezing (SG phase transition) temperature. T_f can also be a function of a (random) magnetic field. Figure 19 shows the simulation results for a 3D Ising EA Gaussian SG. Here all L-sizes intersect at $T \cong 0.95$. However for the 3D Heisenberg class the collective crossings require larger sizes and occur at a lower $T \cong 0.13$, see figure 20. The chiral glass transition seems to take place at a higher $T \cong 0.14$, see section 6.2 below, (Fernandez *et al* 2009).

The most recent efforts use the highly optimized graphics processing units or GPU codes that greatly speed up the simulations allowing one to tackle the AT or GT SG in magnetic

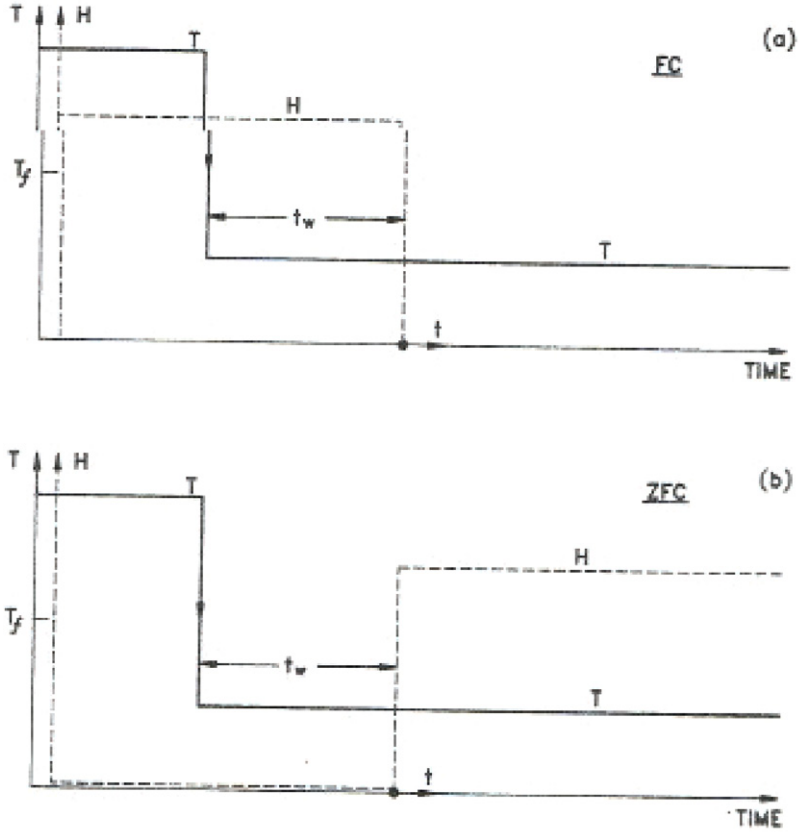

Figure 15. Protocol of FC-ZFC 'waiting-time' magnetization experiments. (*a*) FC, t_w, field-off and measure $M(t)$. (*b*) ZFC, t_w, field-on and measure $M(t)$.

fields (Yavors'kii and Weigel 2012). This is one of the outstanding remaining issues of the SG problem. However, the results are not conclusive, yet there remain indications of dynamical behavior along the AT line, thus no phase transition $(T - H)$ line. Nevertheless, there are still ongoing efforts to finalizes this long-standing question which has significant implications for the controversy between the RSB and droplets models (Leuzzi *et al* 2011, Larson *et al* 2013).

6.2. Chiral glasses

A different type of phase transition for glassy-like behavior was proposed more than 20 years ago by Kawamura (1992), viz., a chiral glass (CG). This symmetry breaking can occur in vector spin systems (x–y or Heisenberg) as illustrated in figure 21. For a Heisenberg material the chiral order parameter is

$$q^{\mu}_{\mathrm{CG},i} = \kappa_i^{\mu(1)}\kappa_i^{\mu(2)}, \tag{8}$$

where μ is a unit vector of the spin triad and

$$\kappa_i^{\mu} = \mathbf{S}_{i+\mu}\cdot(\mathbf{S}_i \times \mathbf{S}_{i-\mu}). \tag{9}$$

$q^{\mu}_{\mathrm{CG},i}$ can be calculated via Monte Carlo simulations that allow the correlation length to be determined as in section 6.1. Then an FSS-analysis on various system sizes would establish the chiral phase transition, see figure 20. Here a comparison is drawn between SG and CG from their L-dependencies. And it appears for the 3D Heisenberg system the CG wins, i.e. its $\xi_{\mathrm{CG}}(T)$ diverges before the SG $\xi_{\mathrm{SG}}(T)$ (Fernandez *et al* 2009, Kawamura 2010). Figure 22 shows these temperature dependencies where the CG phase transition precedes that of the SG.

Unfortunately, one must rely on computer simulations for the CG because its order parameter and predicted critical behavior differ only slightly from those of a SG and are not readily accessible from experiment. Possibly an accurate experimental evaluation of the critical exponents and scaling relations between the CG and SG transitions, when compared with simulation results, would reveal the winner (Kawamura 2010, Campbell and Petit 2010).

6.3. Quantum spin glasses

Can we experimentally 'tune', i.e. reduce, a canonical SG phase transition to near $T = 0$ and study its properties at the lowest possible temperature? This $T = 0$ case then becomes a quantum critical point (QCP) and it represents a quantum phase transition (QPT). Experimentalists can tune the starting phase to a QCP by applying pressure, magnetic field and doping/disorder. Especially interesting here is to use a good Ising SG with a low T_f and subject the SG to a large transverse field, $H_{\perp}$. Theory calculates that quantum fluctuations ($\propto H_{\perp}^2$) are formed that destroy the 'classical' SG phase transition and create a QPT at $T = 0$ (Read *et al* 1995, Sachdev 2011). Beginning in the mid-1990's there has been a flurry of theoretical activity to predict the behavior of quantum SG. Early theoretical predictions for SG in the quantum regime, mainly

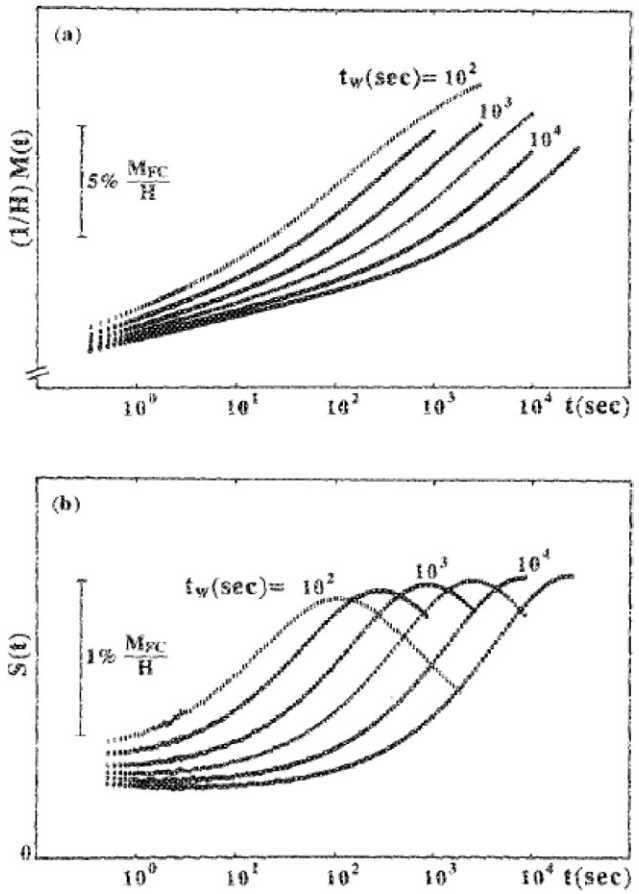

Figure 16. Results of $M(t)$ and $S(t) = (1/H)\partial M/\partial \ln t$ after different waiting times according to the protocol in figure 15. Note the strong dependence on the waiting time, t_w. According to Sandlund *et al* (1988).

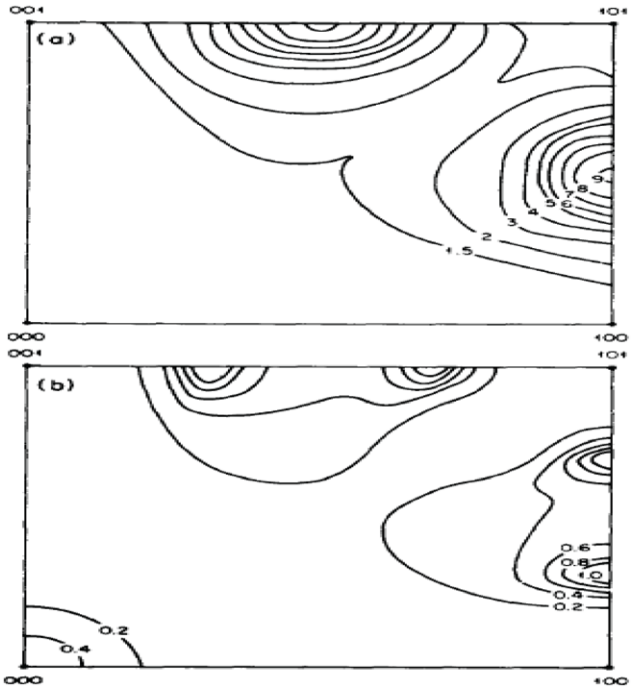

Figure 17. Neutron scattering intensities on **Cu**Mn of commensurate nuclear scattering (*a*) and incommensurate magnetic scattering (*b*) representing the short-range SDW. Note the broadened incommensurate peaks on the right side of (*b*). According to Cable *et al* (1984).

relying on quantum Monte Carlo simulations, include Guo *et al* (1994), 146] and Kopec (1997).

$LiHoF_4$ is a insulating dipole-coupled Ising ferromagnetic ($T_C = 1.5$ K) which when diluted with non-magnetic Y becomes a putative SG. This material has recently received particular attention as to the nature of its SG state. Jönsson *et al* (2007) have observed no divergences in both the linear and non-linear susceptibilities for $LiHo_xY_{1-x}F_4$ with $x = 0.16$ and 0.05. Oppositely, Quilliam *et al* (2012) via dynamical scaling analyses evidence a finite temperature SG phase transition. The debate has continued with the latest results of Piatek *et al* (2013) for $LiHo_xEr_{1-x}F_4$, a mixed Ising—X–Y magnet. These authors conclude the formation of an extended in temperature SG phase using ac-susceptibility and neutron scattering.

By applying a small $H_\perp$ ($\approx$1 T) to $LiHo_{0.167}Y_{0.833}F_4$, the classical SG transition ($T_f = 0.13$ K) can be reduced to a few mK (Wu *et al* 1993). Here there was the claim of a good realization of the classical random-field Ising model (Tabei *et al* 2006). By increasing the transverse magnetic field the hope for a quantum SG phase was used to probe the reduced temperature SG via ac-susceptibility—linear and nonlinear—and as $H_\perp$ was increased and thereby to test the theoretical predictions of moving through the QCP. Here a diverging χ_{nl}, the key criticality of the SG phase transition, was observed in zero-field but it became smeared-out as the $T \to 0$, see figure 23 (Wu *et al* 1993). So the predicted unique frequency-dependent divergences of the quantum SG were not observed and a QCP was not distinguishable. Controversy has entailed the SG state of $Li(HoY)F_4$ with two recent linear/nonlinear susceptibility and magnetization investigations. Accordingly, Jönsson *et al* (2007) claim the absence of both conventional and quantum SG transitions. Contrarily, Ancona-Torres *et al* (2008) presented new susceptibility measurements to verify their earlier assertion of canonical SG behavior. A muon spin relaxation study of $LiHo_xY_{1-x}F_4$ has also found that this compound is not a canonical SG, yet its ground state does exhibit glassy dynamics of a single relaxation time related to a hyperfine interaction (Rodriguez *et al* 2010). So, at present, we do not have a clear proof for both the conventional and quantum SG states in $LiHo(Y; Er)F_4$.

Additional attempts at finding a quantum SG have failed. Some proposals were to use the intermetallic compound $Y_{1-x}Tb_xNi_2Si_2$, a good, metallic Ising SG at a few K for $x < 0.3$ (Wiener *et al* 2000) and URh_2Ge_2, a random-bond (Rh on Ge sites) metallic Ising SG that could be tuned by both annealing and $H_\perp$ (Süllow *et al* 1997). Figure 23 shows the measured phase diagram for the tuning of a quantum SG with $H_\perp$ based upon the $Li(HoY)F_4$ situation. Note the smearing of the susceptibilities (lack of criticality) as the putative QCP is approached. With URh_2Ge_2 one would use a combination of annealing/quenching to increase the random-bond substitutional disorder of the Rh–Ge site exchange, along with the application of $H_\perp$ to tune $T_f \to 0$. Nevertheless, the experimental demands for such low-T, non-linear susceptibility

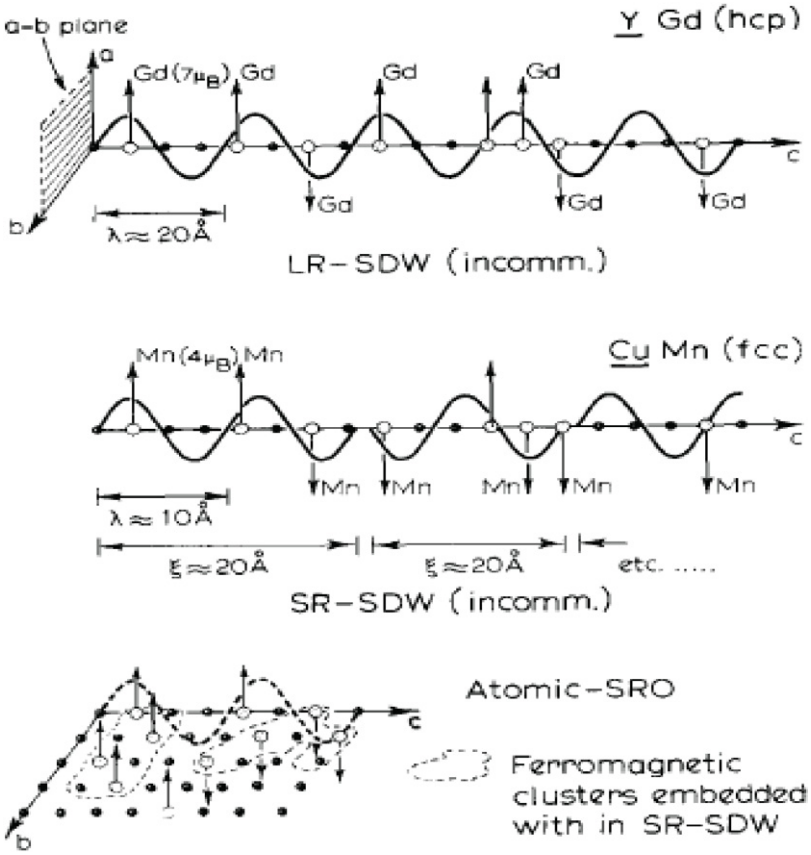

Figure 18. Sketch of the comparison between a short-range (SR-)SDW where the propagation direction $\mathbf{Q}_{SDW}$ changes/switches on a short-range scale, e.g. **Cu**Mn and the conventional long-range SDW of **Y**Gd with only one $\mathbf{Q}_{SDW}$. The SR-SDW displays all the bulk properties of a SG. According to Mydosh (1988).

studies have far exceeded the willingness of experimentalist to attempt them. Therefore, as of today, there is no hard realization of a quantum SG.

7. Spin-off's

The SG phenomenon has long left the regime of random magnetic materials and splashed down into many other areas of science and pseudo-science. Mainly driven by the analytic theories and model-concepts and the computer simulations and algorithms, there are numerous applications of the original SG notions and systems thinking. New, at the very beginning, was the 'physics of complexity' waiting to be applied to these other fields. Recall that all this started 40+ years ago with randomness, competing interactions and frustration that could be depicted by the temperature evolution of the rough multi-valley landscape in phase transitions.

In table 1 we list a collection of these non-magnetic spin-off's to illustrate their extensiveness. Since most of these topics are so broad, their discussion is beyond the scope of this review. Here we recommend the reader to use Google *et al* to obtain the vast amount of information and details about these many spin-off's. Three recent (beyond 1993) topics are: (i) the vortex glass which is a frozen random distribution of magnetic-flux vortices in the type-II high-temperature superconducting state (Blatter *et al* 1994). (ii) the ferroic glasses, displacive ferroelectrics of perovskite exhibiting frequency dependent peaks in the dielectric susceptibilities (relaxors) (Sherrington 2013). (iii) the social networks use SG theory to construct the collective action of links and nodes between various individual collaborators (Matthews 2008).

8. New SG materials and topical behavior

At present (2014) experimental work on SG is mainly driven by the ever-increasing variety of new, mostly strongly correlated electron materials that have been recently fabricated. The magnetic disorder occurs intentionally through alloying, doping, substitutions, etc or unintentionally via (anti)site-mixing, strains, grain boundaries, etc. Which of these materials can we relate to a canonical SG phase transition? Or are they inhomogeneous cluster glasses and superparamagnets with slow crossover behavior towards a glassy ground state? We, for simplicity, omit the cases/examples of long-range-ordered magnetic phase transitions. Materials science and chemistry play a major role in creating these SG-like systems, subsequently leaving to physics to characterize their SG or glassy behavior. A digest of the most interesting topical materials is given in the next sub-sections where we have a resurgence of attention towards basic SG behavior and, in general, glassy dynamics.

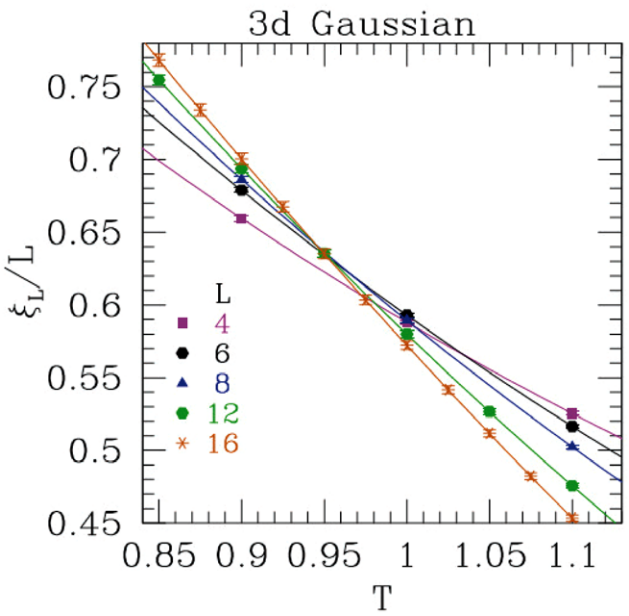

Figure 19. MC simulations using finite-size scalling (FSS) to detect the SG phase transition for the 3D Ising E–A (Gaussian) model. Note the strong crossings of the various system sizes around $T = 1$, indicating a finite temperature SG phase transition. According to Katzgraber *et al* (2006).

8.1. Superconductors

The (near) coexistence of SG and superconducting (SC) phases has been established for many years both experimentally and theoretical (Hüser *et al* 1983, Galitski and Larkin 2002). These mixed system were mainly alloyed pseudo-binary intermetallic compounds with intentional random-site disorder. While the SC T_c^S and the critical fields (H_{c2}) were weakly reduced (or theoretically enhanced) there was a small phase region of clear coexistence of SG and SC.

However, today's efforts for coexistence have focused upon the high temperature superconducting (HTS) oxides and more recently on the Fe-pnictides and Fe-chalcogenides. Figure 24 shows a traditional phase diagram for the HTS cuprates. As the long-range antiferromagnetic order disappears and before the superconducting dome begins, a small putative SG wedge occurs for the hole doped HTS, with no corresponding SG-like phase for the electron doped cuprates.

And there has been considerable experimental work to define a SG glass phase in this small wedge region of figure 24 beginning with Chou *et al* (1995) on $La_{1.96}Sr_{0.04}CuO_4$, as such was early on predicted by Aharony *et al* (1988). Their bulk static measurements detected a good SG transition in a hole-doped regime where neither long-range antiferromagnetism nor SC occurred, i.e. no coexistence. Yet without frequency and time dependent experiments the question remained: How canonical was this cuprate SG? A multitude of additional experiments followed using muon spin relaxation and ac-susceptibility techniques, both long-standing methods often employed to characterize the microsecond dynamics of canonical metallic SG. For the cuprates a dynamical coexistence (phase overlap) was claimed between SG freezing and SC over a small region of hole doping ending in a quantum critical point (Panagopoulos *et al* 2002). However, the word SG is now used in the context of a (cluster) glassy freezing behavior rather than a canonical SG phase transition. Further work extended the glassiness to a 'charge glass' based upon magnetotrasport and noise studies (Raicevic *et al* 2008). When Zn is substituted for Cu the superconductivity is suppressed along with the glassy freezing (Panagopoulos *et al* 2004). Very recent full-detailed experiments on Ni-doped $La_{1.85}Sr_{0.15}CuO_4$ have clearly demonstrated the existence of a canonical SG, but only when the magnetic nature of Ni has quenched the superconductivity (Malinowski *et al* 2011). This paper includes a large number of references describing the quite common SG phases in the transition metal oxides due to the chemical doping with heterovalent cations. A recent inelastic neutron scattering experiment of $Bi_{2+x}Sr_{2-x}CuO_6$ has detected spin fluctuations scanning the SG to SC phase boundary. An incommensurability factor that is proportional to the hole concentration tunes tiny regions of SG and SC coexistence (Enoki *et al* 2013). So for the cuprates we can conclude that a canonical SG does not coexist with a HTS. Nevertheless, there indeed occurs a frozen glassy state in the cuprate phase diagram, most probably due to a slowing down of the antiferromagnetic (quantum) fluctuations with doping.

More recent searches for possible SG and SC coexistence are the Fe-based pnictides and chalcogenides. The Fe-pnictides have a similar phase diagram to the cuprates and their evolution is out of an antiferromagnetic phase through a putative glassy state into the (≈50 K T_c^S max) HTS. Now, however, the antiferromagnetism is not of localized moments but more itinerant in character for these pnictide semimetals, i.e. a SDW begins at the undoped compound. As the various dopings increase the formation temperature of the SDW decreases and overlaps with the superconducting dome. Figure 25 exhibits such $T - x$ phases for various pnictides and poses the question is there an intervening SG coexistence or even a SG discrete phase? An appealing interpretation for coexistence is that of a short-range SDW SG as discussed in section 5. Because of the intrinsic disorder and multiple Fermi surface nestings, the the SDW cannot propagate in a single direction over long distances, so it becomes truncated and switches its direction, thus its properties become that of a SG. Very recently a series of bulk measurements detected a full range of SG or cluster glass behavior for KFe_2As_2 (Grinenko *et al* 2013). Here the disorder is due off-stoichiometry of the Fe, a common problem with these materials, or a random site substitution Fe–As. Further evidence for coexistence, but now in macroscopic phase separation, comes from muon spin relaxation in $LaFeAsO_{0.94}F_{0.06}$ (Takeshita and Kadono 2008, Takeshita and Kadono 2009). And in $BaFe_2As_2$ doped with Cr or Ni the superconductivity is rapidly quenched and the SG state evolves into a cluster glass with increase Cr or Ni (Xu *et al* 2012). As work continues on the pnicitdes spatially resolved spectroscopy (STM/STS) has revealed the microscopic coexistence of SDW and superconductivity in $NaFe_{1-x}Co_xAs$ (Cai *et al* 2013). For $Ba_{1-x}KFe_2As_2$ a collection of transport, XRD and neutron diffraction measurements have proposed an overlapping phase diagram in which there is a clear coexistence between the SDW and the SC phases for $0.2 < x < 0.4$ (Chen *et al* 2009).

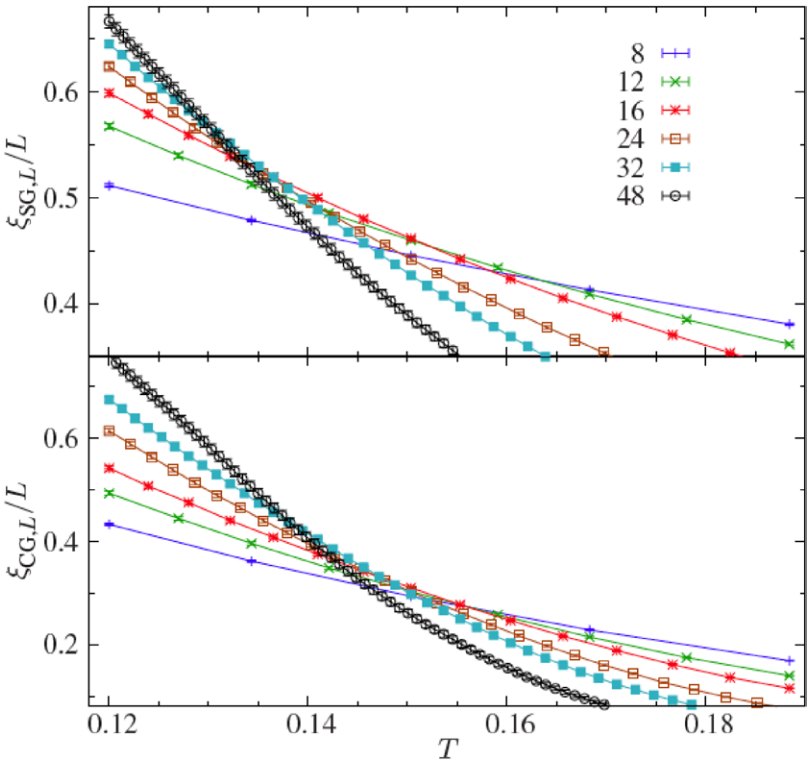

Figure 20. MC simulations and FSS for the 3D Heisenberg E–A model. Upper curve: SG; lower curve: chiral glass (CG). Here the size crossings are at a much lower temperature, $\approx T = 0.1$. This calls into question the possibility of the SG phase transition. Note the chiral glass (CG) T-crossings are at a slightly higher temperature than the SG one; this adds to the possibility of a chiral-glass phase transition. According to Fernandez *et al* (2009) and Kawamura (2010)..

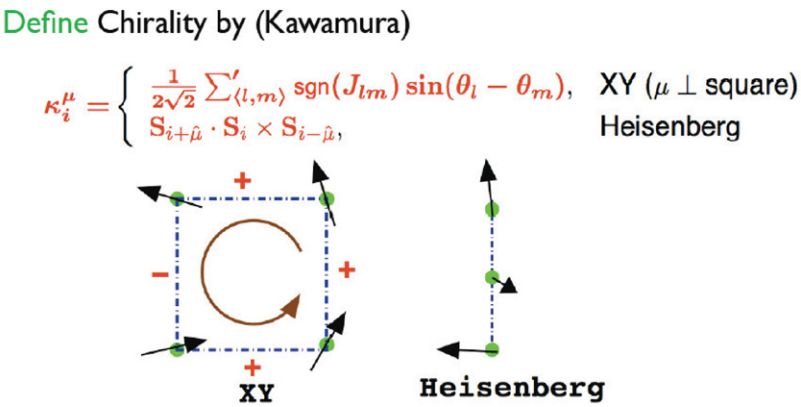

Figure 21. Sketch of the definition of the chiral symmetry breaking leading to the possibility of a chiral-glass phase transition. According to Kawamura (1992); from P Young, lecture notes, unpublished.

However, the question remains open: Is the SDW short range and therefore SG-like. Recent ^{75}As NMR has shown frozen antiferromagnetic domains coexisting with superconductivity in $Ba(Fe_{1-x}Co_x)_2As_2$ (Dioguardi *et al* 2013). Since long-range antiferromagnetic can be excluded, the interpretation is of a frozen cluster-glass behavior. A recent series of thermodynamic measurements on $EuFe_2(As_{1-x}P_x)_2$ has shown a small coexistence region of Eu SG behavior with 25 K T_c superconductivity (Zapf *et al* 2013). The SG behavior is preceded by another coexisting canted antiferromagnetic phase also of the Eu^{2+} moments. Returning to the $BaFe_{2-x}Ni_xAs_2$ pnictide very new neutron scattering experiments claim with Ni doping that optimum superconductivity occurs when the antiferromagnetism order becomes short-range and incommensurate (Lu *et al* 2014). The authors describe this magnetic state as a cluster SG with a mesoscopically separation from the superconducting phase. Nevertheless, we would revert to section 5 and use the concept of a short-range SDW that propagates inhomogeneously through the superconducting matrix. The nearly localized blocks of SDW with different **Q**'s could be mistaken as an antiferromagnetic cluster glass.

The chalcogenides, e.g. $Fe_{1+y}Se_xTe_{1-x}$ also exhibit indications for a coexistence of short-range SDW-SG and superconductivity, usually between 10–15 K, (increased with pressure) as detected by bulk magnetization and inelastic neutron scattering (Katayama *et al* 2010). Figure 26 shows the phase

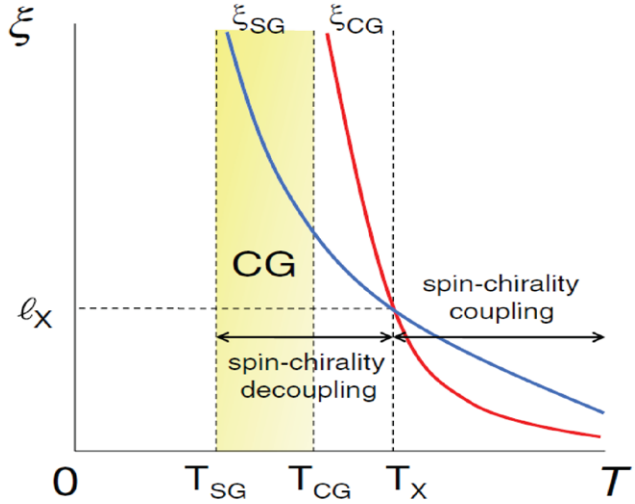

Figure 22. Comparison of the SG correlation length with the CG correlation length as the temperature is lowered. l_x is the CG–SG coupling length. Note the CG ξ diverges faster than the SG one. According to Kawamura (2010).

diagram for Se content and the excess Fe concentration. Note here the deliberate Fe excess and the additional Se–Te alloying, all requiring strict metallurgical constraints. For these compounds the superconducting phase is easily destroyed with Fe off-stoichiometry, for, interstitial Fe is a local moment magnetic and causes a large pair breaking. The delicate balance between magnetism and superconductivity in Fe(TeSe) compound has been discussed by Liu *et al* (2010) who show an inhomogeneous non-bulk superconductivity coexisting with short-range magnetism that could be related to a glassy phase. All these compounds have the substitutional site disorder of '$A_{1-x}B_x$' and an uncontrollable excess of randomly distributed Fe impurities. In the review article by Wen *et al* (2011) there are claims of SG coexisting with SC, however, due to the sample preparation reproducibility, a strict confirmation of a SG transition was not possible. Yet glassy dynamics and slowing down of spin fluctuations were observed in these chalcogenides. A further review of the coexistence of magnetism and superconductivity in pnictides and chalcogenides is complied by Stewart (2011). Unfortunately, here the author does not specify the nature or kind of magnetism. Due to rapid developments in these materials, especially sample quality, we cannot 'draw clear conclusions of this coexistence question' (Stewart 2011). The most recent exploration of the iron-chalcogenides superconductors is Dong *et al* (2013) but little is said about a possible SG state.

8.2. Heavy fermions

Heavy fermion metals are strongly correlated electron intermetallic compounds with very large effective masses consisting of unfilled (3*d*, 4*f* or 5*f* electron) shells of transition-metals, lanthanides or actinides that partially lose their magnetic moments due hybridization or Kondo compensation with their conduction electrons. Here the remaining moment is free to interact magnetically, e.g. RKKY, with its magnetic neighbors. However, the hybridization strongly influences this interaction and adds an anisotropic coupling. Thus, when atomic disorder is present among the ligands, i.e. non-magnetic atoms, these will mediate a random-bond type of SG., see figure 2. Of course, SG behavior could also be generated by randomly substituting a non-magnetic element on the magnetic element site, see below. Because of the strong $f-s$, p, d hybridization and the reduced local moments in heavy fermions a small or even subtle amount of disorder will affect the usually delicate long-range antiferromagnetism. Therefore, it is the strongly correlated heavy-fermion state with the above randomness that enhances the formation of glassy behavior, either a canonical SG or a cluster glass of anti- or ferromagnetic alignments.

In the case of random bonds the combined role of the hybridization modified exchange interaction and the atomic ligand disorder can create a canonical SG. An early suggestion by Gschneidner *et al* (1990) proposed that 'false' heavy-fermion behavior was caused by 'non-magnetic atom disorder' (NMAD) that increased the low temperature specific heat coefficient. Here various Ce-compounds were listed and claimed to be SG rather than heavy fermion. These pseudo-binary materials possessed intentional disorder on the ligand or non-magnetic sites, i.e. NMAD (Gschneidner *et al* 1990). Accordingly, the exchange interaction between the magnetic Ce-sites was randomized and a random-bond SG is expected. However, at that time a full study of the putative SG phase was not performed. The first clear example of a heavy-fermion, unintentional, random-bond SG was URh_2Ge_2 by Süllow *et al* (1997). Here high-quality single-crystals of URh_2Ge_2 exhibited the four hallmarks of a canonical SG (see section 3) with an Ising-like anisotropy. Figure 27 exhibits the FC/ZFC dc-susceptility and the frequency-dependent real and imaginary ac-susceptibitity. It took a number of year to ferret out the ligand disorder and only via XAFS has a random interchange of Rh with Ge been detected by an alternation of Rh and Ge layers in a mixed crystal structure (Booth *et al* 2004). There are now many random bond U and Ce based SG. A popular material is hexagonal U_2TSi_3 where T is a transition metal. Since ferromagnetic interactions dominate, a cluster-glass behavior is found for T = Ir, Ni and Co (Li *et al* 2003, Szlawska *et al* 2010, Szlawska *et al* 2011). A very recent bulk-properties investigation of U_2IrSi_3, another random-bond, heavy-fermion ($\gamma \approx 300$ mJ/moleK^{-2}) material, has found a complicated ground state of ferromagnetic order coexisting with SG freezing (Szlawska *et al* 2014). Also for Ce_2CuSi_3, with Cu and Si site disorder (Li *et al* 2013) and CeAgGa with randomly distributed Ag and Ga sites (Gora *et al* 2011) exhibit glassy states, the former more cluster-glass-like (T_f = 5 K), the latter a good SG with T_f = 2 K. $CeNi_2Sn_2$ SG freezing has been observed within a heavy fermion matrix (Tien *et al* 2002), again via unintentional ligand disorder.

In contrast to the above unintentional disorder there are also deliberately ligand-disordered SG, e.g. $U_3Co_{4+x}Al_{12-x}$ (Tougait *et al* 2007) and $CeNi_{1-x}Cu_x$ (Garcia-Soldevilla *et al* 2000). For the U-based compound there is an added element of strong geometric frustration due to the Kagomé net of uranium atoms. The above references include additional candidates for U-based random ligand SG. $CeNi_{1-x}Cu_x$ has been

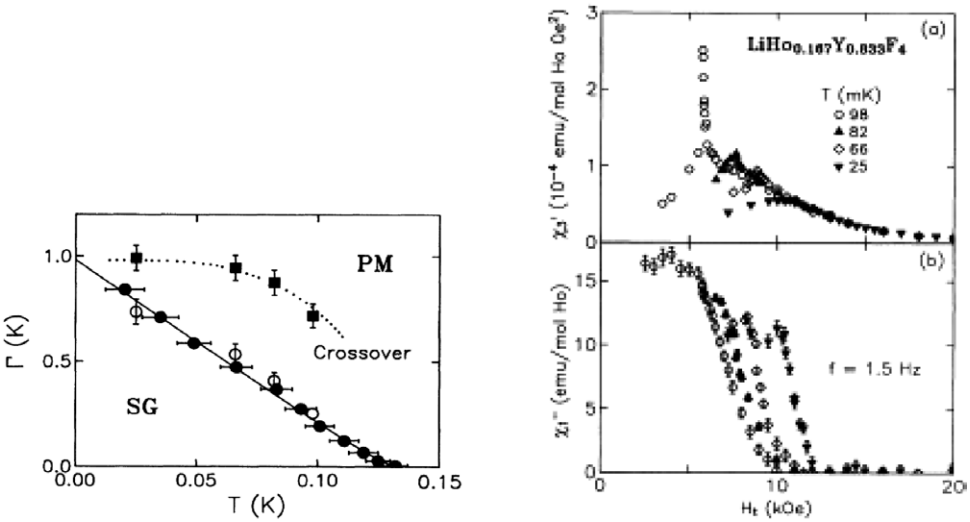

Figure 23. Left: The SG phase is tuned with $Li(Ho_xY_{1-x})F_4$ dilution and $\Gamma = (H_\perp)^2$ is plotted versus T_f, i.e. $T - H$ phase diagram. The crossover line indicates the onset of SG effects from the imaginary part of the ac-susceptibility. Right: linear (imaginary part) and non-linear susceptibilities versus $H_\perp$ for $LiHo_{0.17}Y_{0.83}F_4$. Note how the putative quantum SG transition becomes smeared with $H_\perp$ as the QCP is approached. This does not show the expected SG quantum phase transition. According to Wu *et al* (1993).

Table 1. SG spin-off's from the original local-moment magnetic impurity problem. Applications of spin-glass concepts to diverse non-magnetic systems.

Reference Mydosh (1993)
Neural networks
Computer optimization and algorithms (traveling salesman)
Hetropolymers
Protein folding
Biomolecules
Real (window) glasses
Dipolar and quadrupolar glasses
Orientational molecules (ortho-para hydrogen)
Metal-insulator transitions in 2D
Evolutionary theory
Econometrics and stock market valuation
Vortex glass in high T_c superconductors (magnetic flux) (Blatter *et al* 1994)
Ferroic glasses (relaxors) (Sherrington 2013)
Social networks (Matthews 2008)

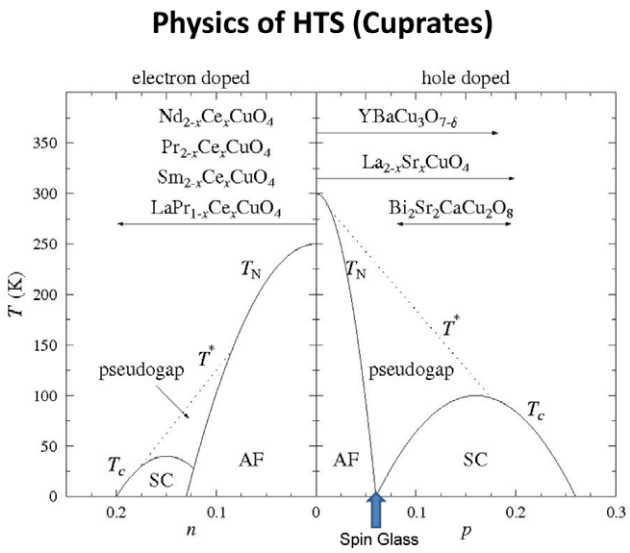

Figure 24. Cuprate high temperature superconductivity (HTS) phase diagram for both hole doped (right) and electron doped (left). The SG-like phase exists and overlaps in the wedge region between the anitferromagnetism and the superconductivity (see arrow). Experiment has yet to find SG behavior in the electron doped HTS.

intensively studied for a decade and exhibits a complicated $(T - x)$ phase diagram that includes long-range antiferromagnetism and a SG region preceding a low temperature ferromagnetic state (Marcano *et al* 2007). The many experiments on this material have led to a cluster-glass model with random anisotropy as its main feature (Iglesias *et al* 2009). A less clear situation is $CePd_{1-x}Rh_xAl$ where the dynamical properties so characteristic of SG freezing have not been studied (Slebarski *et al* 2008). As with all 'pseudo-binary' $x\,(1 - x)$ intermetallic compounds there is always the problem of a 'random' substitution of the two non-magnetic elements. Short-range crystallographic order or even outright precipitation can destroy the random disorder needed for the creation of canonical SG freezing. A very recent puzzle involves the removal of ferromagnetism in $UCo_{1-x}Fe_xGe$. Since both Co and Fe are not magnetic, their random substitution creates random bonds and the possibility of SG formation once the ferromagnetism is destroyed. While a phase diagram has been established for $T - x$ and a quantum critical point proposed, there was no study of SG dynamics (Huang *et al* 2013). Another deliberate ligand disorder Kondo-cluster-glass was suggested for $CePd_{1-x}Rh_x$ (Westerkamp *et al* 2009). Here the ferromagnetism in CePd is reduced with Rh substitution with the hope of finding a ferromagnetic quantum point. However the low temperature dynamical freezing of reduced-moment ferromagnetic clusters intervenes to mask the quantum criticality.

The usual method to create a SG in these strongly correlated materials is to intensionally substitute a non-magnetic element onto a Ce- or U- site in the intermetallic compound. Early on Seaman *et al* (1991) investigated the compound $Y_{1-x}U_xPd_3$, a well-localized magnetic U compound. For

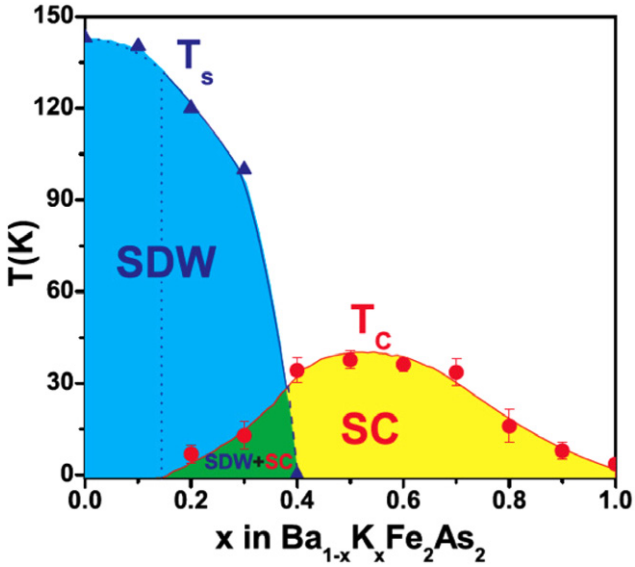

Figure 25. Phase diagram of pnictide, $(Ba_{1-x}K_x)Fe_2As_2$, with coexistence of SDW and SC. Note the SDW—SC overlapping region. With dilution (x) the SDW (T_s) becomes weaker and a SR-SDW appears which may be described as a SG. For many other pnictides the antiferromagnetism is in the form of a SDW and a similar behavior occurs. The SR-SDW interpretation is now becoming acceptable. According to Chen *et al* (2009).

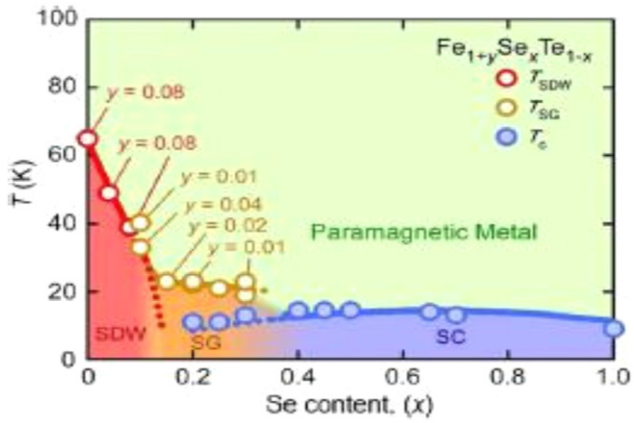

Figure 26. For the Fe-doped chagcognide $Fe_{1+y}Se_xTe_{1-x}$ the SDW and SG regions clearly overlap. At $x = 0.15$ this coexistence is in the form of a SR-SDW where SG behavior appears. Note the SDW/SG/SC all in one phase diagram via Fe_{1+y}. According to Katayama *et al* (2010).

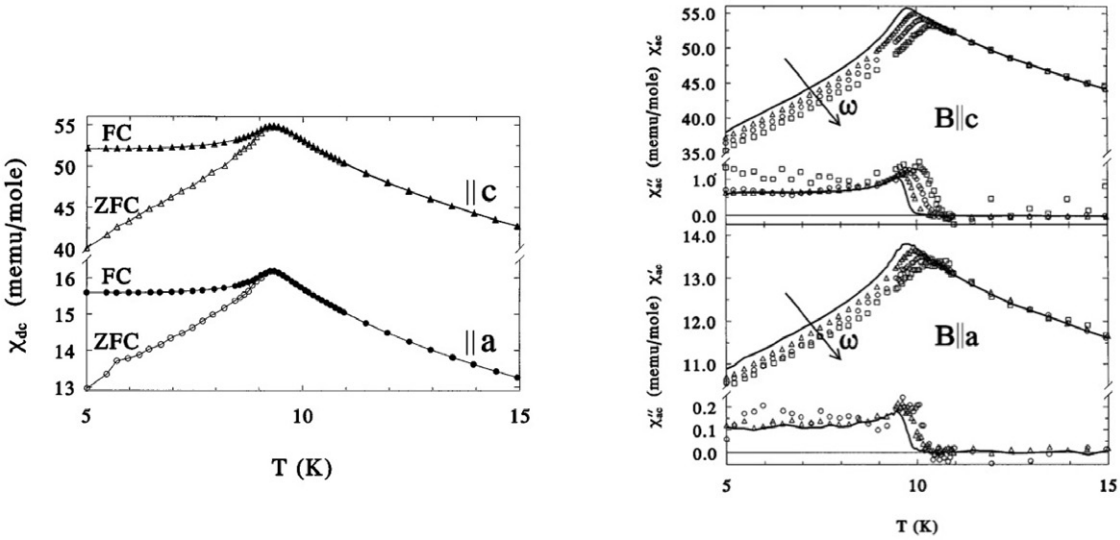

Figure 27. LEFT: FC and ZFC magnetization of URh_2Ge_2 illustrating the SG Ising-like behavior, i.e. easy magnetic axis is **c**. RIGHT: The temperature and frequency dependences of ac-susceptibility (real and imaginary parts) of URh_2Ge_2 demonstrating the canonical SG behavior for this random-bond, single-crystal, heavy-fermion compound. According to Süllow *et al* (1997).

$x = 0.2$–0.4 SG behavior was found at low temperatures (Gajewski *et al* 2000). However, above the T_f a non-Fermi liquid (NFL) state appeared over a wide temperature range. This state is characterized by deviations from the standard Fermi-liquid behavior of the susceptibility, specific heat and resistivity. Even today a full theory of NFL is still missing and recent efforts are continuing to develop it. Unresolved is the effect of strong disorder on the hybridized state and its inclusion into the theory. Could the short-range spin disorder above T_f cause the NFL behavior? The well-studied heavy fermion superconductor $CeCu_2Si_2$ becomes a good SG when La_{1-x} is substituted for Ce_x (Aliev *et al* 1984). For x between 0.2 and 0.4, T_f varies from 0.3 to 1.6 K caused by the dominant RKKY and the site randomness overcoming the hybridization/Kondo effects. Other combinations of random-site-possible SG include $(La_{1-x}Ce_x)_3Al$ (Azechi *et al* 1997) and amorphous (non-crystalline) $La_{1-x}Ce_x$ compounds (Tang *et al* 2007). An unusual example of reentrant SG behavior is the double random magnetic $Ce_{1-x}Er_xFe_2$ compound (Haldar *et al* 2010). An interesting contrast is made between magnetic glasses, reentrant SG and canonical SG by Roy and Chattopadhyay (2009) using bulk magnetization measurements.

The observation of SG behavior in Pr-based compounds has opened another exotic route to SG formation. It was reported

that the well-ordered, stoichiometric compound $PrAu_2Si_2$ exhibits spin glass freezing ($T_f = 3$ K) (Krimmel *et al* 1999). Inelastic neutron scattering then determined the crystal-electric-field excitation of the Pr from its singlet ground state to a nearby magnetic doublet (Goremychkin *et al* 2008). So here we have an induced moment whose exchange coupling is very close to inducing magnetic order. However, dynamical fluctuations of the crystal field levels destabilize the induced moments such that randomness and frustration are created to produce the SG. And in recent years many additional stoichiometric Pr-based compounds have been found to exhibit heavy fermion SG behavior via this crystal-field-fluctuations process (Anupam *et al* 2011, Anand *et al* 2011). Presently the Pr-113 (and Ce-113) compounds have become of interest for their ferromagnetic cluster-glass properties (Anand *et al* 2012a). Here there could also be some ligand disorder enhancing the glassy behavior. New glassy ground states are possible in the $Pr_2Pt_3Si_5$ compounds (Anand *et al* 2012b).

A different class of heavy-fermion conducting oxides are phosphorus-oxide based Ce compounds. For example CeFePO is a non-magnetic and non-superconducting material, yet it exhibits strong ferromagnetic fluctuations indicating that it is close to a long-sought ferromagnetic quantum critical point. Lausberg *et al* (2012) have performed an extensive low-temperature of this compound, including μSR. Their findings for stoichiometric single crystals of CeFePO show a static glassy freezing behavior that is not a canonical SG. Such removes the possibility of a ferromagnetic quantum point. While intentional disorder can be eliminated, an unknown subtle form of randomness, possibility O/P vacancies, related to the delicately layered crystal structure is required to explain the glassy behavior. Through such disorder a metallic spin liquid state at $T = 0$ is improbable.

Theumann and Coqblin (2004) have considered the Kondo to SG transition in heavy fermion materials using a theoretical model consisting of an intrasite Kondo exchange interaction, an intersite random Ising exchange coupling among the local moments and a transverse magnetic field to generate the quantum critical point. These terms with their proper exchange paramaterization in a mean-field solved Hamiltonian give two second-order phase transitions: SG to paramagnetic and then via Kondo to paramagnetic as the temperature is increased. The transverse field is used to tune the quantum phase transition. Since the transition lines do not intersect they generate two quantum critical points. The authors indicate the usefulness of the theory in U, Ce and even Yb disordered compounds with pressure as the tuning parameter.

Many heavy-fermion Ce-based compounds have been classified as SG-like. Most of these materials are not fully studied (see section 3) such that a canonical SG state can be claimed. Nevertheless they are sufficiently characterized to demonstrate some low-temperature freezing and glassy dynamics. While in many of these compounds no SG phase transition is found, there are still present the basic ingredients of disorder and frustration. Therefore, more-detailed investigations of the glassy state for these strongly correlated materials are needed to fully detect the causes of disorder and frustration. Is the disorder intentional (known) or unintentional (to be determined)? How about the frustration: Is it simply geometric or related to the modification of the exchange interactions of the heavy fermions? Such issues remain a vibrant future area of SG research.

8.3. Intermetallics: Heuslers

As was demonstrated early on there are a large number of intermetallic compounds that can be formed into SG with good local moments, disorder and frustration (Mydosh 1993). Since these intermetallic compounds are not strongly correlated the usual RKKY interaction is available, but now, in some rare-earth-based materials the crystal electric fields come into play. The traditional route, without crystal-field effects, is site disorder via magnetic—non magnetic substitutions, e.g. pseudo-binary $La_{1-x}Gd_xAl_2$ (Zomack *et al* 1983). Another method is to take the crystalline intermetallic compound and make it amorphous, e.g. via mechanically ball milling, $GdAl_2$ and Co_2Ge (Zhou and Bakker 1994). Nevertheless, various modern intermetallic materials exist that rely on different approaches to SG-like behavior. Tb_2PdSi_3 shows quasi-one-dimensional behavior at high temperature followed by anisotropic large frequency-dependent freezing (Paulose *et al* 2003). Since in these 213-compounds random ligand substitution is common, glassy freezing may be expected. Additionally, the crystal field levels of Tb cause the Ising-like anisotropy and enhance the disorder by a modified exchange interaction. Another example of a magnetic-field stable SG is the Ising, random-site intermetallic $Y_{1-x}Dy_xRu_2Si_2$ (Tabata *et al* 2010). Here dynamical measurements indicate a mean-field like SG transition persisting even with the applied magnetic field which gives evidence for the RSB model prediction of the AT-line.

More complicated crystal structures of quaternary intermetallic compounds with subtle disorder also lead to SG freezing: $La_{21}Fe_8Sn_7C_{12}$ allows the Fe to be placed in tetrahedra whose antiferromagnetic coupling causes frustration. With the RKKY interaction between the Fe-tetrahedra and some disorder, a FC/ZFC magnetization and a frequency dependent susceptibility peak are evidenced (Benbow *et al* 2009). Another recent non-intentional ligand disordered SG include Gd_2Au_2Cd with 110 K freezing behavior (Rayaprol and Pöttgen 2006). Possible refrigerant applications comprise the heavy rare-earth based bulk metallic amorphous (real glasses), e.g. $Ho_{30}Y_{26}Co_{20}$ (Luo *et al* 2007). Here the SG to paramagnetic transition leads to large entropy changes at low temperatures thus making these compounds useful as magnetic refrigerantors in helium liquefaction processes.

Another huge family of intermetallic compounds can be formed in the ternary Heusler crystal structure: X_2YZ (Felser and Freken 2013). Figure 28 shows the crystal structure for full-Heusler, e.g. Cu_2MnSn and half-Heusler, e.g. ScPtBi (Franz 2010) and the various forms of antisite disorder The magnetic Heuslers are mainly based on the 3*d* transition metals that exhibit a variety of strong magnetic behavior, ferro-/antiferro-/ferrimagnetic including SG of the reentry type. Note the dense packing of elements in figure 28 and the closeness of nearest neighbors. Since these are good conducting compounds, the RKKY is dominant and competing ferro-/antiferromagnetic interactions are created for neighboring magnetic

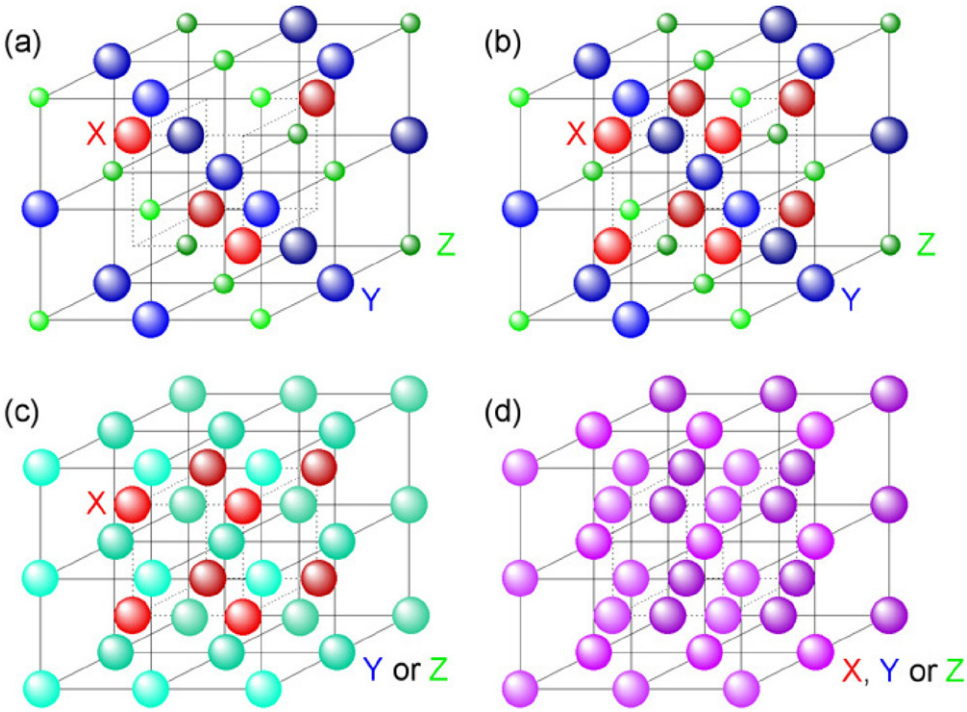

Figure 28. Different Heusler crystal structures: (*a*) Half Heusler, (*b*) Full Heusler, (*c*) Disordered Y or Z and (*d*) Disordered X, Y or Z. Note the affinity for disorder and thus SG behavior in the magnetic-component Heuslers'. According to Webster and Ziebeck (1988).

sites. Also disorder is commonly caused by site exchanges that are now called 'antisite disorder'. Or, the disorder can be intentionally tuned by forming Heusler alloys, e.g. $(1-x)$ $(1+x)$. A detailed μSR study of $Ru_{1.9}Fe_{0.1}CrSi$ (deliberately disordered) shows a complicated extended-temperature region of freezing whose maximum relaxation rate gave T_F around 16 K (Hiroi *et al* 2013).

Many combination of magnetic/non-magnetic elements are available thereby allowing for a rich array of both long-range ordered ferromagnetic and antiferromagnetic Heusler compounds. A typical example of weakly magnetic 'stoichiometric' Heusler compounds are Ru_2CrGe and Ru_2CrSn (Okada *et al* 2008). The former is antiferromagnetic at $T_N = 13$ K, the later SG below 7 K due antisite disorder and vacancies of Sn. When Mn is used as the magnetic element strong ferromagnetism occurs near or far above room temperature usually followed by a reentry transition: either SG, e.g. Mn_2PtGa (Nayak *et al* 2013) or antiferromagnetic, e.g. Fe_2MnGa (Gasi *et al* 2013). Here due to the large exchange anisotropy the formation of domains occurs that become smaller with decreasing temperature thereby generating the glassy dynamics.

Because of the disorder and exchange anisotropy, Heusler materials exhibit notable exchange bias effects that are useful in memory devices and spintronics applications. In addition some of the half-Heusler compounds are half-metallic ferromagnets, i.e. only a single spin-polarized band is filled thereby creating the large spin polarization of electrons needed in spintronic devices (Fuji *et al* 2010). To date there is little evidence for SG behavior in the magnetically ordered half-Heuslers. A review of magnetic multilayers based on Heusler compounds of Co_2MnGe and Co_2MnSn in thin-film form was given by Westerholt *et al* (2005).

The exchange bias (EB) is usually caused by a ferromagnetic matrix embedded with antiferromagnetic or SG clusters. And the recent literature is flooded with such reports. Let consider a few examples where such properties are tuned by Heusler alloying. Chatterjee *et al* (2009) studied the shape-memory alloy $Ni_2Mn_{1.36}Sn_{0.64}$ and found a reentry SG phase coexisting with the matrix ferromagnetism at low temperatures, not a very simple ground state. Yet here the shifted or displaced hysteresis loop denoted the exchange bias phenomenon usually occurring in mixed ferro/antiferro interface couplings (Li *et al* 2007). Further tuning of the above Heusler alloy led to giant exchange bias fields with the reentry SG/ferromagnetic interface caused by excess Mn atoms occupying both Ni and Sn sites randomly, a combination of random site and random bonds (Ma *et al* 2011). Accordingly Mn clusters are formed with large interface regions to enhance the EB field. Additional work on the improved EB properties in these Ni-Mn-Sn alloys include (Esakki Muthu *et al* 2011) and in thin Heusler alloy films (Goscianska *et al* 2012). Very recently a colossal EB was found in the Heusler alloy $Mn_{2+x}Pt_{1-x}Pt$ by Nayak *et al* (2015). The EB was created by field cooling the high-temperature antiferromagnetic state such that ferromagntic clusters were induced to couple with the antiferromagnetic background. The interface exchange interactions of the random subsystems create the colossal EB.

The Heusler alloys are rather complicated heterogeneous materials. Most of the work cited above concentrates on magnetic (magnetization and susceptibility) properties ignoring the difficult metallurgy of random alloy formation and non-stoichiometric compounds. Different heat treatments are not studied and the reproducibility of different sample preparation are also not examined. Most needed here are microscopic

investigations (both metallurgical and physical), beyond the bulk measurements, of the alloy composition topology and the local magnetic behavior. Modern experimental techniques are most available to conduct such experiments. In a recent study of spin-value effects in the 'stoichiometric' Mn_2NiGa Heusler compounds, neutron scattering measurements showed 13% of the Mn occupies Ga sites due to antisite disorder (Singh *et al* 2012). So we can only now imagine the disorder in the Heusler alloys with the key question is it controllable. Despite the disorder and frustration we can conclude that the putative (reentry) SG transitions are not to a canonical SG state. Yet all these inhomogeneous regions show glassy or cluster glass dynamics that we could call SG-like. Again there is a crying need for new microscopic experiments on these materials.

8.4. Pyrochlors and spinels

As noted in section 1 frustration, i.e. crystal lattices in which the antiferromagnetic spin bonds cannot all be satisfied, is a basic, all-important ingredient for the formation of the SG state. For a review of frustrated magnetism, see Lacroix *et al* (2011). But equally important, disorder is also essential. So the SG phase is more easily accessible within a strongly frustrated lattice. Thus we can look towards lattices containing large amounts of geometric frustration, e.g. triangular, Kagome in 2D and pyrochlor, spinel and face-centered-cubic in 3D. With the large frustration measured by a 'significance factor': $f = \Theta_{CW}/T_N$ (Curie–Weiss temperature to magnetic ordering temperature) we can create canonical SG using such lattices with a small amount of disorder. The randomness could be intentional or even unintentional and very difficult to chemically distinguish. Model calculations by Andreanov *et al* (2010) (section 1) have demonstrated various possibilities whereby tiny unintentional disorder produces a SG phase. The latter randomness is a severe problem with the strongly frustrated mainly oxide pryrochlores ($A_2B_2O_7$) and spinels (AB_2O_4) that we now consider. These 3D crystals offer a finite temperature freezing temperature, as opposed to the 2D examples where even for Ising uniaxial magnetism only $T \to 0$ critical behavior is encountered. Here we should note there are other unconventional phenomena and phases in the frustrated pyrochlors. We mention the distinctively new physics of spin ice and spin liquids, reviewed by Gardener *et al* (2010) and also the prediction (Castelnovo *et al* 2008) and putative observation (Bramwell *et al* 2009) of magnetic monopoles in spin ice. Today the search for a quantum spin liquid continues with herbertsmithite, a spin 1/2 Kagome mineral, that supports exotic spin excitations (Han *et al* 2012).

The observations of SG behavior in the pyrochlores has been reviewed in detailed during the past 20 years by Ramirez (2001) and Gardener *et al* (2010). Here the tetrahedral unit-cells are highly frustrated with all AF coupling between the 4 spins as shown in figure 29. Accordingly, any type of subtle disorder would lead to SG behavior. We now present a few recent examples of unusual SG behavior, see Gardener *et al* (2010) for detailed discussion of $Y_2Mo_2O_7$. The niobate pyrochlore $Tb_2Nb_2O_7$ was studied via a series bulk measurements and the claim made for a spin-glass-like freezing at 0.8 K (Jana

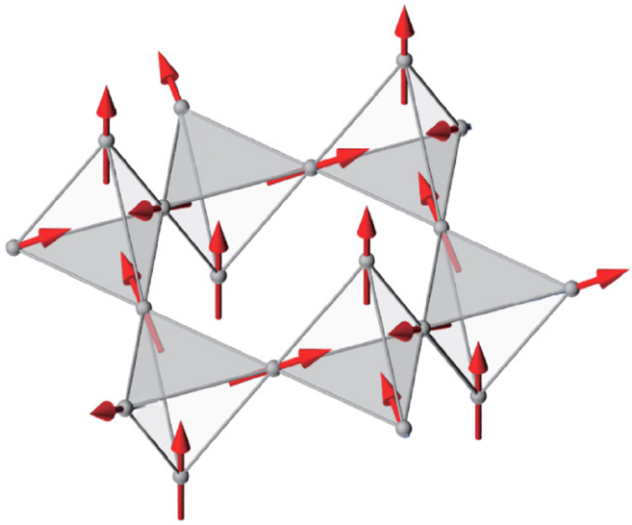

Figure 29. The spin and crystal structure of a few pyrochlor cells. Note the in and out of the four spins on the tetrahedral unit cell. The all antiferromagnetic interactions among the cells create the strong frustration.

et al 2003). In so far as the material is complicated by Tb-CEF effects and there is no examination of possible disorder, the SG behavior remains a mystery. Singh and Lee (2012) investigated the $Tb_2Mo_2O_7$ pyrochlore where both Mo and Tb are magnetic and interact both anti- and ferromagnetically. Based upon analyses of the non-linear and real and imaginary susceptibilities, an unconventional SG transition was claimed. Although chemical disorder was excluded, the authors leave unclear the possibilities of subtle randomness caused by strains, vacancies, site substitutions, etc. More exotic pyrochlors were examined, e.g. $Na_3Co(CO_3)_2Cl$ and evidence presented for partial SG freezing but not a canonical SG transition (Fu *et al* 2013). Again there was no observation of site disorder but no search for other more subtle indications of randomness was performed. Presently the study of pyrochlores has moved into the realm of neutron scattering. A fresh look at the canonical SG $Y_2Mo_2O_7$ by magnetic diffuse scattering has found a frozen coupling between spin and orbital degrees of freedom (Silverstein *et al* 2014). When combined with random fluctuations in the Mo environment these new ingredients could be the main cause of the canonical SG transition. Inelastic neutron scattering has evaluated the CEF levels in $Tb_2Ti_2O_7$ and $Tb_2Sn_2O_7$. The Tb ground-state and excited-state doublets contain a mixture of m_J eigenvalues. It is the precise nature of these CEF manifolds that influence the magnetic ordering, spin ice or glassy freezing at low temperatures (Zhang *et al* 2014).

Spinels (AB_2O_4) are also geometrically frustrated and mainly antiferromagnetically coupled. Early on they have been predicted and found to exhibit insulating SG behavior via random site dilution (Villain 1979, Fiorani *et al* 1984). Recent spinel work has continued along these lines with a typical example of random-bond SG being $CoAl_2O_4$ (Tristan *et al* 2005). Here there is a minor inversion between the Co and Al sites, i.e. $[Al_{1-x}Co_x]_2$ (Tristan *et al* 2008). However, this site substitution was not studied preparatively and chemically in detail. For the random bonds (due to distortions of

the Cu and Ga, Al sublattices) SG-spinels, $CuGa_2O_4$ and $CuAl_2O_4$, a zero point entropy was observed that indicated a very large degeneracy of their ground states (Fenner *et al* 2009). Nagata *et al* (2012) presented an experimental study of the $CuCrTiS_4$ sulfur-based spinel placing it as a short-range interacting Heisenberg SG. Recently the $ZnCr_{2(1-x)}Ga_{2x}O_4$ spinel was investigated for various x-values (LaForge *et al* 2013). Even as $x \to 0$ a new type of 'quasi-SG' was proposed because of long-range interacting spin vacancies resulting from the frustrated spin background. A metallurgical examination of the intersite mixing disorder was carried out on the $CoAl_2O_4$ spinel (Hanashima *et al* 2013). These authors controlled the inversion parameter η in $(Co_{1-\eta}Al_\eta)[Al_{2-\eta}Co_\eta]O_4$ by various heat treatments and determined a SG regime for $\eta \geqslant 0.1$. The results confirm the great sensitivity of the SG state to quenched antisite disorder.

So the progress continues with novel SG and related magnetic behavior in these strongly frustrated pyrochlores and spinels. We are still confronted with the serious problem of determining the unintentional disorder, not simply from magnetic processes but rather from chemical and metallurgical techniques. Here the most modern sample preparation methods and analytic characterizations should be first used before the SG magnetic measurements are performed. Once the former are completed then we can distinguish from the magnetic dynamics, if the material is a canonical SG or if it only shows glassy behavior (gradual freezing or superparamgnetism) without the SG phase transition.

8.5. Other oxides and chalcogenides

There are numerous oxide- and chalcogenides-based (column VI) materials besides those that are high-temperature superconductors, see section 8.1. When combined with a transition metal and a ligand usually of column II or III, a strongly magnetic, insulating compound is formed. Most of these materials are of the Mott–Hubbard type (a strong electron-electron interaction 'U' creates the insulating gap) or the charge-transfer type (the *p*-electrons transfer charge to the *d*-electrons forming the energy gap). Accordingly, the description of such compounds requires a strongly correlated electron approach. In order to approach the SG regime doping, $(1-x)x$, is required either substitution on the ligand sites, i.e. random bonds within the magnetic sites, or direct magnetic ion disorder, i.e. random sites. A typical example of such substitutions is $La_{1.85}Sr_{0.15}Cu_{1-y}Ni_yO_4$ (Malinowski *et al* 2011). Here Sr-doping is used to reduce the strong antiferromagnetism to near $T_N \to 0$, where the superconductivity starts to appear. The Ni-doping randomly introduces small magnetic moments into the Cu-O planes. Thus the combined, interacting magnetism of Ni and Cu acts as a random-site SG whose experimental behavior is fully characteristic of a canonical SG. Detailed analyses of critical behavior and dynamics, e.g. linear/nonlinear ac-susceptibilities, display critical exponents more Ising-like than Heisenberg-like, at least for low concentrations of Ni (Malinowski *et al* 2011). One could also vary the Sr concentration at full Ni substitution ($y = 1$). Now SG and memory effects were found indicating a connection between spin-charge stripes and the SG (Freeman *et al* 2006).

Co-based oxides present a more complicated situation due to the three possible valencies of 2 + , 3 + ; 4 + (and intermediate) depending on the oxygen stoichiometry. Also Co^{3+} possesses three different spin states: high, low and intermediate whose magnetic moments vary as a function of temperature. Nevertheless early on, despite these complexities, a SG state was suggested by Moritomo *et al* (1997) for $La_{2-x}Sr_xCoO_4$. More recent work Wu *et al* (2003) tracks the glassy behavior of $La_{1-x}Sr_xCoO_3$ as x is varied. Their conclusion is that magnetic phase separation occurs leading ferromagnetic cluster freezing. Hence these Sr-doped random-bond Co compounds do not seem to exhibit a canonical SG phase transition. Similar attempts to detect SG behavior were described by Laiho *et al* (2001) in $La_{1-x}Ca_xMnO_3$ where a multiphase diagram was measured as a function of temperature. Here again we have low temperature glassy dynamics without a canonical SG phase transition. A more interesting random site SG is $PbFe_{0.5}Nb_{0.5}O_3$ (Chillal *et al* 2013). Using Mössbauer and neutron diffraction these authors conclude a microscopic coexistence of SG and antiferromagnetism. Very recent work illustrates the intense efforts to fabricated a frustrated single-crystal Co-oxide SG in $Bi_{2-x}Pb_xSr_{2-z}Co_2O_y$ (Hsu *et al* 2014). The x, y, z compound tuning is used for creating random bonds and SG freezing is claimed for certain ratios of Co^{4+}:Co^{3+}.

Such transition metal oxides do have certain possibilities for applications utilizing the frozen SG properties. As an example multiferroic $YMn_{1-x}Cr_xO_3$ exhibits a low temperature SG state due the competing AFM superexchange and FM double exchange caused by the Cr-doping, but maintaing the ferroelectricity (Han *et al* 2014). Another example is the spontaneous exchange bias appearing in phase-separated $La_{1.5}Sr_{0.5}CoMnO_6$. The zero-field EB is attributed to the induced unidirectional anisotropy at the interface of the ferromagnetic regions (Krishna Murthy and Venimadhav 2013). Finally, there are many cases of transition-metal oxides formed or milled into nanoparticles which then show SG interacting freezing rather than noninteracting superparamagnetism, e.g. $La_{0.7}Ca_{0.3}MnO_3$ (Thanh *et al* 2014).

The particular present-day attention to the chalcogenides involves their coexistence of Fe-based superconductivity through the SDW into the SG phase, see section 8.1. Since these materials are metallic the SDW due to random dilution becomes truncated and show many of the properties of a SG. There are, however, a number of non-superconducting chalcogenides that are semiconducting and reveal SG behavior. $BaFe_{2-\delta}Se_3$ for $\delta \approx 0.2$ offers evidence of short-range magnetic correlations of the SG type (Saparov *et al* 2011). Further substitution of Se by S tunes the SG T_f to lower temperatures. Another semiconducting SG is $K_xFe_{2-y}S_2$ where the randomness stems from stoichiometry, defects and local environment disorder (Lei *et al* 2011). While freezing properties are detected the transition to a glassy state is smeared, not that of a good SG. We recall the canonical SG chalcogenides $Eu_xSr_{1-x}S$ of long ago Maletta and Felsch (1979) and the dilute magnetic semiconductor SG: Mn or Fe doped sulfides, tellurides and sellurides (Mydosh 1993). More recently Ge diluted with Mn, grown by molecular-beam-epitaxy, exhibited a variety of SG properties (Jaeger *et al* 2006).

We remark here that the transition-metal based oxides offer many different combinations with a great variation of random substitutions and diverse amounts of competing AF and F super-, double-, RKKY- and dipolar interactions. Yet they are not studied strictly for their intrinsic SG behavior since other more important properties are observed containing new physics. The SG behavior (mostly non-canonical) serves mainly as a distinction between the three types of ordered magnetism, viz., F, AF and SG. Within the modern materials of todays' condensed matter physics, e.g. high-temperature superconductors, heavy-Fermi liquids, exchange bias, spin-ice, magnetic monopoles, etc, SG glass behavior is usually found. However, such examples are typically not of the canonical SG type. For a full description of the ideal, canonical SG among the fluorides and oxides, such as 2D: $Rb_2Cu_{1-x}Co_x F_4$ and 3D: $Fe_{1-x}Mn_xTiO_3$, see Mydosh (1993).

8.6. Miscellaneous and exotic

We now review a number of topical unconventional SG that do not belong in the above categories. Because of the special attention with the unusual interface superconductivity in two insulating complex oxides, e.g. $SiTiO_3$ interfacing with $LaAlO_3$ (Reyren *et al* 2007), we note the analogous SG counterpart: bilayers of AF-$SrMnO_3$ with F-$La_{0.7}Sr_{0.3}MnO_3$ (Ding *et al* 2013). Here the frustration results from the the competing AF and F exchange interactions at the disordered interface. Such bilayers also exhibit a strong exchange bias effect which is correlated with the SG state. Other fabrication techniques, e.g. atomic layer deposition for (Zn,Co)O films, are used to form magnetic structures that indicate SG freezing (Sawicki *et al* 2013).

Along the lines of these special structuring are the nanoparticle superspin glasses (Hiroi *et al* 2011). These authors formed nanoparticles of γ-Fe_2O_3 with diameters of ≈20 nm and magnetic moments of $2 \times 10^4\ \mu_B$. Their magnetic measurements (ac and dc) show both superparamagnetic and SG regions of behavior depending on the interparticle distance which is controlled by a 'capping' process through SiO_2 or oleic acid. Metallic mesoscopic SG of **Ag**Mn were fabricate via electron-beam lithography and photoresist techniques into a wire shape of width and thickness ≈45 nm (Capron *et al* 2013). Here universal conductance fluctuations were measured to determine the phase coherence time of the electrons in the SG state. Size-varied metallic nanoparticles of $TbCu_2$ (≈10 nm) showed 'superantiferromagnetism' with reentry SG freezing below 10 K (Echevarria-Bonet *et al* 2013). And exchange bias, i.e. hysteresis-loop shifts, was created in bilayers of F-Co and SG-**Cu**Mn (Ali *et al* 2007). Here the **Cu**Mn SG replaced the usual antiferromagnet interface layer. Along the same lines of memory effects, a field-pulsed memory was created in unconventional $Tb_{30}Ru_{6.0}Sn_{29.5}$ (Schmitt *et al* 2013). When magnetic-field-pulsed upon cooling, upon warming the magnetization 'remembers' the temperature at which the pulse was applied.

Quasicrystals naturally develop SG properties. Two recent paper have emphasized the canonical SG behavior in dodecagonal $Mn_{76}Si_{18}Cr_9$ (Kashimoto *et al* 2011), icosahehral $Gd_9Mg_{34}Zn_{57}$ (Bud'ko and Canfield 2012) and icosahedral clustered $Gd_3Au_{13}Sn_4$ (Kozelj *et al* 2013). Such SG behavior is a result of the 'quasi-' randomness, i.e. distribution of magnetic-ion distances, of the quasicrystal structure along with the competing AF/F exchange interactions. A new surge of interest in SG quasicrystals has followed the discovery of binary magnetic icosahedral quasicrystals based on rare-earths and cadmium (Goldman *et al* 2013). The solution growth process resulted in icosahedral phase of composition i-$RCd_{7.65}$ for magnetic R = Tm, Er, Dy, Tb and Gd. Especially interesting are the bulk properties of Gd-based i-R-Cd that clearly resembled a good SG freezing transition (T_f = 4.6 K) (Kong *et al* 2014). Figure 30 shows the typical SG magnetization behavior for icosahedral quasicrystal Tb-Mg-Zn. For a review of icosahedral quasicrystals and their SG behavior, see Goldman (2014). A recent two-fold (RKKY interaction and MC simulations) theoretical approach has considered the magnetic behavior of i-RCd quasicrystals. The results indicate spin clustering with weak inter-cluster interaction leading to a quasiperiodic Néel low temperature order, not a conventional SG (Thiem and Chalker 2014).

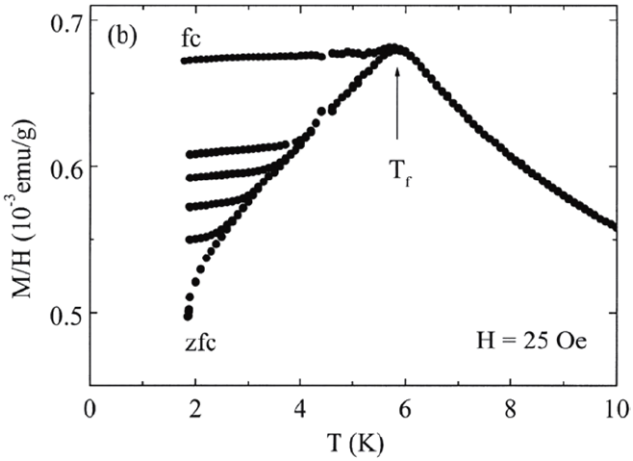

Figure 30. dc magnetization (M/H) of icosahedral quasicrystal Tb-Mg-Zn. After ZFC a field 25 Oe is applied at various temperatures below T_f = 6 K. Note the irreversible (and time-dependent) behavior characteristics of a canonical SG. According to Goldman (2014).

Another unusual SG material we mention in closing this section is the observation of SG behavior in the magnetic coordination polymer $[Co(C_3H_3N_2)_2)]_n$ (Tran and Swiatek-Tran 2008). Although we have attempted to collect and site the most recent and important modern materials and their SG or magnetic glassy behavior, it is impossible to stay up-to-date. The proliferation of new materials especially in the magnetic oxides is enormous (e.g. 5 new SG paper appeared in the July Physical Review). So we must content ourselves with an incomplete survey in order to abridge this review article. The field of SG research has been greatly expanded due to the many recently fabricated compounds, yet the basic SG behaviors remain the same; by determining them for the newly discovered materials, e.g. the i-R-Cd quasicrystals, see figure 30 and the most recent claim of SG behavior in $Li_2(Ir_{1-x}Ti_x)O_3$ where a strong spin-orbit coupling, a new SG ingredient, exists on Ir sites (Manni *et al* 2014). Finally we have the

double perovskites of mixed 3*d* and 5*d* transition metals, e.g., $Sr_2CoO_5O_6$, where there is successive freezing of the magnetic Co and O_5 ions (Binhai *et al* 2014). We can describe and classify these compound by applying the four basic SG experimental properties given in section 3.

9. Conclusions and future

In this review we have focused on the experimental character of the SG phase transition and glassy ground state with a near neglect of the encompassing theory and ever-progressing computer simulations. Such up-dating theoretical overviews may be found from Young (1997), Nishimori (2001), de Demonicis and Giardina (2006), and Stein and Newman (2013). In order to establish a canonical SG we require four experimental properties to be measured: (i) ac-susceptibility as function of temperature, frequency, driving field and external static field, (ii) FC/ZFC magnetization and hysteresis sweeps, (iii) specific heat without a discontinuity or cusp and (iv) time and waiting time dependences. These criteria are examined and illustrate in section 3. If then the material fully confirms to a theoretical model and direct comparisons can be made with theory, we would use the term 'ideal SG'.

Our justification for writing this article, a reexamination and critique after more than 45 years of SG labor, is the resurgence of exciting new materials with SG-like behavior. In our presentation we have emphasized that for most of the recent materials discussed in section 8 an ideal-model or canonical SG is not observed. Yet some of these compounds show good SG behavior with a well-defined T_f. Others exhibit the glassy behavior in their frozen state of weakly interacting or discrete clustering, i.e. the hallmarks of superparamagnetism and no phase transition. Irregardless, they cannot be described within the long-range translational order of AF or F. So irrespective of whether the SG is good, canonical or ideal, there still exists the basic requirement of phenomenon classification or a descriptive framework. Via the SG models and properties we now have such a framework for describing the magnetic phenomena. Here the fundamental ingredients of randomness, frustration and competing interactions form the basic prerequisites of the SG framework. When such ingredients are present we generate a SG through the four experimental properties. Therefore, it is important to distinguish the SG phase from the two translational invariant (AF or F) magnetic states. Note the physical distinction, for it required a long gestation to establish the SG as spontaneous symmetry breaking, while F and AF were already well-established many years before the discovery of SG.

Acknowledgments

I wish to acknowledge helpful suggestions from Peter Young and David Sherrington and also the referees. I would like to thank the many many colleagues who have assisted me during my 45^+ year involvement in the SG: first at Fordham University in New York (late 1960's), then the Kernforschungsanlage in Jülich (early 1970's) and now at Kamerlingh Onnes Laboratory and Institute Lorentz where this present manuscript was composed. My book Mydosh (1993) was mainly written at UC-Santa Barbara in the 1990's and continued in Leiden. It is only recently that I have returned to the SG field due to the heavy citations of the book and today's great interest in material-based SG.

In January of 2015 I received a preprint of another spin glass review by H Kawamura and T Taniguchi to be published as a chapter in the Handbook of Magnetic Materials series.

References

Ancona-Torres C, Silevitch D, Aeppli G and Rosenbaum T F 2008 *Phys. Rev. Lett.* **101** 057201
Aharony A, Birgeneau R, Coniglio A, Kastner M and Stanley H 1988 *Phys. Rev. Lett.* **60** 1330
Ali M, Adie P, Marrows C, Greig D, Hickey B and Stamp R 2007 *Nat. Mater.* **6** 70
Aliev F, Brandt N, Moschcalkov V, Petrenko O, Chudinov S and Yasnitskii R 1984 *Sov. Phys.—JETP* **59** 145
Anand V, Adroja D, Hillier A, Taylor J and Andre G 2011 *Phys. Rev.* B **84** 064440
Anand V, Adroja D and Hillier A 2012a *Phys. Rev.* B **85** 014418
Anand V, Anupam , Hossain Z, Ramakrishnan S, Thamizhavel A and Adroja D 2012b *J. Magn. Magn. Mater.* **324** 2483
Anderson P W, Halperin B and Varma C 1972 *Phil. Mag.* **25** 1
Andreanov A, Chalker J, Saunders T and Sherrington D 2010 *Phys. Rev.* B **81** 014406
Andrei N, Furuya K and Lowenstein J 1983 *Rev. Mod. Phys.* **55** 331
Anupam, Anand V, Hossain Z, Adroja D and Geibel C 2011 *J. Phys.: Condens. Matter* **23** 376001
Azechi L, Medina A and Gandra F 1997 *J. Appl. Phys.* **81** 4179
Benbow E, Dalal N and Latturner S 2009 *J. Am. Chem. Soc.* **131** 3349
Binder K and Young A P 1986 *Rev. Mod. Phys.* **58** 801
Binghai Yan *et al* 2014 *Phys. Rev. Lett.* **112** 147202
Blatter G, Feigel'man M, Geshkenbein V, Larkin A and Vinokour V 1994 *Rev. Mod. Phys.* **66** 1125
Booth C H, Han S-W, Süllow S and Mydosh J A 2004 *J. Magn. Magn. Mater.* **272–6** 941
Bramwell S, Giblin S, Calder S, Aldus R, Prabhakaran D and Fennel T 2009 *Nature* **461** 956
Bray A and Moore M 1985 *Phys. Rev.* B **31** 631
Brodale G, Fisher R, Fogle W, Philips N and van Curen J 1983 *J. Magn. Magn. Mater.* **31–4** 1331
Bud'ko S and Canfield P 2012 *Phil. Mag.* **92** 4492
Cable J, Werner S A, Felcher G P and Wakabaysaki N 1982 *Phys. Rev. Lett.* **49** 829
Cable J, Werner S A, Felcher G P and Wakabaysaki N 1984 *Phys. Rev.* B **29** 1268
Cai P, Zhou X, Ruan W, Wang A, Chen X, Lee D-H and Wang Y 2013 *Nat.Commun.* **4** 1596
Campbell I and Petit D 2010 *J. Phys. Soc. Japan* **79** 011006
Cannella V and Mydosh J A 1972 *Phys. Rev.* B **6** 4220
Capron T, Forestier G, Perrat-Mabilon A, Peaucelle C, Meunier T, Bäuerle C, Lévy L, Carpentier D and Saminadayar L 2013 *Phys. Rev. Lett.* **111** 187203
Castellani C, Di Castro C and Peliti L 1981 *Lecture Notes in Physics* **149** (Berlin: Springer)
Castelnovo C, Moessner R and Sondhi S 2008 *Nature* **451** 42
Chatterjee S, Giri S, De S and Majumdar S 2009 *Phys. Rev.* B **79** 092410
Chen H, Ren Y, Qiu Y, Bao W, Liu R, Wu G, Wu T, Xie Y, Wang X, Huang Q and Chen X 2009 *Europhys. Lett.* **85** 17006
Chillal S, Thede M, Litterst F, Gvasaliya S, Shaplygina T, Lushnikov S and Zheludev A 2013 *Phys. Rev.* B **87** 220403

Chou F, Belk N, Kastner M, Birgeneau R and Aharony A 1995 *Phys. Rev. Lett.* **75** 2204
Daybell M and Steyert W 1968 *Rev. Mod. Phys.* **40** 380
de Almeida J and Thouless D 1978 *J. Phys.* A **11** 983
de Dominicis C and Giardina I 2006 *Random Fields and Spin Glasses* (Cambridge: Cambridge University Press)
de Haas W and van den Berg G J 1934 *Physica* **1** 1115
Ding J, Lebedev O, Turner S, Tian Y, Hu W, Seo J, Panagopoulos C, Prellier W, Van Tendeloo G and Wu T 2013 *Phys. Rev.* B **87** 054428
Dioguardi A P *et al* 2013 *Phys. Rev. Lett.* **111** 207201
Dong C-H, Wang H-D and Fang M-H 2013 *Chin. Phys.* B **22** 087401
Dotsenko V, Feigel'man M and Ioffe L 1991 *Spin Glasses and Related Problems* (Boca Raton, FL: CRC Press)
Edwards S and Anderson P W 1975 *J. Phys.* F **5** 965
Echevarria-Bonet C *et al* 2013 *Phys. Rev.* B **87** 180407
Enoki M, Fujita M, Nishizaki T, Likubo S, Singh D, Chang S, Tranquada J and Yamada K 2013 *Phys. Rev. Lett.* **110** 017004
Esakki-Muthu S, Rama Rao N, Sridhara Rao D, Manivel Raja M, Devarajan U and Arumugam S 2011 *J. Appl. Phys.* **110** 023904
Felsner C and Freken G 2013 *Spintronics* (Berlin: Springer)
Fennewr L, Wills A, Bramwell S, Dahlberg M and Schiffer P 2009 *J. Phys.: Conf. Ser.* **145** 012029
Fernandez L A, Martin-Mayor V, Perez-Gaviro S, Tarancon A and Young A P 2009 *Phys. Rev.* B **80** 024422
Fischer K 1975 *Phys. Rev. Lett.* **34** 1438
Fischer K and Hertz J 1991 *Spin Glasses* (Cambridge: Cambridge University Press)
Fisher D and Huse D 1986 *Phys. Rev. Lett.* **56** 1601
Fiorani D, Viticoli S, Dormann J, Tholence J and Murani A 1984 *Phys. Rev.* B **30** 2776
Franz M 2010 *Nat. Mater.* **9** 536
Freeman P, Boothroyd A, Prabhakaran D and Lorenzana J 2006 *Phys. Rev.* B **73** 014434
Fu Z, Zheng Y, Xiao Y, Bedanta S, Senyshyn A, Simeoni G G, Sy Y, Ruecker U, Koegerler P and Brucket T 2013 *Phys. Rev.* B **87** 214406
Fujii S, Ishida S and Asano S 2010 *J. Phys. Soc. Japan* **79** 124702
Gajewski D, Chau R and Maple B M 2000 *Phys. Rev.* B **62** 5496
Galitski V M and Larken A I 2002 *Phys. Rev.* B **66** 064526
Garcia-Soldevilla J, Gomex-Sal J, Blanco J, Espeso J and Rodriguez-Fernandez J 2000 *Phys. Rev.* B **61** 6821
Gardner J, Gringras M and Greedan J 2010 *Rev. Mod. Phys.* **82** 53
Gasi T, Nayak A, Nicklas M and Felser C 2013 *J. Appl. Phys.* **113** 17E301
Goldman A I, Kong T, Kreyssig A, Jesche A, Ramazanoglu M, Dennis K, Bud'ko S and Canfield P C 2013 *Nat. Mater.* **12** 714
Goldman A I 2014 *Sci. Technol. Adv. Mater.* **15** 044801
Goraus J, Slebarski A, Fijalkowski M and Hawelek L 2011 *Eur. Phys. J.* B **80** 65
Goremychkin E, Osborn R, Rainford B, Macaluso R, Adroja D and Koza M 2008 *Nat. Phys.* **4** 766
Goscianska I, Zaleski K, Glowinski H, Kudryavtsev Yu and Duboeink J 2012 *Acta. Phys. Pol.* A **121** 1179
Grinenko V *et al* 2013 *Phys. Status Solidi* B **10** 1
Gschneidner K A, Tang J, Dhar S and Goldman A 1990 *Physica* B **163** 507
Guo M, Bhatt R and Huse D 1994 *Phys. Rev. Lett.* **72** 4137
Haldar A, Suresh K and Nigam A 2010 *Europhys. Lett.* **91** 67006
Han T-H, Helton J, Chu S, Nocera D, J. Rodriguez -Rivera, Broholm C and Lee Y 2012 *Nature* **492** 406
Han T-C, Wu I-C and Hsu H-K 2014 *J. Appl. Phys.* **115** 17D906
Hanashima K, Kodama Y, Akahoshi D, Kanadani C and Saito T 2013 *J. Phys. Soc. Japan* **82** 024702
Hewson A C 1993 *The Kondo Problem to Heavy Fermions* (Cambridge: Cambridge University Press)
Hiroi K, Komatsu K and Sato T 2011 *Phys. Rev.* B **83** 224423
Hiroi M, Hisamatsu T, Suzuki T, Ohishi K, Ishii Y and Watanabe I 2013 *Phys. Rev.* B **88** 024409
Hsu H C, Lee W-L, Lin J-Y, Young B-L, Kung H-H, Huang J and Chou F C 2014 *J. Phys. Soc. Japan* **83** 024709
Huang K, Hamlin J, Baumbach R, Janoschek M, Kanchanavatee N, Zocco D, Ronning F and Maple M B 2013 *Phys. Rev.* B **87** 054513
Hüser D, Rewiersma J, Mydosh J A and Nieuwenhuys G 1983 *Phys. Rev. Lett.* **51** 1290
Iglesias J, Espeso J, Marcano N and Gomez Sal J 2009 *Phys. Rev.* B **79** 195128
Jaeger C, Bihker C, Vallaitis T, Goennenwein S, Opel M, Gross R and Brandt M 2006 *Phys. Rev.* B **74** 045330
Jana Y, Sakai O, Higashinaka R, Fukazawa H, Meeno Y, Dasgupta P and Ghosh D 2003 *Phys. Rev.* B **68** 174413
Jönsson P, Mathieu R, Wernsdorfer W, Tkachuk A and Barbara B 2007 *Phys. Rev. Lett.* **98** 256403
Kashimoto S, Kocjan A, Jaglicic Z, Jazbec S, Iga H, Ishimasa T and Dolinsek J 2011 *Phys. Rev.* B **84** 224201
Katayama N *et al* 2010 *J. Phys. Soc. Japan* **79** 113702
Katzreaber H, Körner M and Young A P 2006 *Phys. Rev.* B **73** 224432
Kawamura H 1992 *Phys. Rev. Lett.* **68** 3785
Kawamura H 2010 *J. Phys. Soc. Japan* **79** 011007
Kondo J 1964 *Prog. Theor. Phys.* **32** 37
Kondo J 2005 *J. Phys. Soc. Japan* **74** 1
Kondo J 2013 *The Physics of Dilute Magnetic Alloys* (Cambridge: Cambridge University Press)
Kong T, Bud'ko S, Jesche A, McArthur J, Kreyssig A, Goldman A and Canfield P C 2014 *Phys. Rev.* B **90** 014424
Kopec T 1997 *Phys. Rev. Lett.* **79** 4266
Koper G and Hilhorst H 1988 *J. Phys. France* **49** 429
Koper G and Hilhorst H 1989 *Physica* A **155** 431
Kozelj P *et al* 2013 *Phys. Rev.* B **88** 214202
Krimmel A, Hemberger J, Nicklas M, Knebel G, Trinkl W, Brando M, Fritysch V, Loidl A and Ressouche E 1999 *Phys. Rev.* B **59** 6604
Krishna Murthy J and Venimadhav A 2013 *Appl. Phys. Lett.* **103** 252410
Lacroix C, Mendels P and Mila F 2011 *Introduction to Frustrated Magnetism Springer Series in Solid-State Sciences* (Berlin: Springer)
LaForge A, Pulido S, Cava R, Chan B and Ramirez A P 2013 *Phys. Rev. Lett.* **110** 017203
Laiho R, Lähderanta E, Salminen J, Lisunov K and Zakhvalinskii V 2001 *Phys. Rev.* B **63** 094405
Larson D, Katzgraber H, Moore M and Young A P 2013 *Phys. Rev.* B **87** 024414
Lausberg S *et al* 2012 *Phys. Rev. Lett.* **109** 216402
Lei H, Abeykoon M, Bozin E and Petrovic C 2011 *Phys. Rev.* B **83** 180503R
Leuzzi L, Parisi G, Ricci-Tersenghi F and Ruiz-Lorenzo J 2009 *Phys. Rev. Lett.* **103** 267201
Leuzzi L, Parisi G, Ricci-Tersenghi F and Ruiz-Lorenzo J 2011 *Phil. Mag.* **91** 1917
Li D, Nimori S, Shiokawa Y, Haga Y, Yamamoto E and Onuki Y 2003 *Phys. Rev.* B **68** 172405
Li Z, Jing C, Chen J, Yuan S, Cao S and Zhang J 2007 *Appl. Phys. Lett.* **91** 112505
Li D, Nimori S, Ohta S, Yamamura Y and Shikama Y 2013 *J. Phys.: Conf. Ser.* **400** 032044
Liu T *et al* 2010 *Nat. Mater.* **9** 718
Loram J W, Whall T and Ford P J 1970 *Phys. Rev.* B **2** 857
Lu X *et al* 2014 *Phys. Rev.* B **90** 024509
Luo , Q , Zhao D, Pan M and Wang W 2007 *Appl. Phys. Lett.* **90** 211903
Lutes O and Schmit J 1962 *Phys. Rev.* **125** 433
Ma L, Wang W, Lu J, Li J, Zhen C, Hou D and Wu G 2011 *Appl. Phys. Lett.* **99** 182507
Maletta H and Felsch W 1979 *Phys. Rev.* B **20** 1245
Malinowski A, Bezusyy V, Minnikayev R, Dziawa P, Syryanyy Y and Sawicki M 2011 *Phys. Rev.* B **84** 024409
Manni S, Tokiwa Y and Gegenwart P 2014 *Phys. Rev.* B **89** 241102
Marcano N, Gomez Sal J, Especo J, Ferandez-Barquin L and Paulsen C 2007 *Phys. Rev.* B **76** 22419
Matthews J 2008 *Physics Today* **61**(7) 22
Mezard M, Parisi G and Virasoro M 1986 *Spin Glass Theory and Beyond* **9** (Singapore: World Scientific)

Moritomo Y, Higashi K, Matsuda K and Nakamura A 1997 *Phys. Rev.* B **55** R14725
Mulder C, van Duyneveldt A and Mydosh J A 1981 *Phys. Rev.* B **23** 1384
Mydosh J A 1988 *J. Appl. Phys.* **63** 5414
Mydosh J A 1993 *Spin Glasses: an Experimental Introduction* (London: Taylor and Francis)
Nagata S, Keesom P and Harrison H 1979 *Phys. Rev.* B **19** 1633
Nagata S, Koseki N and Ebisu S 2012 *Phil. Mag.* **92** 2957
Nayak A, Nicklas M, Chadov S, Shekhar C, Skourski Y, Winterlik J and Felser C 2013 *Phys. Rev. Lett.* **110** 127204
Nayak A, Nicklas M, Khuntia P, Shekhar C, Skourski Y, Baenitz M and Felser C 2015 to be published
Nishimorei H 2001 *Statistical Physics of Spin Glasses and Information Processing* (Oxford: Clarendon)
Okada H, Koyama K, Watanabe K, Kusakari Y, Kusakan T and Nishihara H 2008 *Appl. Phys. Lett.* **92** 062502
Overhauser A 1959 *Phy. Rev. Lett.* **3** 414
Overhauser A 1962 *Phys. Rev.* **128** 1437
Panagopoulos C, Tallon J, Rainford B, Xiang T, Cooper J and Scott C 2002 *Phys. Rev.* B **66** 064501
Panagopoulos C, Petrovic A, Hillier A, Tallon J, Scott C and Rainford B 2004 *Phys. Rev.* B **69** 144510
Parisi G 1979 *Phys. Rev. Lett.* **43** 1754
Parisi G 1980 *J. Phys.* A **13** 1101 and 1887
Paulose P, Sampathkumaran E, Bitterlich H, Behr G and Löser W 2003 *Phys. Rev.* **67** 21401
Piatek J, Dalla Piazza B, Nikseresht N, Tsyrulin N, Zivkovic I, Kraemer K, Laver M, Prokes K, Matas S, Christensen N and Ronnow H M 2013 *Phys. Rev.* B **88** 014408
Quilliam J, Meng S and Kycia J 2012 *Phys. Rev.* B **85** 184415
Raicevic I, Jaroszynsli J, Popoviv D, Panagopoulos C and Sasagawa T 2008 *Phys. Rev. Lett.* **101** 177004
Ramirez A P 2001 *Handbook of Magnetic Materials* **13** Buschow K H J (Amsterdam: North Holland) p 423
Rayaprol S and Pöttgen R 2006 *Phys. Rev.* B **73** 214403
Read N, Sachdev S and Ye J 1995 *Phys. Rev.* B **52** 384
Reyren N *et al* 2007 *Science* **317** 1196
Rieger H and Young A P 1994 *Phys. Rev. Lett.* **72** 4141
Rodriguez J, Acel A, Carlo J, Dunsiger S, MacDougall G, Russo P, Savici A, Uemura Y, Wiebe C and Luke G 2010 *Phys. Rev. Lett.* **105** 107203
Rodriguez G F, Kenning G G and Orbach R 2013 *Phys. Rev.* B **88** 054302
Roy S and Chattopadhyay M 2009 *Phys. Rev.* B **79** 052407
Sachdev S 2011 *Quantum Phase Transition* 2nd edn (Cambridge: Cambridge University Press)
Sandlund L, Svedlindh P, Granberg P, Nordblad P and Lundgren L 1988 *J. Appl. Phys.* **64** 5616
Sawicki M *et al* 2013 *Phys. Rev.* B **88** 085204
Schmitt D, Prestigiacomo J, Adams P, Young D, Stadler S and Chan J 2013 *Appl. Phys. Lett.* **103** 082403
Seaman C L, Maple M B, Lee B, Ghamaty S, Torikachvili M, Kang J-S, Liu L, Allen J and Cox D 1991 *Phys. Rev. Lett.* **67** 2882
Sharma A and Young A P 2011a *Phys. Rev.* B **83** 214405
Sharma A and Young A P 2011b *Phys. Rev.* B **84** 014428
Sherrington D and Kirkpatrick S 1975 *Phys. Rev. Lett.* **35** 1792
Sherrington D 2013 *Phys. Rev. Lett.* **111** 227601
Silverstein H *et al* 2014 *Phys. Rev.* B **89** 054433
Singh D K and Lee Y S 2012 *Phys. Rev. Lett.* **109** 247201
Singh S *et al* 2012 *Phys. Rev. Lett.* **109** 246601
Slebarski A, Glogowski W, Goraus J and Kaczorowski D 2008 *Phys. Rev.* B **77** 125135
Sompolinsky H and Zippelius A 1981 *Phys. Rev. Lett.* **47** 359
Saparov B, Calder S, Sipos B, Cao H, Chi S, Singh D, Christianson A, Lumsden M and Sefat A 2011 *Phys. Rev.* B **84** 245132
Stein D and Newman C 2013 *Spin Glasses and Complexity* (Princeton, NJ: Princeton University Press)
Stewart G 2011 *Rev. Mod. Phys.* **83** 1589
Suzuki M 1977 *Prog. Theor. Phys.* **58** 1151
Süllow S, Nieuwenhuys G, Menovsky A, Mydosh J A, Mentink S, Mason T and Buyers W 1997 *Phys. Rev. Lett.* **78** 354
Szlawska M, Kaczorowski D and Reehuis M 2010 *Phys. Rev.* B **81** 094423
Szlawska M, Gnida D and Kaczorowski D 2011 *Phys. Rev.* B **84** 134410
Szlawska M, Majewicz M and Kaczorowski D 2014 *J. Phys.: Condens. Matter* **26** 126002
Tabata Y, Matsuda K, Kanada S, Yamazaki T, Waki T, Nakamura H, Sato K and Kindo K 2010 *J. Phys. Soc. Japan* **79** 123704
Tabei S, Gingras M, Kao Y-K, Stasiak P and Fortin J Y 2006 *Phys. Rev. Lett.* **97** 237203
Takeshita S and Kadono R 2008 *J. Phys. Soc. Japan* **77** 103703
Takeshita S and Kadono R 2009 *New J. Phys.* **11** 035006
Tang M, Bai H, Wang W, Bogdanov D, Winzer K, Samwer K and Egami T 2007 *Phys. Rev.* B **75** 172201
Thanh T D, Manh D, Phan T, Phong P, Hung L, Phuc N and Yu S 2014 *J. Appl. Phys.* **115** 17B504
Theumann A and Coqblin B 2004 *Phys. Rev.* B **69** 214418
Thiem S and Chalker J 2014 arXiv:14075868
Tien , C , Lu J and Jang L 2002 *Phys. Rev.* B **65** 214416
Tougait O, Troc R, Zaleski A and Noël H 2007 *Phil. Mag.* **87** 1085
Tran V and Swiatek-Tran B 2008 *Dalton Trans.* **28** 4860
Tristan N, Hemberger J, Krimmel A, Krug von Nidde H-A, Tsurkan V and Loidl A 2005 *Phys. Rev.* B **72** 174404
Tristan N, Zestrea V, Beht G, Klingeler R, Büchner B, Krug von Nidda H, Loidl A and Tsurkan V 2008 *Phys. Rev.* B **77** 094412
van Hemmen J and Morgenstern I 1983 *Lecture Notes in Physics* **192** (Berlin: Springer)
van Hemmen J and Morgenstern I 1986 *Lecture Notes in Physics* **275** (Berlin: Springer)
Verbeek B, Nieuwenhuys G, Stocker H and Mydosh J A 1978 *Phys. Rev. Lett.* **40** 586
Villain J 1979 *Z. Phys.* B **33** 31
Webster P and Ziebeck K 1988 *Landolt-Börnstein New Series Group III,* **19** CBerlin Springer p 75
Wenger L, Hunter G, Mydosh J A, Gotaas J and Rhyne J 1986 *Phys. Rev. Lett.* **56** 1090
Wen J-S, Xi G, Gu G, Tranquanda J M and Bergenau R J 2011 *Rep. Prog. Phys.* **74** 124503
Westerholt K, Bergmann A, Grabis J, Nefedov A and Zabel H 2005 *Lecture Notes in Physics* (Berlin: Springer) **676** 67
Westerkamp T, Deppe M, Küchler R, Brando M, Geibel C, Gegenwart P, Pikul A and Steglich F 2009 *Phys. Rev. Lett.* **102** 206404
Wiener T, Fisher I, Bud'ko S, Kracher A and Canfield P 2000 *Phys. Rev.* B **62** 15056
Wilson K 1975 *Rev.Mod.Phys.* **47** 733
Wu W, Bitko D, Rosenbaum T and Aeppli G 1993 *Phys. Rev. Lett.* **71** 1919
Wu J and Leighton C 2003 *Phys. Rev.* B **67** 174408
Yavors'kii T and Weigel M 2012 *Eur. Phys. J. Spec. Top.* **210** 159
Young A P 1997 *Spin Glasses and Random Fields* **12** (Singapore: World Scientific)
Young A P 2002 *Comput. Phys. Commun.* **146** 107
Young A P 2013 *Bull. Am. Phys. Soc.* **58** F29
Xu S-G, Sun Y-L, Jiang S, Xing H, Jiao L, Yuan H-Q, Fenf C-M, Xu Z-A and Cao G-H 2012 *J. Phys.: Conf. Ser.* **400** 032115
Zapf S, Jeevan H S, Ivek T, Pfister F, Klingert F, Jiang S, Wu D, Gegenwart P, Kremer R K and Dressel M 2013 *Phys. Rev. Lett.* **110** 237002
Zomack M, Baberschke K and Barnes S 1983 *Phys. Rev.* **27** 4135
Zhang J, Fritsch K, Hao Z, Bagheri , Gingras M, Granroth G, Jiramongkolchai P, Cava R and Gaulin B 2014 *Phys. Rev.* B **89** 134410
Zhou G and Bakker H 1994 *Phys. Rev. Lett.* **73** 344