



The impact of Cu content on crystallization kinetics and soft magnetic properties for ductility FePCCu amorphous alloy

Xiangxiang Jiang^a, Cong Liu^{a,*}, Hongzhi Luo^{a,**}, Jing Ding^b, Mingqing Zuo^c, Chen Yang^a, Xuefang Dai^a, Shengli Zhu^{d,e}, Guodong Liu^{a,***}

^a State Key Laboratory of Reliability and Intelligence of Electrical Equipment, School of Materials Science and Engineering, Hebei University of Technology, Tianjin, 300130, China

^b School of Energy and Machinery, Dezhou University, Dezhou, 253023, China

^c College of Materials Science and Engineering, Hunan Joint International Laboratory of Advanced Materials and Technology for Clean Energy, Hunan University, Changsha, Hunan, 410082, China

^d School of Materials Science and Engineering, Tianjin University, Tianjin, 30072, China

^e School of Materials Science and Engineering, Lanzhou Jiaotong University, Lanzhou, 730070, China

ARTICLE INFO

Keywords:

Fe-based amorphous/nanocrystalline alloy
Crystallization kinetics
Soft magnetic properties
Bending ductility

ABSTRACT

Effects of trace addition of Cu in ductility $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7\text{--}1$ at. %) amorphous alloys on the crystallization kinetics, soft magnetic properties and hardness were investigated. With Cu content increasing, the Curie temperature (T_c) and initial crystallization onset temperature (T_{x1}) increase at first and then drop. The nucleation process becomes hard with the increasing of Cu content, and it is more difficult than growth process. The $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ amorphous ribbon demonstrates high saturation magnetization (B_s) of 1.63 T, low coercivity (H_c) of 5.2 A/m, and high initial permeability (μ_i) of 15,000, alongside Vickers hardness (H_v) exceeding 760 and excellent bending ductility. Annealing-induced [amorphous + α -Fe] phase in $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ has good soft magnetic properties, with B_s of 1.66 T, H_c of 9.7 A/m, μ_i of 16,000, and H_v over 1300. Notably, only nanocrystalline α -Fe phase precipitation is observed in its ribbon after annealing at $T_{x2}\text{--}50$ K (T_{x2} , second crystallization onset temperature). At the same time the sample has good flexibility. Fe-based amorphous/nanocrystalline alloys can be as promising option for commercial applications because of their remarkable soft magnetic properties, cost-effectiveness, and exceptional bending ductility.

1. Introduction

Modern technology and improvements in industrial technology revealed some problems of the society, such as excessive energy consumption. It is important to achieve the dual carbon target by improving energy efficiency. Compared to regular silicon steel, Fe-based amorphous/nanocrystalline composites can be applied in generators, transformers, compressors, etc., because they have low coercivity (H_c), high saturation magnetization (B_s), and high permeability (μ) [1–3]. Using materials that have great magnetic character and strong mechanical strength can help equipment work better and last longer, with reducing resource and material costs. Several decades ago, commercially available Nanoperm [4], Finemet [5], and Hitperm [6] alloys have been designed

and put into industry application. However, these Fe-based amorphous/nanocrystalline alloys contain more non-magnetic elements like Zr, Mo, and Nb to enhance the amorphous formation ability (AFA) [7–10]. The addition of these non-magnetic metallic elements, which are more expensive than Fe, not only reduces the B_s of the alloy but also increases the cost of the raw materials. Although FeSiBPCu [11], FeBCCu [12] and FeCoBCCu [13] amorphous/nanocrystalline composites present high B_s above 1.7 T, the expensive element B in these alloys causes high material costs. Balancing the enhancement of soft magnetic properties with the reduction of material costs become a challenge in developing high-performance Fe-based amorphous/nanocrystalline alloys. Consequently, it is essential to explore new Fe-based amorphous/nanocrystalline alloys that offer excellent soft magnetic features, straightforward

* Corresponding author.

** Corresponding author.

*** Corresponding author.

E-mail addresses: liucong010243@163.com (C. Liu), luo_hongzhi@163.com (H. Luo), gdlu1978@126.com (G. Liu).

<https://doi.org/10.1016/j.pnsc.2025.03.005>

Received 1 November 2024; Received in revised form 3 March 2025; Accepted 11 March 2025

Available online 31 March 2025

1002-0071/© 2025 Chinese Materials Research Society. Published by Elsevier B.V. All rights are reserved, including those for text and data mining, AI training, and similar technologies.

compositions, and low costs for industrial applications.

The Fe-P-C amorphous alloy is a common magnetic material used in magnetic devices due to its simple constituent, low price and exceptional soft magnetic properties [14,15]. Previous studies on Fe-P-C amorphous ribbon alloys show that the values of their B_s and H_c are 1.31–1.56 T and 3.3–16.4 A/m, respectively, limiting their industry applications [16,17]. Research shows that the magnetism of Fe-based amorphous alloys can be effected by substituting trace amounts of other elements [18]. Li et al. demonstrated that increasing the P content can refine the grain size and lower the coercivity of Fe-Si-B-P-Nb-Cu alloys [19]. Similarly, the P content can be appropriately increased in the Fe-P-C alloys to achieve grain refinement and lower H_c . Lu et al. discovered that a small amount of Cu doping can improve the AFA, while overdoped Cu may stimulate the formation of α -Fe nanocrystals [20]. Fan et al. discovered that the introduction of Cu inhibited the surface crystallization of high-Fe content Fe₈₆B₇C₇ alloy and improved the amorphous formation [21]. Additionally, because of the positive mixing enthalpy between Fe and Cu, the introduction of Cu provided heterogeneous nucleation sites for α -Fe grains, making it advantageous for the development of nanocrystalline alloys [22,23]. Li et al. improved the soft magnetic properties of Fe-B-P-C-Cu alloys by varying the Cu content. A high saturation magnetization of 1.85 T and a low coercivity of 13.0 A/m were obtained in Fe_{82.9}B₉P₃C₄Cu_{1.1} nanocrystalline alloy [24]. Recently, we synthesized Fe₈₃P₁₁C₆ alloy with Fe content higher than 80 at. %, which possesses outstanding soft magnetic characteristics [25]. In addition, the initial crystalline phase high Fe-content amorphous alloys are typically α -Fe nanocrystals, the influence of Cu on the crystallization process and soft magnetic properties of these alloys still needs further clarification.

In present work, we add Cu element to this high Fe-content Fe₈₃P₁₁C₆ amorphous alloy to improve the soft magnetic characteristics and hardness. Considering that the soft magnetic properties and AFA of Cu-doped Fe-P-C alloys are sensitive to Cu content, they will not be so satisfactory when the Cu content is less than 0.7 at. % or more than 1 at. % [22,23], in present work, we focus on the Cu composition range of 0.7–1 at. %. The effects of Cu content on the AFA, crystallization kinetics and soft magnetic characteristics of Fe_{83-x}P₁₁C₆Cu_x (x = 0.7–1 at. %) amorphous alloys were investigated.

2. Experimental procedures

Ingot with the composition of Fe_{83-x}P₁₁C₆Cu_x (where x = 0.7–1 at. %) were produced induction melting mixtures consisting of pure metals (Fe and Cu), Fe₃P fragments, and graphite blocks. The purities of them are greater than 99.9 % by mass, in an argon environment. Alloy ribbons with approximately thickness of 20–25 μ m and width of 1.5 mm were fabricated using a single-roller melt spinning method, with the copper wheel operating at a circumferential velocity of around 40–45 m/s. The crystal structures of the ribbons, both as-spun and after annealing, were analyzed using X-ray diffraction (XRD, Bruker D8). The structure of precipitated phase and grain size of Fe_{83-x}P₁₁C₆Cu_x (x = 0.7 and 0.9) samples annealed at T_{x2} -50 K were investigated by transmission electron microscopy (TEM, JEM-2100F). The thermal stability of these ribbon samples was examined by differential scanning calorimetry (DSC, METTLER TOLEDO TGA/DSC 1) with heating rates ranging from 0.17 to 0.67 K/s in a high-purity argon atmosphere. Magnetic properties were measured using a vibrating sample magnetometer (VSM, Lakeshore 7500) in a 1 T magnetic field at room temperature. The coercive force and initial permeability of these samples, each approximately 7 cm in length and 1 mm in width, were evaluated using a DC B-H loop analyzer under a maximum field of 800 A/m. The initial permeability was calculated by B-H hysteresis loop. The Curie temperature (T_c) was determined using DSC. The annealing process was performed by quickly placing the samples in a furnace with the target temperature and the samples were maintained at the target temperature for 5 min. The annealing temperatures of the samples ranged from 587 to 594 K for T_c + 10 K, 646–653 K for T_{x1} and 750–755 K for T_{x2} , respectively. During the whole annealing process, the samples were in a

vacuum environment. Hardness measurements were performed using a Vickers hardness indenter with a load of 0.98 N. Bending ductility was assessed by bending a sample, with the bent outer surface analyzed using scanning electron microscopy (SEM, TDCL-4800). The specimens' density was determined from the Archimedes' principle, utilizing deionized water as the working liquid.

3. Result and discussion

3.1. Thermal stability and crystallization kinetics

Fig. 1(a) shows the XRD patterns of Fe_{83-x}P₁₁C₆Cu_x (x = 0.7, 0.8, 0.9 and 1 at. %) as-spun ribbons. In these patterns only broad peaks are observed, and no trace of crystalline peaks can be seen, indicating that only an amorphous phase is synthesized in these as-spun ribbons. Recent studies find that the AFA for amorphous alloy systems is related to the Δq , which is the full-width at the half-maximum (FWHM) of the XRD peak [26]. As appeared in Fig. 1(b), The Δq diminishes with the increment of Cu contents, indicating that increasing Cu content can weaken AFA. The positive mixing enthalpy between Fe and Cu atomic pair is 13 kJ/mol [27], as can be found in the inset of Fig. 1(b), the addition of Cu atoms can cause structural coordination and topological rearrangement. The excessive Cu atoms tend to form Cu clusters and repel Fe atoms, resulting in the decrease of AFA in this alloy system [28].

Fig. 2 (a) displays the DSC curve of the Fe_{83-x}P₁₁C₆Cu_x (x = 0.7, 0.8, 0.9 and 1 at. %) amorphous ribbons. All samples display two distinct exothermic peaks as they crystallize through a two-step process. The Curie temperature (T_c), initial crystallization onset temperature (T_{x1}) and second crystallization onset temperature (T_{x2}) are shown in Fig. 2(b–d), respectively. The T_c and T_{x1} increase from 578 K and 646 K to 587 K and 653 K first and then drop to 584 K and 649 K, respectively. And the T_{x2} decreases with increasing Cu content and then remains almost unchanged with the doping of Cu content. It is worth noting that, for different samples, the temperature span from T_{x1} to T_{x2} is between 97 and 109 K which is beneficial for regulating the precipitation of the initial crystalline phase and restraining the precipitation of other compound phases.

To examine the crystallization behaviors of Fe-P-C-Cu alloys, XRD was measured for Fe_{82.3}P₁₁C₆Cu_{0.7} amorphous ribbon annealing at different temperatures. Fig. 3 (a) shows XRD patterns of Fe_{82.3}P₁₁C₆Cu_{0.7} amorphous ribbon annealed at T_{x1} , T_{p1} , T_{x2} -50 K, T_{x2} and T_{p2} for 5 min, respectively. The T_{p1} and T_{p2} peaks correspond to the reactions of amorphous α -Fe + residual amorphous phase and α -Fe + residual amorphous phase α -Fe + Fe₃P + Fe₃C phase, similar results have also been observed in other Fe-based amorphous alloys [22,23]. It is interesting that only α -Fe precipitation, and no trace of other new phases exists even in the ribbons annealed at a high temperature of T_{x2} -50 K. Therefore, the XRD patterns in Fig. 3 (b) confirm that Fe_{83-x}P₁₁C₆Cu_x (x = 0.7, 0.8 and 0.9 at. %) alloys annealed at T_{x2} -50 K for 5 min are composed of amorphous + α -Fe phase. Using the Scherrer formula, we estimated the average grain size of α -Fe precipitates. The nanocrystalline grain size (D) of Fe_{83-x}P₁₁C₆Cu_x alloys increases from 22.5 nm to 52.5 nm with increasing Cu content from x = 0.7 to x = 0.9. The statistics show that the grain size of the sample with x = 0.7 is distributed in the range of 10–25 nm, with an average of 17.4 nm, as shown in Fig. 4 (a). The high density and uniformity of α -Fe can be observed, which is close to the results calculated by XRD. Fig. 4 (b) shows that the grain size of the sample with x = 0.9 is distributed in a wide range of 8–21 nm, with an average of 13.4 nm. It can be observed that multiple α -Fe agglomerates grow and form clusters, which makes the single grain size relatively small. However, this is different from the calculation results of XRD in some degree. This can be related to the possible consistent orientation of clusters, which can have influence on the intensity and FWHM. This also shows that it is indispensable to observe the size of nanocrystals by TEM tests. The formation of nanocrystals with small grain size can be attributed to the large amount of clusters caused by the addition of Cu, which

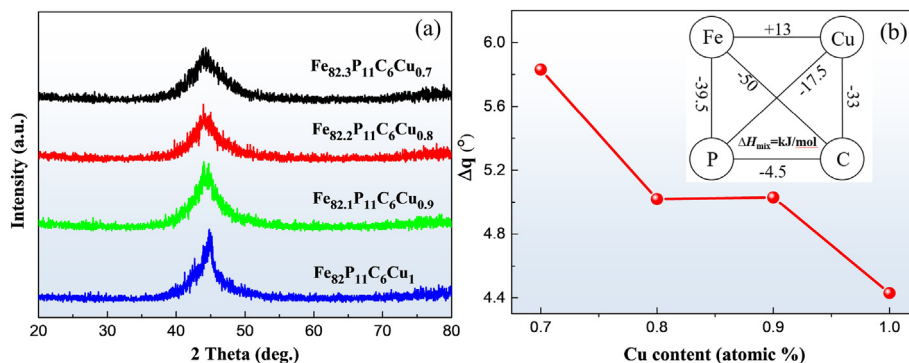


Fig. 1. (a) The XRD patterns of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7\text{--}1.0$ at. %) as-spun ribbons (b) Δq of XRD patterns as a function of Cu content.

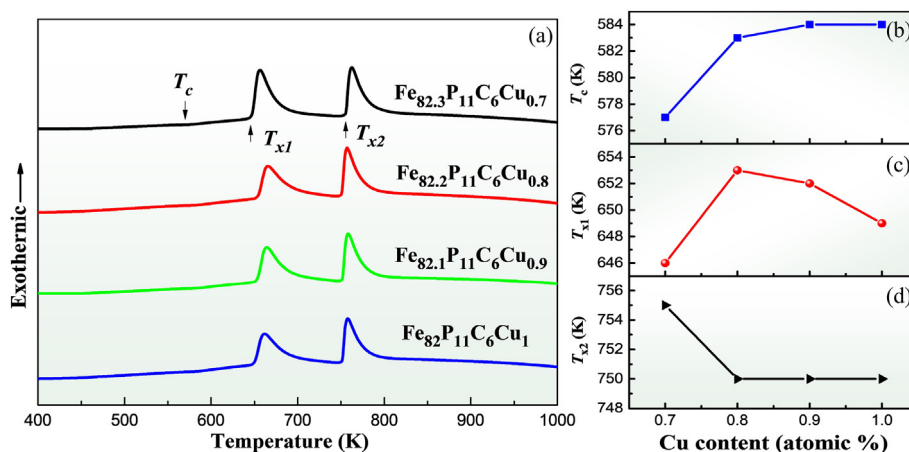


Fig. 2. (a) The DSC curves of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7\text{--}1.0$ at. %) amorphous ribbons at a heating rate of 0.67 K/s (b–d) The Curie temperature T_c and two crystallization onset temperature T_{x1} and T_{x2} as a function of Cu content.

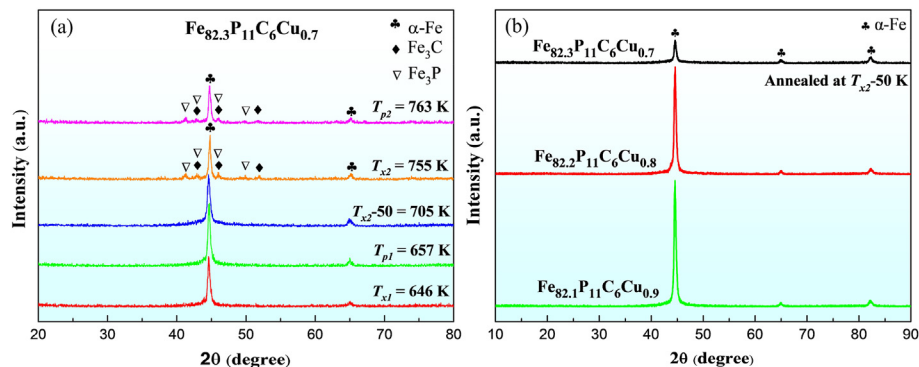


Fig. 3. (a) XRD patterns of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ amorphous ribbon annealed at different temperatures for 5 min (b) XRD patterns of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7, 0.8$ and 0.9 at. %) amorphous ribbons annealed at $T_{x2}-50$ K for 5 min.

aids in the initiation of α -Fe formation and prevents α -Fe phase from growing to the critical size of crystallization by forming multiple clusters of different structures [26,29].

The DSC curves of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7$ and 0.9 at. %) alloys are shown in Fig. 5(a and b). Alloys are heated at different rates of 20, 30, 40, and 80 K/min, respectively. As the heating rate goes up, both T_{x1} and T_{p1} rise, which shows that the crystallization of amorphous alloys is a thermally activated process and exhibits an obvious kinetic effect [30]. We applied the Kissinger equation to determine the energy required for crystallization (E_{x1} and E_{p1}) by using the formula $\ln(T^2/\beta) = E/RT + \text{constant}$ [31]. Here, β is the temperature increase rate, R is a constant for gases, and T represents T_{x1} and T_{p1} . Fig. 5(c and d) shows the Kissinger

curves of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7$ and 0.9 at. %) alloys. The values of activation energies of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy (marked as $E_{x1-0.7}$ and $E_{p1-0.7}$) are 454.71 ± 17.47 and 403.37 ± 9.26 kJ/mol, respectively, and these values for $\text{Fe}_{82.1}\text{P}_{11}\text{C}_6\text{Cu}_{0.9}$ alloy (marked as $E_{x1-0.9}$ and $E_{p1-0.9}$) are 504.62 ± 18.49 and 398.73 ± 6.91 kJ/mol, respectively. It is widely recognized that T_{x1} is linked to the crystal nucleation process, while T_{p1} is linked to the process of growth. Obviously, the value of $E_{x1-0.7}$ is smaller than $E_{x1-0.9}$, while the value of $E_{p1-0.7}$ is larger than $E_{p1-0.9}$. Therefore, the nucleation progress for $\text{Fe}_{82.1}\text{P}_{11}\text{C}_6\text{Cu}_{0.9}$ alloy is more difficult than that of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy. E_{x1} is larger than E_{p1} , which indicates forming crystal nuclei in the alloy is harder than the subsequent growth, probably due to the large size of Cu atom, which heightens the energy barrier and

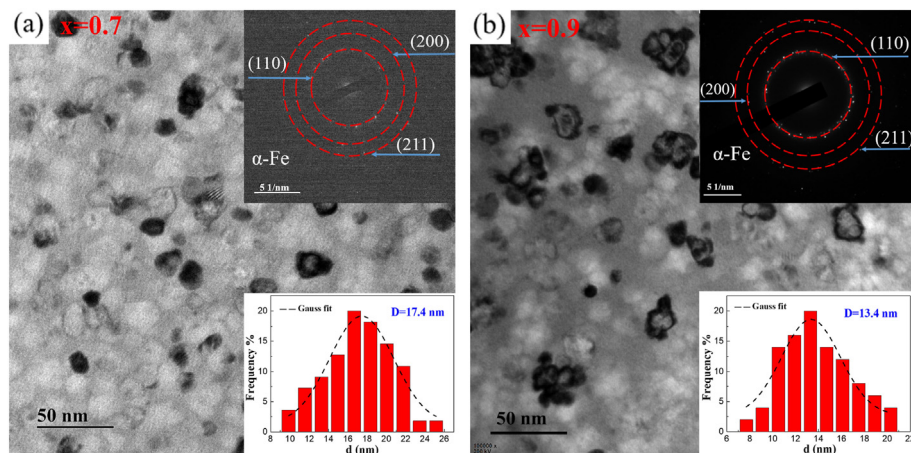


Fig. 4. TEM images of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ((a) $x = 0.7$ and (b) 0.9 at. %) alloys annealed at T_{x2} -50 K, the illustrations are SAED patterns and grain size distribution, respectively.

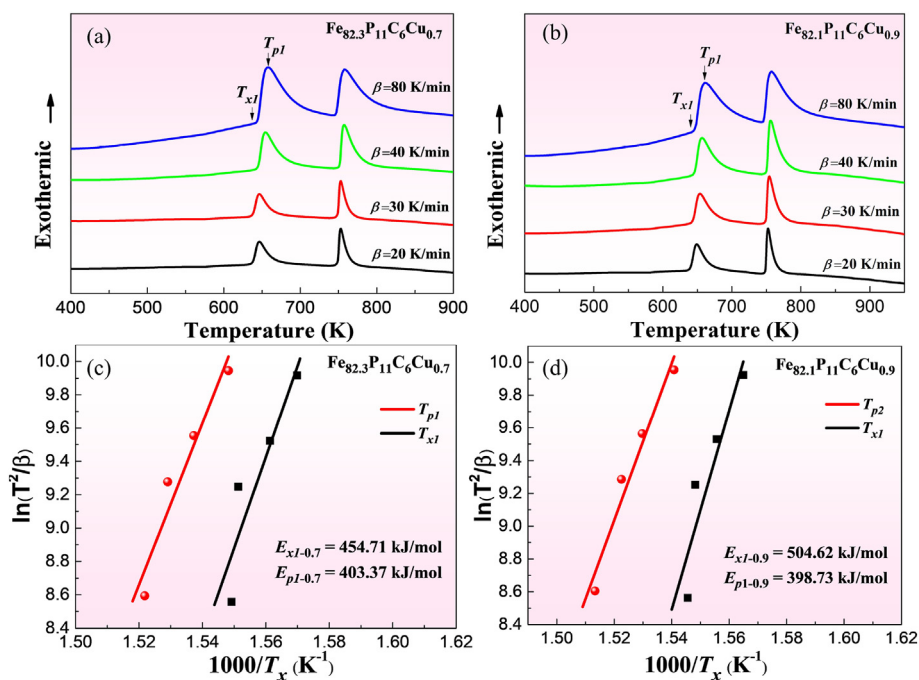


Fig. 5. (a–b) DSC curves of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7$ and 0.9 at. %) ribbons at different heating rates (20, 30, 40, and 80 K/min) (c–d) Kissinger plots of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7$ and 0.9 at. %) ribbons, symbols are experimental data, lines are fitting results.

hinders the diffusion of atoms during the nucleation process. When Cu facilitates the nucleation of α -Fe, it creates a larger atomic gap within the residual amorphous phase, allowing for easier diffusion of atoms. This leads to lower diffusion resistance during grain growth compared to the nucleation process, which suggests that the activation energy for growth is less than that for nucleation [32].

Calculation of amorphous crystallization fraction α obtained by DSC curves is a common method and has been used in different literatures [33,34]. In Fig. 5(a and b) the DSC curves for $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7$ and 0.9 at. %) alloys at different heating rates are measured and the α is calculated from the first exothermic peak. In Fig. 6(a and b), the relation between α and temperature is presented. As the temperature rises, the α -T curves exhibit an S-shaped distribution, demonstrating that the crystallization process of the alloy involves both nucleation and growth, which can be categorized into three distinct stages. For $0 \leq \alpha \leq 0.1$, nucleation is the dominant process, and the crystallization transformation is minimal. In the range of $0.1 \leq \alpha \leq 0.9$, the volume free

energy diminishes while the interface between the crystalline and amorphous phases increases, resulting in a rise in interfacial energy. For $0.9 < \alpha < 1$, the interfacial energy between the crystalline-amorphous interface diminishes, leading to a gradual cessation of crystallization [35,36]. Interestingly, as the heating rate rises, the slope in the second stage declines, and this observation may be linked to the energy accumulation effects [37].

To investigate the nucleation and growth mechanisms of the alloy's first crystallization process in detail, the local Avrami index $n(\alpha)$ is calculated using the extended JMA equation [38]. The value of $n(\alpha)$ is derived from the slope of the curve relating $\ln[-\ln(1-\alpha)]$ to $\ln[(T-T_0)/\beta]$, with the dependence of $n(\alpha)$ on the crystallization fraction presented in Fig. 6(c and d). As shown, the $n(\alpha)$ curves initially rise, then decline, and ultimately increase almost vertically at the end of the crystallization process. For α values between 0.0 and 0.1, $n(\alpha)$ decreases as the heating rate increases. In the range of $0.1 \leq \alpha \leq 0.9$, $n(\alpha)$ is approximately 2.0–4.0 for the $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy and 2.0 to 7.0 for the

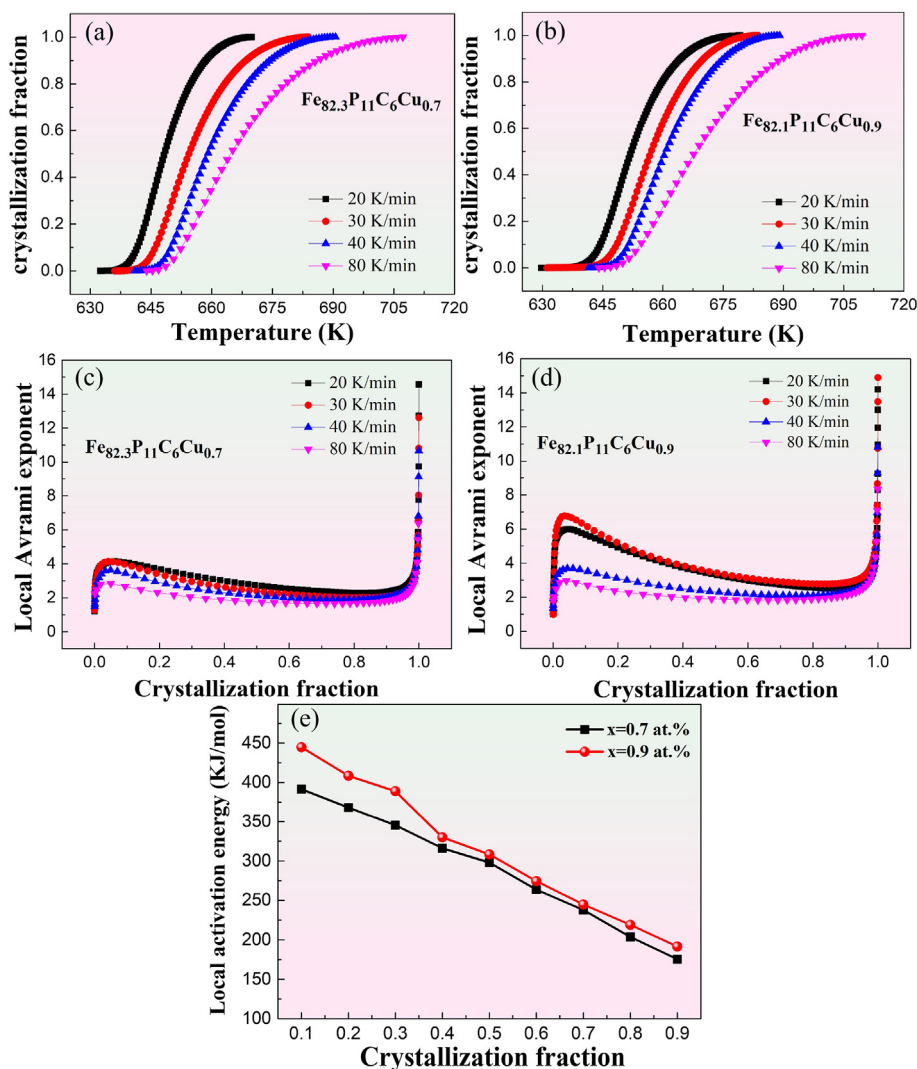


Fig. 6. (a–b) Crystallization fraction as a function of temperature for Fe_{83–x}P₁₁C₆Cu_x (x = 0.7 and 0.9 at. %) alloys at different heating rates (c–d) The local Avrami exponent on the crystallization fraction (e) The relationship between local activation energy and crystallization fraction.

Fe_{82.1}P₁₁C₆Cu_{0.9} alloy, indicating that nucleation rate initially increases before decreasing with higher crystallization fractions. The results show that the nucleation rate decreases with the increase of the heating rate, and the rapid heating is conducive to the centralized nucleation and the synchronous growth of crystal nucleus, which results in the formation of uniform nanocrystalline structures.

To assess the crystallization tendency of Fe–P–C–Cu amorphous alloys, we calculate the local activation energy $E(\alpha)$, which indicates the activation energy at a specific stage corresponding to a crystallization fraction of α . Fig. 6 (e) illustrates E_α decreases with the increase of crystallization fraction, indicating that the nucleation process is more difficult than the growth process. Furthermore, the local activation energy increases with higher Cu content. When Cu content is high, the formation of Cu-rich and P-rich nanoclusters gathering on the amorphous surface enhances the non-uniform nucleation of α -Fe at the interface between Cu and the amorphous phase [39]. This is because the nucleation barrier of non-uniform nucleation is lower than that of uniform nucleation, and the non-uniform nucleation occurring at the Cu and amorphous interfaces is easier than the uniform nucleation within the amorphous phases, and also because the (111) plane of fcc-Cu is well-matched with the (110) plane of α -Fe [40]. Therefore, the α -Fe (110) plane tend to nucleate on the surface of the fcc-Cu (111) plane and reduces the interfacial energy of this alloy.

3.2. Soft magnetic properties

To investigate how magnetic properties are related to the micro-structure of materials, we measured the saturation magnetization (B_s) and coercivity (H_c) of Fe_{83–x}P₁₁C₆Cu_x (x = 0.7, 0.8, and 0.9 at. %) alloys in both as-spun and annealed states (at T_c+10 K and $T_{x2}-50$ K). Fig. 7(a and b) illustrates how B_s and H_c change with varying Cu content. In the as-spun state, H_c ranges from approximately 14 to 40 A/m. After annealing at T_c+10 K the H_c rapidly decreases to 5.3–3.7 A/m, and increases again to 9.7–12.6 A/m after annealing at $T_{x2}-50$ K. Meanwhile, B_s increases from 1.62 T for as-spun Fe_{82.3}P₁₁C₆Cu_{0.7} alloy to 1.66 T after annealing at $T_{x2}-50$ K, due to the precipitation of the α -Fe phase. The initial permeability (μ_i) is 15,000 for the amorphous phase and 16,000 for the [amorphous + α -Fe] phase in the Fe_{82.3}P₁₁C₆Cu_{0.7} alloy. Annealing the amorphous ribbons at T_c+10 K helps relieve the residual internal stress and facilitates the structural relaxation [41], which enhances B_s and reduces H_c in the Fe–P–C–Cu alloy. The increase in B_s may be attributed to the gradual reduction of free volume and the agglomeration of ferromagnetic atoms, which shortens the distance between these atoms and enhances their exchange coupling. Additionally, the decrease in H_c can be linked to the exchange coupling between the agglomeration of Cu atoms (forming a weak ferromagnetic region) and the segregation of Fe atoms (forming a strong ferromagnetic region), which diminishes

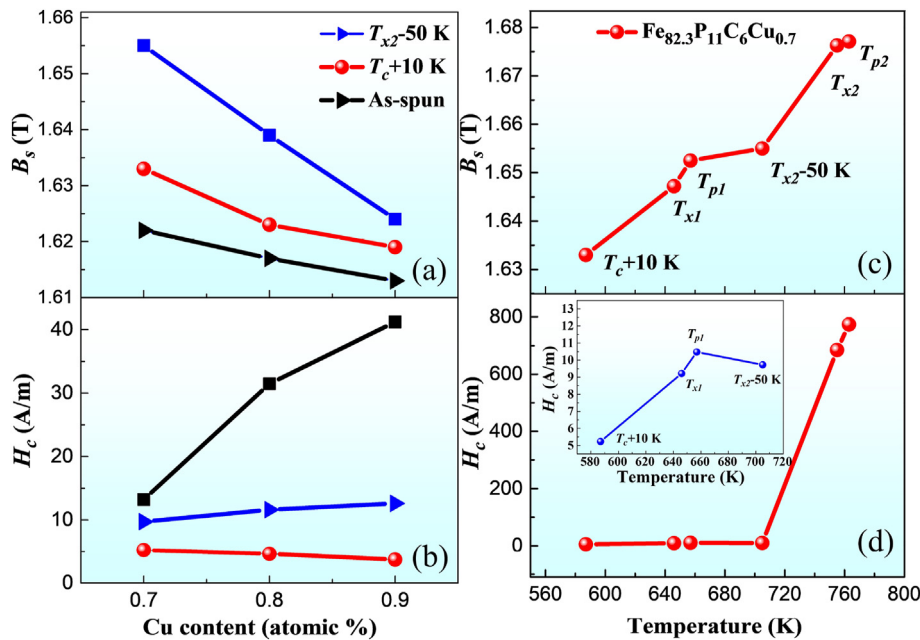


Fig. 7. (a–b) Changes in B_s and H_c with Cu contents of $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7, 0.8$ and 0.9 at. %) ribbons in as-spun, annealed $T_c + 10$ K and $T_{x2}=50$ K for 5 min (c–d) Changes in B_s and H_c with annealing temperatures of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ ribbon, the illustrations are enlarged image of H_c before 720 K.

magnetic anisotropy [42,43].

Notably, $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy show excellent soft magnetic properties with [amorphous + α -Fe] phase even after annealing at high temperature of $T_{x2}=50$ K. As B_s depends on the crystallization phase and the corresponding crystalline fraction [44], and the complete precipitation of the nanocrystalline α -Fe phase after annealing at $T_{x2}=50$ K enhances the B_s . Therefore, the magnetic properties of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy at different annealing temperatures below and above the temperature of $T_{x2}=50$ K were explored. Fig. 7(c and d) shows the B_s and H_c as functions of annealing temperature (T_{x1} , T_{p1} , $T_{x2}=50$ K, T_{x2} , T_{p2}). As the annealing temperature rises, both the crystalline fraction and the grain size of α -Fe increase, leading to improved exchange coupling between the nanocrystalline grains and an enhancement of the alloy's B_s . The inset of Fig. 7 (d) shows that H_c gradually increases from approximately 9.22 to 10.28 A/m with the annealing temperature increasing from T_{x1} to $T_{x2}=50$ K. This increase occurs because α -Fe nanocrystals form and grow over a short period, with the average grain size increasing from 16.5 nm to 26.5 nm as the temperature rises. Previous studies have indicated that H_c is proportional to D^6 , according to the random anisotropy model for nanocrystalline soft magnetic materials, the following equation links H_c to D [45]:

$$H_c = P_c \frac{\langle K \rangle}{J_s} = P_c \frac{v_{cr}^2 K_1^4 D^6}{J_s A_3} = \text{Constant} * K_1^4 D^6 \propto D^6 \quad (1)$$

Here, $\text{Constant} = P_c [v_{cr}^2 / J_s A_3]$ represents the magnetocrystalline anisotropy of the grains, where v_{cr} is the crystalline volume fraction, P_c is a dimensionless pre-factor equal to unity, J_s is the saturation magnetic polarization and K is the ferromagnetic exchange constant. In formula (1), the local magneto-crystalline anisotropy K_1 is closely related to the grain size D . When the grain size (D) is smaller than the exchange length (For Fe-based nano-crystalline alloys, the L_{ex} is 30–40 nm), the distribution of the magnetic anisotropy axis changes randomly at the atomic scale of amorphous and nanocrystalline metals, and the influence of local magnetocrystalline anisotropy is small and may be ignored. Thus, the value of H_c is proportional to D^6 [46]. In present work, the H_c observed also follows the theoretical relationship of $H_c \propto D^6$, indicating that the notable increase in H_c can be attributed to the growth of the α -Fe grains. The deterioration of magnetic properties is due to the rising grain size and magnetocrystalline anisotropy of the α -Fe nanocrystals, which lead

to the increase in H_c . Generally, H_c is influenced by the stress pinning effect associated with magnetic moment rotation, magnetic anisotropy, and surface microstructural inhomogeneity [47]. As illustrated in Fig. 7 (d), at annealing temperatures of T_{x2} and T_{p2} , the α -Fe nanocrystals grow further, and hard magnetic phases such as Fe_3C and Fe_3P are precipitated. These compounds act as pinning sites during the movement of magnetic domain walls, resulting in a significant increase in H_c to 800 A/m and a deterioration of soft magnetic properties.

In addition, according to Fig. 7 (a), the values of B_s decrease with the increasing Cu content, this may be owing to the replacement of Cu for magnetic atom Fe, which results in the weakening of ferromagnetic exchange. Furthermore, the H_c increases with the increasing Cu content at annealing temperature of $T_{x2}=50$ K, as illustrated in Fig. 7 (b), which coincides with the tendency of the grain size of α -Fe phase.

3.3. Mechanical property

Fig. 8 (a) illustrates the variation of H_v with Cu content for $\text{Fe}_{83-x}\text{P}_{11}\text{C}_6\text{Cu}_x$ ($x = 0.7, 0.8$, and 0.9 at. %) in as-spun state and annealing at $T_{x2}=50$ K for 5 min. The values of H_v are in the region of 758–774 for these as-spun amorphous alloys, and increase to 1077–1304 for $T_{x2}=50$ K samples composed of [amorphous + α -Fe] phase. The increase of H_v is because of the precipitation of the α -Fe nanocrystalline phase. Fig. 8 (b) shows the variation of structure and H_v with annealing temperature (T_{x1} , T_{p1} , $T_{x2}=50$ K, T_{x2} , T_{p2}) for $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy. At temperature below $T_{x2}=50$ K, the H_v increases from 1016 to 1304 because of the α -Fe nanocrystals precipitation. And then the H_v increases slowly to about 1377–1376 with the annealing temperature increasing to T_{x2} and T_{p2} , which is due to the decrease of residual amorphous phase, the enlargement of α -Fe grains and the precipitation of Fe_3C and Fe_3P phase.

The SEM image in Fig. 8 (c) shows several shear bands on the bent outer surface of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ as-spun alloy, with no noticeable cracks observed. Fig. 8 (d) shows the bending ductility test of $\text{Fe}_{82.3}\text{P}_{11}\text{C}_6\text{Cu}_{0.7}$ alloy in as-spun state and annealing at $T_{x2}=50$ K, respectively. As illustrated in the inset of Fig. 8 (d), the alloy ribbon can form a very small ring without breaking and can undergo 180° bending deformation without any crack, indicating the as-spun amorphous alloy exhibiting excellent bending ductility. Researches have indicated that when the precipitate only contains α -Fe phase nanocrystals, the softness of the alloy can be

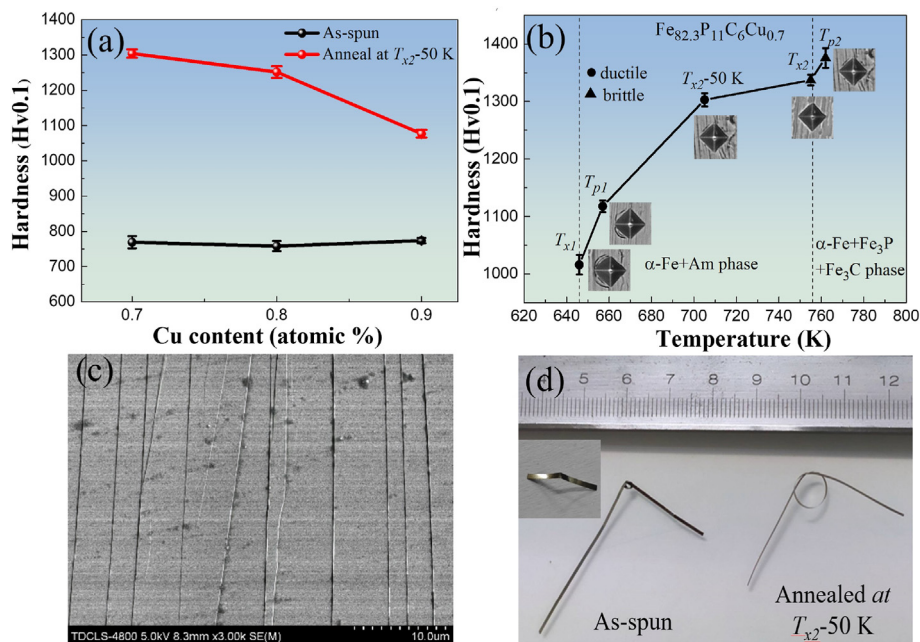


Fig. 8. (a) The relationship between Vickers hardness (H_v) and Cu content of Fe_{83-x}P₁₁C₆Cu_x ($x = 0.7, 0.8$ and 0.9 at. %) amorphous alloy in as-spun state and annealing at T_{x2} -50 K (b) Changes in H_v with annealing temperatures of Fe_{82.3}P₁₁C₆Cu_{0.7} ribbon (c) SEM images of the curved outer surface of Fe_{82.3}P₁₁C₆Cu_{0.7} as-spun ribbon (d) Bending ductility test of Fe_{82.3}P₁₁C₆Cu_{0.7} amorphous alloy after as-spun and T_{x2} -50 K annealing.

reduced [48]. Once the annealing temperature reaches T_{x2} -50 K, the nanocrystalline alloy exhibits brittle fracture, however, it can still bend to form a circle with a diameter of 6 mm without breaking, demonstrating that the ribbon with the [amorphous + α -Fe] phase structure retains good flexibility.

4. Conclusion

This paper investigates the effects of trace Cu substitution for Fe in Fe_{83-x}P₁₁C₆Cu_x ($x = 0.7$ – 1 at. %) amorphous alloys. The AFA of these amorphous alloys decreases with the increasing Cu content. The introducing of Cu promotes the nucleation of the α -Fe phase and facilitates the formation of nanocrystalline alloys. The results of crystallization kinetics show that, the nucleation process of Fe_{82.3}P₁₁C₆Cu_{0.7} amorphous alloy is harder than that of Fe_{82.1}P₁₁C₆Cu_{0.9} glassy ribbon. Compared with grain growth, the alloys are more difficult in the nucleation process. A higher heating rate is more conducive to the formation of new crystal nucleus and is beneficial for the formation of nanocrystalline structures. The amorphous alloys demonstrate excellent soft magnetic properties, including high saturation magnetization (B_s) of 1.61–1.63 T, low coercivity (H_c) of 3.7–5.23 A/m, and high initial permeability (μ_i) of 14,000–15,000 after structural relaxation. The [amorphous + α -Fe] alloys exhibit improved soft magnetic and mechanical properties. The Fe_{82.3}P₁₁C₆Cu_{0.7} alloy with B_s of 1.65 T, H_c of 9.7 A/m, μ_i of 16,000, Vickers hardness (H_v) of 1302, and notable flexibility is typical example. Given their exceptional soft magnetic properties, high hardness, good bending ductility, and flexibility, these low-cost Fe-P-C-Cu alloys are promising candidates for applications in different fields.

CRediT authorship contribution statement

Xiangxiang Jiang: Writing – review & editing, Writing – original draft, Investigation, Formal analysis, Data curation. **Cong Liu:** Writing – review & editing, Supervision, Methodology, Funding acquisition, Conceptualization. **Hongzhi Luo:** Supervision, Project administration, Methodology, Funding acquisition, Conceptualization. **Jing Ding:** Writing – review & editing, Validation, Funding acquisition, Formal analysis, Conceptualization. **Mingqing Zuo:** Formal analysis,

Conceptualization. **Chen Yang:** Writing – review & editing, Investigation. **Xuefang Dai:** Writing – review & editing, Conceptualization. **Shengli Zhu:** Writing – review & editing, Validation, Supervision, Conceptualization. **Guodong Liu:** Writing – review & editing, Methodology, Conceptualization.

Declaration of competing interest

All authors declare that: (i) they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper; and (ii) there are no other relationships or activities that could appear to have influenced the submitted work.

Acknowledgements

The authors are grateful for support from China Postdoctoral Science Foundation (No. 2023M730905), Science Research Project of Hebei Education Department (No. QN2024031), the Shandong Province Youth Fund (No. ZR2024QE439), the Hebei Natural Science Foundation (No. E2024202139).

References

- [1] T. Jiang, M. Zhao, Q. Xiang, Y. Ren, Q. Li, K. Qiu, Effect of 1 at.% Cu addition on the soft magnetic properties of FeSiBPC amorphous/nanocrystalline alloys, *AIP Adv.* 10 (2020) 105123, <https://doi.org/10.1063/5.0024815>.
- [2] Q. Liu, H. Liu, M. Wang, Y. Zhang, Z. Ma, Y. Zhao, W. Yang, Effects of Ni substitution for Fe on magnetic properties of Fe_{80-x}Ni_xP₁₃C₇ ($x = 0$ – 30) glassy ribbons, *J. Non-Cryst. Solids* 463 (2017) 68–71, <https://doi.org/10.1016/j.jnoncrysol.2017.03.005>.
- [3] W. Li, C.X. Xie, C.L. Yao, H.Y. Liu, K.W. Wang, Amorphous formation and magnetic properties of Co-containing Fe-Si-B-P-Cu nanocrystalline alloys, *J. Non-Cryst. Solids* 505 (2019) 87–91, <https://doi.org/10.1016/j.jnoncrysol.2018.10.044>.
- [4] T.B.Y. Naitoh, T. Hatanai, A. Makino, A. Inoue, T. Masumoto, Applications of nanocrystalline soft magnetic Fe-M-B ($M = \text{Zr, Nb}$) alloys, *Nanostruct. Mater.* 8 (1997) 987–995, [https://doi.org/10.1016/S0965-9773\(98\)00034-8](https://doi.org/10.1016/S0965-9773(98)00034-8).
- [5] T. Gheiratmand, H.R.M. Hosseini, Finemet nanocrystalline soft magnetic alloy: investigation of glass forming ability, crystallization mechanism, production techniques, magnetic softness and the effect of replacing the main constituents by other elements, *J. Magn. Magn. Mater.* 408 (2016) 177–192, <https://doi.org/10.1016/j.jmmm.2016.02.057>.

- [6] M.E. McHenry, F. Johnson, H. Okumura, T. Ohkubo, V.R.V. Ramanan, D.E. Laughlin, The kinetics of nanocrystallization and microstructural observations in FINEMET, NANOPERM and HITPERM nanocomposite magnetic materials, *Scr. Mater.* 48 (2003) 881–887, [https://doi.org/10.1016/s1359-6462\(02\)00597-3](https://doi.org/10.1016/s1359-6462(02)00597-3).
- [7] K.Y.Y. Yoshizawa, Magnetic properties of Fe-Cu-M-Si-B (M=Cr, V, Mo, Nb, Ta, W) alloys, *Mater. Sci. Eng. A* 133 (1991) 176–179, [https://doi.org/10.1016/0921-5093\(91\)90043-M](https://doi.org/10.1016/0921-5093(91)90043-M).
- [8] K. Suzuki, A. Makino, A. Inoue, T. Masumoto, Soft magnetic properties of nanocrystalline bcc Fe-Zr-B and Fe-M-B-Cu (M=transition metal) alloys with high saturation magnetization (invited), *J. Appl. Phys.* 70 (1991) 6232–6237, <https://doi.org/10.1063/1.350006>.
- [9] C. Liu, A. Inoue, F.L. Kong, E. Zanaeva, A. Bazlov, A. Churyumov, S.L. Zhu, F.A. Marzouki, R.D. Shull, Fe-B-Si-C-Cu amorphous and nanocrystalline alloys with ultrahigh hardness and enhanced soft magnetic properties, *J. Non-Cryst. Solids* 554 (2021) 120606, <https://doi.org/10.1016/j.jnoncrysol.2020.120606>.
- [10] H. Iwanabe, B. Lu, M.E. McHenry, D.E. Laughlin, Thermal stability of the nanocrystalline Fe-Co-Hf-B-Cu alloy, *J. Appl. Phys.* 85 (1999) 4424–4426, <https://doi.org/10.1063/1.369805>.
- [11] X. Fan, T. Zhang, W. Yang, J. Luan, Z. Jiao, H. Li, Design of FeSiBPCu soft magnetic alloys with good amorphous forming ability and ultra-wide crystallization window, *J. Mater. Sci. Technol.* 147 (2023) 124–131, <https://doi.org/10.1016/j.jmst.2022.11.019>.
- [12] L. Hou, M. Li, C. Jiang, X. Fan, Q. Luo, S. Chen, P. Song, W. Li, Thermal and magnetic properties of Fe(Co)BCCu amorphous alloys with high saturation magnetization of 1.77 T, *J. Alloys Compd.* 853 (2021) 157071, <https://doi.org/10.1016/j.jallcom.2020.157071>.
- [13] L. Hou, B. Wang, L. Liu, X. Mao, M. Zhang, C. Yuan, Z. Li, W. Ju, H. Feng, C. Tang, A. Xia, W. Li, Tailoring magnetic softness of Fe-based amorphous alloys with superior magnetization by magnetic field annealing, *J. Mater. Sci. Technol.* 200 (2024) 27–37, <https://doi.org/10.1016/j.jmst.2024.02.043>.
- [14] T.I.T. Sato, Crystallization of Fe₈₀P₁₃C₇ amorphous alloy powder, *J. Mater. Sci. Lett.* 9 (1990) 652–654, <https://doi.org/10.1007/BF00721793>.
- [15] A.M.a.A.I. Teruo Bitoh, Origin of low coercivity of Fe-(Al, Ga)-(P, C, B, Si, Ge) bulk glassy alloys, *Mater. Trans.* 44 (2003) 2020–2024, <https://doi.org/10.2320/matertrans.44.2020>.
- [16] L. Zhu, Y. Meng, X.B. Zhai, Y.G. Wang, S. Lan, Structure origin of abnormal magnetic behavior of Fe-P-C amorphous alloys, *J. Magn. Magn. Mater.* 472 (2019) 49–52, <https://doi.org/10.1016/j.jmmm.2018.10.001>.
- [17] J. Wang, R. Li, N. Hua, L. Huang, T. Zhang, Ternary Fe-P-C bulk metallic glass with good soft-magnetic and mechanical properties, *Scr. Mater.* 65 (2011) 536–539, <https://doi.org/10.1016/j.scriptamat.2011.06.020>.
- [18] J.E. Gao, H.X. Li, Z.B. Jiao, Y. Wu, Y.H. Chen, T. Yu, Z.P. Lu, Effects of nanocrystal formation on the soft magnetic properties of Fe-based bulk metallic glasses, *Appl. Phys. Lett.* 99 (2011) 052504, <https://doi.org/10.1063/1.3621832>.
- [19] J. Li, J. Zheng, C. Wang, A. He, Y. Dong, Synergistic effects of Si, B and P on microstructure and magnetic properties of Fe-Si-B-P-Nb-Cu alloys, *J. Magn. Magn. Mater.* 545 (2022) 168771, <https://doi.org/10.1016/j.jmmm.2021.168771>.
- [20] H.X. Li, J.E. Gao, Y. Wu, Z.B. Jiao, D. Ma, A.D. Stoica, X.L. Wang, Y. Ren, M.K. Miller, Z.P. Lu, Enhancing glass-forming ability via frustration of nano-clustering in alloys with a high solvent content, *Sci. Rep.* 3 (2013) 1983, <https://doi.org/10.1038/srep01983>.
- [21] X.D. Fan, B.L. Shen, Crystallization behavior and magnetic properties in High Fe content FeBCSiCu alloy system, *J. Magn. Magn. Mater.* 385 (2015) 277–281, <https://doi.org/10.1016/j.jmmm.2015.03.033>.
- [22] R. Xiang, S.X. Zhou, B.S. Dong, G.Q. Zhang, Z.Z. Li, Y.G. Wang, The excellent soft magnetic properties and corrosion behaviour of nanocrystalline FePCu alloys, *J. Mater. Sci. Mater. Electron.* 25 (2014) 2979–2984, <https://doi.org/10.1007/s10854-014-1970-7>.
- [23] Y. Jin, X. Fan, H. Men, X. Liu, B. Shen, FePCu nanocrystalline alloys with excellent soft magnetic properties, *Sci. China Technol. Sci.* 55 (2012) 3419–3424, <https://doi.org/10.1007/s11431-012-4928-0>.
- [24] Y.L. Li, Z.X. Dou, X.M. Chen, K. Lv, F.S. Li, X.D. Hui, Optimization of crystallization behavior and soft magnetic properties of the Si-free Fe-B-P-Cu nanocrystalline alloys by Cu content tuning, *Mater. Sci. Eng., B* 262 (2020) 114740, <https://doi.org/10.1016/j.mseb.2020.114740>.
- [25] J. Ding, C. Liu, G. Sun, J. Cui, S. Lv, Z. Li, J. Tian, S. Zhu, Development of high-performance Fe-rich Fe-P-C amorphous alloys with enhanced magnetization and low coercivity, *Prog. Nat. Sci-Mater.* 34 (2024) 9, <https://doi.org/10.1016/j.pnsc.2024.07.009>.
- [26] M.-X. Li, Y.-T. Sun, C. Wang, L.-W. Hu, S. Sohn, J. Schroers, W.-H. Wang, Y.-H. Liu, Data-driven discovery of a universal indicator for metallic glass forming ability, *Nat. Mater.* 21 (2021) 165–172, <https://doi.org/10.1038/s41563-021-01129-6>.
- [27] A.I. Akira Takeuchi, Classification of bulk metallic glasses by atomic size difference, heat of mixing and period of constituent elements and its application to characterization of the main alloying element, *Mater. Trans.* 46 (2005) 2817–2829, <https://doi.org/10.2320/matertrans.46.2817>.
- [28] D.H.P.K. Hono, M. Ohnuma, H. Onodera, Cu clustering and Si partitioning in the early crystallization stage of an Fe_{73.5}Si_{13.5}B₉Nb₃Cu₁ amorphous alloy, *Acta Mater.* 47 (1999) 997–1006, [https://doi.org/10.1016/s1359-6454\(98\)00392-9](https://doi.org/10.1016/s1359-6454(98)00392-9).
- [29] E. Perim, D. Lee, Y. Liu, C. Toher, P. Gong, Y. Li, W.N. Simmons, O. Levy, J.J. Vlassak, J. Schroers, S. Curtarolo, Spectral descriptors for bulk metallic glasses based on the thermodynamics of competing crystalline phases, *Nat. Commun.* 7 (2016) 12315, <https://doi.org/10.1038/ncomms12315>.
- [30] Q. Dong, P. Song, J. Tan, X.M. Qin, C.J. Li, P. Gao, Z.X. Feng, M. Calin, J. Eckert, Non-isothermal crystallization kinetics of a Fe-Cr-Mo-B-C amorphous powder, *J. Alloys Compd.* 823 (2020) 153783, <https://doi.org/10.1016/j.jallcom.2020.153783>.
- [31] H.E. Kissinger, Reaction kinetics in differential thermal analysis, *Anal. Chem.* 29 (1957) 1702–1706, <https://doi.org/10.1021/ac60131a045>.
- [32] Z.Q. Guo Lu, Zhe Chen, Kewei Zhang, Jiang Yong, Non-Isothermal crystallization kinetics of Fe₇₆Ga₅Ge₅B₆Cu₁P₇ alloy, *Acta Metall. Sin.* 58 (2022) 800–806, <https://doi.org/10.11900/0412.1961.2021.00287>.
- [33] J. Vázquez, C. Wagner, P. Villares, R. Jiménez-Garay, A theoretical method for determining the crystallized fraction and kinetic parameters by DSC, using non-isothermal techniques, *Acta Mater.* 44 (1996) 4807–4813, [https://doi.org/10.1016/S1359-6454\(96\)00127-9](https://doi.org/10.1016/S1359-6454(96)00127-9).
- [34] S.V. Vasiliev, K.A. Svyrydova, N.V. Vasylyeva, V.I. Tkatch, Description of non-isothermal crystallization kinetics of Fe₄₈Co₃₂P₁₄B₆ metallic glass using the isothermal analysis data, *Acta Mater.* 244 (2023) 118558, <https://doi.org/10.1016/j.actamat.2022.118558>.
- [35] T. Paul, A. Loganathan, A. Agarwal, S.P. Harimkar, Kinetics of isochronal crystallization in a Fe-based amorphous alloy, *J. Alloys Compd.* 753 (2018) 679–687, <https://doi.org/10.1016/j.jallcom.2018.04.133>.
- [36] A. Pratap, K.N. Lad, T.L.S. Rao, P. Majmudar, N.S. Saxena, Kinetics of crystallization of amorphous Cu₅₀Ti₅₀ alloy, *J. Non-Cryst. Solids* 345–346 (2004) 178–181, <https://doi.org/10.1016/j.jnoncrysol.2004.08.018>.
- [37] A.H. Cai, G. Zhou, D.W. Ding, H. Wu, Q. An, G.J. Zhou, Q. Yang, P.W. Li, Effect of Ti addition on crystallization behavior of a Zr-based bulk metallic glass, *Thermochim. Acta* 709 (2022) 179159, <https://doi.org/10.1016/j.tca.2022.179159>.
- [38] S. Cheng, C. Wang, M. Ma, D. Shan, B. Guo, Non-isothermal crystallization kinetics of Zr_{41.2}Ti_{13.8}Cu_{12.5}Ni₁₀Be_{22.5} amorphous alloy, *Thermochim. Acta* 587 (2014) 11–17, <https://doi.org/10.1016/j.tca.2014.04.009>.
- [39] A. Makino, H. Men, T. Kubota, K. Yubuta, A. Inoue, FeSiBPCu Nanocrystalline soft magnetic alloys with high B_s of 1.9 Tesla produced by crystallizing hetero-Amorphous phase, *Mater. Trans.* 50 (2009) 204–209, <https://doi.org/10.2320/matertrans.MER2008306>.
- [40] V.G.H.J.D. Ayers, J.A. Sprague, W.T. Elam, The local atomic order of Cu and Fe in heat treated Fe_{73.5}Nb₃Cu₁Si_{13.5}B₉ ribbons, *IEEE Trans. Magn.* 29 (1993) 2664–2666, <https://doi.org/10.1109/20.280832>.
- [41] F. Bai, Y. Dong, L. Xie, Q. Li, A. He, X. Jia, J. Li, X. Wang, Effect of pre-existing nuclei on microstructure and magnetic properties of high B_s FINEMET-like nanocrystalline alloys, *J. Mater. Sci.* 56 (2021) 9254–9262, <https://doi.org/10.1007/s10853-021-05861-x>.
- [42] L.L. Lu, Y. Lin, J. Dai, Q. Yan, Q.H. Xu, F.G. Chen, A. Jain, Y.G. Wang, Co-evolution of the atomic/nano scale structural heterogeneities and magnetic properties of Fe-Si-B-Cu metallic glass during relaxation with composition fluctuations, *J. Non-Cryst. Solids* 618 (2023) 122514, <https://doi.org/10.1016/j.jnoncrysol.2023.122514>.
- [43] Y. Lin, J. Dai, Z.Z. Yang, S.S. Jiang, Q.H. Xu, Y.G. Wang, F.G. Chen, A. Jain, Co-evolution mechanism of the atomic/nano scale structural heterogeneity of Fe-based metallic glasses during relaxation and the effect on magnetic properties, *J. Alloys Compd.* 936 (2023) 168268, <https://doi.org/10.1016/j.jallcom.2022.168268>.
- [44] Z. Zhang, P. Sharma, A. Makino, Role of Si in high B_s and low core-loss Fe_{85.2}B_{10.8}P₄Cu_{0.8}Si_x nano-crystalline alloys, *J. Appl. Phys.* 112 (2012) 103902, <https://doi.org/10.1063/1.4765718>.
- [45] P. Sharma, X. Zhang, Y. Zhang, A. Makino, Influence of microstructure on soft magnetic properties of low coreloss and high B_s Fe₈₅Si₂B₈P₄Cu₁ nanocrystalline alloy, *J. Appl. Phys.* 115 (2014) 17A340, <https://doi.org/10.1063/1.4868188>.
- [46] G. Herzer, Modern soft magnets: amorphous and nanocrystalline materials, *Acta Mater.* 61 (2013) 718–734, <https://doi.org/10.1016/j.actamat.2012.10.040>.
- [47] Z. Hussain, S.H. Babu, V.R. Reddy, Appearance of inverted hysteresis, pinning effect in amorphous FeCoB ribbon with annealing: a Kerr microscopy investigation, *J. Non-Cryst. Solids* 571 (2021) 121073, <https://doi.org/10.1016/j.jnoncrysol.2021.121073>.
- [48] H.K.a.A.I. Baolong Shen, Structure and magnetic properties of Fe_{42.5}Co_{42.5}Nb₇B₈ nanocrystalline alloy, *Mater. Trans.* 43 (2002) 589–592, <https://doi.org/10.2320/matertrans.43.589>.