ELSEVIER

Journal of Electron Spectroscopy and Related Phenomena 75 (1995) 253–272

JOURNAL OF ELECTRON SPECTROSCOPY and Related Phenomena

X-ray magnetic circular dichroism spectroscopy of transition metal thin films

J. Stöhr

IBM Research Division, Almaden Research Center, 650 Harry Road, San Jose, CA 95120, USA

Received 1 September 1995; accepted 5 October 1995

Abstract

A review is given of the principles underlying X-ray magnetic circular dichroism (XMCD) spectroscopy. The main strengths of the technique are highlighted. They are the quantitative determination of spin and orbital magnetic moments and their anisotropies through sum rule analysis of experimental spectra. A discussion is given why and how the spin and orbital magnetic moments in transition metal thin films are modified relative to the bulk. Selected XMCD results for thin films are discussed. "Non-magnetic" spacer layers sandwiched between magnetic layers are shown to become magnetic. The orbital moment is shown to become anisotropic in thin films, revealing that it is the microscopic origin of the magnetocrystalline anisotropy.

Keywords: Anisotropy; Magnetic moment; Spin; Scan rules; Thin film; Transition metal; X-ray magnetic circular dichroism

1. Introduction

Magnetism research has been undergoing a renaissance over the last decade following the discovery of a variety of new scientific phenomena associated with artificially made thin transition metal films. Among them are the theoretical prediction of enhanced magnetic moments in ultrathin films and at surfaces [1], the discovery of perpendicular magnetic anisotropy (PMA) in layered structures [2,3], and the discovery of giant magnetoresistance effects [4,5] and oscillatory exchange coupling [6] in multilayers made by alternating a magnetic and "nonmagnetic" metal. Some of these discoveries are about to have a major impact on the magnetic recording industry, a $50 billion per year world-wide business. An example is the so-called spin-valve sensor [7,8] which is about to be used as a magnetic read head. Other applications are multilayers with PMA which show promise as "blue" magneto-optical media [9], or GMR based structures which offer non-volatile (the information is stored in magnetic bits which survive power failures) alternatives to semiconductor based direct random access memories (DRAMs) [10].

Many of the materials of interest are in the form of artificially layered structures, each layer consisting of a different metal, a few atomic layers thick. It is therefore expected that the properties of these structures may be largely determined by their quasi-two-dimensional structure and the presence of interfaces. The bonding in these structures will be anisotropic, leading to different in-plane versus

0368-2048/95/$09.50 © 1995 Elsevier Science B.V. All rights reserved
SSDI 0368-2048(95)02537-5

out-of-plane properties. One would also envision that the crystal structures of the thin metal layers deviate from those in the bulk or that interfacial alloys are formed. This would change the magnetic moments and their preferred direction; magnetic layers may become magnetically dead and non-magnetic layers may acquire a magnetic moment. Through hybridization, electronic (spin-polarized) interface states may be formed which, if located at the Fermi level, would significantly affect the (magneto) transport across the interface. It is clear that because of the complexity of the materials and the small concentration of some components, state-of-the-art characterization techniques are needed to address scientific and technological issues.

X-ray magnetic circular dichroism (XMCD) spectroscopy, first suggested by Erskine and Stern [11] and pioneered by Schütz et al. [12], is one of those techniques. It has several capabilities not afforded by traditional magnetics techniques [13]. Its foremost strengths are the element-specific, quantitative determination of spin and orbital magnetic moments and their anisotropies. Other strengths are its chemical sensitivity [14], its lateral resolution of at least 1 μm^2 [15], and its sub-monolayer sensitivity [16,17]. It is the purpose of this paper to elucidate the basic concepts of XMCD and emphasize some unique contributions it has already provided to our understanding of thin film magnetism.

2. Magnetism in 3d transition metals

The magnetic properties of the 3d transition metals are mainly determined by d electrons. As shown by Table 1 for the ferromagnets Fe, Co and Ni, the combined 4s and 4p contribution to the magnetic spin moment is less than 5% and the orbital magnetic moment is entirely due to the d electrons [18,19].

Table 2 lists the important interactions and energies which determine the electronic and magnetic structure and properties of the 3d metals. At present, it is difficult, if not impossible, to treat all interactions listed in Table 2 from first principles. One major challenge is the treatment of multi-electron correlation effects on the same footing as band structure effects. Correlation effects give rise to multiplet splitting in experimental X-ray absorption and XMCD spectra [20,21], and for transition metal compounds their inclusion is essential [22,23]. For the transition metals their importance remains a topic of debate [24–26]. We shall use a one-electron formalism throughout this paper, because it is closely related to conventional electronic structure calculations. Furthermore, use of a one-electron picture facilitates the recognition of the basic physical concepts underlying XMCD spectroscopy. In fact, at times we shall even use a simple chemical bonding picture instead of a solid state band picture. Of particular importance in the present context are the magnetic exchange interaction and the spin–orbit interaction which are the origin of the spin and orbital magnetic moments, respectively. As shown in Table 1 the total magnetic moment, which is simply the sum of the spin and orbital parts, is largely (about 90%) determined by the spin moment. Despite its small absolute value, however, the orbital moment plays a crucial role in magnetism; it can be viewed as the microscopic origin of the magnetocrystalline anisotropy. We shall return to this important phenomenon below. Let us take a close look at the origin and importance of the spin and orbital magnetic moments.

2.1. The spin magnetic moment

The origin of the spin magnetic moment in transition metals is most easily understood in the rigid band picture of itinerant ferromagnetism, the so-called Stoner model. In this model the d-band is split by the exchange interaction into spin-up and spin-down bands. If the magnetic domains of the sample are aligned by an external magnetic field in the "up" direction, defined as the $+z$ of a cartesian coordinate system, the center of gravity of the spin-down band is lower in energy than that of the spin-up band by the exchange splitting Δ_{ex}. Hence the spin down is more occupied (majority spin) than with spin-up (minority spin) band. As depicted in Fig. 1 the magnetization $\boldsymbol{M}$ in this picture is in the spin-up direction, parallel to the external magnetic field, because for electrons spin $\boldsymbol{S}$ and magnetic moment $\boldsymbol{m}_s$ are anti-parallel according to the

Table 1
Magnetic moments in 3d transition metals[a]

	M_{tot}	M^{d}_{spin}	M^{sp}_{spin}	M_{orb}
Fe	2.28	2.26	−0.07	0.09
Co	1.71	1.64	−0.07	0.14
Ni	0.69	0.64	−0.02	0.07

[a] Theoretical moments in μ_B: Söderlind et al. [19].

relationship $\boldsymbol{m}_s = -2\mu_B \boldsymbol{S}$, where μ_B is the Bohr magneton. In relating spin and magnetic moment directions it is convenient to think of the spin moment as arising from the holes in the minority band because $\boldsymbol{m}_s$ and $\boldsymbol{S}$ are parallel for holes. For this reason and because X-ray absorption probes the empty valence states, we shall mostly use a hole picture, below. Denoting the number of d holes as N, the spin moment according to Fig. 1 is given by $m_s = (N_\uparrow - N_\downarrow)\mu_B$, and it is positive. In the simple Stoner model the magnetic moment is solely due to the electron spin without any orbital contribution.

In order to describe the electronic structure of transition metals it is convenient to use a Slater–Koster tight binding description of the band structure [27,28]. The symmetry of the electronic structure can then be discussed in terms of the five d orbitals d_{xy}, d_{xz}, d_{yz}, $d_{x^2-y^2}$, and $d_{3z^2-r^2}$, and after summing the band states over the Brillouin zone (BZ) one may define d-orbital or symmetry projected quantities, such as the d-orbital projected density of states or magnetic spin moments. The crystal symmetry for bulk 3d transition metals is always high (f.c.c., b.c.c. or h.c.p.) and hence the bonding and charge distribution is rather isotropic. The contributions of the five d orbitals to the density-of-states (DOS) and the magnetic spin moment are therefore nearly identical. For ultra thin films or surfaces, however, the intrinsic structural anisotropy will result in different contributions from in-plane and out-of-plane orbitals as shown in Fig. 2. For the case of a free standing monolayer the in-plane orbitals have larger overlap (σ-bonding) and their splitting (band width) is larger. The decreased overlap (π-bonding) of the out-of-plane orbitals leads to a band narrowing and a decreased spin-down hole population as shown schematically in Fig. 1. Hence the difference between spin-up and spin-down population is increased for the out-of-plane orbitals, resulting in an enhanced magnetic spin moment, relative to that of the in-plane orbitals. This is exactly what is observed in an electronic structure calculation for a single Co layer, as summarized in Fig. 2. Also, the total d-band spin moment is enhanced relative to the bulk metal, and Daalderop et al. [29] obtain $1.87\,\mu_B$ for a Co monolayer relative to $1.57\,\mu_B$ for bulk Co. Similar results have been obtained for many other surfaces and thin films [1].

Table 2
Interactions and energies in 3d transition metals

Interaction	Characteristic splitting	Characteristic energy per atom/eV	Magnetic effect
d Orbital overlap with neighbors	Band width	5	
Coulomb and exchange interaction of d orbitals on same site	Multiplet splitting	0–2	
Magnetic exchange interaction	Exchange splitting	1	Spin moment
d Orbital interaction in point charges of neighbors	Crystal field splitting	0.1	
Spin–orbit interaction	Spin–orbit splitting	0.05	Orbital moment, magnetocrystalline anisotropy
Magnetic dipole–dipole interaction		10^{-5}	Shape anisotropy

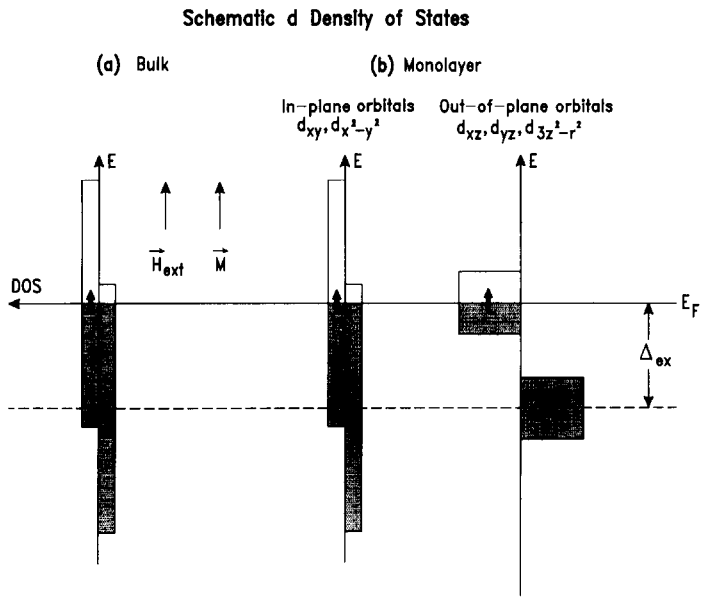

Fig. 1. Origin of the magnetic spin moment in the rigid band picture of ferromagnetism (Stoner model). (a) d band splitting in a bulk transition metal under the influence of the exchange interaction, assuming that the magnetization direction has been aligned by an external field $\vec{H}$ in the "up" direction, corresponding to the $+z$ axis of a cartesian coordinate system. States are filled up to the Fermi level, labeled E_F. For $\vec{H} \| +z$ the spin-down states are lower in energy and hence are more filled (majority states) than the spin-up states (minority states). The center of gravity of spin-up and spin-down bands are separated by the exchange splitting Δ_{ex}. (b) For a monolayer one may distinguish sub-bands comprised of in-plane and out-of-plane d orbitals. Because the in-plane orbitals have larger overlap (σ-bonding) their splitting and hence band width is larger. The decreased overlap (π-bonding) of the out-of-plane orbitals leads to a band narrowing and an decreased number of spin-down holes. The difference between spin-up and spin-down holes, i.e. the magnetic moment, is increased. This is the origin for enhanced spin moments at surfaces and for thin films.

The spin moment is defined in terms of the expectation value of the operator $S_{\tilde{z}}$, where the $\tilde{z}$ axis lies along the magnetization direction and may differ from the crystallographic z axis. It is given by

$$m_s = -\frac{2\mu_B}{\hbar}\langle S_{\tilde{z}}\rangle \tag{1}$$

As indicated in the above equation we shall use units of $\hbar$ for the expectation values of momentum operators (or momenta) and μ_B for the magnetic moments (or moments). Note that moments and momenta have opposite signs. $\langle S_{\tilde{z}}\rangle$ is calculated by summing the matrix elements $\langle\phi_n(\boldsymbol{k})|S_{\tilde{z}}|\phi_n(\boldsymbol{k})\rangle$ over all occupied electronic states $\phi_n(\boldsymbol{k})$. In the absence of spin-orbit (s–o) coupling the spin cannot couple to the lattice and the spin moment is isotropic, i.e. the wavefunctions $\phi_n(\boldsymbol{k})$ are independent of the magnetization direction. Because of the small size of the s–o coupling in 3d transition metals (see Table 2), the spin moment remains isotropic to a very good approximation (up to second order or within about 1%) even in the presence of s–o coupling [30].

2.2. The orbital magnetic moment

An orbital moment exists if there is a net orbital current from the d electron motion around the nucleus. This requires time reversal symmetry to be broken such that the motion of the orbiting electron, on average, is larger in one than the opposite direction. In magnetic materials the symmetry breaking is caused by the s–o coupling. The d-electron orbits may be anisotropic by bonding alone (e.g. the orbits may be confined to the x–y plane) but without s–o coupling they will possess time reversal symmetry (e.g. an in-plane current giving rise to an orbital moment along $+z$ will be cancelled by the opposite current, giving rise to a moment in the $-z$ direction). The size of the orbital

Charge and Spin Anisotropies for Co Monolayer

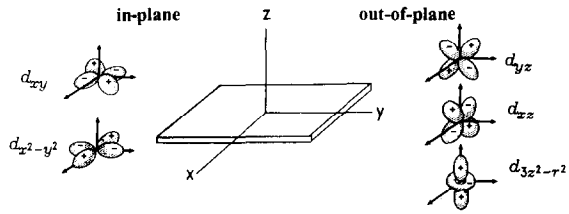

Co monolayer theory: *Daalderop et al., Phys. Rev. B50, 9989 (1994)*

Orbitals	Charge:* $N=N_\uparrow+N_\downarrow$	Spin:(μ_B)* $N_\downarrow$	$N_\uparrow$	$m_s=N_\uparrow-N_\downarrow$
in-plane: d_{xy}, $d_{x^2-y^2}$	**0.48**	0.10	0.38	**0.28**
out-of-plane: d_{xz}, d_{yz}, d_{z^2}	**0.52**	0.04	0.48	**0.44**
Σ (all orbitals)	2.52	0.32	2.20	1.87

* per orbital

Fig. 2. Charge and spin anisotropy for a Co monolayer, caused by different in-plane and out-of-plane d orbital contributions. The table lists d orbital projected quantities, the spin-dependent number of holes, the total number of holes N and the spin moment m_s, calculated by Daalderop et al. [29] for a free standing (111) Co monolayer.

moment in different directions therefore depends on both the d-electron bonding (i.e. the crystal symmetry) and the size of the s–o coupling. The angle dependent orbital moment m_o^α of the d shell along the principal cartesian axes $\alpha = x$, y, or z is given by

$$m_o^\alpha = -\frac{\mu_B}{\hbar}\langle L_\alpha \rangle \tag{2}$$

The orbital momentum $\langle L_\alpha \rangle$ is calculated by summing the matrix elements $\langle \phi_n(\boldsymbol{k}) | L_\alpha | \phi_n(\boldsymbol{k}) \rangle$ over all occupied electronic states $\phi_n(\boldsymbol{k})$. We note that conventional electronic structure calculations underestimate the size of the orbital moment unless an orbital polarization term is included [31]. For a more (less) than half filled d shell m_s and m_o have the same (opposite) sign, i.e. are parallel (antiparallel) according to Hund's rule.

The origin of the orbital magnetic moment and its anisotropy is illustrated in Fig. 3 following a perturbation picture by Bruno [32,33]. In 3d transition metals the d shell is split by band structure and crystal field effects into d-orbitals with a large energy separation (about 1 eV at high symmetry points in the BZ). Let us for simplicity assume that the magnetic exchange splitting is large and all spin-down states are full so that we only need to consider the partially filled spin-up shell [34]. The pure d orbitals shown (e.g. at high symmetry points in the BZ) possess no orbital moment (which is said to be "quenched") because the d orbitals have a perfect balance of $\pm m_l$ states (or have $m_l = 0$) as shown in Fig. 3. The effect of the smaller s–o interaction ($\xi \vec{l} \cdot \vec{s}, \xi \approx 0.05\,\text{eV}$), which can be treated by perturbation theory, is a mixing of the pure or zero-order d orbitals, creating new first-order states $|1\rangle$–$|5\rangle$ which have anisotropic orbital momenta as shown. The orbital momentum of a state $|n\rangle$ is given by the first order perturbation expression

$$\langle L_\alpha^n \rangle = -\frac{\xi}{\hbar}\sum_m \frac{|\langle d_n^\uparrow | L_\alpha | d_m^\downarrow \rangle|^2}{\Delta_{mn}} \tag{3}$$

where the sum is over all other zero-order spin-up states $d_m^\downarrow$ and $\Delta_{mn} = E_m - E_n$ is the energy separation of two states. Hence the size of the orbital momenta is of order $\xi\hbar/\Delta_{mn} \approx 0.1\hbar$, or about 5–10% of the size of the spin moment, in good accord with Table 1. The total orbital momentum is given by the sum over all filled states $|n\rangle$. If all states are filled the orbital momentum vanishes as seen from Fig. 3. The preferred directions of the orbital momenta of the lowest two states are also indicated. The anisotropy is reduced but will persist even when the states are summed over the BZ.

The anisotropy of the orbital moment is closely related to the magnetocrystalline anisotropy, i.e. the difference in the s–o energy ΔE_{so}, when the magnetization direction is changed from the easy axis to the hard axis. As pointed out by Bruno [33], a particularly simple correlation exists between the orbital moment and magnetocrystalline anisotropies if the exchange splitting is larger than the band width. Let us consider this case for a thin film with uni-axial anisotropy (no in-plane anisotropy) and define $m_o^\perp = m_o^z$ and $m_o^\parallel = m_o^x = m_o^y$ for the components perpendicular and parallel to the surface, respectively. We then obtain [33]

$$\Delta E_{so} = E_{so}^\perp - E_{so}^\parallel = -\frac{\xi}{4\mu_B}(m_o^\perp - m_o^\parallel) \tag{4}$$

Here we have used a sign convention such that

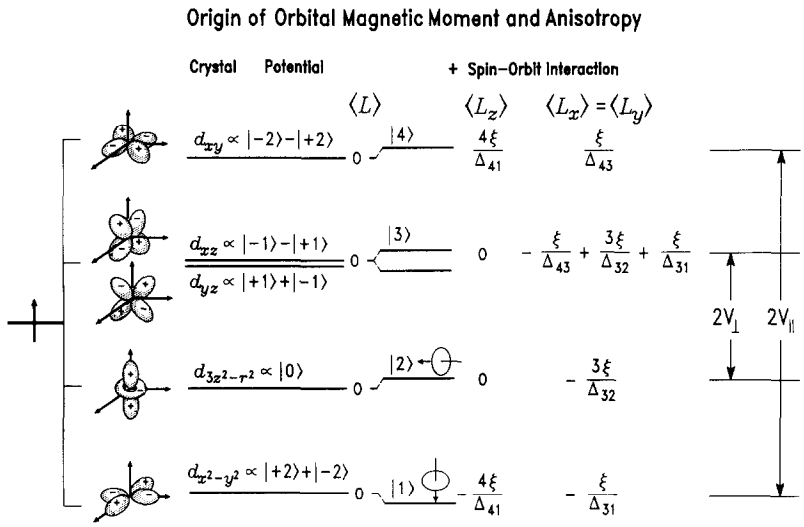

Fig. 3. Origin of the orbital magnetic moment and its anisotropy. For simplicity we assume that the magnetic exchange splitting is large and we consider only states of one spin [34]. Band structure and crystal field effects result in d orbitals which are linear combinations of functions $|m_l\rangle$ $(-2 \leq m_l \leq +2)$. We show an energy scheme where the in-plane splitting $(2V_{\parallel})$ is larger than the out-of-plane splitting $(2V_{\perp})$, as for a free monolayer. The pure d orbitals shown (i.e. at high symmetry points in the BZ) possess no orbital moment. The inclusion of the spin–orbit interaction in lowest order perturbation theory results in new states $|1\rangle$–$|5\rangle$ which have anisotropic orbital momenta (units $\hbar$) as shown, where $\xi \leq 0.1$ eV is the spin–orbit coupling constant and $\Delta_{ij} \approx 1$ eV is the energy separation (taken positive) of a higher energy state i and a lower state j.

ΔE_{so} is negative if the easy axis is perpendicular to the surface [35] and the orbital moment is larger in the easy magnetization direction than the hard one.

3. XMCD: basic concepts and sum rules

The properties of 3d-electrons are best probed in an X-ray absorption experiment by excitation of 2p core electrons to unfilled 3d states as shown in a simple one-electron picture in Fig. 4 [36,37]. X-rays allow elemental specificity because of the different 2p binding energies. There are six sum rules which link polarization dependent p → d X-ray absorption intensities to ground state properties of the d shell. Three sum rules link angle and polarization dependent X-ray absorption intensities to anisotropic d-shell properties: the charge density, the spin density and the angle-dependent orbital moment. Three others allow the determination of angle-integrated d-shell properties: the number of d holes, the magnetic spin moment, and the orbital magnetic moment. We shall discuss these sum rules after reviewing the principles of the XMCD effect.

3.1. Basic concepts — the two-step model

As discussed by Stöhr and Wu [36] the origin of the XMCD effect can be explained by a simple two-step model which may be visualized by means of Fig. 4. Here we have arbitrarily assumed that the magnetization is in the down direction, defined as the $-z$ axis of a cartesian coordinate system. If the wavevector $\vec{k}$ of the X-rays is aligned along the $+z$ axis, the photon spin is "up" with a value $+\hbar$ ("down" with a value $-\hbar$) for right (left) circularly polarized X-rays [38]. In the first step, right or left circularly polarized photons transfer their angular momentum, $\hbar$ and $-\hbar$, respectively, to the excited photoelectron. The electron carries the angular momentum either by the spin or the orbital degree of freedom. Because the spin does not interact directly with the electric field, in the absence of s–o coupling, one can only transfer the photon angular momentum to the orbital part. This is the case for the excitation from an atomic s core-state or if one sums over both s–o components (L_3 plus L_2) of a p core-state. If the core-state is split by the s–o interaction [37], the substates are no longer

X-Ray Magnetic Circular Dichroism Spectroscopy

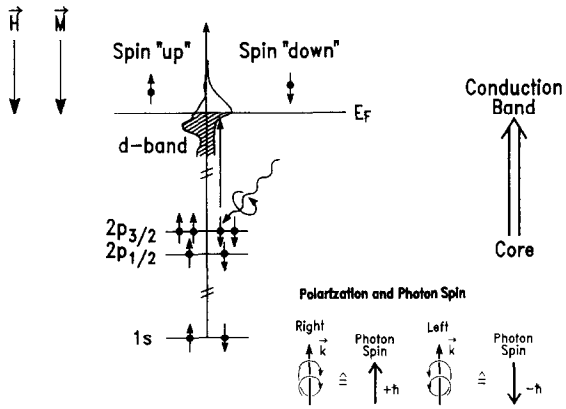

Fig. 4. Electronic transitions in X-ray magnetic circular dichroism, illustrated in a one-electron model [37]. The transitions occur from a core shell (typically L shell) to empty conduction band states above the Fermi level, labeled E_F. The band occupation is shown here for an external magnetic field in the "down" direction, i.e. $\vec{H} \| -z$. Also shown is the correlation of the helicity and wavevector $\vec{k}$ for right and left circular polarization and the photon spin directions. If the light is incident in the $+z$ direction, the photon spin for right circularly polarized light is "up" and has the value $+\hbar$ [38]. The dichroism intensity is defined as the difference between a spectrum obtained with anti-parallel relative orientation of photon spin and external field direction and a spectrum with parallel relative orientation [36].

pure spin states. As a result, the photon angular momentum is transferred to both the orbital and spin degrees of freedom of the excited photoelectron. In fact, a relatively large portion can be transferred to the spin resulting in spin polarized photoelectrons. For the $p_{3/2}$ initial state (L_3 edge), for example, $\vec{l}$ and $\vec{s}$ are parallel, and therefore transfer of the angular momentum $+\hbar$ by right circularly polarized light excites more (62.5%) spin-up than (37.5%) spin-down electrons. The reverse holds for left circularly polarized light. For the $p_{1/2}$ initial state (L_2 edge) $\vec{l}$ and $\vec{s}$ are anti-parallel and right circularly polarized light preferentially couples to spin-down electrons (75% spin-down and 25% spin-up electrons). Again, left circularly polarized light does the opposite. Note, that in the first step "spin-up" and "spin-down" are defined relative to the photon spin direction, and the discussed effects are therefore independent of the magnetic properties of the sample.

The magnetic properties enter in the second step. Here the valence shell acts as a "detector" for the spin and/or orbital momentum of the excited photoelectron. The quantization axis of the detector is given by the magnetization direction which, for maximum dichroism effect, needs to be aligned with the photon spin direction. If the metal is ferromagnetic, an imbalance in empty spin-up and spin-down states will exist and hence the valence shell can act as a "spin detector". Similarly, the valence shell will act as an "orbital momentum detector" if there is an imbalance of states with different magnetic quantum numbers m_l, i.e. in case of s–o splitting in the valence shell. Therefore, for K-shell excitation or for summed L_3 and L_2 spectra, a dichroism effect exists only if the valence shell exhibits an orbital moment. By separating the L_3 and L_2 components one becomes sensitive to the spin. Sum rules, to be discussed below, allow one to quantitatively separate the spin and orbital magnetic contributions of the valence shell in the electronic ground state.

In the above discussion we have assumed that the magnetization direction is fixed so that the XMCD intensity is the difference intensity, obtained for two X-ray helicites. It is easy to show that it is equivalent to fix the X-ray helicity and switch the magnetization direction [36].

3.2. The role of X-ray polarization

The polarized nature of X-rays allows one to probe the electronic and magnetic anisotropy of matter. This is of particular importance for thin films and surfaces which are intrinsically anisotropic. The basic principle underlying this phenomenon is the so called "search light effect" [39]. Because X-ray absorption is governed by electric dipole transitions the photoelectrons are preferentially excited into the direction of the electric field vector $\vec{E}$. This is illustrated in Fig. 5 for $s \rightarrow p$ and $p \rightarrow d$ transitions with linear and plane-polarized light. For $s \rightarrow p$ transitions the electrons are excited from a spherically symmetric s core to bow-shaped empty p valence orbitals. The transition intensity is zero if $\vec{E}$ lies in the nodal plane and is largest if $\vec{E}$ points along the p orbital direction. Thus the $\vec{E}$ vector can be

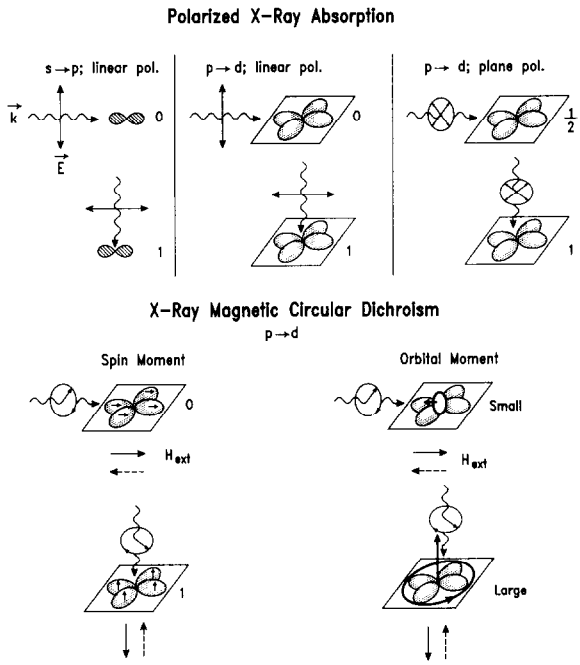

Fig. 5. Polarization dependence of X-ray absorption and dichroism intensities for core-to-valence transitions assuming an oriented p or d valence orbital. The X-ray absorption intensities are best understood by visualizing the electric field vector $\vec{E}$ as a search light. The intensity is zero if $\vec{E}$ points into a nodal direction of the orbital. This comes about because the photoelectron is emitted in the direction of $\vec{E}$ and no empty valence states are available along the nodal direction to "receive" the excited electron. The relative dichroism intensities are those for the spin and orbital sum rules. For spin-only magnetism the dichroism effect is zero if the photon spin (wavevector) and the nodal direction are orthogonal. The orbital sum rule intensity follows the size of the orbital moment in different directions. It agrees with the intuitive picture (see Fig. 3) that an in-plane orbital has a predominantly in-plane electron or hole current and therefore larger out-of-plane orbital moment.

pictured as a "search light" revealing whether there are empty valence states in a given direction. The situation for $p \rightarrow d$ transitions is similar, except that there is a nodal direction for d orbitals instead of a nodal plane (the $d_{3z^2-r^2}$ orbital is an exception and its angular dependence is more complicated, see below). For plane-polarized X-rays the intensities follow from the case of linear polarization, remembering that plane-polarized light can be treated as an incoherent superposition of two orthogonal linear-polarized waves. As discussed below polarized X-ray absorption in non-magnetic samples or magnetically random samples, in general, probes the charge density.

The p → d XMCD case is also illustrated in Fig. 5, for an in-plane d orbital which either carries a spin or an orbital moment. The listed intensities correspond to the spin or orbital sum rules, respectively, to be discussed below. In all cases we have assumed that the photon wave vector $\boldsymbol{k}$ lies along the magnetization direction (i.e. the $\vec{E}$ vector is perpendicular to the magnetization direction), thus optimizing the XMCD effect. The spin dichroism effect is seen to be maximized if the nodal axis and wave vector $\boldsymbol{k}$ are parallel and zero if the nodal axis and $\boldsymbol{k}$ are perpendicular. Note that this differs from the case of p → d absorption of plane-polarized X-rays where the absorption intensity does not vanish if the nodal axis and $\boldsymbol{k}$ are orthogonal. In general, the angle-dependent XMCD intensity is related to the spin density, as discussed in more detail below.

XMCD directly measures the component of the orbital moment along the photon spin direction. An in-plane orbital will typically have a larger out-of-plane than in-plane orbital moment according to the intuitive picture that an in-plane orbital will have a predominantly in-plane electron or hole current. Because the X-ray helicity couples directly to the orbital electron motion one simply measures its component along the photon spin.

3.3. Total-intensity or "white-line" sum rules

The first two sum rules link X-ray absorption "white line" (WL) intensities I_{L_3} and I_{L_2} to the occupation of the d shell. The WL intensity is the resonant intensity at the L_3 and L_2 thresholds as indicated in Fig. 6 and shown more clearly in Fig. 7 for Fe, Co, Ni and Cu. In principle, L-edge X-ray absorption spectra contain contributions from both p → d and p → s transitions, but in practice the p → d channel dominates by a factor of more than 20 [40]. In particular, for a magnetically random sample, the polarization dependent WL intensity is related to the number of d holes in different crystallographic directions, i.e. the (hole) charge density, and the polarization averaged intensity is related to the integrated number of d holes N, i.e. the d shell (hole) occupation number.

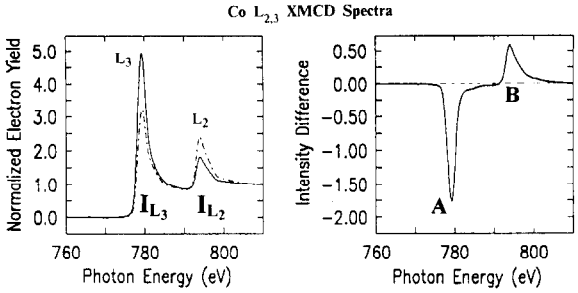

Fig. 6. Normalized X-ray magnetic circular dichroism spectra at the Co L_3 (778 eV) and L_2 (793 eV) edges for Co metal. The original spectra have white line intensities I_{L_3} and I_{L_2} which depend on the relative orientation of photon spin and magnetization direction, shown solid for parallel and dashed for antiparallel alignment. The difference spectrum gives dichroism intensities $A < 0$ and $B > 0$ at the L_3 and L_2 edges, respectively, which are used for sum rule analysis.

Of course, the number of electrons is simply $10 - N$. Note that, despite the creation of a core hole in X-ray absorption, the intensities are related to the occupation in the electronic ground state according to the important initial state rule [41].

The polarization dependent WL intensity for a magnetically random sample with higher than D_{2h} crystal symmetry (z axis along three-fold or higher axis) is given by [30]

$$I^{\alpha}_{\mathrm{wl}} = [I_{L_3} + I_{L_2}]_{\alpha} = \frac{C}{3}\sum_i N^i\left(1 + \frac{7}{B}Q^i_{\alpha}\right) \qquad (5)$$

where $\alpha = x, y$ or z, and C is proportional to the square of the radial p → d transition matrix element. Here N^i is the number of holes per orbital d_i, summed over the Brillouin zone (BZ), so that $N = \Sigma_i N^i$. It can be shown that $B = -4$ for linearly polarized light (electric field vector $\vec{E}\|\alpha$), and $B = 8$ for circularly or plane polarized light (X-ray wave vector $\vec{k}\|\alpha$, $\vec{E} \perp \vec{k}$).

The polarization dependent correction term $(7C/3B)\Sigma_i N^i Q^i_{\alpha}$ to the isotropic intensity $CN/3$ arises from the anisotropy of the d charge-density within the atomic sphere. As shown in Fig. 3 each d orbital is anisotropic and when the band states are summed over the BZ not all d orbitals contribute equally. The resulting charge distribution in the Wigner–Seitz cell then contains an isotropic monopole and anisotropic quadrupole contribution. The two terms in Eq. (5) correspond to these two

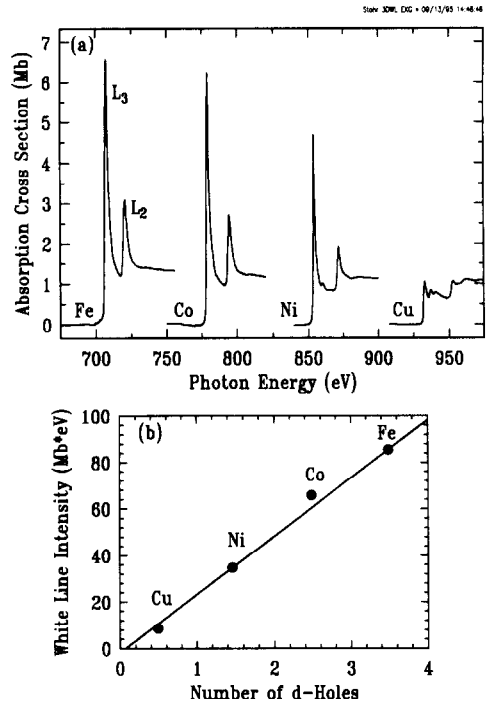

Fig. 7. (a) X-ray absorption spectra recorded by total electron yield detection near the L_3 and L_2 edges for Fe, Co, Ni, and Cu metal, showing the existence of white lines for Fe, Co, and Ni and its near-absence for Cu, due to its nearly filled d shell. Note that we have plotted absolute cross sections which were obtained by fitting the electron yield data to known cross sections [66] below and above the L edges. (b) White line intensity, determined by the method of Chen et al. [44], versus calculated d orbital occupation [18,19].

contributions. This differs from the situation for s → p transitions where the dipolar nature of the p valence shell is directly probed [39].

The factors Q^i_{α} in Eq. (5) are matrix elements $\langle \mathrm{d}_i | Q_{\alpha\alpha} | \mathrm{d}_i \rangle$ of the quadrupole tensor $Q_{\alpha\beta} = \delta_{\alpha\beta} - 3r_{\alpha}r_{\beta}/r^2$, and have the symmetry properties $Q_{\alpha\beta} = Q_{\beta\alpha}$ and $\Sigma_{\alpha} Q_{\alpha\alpha=0}$. They are given in the first column of Fig. 8 together with the polarization factors $1 + 7Q^i_{\alpha}/B$ in Eq. (5). It is apparent that for each orbital Q^i_{α} is very anisotropic. The term Q^i_{α} vanishes when averaged over all directions and over all orbitals d_i. Also, for cubic symmetry the orbitals group into degenerate $\mathrm{e_g}(\mathrm{d}_{x^2-y^2}$ and $\mathrm{d}_{3z^2-r^2})$ and $\mathrm{t_{2g}}(\mathrm{d}_{xy}, \mathrm{d}_{yz}, \mathrm{d}_{xz})$ sets and Q^i_{α} vanishes for each set. The correction term is expected to be large in ultra thin films where the charge density is

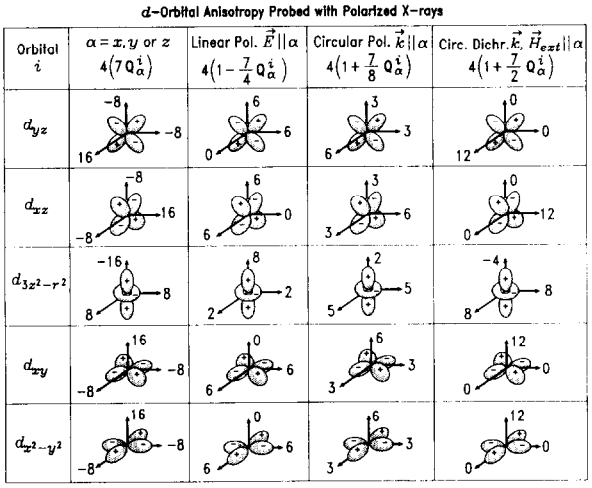

Fig. 8. Calculated matrix elements $Q_\alpha^i = \langle d_i|Q_{\alpha\alpha}|d_i\rangle$, ($\alpha = x, y, z$) and polarization factors in Eqs. (5) and (9) for the d orbitals. Factors are given for X-ray absorption experiments with linearly (electric field vector $\vec{E}\|x, y, z$) and circularly polarized X-rays (X-ray wave vector $\vec{k}\|x, y, z$) and for X-ray circular dichroism studies in an external magnetic field H_{ext} ($\vec{k}, \vec{H}_{\text{ext}}\|x, y, z$). Note $\vec{E} \perp \vec{k}$.

not spherically symmetric. We shall discuss the case of a Co monolayer in Section 4, below.

The property $Q_{xx} + Q_{yy} + Q_{zz} = 0$ results in the important sum rule for the total intensity

$$\sum_\alpha [I_{L_3} + I_{L_2}]_\alpha = CN \tag{6}$$

Eq. (6) also holds for a single measurement of polycrystalline samples or, for samples with higher than twofold symmetry about z, it applies when $\vec{E}(\vec{k})$ for linear (circular) polarized light is at the "magic angle" 54.7° from the z axis.

Application of the sum rule expressed by Eq. (6) to the 3d transition metals shows that there is indeed a linear correlation between the WL intensity of the 3d transition metals with the calculated number of holes in the 3d shell [18,19]. This is shown in Fig. 7 for Fe, Co, Ni and Cu.

3.4. Spin sum rules

Carra et al. [42] have derived a related sum rule for the XMCD intensity

$$I_{\text{spin}}^\alpha = [A - 2B]_\alpha = \frac{C}{3\hbar}(2\langle S_\alpha\rangle + 7\langle T_\alpha\rangle) \tag{7}$$

Here $A = \Delta I_{L_3}$ and $B = \Delta I_{L_2}$ are the L_3 and L_2 dichroism intensities shown in Fig. 6, measured in a geometry $\vec{k}, \vec{H}_{\text{ext}}\|\alpha$, where $\alpha = x, y$ or z denotes the cartesian frame. If we denote the orientations of photon spin and magnetization directions by arrows, the sign convention used in Eq. (7) for the measured intensity is (compare Fig. 4) [36]

$$\Delta I = I^{\uparrow\downarrow} - I^{\uparrow\uparrow} \tag{8}$$

It is also assumed that the external magnetic field $\vec{H}_{\text{ext}}$ is large enough to magnetically saturate the sample. $\langle S_\alpha\rangle$ and $\langle T_\alpha\rangle$ are the expectation values of the spin operator and the intra-atomic magnetic dipole operator $\vec{T} = \vec{S} - 3\hat{r}(\hat{r}\cdot\vec{S})$ for the spin quantization axis aligned along α. In general we can write $T_\alpha = \Sigma_\beta Q_{\alpha\beta} S_\beta$, indicating the coupled charge (Q) and spin (S) components of T. As pointed out by Stöhr and König [30] in 3d transition metals, to a good approximation, the effect of s–o coupling on $\langle T_\alpha\rangle$ can be neglected. Expressing the nearly isotropic spin in terms of d-orbital projected spin moments m_s^i according to $m_s = -(2\mu_B/\hbar)\langle S\rangle = \Sigma_i m_s^i$ we can write $\langle T_\alpha\rangle$ simply as a product of the quadrupolar matrix elements Q_α^i and isotropic spin moments m_s^i according to $\langle T_\alpha\rangle = -(\hbar/2\mu_B)\Sigma_i Q_\alpha^i m_s^i$, reflecting the decoupled nature of charge and spin. The anisotropy of $\langle T_\alpha\rangle$ is therefore closely linked to that of the charge given by the quadrupole terms Q_α^i, and $\langle T_\alpha\rangle$ simply reflects a quadrupole term in the anisotropic spin density within the Wigner–Seitz cell. Polarized X-rays therefore offer the capability of probing the angular distribution of the spins in the Wigner–Seitz cell, whereas conventional magnetometry only probes the integrated number of spins, i.e. the, essentially isotropic, spin moment per atom. For higher than D_{2h} symmetry, we obtain in close analogy to Eq. (5) [30]

$$[A - 2B]_\alpha = -\frac{C}{3\mu_B}\sum_i m_s^i\left(1 + \frac{7}{2}Q_\alpha^i\right)$$
$$= -\frac{C}{3\mu_B}m_{\text{eff}}^\alpha = -\frac{C}{3\mu_B}(m_s + m_D^\alpha) \tag{9}$$

Here we have also linked the sum rule intensity to an effective moment m_{eff}^α which can be viewed as the sum of the isotropic spin moment m_s and the angle dependent intra-atomic dipole moment

$m_D^\alpha = (7/2)\Sigma_i Q_\alpha^i m_s^i$. Similarly to Eq. (6), there is a new sum rule which follows from the property $\Sigma_\alpha m_D^\alpha \propto \Sigma_i m_s^i \Sigma_\alpha Q_\alpha^i = 0$. It allows direct determination of m_s by averaging measurements along the x, y and z axes

$$\sum_\alpha [A - 2B]_\alpha = -\frac{C}{\mu_B} m_s \tag{10}$$

provided the sample is magnetically saturated. Note that Eq. (10) also holds for polycrystalline samples or for a "magic angle" measurement.

3.5. Orbital sum rule

In the presence of an external magnetic field H_{ext} which is sufficiently large to magnetically saturate the sample, the orbital moment m_o^α along the field direction α can be directly determined by use of the sum rule [43]

$$I_{orb}^\alpha = [A + B]_\alpha = -\frac{C}{2\mu_B} m_o^\alpha \tag{11}$$

For thin film samples the case on uniaxial anisotropy (no in-plane anisotropy) is often encountered. For an experimental geometry where $\vec{k}$ and $\vec{H}_{ext}$ are at an angle α with respect to the surface normal we obtain $m_o^\alpha = m_o^\perp \cos^2\alpha + m_o^\parallel \sin^2\alpha$, such that measurements at two angles are needed to determine $m_o^\perp - m_o^\parallel$ and hence $\Delta E_{so} \propto m_o^\perp - m_o^\parallel$. The angle-averaged moment $(m_o^\perp + 2m_o^\parallel)/3$ may be determined in a single magic angle measurement.

4. Anisotropy of charge, spin and orbital moment for Co monolayer

The various angle and polarization dependent sum rules, in principle, allow the determination of anisotropies in the electronic and magnetic densities. The question arises how large these anisotropies are for the 3d transition metals, especially in thin films and at surfaces. After all, the bonding is metallic in nature and so one would expect significantly smaller effects than for covalent systems. For the latter systems large polarization dependent effects are well known to exist and they form the basis of NEXAFS spectroscopy [39]. In the following we shall therefore explore the size of the expected effects for thin transition metal films. Furthermore, our discussion above showed that in all cases anisotropic effects have a common origin in that they arise from unequal contributions of the d orbitals when the $\boldsymbol{k}$-dependent states are summed over the BZ. We therefore expect to find a close relationship between their absolute values and symmetries. This is indeed the case for a Co monolayer and in the following we shall discuss the expected X-ray absorption anisotropies for this case, assuming axial symmetry about the surface normal.

4.1. Charge anisotropy

For a thin film, electronic and magnetic anisotropies may then be discussed in terms of different contributions from in-plane and out-of-plane d orbitals. Defining the in-plane occupation per orbital as $N^\parallel = N^{xy} = N^{x^2-y^2}$ and the out-of-plane occupation per orbital as $N^\perp = N^{xz} = N^{yz} = N^{3z^2-r^2}$, the X-ray absorption intensity for linearly polarized X-rays given by Eq. (5) is proportional to the effective number of holes, according to

$$\vec{E}\|x: \qquad N_{eff}^x = \sum_i N^i\left(1 - \frac{7}{4}Q_x^i\right) = 2N^\perp + 3N^\parallel$$

$$\vec{E}\|z: \qquad N_{eff}^z = \sum_i N^i\left(1 - \frac{7}{4}Q_z^i\right) = 5N^\perp \tag{12}$$

Using the numbers for $N^\parallel = 0.48$ and $N^\perp = 0.52$ from Fig. 2 we obtain $N_{eff}^x = 2.48$ and $N_{eff}^z = 2.60$. Thus the anisotropy in the white line intensity would only be about 5% for linearly polarized X-rays and even smaller for plane polarized X-rays.

4.2. Dipolar anisotropy

Similarly, defining in-plane and out-of-plane spin moments per orbital $m_s^\parallel = m_s^{xy} = m_s^{x^2-y^2}$ and $m_s^\perp = m_s^{xz} = m_s^{yz} = m_s^{3z^2-r^2}$ one would obtain the following effective spin moments, defined by Eq.

(9), in an angle dependent XMCD measurement

$$\vec{k}\|x: \qquad m_{\mathrm{eff}}^{x} = m_{\mathrm{s}} + m_{\mathrm{D}}^{x} = \sum_i m_{\mathrm{s}}^{i}\left(1 + \frac{7}{2}Q_x^i\right) = 5m_{\mathrm{s}}^{\perp}$$

$$\vec{k}\|z: \qquad m_{\mathrm{eff}}^{z} = m_{\mathrm{s}} + m_{\mathrm{D}}^{z} = \sum_i m_{\mathrm{s}}^{i}\left(1 + \frac{7}{2}Q_z^i\right) = 6m_{\mathrm{s}}^{\|} - m_{\mathrm{s}}^{\perp} \tag{13}$$

With the values given in Fig. 2, $m_{\mathrm{s}}^{\|} = 0.28\mu_{\mathrm{B}}$ and $m_{\mathrm{s}}^{\perp} = 0.44\mu_{\mathrm{B}}$, we obtain $m_{\mathrm{eff}}^{x} = 2.20\mu_{\mathrm{B}}$ and $m_{\mathrm{eff}}^{z} = 1.24\mu_{\mathrm{B}}$, which differ by nearly a factor of two. The dipolar moment is therefore larger in-plane ($m_{\mathrm{D}}^{x} = 0.32\mu_{\mathrm{B}}$) than out-of-plane ($m_{\mathrm{D}}^{z} = -0.64\mu_{\mathrm{B}}$). Thus the effect of the anisotropic dipole moment on the XMCD intensity is predicted to be large in thin films and it should be readily measurable.

4.3. Orbital anisotropy

Bruno [32] has estimated the orbital moment anisotropy for (100) and (111) f.c.c. monolayers of Fe and Co and found a larger in-plane than out-of-plane orbital moment, with a difference of $m_{\mathrm{o}}^{\|} - m_{\mathrm{o}}^{\perp} \approx 0.20\mu_{\mathrm{B}}$. From these estimates we expect that the anisotropy of the orbital moment and its preferred direction should be easily measurable by XMCD.

Let us explore the origin of the orbital moment anisotropy in a simple model. As shown in Fig. 1, for a monolayer the in-plane band width will be larger than the out-of-plane bandwidth. Therefore the level structure shown in Fig. 3 may be taken as representative of this case. Also, for Co the minority spin band is approximately half filled ($N = 2.5$, see Fig. 2) and the majority band is full. Then only the lowest two states in Fig. 3 are filled and contribute to the orbital moment. If we define in-plane and out-of-plane splittings $2V_{\|}$ and $2V_{\perp}$, respectively, as shown in Fig. 3, and define $x = V_{\perp}/V_{\|}$ we obtain

$$m_{\mathrm{o}}^{\|} = \frac{\xi\mu_{\mathrm{B}}}{2V_{\|}}\left(\frac{3}{x} + \frac{2}{x+1}\right) \tag{14}$$

and

$$m_{\mathrm{o}}^{\perp} = \frac{\xi\mu_{\mathrm{B}}}{2V_{\|}}4 \tag{15}$$

For the case of a free standing monolayer we have $V_{\|} > V_{\perp}$ (or $x < 1$) and therefore $m_{\mathrm{o}}^{\|} > m_{\mathrm{o}}^{\perp}$ according to Eqs. (14) and (15). The easy axis is predicted to lie in plane which agrees with Bruno's results and those of a first principle calculation [29].

It is interesting to note the correlation between the anisotropy of the orbital moment and the dipolar moment for a Co monolayer. In both cases the in-plane components are larger than the out-of-plane components. This result is, in fact, an example of a more general correlation as will be discussed in Section 6.2, below.

5. Experimental details and data analysis

Quantitative XMCD studies are not easy because intensities have to be accurately determined. Therefore extreme care has to be exercized in the measurements to avoid artifacts such as saturation effects in the strong WL resonances [17]. Also, the presence of large magnetic fields typically causes problems with electron yield measurements which are mostly employed in soft X-ray absorption studies [39]. Owing to space constraints only a few important points will be made here.

Because of the problems associated with making samples of interest in the form of free-standing films, transmission measurements are not generally applicable. However, if possible, such measurements are probably the most reliable as recently demonstrated by Chen et al. [44] for Fe and Co metal. These measurements which proved the reliability of the spin and orbital sum rules should serve as a standard for future measurements. There are two other possible detection schemes, fluorescence and electron yield detection. Fluorescence yield detection should not be used for the 3d transition metals because it does not quantitatively follow the true absorption dichroism signal as recently demonstrated by Duda et al. [45]. The reason is that the L fluorescence yield for the 3d metals contains a dichroic component itself, because the

valence to core decay is governed by the dipole selection rule and hence preserves the spin. Because the total absorption cross section is simply the sum of the fluorescence and Auger channels, the Auger electron yield therefore does not exactly follow the absorption cross section, either. In practice, however, the fluorescence yield is less than 1% of the total decay and even if it was "wrong" by a factor of two the Auger yield would still be correct within 1%. Therefore, for all practical purposes, Auger yield and all other electron yields [39] are good measures of the true absorption cross section.

Fig. 9 shows how to best measure the electron yield in the presence of magnetic fields. Our experimental arrangement shown in the figure is aimed at the measurement of "real" samples, made ex situ. In order to protect the samples from degradation they always contain a capping layer, typically 15–20 Å of Au or Pt. The ultra high vacuum of the electron storage ring and the beam line is decoupled from the vacuum of the sample chamber (typically 10^{-6} Torr) by either a thin diamond window (about 0.4 μm thick), as shown, or a differential pumping section. Because of problems associated with carbon deposition on the diamond window, a differential pumping section is preferable. The incident photon flux is monitored by a Au grid reference monitor, which like the sample, is placed inside a cylindrical cage, as shown. Both cages are kept at a positive bias voltage (greater than 10 V) and serve to extract the photoelectrons from the reference grid and the sample. The direct photocurrents from the grid and the sample serve as the signals used for the XMCD spectra. Typical photocurrents for our measurements were about 1×10^{-10} A. The shown arrangement minimizes asymmetries in the measured signals in the presence of large magnetic fields. The sample is centered in the 5 cm gap of an electromagnet which could be ramped to more than 90% of full field within 1 s. XMCD measurements were recorded in a 10 kOe external magnetic field parallel to the X-ray propagation direction, at variable angles α with respect to the surface normal. X-ray absorption

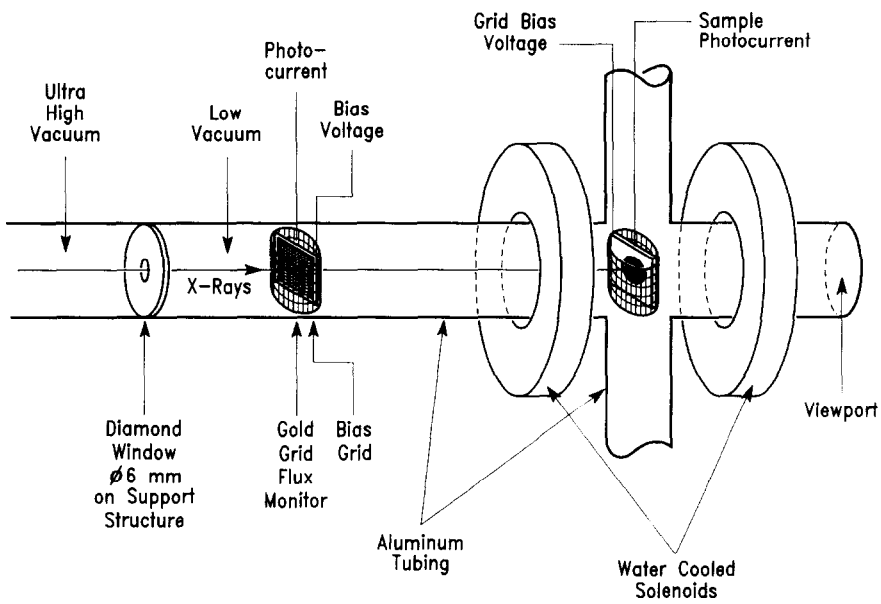

Fig. 9. Experimental arrangement for high-field XMCD measurements. A 0.4 μm thick diamond window, capable of withstanding an atmospheric pressure differential, decouples the ultra vacuum of the monochromator from the high vacuum ($\approx 10^{-6}$ Torr) of the sample chamber made out of aluminum. The intensity of the circularly polarized X-ray beam is first monitored by a gold grid reference monitor ($\approx$ 80% transmission), surrounded by a cylindrical tungsten cage (92% transmission). A similar cage also surrounds the sample which is located in the 5 cm gap of a split-coil electromagnet. The X-rays enter the sample chamber through one of the pole shoes of the magnet, parallel to the magnetic field. The cages are kept at a positive bias voltage (greater than +10 V) and the photocurrents from the Au grid and the sample are directly measured with a current amplifier.

was measured using right circularly polarized X-rays and switching the magnetization direction parallel and then antiparallel to the photon spin at each photon energy step.

The XMCD measurements, reported below, were performed at room temperature at the Stanford Synchrotron Radiation Laboratory (SSRL) on beam line 8–2. Circularly polarized light was obtained by moving a vertically deflecting mirror below the electron orbit plane of the storage ring. By comparing the measured intensity profile as a function of mirror position to a calculated profile we estimate the degree of circular polarization to be $90 \pm 5\%$. Measurements on samples made in the form of wedges were performed as a function of wedge thickness by translating the sample along the wedge direction. The X-ray beam spot size was about 1 mm horizontally and 0.75 mm along the vertical translation direction, assuring adequate spatial resolution.

Data analysis proceeded by dividing the signal from the sample by that from the reference monitor. Such flux normalized XMCD spectra for 200 Å films of Fe, Co, and Ni capped with 20 Å of Pt, obtained with the experimental arrangement in Fig. 9, are shown in Fig. 10. It is seen that there is a small constant offset (about 0.5%) when the magnetic field is switched. This offset, however, is readily eliminated in the difference spectra, the XMCD spectra, as shown in Figs. 10 (b)–(d). The shown XMCD difference spectra give ratios m_o/m_s in excellent agreement with those published by Chen et al. [44] employing transmission measurements, but disagree with those determined by O'Brien and Tonner [46] and Hunter Dunn et al. [17] using electron yield detection.

For the determination of absolute moments we proceeded as follows. We first used the spectra for Fe, Co, and Ni shown in Fig. 10 to determine the constant C in the sum rules. The sum rule dichroism intensity was determined by first subtracting a linear pre-edge background from the two spectra obtained for opposite fields. Both spectra were scaled to the same edge jump (arbitrarily chosen as unity) in the region far above the edges. This ensures that the measured dichroism signal for a given element is normalized to the same number of atoms in the sample [39]. The XMCD intensities were obtained by subtraction and C was determined for each element by using the known bulk magnetic moments listed in Table 1. We assumed C to be element (i.e. atomic number Z) dependent but transferable for a given element. This procedure accounts for the Z- and energy dependence of the radial p → d transition matrix, i.e. of the "resonant" (or WL) and "non-resonant" (or edge jump) cross sections. For Cu we used an extrapolated value $C(Z)$ from the data for bulk Fe, Co and Ni.

6. Applications

6.1. Determination of element specific moments

The discovery [6] of an oscillatory exchange coupling between successive 3d transition metal ferromagnetic layers, separated by a non-ferromagnetic metal layer, has stimulated much work regarding its origin. To explain this coupling, the Ruderman–Kittel–Kasuya–Yosida (RKKY) interaction was adapted to a planar geometry [47,48] or a quantum-well model [49–51] was used. The precise nature of the coupling remains controversial, however [52], and the relationship between the magnetic polarization in the spacer layer and the exchange coupling is imperfectly understood. Here we discuss XMCD measurement which demonstrate that the coupling of the magnetic layers proceeds via spin polarization of the "non-magnetic" Cu spacer layer. While earlier XMCD studies on Co/Pt multilayers [53] had already revealed that a "non-magnetic" metal such as Pt can become magnetic, the Co/Pt system does not exhibit oscillatory exchange coupling. Also Pt is a transition metal whose electronic and magnetic properties are determined by its partially filled d shell. In contrast, the d shell is essentially filled in Cu, making the origin of any induced magnetism an interesting question.

The Co/Cu multilayer samples, grown by dc magnetron sputtering, were members of a family of structures, Si(100)/Ru(50 Å)/20 × {Co(10 Å)/Cu(x Å)}/Ru(15 Å) with $x = 4$ Å, 5.5 Å, and 13 Å. At these Cu layer thicknesses, the coupling between the Co layers is ferromagnetic. We shall refer to these samples as Co(10)/Cu(x). Fig. 11 shows XMCD spectra for various Co/Cu multilayers,

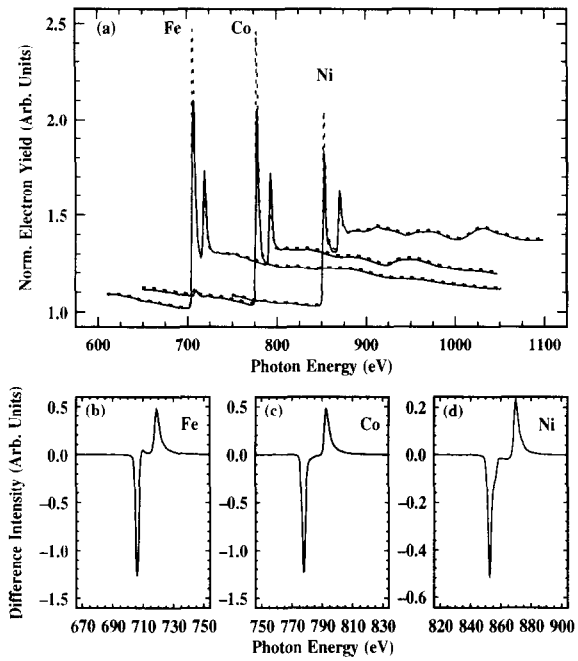

Fig. 10. (a) Dichroism spectra for Fe, Co and Ni measured in a 10 kOe external magnetic field at an X-ray incidence angle of 30° with the experimental arrangement shown in Fig. 9. The samples consisted of 200 Å thick films grown by electron beam evaporation as structures Si(100)/200 Å Cu/200 Å X/15 Å Pt, where X is Fe, Co or Ni. Dashed curves correspond to parallel and solid curves to antiparallel alignment of photon spin and magnetization direction, respectively. (b)–(d) Difference spectra of the spectra in (a), corrected for a constant offset so that the intensity before and above the L edges is zero.

both at the Co and Cu L edges. The Cu $L_{2,3}$ spectra and difference spectra shown in Fig. 11(c) and (d) clearly exhibit a dichroism effect, unambiguously demonstrating a magnetic polarization of Cu.

Because the dichroism effect has the same sign at the Co and Cu $L_{2,3}$ edges, the observed Cu moments are parallel to those of Co. The Co moment is found to be nearly identical to that of bulk Co, independent of Cu thickness. Qualitatively the Cu dichroism effect is seen to weaken with increasing Cu thickness. The Cu polarization is thus found to be concentrated near the Co interface. The spin moment in the Cu d shell has a value of $0.054\mu_B$ for Co(10)/Cu(4) and $0.013\mu_B$ for Co(10)/Cu(13). Furthermore, within error, there is no orbital moment as clearly indicated by the equal L_3 and L_2 dichroism intensities in Fig. 11. The Cu moment and its dependence on Cu thickness is found to be in excellent agreement with self-consistent local spin density functional (LSDA) calculations [54].

The enhanced Cu d moment near the interface is the result of a considerable hybridization of the Cu and Co d orbitals near the interface. The Cu $L_{3,2}$ spectra in Fig. 11(c) clearly show an increase in the WL intensity with decreasing Cu thickness, indicating an increased number of d holes for Cu atoms near the interface. This picture is proven by recent X-ray emission studies of the element specific density of states in Co/Cu multilayers [55]. The studies clearly reveal an increase of the Cu d density of states near the Fermi level arising from hybridization of Cu sp states with Co d states.

Our results strongly suggest that the long-range spin polarization in Cu is predominantly of d character and consequently that the magnetic exchange coupling of the Co layers is largely mediated by the Cu d electrons. The importance of Cu d electrons in the exchange coupling has also been suggested by spin-polarized photoemission measurements for Cu on Co(100) [56].

6.2. Anisotropy of magnetic moments

The microscopic origin of magnetic anisotropy in transition metals has been debated for more than 60 years, dating back to early work by Stoner and Van Vleck [57]. Recently, the interest in this problem has become revived in conjunction with artificially made transition metal films and multilayers which exhibit perpendicular magnetic anisotropy (PMA) [2,3]. It is clear that PMA is due to an intrinsic anisotropy mechanism strong enough to overcome the extrinsic macroscopic shape anisotropy, which favours an in-plane orientation of the magnetization. In the past, experimental studies have mainly concentrated on characterizing the magnetic anisotropy through the measurement of the various phenomenological anisotropy energy constants [33,58] which can be compared with those obtained from electronic structure calculations. For the bulk metals the anisotropy energies are extremely small (10^{-5}–10^{-6} eV atom^{-1}) and the reliable prediction of MCA is still a challenge for the most advanced theoretical methods

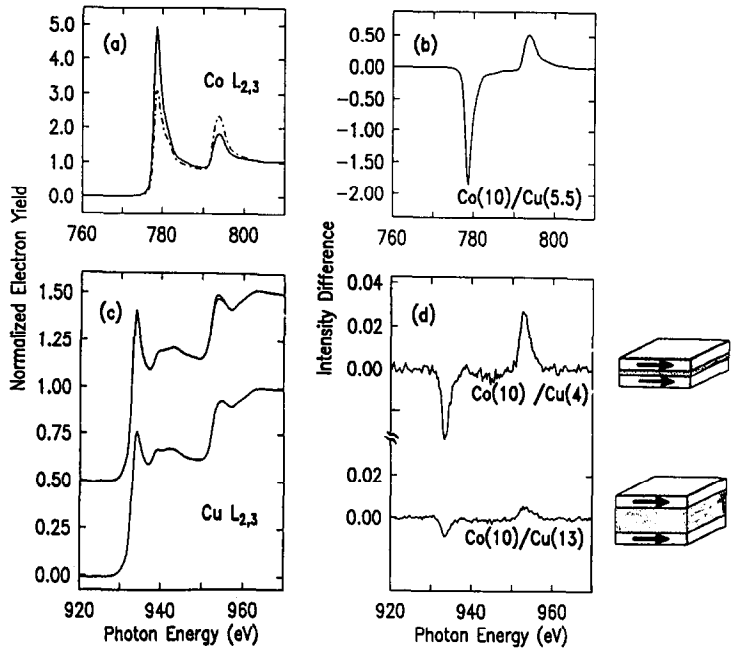

Fig. 11. (a) Co $L_{2,3}$ X-ray absorption spectra for Co(10 Å)/Cu(5.5 Å) recorded with parallel (solid line) and antiparallel (dashed line) alignment of photon spin and sample magnetization directions and (b) the difference spectrum. (c) Cu $L_{2,3}$ spectra and (d) difference spectra for multilayers of the structure Co(10 Å)/Cu(4 Å) and Co(10 Å)/Cu(13 Å). All spectra were measured at 20° grazing X-ray incidence on magnetically saturated samples. The spectra in (a) and (c) were scaled so that the jump far above the edge is unity. Spectra in (c) and (d), respectively, are plotted on the same vertical scale but are offset for clarity.

today. Even if successful, physical insight is often lost because of the complexity of the calculations. For layered materials symmetry breaking at the interfaces coupled with interfacial strain is considered to be the origin of considerably larger anisotropy energies in the 10^{-3}–10^{-4} eV atom^{-1} range. Here we shall address the origin of the magnetocrystalline anisotropy in such structures.

We shall present results for high-field angle dependent XMCD measurements on Au/Co/Au sandwiches [59] which unambiguously show that the perpendicular orientation of the magnetization direction for Co thicknesses $t_{Co} \leq 11$ atomic layers (AL) is a consequence of a large anisotropy of the Co orbital magnetic moment. We also present a simple model which predicts the favoured direction of the orbital moment. This is a crucial step towards the goal of engineering materials with PMA. We also observe an anisotropy in the dipolar moment, as expected from our earlier discussions.

The Au/Co-staircase/Au sample, shown schematically in Fig. 12, consisted of ten Co terraces of 2 mm width and thicknesses between 3 and 12 Al of Co sandwiched between a 28 nm thick (111) Au buffer, grown onto a floatglass substrate, and an approximately 9 AL thick Au capping layer. The Co staircase sample was characterized prior to and after the XMCD measurements by angle dependent polar Kerr hysteresis measurements in fields up to 20 kOe [60]. The sample exhibited a transition from in-plane anisotropy at large Co thickness to out-of-plane behavior at $t_{Co} \leq 11$ Al.

Fig. 12 shows the results from a sum rule analysis of XMCD data obtained for two sample orientations as a function of Co thickness. In the absence of in-plane anisotropies we can write $m_D^{\perp} + 2m_D^{\parallel} = 0$ and separately determined the intra-atomic dipole moment m_D^{α} and the spin moment m_s, by use of Eq. (9). The actual in-plane components of the moments m_D and m_o (see below) were derived from the experimental data taken at angles $\alpha = 65°$ and $\alpha = 0°$ by assuming uniaxial anisotropy such that $m^{\alpha} = m^{\perp}\cos^2\alpha + m^{\parallel}\sin^2\alpha$.

We find that, at room temperature, the spin

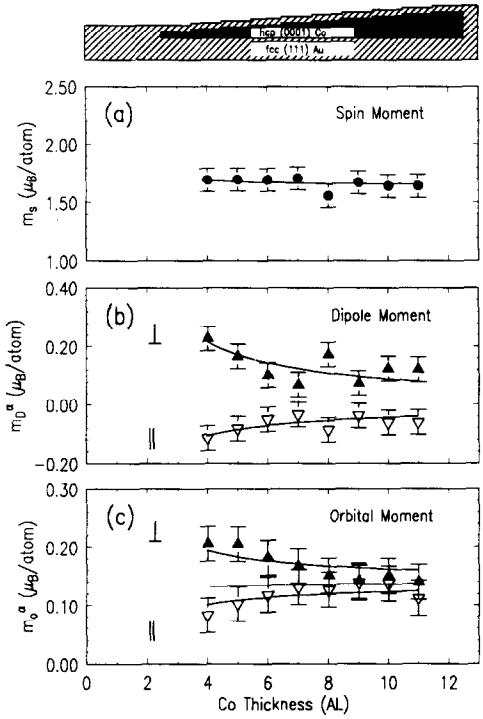

Fig. 12. Schematic picture of the Au/Co/Au wedge sample used in the measurements. (a) Spin moment m_s, (b) dipole moments $m_D^\perp$ and $m_D^\parallel$, and (c) orbital moments $m_o^\perp$ and $m_o^\parallel$ as a function of Co thickness. $m_D^\parallel$ and $m_o^\parallel$ are the in-plane projected moments calculated from the measured quantities at $\alpha = 65°$ and $\alpha = 0°$, as discussed in the text. The solid lines are fits [61] to the data. The light solid line in (c) represents the angle averaged orbital moment.

moment itself (Fig. 12(a)) is essentially thickness independent. The anisotropy in the dipole moment, in contrast, shows a strong Co thickness dependence. At $t_{Co} = 4$ AL we find sizeable dipolar moments $m_D^\parallel = -0.112\mu_B$ and $m_D^\perp = 0.224\mu_B$, i.e. a larger out-of-plane than in-plane component. The data follow a simple $1/t_{Co}$ dilution law (solid lines) leading to large extrapolated corrections $m_D^\parallel = -0.43\mu_B$ and $m_D^\perp = 0.86\mu_B$ for a single Co layer sandwiched between Au.

The orbital moment is also strongly anisotropic. The thickness dependent anisotropy, $\Delta m_o = m_o^\perp - m_o^\parallel$, takes values up to about $0.12\mu_B$ at the 4 AL Co step. Δm_o decays rapidly and becomes smaller than the experimental error for thicknesses larger than 7 AL. A $1/t_{Co}$ behavior, again, can be fitted to the data [61]. We extrapolate monolayer orbital moments of $m_o^\perp = 0.36\mu_B$ and $m_o^\parallel \approx 0\mu_B$ for perpendicular and in-plane orientations, respectively. Here the bulk Co orbital moment, which is essentially isotropic, was assumed to be $m_o = 0.14\mu_B$ for both orientations. The angle averaged orbital moment $(m_o^\perp + 2m_o^\parallel)/3$ is also plotted in Fig. 12(c) and is found to be essentially independent of Co thickness. We believe that the constancy of m_s and m_o are a consequence of two competing and compensating effects, a thin-film enhancement effect and a finite temperature reduction effect. The latter arises from a reduced Curie temperature for thin films [16,62], yielding a reduced moment at room temperature.

The results for the anisotropy of the dipolar moment $m_D^\perp > m_D^\parallel$ and the orbital moment $m_o^\perp > m_o^\parallel$, in the limit of a Co monolayer sandwiched between Au, are inverted from those discussed in Sections 4.2 and 4.3 for a free-standing monolayer. This is caused by the fact that for Au/Co/Au the in-plane Co–Co bonding is weaker than the out-of-plane Co–Au bonding [34]. Thus we have the case $V_\perp > V_\parallel$ which leads to $m_o^\perp > m_o^\parallel$ according to Eqs. (14) and (15), as observed. Also, for $V_\perp > V_\parallel$ we have the opposite case to that shown in Fig. 1 and the moments of the in-plane d orbitals will be larger than those of the out-of-plane orbitals. According to Eq. (13) this leads to $m_D^\perp > m_D^\parallel$, as observed.

The importance of the present results is that they provide direct experimental proof for a simple picture for the microscopic origin of the MCA. Below 11 AL of Co, the anisotropy energy associated with the orbital moment exceeds the value of the extra-atomic spin–spin dipole interaction, which favours in-plane orientation of the spin moment, and the magnetization turns into the perpendicular direction favored by the orbital moment. Because the s–o coupling energy (about 10^{-2} eV atom^{-1}) is large compared to the anisotropy energies associated with the spin and orbital moments (about 2×10^{-4} eV atom^{-1}), the two moments remain coupled (parallel) and we have the interesting situation that the small orbital moment redirects the larger spin moment into a perpendicular alignment (easy axis). The case of perpendicular magnetic anisotropy is of considerable interest for technological applications. In our

H:\CTD_OCR\OCR_TIFF\R06\R0600233\R0600233\ 0270.tif (2272x3120x2 tiff)

simple picture PMA arises from an enhanced orbital moment along the surface normal. We have seen that this requires $V_{\perp} > V_{\parallel}$ so that suitable structures may be engineered by sandwiching a thin magnetic layer between other layers that "bond strongly" to it, as in a Au/Co/Au sandwich. Our results therefore also provide a recipe of how to obtain multilayers with large perpendicular anisotropy.

7. Conclusions

The present paper is intended to outline the basic principles and techniques of quantitative XMCD spectroscopy. We have also given two examples of the use of the technique for the determination of element specific spin and orbital magnetic moments. It is clear that XMCD has already been put to good use in addressing important issues in magnetism that are difficult or impossible to solve with conventional techniques. There are many other capabilities and applications of XMCD which have not been covered here for reasons of space constraints. We shall close this paper by mentioning a few for completeness.

XMCD is not only element specific but even offers chemical specificity as demonstrated by Sette et al. in studies of spinels and garnets [14]. It can be used to measure element-specific hysteresis loops of heteromagnetic systems [63]. The magnetic contributions of different electronic valence subshells can be probed by selection of appropriate core shells. For example, for the Co/Cu system discussed above, Pizzini et al. [64] have measured the K shell dichroism spectra of Co and Cu and elucidated the magnetic contributions of the p valence electrons, supplementing the information on the d electrons discussed here. The temperature dependence of the magnetization in thin films on surfaces has been investigated down to monolayer coverage [16,17,62]. Noteworthy also is the use of XMCD in conjunction with a small oscillating external magnetic field to obtain the element specific a.c. susceptibility [65], which yields information not only about magnetic but also structural properties of the films. Finally, XMCD can be used for magnetic imaging [15], offering elemental specificity together with the capability of studying buried layers.

Acknowledgements

This work was carried out in part at SSRL which is operated by the Department of Energy, Division of Chemical Sciences. I would like to thank my collaborators who were involved in the original work reviewed here, especially Harald König, Reiko Nakajima, Mahesh Samant and Dieter Weller.

References and notes

[1] A.J. Freeman and R. Wu, J. Magn. Magn. Mater., 100 (1991) 497.
[2] U. Gradmann and J. Müller, Phys. Status Solidi, 27 (1968) 313.
[3] P.F. Carcia, A.D. Meinholdt and A. Suna, App. Phys. Lett., 47 (1985) 178.
[4] M.N. Baibich, J.M. Broto, A. Fert, F.N.V. Dau, F. Petroff, P. Eitenne, G. Creuzet, A. Friederich and J. Chazelas, Phys. Rev. Lett., 61 (1988) 2472.
[5] G. Binasch, P. Grünberg, F. Saurenbach and W. Zinn, Phys. Rev. B, 39 (1989) 4828.
[6] S.S.P. Parkin, N. More and K.P. Roche, Phys. Rev. Lett., 64 (1990) 2304.
[7] B. Dieny, V.S. Speriosu, S.S.P. Parkin, B.A. Gurney, D.R. Wilhoit and D. Mauri, Phys. Rev. B, 43 (1991) 1279.
[8] C. Tsang, R.E. Fontana, Jr., T. Lin, D.E. Heim, V.S. Speriosu, B.A. Gurney and M.L. Williams, IEEE Trans. Mag., 30 (1994) 3801.
[9] J.E. Hurst, Jr. and W.J. Kozlovsky, Jpn. J. Appl. Phys., 32 (1993) 5301.
[10] J.M. Daughton, Thin Solid Films, 216 (1992) 162.
[11] J.L. Erskine and E.A. Stern, Phys. Rev. B, 12 (1975) 5016.
[12] G. Schütz, W. Wagner, W. Wilhelm, P. Kienle, R. Zeller, R. Frahm and G. Materlik, Phys. Rev. Lett., 58 (1987) 737.
[13] B.D. Cullity, Introduction to Magnetic Materials, Addison-Wesley, Reading, 1972.
[14] F. Sette, C.T. Chen, Y. Ma, S. Modesti, and N.V. Smith, in S.S. Hasnain (Ed.), X-Ray Absorption Fine Structure, Ellis Horwood, Chichester, 1991, p. 96.
[15] J. Stöhr, Y. Wu, B.D. Hermsmeier, M.G. Samant, G.R. Harp, S. Koranda, D. Dunham and B.P. Tonner, Science, 259 (1993) 658.
[16] L.H. Tjeng, Y.U. Idzerda, P. Rudolf, F. Sette and C.T. Chen, J. Magn. Magn. Mater., 109, (1992) 288.

[17] J. Hunter Dunn, D. Arvanitis, N. Mårtensson, M. Tischer, F. May, M. Russo and K. Baberschke, J. Phys.: Condens. Matter, 7 (1995) 111; W.L. O'Brien and B.P. Tonner, Phys. Rev. B, 52 (1995) 1.
[18] O. Eriksson, B. Johansson, R.C. Albers, A.M. Boring and M.S.S. Brooks, Phys. Rev. B, 42 (1990) 2707.
[19] P. Söderlind, O. Eriksson, B. Johansson, R.C. Albers and A.M. Boring, Phys. Rev. B, 45 (1992) 12911.
[20] F.M.F. de Groot, J.C. Fuggle, B.T. Thole and G.A. Sawatzky, Phys. Rev. B, 42 (1990) 5459.
[21] G. van der Laan and B.T. Thole, Phys. Rev. B, 43 (1991) 13401.
[22] G. van der Laan, B.T. Thole, G.A. Sawatzky and M. Verdaguer, Phys. Rev. B, 37 (1988) 6587.
[23] F.M.F. de Groot, J. Electron Spectrosc. Relat. Phenom., 67 (1994) 529.
[24] C.T. Chen, N.V. Smith and F. Sette, Phys. Rev. B, 43 (1991) 6785.
[25] T. Jo and G.A. Sawatzky, Phys. Rev. B, 43 (1991) 8771.
[26] N.V. Smith, C.T. Chen, F. Sette and L.F. Mattheis, Phys. Rev. B, 46 (1992) 1023.
[27] J.C. Slater and G.F. Koster, Phys. Rev., 94 (1954) 1498.
[28] D.A. Papaconstantopoulos, Handbook of the Band Structure of Elemental Solids, Plenum, New York, 1986.
[29] G.H.O. Daalderop, P.J. Kelly and M.F.H. Schuurmans, Phys. Rev. B, 50 (1994) 9989.
[30] J. Stöhr and H. König, Phys. Rev. Lett., 75 (1995) 3748.
[31] G.H.O. Daalderop, P.J. Kelly and M.F.H. Schuurmans Phys. Rev. B, 44, (1991) 12054.
[32] P. Bruno, Phys. Rev. B, 39 (1989) 865.
[33] P. Bruno, in Magnetismus von Festkörpern und Grenzflächen, KFA Jülich, Jülich, 1993, p. 24.1.
[34] D. Wang, R. Wu and A.J. Freeman, J. Magn. Magn. Mater., 129 (1994) 237.
[35] Note that $\Delta E_{SO} = -K_1$ with the convention $E_{SO} = K_0 + K_1 \sin^2\theta$ used by Bruno [33].
[36] J. Stöhr and Y. Wu, in A.S. Schlachter and F.J. Wuilleumier (Eds.), New Directions in Research with Third-Generation Soft X-Ray Synchrotron Radiation Sources, Kluwer Academic Publishers, Netherlands, 1994, p. 221.
[37] The one-electron diagram shown in Fig. 4 is misleading, especially to the photoemission community, in that it depicts the spin–orbit splitting of the p core shell as an "initial state" effect. In the proper description based on a configuration picture, an atom is excited from a ground or initial state configuration to an excited or final state configuration. While in general the one electron and configuration pictures are not equivalent, equivalence does exist for the case of a d^9 ground state, as discussed elsewhere [36]. This, in fact, justifies use of the one electron model.
[38] The handedness of circularly polarized light is not uniquely defined. We follow Feynman and the convention used in particle physics. See R.P. Feynman, R.B. Leighton and M. Sands, The Feynman Lectures on Physics, Vol. I, Part 2, Addison-Wesley, Reading, 1964.
[39] J. Stöhr, NEXAFS Spectroscopy, Springer Series in Surface Sciences, Vol. 25, Springer, Heidelberg, 1992.
[40] H. Ebert, J. Stöhr, S.S.P. Parkin, M. Samant and A. Nilsson, Phys. Rev. B, in press.
[41] A. Nilsson and N. Mårtensson, Physica B, 208/209 (1995) 19.
[42] P. Carra, B.T. Thole, M. Altarelli and X. Wang, Phys. Rev. Let., 70 (1993) 694.
[43] B.T. Thole, P. Carra, F. Sette and G. van der Laan, Phys. Rev. Lett., 68 (1992) 1943.
[44] C.T. Chen, Y.U. Idzerda, H.-J. Lin, N.V. Smith, G. Meigs, G.H. Ho, E. Pellegrin and F. Sette, Phys. Rev. Lett., 75 (1995) 152.
[45] L.-C. Duda, J. Stöhr, D.C. Mancini, A. Nilsson, N. Wassdahl, J. Nordgren and M.G. Samant, Phys. Rev. B, 50 (1994) 16758.
[46] W.L. O'Brien and B.P. Tonner, Phys. Rev. B, 50 (1994) 12672.
[47] D.M. Edwards and J. Mathon, J. Magn. Magn. Mater., 93 (1991) 85.
[48] D.M. Edwards, J. Mathon, R.B. Muniz and M.S. Phan, Phys. Rev. Lett., 67 (1991) 493.
[49] J.E. Ortega and F.J. Himpsel, Phys. Rev. Lett., 69 (1992) 844.
[50] B.A. Jones and C.B. Hanna, Phys. Rev. Lett., 71 (1993) 4253.
[51] M.C. Muñoz and J.L. Pérez-Diaz, Phys. Rev. Lett., 72 (1994) 2482.
[52] M. van Schilfgaarde and W.A. Harrison, Phys. Rev. Lett., 71 (1993) 3870.
[53] G. Schütz, H. Ebert, P. Fischer, S. Rüegg and W.B. Zeper, Mater. Res. Soc. Symp. Proc., 231 (1992) 77.
[54] M.G. Samant, J. Stöhr, S.S.P. Parkin, G.A. Held, B.D. Hermsmeier, F. Herman, M. van Schilfgaarde, L.-C. Duda, D.C. Mancini, N. Wassdahl and R. Nakajima, Phys. Rev. Lett., 72 (1994) 1112.
[55] A. Nilsson, J. Stöhr, T. Wiell, M. Aldén, P. Bennich, N. Wassdahl, M. Samant, S.S.P. Parkin, N. Mårtensson, J. Nordgren, B. Johansson and H.L. Skriver, Phys. Rev. B, in press.
[56] K. Garrison, Y. Chang and P.D. Johnson, Phys. Rev. Lett., 71 (1993) 2801.
[57] J.H.V. Vleck, Phys. Rev., 52 (1937) 1178.
[58] U. Gradmann, in K.H.J. Buschow (Ed.), Ferromagnetic Materials, Elsevier, Amsterdam, 1993, Vol. 7.
[59] D. Weller, J. Stöhr, R. Nakajima, A. Carl, M.G. Samant, C. Chappert, R. Mégy, P. Beauvillain, P. Veillet and G. Held, Phys. Rev. Lett., 75 (1995) 3752.
[60] D. Weller, Y. Wu, J. Stöhr, M.G. Samant, B.D. Hermsmeier and C. Chappert, Phys. Rev. B, 49 (1994) 12888.
[61] The moments derived by XMCD are average moments over the probed Co volume and are determined by the actual moment profile $m(z)$, the Co film thickness t and the mean electron yield sampling depth λ in Co, according to $\overline{m(t)} = \int_0^t m(z)e^{\frac{-z}{\lambda}}dz / \int_0^t e^{\frac{-z}{\lambda}}dz$. For the fits in Fig. 12 we assumed moments m_I for the two interfacial Co layers, m_V for all interior layers, and $\lambda = 12.5$ AL, as determined independently. The fits so obtained give almost identical

results as a simple dilution law, $m_V + m_l/t$, which is obtained for $\lambda \gg t$.

[62] M. Tischer, D. Arvanitis, T. Yokoyama, T. Lederer, L. Tröger and K. Baberschke, Surf. Sci., 307–309 (1994) 1096.

[63] C.T. Chen, Y.U. Idzerda, H. Lin, G. Meigs, A. Chaiken, G.A. Prinz and G.H. Ho, Phys. Rev. B, 48 (1993) 642.

[64] S. Pizzini, A. Fontaine, C. Giorgetti, E. Dartyge, J.F. Bobo, M. Piecuch and F. Baudelet, Phys. Rev. Lett., 74 (1995) 1470.

[65] A. Aspelmeier, M. Tischer, M. Farle, M. Russo, K. Baberschke and D. Arvanitis, J. Magn. Mater., 146 (1995) 256.

[66] B.L. Henke, E.M. Gullikson and J.C. Davis, At. Data Nucl. Data Tables, 54 (1993) 181.