

<https://doi.org/10.1038/s44306-024-00052-1>

Hybrid magnon-phonon crystals

Check for updates

Liyang Liao¹, Jiacheng Liu², Jorge Puebla³, Qiming Shao^{2,4} & Yoshichika Otani^{1,3,5} ✉

Magnons and phonons are engineered in artificial lattices with tunable modes and band dispersions. Recent advance in magnon-phonon coupling shined a light on combining magnonic and phononic crystals as hybrid magnon-phonon crystals, benefit from the tunable magnon-phonon coupling, the time-reversal symmetry breaking of magnons, and the long lifetime of phonons. This perspective summarizes lattice-based mutual control of magnons and phonons, and proposes the opportunities provided by the hybrid magnon-phonon crystals.

An artificial periodic structure, or artificial lattice, is a powerful tool to modulate the coupling between different degrees of freedom. For example, the electrons in the Moiré superlattices of overlapped two layers with a specific arrangement of points can form superconducting¹ or quantum anomalous Hall states^{2,3}. Designed lattices enhance the light-matter coupling⁴, enabling strong nonlinear effects^{4,5} and controllable laser emission with high efficiency^{6,7}. One may use artificial lattices to tune the coupling through several strategies. Firstly, a periodic structure induces coherent scattering on a wave, creating a designed band dispersion and wave function. The coupling between two waves, related to their band dispersion and wavefunction, is thus naturally controlled by the designed artificial lattices, even if the coupling strength is still uniform. Meanwhile, the periodic structure may directly control the local coupling strength, inducing a periodical (non-uniform) interaction landscape, e.g., the periodic interlayer coupling in the Moiré superlattices^{8,9}. Such non-uniform coupling strength can induce more sophisticated states, like those with entangled spins and valleys in the twisted bilayer graphene.

While the ability of artificial lattices to tune the coupling is mainly demonstrated in electronic and photonic coupling systems, the general principles should apply to various artificial lattices with coupled degrees of freedom. In spintronics, spin waves formed by the collective motion of the spin degree of freedom are tuned in artificial lattices, known as magnonic crystals (Fig. 1a). While spin waves in uniform magnetic materials¹⁰ show abundant tunability via magnetic field^{11,12} and ferroelectricity¹³, the magnonic crystals can additionally obtain a significantly different spectrum, such as tunable band gaps^{14–19}. Modern nano-techniques enable magnonic crystals with a lattice size in sub- μm scale, leading to the application in various devices processing information^{20–22}, especially at GHz frequency. At the same frequency range and characteristic size scale, another significant artificial lattice is the phononic crystal (Fig. 1b) based on surface acoustic wave (SAW). Various physical phenomena, including Klein tunnelling²³ and topological edge states^{24,25} have been observed in phononic crystals. In phononic crystals with sub- μm

scale lattice size, the phononic valley Hall effect and phononic valley Hall edge states at GHz frequency are also demonstrated^{26–29}.

Magnons and phonons inherently couple due to the magnetoelastic interactions, which generally exist in magnetic materials (Fig. 1c). SAW can, therefore, excite ferromagnetic resonance³⁰ and spin pumping³¹, and the time-reversal symmetry breaking due to magnons can induce nonreciprocal-transmission-of phonons^{32–36}. In the magnon-phonon band structure, when the magnon band and the phonon band meet with the same wavevector and frequency, magnon-phonon coupling hybridizes the two waves, opening a gap, showing an anticrossing in the spectra^{37,38}. Due to the distinct symmetry properties of the magnetoelastic interaction, this gap opening can be associated with Berry curvature³⁹, enabling topological magnon-phonon hybrid excitations⁴⁰ and even chiral edge states^{40,41}.


Gathering the functionality of magnonic crystals, phononic crystals, and magnon-phonon coupling, as well as borrowing the successful concepts in the electronic and photonic coupling in artificial lattices, the combination of magnonic and phononic crystals may provide various emergent phenomena and benefit both the fields of phononic and magnonic crystals. Here we define a hybrid magnon-phonon crystal as an artificial lattice that exhibits a phononic and/or magnonic band structure and possesses magnon-phonon coupling. A typical example is shown in Fig. 1d where periodic acoustic scattering centers are made of magnetic materials. In this perspective, we will introduce some recent progress in the relevant fields, to show that the artificial lattice is a powerful tool to modulate the magnon-phonon coupling and discuss the possible structures of a hybrid magnon-phonon crystal. We then discuss future topics to be explored based on the physical properties of the hybrid magnon-phonon crystals, combined with possible experimental characterizing techniques and potential applications.

Recent progress on magnon-phonon coupling in artificial lattices

The simplest combination of the magnonic and phononic crystals is integrating the band gaps of the two excitations. In 2012, V. L. Zhang et al. reported the coexistence of the magnonic and phononic gaps in a linear

¹Institute for Solid State Physics, University of Tokyo, Kashiwa, 277-8581, Japan. ²Department of Electronic and Computer Engineering, The Hong Kong University of Science and Technology, Clear Water Bay, Hong Kong, China. ³Center for Emergent Matter Science, RIKEN, Wako, Saitama, 351-0198, Japan. ⁴Department of Physics and IAS Center for Quantum Technologies, The Hong Kong University of Science and Technology, Clear Water Bay, Hong Kong, China. ⁵Trans-scale Quantum Science Institute, University of Tokyo, Tokyo, 113-8654, Japan. ✉e-mail: yotani@issp.u-tokyo.ac.jp

Fig. 1 | Concept of hybrid magnon-phonon crystals. **a** Schematic of a magnonic crystal made of periodically patterned magnetic materials. **b** Schematic of a phononic crystal, where periodical scatter centers tune the transport of the acoustic waves. **c** Magnon-phonon coupling and the resulting magnon-phonon hybrid spectra. An avoid-crossing point can appear when both frequencies and wavevectors meet. **d** Concept of a hybrid magnon-phonon crystal, including the periodic acoustic scatter centers made of magnetic materials in the real space (lower panel) and the magnon-phonon hybrid band structure in the reciprocal space (upper panel).

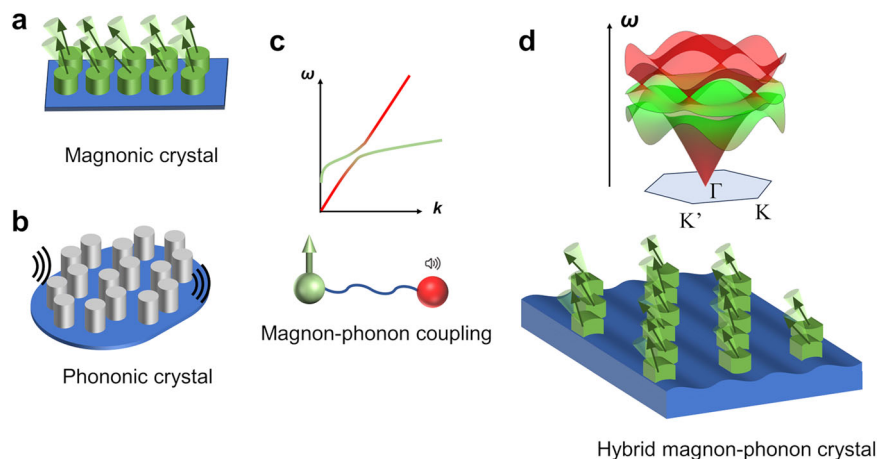

periodic array of Fe and permalloy using the Brillouin spectroscopy⁴². However, the magnon-phonon interaction was deliberately avoided in this study to separate the magnonic and phononic excitations.

The recent progress in magnon-phonon coupling shows abundant intriguing phenomena and possibilities^{43,44}. Coupling the circular polarization of the Rayleigh SAW to the right-handed magnetization precession creates nonreciprocal SAW transmission, i.e., the forward and backward SAWs have different attenuation because they carry opposite circular polarization and excite magnetic resonance with different efficiency. Various approaches can achieve such nonreciprocity, including the shear strains³⁵, magneto-rotation coupling³³, Dzyaloshinskii–Moriya interaction^{36,45}, and synthetic antiferromagnetism^{34,46}. Nonreciprocity can be understood as the magnetic control of the SAWs. In turn, acoustic control of the magnetization direction was reported via phonon-spin angular momentum transfer^{47,48}. This SAW-induced spin torque can also be detected electrically⁴⁹. Meanwhile, the SAW-based devices have also been extended to detect the magnon-phonon coupling in Van der Waals antiferromagnets⁵⁰, achieve on-chip strong magnon-phonon coupling in room temperature³⁸, assist magnetic domain wall motion⁵¹, create⁵² and manipulate⁵³ skyrmions. Thus, instead of separating the magnonic and phononic excitations, combining the magnon-phonon coupling^{43,44} with the artificial lattice may be more competitive in bringing about new opportunities.

A first example is the engineering of a phononic crystal for tuning the magnon-phonon coupling. The strong demand for high-quality cavities in magnon-phonon coupling triggers an approach to manipulating magnons employing a defect in a phononic crystal known as a high-quality acoustic cavity^{54–56}. Hatanaka et al. studied the cavity magnomechanics using phonons confined in a defect within a snow-flake-shaped phononic crystal⁵⁷ (Fig. 2a). Their optical interferometry experiments demonstrate that the phononic crystal cavity allows the spatial confinement of phonon energy, as well as the generation of different modes, with different strain distribution across the cavity. Precise manipulation of magnetoelastic interactions is then achieved by selectively tuning the phononic crystal resonance modes and controlling the external magnetic fields and changes in magnetization direction (angle). Hence, phononic crystals can precisely manipulate the magnons through phonon confinement, which has potential applications in signal processing.

As phononic crystals can tune the magnon-phonon coupling, it is natural to look at the opposite approach, i.e., to tune the coupling via engineering a magnonic crystal. Another recent work by Majumder et al. explores the hybridization of phonons with magnonic crystals⁵⁸. A coherent magnon-phonon coupling within a two-dimensional artificial magneto-elastic crystal is observed by the time-resolved magneto-optical Kerr effect technique (Fig. 2b). Central to their discovery is the formation of binary magnon

polarons, arising from the coherent coupling between two distinct Kittel-type magnon modes and a non-Kittel magnetoelastic mode, with the latter driven by SAW. The strongest coupling is achieved through the matched frequencies and wavevectors of the three modes, leading to a perfect phase match. Notably, the strong coupling exhibited significant anisotropy due to the spatial asymmetry of the arrays, with the coupling strength and the consequent formation of binary magnon-polarons being highly dependent on the direction of the SAW relative to the axes of the nanomagnets. The precise design and manipulation introduce strong coupling at room temperature, showcasing a novel method for controlling magnonic and phononic interactions.

Now, we turn to a more dramatic phenomenon combining the two types of crystals and the properties of the magnetoelastic interaction. As shown in Fig. 2c, in hexagonal phononic crystals, one can introduce asymmetric A site and B site in a unit cell (the dash line hexagon). In the reciprocal space, inequivalent high-symmetry points K and K' are in the first Brillouin zone. The band structures at these k points are known as valleys, like electronic valleys in the hexagonal graphene and transition metal dichalcogenides. Phonon modes at the K and K' points in the Brillouin zone are called K and K' valley phonons, labeled in red and blue bands, respectively.

The K and K' valleys are degenerated as they are time-reversal pairs, i.e., they have the same frequency and different *k* vectors. While magnons are introduced in the same lattice, the time-reversal symmetry can be broken. Hence, a valley-selective phonon-magnon scattering was achieved (Fig. 2c). With an upward magnetic field, phonons in the K valley can pass through the lattice more efficiently. On the contrary, phonons in the K' valley get more scattering from the magnons. The situation reverses when the magnetic field is reversed, as the phonons in the K' valley will now pass more efficiently⁵⁹.

The selective interaction between magnons and phonons is achieved by introducing local circular polarization in the phonon modes with broken spatial inversion symmetry. The asymmetric A and B sites lead to opposite local circular polarization at the A site for the K and the K' valley phonons. Experimentally this is achieved by patterning inversion-symmetry broken lattice using e-beam lithography, and exciting the phonon modes at the corresponding frequency, i.e., matching the wavelength of the applied acoustic wave and the lattice size⁵⁹. As magnons are always right-handed, they can only couple to right-handed phonons (K' valley) when the magnetization is upward and to left-handed phonons (K valley) when the magnetization is downward. Such helicity mismatch effect in the magnon-phonon coupling is an important tool for nonreciprocal SAW devices³². A similar interaction is also observed in a Van-der Waals antiferromagnet at low temperature⁶⁰. Through this effect, magnons can serve as a tool to manipulate the transport of the valley phonons.

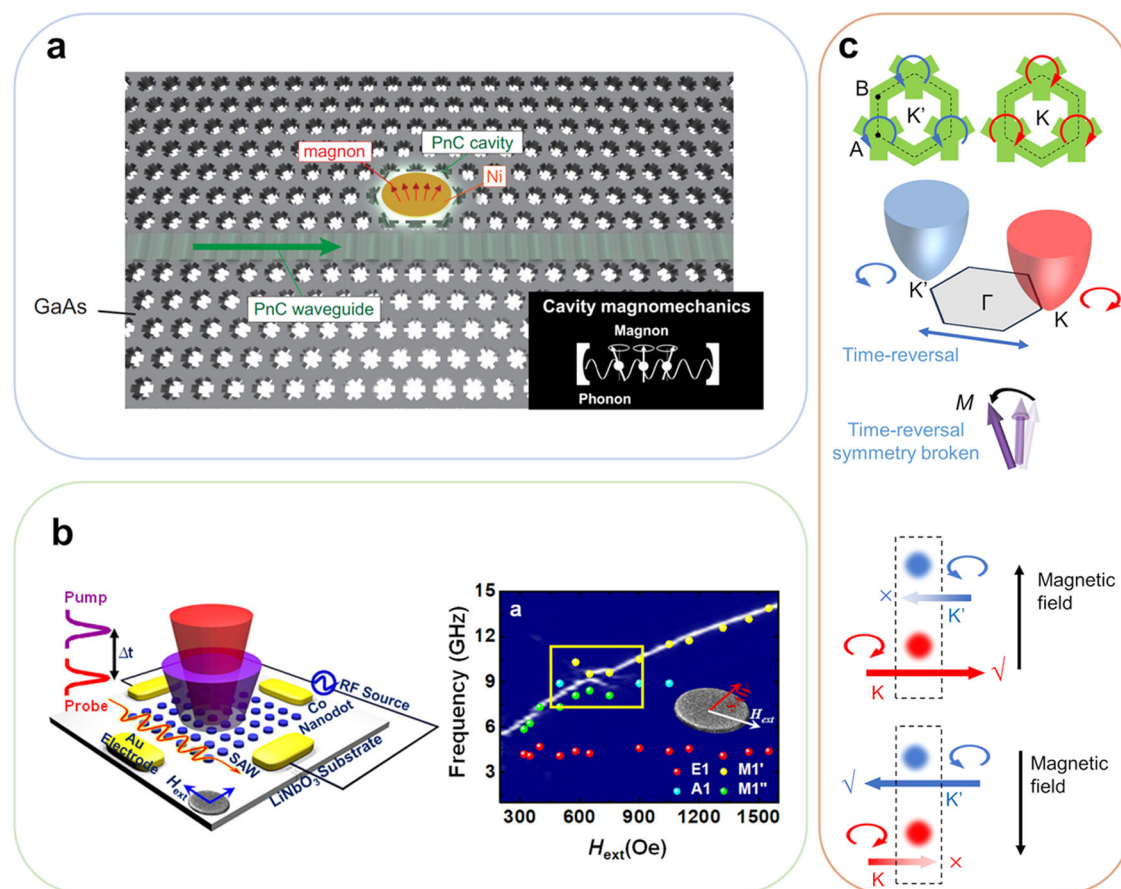


Fig. 2 | Recent progress on magnon-phonon coupling in artificial lattices.

a Engineering a phononic crystal for the magnon-phonon coupling. In the defect of a snow-flake-shaped phononic crystal, phononic energy is confined, and the cavity phonon mode can be selected. A magnetic Ni island is placed inside the cavity, allowing the magnon-phonon coupling. Copied from⁵⁷ with permission of American Physical Society. **b** Engineering a magnonic crystal for the magnon-phonon coupling. The time-resolved magneto-optical Kerr effect detects coherent magnon-phonon-magnon coupling within a two-dimensional artificial magneto-elastic

crystal. Anticrossing shows the strong coupling between a Kittel-type magnon mode and a non-Kittel magnetoelastic mode driven by SAW. Edited from⁵⁸ (open access). **c** Combining the phononic and magnonic crystal for new functionality with the magnon-phonon coupling. The phononic crystal has K and K' valleys as time reversal pairs with opposite chirality, and the magnons break the time-reversal symmetry so that selective control of the valley phonon transport is allowed: an upward magnetic field enables the transport of the K valley phonons, and a downward magnetic field behaves oppositely.

Perspectives on hybrid magnon-phonon crystals


The hybrid magnon-phonon crystals thus enrich the toolbar to modulate the magnon-phonon coupling, as well as providing new opportunities for the magnonic and phononic crystals (Fig. 3). Due to relatively sizeable magnetic damping, magnons usually have a short propagation length, limiting the scale of the magnonic crystals. However, phonons provide a much longer lifetime and propagation length, so magnon-phonon coupling enables magnon-phonon polarons to propagate long distance⁶¹. Hence, a hybrid magnon-phonon crystal can combine the advantage of the long-life phonons and the time-reversal symmetry-breaking nature of the magnons⁵⁹ and may open the avenue for more intriguing states. Since the magnetoelastic interaction can give a magnon-phonon hybrid band structure finite Berry curvature, leading to a Chern insulator-like state with topological edge transport⁴⁰, a properly designed hybrid magnon-phonon crystal may also own chiral edge states (Fig. 3a). Note that the traditional measurement of ports transmission or reflection via a Vector Network Analyzer may not be sufficient to conclude the chiral edge states directly. Instead, technologies that can locally detect the strain of the phononic crystal or dynamic magnetization state on the device surface are needed, such as characterizing strain through transmission-mode microwave impedance microscopy (TMIM)²⁷ or applying optically detected magnetic resonance (ODMR) to characterize the stray field

emitted by the magnonic crystal through the quantum sensor NV-center^{62,63}. Developing the tunable topological edge transport in the hybrid magnon-phonon crystals will advance the waveguides in wave-based computing.

While the magnetic damping limits the magnon lifetime and is usually unfavorable, the resulting loss makes the magnon-phonon hybrid system inherently non-Hermitian^{64,65}. As shown in Fig. 3b, considering the magnetic damping, the imaginary frequency can emerge in the magnon-phonon hybrid band structures. By engineering the hybrid band structures and creating finite areas in the real- and imaginary-frequencies spectra, the non-Hermitian skin effect can be achieved^{66–68}. The surface nature of the SAW can also lead to non-Hermiticity⁶⁹. Hence, the hybrid magnon-phonon crystals may also provide a platform for exploring the non-Hermitian physics⁷⁰.

The phononic crystals can tune the strain components and their distributions^{57,59}. The recently reported strong magnon-phonon coupling³⁸ emphasizes the crucial role of strain components in reaching the strong-coupling regime. Furthermore, the defect in a phononic crystal acts as a cavity^{54–56} that can confine the energy of the acoustic mode (Fig. 3c). Such confinement effect can be achieved or enhanced through engineered flat bands, e.g., by creating moiré patterns⁷¹. Hence, we can expect that through engineering the lattice symmetry and band structure, making cavities with stronger confinement ability, a hybrid magnon-phonon crystal can contribute to further enhancing the magnon-phonon coupling strength, and

Fig. 3 | Perspectives on hybrid magnon-phonon crystals. **a** Designing band structures with nonzero Chern number with the magnetoelastic interaction may enable topological chiral edge modes, which can be detected by a MIM microscope or a N.V. center and help develop tunable waveguides. **b** The imaginary frequency induced by the magnetic damping provides opportunities for non-Hermitian physics. **c** Defect-induced cavity can enhance magnon-phonon coupling, benefiting coherent information processing and the magnetoelectric antennas for wireless communication. **d** Spin-ice-type magnetic textures in artificial lattices interacting with SAWs may be used for neuromorphic reservoir computing.

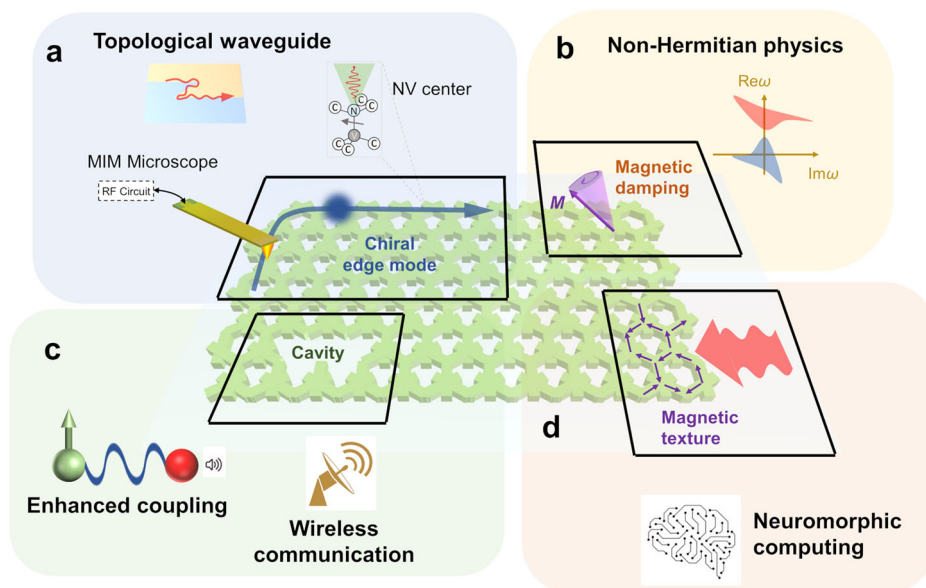

tuning nonlinear effects^{4,5}. The improved coupling can benefit coherent information processing and the miniaturization of magnetoelectric antennas for wireless communication^{72–74}.

Another possible direction for hybrid magnon-phonon crystals is the combination with spin textures. It is known that artificial magnetic lattices can host rich ground states, known as artificial spin ice, due to the dipolar interaction⁷⁵. The magnetic textures lead to rich spin wave fingerprints^{76,77}. The complexity of magnetic textures is a widely used resource for neuromorphic computing called reservoir computing^{78,79}. As the SAWs have shown the ability to probe spin waves and manipulate magnetizations^{47,80}, and the periodic artificial magnetic lattice can also tune the SAW spectra as a phononic crystal, combining SAW with artificial spin ice may create more opportunities for spin-ice-based reservoir computing (Fig. 3d).

We finally briefly introduce the simulation techniques for hybrid magnon-phonon crystals. For GHz on-chip acoustic devices, which mainly use the SAW-based phonons, the acoustic dynamic is described by the elastic equation⁵⁹ and widely solved via the finite element method with the multi-physics simulation software COMSOL. In COMSOL simulation⁸¹, one can design a complete unit cell, including a piezoelectric substrate and a lattice pattern. The “Floquet periodicity” boundary condition is then applied to obtain the band structure (eigenfrequency) of the unit cell lattice and the excited eigenmodes. This approach allows the design and analysis of the lattices with different symmetries. One may not apply periodic boundary conditions for the cavity but use the transmission line model⁸². The entire pattern of the cavity can be placed between the on-chip input and output to explore the response of the cavity pattern. One can use the same modeling but modify the applied physics module to include the magnon bands. For the micromagnetic module, the Landau-Lifshitz-Gilbert equation should include an effective field induced by magnetoelastic coupling, and the equation of motion for the mechanical module should include the magnetoelastic coupling⁸³.

Conclusion

In conclusion, the general principles to tune the coupling between two degree-of-freedom via artificial lattices can apply to the hybrid magnon-phonon crystals. It is then allowed to harvest the property of magnon-phonon coupling, the time-reversal symmetry-breaking nature of magnons, and the long lifetime of phonons in an integrated system. By benefiting from the advanced spectral measurement and local characterization techniques, the hybrid magnon-phonon crystals can provide novel opportunities for topological edge transports in tunable on-chip waveguides. The rich

properties, including the imaginary frequency due to the magnetic damping, cavity effect of the defects in a lattice, the artificial spin ice-type magnetic textures, enable the hybrid magnon-phonon crystal as a potential platform for non-Hermitian physics, magnetoelectric antennas, reservoir computing, etc. Hence, we look forward to further advancement in this area by exploring the above possibilities.

Data availability

No datasets were generated or analysed during the current study.

Received: 10 May 2024; Accepted: 29 July 2024;

Published online: 04 September 2024

References

1. Cao, Y. et al. Unconventional superconductivity in magic-angle graphene superlattices. *Nature* **556**, 43–50 (2018).
2. Serlin, M. et al. Intrinsic quantized anomalous Hall effect in a moiré heterostructure. *Science* **367**, 900–903 (2020).
3. Sharpe, A. L. et al. Emergent ferromagnetism near three-quarters filling in twisted bilayer graphene. *Science* **365**, 605–608 (2019).
4. Maggiolini, E. et al. Strongly enhanced light-matter coupling of monolayer WS₂ from a bound state in the continuum. *Nat. Mater.* **22**, 964–969 (2023).
5. Tahara, H., Sakamoto, M., Teranishi, T. & Kanemitsu, Y. Coherent electronic coupling in quantum dot solids induces cooperative enhancement of nonlinear optoelectronic responses. *Nat. Nanotechnol.* **19**, 744–750 (2024).
6. Chen, Y. et al. Compact spin-valley-locked perovskite emission. *Nat. Mater.* **22**, 1065–1070 (2023).
7. Ripin, A. et al. Tunable phononic coupling in excitonic quantum emitters. *Nat. Nanotechnol.* **18**, 1020–1026 (2023).
8. Lian, B., Liu, Z., Zhang, Y. & Wang, J. Flat Chern Band from Twisted Bilayer MnBi₂Te₄. *Phys. Rev. Lett.* **124**, 126402 (2020).
9. Bistritzer, R. & MacDonald, A. H. Moiré bands in twisted double-layer graphene. *Proc. Nat. Acad. Sci.* **108**, 12233–12237 (2011).
10. Pirro, P., Vasyuchka, V. I., Serga, A. A. & Hillebrands, B. Advances in coherent magnonics. *Nat. Rev. Mater.* **6**, 1114–1135 (2021).
11. Cornelissen, L. J. et al. Long-distance transport of magnon spin information in a magnetic insulator at room temperature. *Nat. Phys.* **11**, 1022–1026 (2015).
12. Lebrun, R. et al. Tunable long-distance spin transport in a crystalline antiferromagnetic iron oxide. *Nature* **561**, 222–225 (2018).

13. Huang, X. et al. Manipulating chiral spin transport with ferroelectric polarization. *Nat. Mater.* **23**, 898–904 (2024).
14. Tang, W. et al. Spin wave modes of width modulated Ni80Fe20/Pt nanostrip detected by spin-orbit torque induced ferromagnetic resonance. *Appl. Phys. Lett.* **111**, 172407 (2017).
15. Richardson, D., Kalinikos, B. A., Carr, L. D. & Wu, M. Spontaneous Exact Spin-Wave Fractals in Magnonic Crystals. *Phys. Rev. Lett.* **121**, 107204 (2018).
16. Chumak, A. V. et al. Storage-recovery phenomenon in magnonic crystal. *Phys. Rev. Lett.* **108**, 257207 (2012).
17. Qin, H., Both, G.-J., Hämäläinen, S. J., Yao, L. & van Dijken, S. Low-loss YIG-based magnonic crystals with large tunable bandgaps. *Nat. Commun.* **9**, 5445 (2018).
18. Wang, Z. K. et al. Observation of frequency band gaps in a one-dimensional nanostructured magnonic crystal. *Appl. Phys. Lett.* **94**, 083112 (2009).
19. Wang, Z. K. et al. Nanostructured Magnonic Crystals with Size-Tunable Bandgaps. *ACS Nano* **4**, 643–648 (2010).
20. Hu, Z., Fu, L. & Liu, L. Tunable Magnonic Chern Bands and Chiral Spin Currents in Magnetic Multilayers. *Phys. Rev. Lett.* **128**, 217201 (2022).
21. Krawczyk, M. & Grundler, D. Review and prospects of magnonic crystals and devices with reprogrammable band structure. *J. Phys.-Condens. Mat.* **26**, 123202 (2014).
22. Chumak, A. V., Serga, A. A. & Hillebrands, B. Magnonic crystals for data processing. *J. Phys. D Appl. Phys.* **50**, 244001 (2017).
23. Jiang, X. et al. Direct observation of Klein tunneling in phononic crystals. *Science* **370**, 1447–1450 (2020).
24. He, C. et al. Acoustic topological insulator and robust one-way sound transport. *Nat. Phys.* **12**, 1124–1129 (2016).
25. Yan, M. et al. On-chip valley topological materials for elastic wave manipulation. *Nat. Mater.* **17**, 993–998 (2018).
26. Nii, Y. & Onose, Y. Imaging an Acoustic Topological Edge Mode on a Patterned Substrate with Microwave Impedance Microscopy. *Phys. Rev. Appl.* **19**, 014001 (2023).
27. Zhang, Q. et al. Gigahertz topological valley Hall effect in nanoelectromechanical phononic crystals. *Nat. Electron.* **5**, 157–163 (2022).
28. Noh, J., Huang, S., Chen, K. P. & Rechtsman, M. C. Observation of Photonic Topological Valley Hall Edge States. *Phys. Rev. Lett.* **120**, 63902 (2018).
29. Ma, T. & Shvets, G. All-Si valley-Hall photonic topological insulator. *New J Phys.* **18**, 025012 (2016).
30. Weiler, M. et al. Elastically driven ferromagnetic resonance in nickel thin films. *Phys. Rev. Lett.* **106**, 117601 (2011).
31. Weiler, M. et al. Spin pumping with coherent elastic waves. *Phys. Rev. Lett.* **108**, 176601 (2012).
32. Tateno, S., Nozaki, Y. & Nozaki, Y. Highly nonreciprocal spin waves excited by magnetoelastic coupling in a Ni/Si bilayer. *Phys. Rev. Appl.* **13**, 034074 (2020).
33. Xu, M. et al. Nonreciprocal surface acoustic wave propagation via magneto-rotation coupling. *Sci. Adv.* **6**, eabb1724 (2020).
34. Shah, P. J. et al. Giant nonreciprocity of surface acoustic waves enabled by the magnetoelastic interaction. *Sci. Adv.* **6**, eabc5648 (2020).
35. Sasaki, R., Nii, Y., Iguchi, Y. & Onose, Y. Nonreciprocal propagation of surface acoustic wave in Ni/LiNbO₃. *Phys. Rev. B* **95**, 020407 (2017).
36. Kü, M. et al. Nonreciprocal Dzyaloshinskii-Moriya Magnetoacoustic Waves. *Phys. Rev. Lett.* **125**, 217203 (2020).
37. Puebla, J., Hwang, Y., Kondou, K. & Otani, Y. Progress in Spinconversion and its Connection with Band Crossing. *Ann. Phys.* **534**, 2100398 (2022).
38. Hwang, Y. et al. Strongly Coupled Spin Waves and Surface Acoustic Waves at Room Temperature. *Phys. Rev. Lett.* **132**, 056704 (2024).
39. Takahashi, R. & Nagaosa, N. Berry curvature in magnon-phonon hybrid systems. *Phys. Rev. Lett.* **117**, 217205 (2016).
40. Go, G., Kim, S. K. & Lee, K. J. Topological Magnon-Phonon Hybrid Excitations in Two-Dimensional Ferromagnets with Tunable Chern Numbers. *Phys. Rev. Lett.* **123**, 237207 (2019).
41. Thingstad, E., Kamra, A., Brataas, A. & Sudbø, A. Chiral Phonon Transport Induced by Topological Magnons. *Phys. Rev. Lett.* **122**, 107201 (2019).
42. Zhang, V. L. et al. Observation of dual magnonic and phononic bandgaps in bi-component nanostructured crystals. *Appl. Phys. Lett.* **100**, 163118 (2012).
43. Li, Y., Zhao, C., Zhang, W., Hoffmann, A. & Novosad, V. Advances in coherent coupling between magnons and acoustic phonons. *APL Mater.* **9**, 060902 (2021).
44. Yang, W.-G. & Schmidt, H. Acoustic control of magnetism toward energy-efficient applications. *Appl. Phys. Rev.* **8**, 021304 (2021).
45. Verba, R., Lisenkov, I., Krivorotov, I., Tiberkevich, V. & Slavin, A. Nonreciprocal Surface Acoustic Waves in Multilayers with Magnetoelastic and Interfacial Dzyaloshinskii-Moriya Interactions. *Phys. Rev. Appl.* **9**, 64014 (2018).
46. Verba, R., Tiberkevich, V. & Slavin, A. Wide-Band Nonreciprocity of Surface Acoustic Waves Induced by Magnetoelastic Coupling with a Synthetic Antiferromagnet. *Phys. Rev. Appl.* **12**, 54061 (2019).
47. Sasaki, R., Nii, Y. & Onose, Y. Magnetization control by angular momentum transfer from surface acoustic wave to ferromagnetic spin moments. *Nat. Commun.* **12**, 2599 (2021).
48. Thevenard, L. et al. Irreversible magnetization switching using surface acoustic waves. *Phys. Rev. B* **87**, 144402 (2013).
49. Chen, C. et al. Direct-Current Electrical Detection of Surface-Acoustic-Wave-Driven Ferromagnetic Resonance. *Adv. Mater.* **35**, 2302454 (2023).
50. Lyons, T. P. et al. Acoustically Driven Magnon-Phonon Coupling in a Layered Antiferromagnet. *Phys. Rev. Lett.* **131**, 196701 (2023).
51. Edrington, W. et al. SAW assisted domain wall motion in Co/Pt multilayers. *Appl. Phys. Lett.* **112**, 052402 (2018).
52. Yokouchi, T. et al. Creation of magnetic skyrmions by surface acoustic waves. *Nat. Nanotechnol.* **15**, 361–366 (2020).
53. Chen, R. et al. Ordered creation and motion of skyrmions with surface acoustic wave. *Nat. Commun.* **14**, 4427 (2023).
54. Hatanaka, D. & Yamaguchi, H. Real-Space Characterization of Cavity-Coupled Waveguide Systems in Hypersonic Phononic Crystals. *Phys. Rev. Appl.* **13**, 024005 (2020).
55. Maldovan, M. Sound and heat revolutions in phononics. *Nature* **503**, 209–217 (2013).
56. Hatanaka, D., Mahboob, I., Onomitsu, K. & Yamaguchi, H. Phonon waveguides for electromechanical circuits. *Nat. Nanotechnol.* **9**, 520–524 (2014).
57. Hatanaka, D., Asano, M., Okamoto, H. & Yamaguchi, H. Phononic Crystal Cavity Magnomechanics. *Phys. Rev. Appl.* **19**, 054071 (2023).
58. Majumder, S., Drobitch, J. L., Bandyopadhyay, S. & Barman, A. Formation of binary magnon polaron in a two-dimensional artificial magneto-elastic crystal. *NPG Asia. Mater.* **15**, 51 (2023).
59. Liao, L. et al. Valley-Selective Phonon-Magnon Scattering in Magnetoelastic Superlattices. *Phys. Rev. Lett.* **131**, 176701 (2023).
60. Cui, J. et al. Chirality selective magnon-phonon hybridization and magnon-induced chiral phonons in a layered zigzag antiferromagnet. *Nat. Commun.* **14**, 3396 (2023).
61. Zhang, J. et al. Long decay length of magnon-polarons in BiFeO₃/La_{0.67}Sr_{0.33}MnO₃ heterostructures. *Nat. Commun.* **12**, 7258 (2021).
62. Casola, F., Van Der Sar, T. & Yacoby, A. Probing condensed matter physics with magnetometry based on nitrogen-vacancy centres in diamond. *Nat. Rev. Mater.* **3**, 17088 (2018).
63. Liu, J., Wu, J., Ren, Z., Yang, S. & Shao, Q. On-chip zero-field spin wave frequency multiplier and its application on qubit quantum control. In *2023 International Electron Devices Meeting (IEDM)*. Vol. 1, 1–4 (IEEE, 2023).

64. McClarty, P. A. & Rau, J. G. Non-Hermitian topology of spontaneous magnon decay. *Phys. Rev. B* **100**, 100405(R) (2019).
65. Hurst, H. M. & Flebus, B. Non-Hermitian physics in magnetic systems. *J. Appl. Phys.* **132**, 220902 (2022).
66. Deng, K. & Flebus, B. Non-Hermitian skin effect in magnetic systems. *Phys. Rev. B* **105**, L180406 (2022).
67. Zhang, K., Fang, C. & Yang, Z. Dynamical Degeneracy Splitting and Directional Invisibility in Non-Hermitian Systems. *Phys. Rev. Lett.* **131**, 036402 (2023).
68. Zhang, K., Yang, Z. & Fang, C. Universal non-Hermitian skin effect in two and higher dimensions. *Nat. Commun.* **13**, 2496 (2022).
69. Bliokh, K. Y., Leykam, D., Lein, M. & Nori, F. Topological non-Hermitian origin of surface Maxwell waves. *Nat. Commun.* **10**, 580 (2019).
70. Bergholtz, E. J., Budich, J. C. & Kunst, F. K. Exceptional topology of non-Hermitian systems. *Rev. Mod. Phys.* **93**, 015005 (2021).
71. Luan, H. Y., Ouyang, Y. H., Zhao, Z. W., Mao, W. Z. & Ma, R. M. Reconfigurable moiré nanolaser arrays with phase synchronization. *Nature* **624**, 282–288 (2023).
72. Nan, T. et al. Acoustically actuated ultra-compact NEMS magnetoelectric antennas. *Nat. Commun.* **8**, 296 (2017).
73. Ji, Y., Zhang, C. & Nan, T. Magnon-Phonon-Interaction-Induced Electromagnetic Wave Radiation in the Strong-Coupling Region. *Phys. Rev. Appl.* **18**, 064050 (2022).
74. Ma, M. et al. High frequency magnetoelectric antenna by acoustic excitation for 5 G communication. *IEEE Anten. Wire. Propag. Lett.* **23**, 1–5 (2024).
75. Skjærvø, S. H., Marrows, C. H., Stamps, R. L. & Heyderman, L. J. Advances in artificial spin ice. *Nat. Rev. Phys.* **2**, 13–28 (2020).
76. Li, Q. et al. Spin-Wave Dynamics in an Artificial Kagome Spin Ice. *Chin. Phys. Lett.* **38**, 047501 (2021).
77. Wang, Y. L. et al. Switchable geometric frustration in an artificial-spin-ice-superconductor heterosystem. *Nat. Nanotechnol.* **13**, 560–565 (2018).
78. Yokouchi, T. et al. Pattern recognition with neuromorphic computing using magnetic field-induced dynamics of skyrmions. *Sci. Adv.* **8**, eabq5652 (2022).
79. Sun, Y. et al. Experimental demonstration of a skyrmion-enhanced strain-mediated physical reservoir computing system. *Nat. Commun.* **14**, 3434 (2023).
80. Thevenard, L. et al. Precessional magnetization switching by a surface acoustic wave. *Phys. Rev. B* **93**, 134430 (2016).
81. Liu, J. et al. Acoustic Reflectors for Anchor Loss Reduction of Thin Film Piezoelectric on Substrate Resonators. In 2021 IEEE MTT-S International Wireless Symposium (IWS) 1–3. <https://doi.org/10.1109/IWS52775.2021.9499583> (2021).
82. Zhou, X. et al. Fish Scale-shaped Acoustic Reflector Array for Quality Factor Enhancement of AlN-on-Silicon MEMS Resonator. In 2019 IEEE International Ultrasonics Symposium (IUS) 1720–1723. <https://doi.org/10.1109/ULTSYM.2019.8926038> (2019).
83. Zhang, J., Yu, W., Chen, X. & Xiao, J. A frequency-domain micromagnetic simulation module based on COMSOL Multiphysics. *AIP Adv.* **13**, 055108 (2023).

Acknowledgements

J.L. and Q.S. acknowledge the funding support from National Key R&D Program of China (Grants No.2021YFA1401500) and RGC General Research Fund (Grant No. 16303322). L.L. would like to thank JSPS for support through “Research Program for Young Scientists”(No. 23KJ0778). Y.O. acknowledge the support from The LANE Chair of Excellence, QSPIN project, at University Grenoble Alpes, and JSPS KAKENHI 19H05629.

Author contributions

L.L. and J. L. prepared figures and wrote the main manuscript text. All authors reviewed and edited the manuscript.

Competing interests

The authors declare no competing interests.

Additional information

Correspondence and requests for materials should be addressed to Yoshichika Otani.

Reprints and permissions information is available at <http://www.nature.com/reprints>

Publisher’s note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Open Access This article is licensed under a Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International License, which permits any non-commercial use, sharing, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if you modified the licensed material. You do not have permission under this licence to share adapted material derived from this article or parts of it. The images or other third party material in this article are included in the article’s Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article’s Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by-nc-nd/4.0/>.

© The Author(s) 2025, corrected publication 2025