



Ring-Opening of Oxiranes using Taeniolite-Supported Tris(β -Diketonato)Zirconium

Yessi Permana¹, Nobuyuki Ichikuni² & Shogo Shimazu²

¹Inorganic & Physical Chemistry Research Division, Institut Teknologi Bandung, Jl. Ganesha 10, Bandung, Jawa Barat 40132, Indonesia

²Department of Applied Chemistry and Biotechnology, Chiba University, 1-33 Yayoi, Inage, Chiba 263-8522, Japan
Email: yessi@chem.itb.ac.id

Abstract. A series of tris(β -diketonato)zirconium(IV) complexes was immobilized into a synthetic clay structure of Taeniolite by an ion-exchange method to generate organic/inorganic hybrid compounds. The hybrid compound served as a good catalyst for ring-opening reactions of methyl, ethyl, and dimethyl oxiranes with various alcohols to generate primary alkoxy alcohols in appreciable selectivity. This method describes a technique to immobilize cationic zirconium complexes without losing selectivity.

Keywords: β -alkoxyalcohols; oxiranes; ring-opening; Taeniolite; tris(β -diketonato)zirconium.

1 Introduction

β -Alkoxyalcohols are versatile precursors in organic synthesis and pharmaceuticals. The synthetic route for such compounds commonly proceeds via ring-opening of oxiranes (epoxides) [1-24] using traditional Lewis acids such as Cu(BF₄)₂ [2,21], Sn(OTf)₂ [11], BF₃ [22], Sc(OTf)₃ [24], and traditional solid acids such as amberlyst-15 [10]. Modified Lewis acid complexes based on salen [5,12] and porphyrin [23] ligands have also been reported. Some heterogeneous catalysts such as zeolites [1,18], monmorillonite K-10 [4], silica gel [6], mesoporous aluminosilicate [9,12,14,15,20], CuO/SiO₂ [19], and sulphated yttria-zirconia [25] have been reported as catalysts in the ring-opening of oxiranes. An alternative reaction method using a microwave technique has also been examined [13], even though such a method still experiences difficulties in scale-up processes. In continuation of our research on oxirane ring-opening reactions [3,7,8] we report herein a new methodology for oxirane ring-opening using clay-supported Zr(IV) diketonates. The clay selected as a host was lithium Taeniolite, denoted as Li-TN [26]. Lewis acidity at the metal center in the complex was improved by utilization of phenyl and fluoro diketone ligands and was observed from its homogeneous state [7,8]. We have previously discussed an immobilization effect of a zirconium complex into clays [3,8] and observed the enhancement in catalytic activities likely due to a desolvation

Received December 4th, 2011, Revised August 24th, 2012, Accepted for publication August 29th, 2012
Copyright © 2012 Published by LPPM ITB, ISSN: 1978-3043, DOI: 10.5614/itbj.sci.2012.44.3.6

The **2b–d**/TN catalysts were prepared in the following, slightly different manner. Lithium Taeniolite (cation exchange capacity, C.E.C, of 2.68 mmol Li⁺/g Taeniolite) of 0.1 g was swollen by deionized water (10 ml). Complexes **2b** and **2c** (50% of Taeniolite C.E.C) were dissolved in methanol (30 ml), and **2d** (50% of Taeniolite C.E.C) in acetone (30 ml). The solution was added to the

swollen Taeniolite, followed by stirring at 35 °C for 48 h and sonication for 1.5 h. Complex/Taeniolite compounds were characterized using PXRD (Bruker AXS MXP3V; Cu-K α) and FT-IR (JEOL JIR-7000). The amount of loaded complexes was examined by calculating the remained concentration of complexes in the filtrate after ion-exchange using a simple UV-Vis technique (Shimadzu UV-2101PC).

2.3 Ring-Opening Reactions of Oxiranes with Alcohols

Methyl, ethyl and dimethyl oxiranes (3.55 mmol), respectively, were added into methanol in excess (10 ml), containing 1 mol% of active species of **2a–d/TN** catalysts. In another series of reactions, methyl oxirane (3.55 mmol) was added to methanol, ethanol, *n*-propanol and *i*-propanol, respectively, in excess (10 ml), containing 1 mol% of active species of **2a/TN** catalyst. Reaction condition was 24 h, 60 °C and 1 atm. The products were analyzed by GC (Rt β -DEXsa column) and GC-MS (Rt β -DEXsm column).

3 Results and Discussion

3.1 Organic/Inorganic Hybrid Compounds

Tris(β -diketonato)zirconium(IV) complexes have been immobilized into clay structure by a facile ion exchange method (Scheme 1), affording a series of organic/inorganic hybrid compounds (**2a–d/TN**). The immobilization of the complexes was confirmed by FT-IR, powder XRD, and UV-Vis analysis. XRD patterns of the compounds (Figure 1) showed a shift of initial d_{001} reflection to lower angles, demonstrating an expansion of clay layers due to a complex immobilization. Unlike the **2a/TN** catalyst, the **2b–d/TN** catalysts revealed a relatively weaker shift towards lower angles despite their theoretically bigger molecular size than **2a**. Such a poor layer expansion will affect substrate diffusion adversely during a catalytic reaction. However, in contrast to **2a/TN**, good crystallinity was observed in the case of immobilized **2b–d** (Figure 1). This may indicate a fair distribution of complexes **2b–d** in interstitial layers of Taeniolite.

The amount of immobilized complexes on Taeniolite was measured by UV-Vis analysis of the filtrate after ion-exchange processes and provided in mmol/g of Taeniolite. Loading amounts and PXRD parameters of Taeniolite layers after immobilization are presented in Table 1.

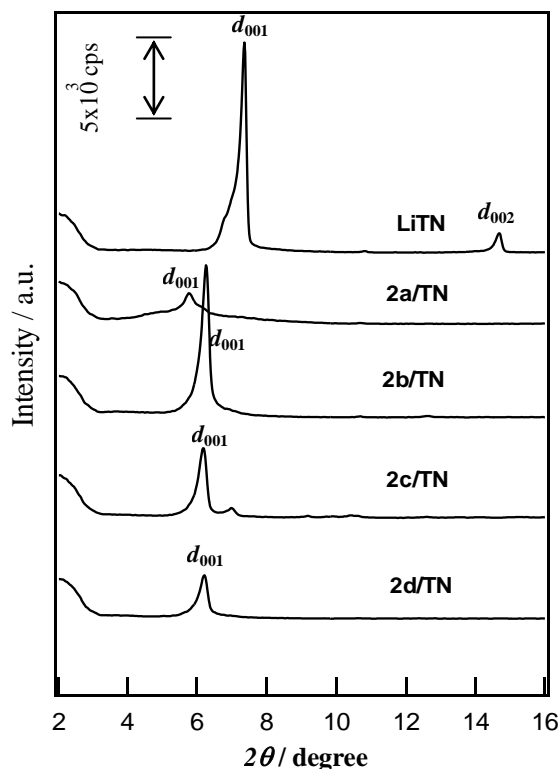



Figure 1 XRD patterns of initial clay (LiTN) and Zr/TN compounds.

Tabel 1 Loading amounts and PXRD parameters^a of Taeniolite-supported tris(β -diketonato)zirconium(IV) complexes.

Sample	L.A. ^b (mmol/g)	d_{001} (nm)	C.S. ^c (nm)
TN	-	1.21	0.25
2a/TN	1.12	1.53	0.57
2b/TN	1.10	1.41	0.45
2c/TN	1.02	1.44	0.48
2d/TN	1.10	1.42	0.46

^a Cu-K α . ^b Loading amount. ^c Clearance space = $d_{001} - 0.96$ nm (thickness of layer).

The loading amount data tell us that the complex substituted about 40% of the lithium host cations. Although no experiment intended to vary the feeding amount to see the influence on catalysis, all reactions conducted in this work employed the same amount of Zr complexes, i.e. 1 mol% of exchanged complexes, and thus a difference in activity due to a feeding amount parameter should be eliminated.

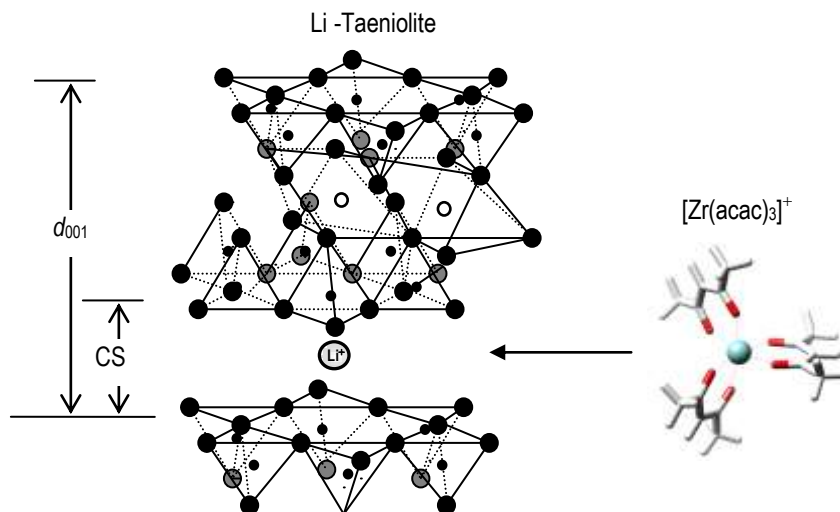

Scheme 2 Schematic illustration of an ion exchange process between exchangeable lithium cation and tris(acetylacetonato)zirconium guest cation (counter anion was omitted for simplification). Taeniolite structure is given as an idealized 2:1 (Tetrahedral–Octahedral–Tetrahedral) structure. C.S. = clearance space of interlayer. Large black balls are oxygen; large grey balls are fluorine; small black balls are silicon; small white balls are magnesium.

The appearance of characteristic bond vibrations of tris(β -diketonato)zirconium, i.e. $\nu\text{C}(\text{arom})\text{-H}$, $\nu\text{C}(\text{sp}^2)\text{-H}$, and $\nu\text{C=O}$, in IR spectra of Taeniolite supported complexes clearly confirmed the presence of the complexes on the Taeniolite structure (Figure 2). There are two possible causes for the complexes' immobilization on clay. First, the complexes were immobilized in their salt forms (cations and anions were being incorporated into clay layers), and second, only cations were immobilized through an ion-exchange process with exchangeable lithium cations. Confirmatory evidence that cationic tris(β -diketonato)zirconium complexes successfully exchanged lithium host cations was observed from vibration disappearances of Cl–O from counter anions (i.e. perchlorate anion) in the IR spectra, which should appear around 1080–1130 cm^{-1} (stretching vibration) and 620–640 cm^{-1} (bending vibration) in the original zirconium complex (Figure 2) [29].


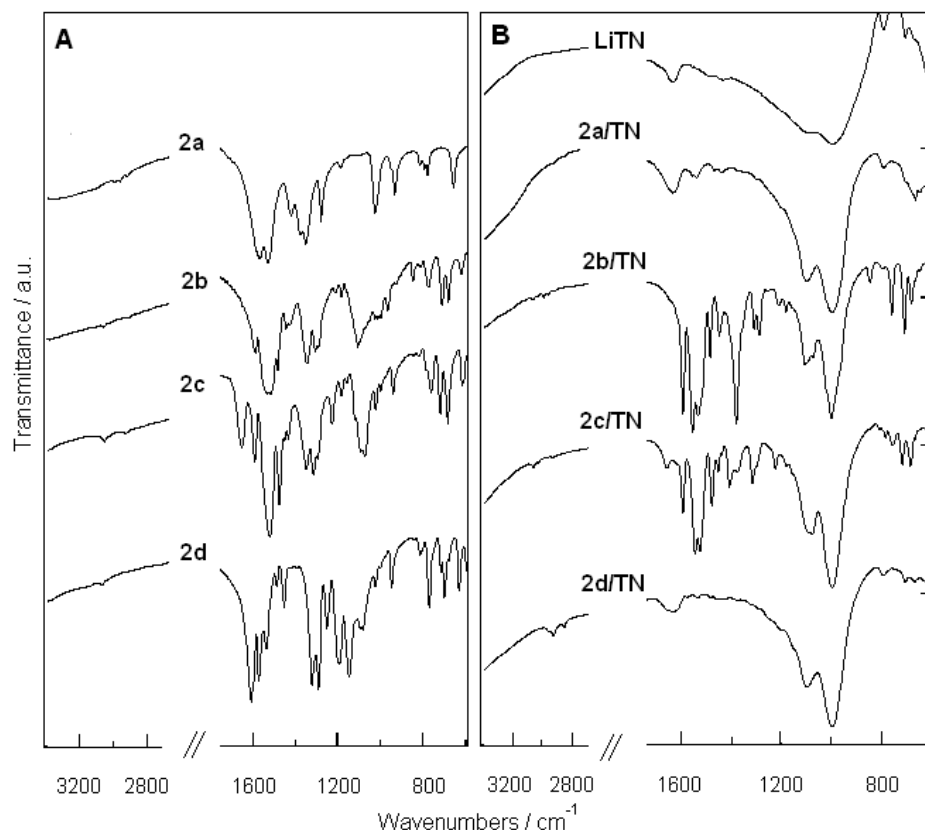


Figure 2 FT-IR spectra of (a) Zr-diketonates prior to immobilization (b) Taeniolite-supported Zr-diketonates. Vibrations were presented at selected wavenumbers for focused discussion (600–1800 and 2800–3200 cm^{-1}).

3.2 Ring-Opening of Oxiranes with Alcohols

Methyl, ethyl and dimethyl oxiranes were found to undergo smooth ring-opening with alcohols, affording primary and secondary alkoxyalcohols when they were catalyzed by Taeniolite-supported Zr β -diketonates (Table 2). The proposed mechanism of an $\text{S}_{\text{N}}1$ mechanism is given in Scheme 3. The complex is predicted to initially provide a vacant space for oxirane-activation by a partial dissociation of coordinated diketone ligands (Scheme 3). A competitive $\text{S}_{\text{N}}2$ mechanism (due to a weak oxirane-activation) is likely the reason for the formation of secondary alkoxyalcohols. A unique activity behavior of Taeniolite-supported Zr β -diketonates is given in Table 2. Entries 2–5 of the table describe an improvement trend in activity, while entries 6–9 describe a significant decline trend. Entries 10–13 describe a moderate decline trend. A factor to consider in rationalizing these phenomena is the clearance space


relative to the molecular size of complexes, as observed from the PXRD patterns of the catalysts (Figure 1).



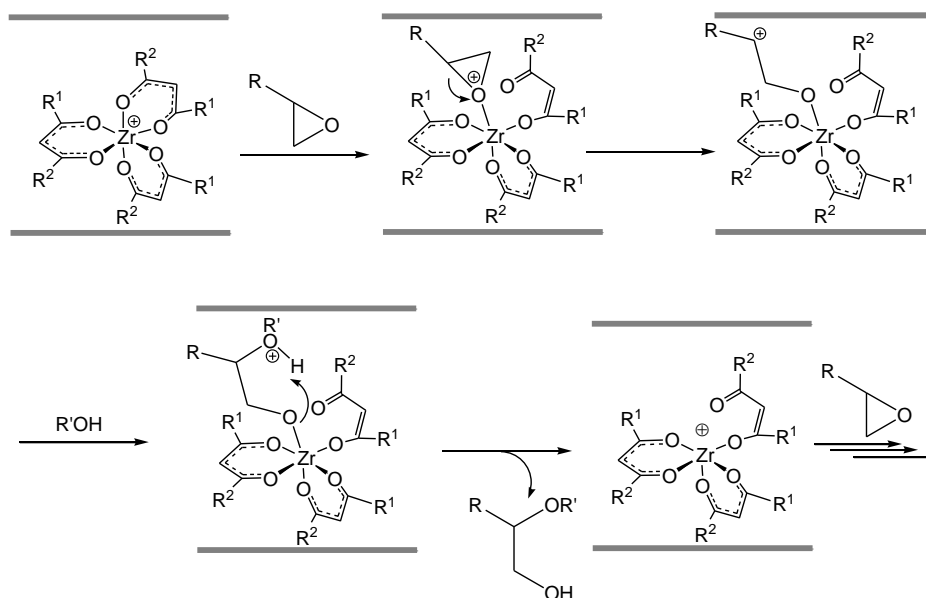


Scheme 3 Proposed mechanism of a ring-opening reaction of oxiranes with alcohols in S_N1 fashion to afford primary alkoxyalcohols. Counter anions from Taeniolite layers not shown for simplicity.

In entries 2–5, a relatively small size of methyl oxirane provides good accessibility for the substrate to diffuse into clay layers, even though some of the clay-supported zirconium complexes possess a relatively low clearance space. The rate-determining step in such a case is likely the substrate diffusion step. In entries 6–9, a relatively large size of ethyl oxirane provides poor accessibility for the substrate to diffuse into clay layers, unless the clearance space of the catalyst is considerably high, such as that on 2a/TN, which in fact demonstrates the highest activity in this series. In entries 10–13, we found that a significant decline trend due to the bulkiness of the substrate was not observed. This can be explained by the fact that the intermediate compound resulted from dimethyl oxirane activation is a tertiary carbocation, which is more stable than a secondary carbocation resulted from monoalkyl oxiranes, such as methyl and ethyl oxiranes. Such an intermediate stabilization provides a longer lifetime of the intermediate to react with a nucleophile. Supportive evidence for this suggestion can be found in the higher selectivity of the primary isomers for the ring-opening of dialkyl oxiranes (Table 2, entries 10–13).


Table 2 Synthesis of primary methoxyalcohols (**3**) promoted by Taeniolite-supported tris(β -diketonato)zirconium(IV) in comparison with their homogeneous counterparts (given in parentheses).

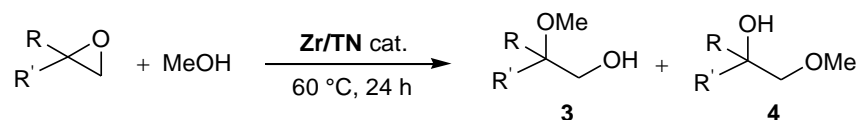

Entry	Oxiranes	Cat.	Conversion ^a / %		Selectivity ^b (3) / %	
1		Li/TN	24		20	
2		2a /TN	>99	(41)	58	(34)
3		2b /TN	100	(93)	56	(46)
4		2c /TN	100	(>99)	52	(52)
5		2d /TN	100	(100)	39	(52)
6		2a /TN	98	(9)	47	(24)
7		2b /TN	60	(99)	47	(45)
8		2c /TN	17	(>99)	31	(45)
9		2d /TN	18	(>99)	46	(45)
10		2a /TN	78	(66)	>99	(87)
11		2b /TN	91	(93)	100	(>99)
12		2c /TN	55	(100)	>99	(100)
13		2d /TN	69	(>99)	96	(100)

^a Conversion was calculated by GC. ^b Selectivity was confirmed by GC-MS.

We have seen the effect of alcohol nucleophiles on the catalysis of oxirane ring-opening using homogeneous Zr(IV) in one of our previous reports [7]. Here we have attempted to investigate the same effect when the reactions were catalyzed by immobilized Zr(IV) complexes. The reactions taken as models were the ring-opening reactions of methyl oxirane with methanol, ethanol, *n*-propanol, and *i*-propanol, which were catalyzed by the **2a**/TN catalyst. The catalytic data of these reactions are given in Table 3. The data show that the ring-opening reaction of methyl oxirane was independent of the type of alcohol when **2a**/TN was employed in the reaction. This was likely due to a desolvation property inside the Taeniolite layers, which consequently enhanced the Lewis acidity of the complex, as it was poorly solvated [3,27,28]. Such a property is uniquely important because the same reaction with bulky nucleophiles demonstrates a considerably lower activity when catalyzed by the homogeneous counterparts (Table 3, entry 4).

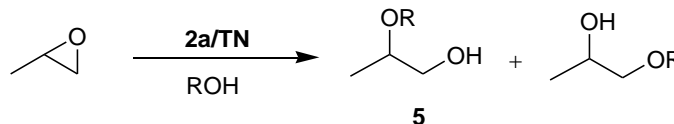Table 3 Ring-opening of methyl oxirane with various alcohols using the **2a/TN** catalyst in comparison with **2a** (given in parentheses).

Entry	Alcohol	Conversion ^a / %	Selectivity ^b (5) / %
1	MeOH	>99 (41)	58 (34)
2	EtOH	>99 (80)	42 (17)
3	<i>n</i> -PrOH	97 (15)	52 (24)
4	<i>i</i> -PrOH	98 (6)	43 (30)

^a Conversion was calculated by GC. ^b Selectivity was confirmed by GC-MS. Reaction conditions were 60 °C, 1 atm, 24 h.

4 Conclusion

A series of organic/inorganic compounds prepared by immobilization of tris(β -diketonato)zirconium(IV) complexes into Taeniolite has been synthesized. The compound serves as a good catalyst for the ring-opening reactions of methyl, ethyl, and dimethyl oxiranes with various alcohols to generate primary alkoxy alcohols in appreciable selectivity. While bulky nucleophiles proceed in a very low activity of oxirane ring-opening in a homogeneous state, such nucleophiles show a significantly higher activity when the zirconium active species is immobilized into Taeniolite.

Acknowledgements

YP acknowledges Riset KK ITB, IMHERE-ITB and Hibah Kerma LN DIKTI for partial support of the work.

References

- [1] Takeuchi, H., Kitajima, K., Yamamoto, Y. & Mizuno, K., *The Use of Proton-Exchanged X-Type Zeolite in Catalysing Ring-Opening Reactions of 2-Substituted Epoxides with Nucleophiles and Its Effect on Regioselectivity*, J. Chem. Soc., Perk. T. 2, **2**, pp. 199-203, 1993.
- [2] Barluenga, J., Vázquez-Villa, H., Ballesteros, A. & González, J.M., *Copper(II) Tetrafluoroborate Catalyzed Ring-Opening Reaction of Epoxides with Alcohols at Room Temperature*, Org. Lett., **4**, pp. 2817-2819, 2002.
- [3] Permana, Y., Shimazu, S., Ichikuni, N. & Uematsu, T., *Selective Synthesis of Primary Methoxypropanol Using Clay Supported Tris(2,4-*

- pentanedionato*)zirconium(IV), J. Mol. Catal. A-Chem., **221**, pp. 141-144, 2004.
- [4] Chakraborti, A.K., Kondaska, A. & Rudrawar, S., *Scope and Limitations of Montmorillonite K 10 Catalysed Opening of Epoxide Rings by Amines*, Tetrahedron, **60**, pp. 9085-9091, 2004.
- [5] Dooos, B.M.L., Geurts, W.A. & Jacobs, P.A., *Coordination of CrIII(Salen) on Functionalised Silica for Asymmetric Ring-Opening Reactions of Epoxides*, Catal. Lett., **97**, pp. 125-129, 2004.
- [6] Chakraborti, A.K., Rudrawar, S. & Kondaskar, A., *An Efficient Synthesis of 2-Amino Alcohols by Silica Gel Catalysed Opening of Epoxide Rings by Amines*, Org. Biomol. Chem., **2**, pp. 1277-1280, 2004.
- [7] Permana, Y., Shimazu, S., Ichikuni, N. & Uematsu, T., *Studies on Tris(B-Diketonato)Zirconium(IV); Syntheses, Characterization and Catalytic Activity for Ring-Opening of Oxirane*, Catal. Commun., **6**, pp. 426-430, 2005.
- [8] Shimazu, S., Hong Zou, Hara, T. & Ichikuni, N., *Regioselective Ring Opening Reactions of Oxiranes with Acrylic Acid by Clay Supported Zirconium β -Diketonate Catalysts*, J. Ion Exchange. A., **18**, pp. 584-589, 2007.
- [9] Robinson, M.W.C., Buckle, R., Mabbett, I., Grant, G.M. & Graham, A.E., *Mesoporous Aluminosilicate Promoted Alcoholysis of Epoxides*, Tetrahedron Lett., **48**, pp. 4723-4725, 2007.
- [10] Liu, Y.-H., Liu, Q.-S. & Zhang, Z.-H., *Amberlyst-15 As A New and Reusable Catalyst for Regioselective Ring-Opening Reactions of Epoxides to B-Alkoxy Alcohols*, J. Mol. Catal. A-Chem., **296**, pp. 42-46, 2008.
- [11] Mancilla, G., Femenía-Ríos, M., Macías-Sánchez, A.J. & Collado, I.G., *Sn(OTf)₂ Catalysed Regioselective Styrene Oxide Ring-Opening with Aromatic Amines*, Tetrahedron, **64**, pp. 11732-11737, 2008.
- [12] Guo, X.-F., Kim, Y.-S. & Kim, G.-J., *Chiral (Salen) Cobalt Complexes Encapsulated in Mesoporous MFI as an Enantioselective Catalyst for Asymmetric Ring-Opening of Terminal Epoxides*, Top. Catal., **52**, pp. 153-160, 2008.
- [13] Torborg, C., Hughes, D.D., Buckle, R., Robinson, M.W.C., Bagley, M.C., Graham, A.E., *Rapid Ring-Opening Reactions of Epoxides using Microwave Irradiation*, Synthetic Commun., **38**, pp. 205-211, 2008.
- [14] Robinson, M.W.C., Davies, A.M., Mabbett, I., Apperley D.C., Taylor, S.H., Graham, A.E., *Synthesis and Catalytic Activity of Nanoporous Aluminosilicate Materials*, J. Mol. Catal. A-Chem., **314**, pp. 10-14, 2009.
- [15] Robinson, M.W.C., Davies, A.M., Richard, B., Mabbett, I., Taylor, S.H., Graham, A.E., *Epoxide Ring-Opening and Meinwald Rearrangement Reactions of Epoxides Catalyzed by Mesoporous Aluminosilicates*, Org. Biomol. Chem., **7**, pp. 2559-2564, 2009.

- [16] Li, Y., Hao, H.-D. & Wu, Y., *Facile Ring-Opening of Oxiranes by H₂O₂ Catalyzed by Phosphomolybdic Acid*, Org. Lett., **11**, pp. 2691-2694, 2009.
- [17] Jafarpour, M., Rezaeifard, A. & Aliabadi, M., *An Environmentally Benign Catalytic Method for Efficient and Selective Nucleophilic Ring Opening of Oxiranes by Zirconium Tetrakis(dodecyl Sulfate)*, Helv. Chim. Acta, **93**, pp. 405-413, 2010.
- [18] Selvin, R., Selva Roselin, L., Praveen Kumar, K. & Arul, S., *Nanocrystalline Zeolite Beta: An Efficient Catalyst for The Regioselective Alcoholysis of Epichlorohydrin*, Sci. Adv. Mater., **2**, pp. 190-194, 2010.
- [19] Zaccheria, F., Santoro, F., Psaro, R. & Ravasio, N., *Cuo/Sio₂: A Simple And Efficient Solid Acid Catalyst For Epoxide Ring Opening*, Green Chem., **13**, pp. 545-548, 2011.
- [20] Das, S. & Asefa, T., *Epoxide Ring-Opening Reactions with Mesoporous Silica-Supported Fe(III) Catalysts*, ACS Catal., **1**, pp. 502-510, 2011.
- [21] Capes, A.S., Crossman, A.T., Webster, L.A., Ferguson, M. A.J. & Gilbert, I.H., *Investigation of Copper(II) Tetrafluoroborate Catalysed Epoxide Opening*, Tetrahedron Lett., **52**, pp. 7091-7094, 2011.
- [22] Izquierdo, J., Rodríguez, S. & González, F.V., *Regioselective Ring Opening and Isomerization Reactions of 3,4-Epoxyesters Catalyzed by Boron Trifluoride*, Org. Lett., **13**, pp. 3856-3859, 2011.
- [23] Venkatasubbaiah, K., Zhu, X., Kays, E., Hardcastle, K.I. & Jones, C.W., *Co(III)-Porphyrin-Mediated Highly Regioselective Ring-Opening of Terminal Epoxides with Alcohols and Phenols*, ACS Catal., **1**, pp. 489-492, 2011.
- [24] Hu, X., Gao, B., Chu, Y., Li, W., Liu, X., Lin, L. & Feng, X., *Enantioselective Synthesis of β -Pyrazole-Substituted Alcohols through an Asymmetric Ring-Opening Reaction of Meso-Epoxides*, Chem.-Eur. J., **18**, pp. 3473-3477, 2012.
- [25] Kahandal, S.S., Kale, S.R., Disale, S.T. & Jayaram, R.V., *Sulphated Yttria-Zirconia as A Regioselective Catalyst System for The Alcoholysis of Epoxides*, Catal. Sci. Technol., **2**, pp. 1493-1499, 2012.
- [26] Newman, A.C.D., *Chemistry of Clay and Clay Minerals*, Harlow, Longman, pp. 81-83, 1987.
- [27] Suzuki, N., Yamamoto, D., Anaguchi, N., Tsuchiya, H., Aoki, K. & Kanzaki, Y., *The Ion-Exchange Property of Some Layered Inorganic Materials with Potassium Ion, Rubidium Ion and Cesium Ion, and Selective Cesium Ion-Exchange of Synthetic Mica*, Bull. Chem. Soc. Jpn, **73**, pp. 2599-2603, 2000.
- [28] Suzuki, N., Itoh, M., Igarashi, M. & Kanzaki, Y., *Solid NMR Study of the Ion-Exchange Properties on γ -Titanium Phosphate with Alkali Metal Ions*, J. Ion Exchange, **14**, pp. 169-172, 2003.

- [29] Pejov, L. & Petruševski, V.M., *Fourier Transform Infrared Study of Perchlorate ($^{35}\text{ClO}_4^-$ and $^{37}\text{ClO}_4^-$) Anions Isomorphously Isolated in Potassium Permanganate Matrix. Vibrational Anharmonicity and Pseudo-Symmetry Effects*, J. Phys. Chem. Solids, **63**, pp. 1873-1881, 2002.