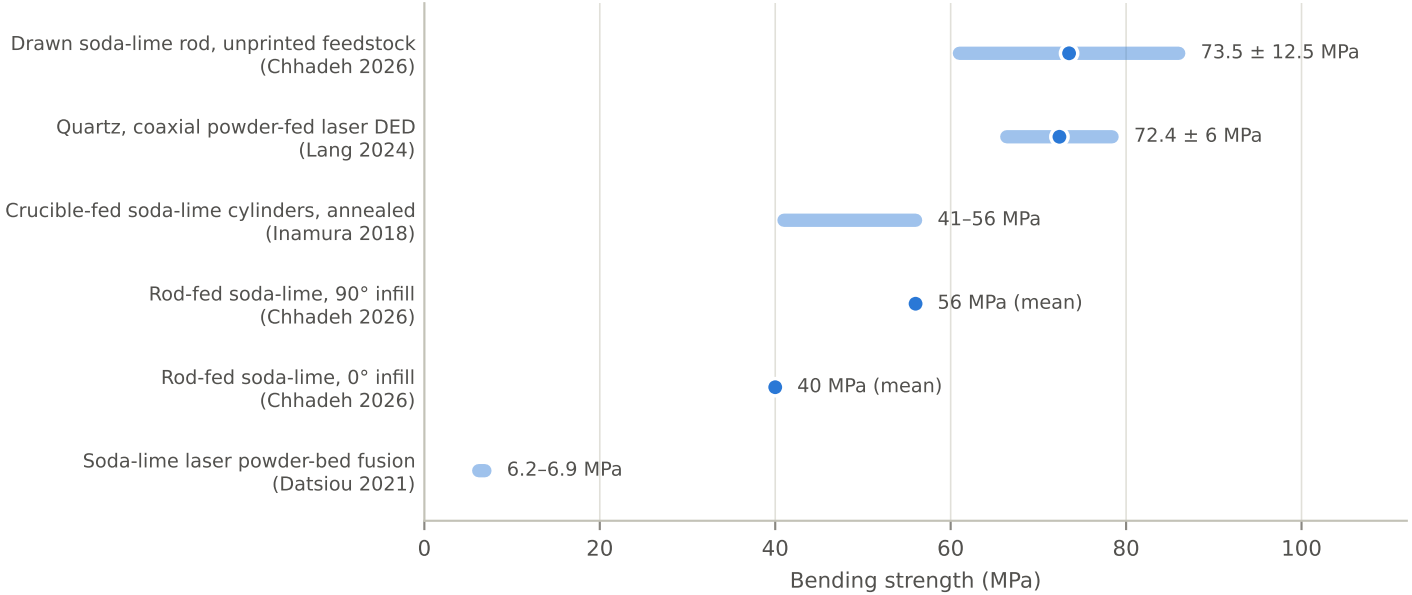
Drawn soda-lime rod, unprinted feedstock (Chhadeh 2026)
73.5 ± 12.5 MPa
Quartz, coaxial powder-fed laser DED (Lang 2024)
72.4 ± 6 MPa
Crucible-fed soda-lime cylinders, annealed (Inamura 2018)
41–56 MPa
Rod-fed soda-lime, 90° infill (Chhadeh 2026)
56 MPa (mean)
Rod-fed soda-lime, 0° infill (Chhadeh 2026)
40 MPa (mean)
Soda-lime laser powder-bed fusion (Datsiou 2021)
6.2–6.9 MPa
0
20
40
60
80
100
Bending strength (MPa)