Supplementary Material

Unraveling the underlying structural & transport mechanism of lithium-ion within Lithium bis(trifluoromethanesulfonyl)imide subjected to organic & inorganic matrix based Eutectogel

Shreyash P. Deshmukh [a], Rontu Das [a], Debashis Kundu [a]*

[a] Department of Chemical Engineering, Institute of Chemical Technology Marathwada Campus, Jalna, Maharashtra, 431203, India

* Corresponding author's email: d.kundu@marj.ictmumbai.edu.in

Table/Figure No.	Description	Page No.
Table S1.	Composition of Silica Gel and β – PVDF-HFP based eutectogels.	S3
Table S2.	Number of atoms in different eutectogels with initial system details.	S4
Figure S1.	Total energy profile during NPT equilibration. (a) SiO_2 based system (b) PVDF-HFP based system	S5
Figure S2.	Density profile during NPT equilibration. (a) PVDF-HFP based system (b) SiO_2 based system	S6
Figure S3.	System volume profile during NPT equilibration. (a) SiO_2 based system (b) PVDF-HFP based system	S7
Figure S4.	The final structures of (a) silica gel based eutectogel (b) of β-PVDF-HFP based eutectogel after 15 ns of final production run.	S8
Figure S5.	The final structure of silica gel based eutectogel after (a) initial system, (b) 5 ns, (c) 10 ns, and (d) 15 ns.	S9
Figure S6.	The final structure of β-PVDF-HFP based eutectogel after (a) initial system, (b) 5 ns, (c) 10 ns, and (d) 15 ns.	S10
Figure S7.	RDF of (a) Si – N (NMAC), (b) Si – O (NMAC), (c) Si – N (LiTFSI), (d) Si – O (LiTFSI), e) Si – F (LiTFSI), and f) Li – O (Silica gel).	S11
Figure S8.	RDF of the oxygen atom to lithium-ion in LITFSI (a) 0-	S13

	11.20ns (b) 11.21-15.00 ns. I. Schematic representation of oxygen moiety of silica gel and lithium ion of LITFSI	
Table S3.	Radial distribution Function and Coordination number of silica gel based eutectogel.	S14
Figure S9.	RDF of (a) H(NMAC) – N(TFSI), (b) H(NMAC) – O(TFSI), (c) H(NMAC) – F(TFSI), (d) H(NMAC) – F1(PVDF), (e) H(NMAC) – F2(PVDF), and (f) H(NMAC) – F3(PVDF).	S16
Table S4.	Radial Distribution Function and Coordination number of *β*-PVDF-HFP based eutectogel.	S18
Figure S10.	The MSD curve of TFSI ion in LiTFSI in silica gel based eutectogel. (a) ETG – 1, (b) ETG – 2, (c) ETG – 3, (d) ETG – 4, and (e) ETG – 5.	S20
Figure S11.	The MSD curve of O in NMAC in silica gel based eutectogel. (a) ETG – 1, (b) ETG – 2, (c) ETG – 3, (d) ETG – 4, and (e) ETG – 5.	S21
Figure S12.	The MSD curve of TFSI ion in LiTFSI in *β*-PVDF-HFP based eutectogel. (a) ETG – A, (b) ETG – B, (c) ETG – C, (d) ETG – D, and (e) ETG – E.	S22
Figure S13.	The MSD curve of O in NMAC in *β*-PVDF-HFP based eutectogel. (a) ETG – A, (b) ETG – B, (c) ETG – C, (d) ETG – D, and (e) ETG – E.	S23
Figure S14.	The MSD curve of F3 in *β*-PVDF-HFP in *β*-PVDF-HFP based eutectogel. (a) ETG – A, (b) ETG – B, (c) ETG – C, (d) ETG – D, and (e) ETG – E.	S24
Table S5.	MSD value of silica gel based eutectogel.	S21
Table S6.	MSD value of *β*-PVDF-HFP based eutectogel.	S23

Table S1. Composition of Silica Gel and β – PVDF-HFP based eutectogels.

DES	Molar ratio			
	LiTFSI	NMAC	Silica gel	β-PVDF-HFP
ETG – 1	1	4	0.069	0
ETG – 2	1	4	0.052	0
ETG – 3	1	4	0.042	0
ETG – 4	1	4	0.034	0
ETG – 5	1	4	0.029	0
ETG – A	1	4	0	1
ETG – B	1	4	0	2
ETG – C	1	4	0	3
ETG – D	1	4	0	4
ETG – E	1	4	0	5

Table S2. Number of atoms in different eutectogels with initial system details.

DES	Number of atoms				Total number of atoms	Initial box geometry (nm^3)	Final box geometry (nm^3)	Final density ($Kg.m^{-3}$)
	LiTFSI	NMAC	Silica gel	β-PVDF-HFP				
ETG – 1	7072	21216	1767	0	30055			1322.05
ETG – 2	7184	21552	1368	0	30104			1316.77
ETG – 3	7248	21720	1083	0	30051			1306.28
ETG – 4	7280	21840	912	0	30032			1300.36
ETG – 5	7312	21936	798	0	30046			1302.74
ETG – A	2384	7152	0	20413	29949			1570.74
ETG – B	1424	4272	0	24386	30082			1573.70
ETG – C	1008	3024	0	25893	29925			1586.74
ETG – D	784	2352	0	26852	29988			1591.02
ETG – E	640	1920	0	27400	29960			1589.21

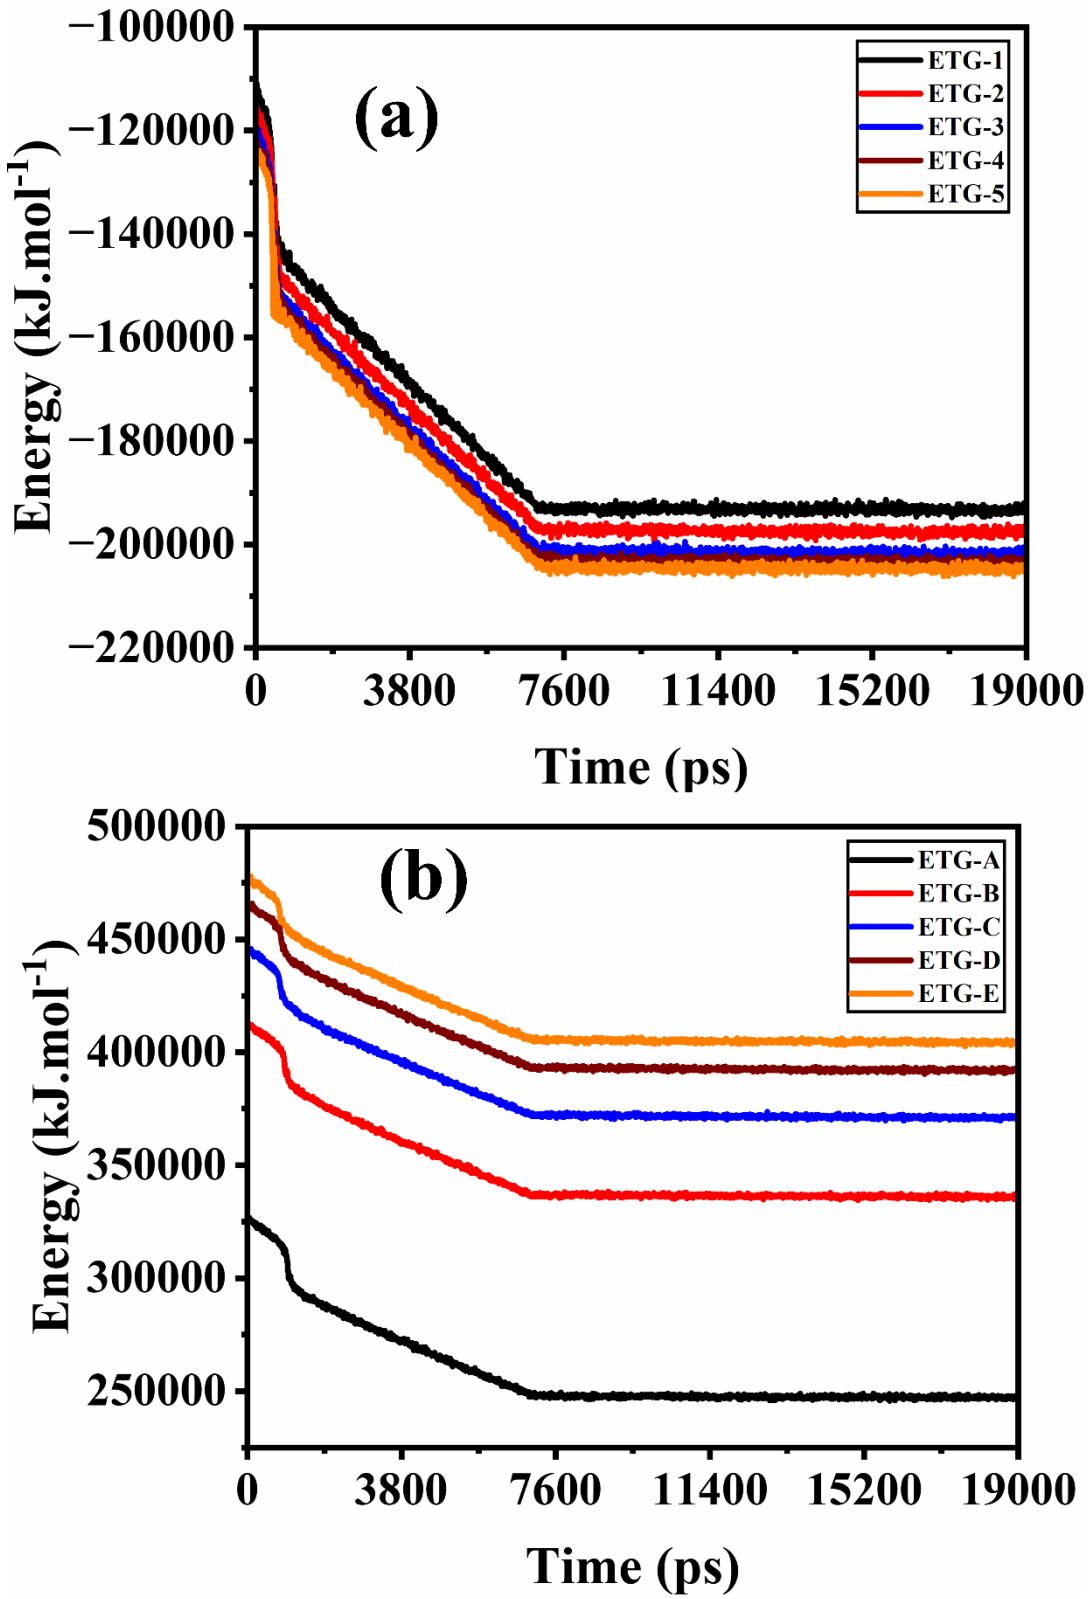


Figure S1. Total energy profile during NPT equilibration. (a) SiO_2 based system (b) PVDF-HFP based system

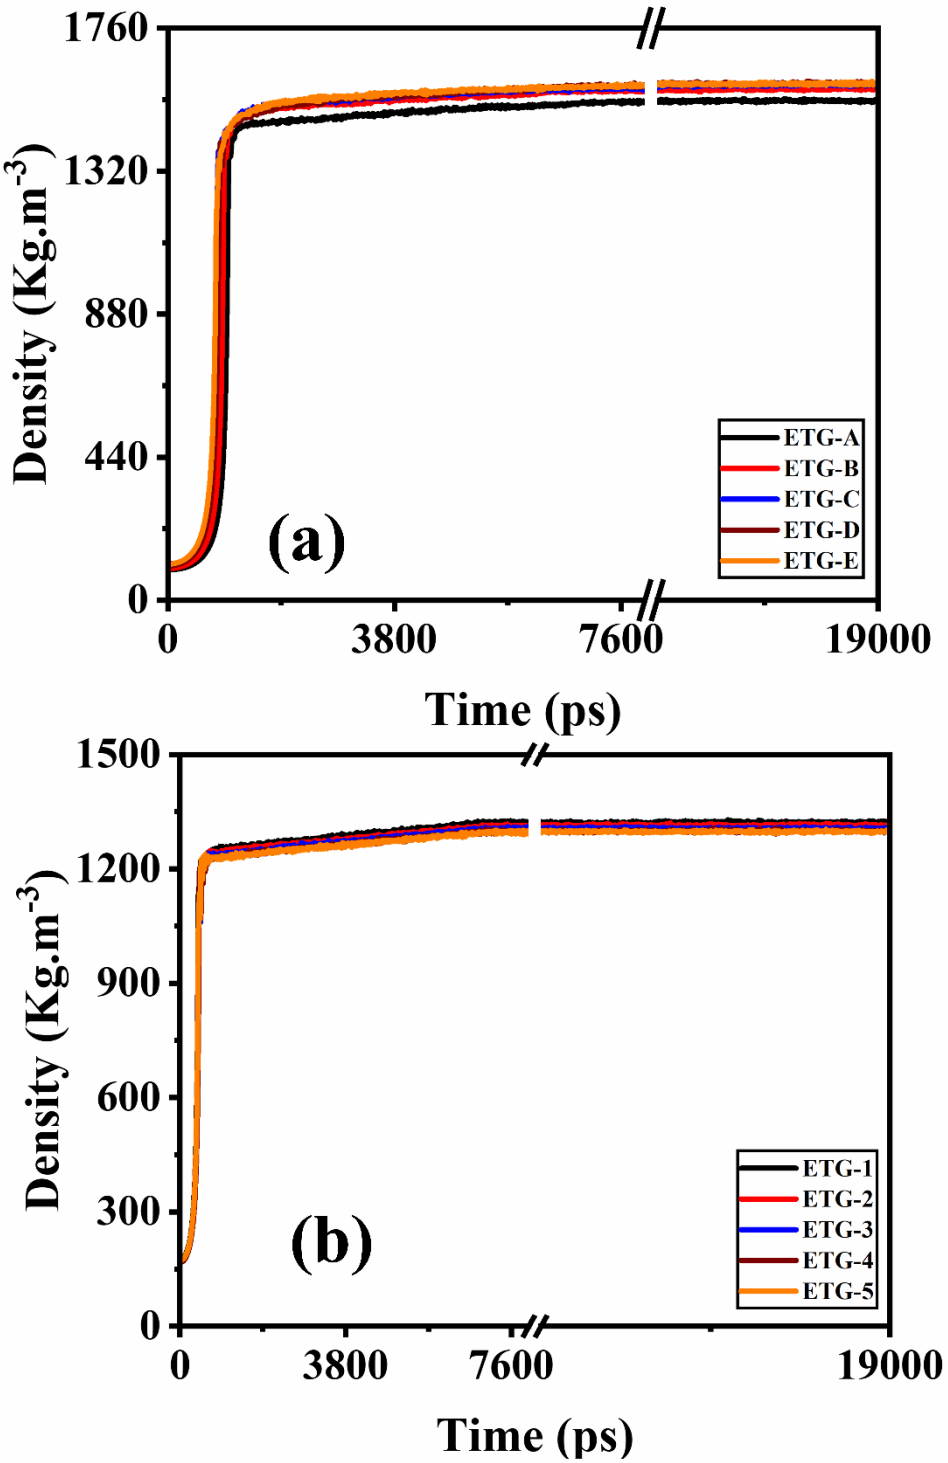


Figure S2. Density profile during NPT equilibration. (a) PVDF-HFP based system (b) SiO_2 based system

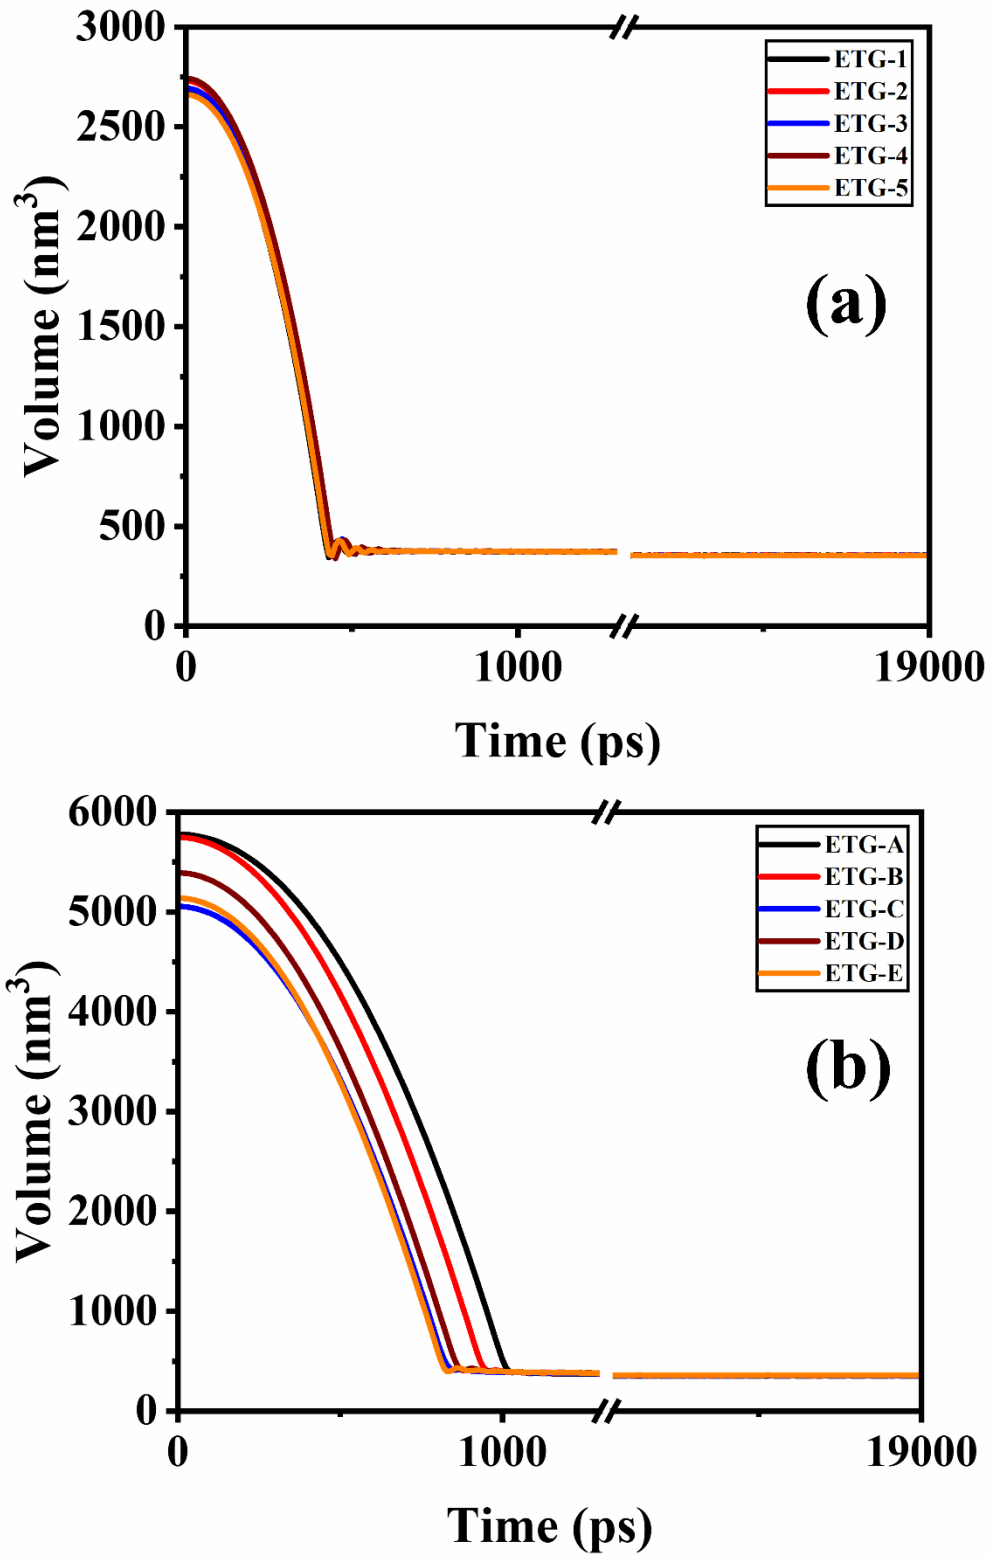


Figure S3. System volume profile during NPT equilibration. (a) SiO_2 based system (b) PVDF-HFP based system

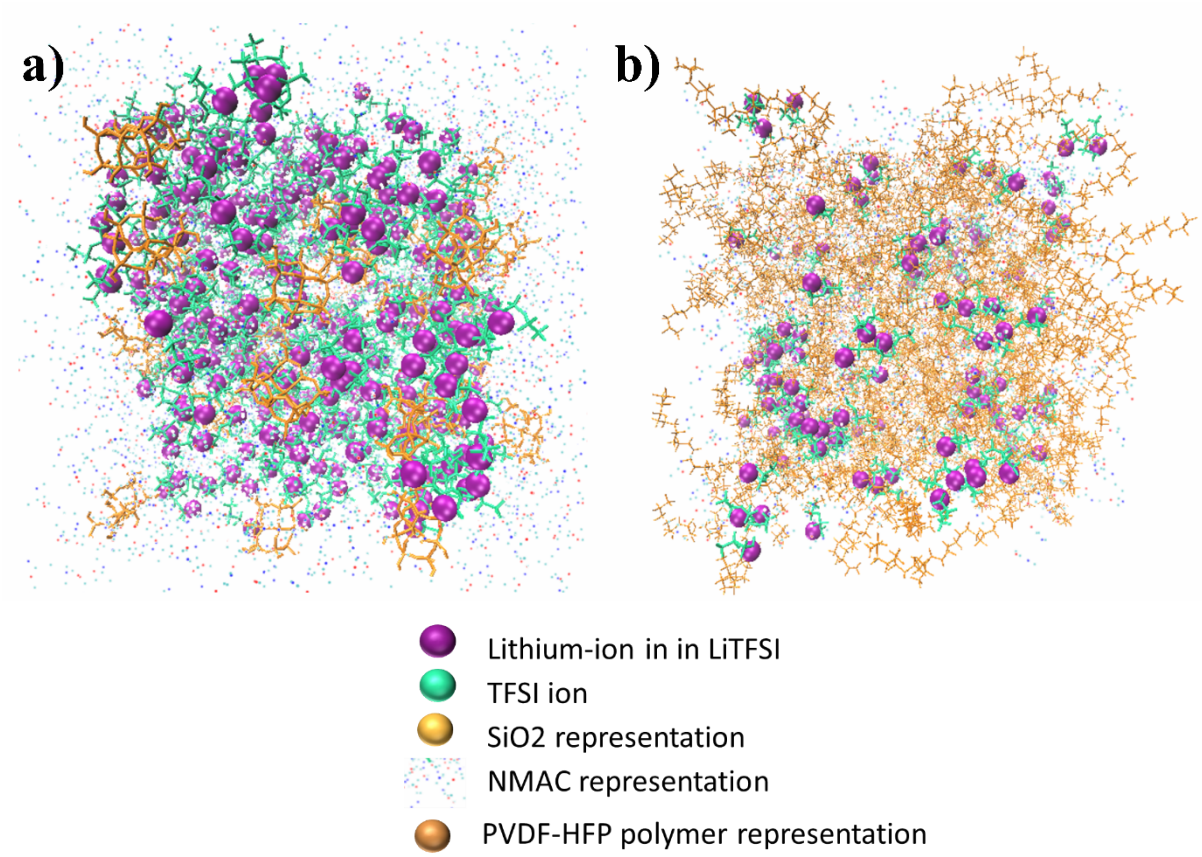


Figure S4. The final structures of (a) silica gel based eutectogel (b) of *β*-PVDF-HFP based eutectogel after 15 ns of final production run.

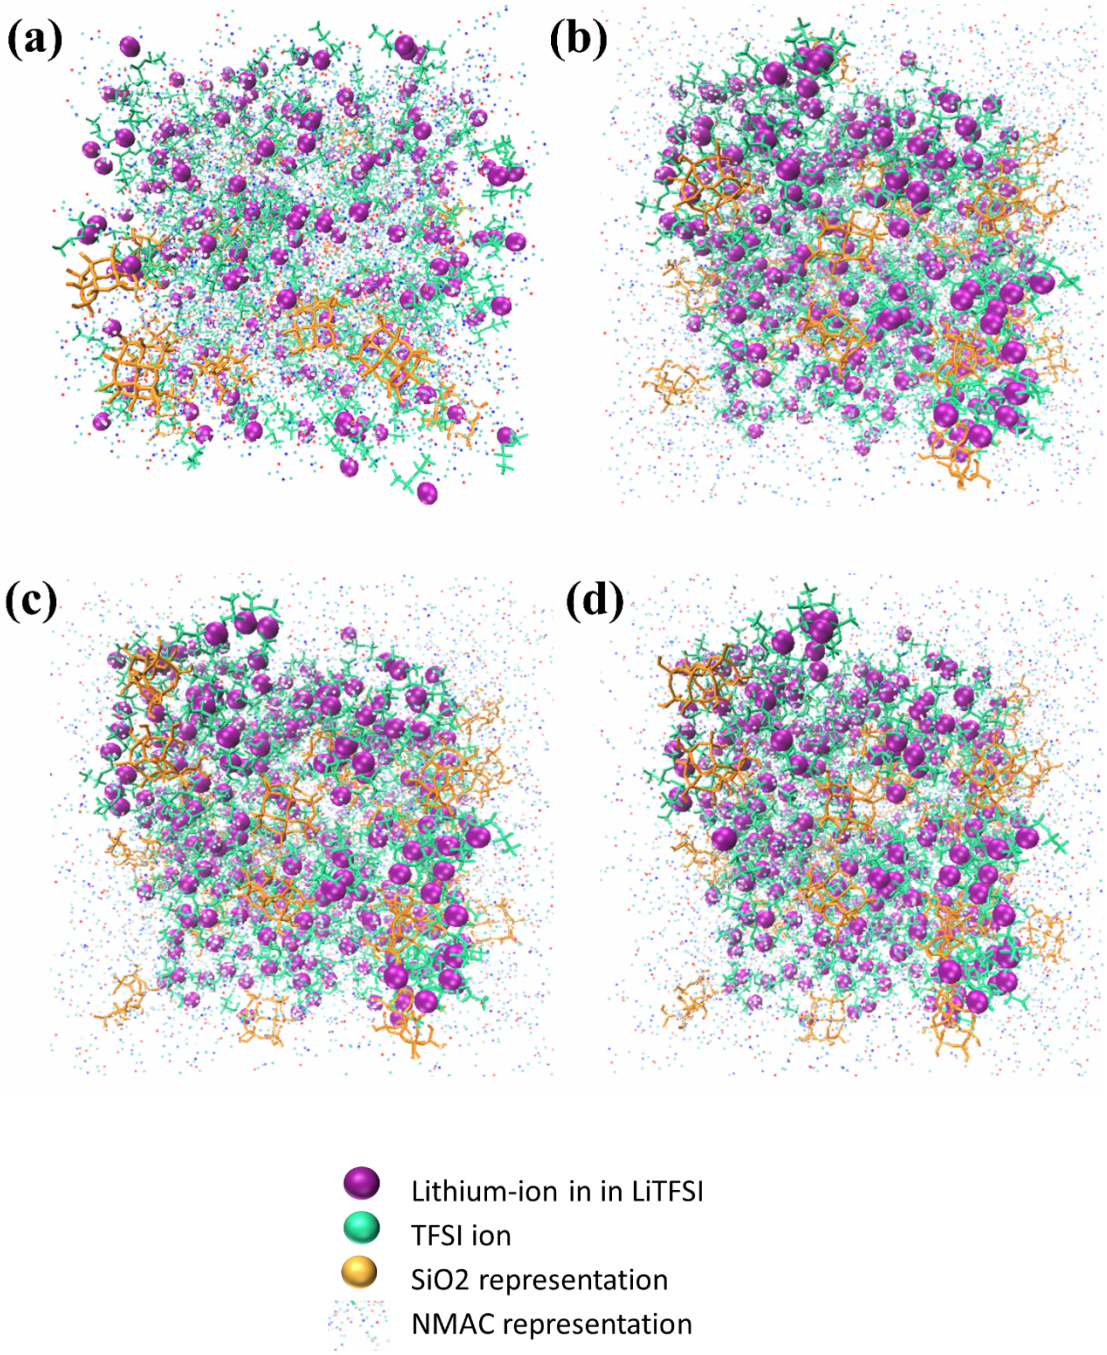


Figure S5. The final structure of silica gel based eutectogel after (a) initial system, (b) 5 ns, (c) 10 ns, and (d) 15 ns.

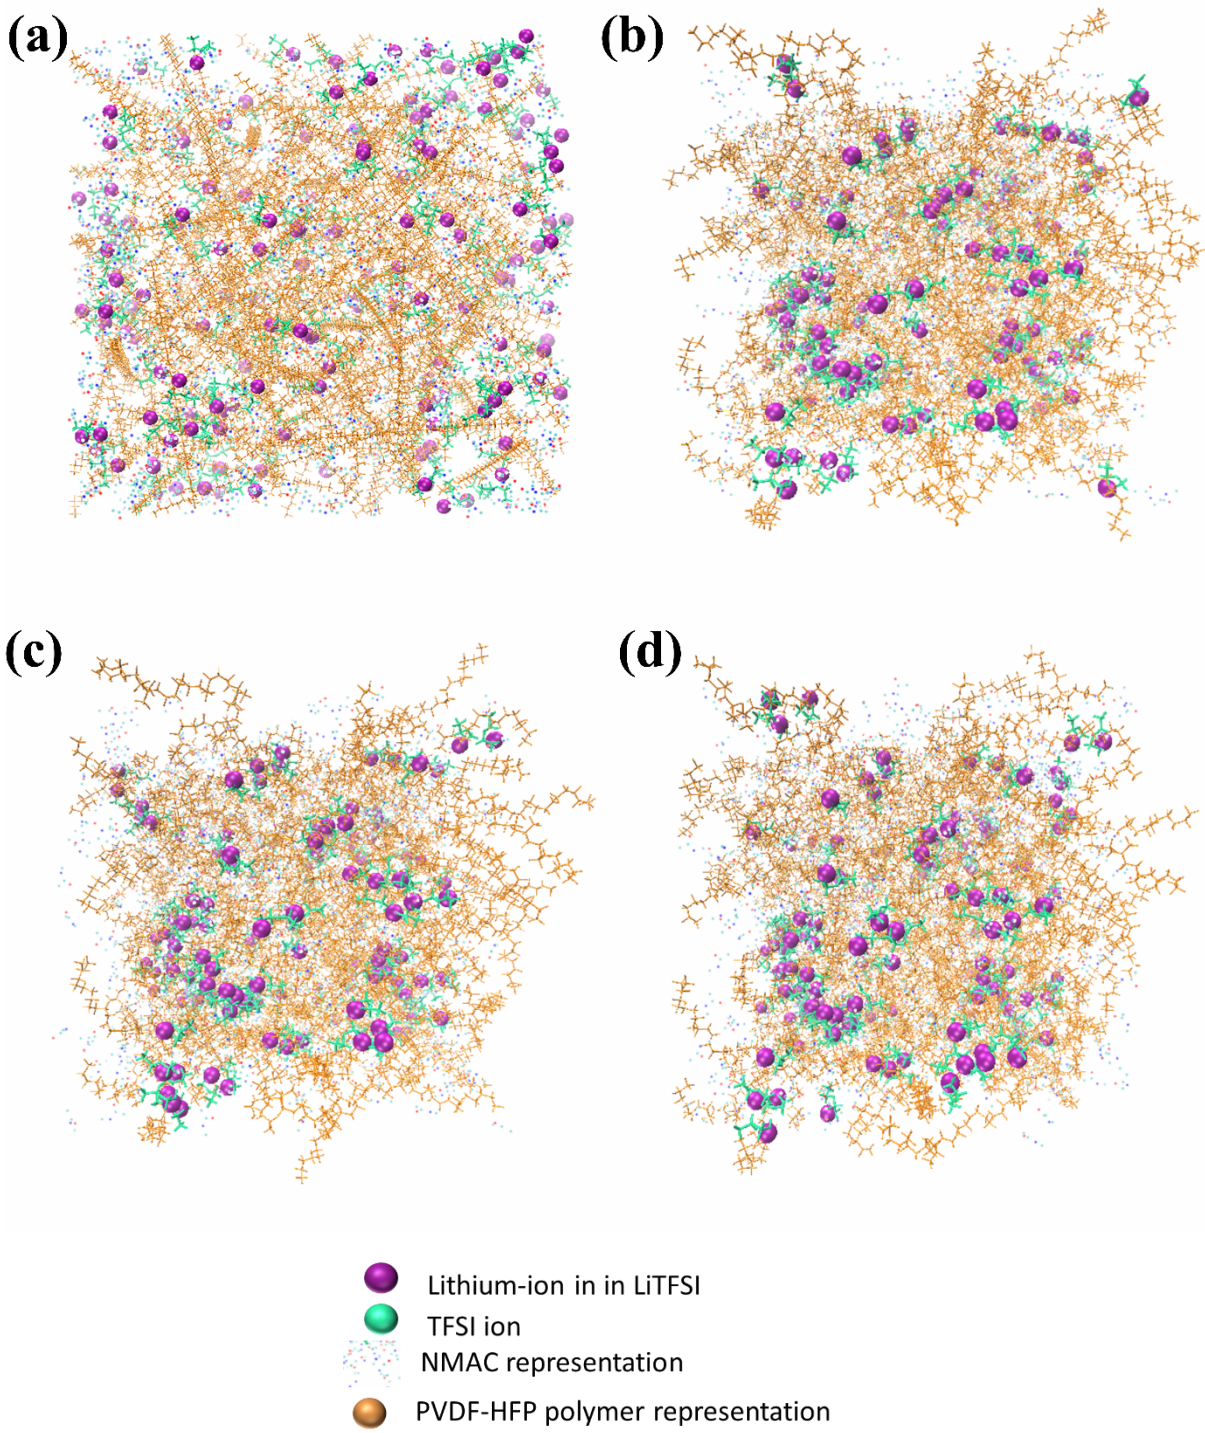
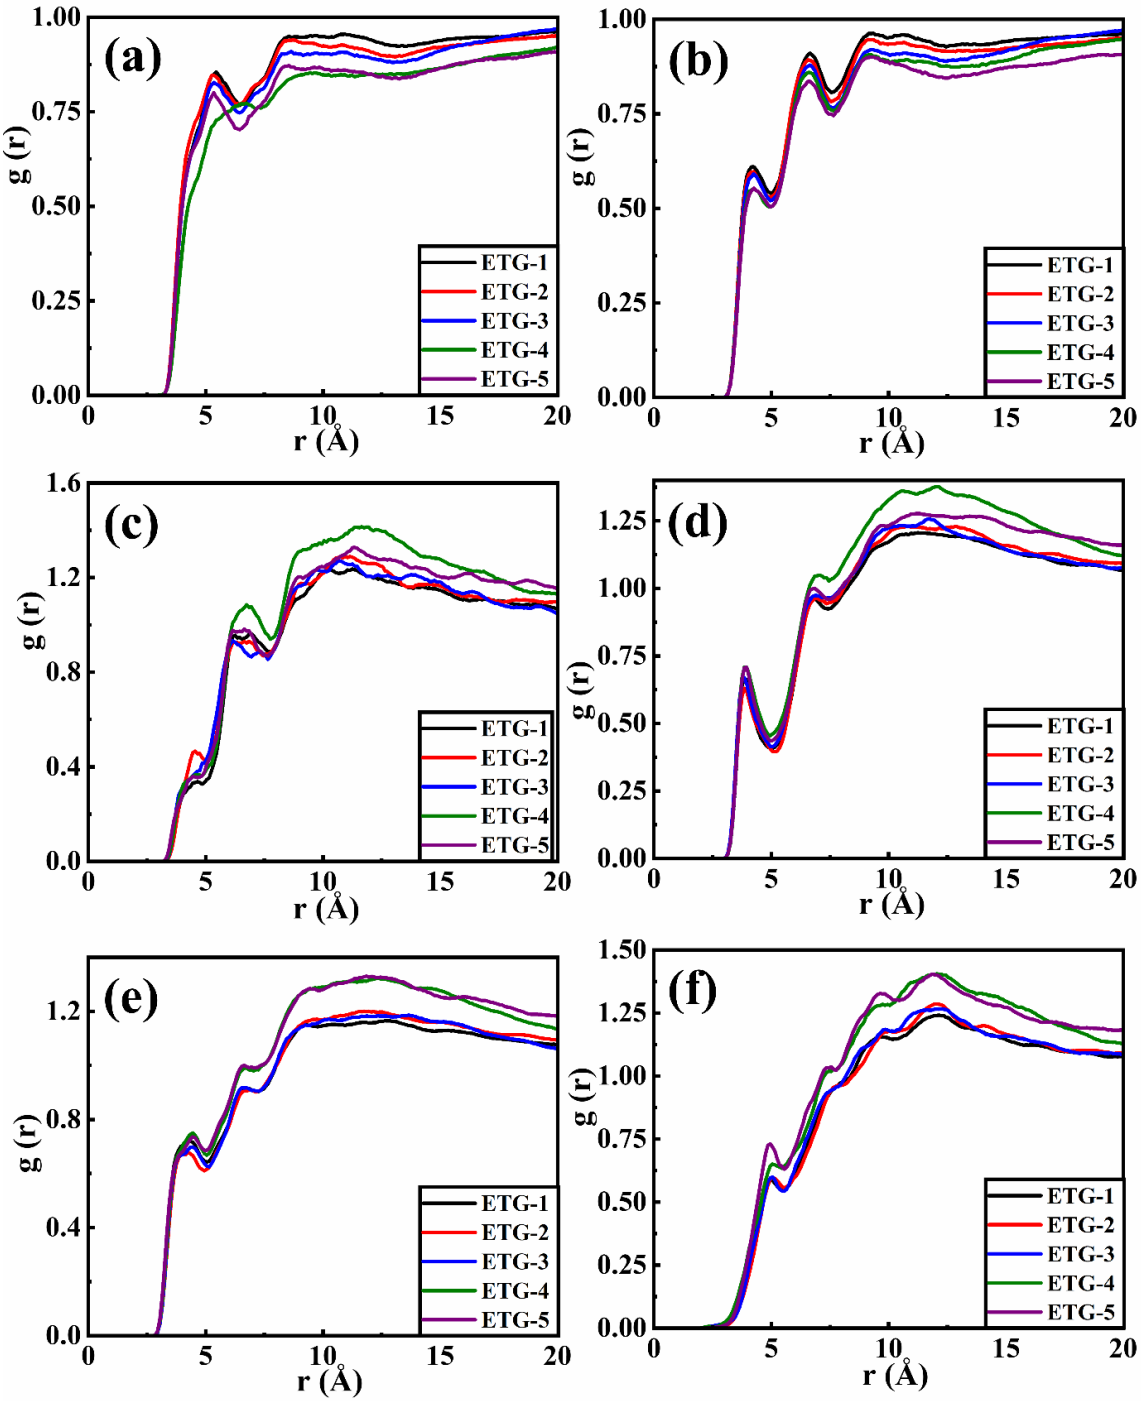


Figure S6. The final structure of *β*-PVDF-HFP based eutectogel after (a) initial system, (b) 5 ns, (c) 10 ns, and (d) 15 ns.


(a)
(b)
(c)
(d)
(e)
(f)
g (r)
r (Å)
ETG-1
ETG-2
ETG-3
ETG-4
ETG-5

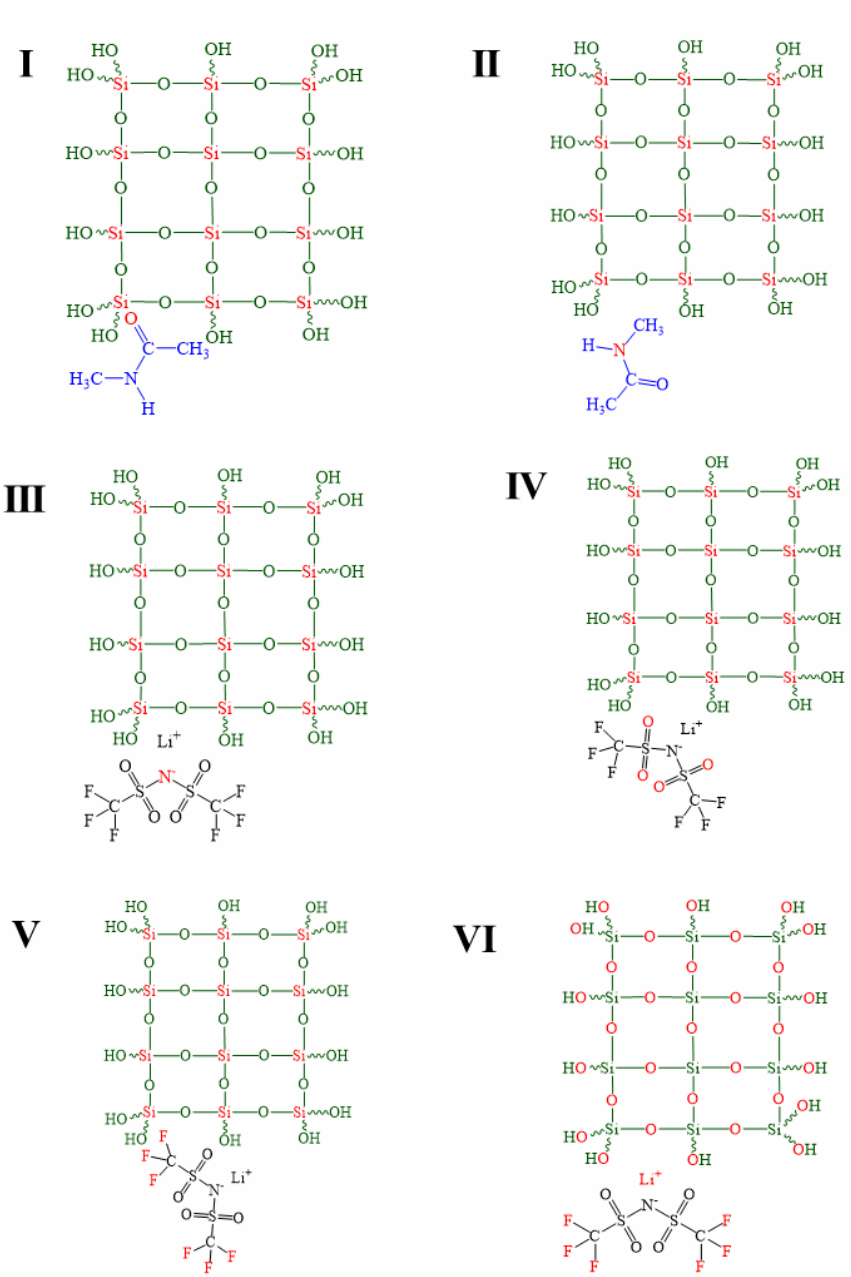


Figure S7. RDF of silica gel based eutectogel system (a) Si – N (NMAC), (b) Si – O (NMAC), (c) Si – N (LiTFSI), (d) Si – O (LiTFSI), e) Si – F (LiTFSI), and f) Li – O (Silica gel). I. schematic representation of O(NMAC) – Si(SiO_2) interaction, II. schematic representation of N(NMAC) – Si(SiO_2) interaction, III. schematic representation of N(LITFSI) – Si(SiO_2) interaction, IV. schematic representation of O(LITFSI) – Si(SiO_2) interaction, V. schematic representation of F(LITFSI) – Si(SiO_2) interaction, VI. schematic representation of F(LITFSI) – O(SiO_2) interaction.

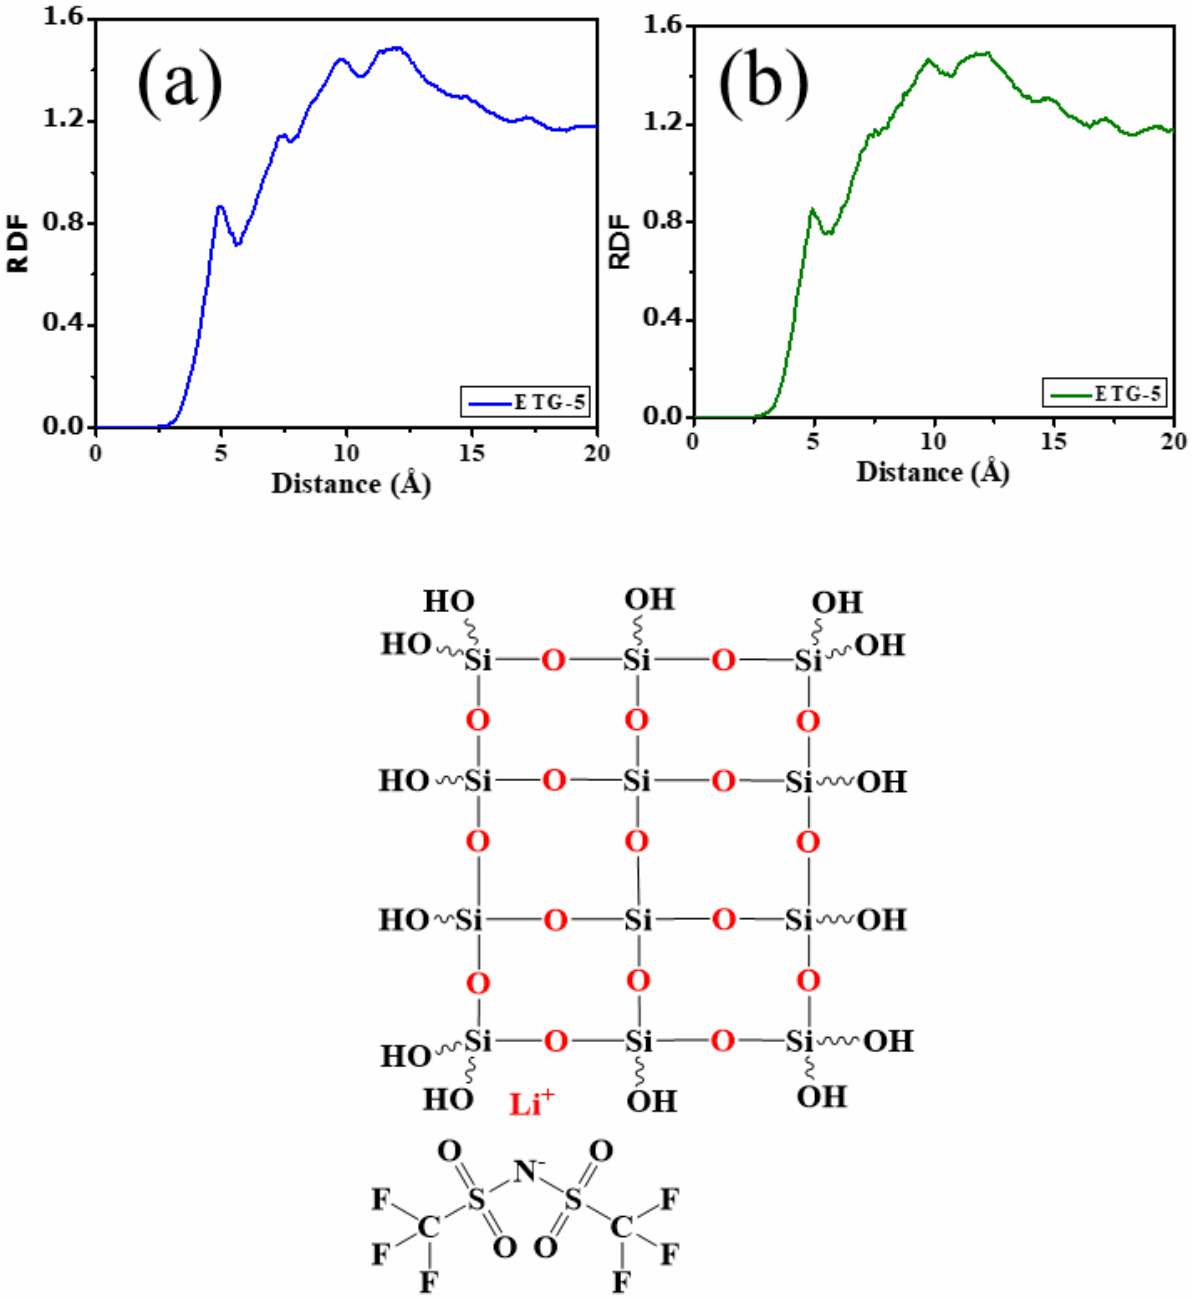
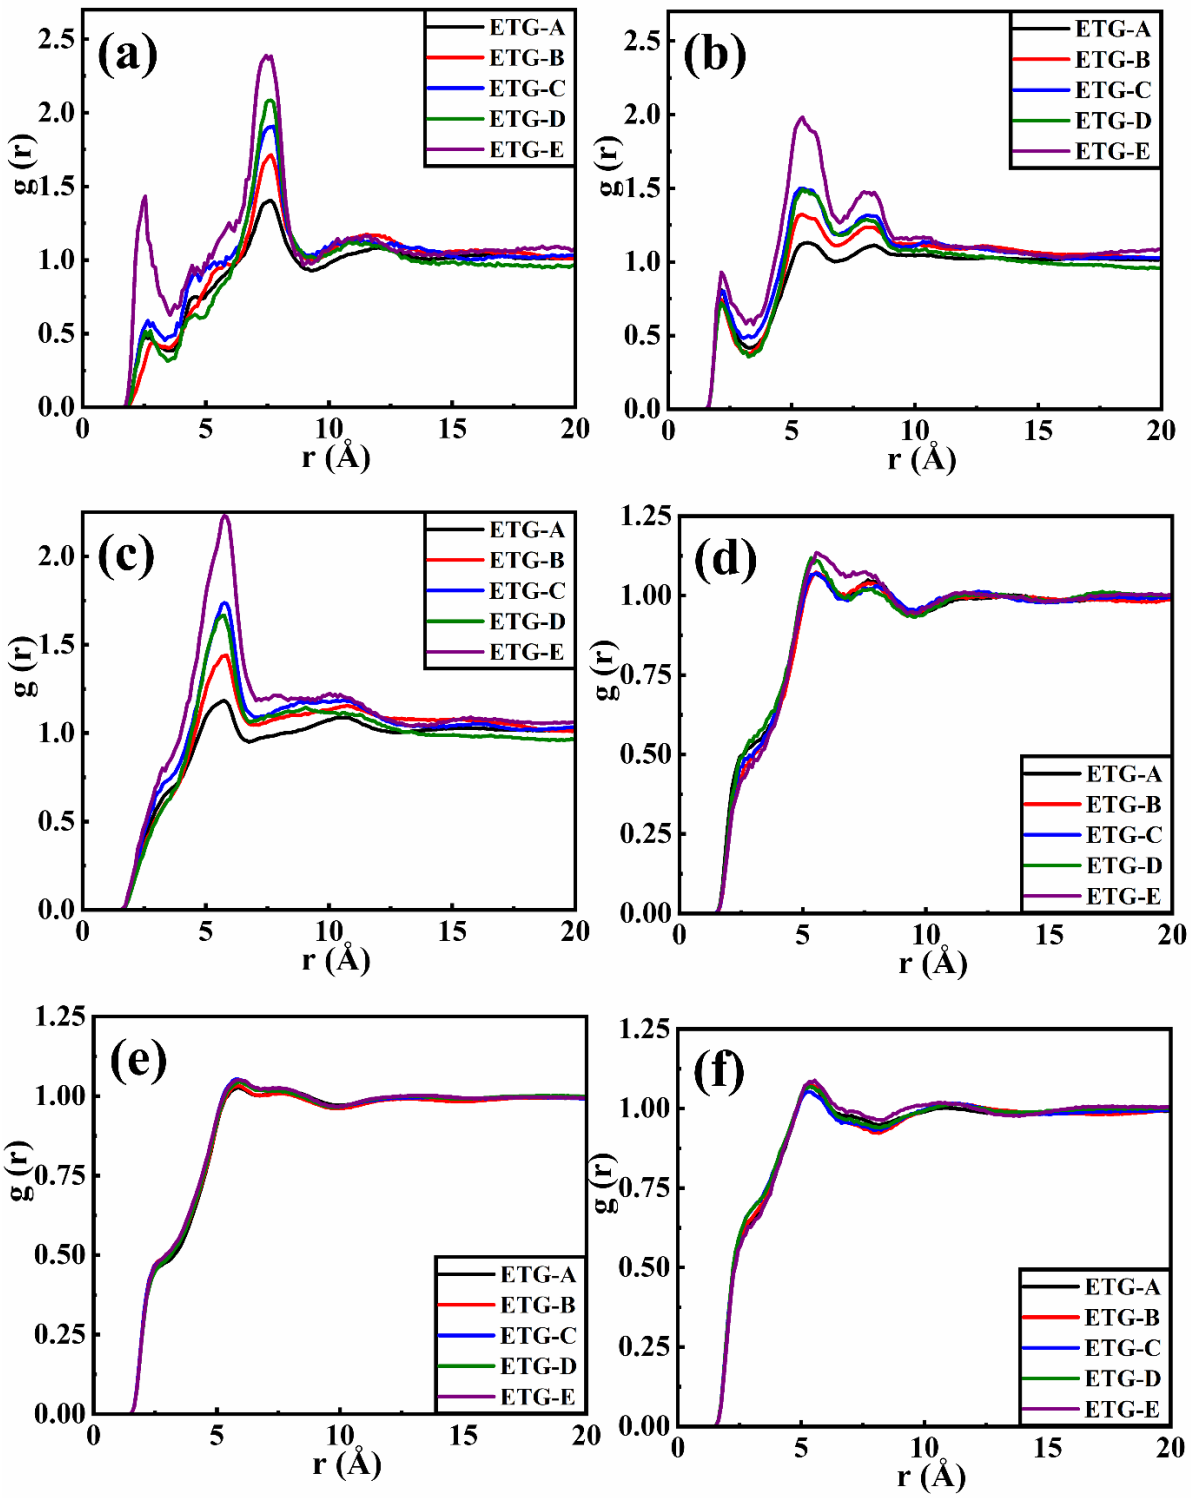


Figure S8. RDF of the oxygen atom to lithium-ion in LITFSI (a) 0-11.20ns (b) 11.21-15.00 ns. I. Schematic representation of oxygen moiety of silica gel and lithium ion of LITFSI

Table S3. Radial distribution Function and Coordination number of silica gel based eutectogel.

Components	Eutectogel	Distance (Å)	RDF	CN	Distance (Å)	RDF	CN	Distance (Å)	RDF	CN
Li-N (TFSI)	ETG – 1	2.65	5.35	0.41	3.65	3.29	1.45	4.85	0.54	2.17
	ETG – 2		4.78	0.39		3.01	1.44		0.66	2.20
	ETG – 3		4.82	0.41		2.81	1.46		0.62	2.20
	ETG – 4		4.98	0.43		2.80	1.45		0.60	2.18
	ETG – 5		2.47	0.20		1.68	0.73		0.54	1.19
Li-O (TFSI)	ETG – 1	2.85	0.85	3.35	4.15	1.07	1.93	-	-	-
	ETG – 2		0.86	3.37		1.10	1.91			
	ETG – 3		0.86	3.37		1.14	1.93			
	ETG – 4		0.91	3.38		1.18	1.90			
	ETG – 5		0.42	1..69		0.89	0.99			
Li-N (NMAC)	ETG – 1	7.45	0.73	5.18	-	-	-	-	-	-
	ETG – 2		0.71	5.05						
	ETG – 3		0.71	5.11						
	ETG – 4		0.71	5.09						
	ETG – 5		0.71	5.22						
Li-O (NMAC)	ETG – 1	3.25	0.06	0.15	8.35	0.72	8.38	-	-	-
	ETG – 2		0.06	0.15		0.70	8.26			
	ETG – 3		0.06	0.14		0.69	8.37			
	ETG – 4		0.06	0.14		0.69	8.26			
	ETG – 5		0.05	0.15		0.70	8.50			
Li-F	ETG – 1	1.75	0	1	2.55	0.03	3	-	-	-
	ETG – 2		0	1		0.03	3			
	ETG – 3		0	1		0.03	3			
	ETG – 4		0	1		0.03	3			
	ETG – 5		0	1		0.04	3			
Si-N (NMAC)	ETG – 1	6.45	0.77	3.55	-	-	-	-	-	-
	ETG – 2		0.77	3.65						

	ETG – 3		0.75	3.55							
	ETG – 4		0.75	3.22							
	ETG – 5		0.70	3.44							
Si-O (NMAC)	ETG – 1	4.95	0.54	0.97	7.55	0.81	6.23	-	-	-
	ETG – 2		0.53	0.96		0.78	6.22			
	ETG – 3		0.52	0.95		0.77	6.13			
	ETG – 4		0.50	0.91		0.76	6.05			
	ETG – 5		0.50	0.91		0.75	5.97			
Si-N (TFSI)	ETG – 1	4.85	0.33	0.11	7.75	0.89	1.65	-	-	-
	ETG – 2		0.43	0.14		0.88	1.69			
	ETG – 3		-	-		0.86	1.71			
	ETG – 4		-	-		0.94	1.86			
	ETG – 5		-	-		0.88	1.72			
Si-O (TFSI)	ETG – 1	5.05	0.41	0.96	7.45	0.92	5.76	-	-	-
	ETG – 2		0.39	0.97		0.95	5.83			
	ETG – 3		0.41	1.03		0.96	6.09			
	ETG – 4		0.46	1.10		1.03	6.49			
	ETG – 5		0.43	1.06		0.96	6.15			
Si-F (TFSI)	ETG – 1	5.05	0.64	2.04	7.25	0.90	8.77	-	-	-
	ETG – 2		0.61	1.94		0.91	8.69			
	ETG – 3		062	2.03		0.91	8.92			
	ETG – 4		0.66	2.16		0.98	9.61			
	ETG – 5		0.68	2.17		0.99	9.78			
Li-O (Silica gel)	ETG – 1	5.45	0.55	0.62	-	-	-	-	-	-
	ETG – 2		0.55	0.47						
	ETG – 3		0.54	0.38						
	ETG – 4		0.63	0.36						
	ETG – 5		0.64	0.34						


(a)
(b)
(c)
(d)
(e)
(f)
ETG-A
ETG-B
ETG-C
ETG-D
ETG-E
g (r)
r (Å)

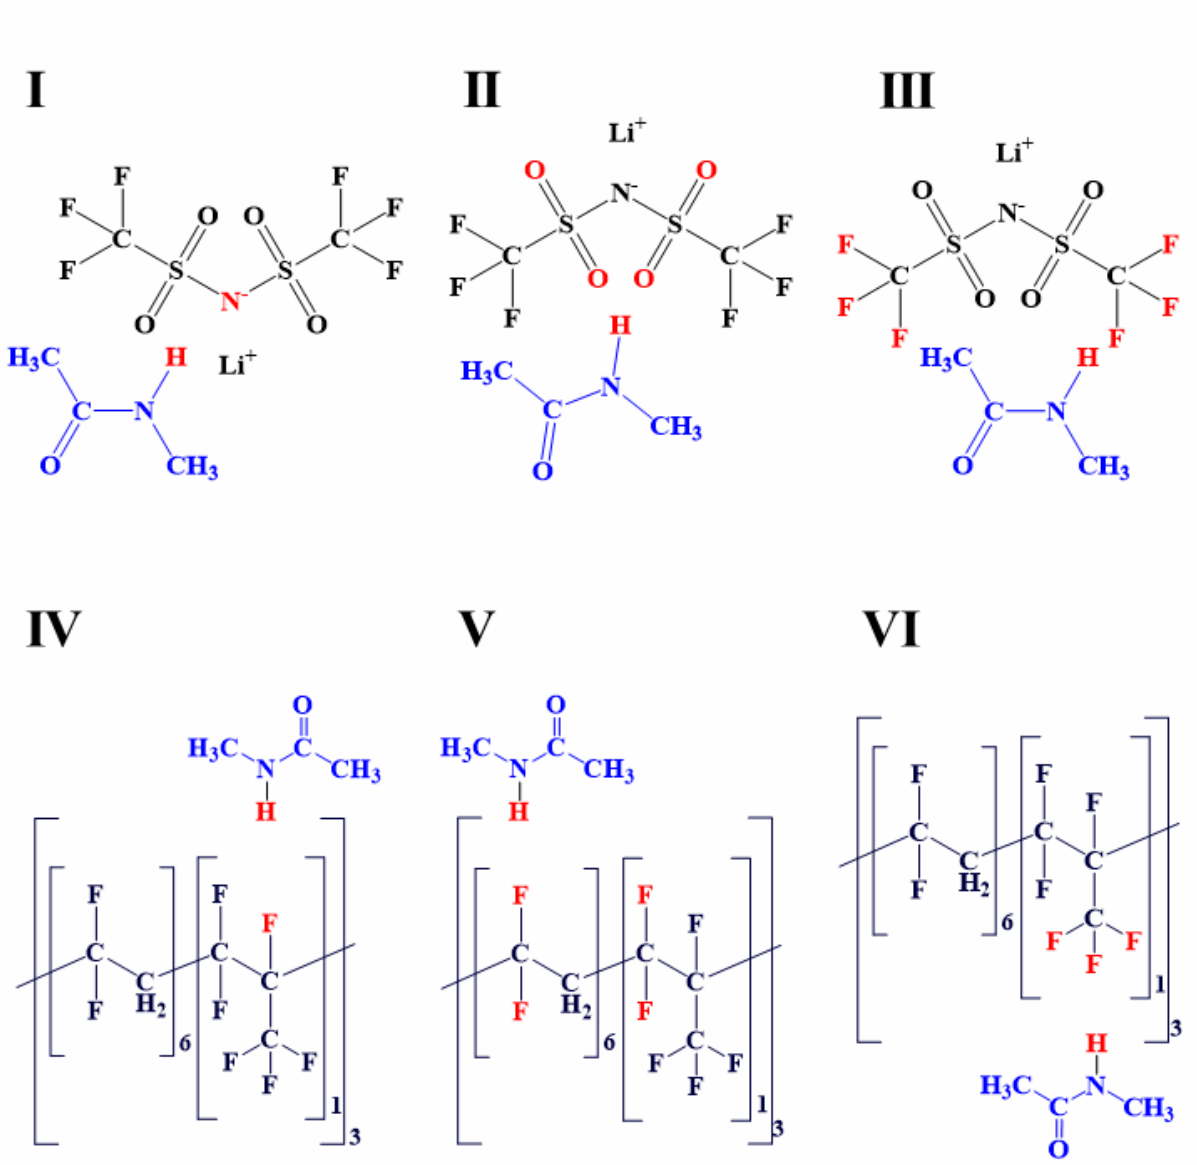


Figure S9. RDF of *β*-PVDF-HFP based eutectogel system (a) H(NMAC) – N(TFSI), (b) H(NMAC) – O(TFSI), (c) H(NMAC) – F(TFSI), (d) H(NMAC) – F1(PVDF), (e) H(NMAC) – F2(PVDF), and (f) H(NMAC) – F3(PVDF). I. schematic representation of N(LITFSI) – H(NMAC) interaction, II. schematic representation of O(LITFSI) – H(NMAC) interaction, III. schematic representation of F(LITFSI) – H(NMAC) interaction, IV. schematic representation of F1(PVDF) – H(NMAC) interaction, V. schematic representation of F2(LITFSI) – H(NMAC) interaction, and VI. schematic representation of F3(PVDF) – H(NMAC) interaction

Table S4. Radial Distribution Function and Coordination number of β-PVDF-HFP based eutectogel.

Components	Eutectogel	Distance (Å)	RDF	CN	Distance (Å)	RDF	CN
Li-N (NMAC)	ETG – A	4.85	0.84	0.56	-	-	-
	ETG – B		0.87	0.55			
	ETG – C		0.97	0.55			
	ETG – D		0.95	0.40			
	ETG – E		1.11	0.54			
Li-O (NMAC)	ETG – A	3.25	0.13	0.37	-	-	-
	ETG – B		0.17	0.44			
	ETG – C		0.23	0.47			
	ETG – D		0.15	0.35			
	ETG – E		0.39	0.49			
Li-N (TFSI)	ETG – A	2.55	10.27	0.19	3.65	4.04	1.32
	ETG – B		13.28	0.14		4.42	1.25
	ETG – C		16.75	0.10		6.21	1.26
	ETG – D		23.58	0.09		8.99	1.22
	ETG – E		29.27	0.13		9.27	1.21
Li-O (TFSI)	ETG – A	2.95	1.80	3.09	4.15	2.45	4.79
	ETG – B		3.85	3.02		3.77	4.58
	ETG – C		4.19	2.90		4.35	4.39
	ETG – D		4.42	2.95		6.00	4.44
	ETG – E		6.79	2.87		4.91	4.37
Li-F (TFSI)	ETG – A	1.65	0	1	2.55	0.84	3
	ETG – B		0	1		0.049	3
	ETG – C		0	1		0.03	3
	ETG – D		0	1		0.05	3
	ETG – E		0	1		0.11	3
Li-F (PVDF-F2)	ETG – A	2.75	0.05	0.06	-	-	-
	ETG – B		0.08	0.13			
	ETG – C		0.11	0.22			
	ETG – D		0.10	0.25			
	ETG – E		0.08	0.18			
H-N	ETG – A	3.45	0.38	0.02	9.25	0.93	1.43

(TFSI)	ETG – B		0.41	0.01		1.00	0.92
	ETG – C		0.45	0.01		1.03	0.70
	ETG – D		0.31	0.01		1.02	0.53
	ETG – E		0.63	0.02		0.98	0.51
H-O (TFSI)	ETG – A	3.35	0.42	0.13	6.85	1.00	2.09
	ETG – B		0.38	0.07		1.11	1.37
	ETG – C		0.49	0.06		1.17	1.08
	ETG – D		0.36	0.03		1.18	0.80
	ETG – E		0.59	0.04		1.27	0.83
H-F (TFSI)	ETG – A	6.75	0.95	3.13	-	-	-
	ETG – B		1.05	2.07			
	ETG – C		1.09	1.67			
	ETG – D		1.06	1.21			
	ETG – E		1.18	1.28			
H-F1 (PVDF)	ETG – A	6.75	0.99	1.47	-	-	-
	ETG – B		0.99	1.71			
	ETG – C		0.99	1.80			
	ETG – D		0.99	1.90			
	ETG – E		1.05	1.95			

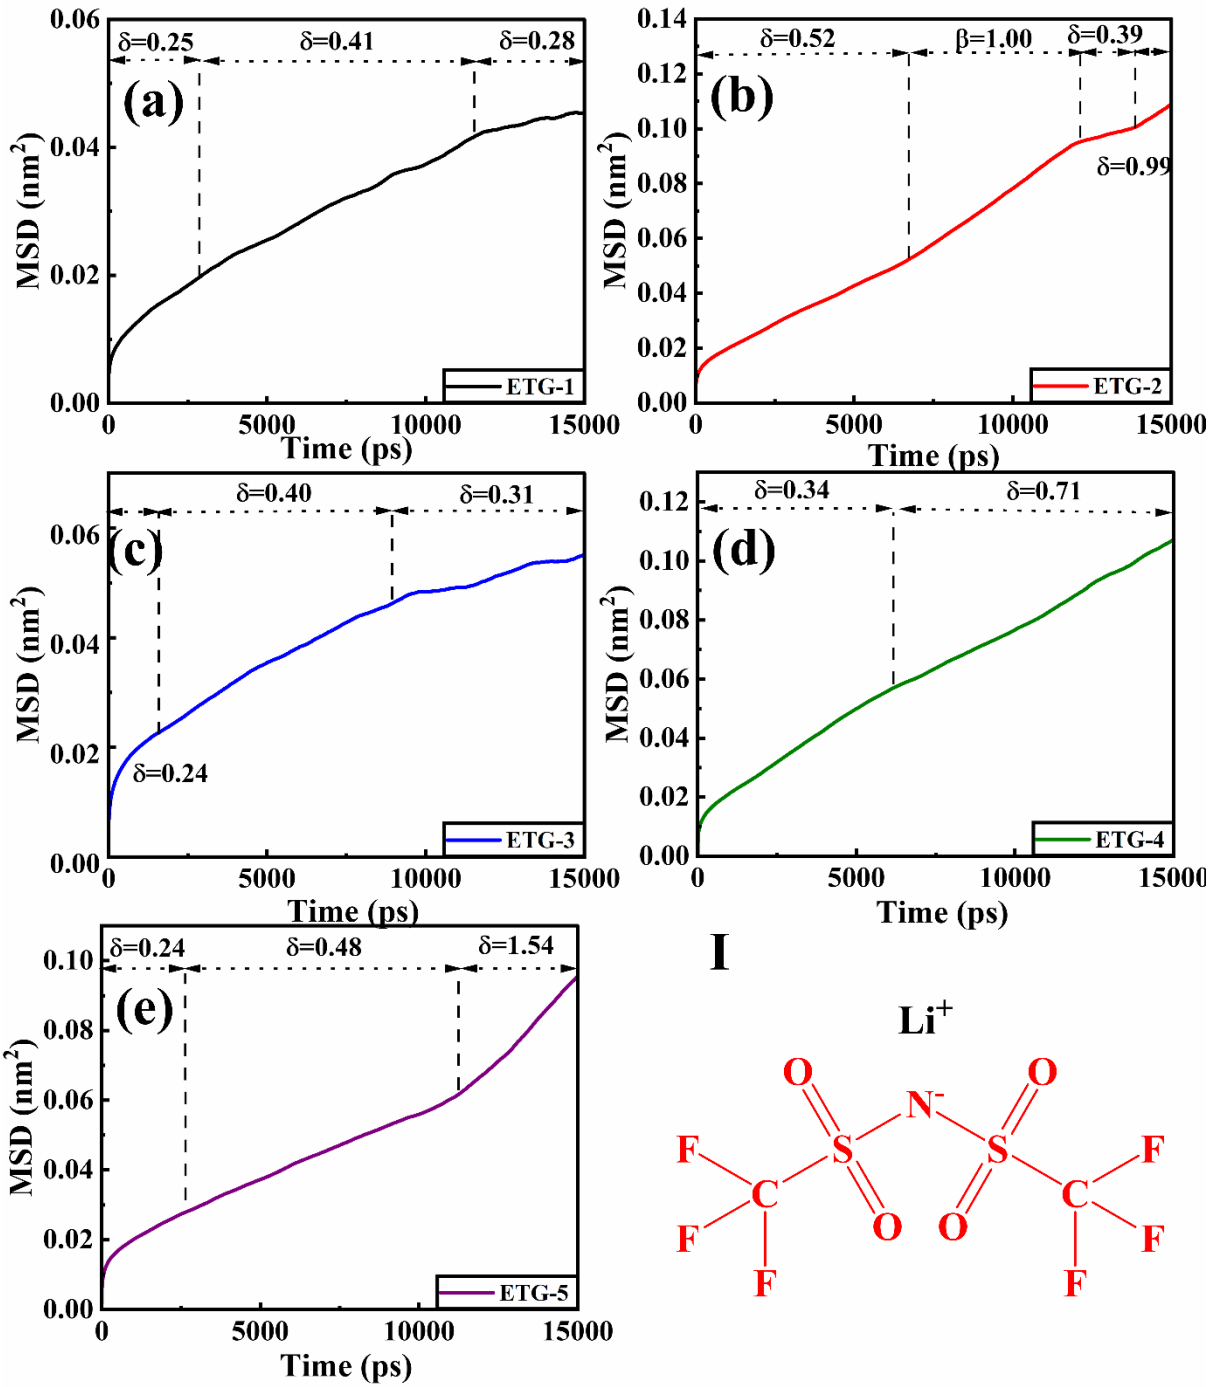


Figure S10. The MSD curve of TFSI ion in LiTFSI in silica gel based eutectogel. (a) ETG – 1, (b) ETG – 2, (c) ETG – 3, (d) ETG – 4, and (e) ETG – 5.

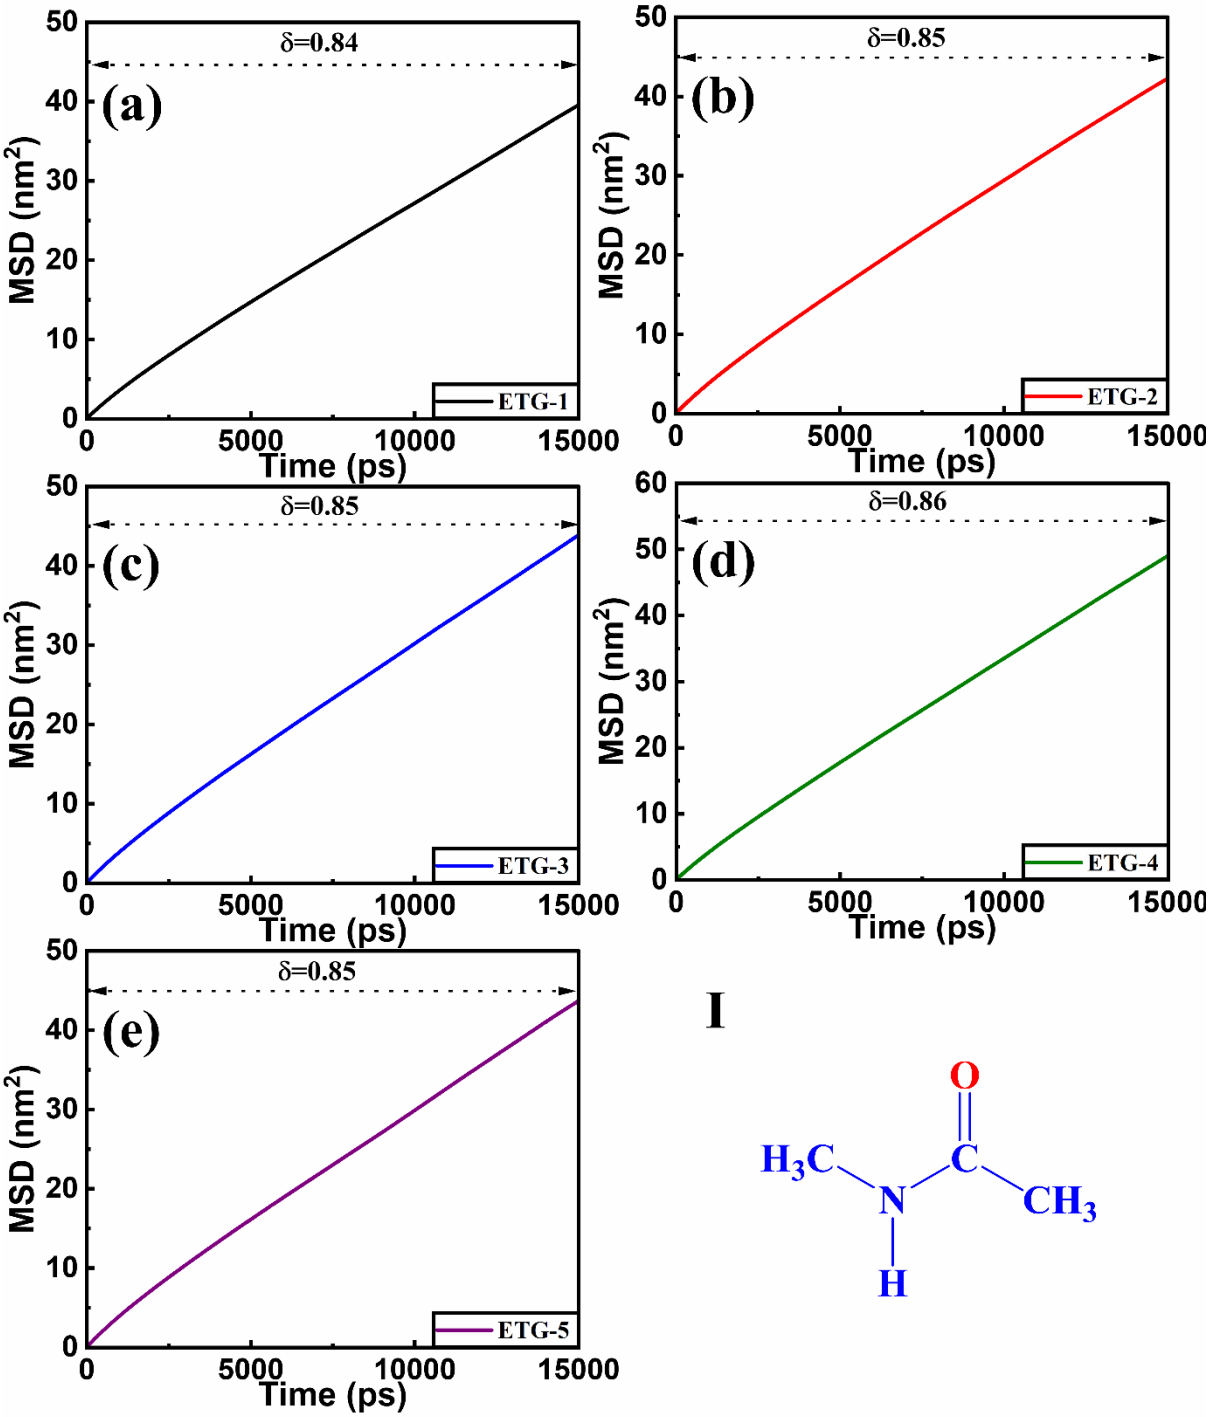


Figure S11. The MSD curve of O in NMAC in silica gel based eutectogel. (a) ETG – 1, (b) ETG – 2, (c) ETG – 3, (d) ETG – 4, and (e) ETG – 5.

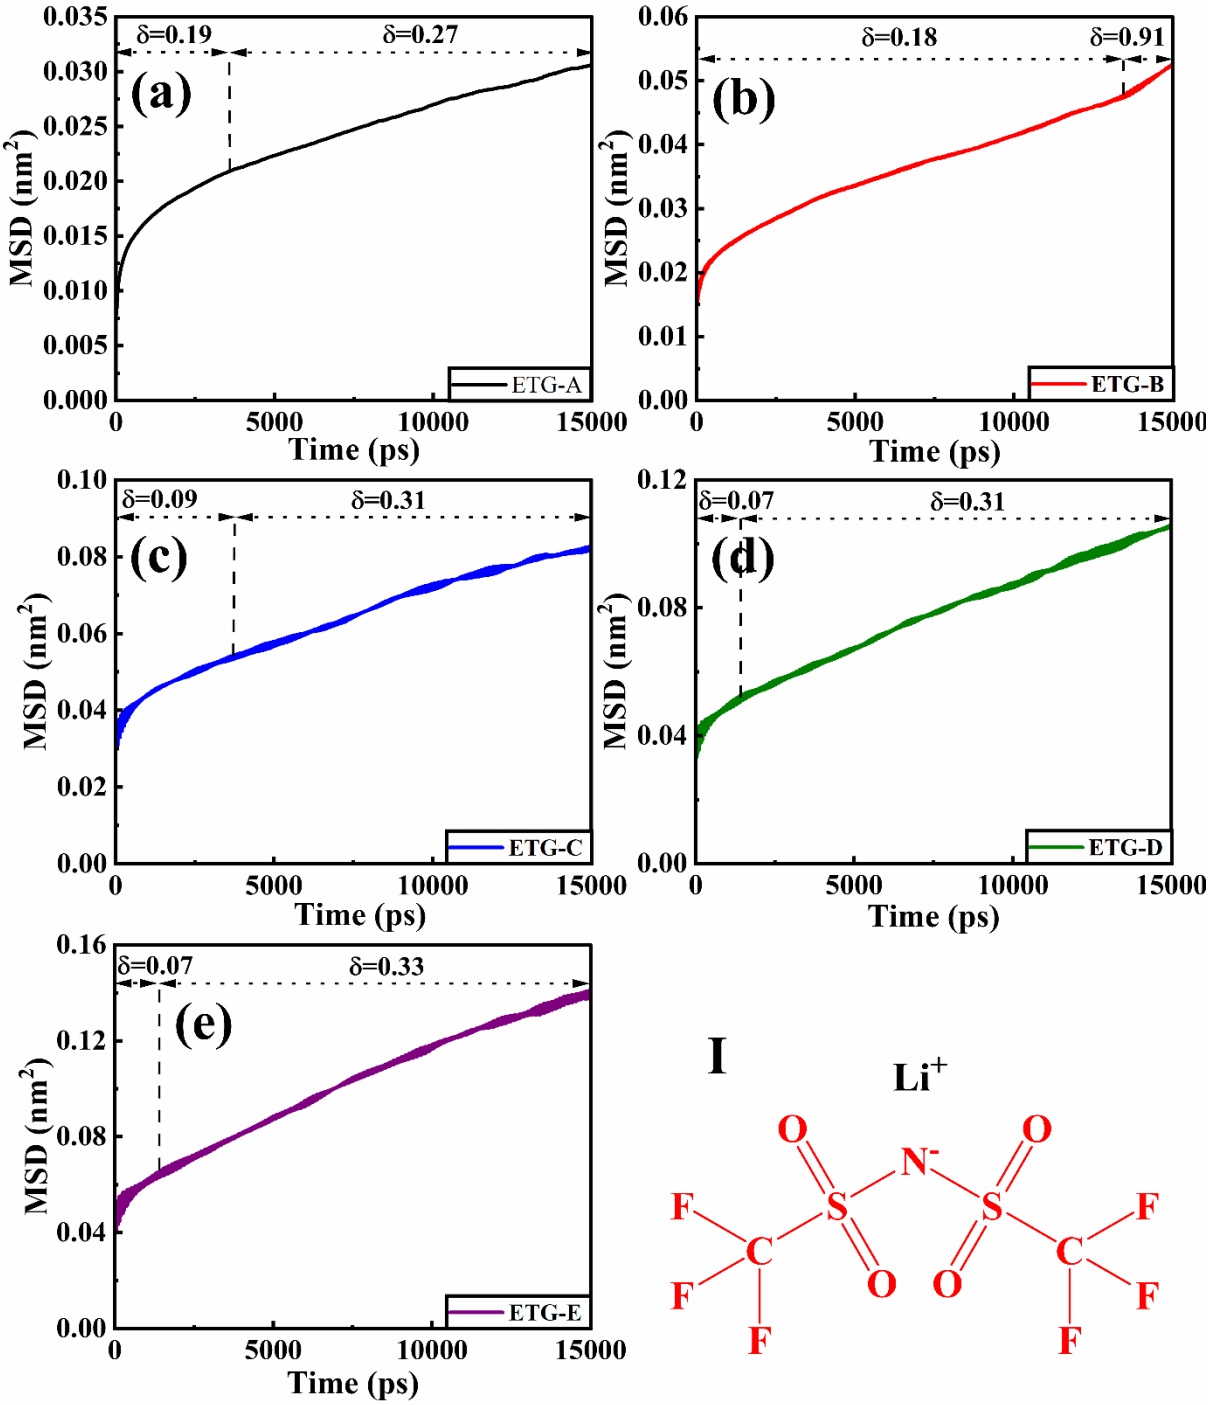


Figure S12. The MSD curve of TFSI ion in LiTFSI in *β*-PVDF-HFP based eutectogel. (a) ETG – A, (b) ETG – B, (c) ETG – C, (d) ETG – D, and (e) ETG – E.

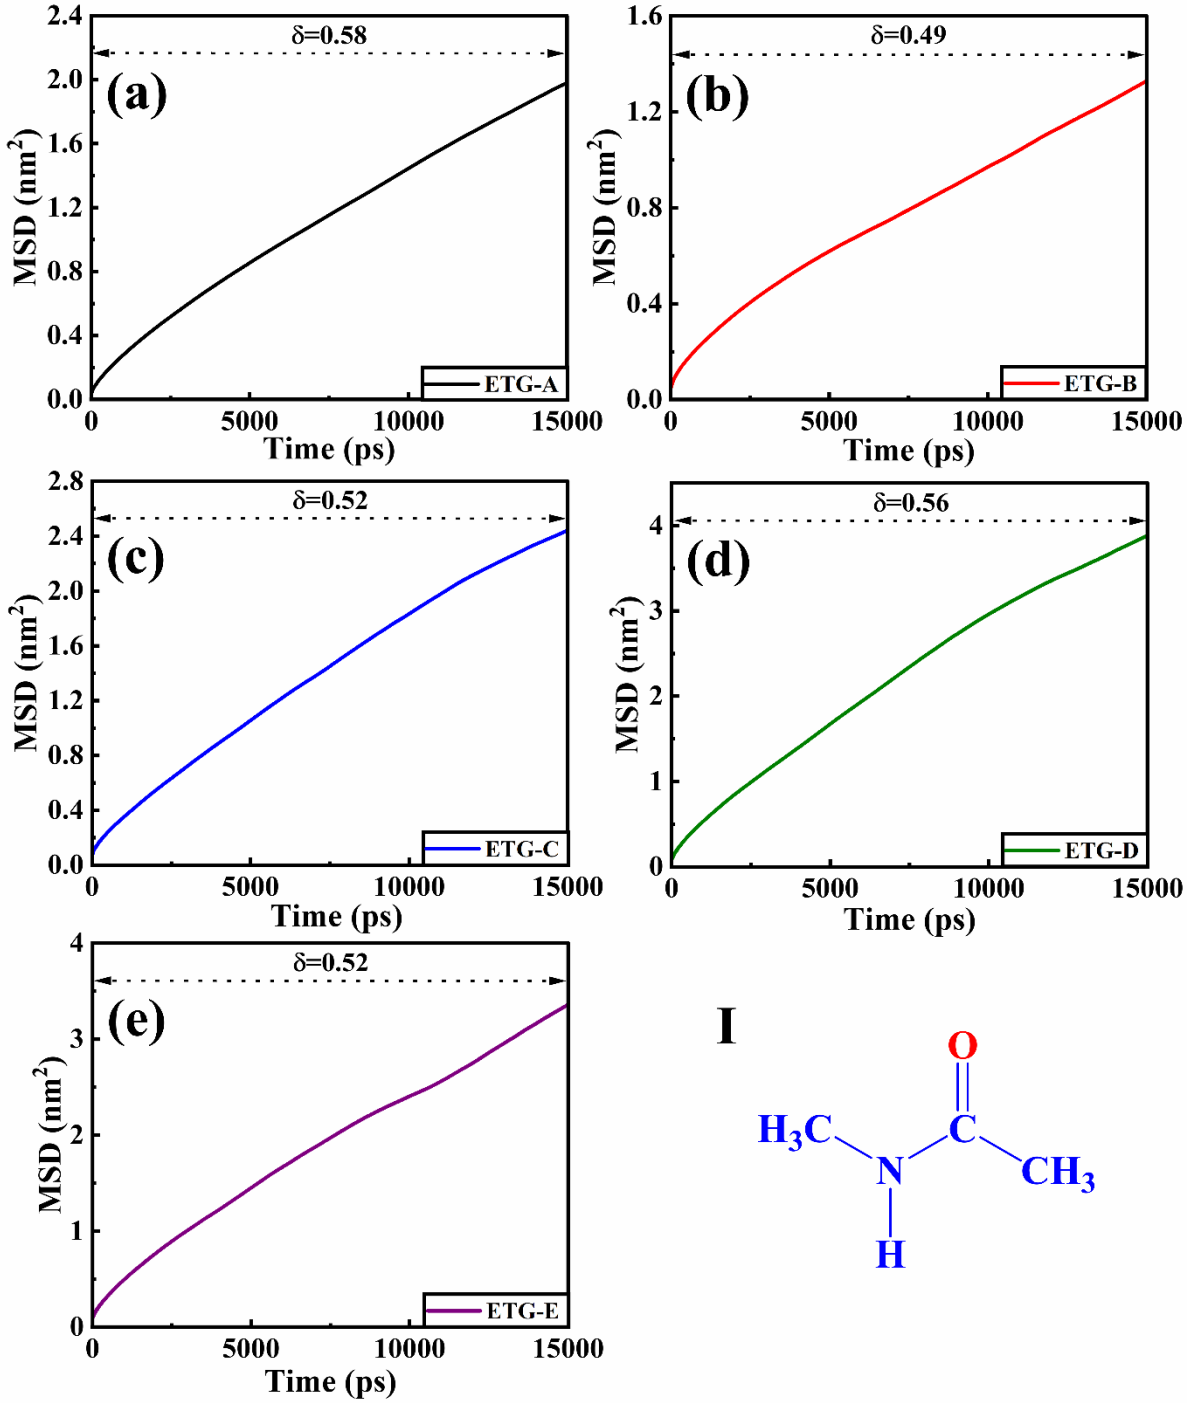


Figure S13. The MSD curve of O in NMAC in *β*-PVDF-HFP based eutectogel. (a) ETG – A, (b) ETG – B, (c) ETG – C, (d) ETG – D, and (e) ETG – E.

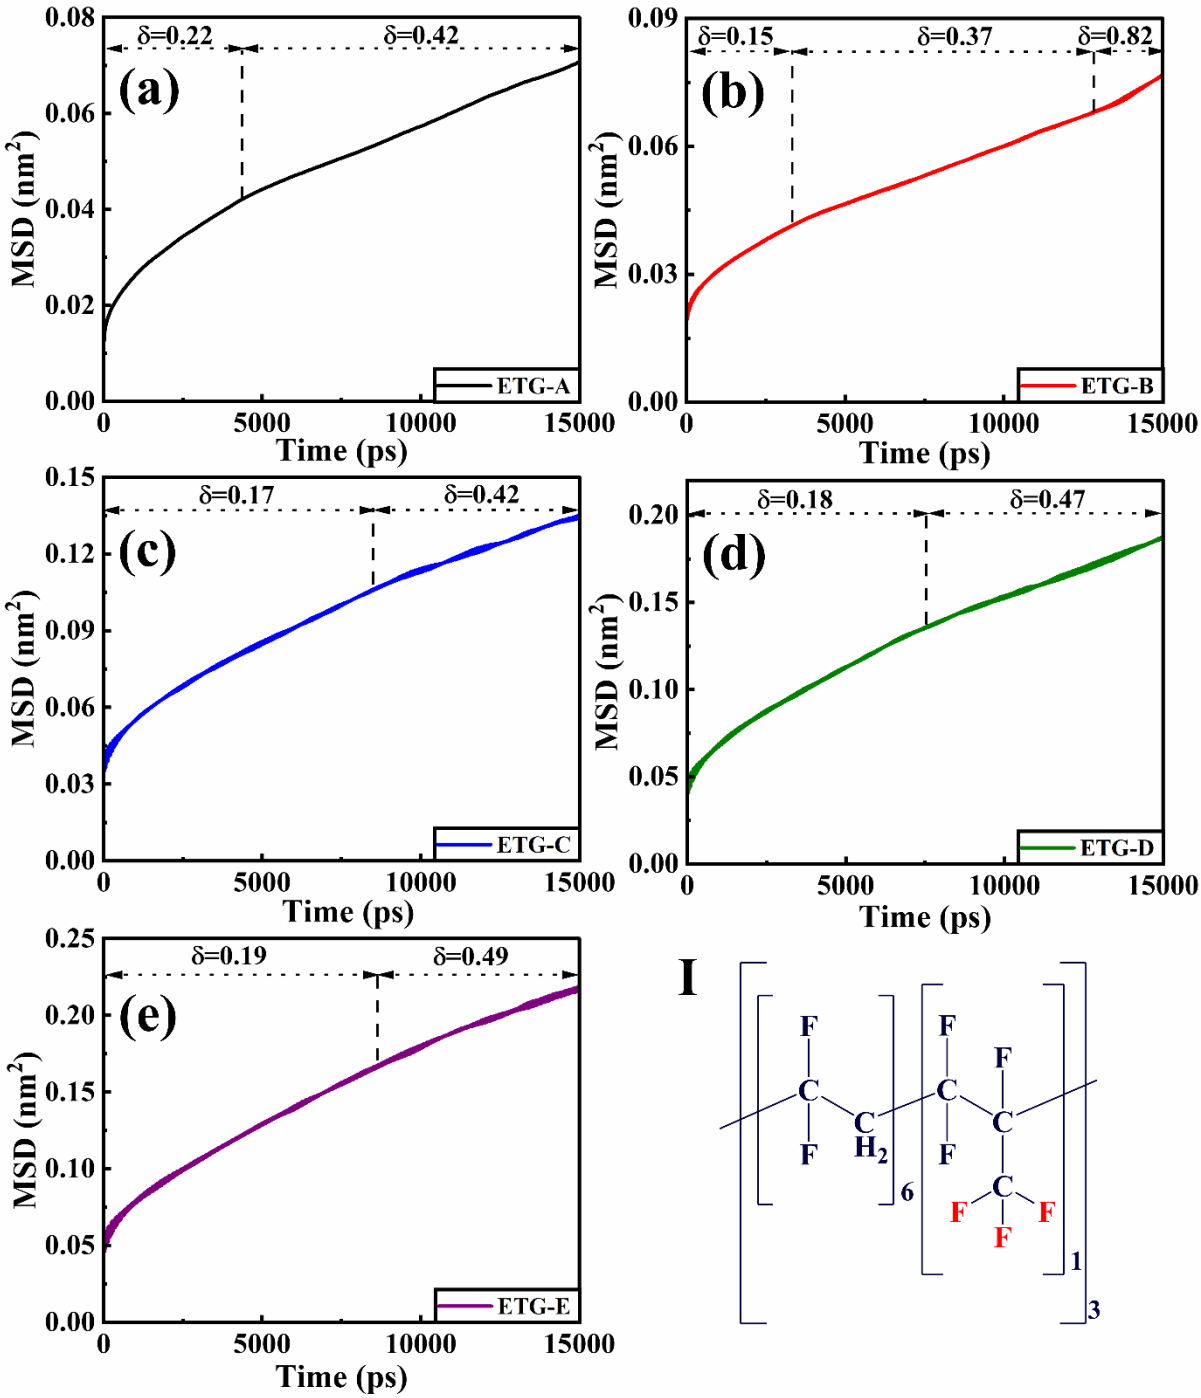


Figure S14. The MSD curve of F3 in *β*-PVDF-HFP in *β*-PVDF-HFP based eutectogel. (a) ETG – A, (b) ETG – B, (c) ETG – C, (d) ETG – D, and (e) ETG – E.

Table S5. MSD value of silica gel based eutectogel.

Component	Eutectogel	Time (ps)	MSD (x10³ nm²)	Time (ps)	MSD (x10³ nm²)	δ	D_Λ ($m^2.s^{-1}$)	Time (ps)	MSD (x10³ nm²)	Time (ps)	MSD (x10³ nm²)	δ	D_Λ ($m^2.s^{-1}$)	Time (ps)	MSD (x10³ nm²)	Time (ps)	MSD (x10³ nm²)	δ	D_Λ ($m^2.s^{-1}$)	Time (ps)	MSD (x10³ nm²)	Time (ps)	MSD (x10³ nm²)	δ	D_Λ (m^2/s)
LiTFSI – Li	ETG–1	10	4	2900	20	0.26	-	2900	20	11560	42	0.55	-	11560	42	15000	45	0.32	-	-	-	-	-	-	-
	ETG–2	10	4	7560	48	0.36	-	7560	48	12230	83	1.15	-	12230	83	13750	87	0.42	-	13750	87	15000	96	1.10	1.17×10^{-12}
	ETG–3	10	4	8850	35	0.31	-	8850	35	15000	43	0.37	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–4	10	4	6090	46	0.37	-	6090	46	15000	94	0.79	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–5	10	4	11520	52	0.65	-	11520	52	15000	84	1.80	-	-	-	-	-	-	-	-	-	-	-	-	-
LiTFSI–N	ETG–1	10	7	1730	16	0.17	-	1730	16	11530	42	0.51	-	11530	42	15000	45	0.32	-	-	-	-	-	-	-
	ETG–2	10	4	7060	45	0.35	-	7060	45	12190	85	1.15	-	12190	85	13690	89	0.42	-	13690	89	15000	98	1.07	1.16×10^{-12}
	ETG–3	10	4	3800	22	0.27	-	3800	22	8580	35	0.56	-	8580	35	15000	43	0.38	-	-	-	-	-	-	-
	ETG–4	10	4	6380	48	0.37	-	6380	48	15000	95	0.79	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–5	10	4	11110	49	0.34	-	11110	49	15000	83	1.73	-	-	-	-	-	-	-	-	-	-	-	-	-
LiTFSI – O	ETG–1	10	6	920	15	0.21	-	920	15	11830	48	0.45	-	11830	48	15000	52	0.29	-	-	-	-	-	-	-
	ETG–2	10	6	7230	50	0.33	-	7230	50	12170	90	1.11	-	12170	90	13740	94	0.41	-	13740	94	15000	103	1.03	1.18×10^{-12}
	ETG–3	10	6	3760	26	0.25	-	3760	26	8850	41	0.53	-	8850	41	15000	50	0.39	-	-	-	-	-	-	-

	ETG–4	10	3	4930	44	0.46	-	4930	44	15000	102	0.75	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–5	10	6	11480	58	0.33	-	11480	58	15000	90	1.65	-	-	-	-	-	-	-	-	-	-	-	-	-
LiTFSI – F	ETG–1	10	9	2420	36	0.26	-	2420	36	11470	64	0.37	-	11470	64	15000	69	0.26	-	-	-	-	-	-	-
	ETG–2	10	5	6900	64	0.38	-	6900	64	11920	105	0.91	-	11920	105	13870	112	0.39	-	13870	112	15000	121	0.95	1.28×10^{-12}
	ETG–3	10	8	700	27	0.27	-	700	27	9040	57	0.30	-	9040	57	15000	67	0.29	-	-	-	-	-	-	-
	ETG–4	10	9	6100	67	0.32	-	6100	67	15000	119	0.64	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–5	10	9	1540	32	0.26	-	1540	32	11140	73	0.41	-	11140	73	15000	108	1.33	-	-	-	-	-	-	-
TFSI	ETG–1	10	7	1400	23	0.25	-	1400	23	11580	53	0.40	-	11580	53	15000	57	0.28	-	-	-	-	-	-	-
	ETG–2	10	2	6740	52	0.52	-	6740	52	12250	96	1.01	1.31×10^{-12}	12250	96	13750	100	0.39	-	13750	100	15000	109	0.99	1.2×10^{-12}
	ETG–3	10	7	1300	22	0.25	-	1300	22	9350	48	0.40	-	9350	48	15000	55	0.31	-	-	-	-	-	-	-
	ETG–4	10	7	6100	57	0.34	-	6100	57	15000	107	0.71	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–5	10	7	1130	21	0.24	-	1130	21	11470	63	0.48	-	11470	63	15000	96	1.54	-	-	-	-	-	-	-
NMAC – O	ETG–1	10	84	15000	39,560	0.84	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–2	10	86	15000	42,276	0.85	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–3	10	88	15000	43,893	0.85	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–4	10	91	15000	49,063	0.86	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–5	10	88	15000	43,703	0.85	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-

Table S6. MSD value of β-PVDF-HFP based eutectogel.

Component	Eutectogel	Time (ps)	MSD (nm^2)	Time (ps)	MSD (nm^2)	δ	D_A ($m^2.s^{-1}$)	Time (ps)	MSD (nm^2)	Time (ps)	MSD (nm^2)	δ	D_A ($m^2.s^{-1}$)	Time (ps)	MSD (nm^2)	Time (ps)	MSD (nm^2)	δ	D_A ($m^2.s^{-1}$)
LiTFSI–Li	ETG–A	20	0.005	4400	0.013	0.17	-	4400	0.013	15000	0.020	0.37	-	-	-	-	-	-	-
	ETG–B	20	0.012	13980	0.037	0.17	-	13980	0.037	15000	0.040	1.00	4.5×10^{-13}	-	-	-	-	-	-
	ETG–C	20	0.030	10790	0.055	0.10	-	10790	0.055	15000	0.063	0.39	-	-	-	-	-	-	-
	ETG–D	20	0.034	15000	0.085	0.19	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–E	20	0.045	7450	0.083	0.10	-	7450	0.083	15000	0.110	0.41	-	-	-	-	-	-	-
LiTFSI–N	ETG–A	20	0.005	6720	0.014	0.18	-	6720	0.014	15000	0.020	0.42	-	-	-	-	-	-	-
	ETG–B	20	0.012	13200	0.034	0.16	-	13200	0.034	15000	0.038	1.03	4.4×10^{-13}	-	-	-	-	-	-
	ETG–C	20	0.030	10840	0.058	0.10	-	10840	0.058	15000	0.064	0.29	-	-	-	-	-	-	-
	ETG–D	20	0.035	6520	0.058	0.09	-	6520	0.058	15000	0.082	0.42	-	-	-	-	-	-	-
	ETG–E	20	0.045	9080	0.087	0.11	-	9080	0.087	15000	0.108	0.43	-	-	-	-	-	-	-
	ETG–	2	0.007	1100	0.011	0.14	-	1100	0.011	15000	0.025	0.2	-	-	-	-	-	-	-

	A	0									9								
	ETG–B	20	0.014	13070	0.042	0.17	-	13070	0.042	15000	0.048	0.95	-	-	-	-	-	-	-
	ETG–C	20	0.032	1380	0.040	0.05	-	1380	0.040	9720	0.065	0.24	-	9720	0.065	15000	0.075	0.34	-
	ETG–D	20	0.038	2090	0.050	0.06	-	2090	0.050	15000	0.102	0.36	-	-	-	-	-	-	-
	ETG–E	20	0.048	7270	0.096	0.12	-	7270	0.096	15000	0.131	0.44	-	-	-	-	-	-	-
LiTFSI–F	ETG–A	20	0.011	1970	0.029	0.21	-	1970	0.029	15000	0.042	0.19	-	-	-	-	-	-	-
	ETG–B	20	0.018	3070	0.041	0.16	-	3070	0.041	13570	0.061	0.27	-	13570	0.061	15000	0.065	0.73	-
	ETG–C	20	0.037	1780	0.058	0.10	-	1780	0.058	15000	0.098	0.24	-	-	-	-	-	-	-
	ETG–D	20	0.042	1310	0.062	0.09	-	1310	0.062	15000	0.122	0.28	-	-	-	-	-	-	-
	ETG–E	20	0.053	1590	0.077	0.09	-	1590	0.077	15000	0.165	0.34	-	-	-	-	-	-	-
TFSI	ETG–A	20	0.008	3540	0.021	0.19	-	3540	0.021	15000	0.031	0.27	-	-	-	-	-	-	-
	ETG–B	20	0.015	13350	0.047	0.17	-	13350	0.047	15000	0.052	0.91	-	-	-	-	-	-	-
	ETG–C	20	0.034	3830	0.054	0.09	-	3830	0.054	15000	0.082	0.31	-	-	-	-	-	-	-

	ETG–D	20	0.039	1400	0.051	0.07	-	1400	0.051	15000	0.106	0.30	-	-	-	-	-	-	-
	ETG–E	20	0.049	1400	0.065	0.07	-	1400	0.065	15000	0.141	0.33	-	-	-	-	-	-	-
NMAC–O	ETG–A	20	0.043	15000	1.980	0.58	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–B	20	0.052	15000	1.329	0.49	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–C	20	0.080	15000	2.444	0.52	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–D	20	0.097	15000	3.886	0.56	-	-	-	-	-	-	-	-	-	-	-	-	-
	ETG–E	20	0.104	15000	3.363	0.52	-	-	-	-	-	-	-	-	-	-	-	-	-
NMAC–NMAC–NH	ETG–A	20	0.032	4630	0.781	0.58	-	4630	0.781	15000	1.946	0.78	-	-	-	-	-	-	-
	ETG–B	20	0.041	2070	0.339	0.45	-	2070	0.339	15000	1.293	0.68	-	-	-	-	-	-	-
	ETG–C	20	0.069	9450	1.719	0.52	-	9450	1.719	15000	2.397	0.72	-	-	-	-	-	-	-
	ETG–D	20	0.084	10280	2.963	0.57	-	10280	2.963	15000	3.827	0.68	-	-	-	-	-	-	-
	ETG–E	20	0.091	8530	2.146	0.52	-	8530	2.146	11180	2.574	0.67	-	11180	2.574	15000	3.355	0.90	-
NMAC–NH	ETG–A	20	0.051	15000	1.980	0.55	-	-	-	-	-	-	-	-	-	-	-	-	-

	ETG–B	20	0.061	2520	0.412	0.40	-	2520	0.412	15000	1.324	0.65	-	-	-	-	-	-	-
	ETG–C	20	0.089	11150	1.991	0.49	-	11150	1.991	15000	2.425	0.66	-	-	-	-	-	-	-
	ETG–D	20	0.105	9820	2.889	0.54	-	9820	2.889	15000	3.852	0.68	-	-	-	-	-	-	-
	ETG–E	20	0.113	8630	2.199	0.49	-	8630	2.199	10630	2.515	0.64	-	10630	2.515	15000	3.402	0.88	-
PVDF–F1	ETG–A	20	0.011	4360	0.037	0.23	-	4360	0.037	15000	0.060	0.40	-	-	-	-	-	-	-
	ETG–B	20	0.017	12960	0.058	0.19	-	12960	0.058	15000	0.065	0.74	-	-	-	-	-	-	-
	ETG–C	20	0.036	6760	0.086	0.15	-	6760	0.086	15000	0.120	0.41	-	-	-	-	-	-	-
	ETG–D	20	0.043	6780	0.113	0.17	-	6780	0.113	15000	0.162	0.45	-	-	-	-	-	-	-
	ETG–E	20	0.050	11570	0.173	0.19	-	11570	0.173	15000	0.195	0.45	-	-	-	-	-	-	-
PVDF–F2	ETG–A	20	0.010	4060	0.030	0.21	-	4060	0.030	15000	0.051	0.39	-	-	-	-	-	-	-
	ETG–B	20	0.017	13620	0.057	0.19	-	13620	0.057	15000	0.062	0.85	-	-	-	-	-	-	-
	ETG–C	20	0.035	9280	0.092	0.16	-	9280	0.092	15000	0.112	0.40	-	-	-	-	-	-	-
	ETG–D	20	0.042	4640	0.091	0.14	-	4640	0.091	15000	0.152	0.44	-	-	-	-	-	-	-

	ETG–E	20	0.049	4690	0.108	0.14	-	4690	0.108	15000	0.188	0.47	-	-	-	-	-	-	-
PVDF–F3	ETG–A	20	0.013	4490	0.043	0.22	-	4490	0.043	15000	0.071	0.42	-	-	-	-	-	-	-
	ETG–B	20	0.019	3270	0.041	0.15	-	3270	0.041	13310	0.069	0.37	-	13310	0.069	15000	0.077	0.82	-
	ETG–C	20	0.038	8570	0.106	0.17	-	8570	0.106	15000	0.134	0.42	-	-	-	-	-	-	-
	ETG–D	20	0.046	6870	0.130	0.18	-	6870	0.130	15000	0.188	0.47	-	-	-	-	-	-	-
	ETG–E	20	0.053	8570	0.167	0.19	-	8570	0.167	15000	0.219	0.49	-	-	-	-	-	-	-